

# RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

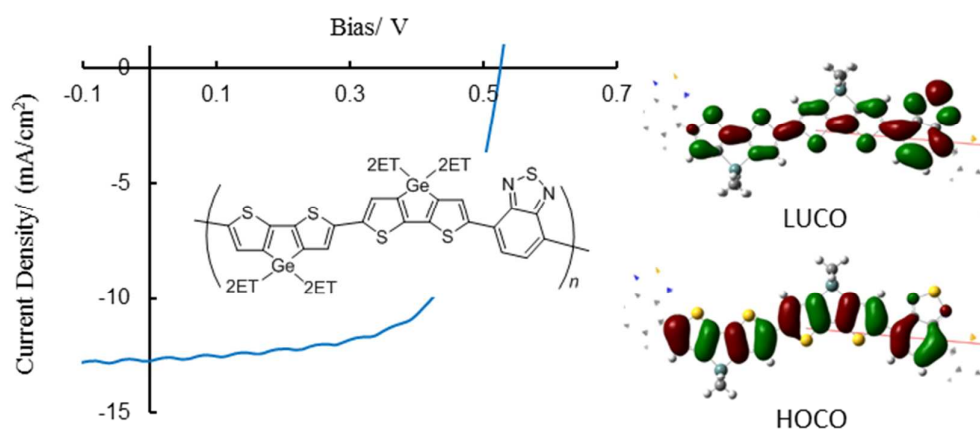

New donor-acceptor  $\pi$ -conjugated polymers composed of alternating bi(dithienogermole) and benzo- or pyridinethiadiazole units were prepared and their potential applications as active materials for bulk heterojunction-type polymer solar cells and thin film transistors were explored.

## ARTICLE

Cite this:  
10.1039/X0XX00000X

DOI:

# Synthesis of conjugated D-A polymers bearing bi(dithienogermole) as a new donor component and their applications to polymer solar cells and transistors

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/X0XX00000X

[www.rsc.org/](http://www.rsc.org/)

Joji Ohshita,<sup>a,\*</sup> Masayuki Miyazaki,<sup>a</sup> Makoto Nakashima,<sup>a</sup> Daiki Tanaka,<sup>a</sup> Yousuke Ooyama,<sup>a</sup> Takuya Sasaki,<sup>b</sup> Yoshihito Kunugi,<sup>b</sup> Yasushi Morihara<sup>c</sup>

New donor-acceptor  $\pi$ -conjugated polymers composed of alternating bi(dithienogermole) (DTG2) and benzo- (BT) or pyridinethiadiazole (PT) units (**pDTG2-BT** or **pDTG2-PT**) were prepared and their optical, electrochemical, photovoltaic, and semiconducting properties were investigated. **pDTG2-BT** showed two absorption maxima at 738 and 686 nm, respectively. Of the two, one at longer wavelength likely due to the aggregated polymer segments was relatively intensified, when the spectrum was measured in film. In contrast, **pDTG2-PT** showed one broad band at 686 nm, which shifted to longer wavelength at 748 nm in film. These results indicate stronger interchain interaction for **pDTG2-BT**. Cyclic voltammograms of the polymer films showed pseudo-reversible profiles and the anodic peak of **pDTG2-BT** appeared at lower potential than that of **pDTG2-PT**, indicating the higher-lying HOMO (Highest Occupied Molecular Orbital) for **pDTG2-BT**. The polymer electronic states were also examined by the quantum chemical calculations on the polymer models. Of those polymers, **pDTG2-BT** exhibited the higher photovoltaic performance. The power conversion efficiency of the cell (ITO/PEDOT:PSS/**pDTG2-BT**:PC<sub>71</sub>BM/LiF/Al) reached 4.30% with  $V_{oc} = 0.53$  V,  $J_{sc} = 12.68$  mA/cm<sup>2</sup>, and FF = 0.64, presumably reflecting the stronger interchain interaction, although **pDTG2-PT** afforded higher  $V_{oc}$ , arising from its lower-lying HOMO. **pDTG2-BT** also exhibited higher performance as a thin film transistor material than **pDTG2-PT**. The performance of the cell with **pDTG2-BT** was also higher than that based on a similar alternating dithienogermole (DTG)-BT polymer, reported previously.

## Introduction

Bulk heterojunction polymer solar cells (BHJ-PSCs) are of current interest because of their potential applications in lightweight and flexible modules and simple fabrication by a solution process. In this system, a blend film consisting of an electron-donating host polymer and an electron-accepting guest material, such as PCBM, is employed as the active layer. In this area, conjugated donor-acceptor (D-A) polymers have been extensively studied as the host polymers.<sup>1</sup> The broad and red-shifted absorptions of D-A polymers make it possible to utilize the wide range of wavelengths in sunlight. High carrier transporting properties of the polymer films are also desired for the host polymers.

On the other hand, dithienosilole (DTS) has been developed as an interesting  $\pi$ -conjugated system. Its highly planar structure and well-known  $\sigma^*-\pi^*$  interaction between silicon  $\sigma^*$ - and bithiophene  $\pi^*$ -orbital leads to extended conjugation.<sup>2</sup>

DTS has been extensively studied as a promising donor component of D-A polymers for BHJ-PSCs,<sup>3</sup> since Yang and co-workers prepared a DTS-benzothiadiazole (BT) alternating copolymer (**pDTS-BT** R = 2-ethylhexyl in Chart 1) and demonstrated its efficient photovoltaic properties.<sup>3a</sup> Recently, we introduced dithienogermole (DTG) as a new donor unit, hypothesizing that the introduction of the heavier germanium atom in place of silicon would provide stronger chain-chain interactions to enhance the carrier mobility in the polymer film (**pDTG-BT** in Chart 1).<sup>4a,b</sup> At nearly the same time, Reynolds et al and Leclerc et al also reported the synthesis of DTG-containing photovoltaic polymers.<sup>4c,d</sup> As expected, some DTG-containing polymers exhibited superior photovoltaic performance in BHJ-PSC compared with the DTS analogues, primarily due to their higher current density.<sup>5</sup> In the course of our studies to further improve the photovoltaic properties of DTG-containing polymers, we demonstrated that introduction

of pyridinodithiadiazole (PT) in place of BT led to the enhanced photovoltaic properties (**pDTG-PT** in Chart 1).<sup>6</sup>

Recently, a bi(dithienosilole)-benzothiadiazole alternating polymer (**pDTS2-BT** R = *n*-octyl) was prepared and it was found that **pDTS2-BT** exhibited improved thin film transistor (TFT) activity than that of **pDTS-BT** (R = *n*-octyl), likely due to the stronger  $\pi$ - $\pi$  stacking, enhancing the film hole-transporting properties (Chart 1).<sup>7</sup> These results were suggestive of a potential of bidithienosilole as the efficient donor unit for the D-A host polymers that can be used as the host polymers in high performance BHJ-PSCs. However, similar approach has not been applied to DTG polymers. In this paper, we report the synthesis of new bi(dithienogermole) (DTG2)-BT and -PT alternating polymers and their optical, electrochemical, photovoltaic, and semiconducting properties.

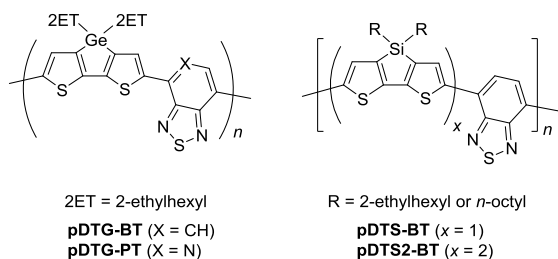


Chart 1. DTG- and DTS-containing D-A polymers.

## Experimental

### General


All reactions were carried out in dry argon. Diethyl ether and chlorobenzene that were used as the reaction solvents were distilled from calcium hydride and stored over activated molecular sieves before use. NMR spectra were recorded on a Varian System 500 spectrometer. UV-Vis spectra were measured with a Hitachi U-2910 spectrometer. Molecular weight of **pDTG2-PT** was determined relative to polystyrene standards by gel permeation chromatography (GPC) using THF as an eluent and serially connected Shodex KF2001 and KF2002 columns. Thermogravimetric analysis (TGA) was carried out on a SII TG/DTA-6200 analyser under a gentle nitrogen flow of 30 mL/min at a heating rate of 10 °C/min. Fabrication and evaluation of BHJ-PSCs were performed as reported in the literature.<sup>6</sup> Bottom contact TFTs were fabricated by spin-coating 0.4 wt% chlorobenzene solutions of the polymers on patterned substrates with integrated array electrodes ( $d = 210$  nm,  $L = 10$   $\mu$ m,  $W = 2$  cm), in a fashion similar to that reported in the literature.<sup>8</sup>

### Preparation of pDTG2-BT and pDTG2-PT

A mixture of **DTG2Sn**<sup>†</sup> (0.244 g, 0.195 mmol), dibromobenzo-thiadiazole (0.057 g, 0.194 mmol), Pd<sub>2</sub>(dba)<sub>3</sub> (3.6 mg, 0.0040 mmol), P(*o*-Tol)<sub>3</sub> (6.0 mg, 0.020 mmol), CuO (15.7 mg, 0.197 mmol), and 15 mL of chlorobenzene was heated to reflux for 5 days. The resulting precipitates were filtered and extracted

with chlorobenzene. To remove the residual palladium and copper, The filtrate and the extract were combined and stirred at 80 °C for 2 h with 30 mL of an aqueous solution of sodium *N,N*-diethyldithiocarbamate trihydrate (10 wt%). The organic layer was separated and washed with water, 3% acetic acid (aq), then water again. After drying the organic layer with anhydrous magnesium sulfate, the solvent was evaporated and the residue was precipitated from ethanol to provide a black solid. The solid was placed in a Soxhlet extractor and washed with hot methanol, ethyl acetate, and hexane, in this order. The resulting solid that was insoluble in those hot solvents was extracted with hot toluene. Polymer **pDTG2-BT** was obtained as a black solid by pouring the toluene extract to hexane (53 mg, 16% yield): m.p. > 300°C, <sup>1</sup>H NMR ( $\delta$  in C<sub>6</sub>D<sub>4</sub>Cl<sub>2</sub>, 500 MHz), 8.59-8.33 (br, 2H), 7.88-7.63 (br, 2H), 7.55-7.39 (br, 2H), 1.74-1.62 (br, 4H), 1.34-1.14 (br, 40H), 0.94-0.811 (br, 24H); <sup>13</sup>C NMR ( $\delta$  in C<sub>6</sub>D<sub>4</sub>Cl<sub>2</sub>, 125 MHz) 37.56-37.06, 36.14-35.47, 30.16-28.90, 23.94-23.12, 15.02-14.23, 11.29-10.99, sp<sup>2</sup> carbon signals could not be observed, likely due to the signal broadening.

Polymer **pDTG2-PT** was obtained as a black solid, in a fashion similar to that above. For Soxhlet extraction, hot benzene was used in place of hot toluene: m.p. > 300°C, <sup>1</sup>H NMR ( $\delta$  in CD<sub>2</sub>Cl<sub>2</sub>, 500 MHz) 8.80-8.50 (br m, 1H), 8.24-8.12 (br m, 1H), 7.28-7.06 (br, 2H), 7.00-6.88 (br, 1H), 1.92-1.86 (br, 4H), 1.46-1.02 (br m, 40H), 1.00-0.74 (br, 24H), <sup>13</sup>C NMR ( $\delta$  in C<sub>6</sub>D<sub>4</sub>Cl<sub>2</sub>, 125 MHz) 37.51-37.10, 36.03-35.66, 29.38-28.87, 23.51-23.20, 21.15-20.77, 14.52-14.26, 11.24-10.90, sp<sup>2</sup> carbon signals could not be observed, likely due to the signal broadening.

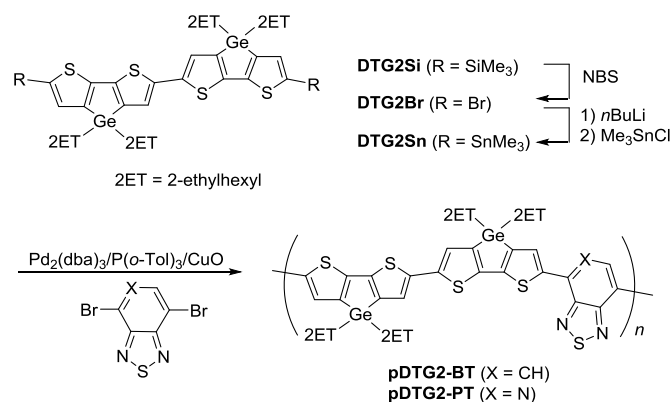

Scheme 1 Synthesis of DTG2-containing polymers.

## Results and discussion

### Polymer synthesis

A DTG2 monomer (**DTG2Sn**) was prepared by bromination of bis(trimethylsilyl)bi(dithienogermole) (**DTG2Si**)<sup>8</sup> with NBS yielding the dibromide (**DTG2Br**), followed by lithiation then stannylation, as presented in Scheme 1. Polymers with alternating DTG2 and BT or PT units were synthesized as black solids by Stille coupling of **DTG2Sn** and dibromobenzo- or

pyridinotriazole, respectively, in refluxing chlorobenzene using Pd<sub>2</sub>(dba)<sub>3</sub>/P(*o*-Tol)<sub>3</sub>/CuO as the catalyst (Scheme 1), similarly to what was previously reported for **pDTG-BT**<sup>4a</sup> and **pDTG-PT**.<sup>6</sup> Table 1 summarizes the polymer properties. **pDTG2-PT** showed good solubility in chloroform, THF, and aromatic solvents, but insoluble in methanol, hexane, and ethyl acetate, e.g. 1.0 g/L in ODCB (*o*-dichlorobenzene). Whereas, **pDTG2-BT** was much less soluble. At room temperature, it was moderately soluble in ODCB (0.32 g/L) and CB (chlorobenzene), but insoluble in chloroform, THF, toluene, hexane, methanol, and ethyl acetate. The polymers exhibited good film forming properties by spin-coating to provide amorphous films. No XRD peaks were detected for the films, even after annealing and the AFM images showed smooth surface (Figure S-2 and S-3<sup>†</sup>).

The molecular weight of **pDTG2-PT** was determined by GPC to be  $M_n = 13,000$  with polydispersity ( $M_w/M_n$ ) of 1.2, relative to polystyrene standards. How the GPC molecular weights of the present polymers correlate the real values is unclear. However, for a similar DTS polymer, the GPC data showed good agreement with that determined by the NMR spectroscopy.<sup>8</sup> GPC analysis of **pDTG2-BT** could not be performed because of its low solubility. Our previous work indicated that **pDTG-PT** was less soluble than **pDTG-BT**, because of the higher polarity of PT than BT. In contrast to this, **pDTG2-BT** showed lower solubility than that of **pDTG2-PT**. This seems to be indicative of the higher molecular weight of **pDTG2-BT** than that of **pDTG2-PT**. The polymer structures were verified by <sup>1</sup>H and <sup>13</sup>C NMR spectra. Although the spectra revealed only broad signals, the proton integration ratios sufficiently agreed with the theoretical values (Fig. S-1<sup>†</sup>). Some unidentified signals with low intensities were also seen in the spectra. No stannyl end groups were detected in the spectra.

Table 1. Properties of DTG2- and DTG-containing polymers

Polym	$M_n$ ( $M_w/M_n$ )	UV-Vis Abs $\lambda_{max}$ /nm <sup>a</sup>		TG $T_d^5/^\circ\text{C}^b$
		in CB	as film	
<b>pDTG2-BT</b>		<i>686, 738</i>	<i>688, 741</i>	402
<b>pDTG2-PT</b>	13,000 (1.2)	686	748	367
<b>pDTG-BT</b> <sup>c</sup>	15,000 (1.7)	651, 760 <sup>d</sup>	687, 760	401
<b>pDTG-PT</b> <sup>e</sup>	6,200 (1.5)	745	739	405

<sup>a</sup>Data for minor bands and shoulders are given in *italic*. <sup>b</sup>In nitrogen. <sup>c</sup>See reference 4a. <sup>d</sup>In chloroform. <sup>e</sup>See reference 6.

### Optical, electrochemical, and thermal properties

UV-Vis absorption spectra of polymers **pDTG2-BT** and **pDTG2-PT** were measured in CB solutions and as spin-coated films on quartz plates, revealing broad absorption bands, as depicted in Figure 1. **pDTG2-BT** showed two absorption maxima. The major band at 738 nm reflects the interchain interactions in the aggregated polymer chains. The interactions enhance the polymer planarity and/or through space electronic  $\pi$ - $\pi$  interactions to lead to a low-energy shift of the band. On the other hand, the minor one at higher energy ( $\lambda_{max} = 686$  nm) is likely due to the aggregation-free polymer segments. Similar UV-Vis spectra have been previously reported for **pDTS-BT**<sup>3a</sup>

and **pDTG-BT**<sup>4a</sup>, and the appearance of red-shifted bands by the formation of aggregates by lowering the measurement temperature and evaporation of the solvent have been well studied for conjugated polymers.<sup>9</sup> In fact, the lower-energy band of **pDTG2-BT** was relatively intensified and the higher-energy band was weakened, when measured as a film. This is similar to the UV-Vis absorption properties of **pDTG-BT**, which reveals a shoulder peak at lower energy in addition to the major peak and the shoulder peak is intensified in film (Table 1). However, the aggregated band of **pDTG-BT** was observed only as a shoulder in the solution phase, indicating the stronger interchain interaction for **pDTG2-BT**. The aggregation-free band of **pDTG2-BT** was red-shifted from that of **pDTG-BT**. This contrasts the results of computer simulation on polymer models in the gas phase, which shows similar electronic states for these polymers (*vide infra*).

As can be seen in Figure 1, **pDTG2-PT** showed a broad single absorption peak at nearly the same energy as the minor peak of **pDTG2-BT**. This is also in marked contrast to that computation on their models provided a smaller band gap for the PT-containing model (*vide infra*). Broadening of the absorption band of **pDTG2-PT** may be understood again by the existence of aggregated segments. However, it is likely that the interaction is not as strong as that in **pDTG2-BT** and the aggregated band is not clearly seen. Measuring the absorption spectrum of **pDTG2-PT** as a film further broadened the band and moved the maximum to lower energy, indicating enhanced interchain interactions in film. Polymer **pDTG-PT** showed the absorption band at lower energy by approximately 60 nm in solution than that of **pDTG2-PT** with no evident spectral changes depending on the states (in solution or film). This is likely due to that the efficient interchain interactions took place for **pDTG-PT** even in the solution phase, arising from the highly polar pyridine units. However, for **pDTG2-PT**, the lower incorporation ratio of pyridine units in the polymer backbone leads to the relatively weak interaction in solutions and the considerable interactions are involved only in film. It was also demonstrated that **pDTG-PT** showed the major band at lower energy by approximately 100 nm than that of **pDTG-BT**, although **pDTG-PT** had a smaller molecular weight, presumably due to the more polar PT structure which enhances the interchain interaction. However, in the present study, **pDTG2-BT** exhibited stronger interchain interaction than **pDTG2-PT**. Although we do not have any direct evidences, it is not unusual to assume that the stronger interaction of **pDTG2-BT** as compared to **pDTG2-PT** would be due to the higher molecular weight.

We also measured cyclic voltammograms (CVs) of the polymer films containing tetrabutylammonium perchlorate (TBAP) as a supporting electrolyte, as shown in Figure 2. They showed pseudo-reversible anodic behaviors and **pDTG2-PT** showed the oxidation onset at higher potential, reflecting the stronger electron-withdrawing properties of PT as compared to BT, similarly to that the CV of **pDTG-PT** revealed a lower oxidation potential than that of **pDTG-BT**.<sup>5</sup>



Thermal stability of the polymers was investigated by TGA in nitrogen and the temperatures of 5% weight loss ( $T_d^5$ ) were noted as listed in Table 1. Thermal decomposition of the polymers occurred around 400 °C, showing good thermal stability of the present polymers. The data are comparable to those of **pDTG-BT**<sup>4a</sup> and **pDTG-PT**,<sup>6</sup> although  $T_d^5$  value of **pDTG2-PT** was slightly lower than others.

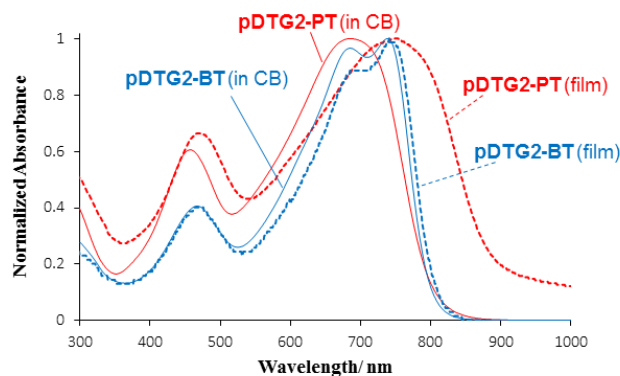


Fig. 1 UV-Vis absorption spectra of DTG2-containing polymers.

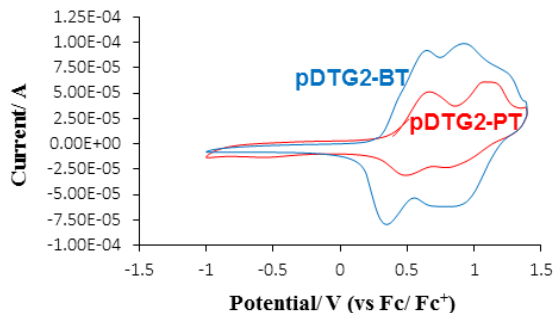


Fig. 2 CVs of films of DTG2-polymers containing TBAP as supporting electrolyte (polymer : TBAP = 1 : 10 in weight).

### Quantum chemical calculations

To understand the differences of electronic properties between **pDTG-BT** and **pDTG2-BT**, we carried out crystal orbital (CO) calculations on the polymer models simplified by the use of methyl groups as the substituents on the germanium atoms (**pDTG-BT0** and **pDTG2-BT0**) at the level of B3LYP/6-31G(d) on the Gaussian 09 program. Optimized geometries of the unit cells, and HOCO and LUCO (highest occupied and lowest unoccupied CO) profiles of the polymers are depicted in Figure 3. For these polymers, several stable conformations may exist. With respect to the orientation of the sulphur atoms, *anti*-conformation for the DTG-BT and DTG-DTG bonding seemed to be favourable as compared to the *syn*-conformation, because of the steric repulsion between the C-H bonds of DTG and BT units for the *syn*-conformation. However, the *syn-syn-anti-anti*- and *syn-anti-anti*-isomers presented in Figure 3 were found to be slightly more stable than the all-*anti* isomers for **pDTG-BT0** and **pDTG2-BT0**, respectively. The polymer

optimized geometries show high planarity with the interplane angles less than 1°.

Table 2. HOCO and LUCO energy levels and band gaps for model polymers, derived from DFT calculations at B3LYP/6-31G(d)

polym	HOCO /eV	LUCO /eV	band gap/ eV
<b>pDTG-BT0</b>	-4.43	-2.96	1.47
<b>pDTG2-BT0</b>	-4.33	-2.81	1.52
<b>pDTG2-PT0</b>	-4.42	-3.03	1.38

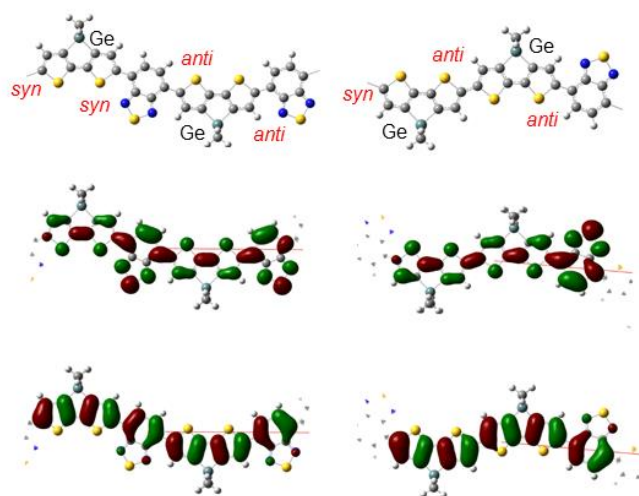


Fig. 3 Optimized geometries (top), LUCO (middle) and HOCO (bottom) profiles of unit cells of model polymers **pDTG-BT0** (left) and **pDTG2-BT0** (right) with methyl groups on Ge atoms, derived from DFT calculations at B3LYP/6-31G(d).

The HOCO and LUCO energy levels and the band gaps derived from the calculations are summarized in Table 2. Reasonably, both the HOCO and LUCO are destabilized as increasing the incorporation ratio of the electron rich DTG units in the polymer chain from DTG/BT = 1/1 in **pDTG-BT0** to 2/1 in **pDTG2-BT0**. The band gap energy of **pDTG-BT0** was calculated to be slightly smaller than that of **pDTG2-BT0**, disagreeing with the UV-Vis absorption data, i.e. the aggregation-free band of **pDTG-BT** appeared at higher energy by 35 nm than that of **pDTG2-BT** (Table 1). This may be due to the existence of large 2-ethylhexyl substituents on the germanium atoms in **pDTG2-BT**. The substituents may cover the DTG2 plane to restrict the rotation around the DTG-DTG bonds, enhancing the planarity. Whereas, the DTG-BT bonds seem to be less affected by the substituents, thus being able to more freely rotate. Consequently, **pDTG2-BT** would possess higher planarity in the polymer chain. A model of **pDTG2-PT** (**pDTG2-PT0**) was also calculated, again revealing high planarity of the  $\pi$ -conjugated system (Figure S-4<sup>†</sup>). The lower HOCO and LUCO energy levels and the smaller band gap than those of **pDTG2-BT0** as listed in Table 2 arise from the stronger D-A interaction between DTG2 and PT than that

between DTG2 and BT. However, in the real system, the aggregation-free bands of **pDTG2-BT** and **pDTG2-PT** appeared at nearly the same wavelength, presumably due to the larger molecular weight of **pDTG2-BT**, which balances the stronger D-A interaction in **pDTG2-PT**.

### Photovoltaic and semiconducting properties

BHJ-PSCs using the present polymers as the host materials and PC<sub>71</sub>BM as the guest were fabricated with the structure of ITO (150 nm)/PEDOT: PSS (30 nm)/ **pDTG2**-polymer: PC<sub>71</sub>BM (1:2.5 wt ratio, ca. 80 nm)/ LiF (0.5 nm)/Al (80 nm) and an active area of 0.25 cm<sup>2</sup>, in a fashion similar to what was reported previously.<sup>6</sup> As expected, the cells showed clear photovoltaic properties (Figure 4). Annealing the active layers as well as the devices did not affect the results. The photovoltaic parameters of the cells are listed in Table 3 in comparison with those of **pDTG-BT**<sup>4a</sup> and **pDTG-PT**,<sup>6</sup> reported previously. Notably, the cell with **pDTG2-BT** exhibited higher performance than the one with **pDTG2-PT**. Although the open-circuit voltage ( $V_{oc}$ ) of the **pDTG2-BT**-based cell is lower than that based on **pDTG2-PT**, due to the higher lying HOMO (Highest Occupied Molecular Orbital) of **pDTG2-BT**, its larger current density efficiently raises the power conversion efficiency (PCE). It is most likely that the higher degree of interchain interaction of **pDTG2-BT** is responsible for the higher current density. The PCE of **pDTG2-BT**-based device is also higher than the similar devices with **pDTG-BT** (PCE = 1.21%)<sup>4a</sup> and **pDTG-PT** (PCE = 2.92%),<sup>6</sup> reported previously by us.

Spin-coated films of the present polymers were investigated as p-type semiconducting materials (Figure S-5<sup>†</sup>) and the data are also listed in Table 3. Polymer **pDTG2-BT** shows higher mobility than that of **pDTG2-PT**, in accordance with the higher  $J_{sc}$  for **pDTG2-BT**-based PSC. It is also noted that the mobility of **pDTG2-BT** is approximately 10 times higher than that of **pDTS2-BT** ( $\mu_{FET} = 3 \times 10^{-4}$  cm<sup>2</sup>V<sup>-1</sup>s<sup>-1</sup>), reported previously.<sup>7</sup> This may be due to the film morphology. However, no evident differences were observed in the AFM images of the films (Figure S-3), thus being attributable primarily to the enhanced polymer interchain interaction in the film for **pDTG2-BT**.

Table 3. PSC and TFT parameters based on DTG2-polymers

Polym	PSC			TFT		
	$J_{sc}/\text{mAcm}^{-1}$	$V_{oc}/\text{V}$	FF	PCE/%	$\mu_{FET}/\text{cm}^2\text{V}^{-1}\text{s}^{-1}$	$I_{on}/I_{off}$
<b>pDTG2-BT</b>	12.69	0.53	0.64	4.30	$3.8 \times 10^{-3}$	$10^5$
<b>pDTG2-PT</b>	3.66	0.60	0.43	0.94	$1.4 \times 10^{-4}$	$10^4$

### Conclusions

We successfully prepared two D-A polymers containing DTG2 as the donor and applied them as BHJ-PSC and TFT materials. Although quantum chemical calculations on their models showed that DTG2-polymers should have similar electronic structures to those of the corresponding DTG-polymers with slightly larger band gaps, the **pDTG2-BT**-based PSC exhibited

remarkably higher performance than those of **pDTG-BT**-based one, reported previously.<sup>4a</sup> It is also noteworthy that **pDTG2-BT** showed superior performance as the active material for TFT to **pDTS2-BT**, indicating the potential of DTG2. This is likely due to high planarity of the DTG2 unit. In addition, high solubility of the DTG2-containing polymers arising from four solubilizing groups on the germanium atoms seems to improve the film-forming properties as compared to DTG-containing ones, thus being responsible for the enhanced performance. The results demonstrated in this paper clearly shows the potential of DTG2 as the donor component of D-A polymers, providing opportunities to design new functional materials.

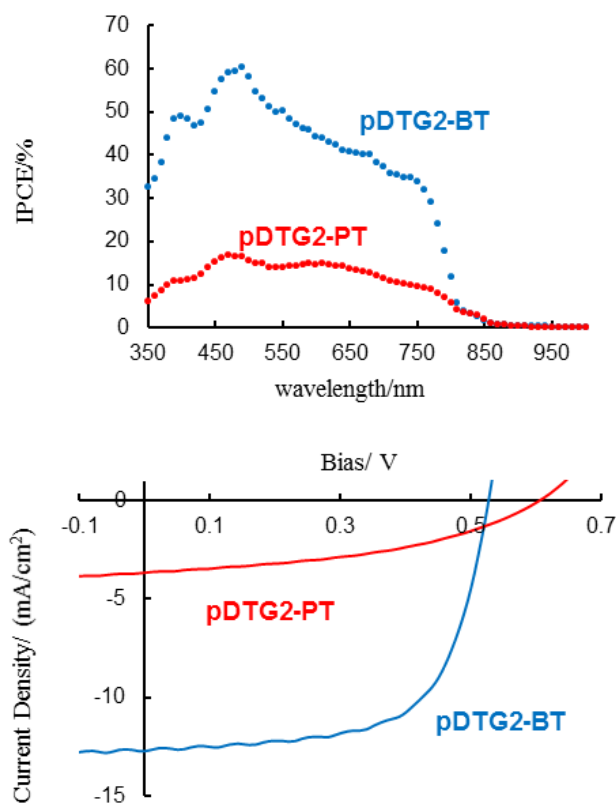


Fig. 4 IPCE (incident photon-to-current conversion efficiency) (top) and  $J$ - $V$  (bottom) characteristics of BHJ-PSCs based on DTG2-containing polymers.

### Acknowledgements

This work was supported by a Grant-in-Aid for Scientific Research (B) (No.26288094) from the Ministry of Education, Culture, Sports, Science and Technology, Japan. We also thank Prof. Kazuyoshi Tanaka and Prof. Hiroyuki Fueno for the assistance in crystal orbital calculations.

### Notes and references

<sup>a</sup> Department of Applied Chemistry, Graduate School of Engineering, Hiroshima University, Higashi-Hiroshima 739-8527, Japan.

## ARTICLE

<sup>b</sup> Department of Applied Chemistry, Faculty of Engineering, Tokai University, 4-1-1 Kitakaname, Hiratsuka 259-1292, Japan.

<sup>c</sup> Synthesis Research Laboratory, Kurashiki Research Center, Kuraray Co., Ltd., 2045-1 Sakazu, Kurashiki 710-0801, Japan.

† Electronic Supplementary Information (ESI) available: [Experimental procedure for monomer preparation, <sup>1</sup>H NMR spectra of **pDTG2-BT** and **pDTG2-PT**, XRD patterns and AFM images of the polymer films optimized geometry, and LUCO and HOCO profiles of model polymer **pDTG2-PT0**, and response curves of TFTs with **pDTG2-BT** and **pDTG2-PT**]. See DOI: 10.1039/b000000x/

- 1 For a recent review, see Y.-F. Lee, *Acc. Chem. Res.*, 2012, **45**, 723.
- 2 (a) J. Ohshita, *Macromol. Chem. Phys.*, 2001, **210**, 1360; (b) J. Ohshita, M. Nodono, T. Watanabe, Y. Ueno, A. Kunai, Y. Harima, K. Yamashita and M. Ishikawa, *J. Organomet. Chem.*, 1998, **553**, 487; (c) J. Ohshita, M. Nodono, H. Kai, T. Watanabe, A. Kunai, K. Komaguchi, M. Shiotani, A. Adachi, K. Okita, Y. Harima, K. Yamashita and M. Ishikawa, *Organometallics*, 1999, **18**, 1453.
- 3 (a) J. Hou, H.-Y. Chen, S. Zhang, G. Li and Y. Yang, *J. Am. Chem. Soc.*, 2008, **130**, 16144; (b) L. Huo, H.-Y. Chen, J. Hou, T. L. Chen and Y. Yang, *Chem. Commun.*, 2009, 5570; (c) M. Zhang, X. Guo, Z.-G. Zhang and Y. Li, *Polymer*, 2001, **52**, 5464; (d) J. Peet, L. Wen, P. Byrne, S. Rodman, K. Forberich, Y. Shao, N. Drolet and R. Gaudiana, *Appl. Phys. Lett.*, 2011, **98**, 043301; (e) S. Subramaniyan, H. Xin, F. S. Kim, S. Shoaee, J. R. Durrant and S. A. Jenekhe, *Adv. Energy. Mater.*, 2011, **1**, 854; (f) S. Subramaniyan, H. Xin, F. S. Kim and S. A. Jenekhe, *Macromolecules*, 2011, **44**, 6245; (g) T.-Y. Chu, J. Lu, S. Beaupre, Y. Zhang, J.-R. Pouliot, S. Wakim, J. Zhou, M. Leclerc, Z. Li, J. Ding and Y. Tao, *J. Am. Chem. Soc.*, 2011, **133**, 4250; (h) Y. Ie, J. Huang, Y. Uetani, M. Karakawa and Y. Aso, *Macromolecules*, 2012, **45**, 4564; (i) X. Guo, N. Zhou, S. Lou, J. W. Hennek, R. P. Ortiz, M. R. Butler, P.-L. Boudreault, J. Strzalka, P.-O. Morin, M. Leclerc, J. T. L. Navarrete, M. A. Ratner, L. X. Chen, P. H. Chang, A. Facchetti and T. J. Marks, *J. Am. Chem. Soc.*, 2012, **134**, 18427.
- 4 (a) J. Ohshita, Y.-M. Hwang, T. Mizumo, H. Yoshida, Y. Ooyama, Y. Harima and Y. Kunugi, *Organometallics*, 2011, **30**, 3233; (b) Y.-M. Hwang, J. Ohshita, Y. Harima, T. Mizumo, Y. Ooyama, Y. Morihara, T. Izawa, T. Sugioka and A. Fujita, *Polymer*, 2011, **52**, 3912; (c) C. M. Amb, S. Chen, K. R. Graham, J. Subbiah, C. E. Small, F. So and J. R. Reynolds, *J. Am. Chem. Soc.*, 2011, **133**, 10062; (d) D. Gendron, P.-O. Morin, P. Berrouard, N. Allard, B. R. Aïch, C. N. Garon, Y. Tao and M. Leclerc, *Macromolecules*, 2011, **44**, 7188.
- 5 (a) C. E. Small, S. Chen, J. Subbiah, C. M. Amb, S. W. Tsang, T. H. Lai, J. R. Reynolds and F. So, *Nature Photonics*, 2012, **6**, 115; (b) C. P. Yau, Z. Fei, R. S. Ashraf, M. Shahid, S. E. Watkins, P. Pattanasattayavong, T. D. Anthopoulos, V. G. Gregoriou, C. L. Chohos and M. Heeney, *Adv. Mater.*, 2014, **24**, 678.
- 6 J. Ohshita, M. Miyazaki, F.-B. Zhang, D. Tanaka and Y. Morihara, *Polymer J.*, 2013, **45**, 979.
- 7 P. M. Beaujuge, W. Pisula, H. K. Tsao, S. Ellinger, K. Müllen and J. R. Reynolds, *J. Am. Chem. Soc.*, 2009, **131**, 7514.
- 8 J. Ohshita, M. Miyazaki, D. Tanaka, Y. Morihara, Y. Fujita and Y. Kunugi, *Polym. Chem.*, 2013, **4**, 3116.
- 9 For example, see (a) S. Yue, G. C. Berry and R. D. McCullough, *Macromolecules*, 1996, **29**, 933; (b) C.-Z. Zhou, T. Liu, T.-T. Lin, X.-H. Zhan, Z.-K. Chen, *Polymer*, 2005, **46**, 10952; (c) J. Clark, C.

Silva, R. H. Friend and F. C. Spano, *Phys. Rev. Lett.*, 2007, **98**, 206406; (d) S. T. Turner, P. Pingel, R. Steyrleuthner, E. J. W. Crossland, S. Ludwig and D. Neher, *Adv. Funct. Mater.*, 2011, **21**, 4640.