

Journal of Materials Chemistry B

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Large Area Uniform Deposition of Silver Nanoparticles Through Bio-inspired Polydopamine Coating on Silicon Nanowire Arrays for Practical SERS

Applications

Merve Selen Akin¹, Mehmet Yilmaz¹, Esra Babur¹, Betul Ozdemir¹, Hakan Erdogan¹, Ugur Tamer² and Gokhan Demirel^{1,}*

¹Bio-inspired Materials Research Laboratory (BIMREL), Department of Chemistry, Gazi University, 06500 Ankara, TURKEY

²Department of Analytical Chemistry, Faculty of Pharmacy, Gazi University, 06330 Ankara, TURKEY

** To whom correspondence should be addressed.*

E-mail: nanobiotechnology@gmail.com (GD).

Abstract

Despite the significant progress, the controlled deposition of nanoparticles onto the support materials having 3-D nano-morphologies is still facing challenges due to the limited diffusion of metal ions into the nanostructures and uncontrolled aggregation of nanoparticles. In this study, a simple yet versatile alternative is demonstrated to control silver nanoparticle (AgNP) density and morphology onto the 3-D silicon nanowire (SiNW) arrays based on bio-inspired polydopamine (PDOP) coating and electroless plating approaches for practical surface-enhanced Raman spectroscopy (SERS) applications. In order to control silver deposition and its morphology and to optimize the SERS performance of AgNP decorated SiNW arrays, the effect of some key experimental parameters including SiNW length and morphology, silver reduction time and PDOP thickness are investigated in detail. The optimized samples demonstrate remarkable surface-enhancement ability in Raman signals with high reproducibility (lower than ~10% spot-to-spot and sample-to-sample). Interestingly, it is found that PDOP coating not only serves as a reducing agent for the deposition of AgNPs

on SiNW arrays in controlled manner, but also contributes the observed SERS enhancements in terms of improving photon scattering and promoting electron transfer processes due to its organic semiconductor nature.

1. Introduction

Surface-enhanced Raman spectroscopy (SERS) has attracted increasing interest as a powerful analytical tool for the detection of chemical and biological molecules since its discovery.¹⁻⁵ In SERS studies, the enhancement of Raman signals fundamentally stems from the electromagnetic field in close vicinity of nanostructures with plasmonic features on a surface.³ In this context, to gain the unique SERS spectra of target molecules at trace amounts, a series of innovative strategies have been proposed to develop a reliable, sensitive, and selective SERS-based sensing platform.^{2,6} Although the employment of noble metal nanoparticles such as gold and silver on solid substrates is undoubtedly a simple and facile method for creating such platforms, their uncontrolled aggregation leads to a poor reproducibility and discrepancy in the resulting SERS signals which limit their applications.^{7,8} Alternatively, to eliminate the uncontrolled aggregation and to achieve spatial arrangement of nanostructures, much more sophisticated nanofabrication techniques such as oblique angle deposition,⁹ nanosphere lithography,¹⁰ electron beam lithography,¹¹ and focused ion beam milling¹² are currently available. The substrates prepared by these techniques have provided large Raman enhancement ability and good SERS reproducibility due to multiple hot spot generations, cavity resonances, and propagation of surface plasmon resonances (SPRs).^{13,14} On the other hand, these techniques are too technologically demanding and quite expensive in the fabrication of large quantities of substrates.¹⁵

According to recent theoretical and experimental reports, precise control of the size and uniformity of noble metal nanoparticles on surfaces with 3-D morphology is a key issue

in fabrication of SERS based sensor platforms.^{16,17} To address this issue, many methods including vapor phase deposition, sputtering, electrochemical plating and immobilization have been investigated.¹⁸⁻²³ For example, Zhang et al. reported the SERS performance of silver-coated silicon nanowire (SiNW) arrays in terms of enhancement ability, stability, and reproducibility.¹⁵ Although the optimized silver-coated SiNW arrays exhibited good SERS performances, fabrication procedure of this platform requires multistep and complicated procedures and unwanted impurities related to use of chemicals and solvents may also pose a serious deterrent to sensitive and selective detection. Besides, there is no data on the morphology change of the deposited silver over time and its effect on the SERS efficiency. In another study, silver nanoparticles (AgNPs) were directly grown on SiNWs through galvanic redox reaction without any organic contamination.²⁴ Despite of easiness of the proposed method to fabricate SERS-active substrate, the uncontrolled growth of AgNPs with broad size distribution as well as tendency of AgNPs to grow at the tips of SiNWs due to limited diffusion of silver are major drawbacks that limit the practical application of SERS. In a similar way, Galopin et al. fabricated SiNWs by the vapor-liquid-solid growth mechanism and AgNPs were then deposited by an electroless deposition technique.²⁵ Non-uniform silver deposition with different morphology was observed on the upper and lower parts of each array probably due to diffusion limitation and crossing and contact between SiNWs. These reports clearly show that simple but effective new strategies for the fabrication of nanoparticle decorated 3-D nano-morphologies in controlled manner are still needed for SERS applications in order to reach their full potential.

In this study, we proposed a simple and versatile method to control size and uniformity of AgNPs on vertically aligned SiNW arrays as an ideal SERS platform through polydopamine (PDOP) coating. The main advantage of PDOP is, as inspired from naturally in mussels, ability to be deposited on almost all types of inorganic and organic substrates with

controllable film thickness and durable stability as well as excellent biocompatibility.^{26,27} The vast functional groups of PDOP including catechol, amine and imine also serve as both reducing agent toward metal ions and anchor for grown metal nanoparticles neither using additional reductants nor metallic seed particles.²⁶ Moreover, PDOP coating will provide remarkable contribution for SERS enhancement in some respects due to its unique organic semiconductor nature.²⁶ In order to control silver deposition and its morphology and to optimize the SERS performance of AgNP decorated SiNW arrays, we investigated the effect of some experimental parameters such as SiNW length and morphology, silver reduction time and PDOP thickness in detail. Our proposed system resulted in well-controlled and uniform deposition of AgNPs on SiNWs with remarkable SERS performance in terms of enhancement, simplicity and reproducibility.

2. Experimental Section

Fabrication of Silicon Nanowire Arrays: The silicon nanowire arrays were prepared via metal-assisted chemical etching technique as reported elsewhere.²⁸⁻³¹ Briefly, silicon wafers with (001) crystallographic orientations and 1-10 Ω .cm resistivity were first sonicated in ethanol and acetone for 5 min, respectively. They were then transferred into a mixture of H_2SO_4 and H_2O_2 having a volume ratio of 3:1 at 70°C. After 60 min, the wafers were removed, washed with water, and dried with N_2 gas. Finally, they were treated in a UV/ozone chamber for 10 min. Following the pre-cleaning steps, the samples were immersed into HF solution (1 min) and immediately transferred in a Teflon baker containing 0.02 M of AgNO_3 and 4.6 M of HF (1:1 v/v) for 1 min. Finally, silver nanoparticle covered wafers were dipped into etching solution (HF (4.6 M): H_2O_2 (30%), 10:1 v/v) at room temperature for various durations (10-120 min). After a certain time, samples were removed and rinsed with water and HNO_3 to remove Ag dendrites which were formed as by-products.

Silver Nanoparticle synthesis on SiNW arrays: For silver nanoparticle synthesis, the as-prepared SiNW arrays were first coated with PDOP film. Typically, the SiNW arrays were immersed into a dopamine solution (2 mg/mL in 10 mM Tris buffer, pH 8.5) at room temperature for various durations (1 h-24 h). The samples were then rinsed with water and dried with N₂ gas. Finally, PDOP coated SiNWs were treated with an ionic silver solution (50 mM AgNO₃ in double distilled water) for varying reduction time periods (3-24 h) to grow AgNPs along the PDOP coated SiNWs.

Characterization: The morphologies of fabricated samples were characterized by using a Quanta 400F field-emission scanning electron microscope (FE-SEM) with an acceleration voltage of 10 kV. The thicknesses of PDOP films on the SiNWs, which were measured indirectly using a smooth silicon wafer placed next to the SiNW samples during PDOP deposition, were analyzed with a variable-angle spectroscopic-phase-modulated ellipsometer (UVISEL, Jobin Yvon-Horiba). In the layer thickness analysis, a four-phase model consisting of silicon substrate/SiO₂/overlayer/air was assumed. All thickness values given in the text are the averages of at least three measurements taken at three different locations on each sample surface.

In SERS studies, a Delta Nu Examiner Raman Microscopy system equipped with a 785 nm laser source, a motorized microscope stage sample holder, and a cooled charge-coupled device (CCD) detector was employed in the range of 200–2000 cm⁻¹. The related Raman instrument parameters were as follows: 20X objective, 30 μm spot size, 30 s acquisition time, and 150 mW laser power. For all measurements, baseline correction was performed. To evaluate the SERS performance, methylene blue (MB) was selected as Raman reporter molecule and 3 μL of 1 mM aqueous solution of MB dropped onto the Ag nanoparticle decorated SiNW arrays and kept in a hood until dry. The drying procedure led to coin-shaped Raman sample sizes of 4 ± 1 mm onto the sample surfaces. For each sample, at

least ten Raman spectra were collected from the different spots of substrate to determine the reproducibility and homogeneity.

3. Results and Discussion

In the first part of this study, we fabricated SiNW arrays having varying morphologies through a well-known metal-assisted chemical etching²⁸⁻³¹ method by controlling the etching time period. We kept constant the etching temperature for all experiments at 25°C and set the etching time at 10 min, 30 min, 60 min and 120 min, respectively. Typical cross-sectional and top-view SEM images of the fabricated samples are depicted in Figure 1. It can be clearly seen that the SiNWs are vertical to the Si wafer surface with varying lengths as desired. The diameter and length of the fabricated SiNWs were measured by employing freeware IMAGEJ software. When the etching time reached 10 min, the surface of the silicon wafer was fully covered by many uniformly generated and freestanding SiNWs with a length of $8.2 \pm 0.8 \mu\text{m}$ (Figure 1a and 1e). As the etching time period increased, the SiNWs gradually elongated and numerous sharp tips emerged. The length of SiNWs were determined as $24.3 \pm 1.9 \mu\text{m}$, $37.5 \pm 2.7 \mu\text{m}$, and $62.5 \pm 3.3 \mu\text{m}$ for the cases of 30, 60, and 120 min of etching time periods, respectively (Figure 1b,c,d). For long etching process (i.e., 60 and 120 min), the interconnection of SiNWs on top of them can easily be observed through the top-view SEM images (Figure 1g and 1h). Tangled SiNWs with a certain length are held together in bundles due to effective surface tensional forces during drying process and subsequently the van der Waal forces hold SiNWs together.^{32,33} In addition to these, it is observed that the as-prepared SiNWs have almost the same diameter throughout the length of nanowire independent of etching time periods. The diameters of SiNWs are in the range of 50-300 nm (Figure 1a-d).

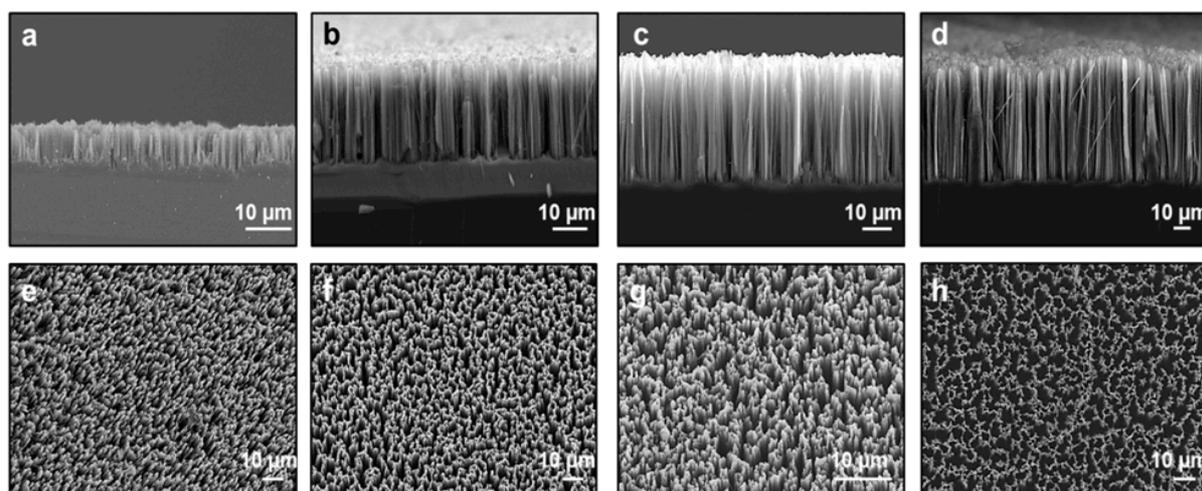


Figure 1. Cross-sectional and top-view SEM images of vertical aligned SiNW arrays for (a, e) 10 min, (b, f) 30 min, (c, g) 60 min, and (d, h) 120 min of etching time periods.

To evaluate the effect of surface morphologies of fabricated SiNW arrays on SERS performances, a thin layer of PDOP (~ 7 nm) was first coated on the SiNW surfaces by controlling oxidative polymerization time of dopamine, and silver nanoparticles were subsequently grown *in-situ* on the PDOP coated SiNWs into the 50 mM AgNO_3 solution for 24h. For all SERS measurements, methylene blue (MB) molecule was used as a Raman reporter. Typically, 3 μL of MB solution (1 mM) was dropped onto the sample surfaces and kept in a hood until dry. Drying process led to coin-shaped Raman sample sizes of 4 ± 1 mm. Figure 2 reveals the SERS spectra of MB molecules obtained from these samples. All collected spectra are precise and have acceptable signal-to-noise ratios consistent with the earlier reports for MB.^{9,34,35} For all cases, the most prominent peaks in the spectra of MB are the ring stretch ($\nu(\text{C}-\text{C})$) at ~ 1621 cm^{-1} , symmetric and asymmetric C-N stretches ($\nu_{\text{sym}}(\text{C}-\text{N})$ and $\nu_{\text{asym}}(\text{C}-\text{N})$) at ~ 1398 and ~ 1436 cm^{-1} , respectively, and the C-N-C skeletal deformation mode ($\delta(\text{C}-\text{N}-\text{C})$) at ~ 449 cm^{-1} . For short etching time period (10 min), Raman spectra with a low SERS signal intensity was detected (Figure 2a) possibly due to the dense silver nanoparticle formation onto samples led to disappearing of unique features of SiNW arrays

such as high-aspect ratio, sharp vertices, and interwire coupling which is disadvantages for SERS enhancement.¹⁵ Increasing etching time from 10 min to 30 min resulted in a highly remarkable (six-fold) increment in the SERS signal intensity according to prominent peak at around 1620 cm^{-1} . This result is somewhat expected. The interconnection on SiNWs with forest-like, highly tangled and uniformly closely-packed structure proved to be an ideal SERS substrate (Figure 1b, f and Figure 2d). Further increment in etching time (60 and 120 min) led to Raman signals with lower intensity (Figure 2c and 2b) possibly due to the discrete and bundled morphologies of SiNWs (Figure 1g and 1h). These morphologies may be created some dead points over the Raman spot size and lowered the SERS performance of SiNW arrays. To quantify and compare the SERS performance of Ag nanoparticle decorated samples (Ag@SiNWs), we also calculated the SERS enhancement factors (EF) by applying following equation using Raman intensity peak of MB at around 1620 cm^{-1} ;

$$EF = (N_{\text{Bulk}} \times I_{\text{AgNP@SiNW}}) / (N_{\text{AgNP@SiNW}} \times I_{\text{Bulk}}) \quad (1)$$

Where I_{Bulk} and $I_{\text{AgNP@SiNW}}$ are the Raman intensities of pure bulk MB and the adsorbed MB on the AgNP@SiNW arrays, and the N_{bulk} and $N_{\text{AgNP@SiNW}}$ are the number of MB molecules for the reference sample (in our case smooth silver film ($\sim 30\text{ nm}$) deposited on the pristine silicon wafer surface by PVD) and AgNP@SiNW arrays at different fabrication conditions. The calculated EFs for samples fabricated at 10, 30, 60, and 120 min etching time periods are 6.5×10^5 , 3.6×10^6 , 1.2×10^6 , and 1.1×10^6 , respectively. It should be noted that these EFs are average SERS EFs which indicate the SERS signal averaged over the entire area of interrogation.⁹

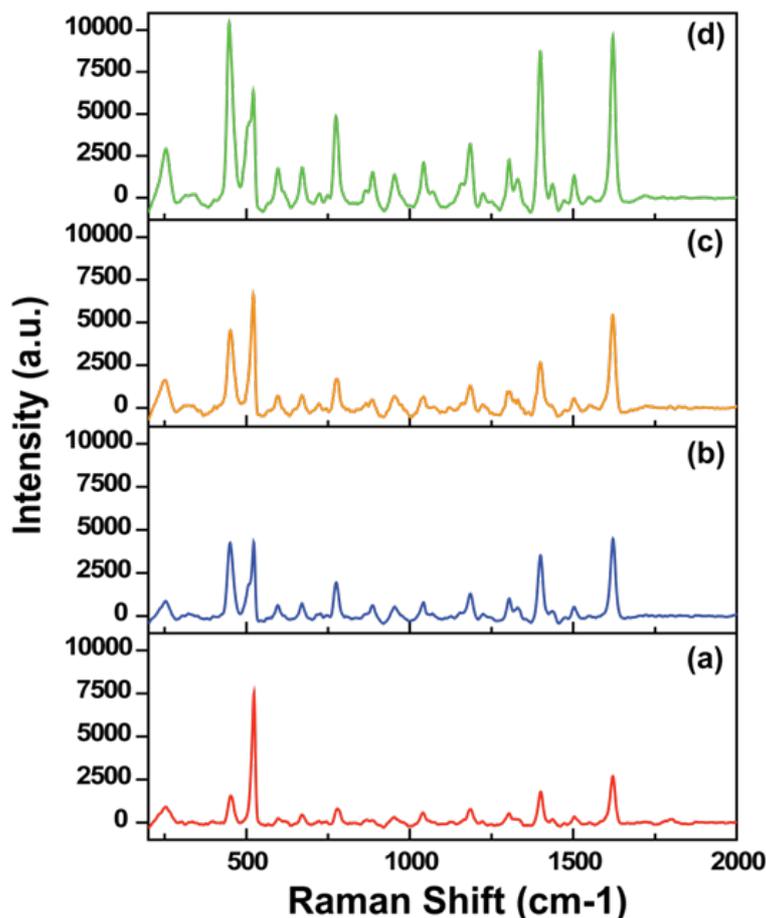


Figure 2. SERS spectra of MB on the AgNP@SiNW arrays fabricated at different etching time periods: (a) 10 min, (b) 120 min, (c) 60 min and, (d) 30 min.

Uniform deposition and distribution of plasmonic noble metal nanostructures such as AgNPs on the SiNW surfaces is the essential to acquire reproducible Raman spectra with high efficiency. Silver, which provides a higher SERS enhancement efficiency in the visible light wavelength region compared to gold or others, is mostly used as the metal to incorporate in 3-D nanostructured samples.^{15,36} To investigate the morphology and distribution of AgNPs on SiNW arrays and their relevant SERS performances, the AgNPs were grown *in-situ* on the PDOP coated SiNW samples at varying reduction time periods (3-24 h). In the case of AgNP formation, the catechol groups in PDOP film are mainly responsible for the *in-situ* formation of AgNPs due to their ability to release electrons when oxidized into the corresponding

quinone groups which trigger reduction processes of silver cations to silver nanoparticles.²⁶ For all samples, which were used for the AgNP deposition, we fixed etching time for SiNW fabrication at 30 min and PDOP thickness on SiNWs at ~ 7 nm. Figure 3 shows the cross-sectional SEM images of AgNP deposited SiNW arrays at varying reduction time periods. In the case of 3 h reduction time, lower particle density and higher size distribution for deposited AgNPs on SiNWs was observed compared with the other situations (Figure 3a and 3d). The size distribution of AgNPs is in the range of 12-70 nm with average size of 30 nm. For this case, the AgNPs are highly separated from each other. Consequently, it is not surprising to observe the lowest SERS enhancement of this set with 1.5×10^6 EF value (Figure 4a). We perceive that the resulting SERS enhancement may be attributed to the underlying substrate. Since the 3-D SiNW arrays have a large surface area and a huge amount of surface electrons, incident electromagnetic wave may effectively entrap and lead to further enhancement of surface plasmon resonance of AgNPs on SiNWs.²⁴ Moreover, PDOP coating on SiNWs may be another contributor for SERS enhancement. Recent reports have showed that PDOP is an organic semiconductor and it has a broad range adsorption capability lead to generate electrons.²⁶ Therefore, a thin layer of PDOP coating may promote the electron transfer to AgNPs resulting into enhancement of surface plasmon resonance. Increasing reduction time period from 3 h to 12 h resulted in a remarkable change in morphology and size as well as surface density of AgNPs. The AgNPs are in the range of 20-80 nm with average size of 60 nm (Figure 3b and 3e). Since the size and surface density of AgNPs increased, the nanoparticles get closer and closer. Garcia-Vidal and Pendry have proposed a model that can be applied to our case to quantitatively measure the electromagnetic interaction between adjacent metallic objects.³⁷ In their model, they reported that the average enhancement increases from 10^3 for “isolated” particles to a maximum of 10^6 for the case $d = 2R$ where the particles are in direct contact. In this equation, d is the distance between the centers of two

adjacent particles and $2R$ is also the particle diameter.³⁷ For the case of 12 h reduction time period, since d is quite lower than $2R$ (see Figure 3e), it is reasonable to expect huge local electric field and resultant SERS enhancement. The representative Raman spectra of related SERS substrate (Figure 4b) showed a higher Raman intensity with 2.2×10^6 EF value. Further increment in reduction time (24 h) led to dramatic change in surface morphology of AgNPs on SiNWs. Figure 3c and 3f depict the disappearance of discrete AgNPs and merge of nanoparticles due to excessive growth by time. Highly porous and densely packed nature of this substrate had an enormously higher SERS performance (Figure 4c) with calculated EF value of 3.6×10^6 compared with the other situations. Garcia-Vidal and Pendry have also analyzed the quantitative dependence of the localized plasmon mode on the surface roughness for the case of $d \leq 2R$ and observed that the enhancement effect diminishes with decreasing roughness.³⁷ In our case, highly dense and porous morphology of AgNPs on the SiNWs exhibited the highest Raman efficiency.

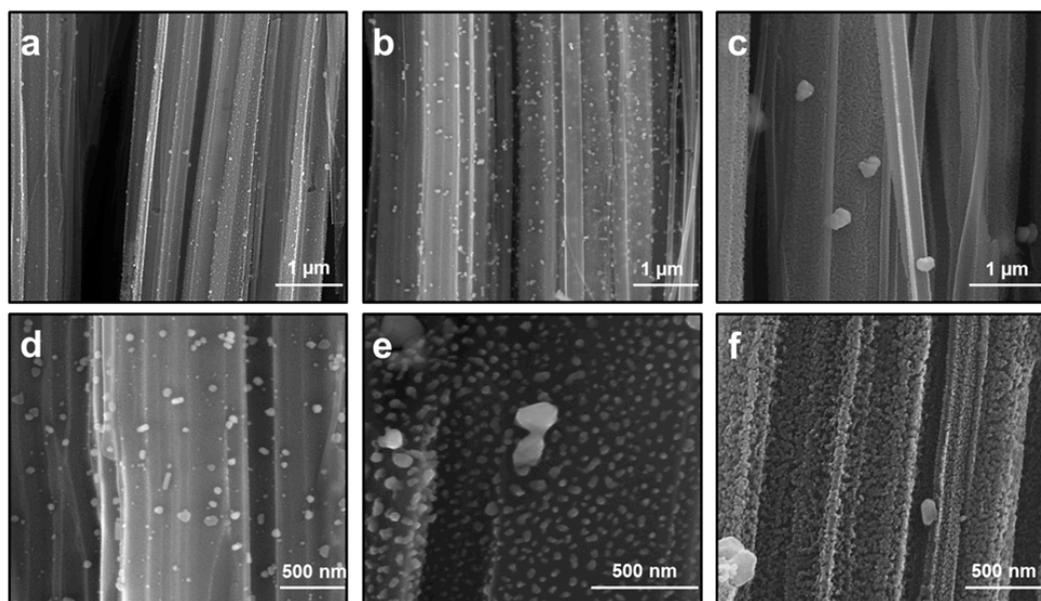


Figure 3. SEM images of AgNP deposited SiNWs for (a, d) 3 h, (b, e) 12 h, and (c, f) 24 h of silver ion reduction time. Each sample was etched for 30 min and coated with the same thickness of PDOP (~ 7 nm).

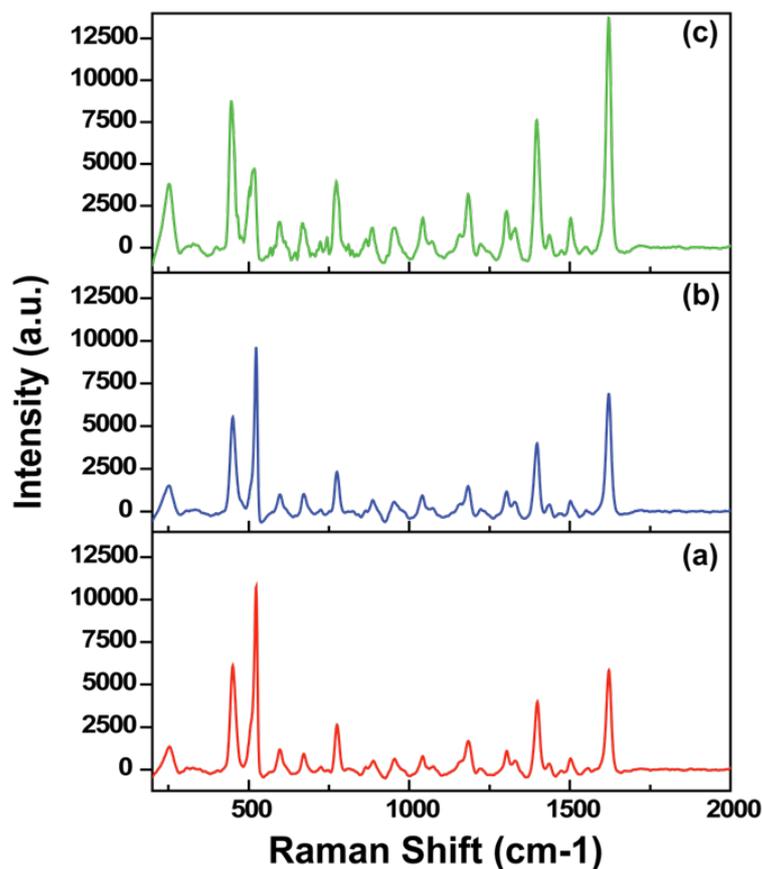


Figure 4. SERS spectra of MB on the AgNP@SiNW arrays fabricated at different silver ion reduction time periods: (a) 3h, (b) 12h, and (c) 24h.

The PDOP coating based on oxidative polymerization of dopamine molecules under alkaline condition with oxygen as the oxidant is a simple, very effective and material independent route. By this way, various materials either organic or inorganic may easily be modified in controlled manner.^{26,27} Since the pioneering work by Messersmith group,²⁷ PDOP coating have been widely investigated in a variety of fields. However, the polymerization mechanism of dopamine is still not fully understood due to the complex redox process and the generation of a series of intermediates during the reaction processes. According to previous reports,²⁶ dopamine is first oxidized to dopaminequinone and subsequently transformed to leukodopaminechrome through intramolecular cyclization under alkaline condition.

Afterwards, leukodopaminechrome suffers from oxidization and rearrangement to form 5,6-dihydroxyindole, which is easily further oxidized to 5,6-indolequinone.²⁶ These two molecules are formed multiple isomers of dimers and higher oligomers which may self-assemble further into the cross-linked polydopamine. Meanwhile, it is also found that a considerable amount of unpolymerized dopamine is also formed a self-assembled complex with its oxidative product, 5,6-dihydroxyindole.³⁸ Therefore, PDOP may be considered to be an aggregate of monomers similar to other synthetic or biological polymers. One of the remarkable advantages of PDOP coating is to reduce metal ions into metal nanoparticles. In this context, neither additional reducing agents nor metallic seed particles are required. Moreover, recent reports have demonstrated that PDOP has unique optical and electrical properties which are needed to keep in mind in SERS investigation. For these reasons, we evaluated the PDOP film thickness on the SERS performances of proposed platforms. In this set of experiments, we fixed etching time for SiNW fabrication at 30 min and reduction time for silver ions at 24 h. By changing PDOP polymerization time periods (1 h-24 h), PDOP thickness deposited on SiNWs have been manipulated. The thicknesses of deposited PDOP films on SiNWs were measured indirectly using a smooth silicon wafer placed next to the samples during polymerization. As expected, thicknesses of PDOP layer increased when the polymerization time period was increased. The PDOP thicknesses were found 2.2 ± 0.86 nm for 1 h, 6.78 ± 1.21 nm for 3 h, 11.8 ± 1.03 nm for 6 h, 22.6 ± 2.17 nm for 12 h, and 38.3 ± 2.41 nm for 24 h of polymerization time, respectively. Bernsmann et al. and Lee et al. independently showed that the maximum thickness of the PDOP film in a single reaction step is about 50 nm and further increasing the concentration of the dopamine monomer or prolonging the reaction time does not help to increase the thickness of the film.^{27,39}

Figure 5 compares the SERS spectra of MB molecules obtained from above mentioned samples. In a short polymerization time period (1h), a quite reasonable Raman spectrum with

high intensity was obtained (Figure 5a). The SERS intensity increased with the PDOP polymerization time from 1h to 3h, and reaches its maximum (Figure 5b). Interestingly, increasing PDOP polymerization time periods from 3 h to 6 h led to a dramatic decrease in intensity of Raman signal. The same inclination was observed in further polymerization times of PDOP (Figure 5c-e). This issue may be attributed to the thickness of PDOP. For the cases of 1h and 3h of polymerization time periods, the chemical interactions between the AgNPs and PDOP layer may be enhanced the scattering process. The electrons in the AgNP-conducting band are excited to the lowest unoccupied molecular orbital of PDOP by incident laser, and this unstable state relaxes through jumping back of electrons. Subsequently, a dipole between the AgNP and PDOP as well as adsorbate MB is formed as a result of this process. These surface dipoles may couple, resonate and transmit due to near field effect.²⁴ The resultant dipoles may improve the scattering process and led to increase SERS intensity. Additionally, promoted electron transfer to AgNPs from PDOP layer due to its broad band adsorption capability may contribute to enhance surface plasmon resonance of AgNPs as well as SERS performance.²⁶ However, for thicker PDOP layer (6 h-24 h), contributions of above mentioned issues remain limited and may not improve the SERS intensity efficiently. In these cases, we assume that high density molecular stacking and un-uniform molecular arrangement of PDOP film prevent the electronic movement and scattering. However, theoretical modeling and more detailed experiments are still needed to better understand this phenomenon.

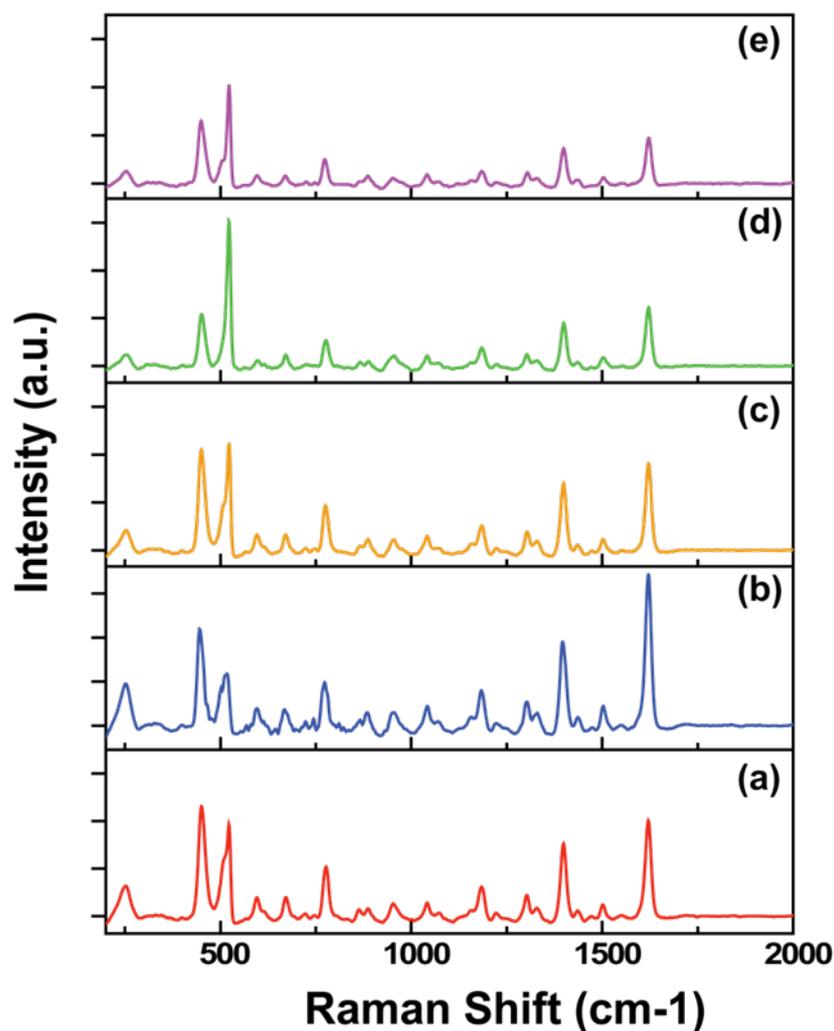


Figure 5. SERS spectra of MB on the AgNP@SiNW arrays fabricated at different polymerization time of PDOP: (a) 1h, (b) 3h, (c) 6h, (D) 12h, and (e) 24h.

It is well-known that the poor reproducibility of Raman signals in SERS studies is the main obstacle that should be concerned to prove the proposed system as an ideal SERS substrate. To evaluate the reproducibility of our substrate, we collected SERS spectra of MB molecules from 50 randomly selected positions on the optimized AgNP@SiNW arrays under identical experimental conditions (Figure 6). It is clear that for all runs, Raman spectra with high reproducibility efficiency were determined. To clarify and quantify the reproducibility, we calculated relative standard deviation (RSD) for the spectra given in Figure 6. Table 1

shows the RSD values in intensity changes and position shift of prominent Raman peaks. According to RSD values and peak positions, we can conclude that RSD values below 0.21 revealed a good reproducibility across the entire area of the optimized AgNP@SiNW arrays. One exception is the peak at around 521 cm^{-1} . This peak is originated from the nature of SiNW arrays.⁴⁰

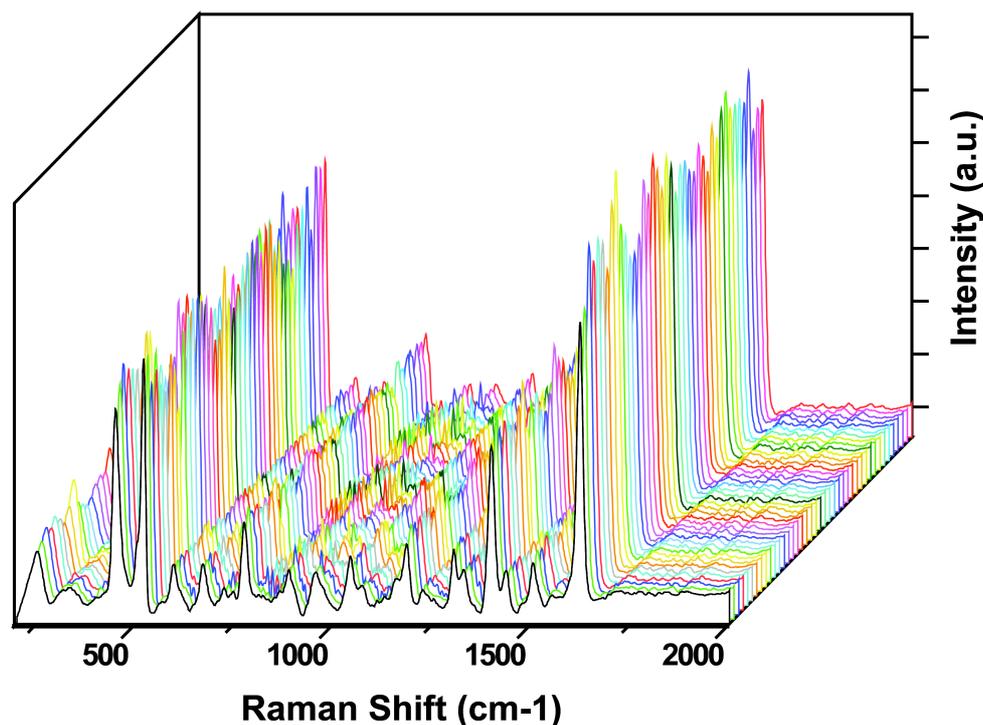


Figure 6. Reproducibility of SERS spectra of MB collected on the randomly selected 11 spots of the optimized AgNP@SiNW arrays.

Table 1. RSD values for the major peaks of the SERS spectrum for the optimized substrate of AgNP@SiNW arrays.

Peak Position (cm^{-1})	1621 \pm 0.5	1398 \pm 0.8	1303 \pm 0.5	1183 \pm 0.8	774 \pm 0.6	521 \pm 1	449 \pm 0.8
RSD Value	0.08	0.1	0.09	0.09	0.13	0.21	0.07

4. Conclusion

In this paper, we reported a simple yet very effective way to control size and density of silver nanoparticles on 3-D SiNWs arrays based on bio-inspired PDOP coating for practical SERS applications. The optimized AgNP decorated SiNW arrays exhibit remarkable surface-enhancement ability in Raman signals with high reproducibility (lower than ~10% spot-to-spot and sample-to-sample). Interestingly, it is found that PDOP coating not only serves as a reducing agent for the deposition of AgNPs on SiNW arrays, but also contributes the SERS enhancement in terms of improving photon scattering and promoting electron transfer processes due to its organic semiconductor nature. Although there are still many challenges ahead related to SERS, the present concept can be regarded as an important step towards the fabrication of an ideal SERS platform and may open up intriguing opportunities for practical SERS applications.

Acknowledgements

This work was supported by the Scientific and Technological Research Council (TUBITAK) grant number 111M237. M. Y. is supported by TUBITAK BIDEB fellowship. M. S. A. and M. Y. contributed equally to this work.

References

- [1] M. G. Albrecht and J. A. Creighton, *J. Am. Chem. Soc.*, 1977, **99**, 5215.
- [2] M. Moskovits, *J. Raman Spectrosc.*, 2005, **36**, 485.
- [3] P. L. Stiles, J. A. Dieringer, N. C. Shah and R. R. Van Duyne, *Annu. Rev. Anal. Chem.*, 2008, **1**, 601.
- [4] R. M. Jarvis and R. Goodacre, *Chem. Soc. Rev.*, 2008, **37**, 931.
- [5] A. G. Ryder, *Curr. Opin. Chem. Biol.*, 2005, **9**, 489.
- [6] X. M. Qian and S. Nie, *Chem. Soc. Rev.*, 2008, **37**, 912.
- [7] J. F. Li, Y. F. Huang, Y. Ding, Z. L. Yang, S. B. Li, X. S. Zhou, F. R. Fan, W. Zhang, Z. Y. Zhou and B. Ren, *Nature*, 2010, **464**, 392.
- [8] M. P. Cecchini, V. A. Turek, J. Paget, A. A. Kornyshev and J. B. Edel, *Nat. Mater.*, 2013, **12**, 165.
- [9] M. Yilmaz, E. Senlik, E. Biskin, M. S. Yavuz, U. Tamer and G. Demirel, *Phys. Chem. Chem. Phys.*, 2014, **16**, 5563.
- [10] C. L. Haynes and R. P. Van Duyne, *J. Phys. Chem. B*, 2001, **105**, 5599.
- [11] N. Felidj, J. Aubard, G. Levi, J. Krenn, A. Hohenau, G. Schider, A. Leitner and F. Aussenegg, *Appl. Phys. Lett.*, 2003, **82**, 3095.
- [12] A. G. Brolo, E. Arctander, R. Gordon, B. Leathem and K. L. Kavanagh, *Nano Lett.*, 2004, **4**, 2015.
- [13] W. Wei, K. Chen and G. Ge, *Adv. Mater.*, 2013, **25**, 3863.

- [14] M. D. Doherty, A. Murphy, J. McPhillips, R. J. Pollard and P. Dawson, *J. Phys. Chem. C*, 2010, **114**, 19913.
- [15] B. Zhang, H. Wang, L. Lu, K. Ai, G. Zhang and X. Cheng, *Adv. Funct. Mater.*, 2008, **18**, 2348.
- [16] I. Yoon, T. Kang, W. J. Choi, J. Kim, Y. D. Yoo, S. W. Joo, Q. H. Park, H. Ihee and B. Kim, *J. Am. Chem. Soc.*, 2009, **131**, 758.
- [17] X. T. Wang, W. S. Shi, G. W. She, L. X. Mu and S. T. Lee, *Appl. Phys. Lett.*, 2010, **96**, 053104.
- [18] S. Chan, S. Kwon, T. W. Koo, L. P. Lee and A. A. Berlin, *Adv. Mater.*, 2003, **15**, 1595.
- [19] D. Y. Wu, J. F. Li, B. Ren and Z. Q. Tian, *Chem. Soc. Rev.*, 2008, **37**, 1025.
- [20] S. J. Huo, X. K. Xue, Q. X. Li, S. F. Xu and W. B. Cai, *J. Phys. Chem. B*, 2006, **110**, 25721.
- [21] L. L. Bao, S. M. Mahurin, C. D. Liang and S. Dai, *J. Raman Spectrosc.*, 2003, **34**, 394.
- [22] J. G. Fan and Y. P. Zhao, *Langmuir*, 2008, **24**, 14173.
- [23] M. L. Zhang, C. Q. Yi, X. Fan, K. Q. Peng, N. B. Wong, M. S. Yang, R. Q. Zhang and S. T. Lee, *Appl. Phys. Lett.*, 2008, **92**, 043116.
- [24] M. L. Zhang, X. Fan, H. W. Zhou, M. W. Shao, J. A. Zapien, N. B. Wong and S. T. Lee, *J. Phys. Chem. C*, 2010, **114**, 1969.
- [25] E. Galopin, J. Barbillat, Y. Coffinier, S. Szunerits, G. Patriarche and R. Boukherroub, *ACS Appl. Mater. Inter.*, 2009, **1**, 1396.
- [26] Y. Liu, K. Ai and L. Lu, *Chem. Rev.*, 2014, DOI: 10.1021/cr400407a

- [27] H. Lee, S. M. Dellatore, W. M. Miller and P. B. Messersmith, *Science*, 2007, **318**, 426.
- [28] X. Li and P. W. Bohn, *Appl. Phys. Lett.*, 2000, **77**, 2572.
- [29] K. Peng, Y. Xu, Y. Wu, Y. Yan and S. T. Lee, *Small*, 2005, **1**, 1062.
- [30] K. Peng, J. Hu, Y. Yan, Y. Wu, H. Fang, Y. Xu, S. T. Lee and J. Zhu, *Adv. Funct. Mater.*, 2006, **16**, 387.
- [31] Z. Huang, N. Geyer, P. Werner, J. De Boor and U. Gosele, *Adv. Mater.*, 2011, **23**, 285.
- [32] D. Kumar, S. K. Srivastava, P. Singh, K. Sood, V. Singh, N. Dilawar and M. Husain, *J. Nanopart. Res.*, 2010, **12**, 2267.
- [33] T. Qiu, X. Wu, J. Shen, P. C. Ha and P. K. Chu, *Nanotechnology*, 2006, **17**, 5769.
- [34] Q. Hao, B. Wang, J. A. Bossard, B. Kiraly, Y. Zeng, I. K. Chiang, L. Jensen, D. Werner and T. J. Huang, *J. Phys. Chem. C*, 2012, **116**, 7249.
- [35] L. Li, T. Hutter, A. S. Finmore, F. M. Huang, J. J. Baumberg, S. R. Elliott, U. Steiner and S. Mahajan, *Nano Lett.*, 2012, **12**, 4242.
- [36] E. Mulazimoglu, S. Coskun, M. Gunoven, B. Butun, E. Ozbay, R. Turan and H. E. Unalan, *Appl. Phys. Lett.*, 2013, **103**, 083114.
- [37] F. J. Garcia-Vidal and J. Pendry, *Phys. Rev. Lett.*, 1996, **77**, 1163.
- [38] S. Hong, S. Yun, S. Choi, I. T. Kim and H. Lee, *Adv. Funct. Mater.*, 2012, **22**, 4711.
- [39] F. Bernsmann, V. Ball, F. D. R. Addiego, A. Ponche, M. Michel, J. J. D. A. Gracio, V. R. Toniazco and D. Ruch, *Langmuir*, 2011, **27**, 2819.
- [40] S. Piscanec, M. Cantoro, A. Ferrari, J. Zapien, Y. Lifshitz, S. Lee, S. Hofmann and J. Robertson, *Phys. Rev. B*, 2003, **68**, 241312.