

Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

(Review article) Submitted to Journal of Materials Chemistry C

Solution-Based Synthesis of Anisotropic Metal Chalcogenide Nanocrystals and Their Applications

Yuho Min[†], Geon Dae Moon[†], Chang-Eun Kim, Ji-Hwan Lee, Heesung Yang,
Aloysius Soon, and Unyong Jeong*

Department of Materials Science and Engineering, Yonsei University,
134 Shinchon-dong, Seoul, Korea

Corresponding Author: E-mail: ujeong@yonsei.ac.kr

Keywords: metal chalcogenides, anisotropic nanocrystals, nanowires, nanosheets,
solution-based synthesis, DFT simulations, application of metal chalcogenides

(Review article) Submitted to Journal of Materials Chemistry C

Abstract

This article reviews recent advances in solution phase synthesis to generate 1-D and 2-D anisotropic metal chalcogenide (MC) nanostructures with a focus on using different growth mechanisms to control the shapes of the MCs. Four different synthetic approaches have been reviewed: naturally favoured growth due to its intrinsically anisotropic crystal structure, modified anisotropic growth by changing surface energies or utilizing organic templates, oriented attachment of small nanocrystal building blocks to form nanowires or nanosheets, and chemical transformation from existing nanostructures into new species. We discuss current understanding of the thermodynamic and kinetic aspects associated with the mechanisms of forming these anisotropic MC nanostructures. We provide examples of representative applications of anisotropic chalcogenide nanomaterials that are expected to be practically meaningful in the near future. The applications include electrodes for lithium ion batteries, photodetectors, thermoelectric devices, and solar cells. Brief review of other potential applications (oxygen reduction reaction, localized surface plasmon resonance, topological insulator, superconductor) are provided as well. This review ends with discussions on the challenges to be investigated thoroughly in the solution-based synthesis of anisotropic nanomaterials, which includes surface energy control, correcting the nucleation & growth mechanism, removal of organic surfactant, kinetic study on the chemical transformation, scale-up of production, and eco-friendly synthesis.

(Review article) Submitted to Journal of Materials Chemistry C

1. Introduction

Having the ability to exert a control over the shape of nanocrystals has always been desired and essential to tune their chemical or physical properties for target applications.¹⁻³ Anisotropic nanocrystals have unique properties that are direction-dependent and have the ability to confine the motion of electrons, holes, excitons, phonons, and plasmons in specific and controlled directions.^{1,3} Such uniqueness have been employed in electronics (conducting platforms, transistors, electromechanical devices),⁴⁻⁷ energy conversion and storage devices (Li ion batteries, solar cells, thermoelectrics, piezoelectrics),⁸⁻¹⁷ optical devices (lasers, OLED, photodetectors),¹⁸⁻²¹ and electrochemical devices (catalysis, gas sensors).^{22,23} Anisotropic nanocrystals have been observed in many materials including carbons, silicon, metals, metal oxides, chalcogenides, carbides, nitrides, and their compounds.^{24,25}

Although anisotropic metal chalcogenide (MC) nanocrystals have recently been investigated with much interest (with regards to their applications), remarkable advances have been made with anisotropic nanocrystals in diverse areas of modern technology.¹ These MC nanocrystals are also strong candidate materials for thermoelectric devices. Energy harvested from heat loss and cooling electronic devices by effective heat transfer have motivated the studies on the chalcogenide-based thermoelectric devices.²⁶ In photovoltaic and photodetector devices, MC nanocrystals have shown to absorb sun light, hence they can play as exciton generators and charge transport materials.²⁷⁻²⁹ The MC nanocrystals with a layered crystal structure and their composites with carbon materials are promising candidates that can intercalate Li⁺ ions reversibly, which can be used as electrodes for batteries.³⁰⁻³³ In addition to these applications, novel applications are recently being investigated for these MCs. As an alternative to noble metals, doped MC nanostructure has attracted interest as an efficient catalyst for the oxygen

(Review article) Submitted to Journal of Materials Chemistry C

reduction reaction^{34,35} and as a patternable material whose localized surface plasmon resonance is tunable.^{36,37} The topological insulating characteristics³⁸ and superconductivity³⁹ of MC nanostructures are also considered as new areas of research for this class of materials.

Anisotropic MC nanocrystals have predominantly been synthesized in solutions because the size and shape of the nanocrystals can be controlled precisely and the solution-processed printing is an inexpensive way to produce MC films.⁴⁰⁻⁴³ Chalcogens (S, Se, Te) and certain MCs are representative materials having the preferred directional growth. The shape of nanocrystals is known to be dominated by the total minimum surface energy of the crystal facets; this is known as the Gibbs-Wulff theorem.⁴⁴ In many chalcogenides, the minimized total surface energies are found in the 1-D shapes because of the asymmetric bond strength. Se and Te are well known to grow into nanowires or nanotubes.^{45,46} The layer-structured chalcogenides grow into 2-D nanoplates or nanosheets, as frequently observed in Bi₂Se₃, Bi₂Te₃, MoS₂, and SnS₂, etc. Table 1 summarizes the thermodynamic preference in shape and crystal structure of MC nanocrystals. It varies in the metal species and the stoichiometric ratio of the metal to chalcogen (M_xQ_y, M=metal, Q=S, Se, Te). These materials, according to each category, are listed and the tendency to form the anisotropic shape is noted as 'strong' or 'medium' in the table. The preparation of chalcogenides that do not have any preferential growth direction requires purposeful shape-guiding. Normally, the shape of nanocrystals obtained through thermodynamically-controlled growth reflects the inherent symmetry of the crystal structure, which is spherical or near spherical due to uniform growth of all crystal facets. Reduction of the surface energy of a certain facet is a powerful way to obtain anisotropic MCs, which can be achieved by selectively attaching organic surfactants or using the organic templates as the shape-determining reactor. The MC nanocrystals can then be merged to form 1-D or 2-D nanostructures. Such oriented

(Review article) Submitted to Journal of Materials Chemistry C

attachment can be tailored by engineering the interaction between the nanocrystals. Chemical transformation of pre-existing anisotropic nanocrystals into others has recently received a lot of interest because it allows preparation of nanocrystals that are chemically different, but have the same shape and dimensions. MC nanocrystals reported to date are tabulated (Table 2) according to their synthetic pathways.

This review highlights the common solution-based synthesis of anisotropic MC nanocrystals and the recent advances in applications, with some guidance from first-principles simulations and computations. The synthetic pathways of 1-D and 2-D structures are dealt with in separate sections. We begin with the direct synthesis from organometal precursors and then review the chemical transformation of the premade nanocrystals into others. The application section mainly focuses on the research areas which can be practically meaningful in the near future, and then introduces a few emerging topics in physics and chemistry. We conclude this review with discussion on the challenges and future directions in the solution-based synthesis and their applications.

2. Direct synthesis of 1-D chalcogenides

2-1. Intrinsically anisotropic growth

Selenium (Se) and Tellurium (Te) inherently grow into anisotropic nanostructures due to the covalent bond in a helical chain along the *c*-axis. The helical chains are hexagonally closely-packed through van der Waals interaction. Thus, the stronger atomic bond strength in the *c*-axis results in rapid growth along that direction. Figure 1A shows the crystal structure of Te with the lattice spacings calculated by density-functional theory (DFT) with Grimme's van der Waals correction.⁴⁷ We performed the DFT calculation within generalized gradient

(Review article) Submitted to Journal of Materials Chemistry C

approximation (GGA) for exchange-correlation functional, given by Perdew, Burke and Ernzerhof (PBE) as implemented in the Vienna *ab initio* simulation package (VASP).⁴⁸ The kinetic energy cutoff for the planewave basis set is set to 500 eV and the core level interactions are represented by the projector augmented wave (PAW) potentials.⁴⁹ From our first-principle density-functional theory (DFT) calculations, we find the surface energy of the basal plane (normal to the *c*-axis) is indeed relatively higher (0.616 J/m²) than those of the prism planes (~0.463 J/m²), clearly reflecting that cutting the stronger covalent bonds in the *c*-direction involves a larger energetic cost to form that surfaces. Due to this difference on surface energies, the calculated theoretical Gibbs-Wulff shape favors growth along the *c*-axis rather than the *a*- and *b*-axis. This corroborates the fact that selenium nanowires are reported to show a preferential growth along the [001] direction in a wet chemical process.⁵⁰ The 1-D growth of this system is also attributed to the minimizing of the area of facets (i.e. basal planes) with relatively high surface energies, lowering the total free energy of the system. But in a dry vapor-solid process with relatively high temperature (~950 °C), the seed effect was found to be more dominant in the growth of nanowires.⁵¹

Considerable effort has been devoted to generate diverse 1-D Se and Te nanostructures in solution-based synthesis.⁵²⁻⁶⁶ Yu and co-workers synthesized *t*-Te nanowires 4-9 nm in diameter and hundreds of micrometers in length using hydrothermal methods (Figures 1B, C).⁶⁷ HR-TEM images clearly showed that the *t*-Te nanowires grew predominantly along the *c*-axis. Because Se and Te can form a solid solution on the basis of Hume-Rothery rule, binary Se_xTe_y alloys also tend to grow favorably along the *c*-axis, allowing the formation of Se_xTe_y and Se_xTe_y@Te core-shell nanorods.^{68,69}

(Review article) Submitted to Journal of Materials Chemistry C

Pnictogen chalcogenides, M_2Q_3 ($M = \text{Bi, Sb}$; $Q = \text{S, Se, Te}$), are nanocrystals with a highly anisotropic crystal structure. Pnictogen chalcogenides have been extensively investigated because of their promising thermoelectric and optoelectronic properties. Interestingly, in addition to their 2-D structures, Bi_2S_3 , Sb_2S_3 , and Sb_2Se_3 possess a strong tendency to grow along the c -axis into a 1-D nanostructure. Such tendency is attributed to the chain-like molecular conformation that results from V-VI bonding and van der Waals interactions between the chains (Figure 1D). This anisotropic growth mode may, once again, be accounted for on thermodynamic grounds, referring to their surface Gibbs free energy differences between different surfaces. This is illustrated using the orthorhombic Bi_2S_3 as an example. Using first-principles DFT calculations, it was shown that the surface free energy of the (001) surface of Bi_2S_3 (0.423 J/m^2) was higher than the other low-index surfaces.⁷⁰ Two other low index facets — (100) and (010) facets (0.359 J/m^2 and 0.349 J/m^2 , respectively) — had slightly different surface energies, but were both similarly lower than that of (001). Thus, to afford the minimization of the free energy of the system during growth, Bi_2S_3 is thermodynamically driven to conform to a crystal morphology (i.e. a rod-like shape) which minimizes the area of (001) facet, while maximizing that of the other two facets. A schematic of this equilibrium crystal shape of Bi_2S_3 is shown in figure 1D.

In numerous experimental studies, Bi_2S_3 nanorods were synthesized through a hot injection method with elemental sulfur, bismuth chloride, and oleylamine.⁷¹ Bismuth chloride dissolved in oleylamine was first transformed into BiOCl , then further reduced into elemental bismuth by the amine groups when the solution was heated up to $170 \text{ }^\circ\text{C}$. Uniformly-sized Bi_2S_3 nanorods were produced by rapid hot injection of a sulfur solution. The as-synthesized Bi_2S_3 nanorods were single crystals that showed preferential growth

(Review article) Submitted to Journal of Materials Chemistry C

along the [001] direction (Figure 1E, F). If some form of kinetic hindrance occurs during the reaction, the final shape of nanocrystal may deviate from the ideal one-dimensional morphology, e.g. partially generating quasi-two-dimensional crystals as the kinetic shape. This could then explain the experimental observation in the growth of Bi_2S_3 nanowire, where small portions of nanoplates were grown together with thin and long nanowires.⁷² This delicate difference in the relative surface free energy of the various prism facets of Bi_2S_3 can be used to tailor and design the desired morphology for its specific application. Sb_2S_3 and Sb_2Se_3 favorably crystallized into nanorods with an orthorhombic crystal structure.⁷³ Zheng and co-workers reported the hydrothermal synthesis of 1-D Sb_2Se_3 nanostructures with controlled aspect ratios.⁷⁴ Short nanorods were produced at high temperatures (150 °C), which is due to rapid exhaustion of the sources (Sb^{3+} and Se^{2-}) and sequential lack of driving force for nucleation and growth into nanowires. Thick, long nanorods were prepared at high concentrations by continuous reaction between Sb^{3+} and Se^{2-} . The diameter of the nanowires slightly increased with the prominent increase of the length until the sources were consumed completely.⁷⁴

2-2. Growth by surface energy control

During thermodynamic growth of nuclei, the fastest growing facets should disappear eventually due to the increased surface energy, while the slowest growing facets should survive as the final planes of the product. Controlled growth of nanocrystals with anisotropic morphologies has been extensively investigated by adjusting organic surfactants over the past two decades. Although MC nanoparticles with diverse asymmetric shapes had been experimentally achieved with controlling the surface energies, the interaction between

(Review article) Submitted to Journal of Materials Chemistry C

organic molecules and specific facets is still in lack of understanding. This surface energy minimization possibly enables evolution into 1-D nanostructures in a way that specific binding of surfactant molecules to a preferred facet reduces the surface energy of the plane. First principles electronic structure simulation revealed the effect of organic surfactant binding on the various surfaces of a CdSe crystal.^{75,76} The typical capping agents include phosphonic acids (PA), phosphine oxides (PO), trimethylamines (TMA), and carboxylic acids (CA). The (0001), (000 $\bar{1}$), (01 $\bar{1}$ 0), and (11 $\bar{2}$ 0) facets were selected and systematically examined on the effect of binding energy with ligands. Figure 2A shows the configurations of the PO and PA bound to the four facets of Cd₃₃Se₃₃ dots. The energy was stable when Cd or Se atoms made bonds with the oxygen double bonded to the phosphor (PO and PA) or the carbon (CA). For TMA molecules, the binding took place between Cd or Se atoms and the lone pair electrons on the nitrogen atom. Binding energies between the surfactant molecules and the facets of Cd_xSe_x (x=15, 33) were calculated (Table 3). PO and PA were found to bind more strongly to the nonpolar side facets with Barvais indices (01 $\bar{1}$ 0) or (11 $\bar{2}$ 0) than to the polar surfaces (0001) and (000 $\bar{1}$). The preference in binding facets indicates faster growth of polar facets than the nonpolar facets for reducing the total surface energies of the resulting nanostructures. For polar facets, the binding energies of these surfactants to the (0001) surface were much smaller than (000 $\bar{1}$), indicating that the growth of CdSe along the *c*-axis would be dominated by the Se-terminated (0001) facet. In many experimental synthesis reactions, CdSe spheres have been produced in the presence of CA surfactants,⁷⁷ which is attributed to the small and weak binding energies of CA on the CdSe surfaces.

(Review article) Submitted to Journal of Materials Chemistry C

Unlike other surfactants, trimethylamine (TMA) binds slightly stronger to the Se-terminated (0001) facets, which can induce the faster growth of Cd-dominated (000 $\bar{1}$) along the c-axis.

The crystal structures could be engineered by surfactant molecules through fine-tuning of surface energies. Generally, wurtzite is a thermodynamically stable crystal structure for both CdS and CdSe in bulk states. The metastable zinc blend phase has been mainly allowed at low reaction temperature (< 240 °C) or in small size limit (< 4.5 nm). Indeed, zinc blend CdS nanowires with 15 nm diameter could be successfully synthesized even at high reaction temperature (310 °C). Theoretical analysis confirmed that trioctylphosphine (TOP) molecules are likely to bind strongly to the (001) surface of the zinc blend CdS than to the surfaces of the wurtzite CdS (Table 3).⁷⁸ In some cases, a mixture of surfactants can effectively direct 1-D growth. Ultrathin (1.7 nm) hexagonal Cu₂S nanowires as long as tens of micrometers were successfully synthesized using a mixture of dodecanethiol (DT) and oleic acid (OA) as the solvent.⁷⁹ DT served as the primary capping ligand for nanowire growth through the formation of thiol-to-Cu(I) bonding on the surface. The growth of Cu₂S nanowires could be attributed to the synergistic effect of the solvent OA and the adsorbent affinity of DT.

The energy decrease of the target facet by the organic surfactant is often not large enough to guide the growth to a 1-D nanostructure. In this case, use of an organic template whose molecules form complexes with the inorganic sources can be a powerful way to generate anisotropic nanocrystals.⁸⁰⁻⁸² Due to the preferential bonding of the organic molecule to a specific inorganic element, the inner surface of the template is covered by the preferred element. The reduced atoms are stabilized by the complex molecules and nuclei are initiated at the inner surface of the template. Consecutive assembly of the inorganic elements in a 1-D template facilitates the growth into nanowires. Ma and co-workers demonstrated that PbTe can

(Review article) Submitted to Journal of Materials Chemistry C

be synthesized into nanowires and nanorods in the presence of sucrose templating molecules.⁸² Normally, PbTe grows thermodynamically into spherical or cubic nanoparticles due to its preferred isotropic cubic crystal structure. The key factor in promoting the 1-D growth was the addition of sucrose, which has hydroxyl groups that interact exclusively with Pb (Figure 2B). In addition, the π - π electron interactions of sucrose served as an organic template for the growth of nanowires. PbTe nanocubes and flower-shaped clusters were synthesized under the same conditions when sucrose was replaced by other typical surfactants such as trioctylphosphine (TOP) and trioctylphosphine oxide (TOPO). Selective interactions between the hydroxyl groups and Pb atoms were confirmed by replacing Pb with Pt in the same synthesis process. Pt source caused the formation of highly agglomerated randomly-shaped PtTe crystals in the same experimental condition. This result suggests the lack of effective interactions between sucrose and both elements (Pt, Te). PbTe nanowires with a thickness of 10-16 nm and length of 400-600 nm were obtained in the presence of sucrose by injecting precursors into pentanediol solvent heated at 210 °C.

This templating approach is a promising way to synthesize diverse MC nanocrystals.. However, several factors determining the shape of the nanocrystals are mingled; the effect of the reduction rate of the precursors, the change of dipole according to the solvent in use, the stability and thermodynamic shape of the template in the synthetic condition, and so on. Hence, weak complexation between the source element and surfactant molecules may not large enough to generate stable templates. In this case, the use of the ionic surfactants can be a noticeable approach to produce anisotropic nanocrystals. The molecules containing ionic charges exist in the forms of vesicles or micelles when their concentration is over a critical value. Zhang and coworkers successfully synthesized Sb₂Te₃ nanobelts with a length of

(Review article) Submitted to Journal of Materials Chemistry C

several tens to hundred micrometers in the presence of an anionic surfactant, sodium bis(2-ethylhexyl)sulfosuccinate (AOT).⁸³ The pnictogen chalcogenides such as Bi₂Se₃, Bi₂Te₃, and Sb₂Te₃ have been known to preferentially form 2-D anisotropic crystal structures. However, the AOT molecules suppressed the growth along the *a*- or *b*- axes of the Sb₂Te₃ crystals and formed 1-D templates in which the growth of the crystal is confined. In the absence of AOT, irregular 2-D nanoplates were obtained under identical reaction conditions (Figure 2C). Ionic surfactant AOT has been also used for controlled synthesis and evolution of ZnS nanowires with diameters of 30 nm and lengths up to 2.5 μm.⁸⁴ Under specific AOT concentration, rod-like micelle of AOT acts as a template for the formation of ZnS nanowires. Zn-thiourea complexes may undergo slow decomposition to produce nanowires in the micelle templates. The same group has also produced ZnSe nanorods using the AOT micelle-template.⁸⁵

2-3. Axial growth by oriented attachment of nanocrystals

Classically, crystal has been considered to grow through i) spontaneous growth of nuclei by consecutive atomic addition or ii) dissolution of unstable small particles followed by reprecipitation onto more stable particles. The latter concept, the so-called Ostwald ripening process, is based on the solubility difference explained by the Gibbs-Thompson equation.^{86,87} The ripening process has been used to explain particle coarsening, but cannot fully explain the crystal growth behavior or the shape evolution.⁸⁸ Since Penn and Banfield first pioneered the oriented attachment as a new crystal growth mechanism,⁸⁹⁻⁹¹ several anisotropic growth in MC nanocrystals including CdTe, CdSe, CdS, PbSe, ZnS, and ZnSe, was explained.⁹²⁻⁹⁹ The oriented attachment refers to the direct self-organization of two particles into a single crystal caused by sharing a common crystallographic orientation. A large single crystal can

(Review article) Submitted to Journal of Materials Chemistry C

form through consecutive attachment of the small nanocrystals, which is different from the simple physical assembly of nanomaterials (which we will discuss later). Because the oriented attachment involves the assembly of nanocrystal building blocks, tailoring the way of attachment generates 1-D or 2-D structures with tunable properties. The driving force of this attachment is removal of the high-energy surfaces.⁸⁸ As particles approach one another in solution, they are assembled by additional energy between the surfactants (van der Waals interactions or dipole interactions). When the areal density of the capping agent on high energy surfaces is low or negligible, the surfaces meet each other and form long nanowires or nanobelts (Figure 3A). The defects such as misorientation and stacking faults are caused by the direct coagulation of the nanocrystals.^{100,101} After coalescence, the nanocrystals are thought to rearrange into a particle with identical crystallography, which raises the possibility of transformation into a large single crystal.^{102,103} The epitaxial rearrangement takes place through relaxation of the stress caused by misorientation at the attachment interface. However, the growth via the ripening process can occur simultaneously along orientated attachment. Theoretical and experimental studies have demonstrated that strong surface adsorption of capping ligands to a specific facet can hinder growth *via* the ripening process and facilitate pure oriented growth.¹⁰⁴⁻¹⁰⁶ Surface adsorption of anions was confirmed to slow down the ripening process because the anions were able to effectively restrict the dissolution of particles in solution.¹⁰⁷

Barnard and co-workers have demonstrated experimentally and theoretically, that the growth of CdSe nanowire is based on the oriented attachment rather than the continuous axial growth of nanorods (Figure 3A,B).¹⁰⁸ CdSe nanowires were synthesized by reacting cadmium acetate (CdAc₂) and selenourea in alkylamine solution (octylamine or oleylamine).

(Review article) Submitted to Journal of Materials Chemistry C

The synthesis involved three different growth stages: (i) the formation of initial nanocrystals, (ii) pre-wire aggregates with the configuration of a string of pearls, and (iii) structural transformation into single-crystal nanowires by thermally annealing the pre-wire aggregates. The pre-wire aggregates of which the thickness was similar to the diameter of nanocrystals could be interpreted as the key evidence of the oriented attachment. The oriented attachment was described with a thermodynamic model based on the Gibbs free energy. The total free energy G is described in terms of surface energy (γ) weighted by the factors f (such that $\sum_i f_i = 1$),

$$G = \Delta G_f^o + \frac{M}{\rho}(1-e)q \sum_i f_i \gamma_i \quad (1)$$

where ΔG_f^o is the standard free energy for the formation of bulk materials, M is molar mass, ρ is the density, q is the surface to volume ratio, and e is the volume dilation induced by the surface stresses σ_i . Details about the assumptions and simplification can be found in the reference.¹⁰⁸ According to the thermodynamic model and first-principles calculations, CdSe basically prefers to grow as short nanorods (aspect ratio: 2~4), indicating that the thermodynamic axial growth by consecutive atomic addition is not a dominant formation mechanism. Furthermore, kinetically-controlled axial growth alone was also proved not to be a dominant mechanism from the calculating the nucleation probability on the surfaces of the CdSe nanorods. The growth along $\langle 0001 \rangle$ direction *via* attachment of (0001) facets was the most, energetically, stable for the growth of CdSe nanowires.

Murray and co-workers synthesized nearly defect-free and highly uniform PbSe nanowires *via* the oriented attachment.⁹⁶ By tailoring reaction conditions, nanowires with diverse shapes were prepared such as straight, zigzag, helical, branched, and tapered

(Review article) Submitted to Journal of Materials Chemistry C

nanowires. Attachment of the {100}, {110}, or {111} facets was dependent on the chemical nature of the surfactant(s) used in the synthesis. In the presence of oleic acid only or the co-surfactants of oleic acid and n-tetradecylphosphonic acid (TDPA), nanocrystals assembled along the <100> axis, which was attributed to faster growth of the {111} facet than the {100} facet. Dipole moment along the <100> axis aligned the nanocrystals into nanowires. By replacing TDPA with long, aliphatic primary amines (dodecylamine, hexadecylamine (HDA), oleylamine, etc.), octahedral PbSe nanocrystals containing eight {111} facets formed preferentially due to selective blocking of the {111} facets by the binding of amines. Two types of zigzag nanowires were obtained depending on the attachment mode of the octahedron nanocrystals (Figure 3C,D). Helical nanowires formed when HDA and oleic acid were used as co-surfactants in the reaction medium of trioctylamine. Although PbSe crystals have a highly symmetric cubic structure, oriented attachment leads to successful synthesis of PbSe nanowires with the same crystal structure. The concept of dipole-dipole interactions as a driving force directing 1-D nanostructures has been proposed previously.⁹² In a subsequent study, Murray and co-workers reported the formation of PbSe/PbS core-shell heterostructures using the pre-formed PbSe nanowires as the building blocks.¹⁰⁹

Highly uniform nanocrystals can assemble to form superstructures with regular particle-particle distances. Self-assembly of the nanocrystals is governed by the attractive forces between the nanocrystals such as van der Waals, Coulombic, and dipole-dipole interactions. It is, currently, not under precise control whether the nanocrystals evolve into as superstructure by the physical self-assembly or grow to a single crystal by the oriented attachment. One of the key factors inducing the oriented attachment is to control the degree of passivation of target surfaces with organic surfactants. The others include solvent species, reaction temperature, and

(Review article) Submitted to Journal of Materials Chemistry C

concentration of nanocrystals. These interactions are often entangled, which makes it difficult to predict the product. Directed alignment of nanocrystals by external forces may help the oriented attachment process. Alignment of anisotropic nanoparticles is challenging because the interaction between anisotropic nanocrystals is direction-dependent, typically causing raft-like assembly with short range ordering.¹¹⁰⁻¹¹² In the presence of an external electric field, the MC nanorods are forced to align along the E-field.¹¹³⁻¹¹⁵ Russell and co-workers reported 'self-corralling' of CdSe nanorods under an applied electric field.¹¹⁶ The permanent dipole moment and inherent dielectric property of CdSe nanorods enhanced the alignment of nanorods along their long axis, parallel to the field. This alignment followed by epitaxial merging of the nanocrystals may enable the preparation of long single-crystal nanowires, which may allow the fabrication of aligned nanowires on a substrate.

3. Direct synthesis of 2-D chalcogenides

3-1. Intrinsically anisotropic 2-D growth

The shape of nanocrystals is dominated by the surface energy of the facets. For some MCs, 2-D shapes (nanoplates, nanodiscs, nanoflakes, nanosheets) are thermodynamically favored. Examples include the VA-VIA (GeS^{117} , GeSe^{117} , $\text{SnS}^{118,119}$, and SnSe^{120}), VIIIB-VIA ($\text{FeSe}^{121,122}$ and FeTe^{121}), IVB-VIA ($\text{TiQ}_2^{123-127}$, ZrQ_2 , and HfQ_2 , $Q = \text{S}, \text{Se}, \text{Te}^{123,124,126,128}$), VB-VIA ($\text{NbSe}_2^{126,129}$ and $\text{TaSe}_2^{126,130}$), VIB-VIA (MoS_2 , MoSe_2 , WS_2 , and $\text{WSe}_2^{131-133}$), and VA-VIA (Bi_2Se_3 , Bi_2Te_3 , and $\text{Sb}_2\text{Te}_3^{134-139}$). The structural preferences of the materials listed above have been confirmed by theoretical studies^{123,140} and vapor-phase synthesis¹⁴¹⁻¹⁴³ which has no surfactant-driven effect. The basic crystal structures of the metal chalcogenides are illustrated in Figure 4. They commonly assume the chemical

(Review article) Submitted to Journal of Materials Chemistry C

stoichiometries of MX_2 or M_2X_3 , where M is the metal and X is the chalcogen. In these structures, the M atoms are often 6-fold coordinated (octahedral distortion occurs when M is a VB or VIB metal atom, see Figure 4A, 4B, and 4D), while the X atoms are 3-fold coordinated (and also 6-fold for the case of M_2X_3 , see Figure 4C). Due to this unique structuring, the 3-fold coordinated X chalcogenide ions form localized pairs of electrons, frequently leading to the formation of van der Waals-bonded layered structures, exposing X-terminated layers. Metal chalcogenides may occasionally take on the MX stoichiometry and assume the distorted B1 structure (Figure 4E). These metal chalcogenides are characterized by a MX stoichiometric bi-layered structure, weakly bonded by van der Waals forces.

In solution-based synthesis, the use of surfactants to prevent aggregation of nanocrystals affects the thermodynamic preference and often generates unexpected structures. Jeong and co-workers recently reported a surfactant-free synthesis of Bi_2Te_3 and Bi_2Se_3 nanoflakes in a gram scale (Figure 5).¹³⁷ Formations of the 2-D nanocrystals in the absence of any surfactant are a strong evidence of the preference in the growth direction. The layered crystal structures of bismuth chalcogenides are illustrated in Figure 5A. Five successive atomic planes [$\text{Te}_1(\text{Se}_1)$ -Bi- $\text{Te}_2(\text{Se}_2)$ -Bi- $\text{Te}_1(\text{Se}_1)$] constitute one quintuple along the *c*-axis. Basically, bismuth chalcogenides preferentially grow into 2-D nanostructures because of weak Van der Waals interactions between adjacent $\text{Te}_1(\text{Se}_1)$ atomic planes that confer bismuth chalcogenides with an intrinsically anisotropic bonding nature. Because the top and bottom surfaces which consist of Te or Se atoms are not stabilized by surfactant, secondary nanoplates grew vertically, as shown in Figure 5B, D. Clear lattice fringes are visible in the HR-TEM images shown in Figure 5C (Bi_2Te_3) and Figure 5E (Bi_2Se_3) and the corresponding selected area electron diffraction (SAED) patterns demonstrate the single crystalline nature

(Review article) Submitted to Journal of Materials Chemistry C

of the nanoplates. The cross-section of the Bi_2Se_3 nanocrystals (Figure 5F) indicated 6 quintuples in thickness.

As long as the agglomeration is avoided or the aggregates are redispersed in solution by ultrasonic treatment, syntheses of the surfactant-free 2-D nanocrystals deserve further investigation. The layer-structured MCs have a high chance of success to be produced in the absence of surfactant. In most layered MCs, stacking of the atomic layer ends typically with the negatively-charged chalcogen atoms or the positively-charged metal atoms. Depending on the metal species and crystal structure, the uniform direction of the dipoles over the large basal planes provides better colloidal stability compared to the isotropic particles. Slight amount of inorganic chalcogenide ligands may greatly enhance the colloidal stability in polar solvents. Recently, Talapin and coworkers found that various molecular metal chalcogenide complexes (MCCs) such as $[\text{Sn}_2\text{S}_6]^{4-}$ and $[\text{Sn}_2\text{Se}_6]^{4-}$ could serve as convenient ligands for colloidal nanocrystals.¹⁴⁴ The surface inorganic surfactants greatly facilitate charge transport between individual nanocrystals.¹⁴⁵ The insulating organic surfactants of the typical 2-D nanocrystals diminish the unique properties of the 2-D nanocrystals such as high electron mobility and topological insulator. The inorganic ligands may allow the use of solution-based 2-D MCs as the semiconducting active layer for future electronic devices.

3-2. Surfactant-driven growth of 2-D nanocrystals

2-D growth of MCs that does not form a layered structure is a challenging subject because of the lack of a driving force for anisotropic growth. As in the case of 1-D growth, 2-D chalcogenide nanostructures can be obtained *via* surfactant-driven growth. In addition to lowering the surface energy of specific facets, surfactants can serve as soft templates for 2-D

(Review article) Submitted to Journal of Materials Chemistry C

nanocrystals. For example, the hexagonal wurtzite crystals normally grow isotropically into 0-D nanocrystals or into 1-D nanowires because the (0001) facet has the highest surface energy.¹⁴⁶ Recently, Hyeon and coworkers succeeded in preparing for lamellar-structured CdSe nanosheets as thin as 1.4 nm.¹⁴⁷ They employed a soft colloidal template method, in which organic layers consisting of cadmium chloride alkyl amine complexes functioned as 2-D templates to generate CdSe nanosheets. In a zinc blend cubic structure, polar axes along the $\langle 111 \rangle$ or $\langle 001 \rangle$ direction usually facilitate 1-D nanocrystal growth. Such dipole moments exist as the alternating layers of Cd and Se elements. Recently, Peng and coworkers synthesized CdSe 2-D quantum disks (1-3 nm in thickness) with a zinc blend crystal structure.¹⁴⁸ The 2-D CdSe quantum disks were synthesized by suppressing the growth along the polar axes. More specifically, basal planes with exposed layers of Cd ions were passivated by the negatively-charged carboxylate groups of the deprotonated fatty acid ligands, thereby neutralizing the dipole from the Cd ions. The close packing of the hydrocarbon chains of the fatty acids enabled the 2-D growth of CdSe nanocrystals. Various 2-D chalcogenide nanocrystals with non-layered structures have also been prepared using a similar synthetic route, including Cu_{2-x}Se nanodiscs,¹⁴⁹ In_2S_3 nanosheets,¹⁵⁰ and NiTe_2 nanoflakes.¹⁵¹ Dubertret and co-workers extended this strategy to synthesize CdSe/CdS and CdSe/CdZnS core-shell nanoplatelets.¹⁵² They first synthesized zinc blend CdSe nanoplatelets capped by carboxylate ligands,¹⁵³ and exchanged the ligand by dodecanethiol without disrupting the shape of the thin nanoplatelets. Layer-by-layer deposition of S and Cd enabled CdS coating with a controllable shell-thickness.

The organic surfactants can serve as carbon source during high temperature sintering. Very recently, carbon-coated FeS nanosheets with lateral lengths of 100~200 nm and

(Review article) Submitted to Journal of Materials Chemistry C

thicknesses of 4~10 nm have been prepared by surfactant-assisted solution-based synthesis.¹⁵⁴ The governing factor in controlling the morphology of the FeS nanocrystals was the shape of the micelle directed by 1-dodecanethiol (DDT). DDT was used as both the sulfur source and the surfactant to produce the 2-D FeS nanostructures. At a high concentration of DDT (molar ratio of Fe(acac)₃: DDT = 1:20), an Fe/DDT complex with a lamellar structure was formed in oleylanmine solution. The complex served as a soft template for the nucleation and growth of the FeS nanosheets. Spherical micelles of Fe/DDT complex were formed at a lower concentration of DDT (1:4), hence polycrystalline nanoparticles of FeS were produced. The hydrocarbon tails of DDT at the surfaces of the nanosheets turned into an amorphous carbon layer after sintering at 400°C under nitrogen atmosphere, resulting in the formation of carbon-coated FeS nanosheets.

Surfactants can tweak the growth condition for further fine-tuning 2-D grow regime. The effects of surfactant on the synthesis of ultrathin (~4 nm) Bi₂Se₃ nanodiscs and nanosheets have recently been investigated (Figure 6).¹³⁶ Bi₂Se₃ grew faster laterally and the basal planes were covered with negatively-charged Se atoms. When negatively charged surfactant, poly(acrylic acid) (PAA), was used, flower-like nanocrystals were obtained, which were similar to the surfactant-free products. In contrast, well-defined Bi₂Se₃ nanodiscs were obtained in the presence of a weakly-positive polymer surfactant, poly(vinylpyrrolidone) (PVP). The effect of surfactant charge on the 2-D shape formation was examined by mixing PVP and poly(ethylene imine) (PEI) as co-surfactants at different molar ratios: 10:0 (Figures 6A, B), 9:1 (Figure 6C), 8:2 (Figure 6D), 3:7 (Figure 6E), and 0:10 (Figure 6F). Binding of the positively-charged primary amines to the basal plane was much stronger than that of the tertiary amines in PVP. As the molar ratio of PEI increased,

(Review article) Submitted to Journal of Materials Chemistry C

the surface energy of the basal plane decreased, resulting in wide nanosheets with maintaining the thickness of the nanodiscs. This effect of surfactant charge was utilized to synthesize various 2-D MCs in the form of nanoplates and nanosheets. Sb_2Te_3 hexagonal nanoplates have been synthesized using both solvothermal¹³⁸ and hydrothermal approaches.¹³⁹

3.3 Formation of 2-D nanocrystals by lateral attachment

Although oriented attachment is a relatively new synthetic route, recent advances have proven that this strategy can be used to generate diverse 2-D MC nanocrystals.¹⁵⁵⁻¹⁶⁰ Preparation of the 2-D MC nanocrystals by the oriented attachment is relatively easier than the formation of 1-D nanocrystals by the same approach. The layer-structured MCs tend to expose chalcogen atoms on the top and bottom surface of the nanocrystals. Thus, passivation of those surfaces can be selectively achieved even with weakly-binding surfactants rather than the side surfaces. Growth into nanoplates or nanosheets is energetically favorable due to the reduced surface energy in the top and bottom surface. The side surfaces with a higher energy should be the active sites leading to the oriented attachment. This oriented attachment is expected to be more effective when the thickness of the nanocrystals is small and the binding of surfactants to the top and bottom surface is strong.

The time-dependent shape evolution during the lateral oriented attachment has been observed in several 2-D MC nanocrystal system.^{136,161} For example, single-crystalline SnSe nanosheets with a thickness of ~ 1 nm and a width of ~ 300 nm are synthesized by heating a mixture solution of SeO_2 , $\text{SnCl}_4 \cdot 5\text{H}_2\text{O}$, oleylamine, and 1,10-phenanthroline (Phen) at 120 °C followed aging at 260 °C for 30 min. The TEM studies visualized the growth process

(Review article) Submitted to Journal of Materials Chemistry C

which included nucleation of SnSe nanocrystals, aggregation of the nanocrystals into 2-D polycrystalline pseudo-sheets, transformation of the pseudo-sheets into single-crystalline nanosheets. This growth mechanism was consistent with the result demonstrated by Schaak and co-workers.¹²⁰ In their synthesis, 1,10-phenanthroline (Phen) played a vital role as a capping agent in determining the formation of SnSe nanosheets. In an early stage, Phen bound strongly to the basal plane of the newly formed SnSe nanosheets in cooperation with oleylamine, which suppressed the vertical growth of nanosheets. In the absence of Phen, 3-D SnSe nanoflowers were obtained because the stabilization of the basal plane by oleylamine molecules was insufficient to prevent the secondary growth of SnSe nanoplates on the basal planes.

Weller and co-workers utilized this strategy to synthesize PbS nanosheets from PbS nanoparticles¹⁵⁸ (Figure 7). They based their approach on the standard synthetic protocol used to prepare spherical PbS nanoparticles except the addition of chlorine-containing solvents such as 1,2-dichloroethane (DCE) in the oleic acid. In the absence of DCE solvent, PbS nanoparticles were prepared as illustrated in path A of Figure 7A. The chlorine-containing solvent modified the nucleation and growth rate during primary nanocrystal formation, which enabled survival of the highly reactive {110} surfaces in small nanocrystals during the early stage of the reaction. These tiny nanocrystals merged into 2-D nanosheets (paths B, C in Figure 7A) because the oleic acid self-assembled monolayer exclusively decreased the surface energy of the {100} facet. Growth of the nanosheet was monitored by UV-visible spectroscopy (Figure 7B) and HR-TEM (Figures 7C-F). During the early stage of the reaction, small and isolated quantum dots appeared in ~50 sec, as shown by the black spectrum in Figure 7B and the HR-TEM image in Figure 7C. As the reaction

(Review article) Submitted to Journal of Materials Chemistry C

evolved, the fluorescence band of the quantum dots decreased and an absorption peak corresponding to the nanosheet became visible as the oriented attachment of the primary nanocrystals proceeded.

4. Chemical transformation

Chemical transformation from a premade nanocrystal into another is a powerful route to obtain nanocrystals of diverse shapes and chemical compositions that cannot be obtained directly *via* the conventional synthetic approaches.^{162,163} The synthetic parameters to control the size, shape, and composition of the product nanocrystals are mingled in classical solution-based synthesis. Such multiple control factors interrupt fine-tuning of these variables. However, chemical transformation without any separate homogeneous nucleation allows systematic control over synthetic variables. Chemical transformation has been exploited as a new synthetic tool to generate 1-D and 2-D nanostructures with more complex morphological features than those obtained by direct synthesis, has been increasing its capacity to more arbitrary material systems.

Chemical transformation can be divided into three categories based on the underlying mechanism: alloy formation, ion exchange reaction, and galvanic replacement. Alloy formation is accomplished by mutual diffusion between atoms in premade solids and dissolved atoms in a reduced form. This strategy has been used to generate various MC nanostructures with diverse morphologies including nanoparticles (ZnS^{164} , CdS^{165} , PbS^{166}), nanotubes ($\text{Ag}_2\text{Se}^{167}$, $\text{Bi}_2\text{Te}_3^{168,169}$, CoTe_2^{170} , CoTe^{171}), nanowires ($\text{Ag}_2\text{Se}^{66,172}$, $\text{Ag}_2\text{Te}^{162,173}$, $\text{Bi}_2\text{Te}_3^{174}$, CdTe^{175} , $\text{PbTe}^{175,176}$, $\text{La}_2\text{Te}_3^{177}$), heterojunction double dumbbell $\text{Ag}_2\text{Te}-\text{Te}-\text{Ag}_2\text{Te}$ nanowires¹⁷⁸, and tri-wing Ag_2Te nanoribbons.¹⁷⁹ Chalcogens (Se, Te) are considered an ideal model system to prepare 1-D MCs because of their inherent tendency to grow into 1-D shapes and their high

(Review article) Submitted to Journal of Materials Chemistry C

reactivity with metal precursors. For example, Yu and co-workers have utilized Te nanowires as starting materials to prepare various 1-D metal telluride nanostructures (Bi_2Te_3 , CdTe, PbTe).^{174,175} The reaction processes were simple. Metal cations (Bi^{3+} , Cd^{2+} , Pb^{2+}) were reduced to their neutral elements (Bi, Cd, Pb) using hydrazine hydrate as a reducing agent. The neutral elements reacted with Te nanowires to form metal telluride nanowires. An example of the CdTe system is provided below:



Exchange of metal cations in the MC nanocrystals is a useful technique to diversify the accessible material species. Chalcogen anions, which are typically larger than metal cations, play a vital role as a frame preserving the structure of MC materials. Metal cations are mobile within their ionic structures, hence they can be replaced by other cations under appropriate conditions. Numerous research groups have used a solution phase approach to generate 1-D chalcogenide nanostructure *via* cation exchange reactions (CdTe^{162} , ZnTe^{162} , PbTe^{162} , $\text{CdSe}^{66,180}$ nanowires, PbS^{181} , ZnSe^{182} nanorods, PtTe_2^{162} nanotubes). Jeong and co-workers systematically demonstrated the chemical transformation of Te nanowires into Ag_2Te nanowires *via* a topotactic alloying process, and then subsequently conducted cation exchange using the Ag_2Te nanowires to generate diverse MC nanowires (CdTe, ZnTe, PbTe) and PtTe_2 nanotubes (Figure 8A).¹⁶² The as-synthesized Te nanowires with a single-crystal structure (Figure 8B) transformed spontaneously into single crystalline Ag_2Te nanowires with no drastic morphological changes (Figure 8C). This structural preservation can be explained by topotactic lattice matching between

(Review article) Submitted to Journal of Materials Chemistry C

trigonal Te and monoclinic Ag_2Te lattices, despite the large volume increase during transformation. Compared to Ag_2Te , other metal tellurides (CdTe , ZnTe , PbTe) are more soluble in polar solvents, which thermodynamically prohibits cation exchange to create other metal telluride nanowires from Ag_2Te (Figure 8D). Cation exchange was successfully accomplished by introducing a complexation ligand, tributylphosphine (TBP) which forms selective binding to silver. This example proves that careful choice of ligand can facilitate thermodynamically unfavorable exchanges by reversing the solubility order. Single crystallinity was preserved in the product metal chalcogenide nanowires due to the small volume change. In the transformation of CdTe into PtTe_2 , cation exchange was thermodynamically favorable due to the much lower solubility of PtTe_2 than CdTe . The exchange reaction caused a large volume decrease, resulting in the production of PtTe_2 nanotubes (Figure 8E,F).


This approach can be used to obtain 2-D nanocrystals with non-layered crystal structures. However, the chemical transformation of 2-D nanostructures remains largely unexplored. Cheon and coworkers reported the cation exchange reaction of layered TiS_2 nanodiscs to toroidal Cu_2S nanostructures (Figure 9A).¹⁸³ They first synthesized TiS_2 nanodiscs stabilized by oleylamines (Figure 9B-D). Addition of CuCl_2 to the nanodisc suspension and subsequent heating at 200°C for 30 min yielded Cu_2S toroids (Figure 9E-G). The resulting toroids with a hole in their center were highly symmetrical and double-convex. This transformation was driven by a regioselective edge reaction and ion diffusion through nanochannels between layers. The replacement of TiS_2 with Cu ions took place at the edge of the nanodiscs during the early reaction stages, and then subsequent ion diffusion through the interlayer in the TiS_2 nanodiscs resulted in the formation of heteroepitaxial TiS_2 - Cu_2S intermediates. As the replacement reaction proceeded, double-convex toroidal Cu_2S structures were generated.

(Review article) Submitted to Journal of Materials Chemistry C

In contrast to cation exchange, anion exchange causes considerable structural changes. Thus, more energy is required to overcome the kinetic barrier than that required for cation exchange. Anion exchange has rarely been explored compared to cation exchange reactions (CdS, CdSe, CdTe nanotubes).^{184,185} CdSe nanotubes with CdSe thorns on their surfaces were synthesized from Cd(OH)₂ nanowire bundles through an anion exchange reaction by Se.¹⁸⁵ Cd(OH)₂ nanowire bundles were synthesized first on a glass substrate in aqueous phase. Rapid exchange between OH⁻ and Se²⁻ as well as fast outward diffusion of Cd²⁺ in the aqueous solution resulted in the formation of tubular structures. Subsequent nucleation and growth of CdSe thorns on the nanotube surface proceeded until the Cd sources were consumed completely. The surface morphology of the nanotubes was dependent on the concentration of the Se ions. Nanotubes with clean and smooth surfaces formed without any thorn at high Se concentrations, which was attributed to uniform chemical reaction along the entire length of the nanowire bundles. Meanwhile, CdSe thorns on the nanotube were generated at low Se concentrations due to localized exchange reactions with Cd²⁺ ions diffusing out from the bundles. The anion exchange reaction was also observed in tin chalcogenide structures. SnSe nanosheets with a layered structure were transformed into SnTe nanosheets with a non-layered cubic structure, *via* solution phase anion exchange.¹⁸⁶ The bond energy difference between trioctylphosphine (TOP) as a chalcogen complex agent and chalcogen elements drove the exchange reaction. Because the P=Se bond is stronger than P=Te, TOP-Se is favorably formed in a reaction system that includes TOP-Te and SnSe, which drives the anion exchange reaction. SnTe nucleated with crystallographic alignment on SnSe nanosheets, which were consumed to yield porous SnTe nanosheets.

(Review article) Submitted to Journal of Materials Chemistry C

Galvanic replacement is considered a simple and effective way to prepare 1-D noble metal nanostructures.¹⁸⁷ The redox potential difference between elements leads to deposition of the more noble elements and dissolution of the less noble elements. Yang and co-workers utilized redox reactions to prepare Au, Ag, Pd, and Pt nanowires from LiMo_3Se_3 nanowires; the latter nanowires functioned as both templates and reducing agents.¹⁸⁸ Metal ions (AuCl_4^- , Ag^+ , PdCl_4^{2-} , PtCl_4^{2-}) in aqueous solution were reduced and subsequently deposited on the nanowire templates. Meanwhile, the nanowire template was oxidized and dissolved in aqueous solution. The following redox reaction between LiMo_3Se_3 and Au took place:



Pt nanotubes, Pt nanowires, and Pd nanowires a few nanometers in diameter have been successfully prepared by galvanic replacement using Te template nanowires.¹⁸⁹ In a typical synthesis, metal precursors (H_2PtCl_6 , PdCl_2) are added to an ethylene glycol suspension of Te nanowires at 50°C . Interestingly, the resulting products had different morphologies. In the case of the Pt nanotubes, some Pt nanoshells formed during the early stages of the reaction, which permitted the inter-diffusion of reactant ions across the shell. As galvanic replacement proceeded, the Pt nanoshells grew inwards at the cost of the Te templates. Based on stoichiometric relationships, this reaction involves the replacement of equivalent molar amounts of Pt by TeO_3^{2-} . The smaller molar volume of Pt ($\sim 9 \text{ cm}^3/\text{mol}$) than that of Te ($\sim 20 \text{ cm}^3/\text{mol}$) yielded a tubular structure. Furthermore, the molar volume of two moles of Pd ($\sim 18 \text{ cm}^3/2 \text{ mol}$) is similar to that of 1 mol of Te, which resulted in solid Pd nanowires. In 2-D nanostructures, Sb_2Te_3 hexagonal nanoplates were transformed into porous 3-D network-shaped Te plates.

(Review article) Submitted to Journal of Materials Chemistry C

Tartaric acid (TA) in the reaction solution aided the dissolution of Sb^{3+} ions from Sb_2Te_3 by forming $\text{Sb}(\text{TA})_x^{3+}$. Simultaneously, Te^{2-} ions were oxidized by O_2 to Te^0 ; the latter nucleated preferentially on the Sb_2Te_3 surfaces and acted as seeds for growth into porous 3-D Te plates. The Te structure was further transformed into porous Pt, Pd, and Au plates *via* galvanic replacement reactions in the presence of metal precursors (H_2PtCl_6 , PdCl_2 , HAuCl_4).¹⁹⁰

5. Applications

Interest in anisotropic 1-D and 2-D nanostructures has been steadily increasing due to their large surface area, quantum confinement effect, and superior optoelectrical or thermoelectrical properties. Anisotropic geometry and size reduction comparable to the Debye length can alter the optical, electric, and magnetic properties of the bulk counterparts. Focusing on MCs prepared in solution phases, the major interests for practical applications are thermoelectric power generation or electronic device cooling, high performance electrodes for batteries, nanocrystal-based photovoltaic devices, and photodetectors. Recently, new potential uses of the solution-based MC nanocrystals are being investigated, which include localized surface plasmon resonance (LSPR) and oxygen reduction reaction. MC thin films prepared by the vacuum process have shown the possibilities as new class of materials such as topological insulator, semiconductor with a high electron mobility, and superconductor. Although the organic surfactants indispensable in solution chemistry diminish such superior physical properties, solution-based approach has large room to achieve such physical properties. This section reviews recent advances in the practical applications of the anisotropic MC nanocrystals, and introduce briefly the potential applications.

5-1. Anodes of Li ion batteries

(Review article) Submitted to Journal of Materials Chemistry C

Graphite, which is conventionally used as the anode of lithium ion batteries (LIBs), has a small theoretical capacity of 372 mA h g^{-1} , which is too low to meet the current need in electronic devices. A number of 2-D metal disulfide (MS_2) nanocrystals such as MoS_2 , WS_2 , and SnS_2 are considered as promising alternatives to graphite.³⁰⁻³³ Their theoretical capacities are typically twice that of graphite and their layered structures (S-M-S) facilitate reversible intercalation of Li ions (Figure 10A). The synthesis of the metal disulfides has been actively developed during the last five years. Hydrothermal and solvothermal methods have been widely used for the synthesis of the 2-D MS nanocrystals and their hybrid composite materials with graphene or CNTs.^{33,191} These methods facilitate the large scale production of the high quality 2-D MS nanocrystals at low cost and in a short processing time. Thermal decomposition approach is promising to prepare the stoichiometric 2-D MS_2 nanocrystals with massive production for industrial needs.³² Free standing 2-D MoS_2 or WS_2 nanosheets were synthesized by decomposition of single-source precursors containing metal and sulfur sources in oleylamine which could cover the surfaces of the 2-D MS nanosheets. This oleylamine molecule functions as a protective layer for the oxidation and aggregation.¹⁹² Exfoliation of bulk materials in a liquid phase is a relatively new approach to prepare thin 2-D nanosheets.^{193,194} Ultrasonic treatment in organic solvents helped the exfoliation of the bulk materials. The surface energy of the bulk material in the solvent should be minimized to lower the energy requested for exfoliation, hence the surface energy of the solvent should be similar to that of the bulk material.

With thermal decomposition method, Chen and co-workers reported that LIBs with anode electrodes fabricated with 2-D SnS_2 nanoplates showed enhanced capacities.³² The discharge capacity was as high as 1311 mA h g^{-1} in the first cycle, which is close to the sum of the theoretical irreversible capacity (587 mA h g^{-1}) and maximum theoretical reversible capacity

(Review article) Submitted to Journal of Materials Chemistry C

(645 mA h g⁻¹). The average discharge capacity (583 mA h g⁻¹), close to 90% of the maximum theoretical reversible value, was stable and reversible up to 30 cycles. These excellent electrochemical properties were attributed to enhanced diffusion kinetics of lithium ions by the finite lateral size and open edges of the nanoplates. Recently, the same group synthesized ZrS₂ nanodiscs with tunable lateral dimensions (20, 35, and 60 nm) and systematically studied the effect of size on Li ion intercalation (Figures 10B, C).¹²⁸ The average discharge capacities of the 20, 35, and 60 nm ZrS₂ nanodiscs were 586, 527, and 433 mA h g⁻¹, respectively (Figure 10D). The 20 nm nanodiscs had a capacity 2.3 times greater than that of bulk ZrS₂ material (255 mA h g⁻¹). The retention capacities of the small nanoplates were ~80, ~77, and ~71% of the original capacities, respectively, while the retention of bulk ZrS₂ decreased continuously and was only 39% after 50 cycles (Figure 10E).

MS₂/carbon composite nanocrystals such as FeS/C,¹⁵⁴ SnS₂/graphene,¹⁹⁵ CoS₂/C,¹⁹⁶ MoS₂/graphene,^{191,197} MoS₂/CNTs,¹⁹⁸ and MoS₂/C have even more outstanding electrochemical properties than bare MS₂ nanoplates when they were used as anodes for LIBs.¹⁹⁹ Incorporation of carbon materials improves the charge current, effective surface area, and chemical tolerance of MS₂ nanocrystals. MoS₂/graphene composite nanosheets were synthesized by a one-step solution phase method.¹⁹¹ The first charge and discharge capacities of the MoS₂/graphene composites were 2200 and 1300 mA h g⁻¹, respectively, which are higher than those of bare MoS₂ and graphene. In addition, the cycling behavior exhibited a reversible capacity of 1290 mA h g⁻¹ for up to 50 cycles, while the reversible capacity of the bare MoS₂ electrode declined to 605 mA h g⁻¹ after 50 cycles. The high capacity and enhanced cycling stability of the composite were attributed to effective and rapid charge carrier transport back and forth from the MoS₂ layers to the graphene layer. Nanostructured SnS₂, although a promising anode material for LIBs, has the

(Review article) Submitted to Journal of Materials Chemistry C

drawbacks of large volume changes and accompanying decreases in capacity during electrochemical cycling.²⁰⁰ One solution to minimize the volume expansion is to distribute the tin-based materials evenly throughout another phase matrix. Zhi and co-workers prepared porous SnS₂/graphene composites through a two-step approach.¹⁹⁵ SnO₂ nanoparticles were formed on the surface of graphene nanosheets and then transformed into 2-D SnS₂ nanoplates by reaction with H₂S gas. The reversible capacity of the SnS₂/graphene composites was 650 mA h g⁻¹ after 50 cycles, which is much higher than that of bare SnS₂ nanoplates (277 mA h g⁻¹). These results suggest that graphene layer functions both as a buffer matrix and a conducting pathway to improve cycling durability.

5-2. Photodetectors

Photodetectors that contain nanocrystal solids are some of the simplest optoelectronic devices. The electrical conductivity of the nanocrystal solids changes under illumination due to the increase in density of mobile charge carriers.²⁰¹ Photodetectors require high sensitivity, selectivity, and stability. Many MCs has high absorption coefficient and good photostability, which is excellent characteristic of photodetecting materials. Various MC nanowires have been tested for the purpose because of their tunable electronic structure and band gap as well as the enhanced conduction of charge carriers in the length direction. Among various 1-D MC nanocrystals,²⁰²⁻²¹¹ silver sulfide (Ag₂S) is known as an excellent optical sensing material with a superior chemical stability. Li and co-workers reported a simple route to generate single crystalline Ag₂S nanowires that involves addition of sulfur powder into octadecylamine solution containing a Ag(NO₃)₃ precursor at 120°C (Figure 11).²¹¹ The nanowires had diameters ranging from 10 to 30 nm and lengths up to hundreds of micrometers. The photoelectric properties of the

(Review article) Submitted to Journal of Materials Chemistry C

individual Ag_2S nanowires were investigated under UV illumination. The current increased sharply from 2.3 to 594 pA upon UV illumination, but the current decreased to dark current within 1 s upon turn-off of the UV light. This time-resolved photocurrent indicates that the dynamic response was stable and reproducible during the on-and-off states (Figure 11B). Furthermore, the photocurrent increased as the pressure decreased without detectable changes in the dark current (Figure 11C). Golberg and co-workers demonstrated a fast response photodetector made of Sb_2Se_3 nanowires synthesized by a hydrothermal process.²⁰⁸ The current sharply increased from 4 pA (dark state) to 58 pA under 600 nm illumination. The rise and decay times were below 0.3 s. The rapid response time, high sensitivity of external quantum efficiency, good chemical stability, and good conduction along their length direction indicate that Sb_2Se_3 nanowires are promising candidates for photodetector devices.

Compared to conventional one-component (inorganic or organic) photodetectors, organic-inorganic hybrid photodetectors have unique features conferred by combination of the low ionization potential of organic molecules and the high electron affinity of inorganic components. These hybrid devices provide good physical flexibility and tunable functionality. Hybrid photodetectors with different combinations of organic and inorganic components have been fabricated.²¹²⁻²¹⁴ Hybrid photodetectors composed of conjugated polymer, poly(3-hexylthiophene) (P3HT), and CdSe nanowires were fabricated on a rigid SiO/Si substrate, a flexible PET substrate, and printing paper.²¹⁵ These devices showed an enhanced photocurrent and more rapid response and recovery times than photodetectors fabricated using only one component. This was attributed to the high hole-transport rate of the polymer P3HT, the high electrical conductivity of the CdSe nanowires, and the synergistic effect of absorption spectra in the visible range. The devices fabricated on flexible substrates exhibited good flexibility, folding

(Review article) Submitted to Journal of Materials Chemistry C

strength, excellent wavelength-dependent electrical stability, and rapid response to high-frequency light signals.

5-3. Thermoelectric devices

Solid-state power generation and cooling systems based on thermoelectric effects have received great attention.^{26,216-218} Thermoelectric devices composed of *p*- and *n*-type semiconductors can directly convert waste heat to electricity and *vice versa*. Bi₂Te₃ and its alloys with Se or Sb are some of the best thermoelectric materials at low temperatures (~80 °C) and PbTe-related materials are also strong candidates at slightly higher temperatures (~300 °C). Therefore, they have been widely used in low temperature power generation and small-scale cooling of electronic devices. The energy conversion efficiency of a thermoelectric device is evaluated by the dimensionless thermoelectric figure of merit (*ZT*), $ZT = S^2\sigma T/\kappa$, where *S*, σ , *T*, and κ are the Seebeck coefficient, electrical conductivity, temperature, and thermal conductivity, respectively. Recent theoretical and experimental advances have confirmed that introduction of nanoscale constituents increases the power factor ($S^2\sigma$) through a quantum confinement effect. The nano-sized grains reduce thermal conductivity (κ) more effectively than the reduction in electrical conductivity (σ). Furthermore, introduction of heterostructures in the nanocomposite can increase the Seebeck coefficient (*S*) due to a carrier filtering effect.^{137, 218-220} In this respect, better control over the grain size and shape of thermoelectric nanocrystals can be obtained using a bottom-up solution approach.²²¹⁻²²⁷

Wu and coworkers synthesized 1-D barbell-shaped Bi₂Te₃-Te-Bi₂Te₃ heterostructures consisting of a Te nanowire and Bi₂Te₃ plates set at the two ends of the nanowire (Figures 12 A, B).²²⁷ They used a two-step conversion process. Te nanowires were synthesized by reducing

(Review article) Submitted to Journal of Materials Chemistry C

tellurium dioxide with hydrazine hydrate solution. Once the formation of Te nanowires was completed, bismuth nitrate solution was hot-injected into the Te nanowire suspension at 160°C, which allowed the Te nanowires to be converted into the barbell-shaped Te-Bi₂Te₃ heterostructures. By keeping the concentration of Bi low, Bi deposited to the axial growth tips and suppressed the random deposition on the surfaces in the radial direction. The heterostructured composite was fabricated by hot pressing. ZT of the heterostructured composite was two orders higher than that of a pure Te nanowire composite (Figure 12B). The improved thermoelectric properties are mainly due to the enhanced Seebeck coefficient (S) caused by the carrier filtering and the decreased thermal conductivity (κ) caused by phonon scattering.

In terms of the grain boundaries to enhance the phonon scattering, thin 2-D nanostructures such as nanoplates or nanosheets are promising because their face-to-face packing can generate tremendous boundaries along the pathway of the phonons. Several groups have investigated 2-D Bi₂Te₃-related structures in the past decade.^{137, 221-224} Hyeon and coworkers synthesized Bi₂Te₃ nanoplates with a thickness of ~1 nm. They investigated the thermoelectric properties of bulk pellets prepared by spark plasma sintering (Figures 12C, D).²²³ Both the electrical (σ) and thermal (κ) conductivities increased as the sintering temperature was raised due to enhanced densification and grain growth during sintering. A maximum ZT value of 0.62 was achieved at 400 K from the nanoplate bulk pellets sintered at 250°C (Figure 12D).

Challenging issues associated with the use of nanocrystals for electric devices are removal of organic surfactant and thermal treatment without severely damaging the as-synthesized materials. A high sintering temperature (typically > 400°C) is required to decompose the organic surfactants. The insulating organic residue left behind by incomplete removal caused the material density of the pellet low and decreased the power factor of thermoelectric devices. Specifically,

(Review article) Submitted to Journal of Materials Chemistry C

MC nanocrystals can form multi-component alloys at high sintering temperatures, which is not desirable for high-performance, reliable devices. Jeong and coworkers demonstrated scalable, high-yield production of surfactant-free Bi_2Te_3 and Bi_2Se_3 nanoflakes.¹³⁷ Simple mixing of the nanoflake suspensions allowed homogeneous distribution of the two nanocrystal species, hence fine control of the chemical composition of the $\text{Bi}_2\text{Te}_3/\text{Bi}_2\text{Se}_3$ nanocomposites was possible. The ZT value was 0.7 at 400 K in a broad range of Bi_2Se_3 contents (10~15 wt%), which is highly advantageous in preparing reliable devices because the ZT value of three component alloy nanocrystals ($\text{Bi}_2\text{Te}_{3-x}\text{Se}_x$) is too sensitive to the atomic composition of Se (x).

5-4. Solar cells

MC semiconductors have been considered promising materials for the absorber layer and charge transport layer in thin film photovoltaic devices such as CdTe solar cells and $\text{Cl}(\text{G})\text{Se}$ solar cells. The chalcogenide films in the cells with a high power conversion efficiency (η) have been prepared by chemical bath deposition (CBD) or vapor phase depositions including evaporation, sputtering, sublimation, vapor transient deposition (VTD), and chemical vapor deposition (CVD).²²⁸⁻²³⁰ Recent advances in colloidal science have facilitated simple and eco-friendly synthetic approaches to produce various nanocrystals for use in photovoltaic devices. Use of the nanocrystal inks can significantly reduce production costs through the inexpensive deposition methods such as spraying, doctor blading, spin-casting, dip coating, and roll-to-roll printing. Although the films prepared from the MC nanocrystals has been considered inferior to the conventional films made by the vacuum processes, the solution-processed thin film solar cells has seen continuous improvement in the conversion efficiency.

(Review article) Submitted to Journal of Materials Chemistry C

Several research groups have devoted considerable effort toward synthesizing various colloidal nanocrystal inks.^{40-43,231,232} In contrast to quasi-spherical nanocrystals, 1-D nanostructures may enhance carrier mobility and device efficiency by reducing the frequency of electron hopping and electron-hole recombination in the absorber layer film.^{11,233,234} Korgel and co-workers demonstrated a photovoltaic device made of CuInSe₂ nanowires.²³⁴ The nanowires were 20 nm thick and several micrometers long. These were Indium-deficient with an average composition of Cu_{1.0}In_{0.6}Se_{2.0}. Free-standing fabric made of the nanowires was used to measure the photovoltaic response. Although the efficiency of the device was low ($\eta=0.1\%$) due to the low open circuit voltage (V_{oc}) and fill factor (FF), these results exhibited the feasibility of CuInSe₂ nanowires as the active layer for photovoltaic devices. The low power conversion efficiency originated from the voids and the random orientation of the nanowires, which reduced conductivity and prevented the carrier transport to their corresponding electrodes. The nanowire/quantum dot composite device enhanced transport connectivity. Conversion efficiency could potentially be improved by preparing defect-free nanowires and optimizing the alignment of the nanowires. Combining nanowires with spherical nanocrystals could also potentially improve device performance. Incorporating colloidal CdSe quantum dots into CdSe nanowires improved the conversion efficiency ($\eta=0.13\%$) photovoltaic performance.²³³ A photovoltaic device comprising CdSe quantum dots and CdTe nanorods as the active layer has also been reported.²³⁵ Due to the band alignment between the CdSe and CdTe nanocrystals, excited electrons transferred to the CdSe phase, while holes moved to the CdTe phase. Sintering of the nanorods enhanced the carrier mobility and the power conversion efficiency ($\eta=2.9\%$). Lin and coworkers utilized wurtzite-structured CdSe nanowires to fabricate a solar cell with the

(Review article) Submitted to Journal of Materials Chemistry C

configuration of ITO/ZnO/CdSe NWs/PEDOT:PSS/Pt. They reported a conversion efficiency of 3.6% for this configuration.²³⁶

Remarkable improvement of the power conversion efficiency has been achieved in the solar cells based on the I-III-VI₂ nanocrystals such as CuInSe₂ (CISE) and Cu(In_xGa_{1-x})Se₂ (CIGSe).²³⁷⁻²³⁹ Facile solution synthesis of CISE and related nanocrystal inks has been developed to prepare nanocrystal inks. In addition to 0-D nanocrystals,⁴⁰⁻⁴³ anisotropic 1-D and 2-D crystals in the forms of CuInSe₂ nanowires²⁴⁰, CuInSe₂ nanoplatelets,²⁴¹ Cu_{2-x}S_ySe_{1-y} nanowires,²⁴² CuIn_{1-x}Ga_xS₂ (CIGS) nanorods²⁴³, and Cu₂ZnSnS₄ (CZTS) nanorods²⁴⁴ have been synthesized by solvothermal method in the presence of the corresponding organometal precursors. Fine control of the chemical composition of the nanocrystals is the pre-requisite for a high performance device. Grain growth of the nanocrystals into high quality large crystals without incorporating micropores is another key factor. Agrawal and coworkers reported 5.5% efficiency using the CISE nanocrystal absorber layer after solid state densification of the layer during the selenization process.²³⁸ Very recently, the same group prepared a CIGS absorber layer film and partially exchanged the S anions by Se to form CIGSSe layer. They reported 12% conversion efficiency by the process.²³⁷ Jeong et al. achieved 8.2% efficiency with a CISE nanocrystal layer followed by high temperature densification.²³⁹ In spite of the abrupt increase of the conversion efficiency, the chemical composition of ternary or quaternary MCs has yet to be controlled. And the effect of nanocrystal shape has not been studied. As it comes to the densification of the nanocrystal layer, in-situ self-assembly of the 1-D or 2-D nanocrystals into superstructures during the coating process may facilitate the formation of a non-porous crystal layer. The organic surfactants obstruct densification of the nanocrystals and the vapors cause elemental contamination which is not controlled. The synthesis of surfactant-free multicomponent nanocrystals is in great need.²⁴⁵

(Review article) Submitted to Journal of Materials Chemistry C

Conjugated polymer-MC bulk heterojunction hybrid solar cells have been actively prepared during the last ten years.²⁴⁶⁻²⁴⁸ These hybrid systems take advantage of the flexible nature of polymers and the wider light absorption of inorganic materials than organic materials. Most polymer-based hybrid solar cells consist of an interpenetrated network of electron donor and acceptor phases with bulk heterojunction interfaces. Alivisatos and co-workers first demonstrated a CdSe nanorod/poly(3-hexylthiophene) (P3HT) hybrid solar cell created by spin casting a solution of CdSe nanorods in P3HT.²⁴⁹ Because CdSe and P3HT have complementary absorption spectra in the visible spectrum, devices composed of blended nanorod-polymer materials have a wide photocurrent spectrum from UV to 720 nm. A power conversion efficiency of 1.7% was obtained. Since then, conversion efficiency has been steadily increased by adding additives to enhance the crystallinity of P3HT²⁵⁰ or using different conjugated polymers.^{251,252} Conjugated polymers used widely in hybrid solar cells have relatively large band gaps (~1.9 eV), which limited absorption of the low energy solar spectrum from red to NIR. Low band gap polymers are promising candidates as an organic component for efficient light harvesting. Recently, CdSe tetrapods were combined with a low bandgap polymer (PCPDTBT), resulting in a power conversion efficiency of 3.13% under AM 1.5 illumination (Figure 13).²⁵³ MC nanocrystals have also been used as light-absorbing sensitizers in organic-TiO₂ heterojunction hybrid solar cells. Although the performance of these solid-state DSSCs is lower than that of liquid-electrolyte-based DSSCs, the recent progress reported by Gratzel and coworkers is promising. This group generated Sb₂S₃ nanoparticles on a porous TiO₂ layer by chemical bath deposition, and then the pores were filled with P3HT by spin-coating.²⁵⁴ The resultant hybrid cell showed a high conversion efficiency ($\eta = 5.13\%$) and highly stable photovoltaic performance in air without sealing the cell. Seok and coworkers further investigated

(Review article) Submitted to Journal of Materials Chemistry C

the same system to find the best conducting polymer for hole injection from the Sb_2S_3 sensitizer nanocrystals. They achieved $\eta=6.18\%$ at 1.5 AM 1.5 G radiation²⁵⁵ So far, spherical quantum dot sensitizers have been used attached to the surfaces of the porous metal oxide network. Anisotropic MCs such as nanorods and nanoplates deserve thorough investigation for the hole injection and chemical correlation with the polymer layer.

5-5. Other potential applications

Besides the aforementioned applications, the solution-based MC nanocrystals have recently been investigated as potential materials for localized surface plasmon resonance (LSPR) and oxygen reduction. The topological insulating property and superconductivity of layer-structured MCs are now active in physical studies. Although most current studies have been conducted with MCs prepared through the vacuum processes, a solution-based approach is still advantageous in the copious amount of production and structural control.

Surface plasmon is a light wave that evolves as a result of resonant interactions between the electromagnetic field of incident light and the plasma of electrons confined in a restricted dimension. Plasmons confined in nano-sized dimensions oscillate locally with a frequency known as the localized surface plasmon resonance (LSPR). The intensity and frequency of surface plasmon absorption bands are highly dependent on the characteristics of the material, such as the material species, size, shape, and additives on the surface.²⁵⁶ Resonant waves are sensitive to the dielectric properties of the surrounding and can be tuned by external electromagnetic waves,²⁵⁷ which enables the surface plasmon to be utilized for sensing,²⁵⁸ imaging,²⁵⁹ information processing,²⁶⁰ and optoelectronic purposes.²⁶¹ LSPRs have been extensively characterized with metal nanoparticles (Au, Ag, Pt, Cu etc.). Semiconductors have

(Review article) Submitted to Journal of Materials Chemistry C

an additional control variable in LSPR, which is tunability of the carrier concentration by doping. Copper chalcogenide nanocrystals has been the species studied the most so far.²⁶²⁻²⁶⁵ When Cu is slightly deficient with respect to S or Se, the nanocrystals contain a large number of free hole carriers in the valence band. The LSPR bands of CuS nanoparticles blue-shifted as the dopant concentration was increased. Recently, the effects of morphology on the LSPR response has been investigated in a Cu_{2-x}S nanodisk system.³⁷ In-plane and out-of-plane dipolar resonances were determined. The wavelengths, line shapes, and relative intensities of these plasmon bands were tuned by controlling the geometric aspect ratio of the disk or free carrier densities.

Most research on the cathodes of fuel cells has focused on Pt based-materials because of their excellent electrocatalytic performance. However, Pt based-materials show severe Pt-dependence,²⁶⁶ the kinetics of the oxygen reduction reaction (ORR) are slow,²⁶⁷ and there is CO deactivation.²⁶⁸ Various MCs are considered promising Pt-free ORR electrocatalysts because of their low cost, high tolerance to methanol and halide ions, and simple solution-based synthetic approach.²⁶⁹ For example, CoSe_2 -DETA (DETA=diethylenetriamine) hybrid nanobelts show good electrocatalytic performance with respect to ORR (onset potential of ca. 0.71 V) in acidic media. This good performance is ascribed to the large specific surface area and well-defined layered structure of CoSe_2 -DETA constructed with small DETA molecules.²⁷⁰ Long-term stability of the CoSe_2 -DETA still needs to be addressed before these can be used practically.²⁷⁰ The properties of MC cathodes can be improved by introducing other nanoparticles. For example, adding Fe_3O_4 nanoparticles to the CoSe_2 hybrid nanobelt catalyst resulted in an increase of onset potential and current density.²⁷⁰ Although the electrocatalytic activity of this catalyst is still lower than that of Pt-based catalysts, these hybrid MC systems deserve further investigation.

(Review article) Submitted to Journal of Materials Chemistry C

Topological insulator is an unconventional quantum phase of semiconducting or insulating matter that possesses a metallic conductivity on their surfaces.²⁷¹⁻²⁷³ Surface electronic states are spin polarized and protected by time-reversal symmetry. Significant efforts have been devoted to investigate the potential application of topological insulators in spintronics and quantum information processing.^{274,275} The number of publications on the layered MC materials, mainly V-VI (V=Bi, Sb; VI=Se, Te), has been increasing dramatically since these family of compounds were predicted to be three-dimensional topological insulators with unique surface states composed of a single Dirac cone at the Γ point.²⁷⁶⁻²⁷⁹ Currently, most studies on topological insulators have been conducted with chalcogenides obtained through vapor-phase synthesis. Fine control of the thickness, defects, and atomic states at the surfaces are challenging issues. And the synthesis of wide 2-D MC nanosheets (larger than at least a few micrometers) should be synthesized in a highly reproducible manner. And, the organic surfactants are serious obstacle of the solution-based MC nanocrystals in this area. Surfactant-free or inorganic surfactant systems during the preparation of MC nanocrystals create the clean surface and cause the negligible change of the surface electronic state. Solving these issues of synthesis is expected to draw advance in MC-based transistors.

Some MCs have recently emerged as a new class of superconductors that are electrically conductive without resistance below a certain temperature.²⁸⁰⁻²⁸² Iron chalcogenides (FeSe, FeTe) with a layered structure are considered high-superconducting transition temperature (T_c) superconductors.²⁸³ In addition, unconventional superconducting states are expected from the interaction between magnetism and superconductivity. Iron selenide (FeSe) has shown superconducting properties with a T_c of 8K.²⁸⁴ The T_c of FeSe has been improved up to ~ 14 K by doping Te²⁸⁵ and to over 30 K under high pressure with a dT_c/dP rate of ~ 9.1 K Gpa⁻¹.²⁸⁶

(Review article) Submitted to Journal of Materials Chemistry C

Sulfur-doped $\text{FeSe}_{1-x}\text{S}_x$ systems ($x = 0.2$) have a T_c of 15.5 K.²⁸⁷ Superconductivity at above 30 K was recently reported for $\text{K}_{0.8}\text{Fe}_2\text{Se}_2$ due to alkali intercalation between the FeSe layers.²⁸⁸ Despite recent advances in iron based-superconductors, their chemical complexity, local structure, and the relationship between magnetism and superconductivity need to be understood to clarify the mechanism.²⁸⁹ Unfortunately, no MCs synthesized by a solution approach have been reported to possess superconductivity. We attribute this to the difficulty in fine control of the chemical composition, defects, and surface states in solution-based approaches. It is a challenging subject to realize the superconductivity in the materials synthesized in a solution.

6. Challenges

This review summarized four different approaches to synthesize anisotropic MC nanocrystals; intrinsic growth into 1-D or 2-D nanostructure, crystal growth in organic templates, oriented attachment, and chemical transformation. A number of challenges should be addressed in the solution-based synthesis of the anisotropic MC nanocrystals to realize practical applications in industry. 1) through understanding on the surface energy decrease by surfactants, 2) adopting chemical transformations in the nucleation and growth of MC nanocrystals, 3) removal of organic surfactant, 4) kinetic study on the chemical transformation, 5) scale-up of production to meet the industrial need, and 6) eco-friendly synthesis.

In the synthesis utilizing organic surfactants, the decrease in surface energy depends on the number of binding and the binding energy between the surfactant molecules and the inorganic surfaces. Binding exclusively to a specific surface can facilitate the oriented attachment to form nanowires or nanoplates, but binding to all the surfaces helps self-assembly of the nanocrystals into superstructures. In the layer-structured materials, the number of crystal surfaces exposed to

(Review article) Submitted to Journal of Materials Chemistry C

the solution is limited (typically 2 surfaces) and the surfactant molecules adsorb on the top and bottom surfaces without binding to the side surface. The small flat nanocrystals go through the oriented attachment side-by-side and form larger nanoplates or nanosheets, hence oriented attachment in 2-D structures is natural as seen in many recent publications.^{136,158,161} On the contrary, the oriented attachment for generating 1-D nanomaterials requests delicate control of binding of surfactant molecules. The small building block nanocrystals to be used for this oriented attachment may be isotropic or shows small deviation from an isotropic shape. The number of surfaces of those nanocrystals is large and the atomic composition of the surfaces is not simple. To succeed in exclusive binding of surfactant molecules to a specific surface of the building block nanocrystals, we need precise quantitative information on the binding energy and the resulting surface energy decrease. Unfortunately, the information is yet to be understood because the binding is affected by as many reaction conditions as surfactant molecules, MC crystal structures, precursors, solvent, temperature, and pH, etc. Additional issue regarding to the surfactant is the assembly of the building block nanocrystals that are driven by interaction between the surfactant molecules. This surfactant interaction may induce self-assembly of the building blocks to form superstructures or cause the formation of templates such as micelles or vesicles consisting of the surfactant molecules and the MC elements. Currently, it is not clear which molecules can exist as the organometal complex and form such templates during the synthesis. Several anisotropic MCs have been prepared by the template-based synthesis, but the physics on the formation of such templates needs thorough investigation. The physics is more complicated than the micelle formation of pure organic molecules because the interaction between the inorganic elements incorporated in the organic molecules should be taken into consideration in the assembly of the complex molecules.

(Review article) Submitted to Journal of Materials Chemistry C

Another challenge in the synthesis of anisotropic MC nanocrystals is the lack of knowledge on how the chemical composition of the nanocrystals is determined. The theory of conventional nucleation and growth in a solution phase has been established under the assumption of stoichiometric supply of elemental sources. Concentration of a source element is determined by the reduction rate of the precursor. Finding a synthetic condition at which the reduction rates of the source molecules are the same is critical in the nanocrystal synthesis. It is not certain whether the elemental composition of a product nanocrystal is identical to the elemental concentration of the sources in the nucleation and growth steps. Because the equilibrium constants of the precursors are different and vary during the synthesis, it is almost impossible to maintain the concentration of the source elements stoichiometric. This hypothesis leads to the existence of chemical transformation taking place during the nanocrystal synthesis. In the MC nanocrystals, the *in-situ* chemical transformation is the alloy formation.¹⁶³ Taking an example with CdSe quantum dots, the nuclei might be Cd-rich or Se-rich or even pure Cd or Se, and then the other element forms alloy nanocrystals with the stoichiometric composition of 1:1. The alloy formation is spontaneous because the alloy composition is thermodynamically more stable. As long as initial nuclei do not grow into anisotropic structure, the overall shape of the final product will be 0-D and the precise facets will be determined by surface energy of the nanocrystal. Hence, the shape of 0-D nanocrystals is not very sensitive to reaction temperature. In the anisotropic MC nanocrystals, however, the fast anisotropic growth of one component can result in completely different shape of final product although the chemical composition of the nanocrystals is identical. For example, The shape of Bi₂Te₃ is strongly dependent on the reaction temperature, typically varying from 2-D nanoplates at high temperatures (~200 °C) to nanowires with lots of nanoplates growing in the radial direction at lower temperatures (~150 °C), or to

(Review article) Submitted to Journal of Materials Chemistry C

nanowires with multiple grains at much lower temperatures (~ 100 °C).²⁹⁰ At the high temperatures, the elemental fraction of the reduced Bi and Te is considered similar to 2:3, hence the stable stoichiometric 2-D nanoplates could be nucleated and grown. At the low temperatures, Te grows first into the nanorods or nanowires because of its intrinsic preference to 1-D structure, and then they were transformed into Bi_2Te_3 . Shape of the final product should depend on the length of pure Te nanowires before Bi started to form alloy. This result is an example showing the importance of understanding the reaction kinetics in the shape control of anisotropic nanocrystals. Unfortunately, the kinetics has not been studied thoroughly. For the ternary or quaternary nanocrystals, monitoring the reaction kinetics is a very difficult task at the current stage. Data on the basis of the reduction rate of the precursors in a variety of solution conditions should be accumulated by both experimental and theoretical studies.

Surfactants are critical in preparation of stable colloidal suspension and in the shape control of MC nanocrystals. However, the organic surfactants are problematic in practical uses. Many applications involve sintering of the MC nanocrystal films which aims at preparation of nanograined composites (thermoelectric devices) or simply at solution processing for cost-effective device fabrication (CI(G)S solar cell). The insulating organic layer plays as a barrier for charge injection and diminishes the expected properties from the pure MCs. The surfactant molecules change the surface electronic state of the individual MC nanocrystals, hence studies on the topological insulator and the high-mobility semiconductor have been conducted with the MC films obtained by the dry-processes. Nanocrystal thick films often exhibit weak mechanical strength caused by the low material density and micropores generated during the sintering the nanocrystal films. The problem regarding the use of surfactants can be tackled by the synthesis of surfactant-free nanocrystals, ligand exchange by volatile organic molecules, or the use of

(Review article) Submitted to Journal of Materials Chemistry C

inorganic surfactants. The surfactant-free synthesis is promising for the 2-D MC nanocrystals because their basal surfaces are covered with chalcogen atoms. The slightly negative charge of the chalcogen atoms can provide colloidal stability of the nanocrystals. Although the stability without surfactant is limited, the nanoplates can be redispersed in the solution by simple ultrasonication and formulated into nanocrystal inks. If the application is to produce thick films of MC crystals through thermal treatment, slurry-like ink is useful for the coating process. When the long-term stability is critical, the organic surfactant can be replaced by volatile molecules before being used. Employing inorganic ligands looks promising because such surfactants do not form the insulating barrier layer on the nanocrystal surfaces. The approach allows low-temperature thermal annealing which facilitates fabrication of flexible devices on polymer substrates. Furthermore, the inorganic surfactants are expected to maintain the high charge mobility and topological insulating nature of the 2-D MC nanocrystals. Recently, molecular metal chalcogenide complexes (MCCs) based on Sn or Cu metal element have been successfully employed as the inorganic surfactants.^{144,145} The other MCCs should be developed for diverse MC compositions.

The nanocrystals can be used as templates that can be chemically transformed into diverse anisotropic nanocrystals. However, thermodynamic aspects and the reaction kinetics of the chemical transformation are not well established yet. Solubility products of the reactant and the product MC nanocrystals are regarded to determine whether the reaction can proceed or not. When the product nanocrystal has a lower solubility in the solution than that of the reactant nanocrystal, the reaction takes place spontaneously. Otherwise, the chemical transformation requests addition of organic molecules which bind selectively to one element of the initial nanocrystal so that the solubility product of the initial nanocrystal can be increased. So far, the

(Review article) Submitted to Journal of Materials Chemistry C

solubility products of MC materials are rarely obtainable in most solution conditions. And, the binding energy between organic molecules and inorganic elements not tabulated thoroughly, hence selective bindings to adjust the solubility are not in data base. The chemical transformation involves material diffusion, rearrangement of crystal structure, and accumulation of mechanical stress. The reaction kinetics and mechanism to preserve the single crystallinity during the transformation should be explored further to crystal structure of the product nanocrystals.

Precise shape control and heterostructure design are the main advantages of the solution-based synthesis. When it comes to the amount of production, mechanical milling of bulk MCs into a fine powder is more profitable in the cost. Because most applications of the anisotropic MC nanocrystals use thick films sintered at high temperatures, the gram scale production is not sufficient. For example, one pellet specimen for thermoelectric test requests about 0.5 g of nanocrystals. The CIGS solar module or a set of LIB coin cell electrodes also need similar amount for each test. Recently, a few groups demonstrated a high yield synthesis in the scale of about 1.4 g/180 ml.¹³⁷ The synthesis should be scaled up to kg production per batch for industrial use. Obstacles to achieve the massive production are the relatively low solubility of the MC precursors, pressure build-up by the gaseous by-products during the synthesis, and inhomogeneous mixing in large scale reactors which is problematic in fast reaction systems. Continuous-flow reaction systems can be an alternative way to the batch systems. Fast mixing, easy temperature control, and small amount consumption of reagents are advantageous over the batch-type reaction. Recently, Seeberger and coworkers demonstrated a microfluidic system to produce isotropic quantum dots.²⁹¹ Jeon and coworkers reported the synthesis of ZnSe@ZnS core-shell quantum dots in a microfluidic reaction system.²⁹² Production of anisotropic nanomaterials has not been reported in the continuous reaction systems. Scale-up of the

(Review article) Submitted to Journal of Materials Chemistry C

continuous-flow reaction and the parallel integration of the set-up may facilitate massive production to meet the industrial need.

Nanocrystal inks are gaining tremendous attention to achieve cost-effective coating process. Eco-friendly synthesis becomes important. Currently, MC nanocrystals are synthesized mainly by the solvothermal approach in which the reaction is conducted at a high temperature (typically around 200°C) in organic solvents. The use of solvents with a high boiling temperature in the approach makes it difficult to recycle the solvents. Synthesis in water or volatile alcohols is desirable in terms of the environment friendliness. The reaction yield of 100% is also an important issue in the inorganic synthesis in order to prevent contamination by toxic elements. Especially the chemical transformation approach uses excess amount of a source material for exchange reaction when the transformation is not favored in energetics.¹⁶²

Acknowledgement. This work was supported by Samsung Research Funding Center of Samsung Electronics under Project Number SRFC-MA1301-07 and the Global Frontier R&D Program (2013-073298). Computational resource has been provided by the KISTI supercomputing center (KSC-2013-C3-040).

References

- 1 W. Shi, R. W. Hughes, S. J. Denholme and D. H. Gregory, *CrystEngComm*, 2010, **12**, 641.
- 2 C. Burda, X. Chen, R. Narayanan and M. A. El-Sayed, *Chem. Rev.*, 2005, **105**, 1025.
- 3 P. R. Sajanlal, T. S. Sreeprasad, A. K. Samal and T. Pradeep, *Nano Rev.*, 2011, **2**, 5883.
- 4 J. Zhu, B. S. Shim, M. D. Prima and N. A. Kotov, *J. Am. Chem. Soc.*, 2011, **133**, 7450.
- 5 D. Azulai, T. Belenkova, H. Gilon, Z. Barkay and G. Markovich, *Nano Lett.*, 2009, **9**,

(Review article) Submitted to Journal of Materials Chemistry C

- 4246.
- 6 J.-Y. Lee, S. T. Connor, Y. Cui and P. Peumans, *Nano Lett.*, 2008, **8**, 689.
- 7 S. De, P. E. Lyons, S. Sorel, E. M. Doherty, P. J. King, W. J. Blau, P. N. Nirmalraj, J. J. Boland, V. Scardaci, J. Joimel and J. N. Coleman, *ACS Nano*, 2009, **3**, 714.
- 8 A. S. Arico, P. Bruce, B. Scrosati, J.-M. Tarascon and W. V. Schalkwijk, *Nat. Mater.*, 2005, **4**, 366.
- 9 H. Li, Z. Wang, L. Chen and X. Huang, *Adv. Mater.*, 2009, **21**, 4593.
- 10 X. Wang, L. Zhi and K. Mullen, *Nano Lett.*, 2008, **8**, 323.
- 11 A. I. Hochbaum and P. Yang, *Chem. Rev.*, 2010, **110**, 527.
- 12 B. M. Kayes, H. A. Atwater and N. S. Lewis, *J. Appl. Phys.*, 2005, **97**, 114302.
- 13 T. C. Harman, P. J. Taylor, M. P. Walsh and B. E. LaForge, *Science*, 2002, **297**, 2229.
- 14 K. F. Hsu, S. Loo, F. Guo, W. Chen, J. S. Dyck, C. Uher, T. Hogan, E. K. Polychroniadis and M. G. Kanatzidis, *Science*, 2004, **303**, 818.
- 15 R. Venkatasubramanian, E. Siivola, T. Colpitts and B. O'Quinn, *Nature*, 2001, **413**, 597.
- 16 Z. L. Wang, *Adv. Funct. Mater.*, 2008, **18**, 3553.
- 17 X. Wang, J. Song and Z. L. Wang, *J. Mater. Chem.*, 2007, **17**, 711.
- 18 C.-H. Cho, C. O. Aspetti, M. E. Turk, J. M. Kikkawa, S.-W. Nam and R. Agarwal, *Nat. Mater.*, 2011, **10**, 669.
- 19 J. A. Schuller, E. S. Barnard, W. Cai, Y. C. Jun, J. S. White and M. L. Brongersma, *Nat. Mater.* 2010, **9**, 193.
- 20 E. C.-W. Ou, L. Hu, G. C. R. Raymond, O. K. Soo, J. Pan, Z. Zheng, Y. Park, D. Hecht, G. Irvin, P. Drzaic and G. Gruner, *ACS Nano*, 2009, **3**, 2258.
- 21 S. A. McDonald, G. Konstantatos, S. Zhang, P. W. Cyr, E. J. D. Klem, L. Levina and E. H. Sargent, *Nat. Mater.*, 2005, **4**, 138.
- 22 B. Lim, M. Jiang, P. H. C. Camargo, E. C. Cho, J. Tao, X. Lu, Y. Zhu and Y. Xia, *Science*, 2009, **324**, 1302.
- 23 D. R. Kauffman, D. C. Sorescu, D. P. Schofield, B. L. Allen, K. D. Jordan and A. Star, *Nano Lett.*, 2010, **10**, 958.
- 24 C. N. R. Rao, F. L. Deepark, G. Gundiah and A. Govindaraj, *Prog. Solid State Chem.*, 2003, **31**, 5.
- 25 X. Wang and Y. Li, *Inorg. Chem.*, 2006, **45**, 7522.

(Review article) Submitted to Journal of Materials Chemistry C

- 26 L.E. Bell, *Science*, 2008, **321**, 1457.
- 27 D. V. Talapin, J.-S. Lee, M. V. Kovalenko and E. V. Shevchenko, *Chem. Rev.*, 2010, **110**, 389.
- 28 H. Zhong, S. S. Lo, T. Mirkovic, Y. Li, Y. Ding, Y. Li and G. D. Scholes, *ACS Nano*, 2010, **4**, 5253.
- 29 M. He, F. Qiu and Z. Lin, *J. Phys. Chem. Lett.*, 2013, **4**, 1788.
- 30 G. Du, Z. Guo, S. Wang, R. Zeng, Z. Chen and H. Liu, *Chem. Commun.*, 2010, **46**, 1106.
- 31 H. Liu, D. Su, G. Wang and S. Z. Qiao, *J. Mater. Chem.*, 2012, **22**, 17437.
- 32 J.-W. Seo, J.-T. Jang, S.-W. Park, C. Kim, B. Park and J. Cheon, *Adv. Mater.*, 2008, **20**, 4269.
- 33 H. Hwang, H. Kim and J. Cho, *Nano Lett.*, 2011, **11**, 4826.
- 34 P. Chen, T.-Y. Xiao, H.-H. Li, J.-J. Yang, Z. Wang, H.-B. Yao and S.-H. Yu, *ACS Nano*, 2012, **6**, 712.
- 35 S. Liu, Z. Zhang, J. Bao, Y. Lan, W. Tu, M. Han and Z. Dai, *J. Phys. Chem. C*, 2013, **117**, 15164.
- 36 J. M. Luther, P. K. Jian, T. Ewers and A. P. Alivisatos, *Nat. Mater.*, 2011, **10**, 361.
- 37 S.-W. Hsu, K. On and A. R. Tao, *J. Am. Chem. Soc.*, 2011, **133**, 19072.
- 38 F. Xiu, L. He, Y. Wang, L. Cheng, L.-T. Chang, M. Lang, G. Huang, X. Kou, Y. Zhou, X. Jiang, Z. Chen, J. Zou, A. Shailos and K. L. Wang, *Nat. Nanotechnol.*, 2011, **6**, 216.
- 39 Z.-A. Ren and Z.-X. Zhao, *Adv. Mater.*, 2009, **21**, 4584.
- 40 C. Jiang, J.-S. Lee and D. V. Talapin, *J. Am. Chem. Soc.*, 2012, **134**, 5010.
- 41 M. G. Panthani, V. Akhavan, B. Goodfellow, J. P. Schmidtke, L. Dunn, A. Dodabalapur, P. F. Barbara and B. A. Korgel, *J. Am. Chem. Soc.*, 2008, **130**, 16770.
- 42 C. Steinhagen, M. G. Panthani, V. Akhavan, B. Goodfellow, B. Koo and B. A. Korgel, *J. Am. Chem. Soc.*, 2009, **131**, 12554.
- 43 Q. Guo, H. W. Hillhouse and R. Agrawal, *J. Am. Chem. Soc.*, 2009, **131**, 11672.
- 44 J. A. Venables, *Introduction to Surface and Thin Film Processes*, Cambridge University Press, Cambridge, 2000, p. 4.
- 45 B. Gates, B. Mayers, B. Cattle and Y. Xia, *Adv. Funct. Mater.*, 2002, **12**, 219.
- 46 B. Mayers and Y. Xia, *J. Mater. Chem.*, 2002, **12**, 1875.
- 47 S. Grimme, *J. Comp. Chem.*, 2006, **27**, 1787.

(Review article) Submitted to Journal of Materials Chemistry C

- 48 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865.
- 49 P. E. Blöchl, *Phys. Rev. B*, 1994, **50**, 17953.
- 50 X. Gao, T. Gao and L. Zhang, *J. Mater. Chem.*, 2003, **13**, 6.
- 51 L. Ren, H. Zhang, P. Tan, Y. Chen, Z. Zhang, Y. Chang, J. Xu, F. Yang and D. Yu, *J. Phys. Chem. B*, 2004, **108**, 4627.
- 52 Z. Liu, S. Li, Y. Yang, Z. Hu, S. Peng, J. Liang and Y. Qian, *New J. Chem.*, 2003, **27**, 1748.
- 53 X. Cao, Y. Xie, S. Zhang and F. Li, *Adv. Mater.*, 2004, **16**, 649.
- 54 B. Gates, Y. Yin and Y. Xia, *J. Am. Chem. Soc.*, 2000, **122**, 12582.
- 55 B. Zhang, W. Dai, X. Ye, W. Hou and Y. Xie, *J. Phys. Chem. B*, 2005, **109**, 22830.
- 56 S. Xiong, B. Xi, W. Wang, C. Wang, L. Fei, H. Zhou and Y. Qian, *Cryst. Growth Des.*, 2006, **6**, 1711.
- 57 M. Mo, J. Zeng, X. Liu, W. Yu, S. Zhang and Y. Qian, *Adv. Mater.*, 2002, **14**, 1658.
- 58 Q. Lu, F. Gao and S. Komarneni, *Adv. Mater.*, 2004, **16**, 1629.
- 59 Z. Liu, Z. Hu, J. Liang, S. Li, Y. Yang, S. Peng and Y. Qian, *Langmuir*, 2004, **20**, 214.
- 60 Z. Liu, Z. Hu, Q. Xie, B. Yang, J. Wu and Y. Qian, *J. Mater. Chem.*, 2003, **13**, 159.
- 61 B. Xi, S. Xiong, H. Fan, X. Wang and Y. Qian, *Cryst. Growth Des.*, 2007, **7**, 1185.
- 62 B. Zhang, W. Hou, X. Ye, S. Fu and Y. Xie, *Adv. Funct. Mater.*, 2007, **17**, 486.
- 63 Z.-H. Lin, Z. Yang and H.-T. Chang, *Cryst. Growth Des.*, 2008, **8**, 353.
- 64 J.-W. Liu, J.-H. Zhu, C.-L. Zhang, H.-W. Liang and S.-H. Yu, *J. Am. Chem. Soc.*, 2010, **132**, 8945.
- 65 D. Qin, J. Zhou, C. Luo, Y. Liu, L. Han and Y. Cao, *Nanotechnology*, 2006, **17**, 674.
- 66 U. Jeong, Y. Xia and Y. Yin, *Chem. Phys. Lett.*, 2005, **416**, 246.
- 67 H.-S. Qian, S.-H. Yu, J.-Y. Gong, L.-B. Luo and L.-F. Fei, *Langmuir*, 2006, **22**, 3830.
- 68 G. D. Moon, Y. Min, S. Ko, S.-W. Kim, D.-H. Ko and U. Jeong, *ACS Nano*, 2010, **4**, 7283.
- 69 U. Mizutani, *Hume-Rothery Rules for Structurally Complex Alloy Phases*, CRC Press, London, 2008.
- 70 Y. Wang, J. Chen, P. Wang, L. Chen, Y.-B. Chen and L.-M. Wu, *J. Phys. Chem. C*, 2009, **113**, 16009.
- 71 R. Malakooti, L. Cademartiri, Y. Akcakir, S. Petrov, A. Migliori and G. A. Ozin, *Adv. Mater.*, 2006, **18**, 2189.

(Review article) Submitted to Journal of Materials Chemistry C

- 72 H. Zhang, Y. Ji, X. Ma, J. Xu and D. Yang, *Nanotechnology*, 2003, **14**, 974.
- 73 Y. Yu, R. H. Wang, Q. Chen and L.-M. Peng, *J. Phys. Chem. B*, 2006, **110**, 13415.
- 74 J. Ma, Y. Wang, Y. Wang, Q. Chen, J. Lian and W. Zheng, *J. Phys. Chem. C*, 2009, **113**, 13588.
- 75 A. Puzder, A. J. Williamson, N. Zaitseva, G. Galli, L. Manna and A. P. Alivisatos, *Nano Lett.*, 2004, **4**, 2361.
- 76 L. Manna, L. W. Wang, R. Cingolani and A. P. Alivisatos, *J. Phys. Chem. B*, 2005, **109**, 6183.
- 77 L. Qu, Z. A. Peng and X. Peng, *Nano Lett.*, 2001, **1**, 333.
- 78 A. Nag, A. Hazarika, K. V. Shanavas, S. M. Sharma, I. Dasgupta and D. D. Sarma, *J. Phys. Chem. Lett.*, 2011, **2**, 706.
- 79 Z. Liu, D. Xu, J. Liang, J. Shen, S. Zhang and Y. Qian, *J. Phys. Chem. B*, 2005, **109**, 10699.
- 80 E. Lifshitz, M. Bashouti, V. Kloper, A. Kigel, M. S. Eisen and S. Berger, *Nano Lett.*, 2003, **3**, 857.
- 81 P. Xue, R. Lu, D. Li, M. Jin, C. Tan, C. Bao, Z. Wang and Y. Zhao, *Langmuir*, 2004, **20**, 11234.
- 82 Q. Yan, H. Chen, W. Zhou, H. H. Hng, F. Y. C. Boey and J. Ma, *Chem. Mater.*, 2008, **20**, 6298.
- 83 W. Shi, J. Yu, H. Wang and H. Zhang, *J. Am. Chem. Soc.*, 2006, **128**, 16490.
- 84 R. Lv, C. Cao and H. Zhu, *Mater. Res. Bull.*, 2004, **39**, 1517.
- 85 R. Lv, C. Cao, H. Zhai, D. Wang, S. Liu and H. Zhu, *Solid State Commun.* 2004, **130**, 241.
- 86 T. Sugimoto, *Adv. Colloid Interface Sci.*, 1987, **28**, 65.
- 87 J. W. Mullin, *Crystallization*, 3rd Ed, Butterworth-Heinemann, Stoneham, MA, 1997.
- 88 Q. Zhang, S.-J. Liu and S.-H. Yu, *J. Mater. Chem.*, 2009, **19**, 191.
- 89 R. L. Penn and J. F. Banfield, *Am. Mineral.*, 1998, **83**, 1077.
- 90 R. L. Penn and J. F. Banfield, *Science*, 1998, **281**, 969.
- 91 J. F. Banfield, S. A. Welch, H. Zhang, T. T. Ebert and R. L. Penn, *Science*, 2000, **289**, 751.
- 92 Z. Tang, N. A. Kotov and M. Giersig, *Science*, 2002, **297**, 237.
- 93 F. Jiang, J. Liu, Y. Li, L. Fan, Y. Ding and Y. Li, *Adv. Funct. Mater.*, 2012, **22**, 2402.
- 94 N. Pradhan, H. Xu and X. Peng, *Nano Lett.*, 2006, **6**, 720.

(Review article) Submitted to Journal of Materials Chemistry C

- 95 W.-K. Koh, A. C. Bartnik, F. W. Wise and C. B. Murray, *J. Am. Chem. Soc.*, 2010, **132**, 3909.
- 96 K.-S. Cho, D. V. Talapin, W. Gaschler and C. B. Murray, *J. Am. Chem. Soc.*, 2005, **127**, 7140.
- 97 P. D. Cozzoli, L. Manna, M. L. Curri, S. Kudera, C. Giannini, M. Striccoli and A. Agostiano, *Chem. Mater.*, 2005, **17**, 1296.
- 98 G. Zhu, S. Zhang, Z. Xu, J. Ma and X. Shen, *J. Am. Chem. Soc.*, 2011, **133**, 15605.
- 99 B. B. Srivastava, S. Jana, D. D. Sarma and N. Pradhan, *J. Phys. Chem. Lett.*, 2010, **1**, 1932.
- 100 D. Moldovan, V. Yamakov, D. Wolf and S. R. Phillpot, *Phys. Rev. Lett.*, 2002, **89**, 206101.
- 101 E. R. Leite, T. R. Giraldi, F. M. Pontes, E. Longo, A. Beltran and J. Andres, *Appl. Phys. Lett.*, 2003, **83**, 1566.
- 102 Z. Zhuang, J. Zhang, F. Huang, Y. Wang and Z. Lin, *Phys. Chem. Chem. Phys.*, 2009, **11**, 8516.
- 103 H. Zheng, R. K. Smith, Y.-W. Jun, C. Kisielowski, U. Dahmen and A. P. Alivisatos, *Science*, 2009, **324**, 1309.
- 104 F. Huang, H. Zhang and J. F. Banfield, *Nano Lett.*, 2003, **3**, 373.
- 105 J. Zhang, Z. Lin, Y. Lan, G. Ren, D. Chen, F. Huang and M. Hong, *J. Am. Chem. Soc.*, 2006, **128**, 12981.
- 106 J. Zhang, Y. Wang, J. Zheng, F. Huang, D. Chen, Y. Lan, G. Ren, Z. Lin and C. Wang, *J. Phys. Chem. B*, 2007, **111**, 1449.
- 107 Z. Hu, G. Oskam, R. L. Penn, N. Pesika and P. C. Searson, *J. Phys. Chem. B*, 2003, **107**, 3124.
- 108 A. S. Barnard, H. Xu, X. Li, N. Pradhan and X. Peng, *Nanotechnology*, 2006, **17**, 5707.
- 109 D. V. Talapin, H. Yu, E. V. Shevchenko, A. Lobo and C. B. Murray, *J. Phys. Chem. C*, 2007, **111**, 14049.
- 110 S. A. Claridge, A. W. Castleman, S. N. Khanna, C. B. Murray, A. Sen and P. S. Weiss, *ACS Nano*, 2009, **3**, 244.
- 111 K. Liu, N. Zhao and E. Kumacheva, *Chem. Soc. Rev.*, 2011, **40**, 656.
- 112 M. Zanella, G. Bertoni, I. R. Franchini, R. Brescia, D. Baranov and L. Manna, *Chem. Commun.*, 2011, **47**, 203.

(Review article) Submitted to Journal of Materials Chemistry C

- 113 S. Ahmed and K. M. Ryan, *Chem. Commun.*, 2009, 6421.
- 114 K. M. Ryan, A. Mastroianni, K. A. Stancil, H. Liu and A. P. Alivisatos, *Nano Lett.*, 2006, **6**, 1479.
- 115 D. Kelly, A. Singh, C. A. Barrett, C. O'sullivan, C. Coughlan, F. R. Laffir, C. O'Dwyer and K. M. Ryan, *Nanoscale*, 2011, **3**, 4580.
- 116 S. Gupta, Q. Zhang, T. Emrick and T. P. Russell, *Nano Lett.*, 2006, **6**, 2066.
- 117 D. D. Vaughn II, R. J. Patel, M. A. Hickner and R. E. Schaak, *J. Am. Chem. Soc.*, 2010, **132**, 15170.
- 118 J.-G. Kang, J.-G. Park and D.-W. Kim, *Electrochem. Commun.*, 2010, **12**, 307.
- 119 Y. Zhang, J. Lu, S. Shen, H. Xu and Q. Wang, *Chem. Commun.*, 2011, **47**, 5226.
- 120 D. D. Vaughn II, S.-I. In and R. E. Schaak, *ACS Nano*, 2011, **5**, 8852.
- 121 K. D. Oyler, X. Ke, I. T. Sines, P. Schiffer and R. E. Schaak, *Chem. Mater.*, 2009, **21**, 3655.
- 122 L. Chen, H. Zhan, X. Yang, Z. Sun, J. Zhang, D. Xu, C. Liang, M. Wu and J. Fang, *CrystEngComm*, 2010, **12**, 4386.
- 123 J. A. Wilson and A. D. Yoffe, *Adv. Phys.*, 1969, **18**, 193.
- 124 W. Jaegermann and H. Tributsch, *Prog. Surf. Sci.*, 1988, **29**, 1.
- 125 Y. Arnaud and M. Chevreton, *J. Solid. State. Chem.*, 1981, **39**, 230.
- 126 S. Jeong, D. Yoo, J.-T. Jang, M. Kim and J. Cheon, *J. Am. Chem. Soc.*, 2012, **134**, 18233.
- 127 V. V. Plashnitsa, F. Vietmeyer, N. Petchsang, P. Tongying, T. H. Kosel and M. Kuno, *J. Phys. Chem. Lett.*, 2012, **3**, 1554.
- 128 J.-T. Jang, S. Jeong, J.-W. Seo, M.-C. Kim, E. Sim, Y. Oh, S. Nam, B. Park and J. Cheon, *J. Am. Chem. Soc.*, 2011, **133**, 7636.
- 129 R. V. Coleman, B. Giambattista, P. K. Hansma, A. Johnson, W. W. McNairy and C. G. Slough, *Adv. Phys.*, 1988, **37**, 559.
- 130 R. H. Friend and D. Jerome, *J. Phys. C-Solid state Phys.*, 1979, **12**, 1441.
- 131 L. Rapoport, Y. Bilik, Y. Feldman, M. Homyonfer, S. R. Cohen and R. Tenne, *Nature*, 1997, **387**, 791.
- 132 B. Radisavljevic, A. Radenovic, J. Brivio, V. Giacometti and A. Kis, *Nat. Nanotechnol.*, 2011, **6**, 147.
- 133 C. Lee, Q. Li, W. Kalb, X.-Z. Liu, H. Berger, R. W. Carpick and J. Hone, *Science*, 2010,

(Review article) Submitted to Journal of Materials Chemistry C

- 328, 76.
- 134 J. Zhang, Z. Peng, A. Soni, Y. Zhao, Y. Xiong, B. Peng, J. Wang, M. S. Dresselhaus and Q. Xiong, *Nano Lett.*, 2011, **11**, 2407.
- 135 W. Lu, Y. Dong, Y. Chen, Z. L. Wang and J. Fang, *J. Am. Chem. Soc.*, 2005, **127**, 10112.
- 136 Y. Min, G. D. Moon, B. S. Kim, B. Lim, J.-S. Kim, C. Y. Kang and U. Jeong, *J. Am. Chem. Soc.*, 2012, **134**, 2872.
- 137 Y. Min, J. W. Roh, H. Yang, M. Park, S. I. Kim, S. Hwang, S. M. Lee, K. H. Lee and U. Jeong, *Adv. Mater.*, 2013, **25**, 1425.
- 138 W. Wang, B. Poudel, J. yang, D. Z. Wang and Z. F. Ren, *J. Am. Chem. Soc.*, 2005, **127**, 13792.
- 139 W. Shi, L. Zhou, S. Song, J. Yang and H. Zhang, *Adv. Mater.*, 2008, **20**, 1892.
- 140 F. Hulliger, *structural chemistry of layer-type phases*, ed. B. F. A. Levy, D. Reidel publishing Company, Dordrecht, Holland, 1976, ch. 4, vol. 5, p. 91.
- 141 Y. Takemura, H. Suto, N. Honda, K. Kakuno and K. Saito, *J. Appl. Phys.*, 1997, **81**, 5177.
- 142 X. J. Wu, Z. Z. Zhang, J. Y. Zhang, Z. G. Ju, B. H. Li, B. S. Li, C. X. Shan, D. X. Zhao, B. Yao and D. Z. Shen, *Thin Solid Films*, 2009, **516**, 6116.
- 143 M. A. Malik, M. Afzaal and P. O'Brien, *Chem. Rev.*, 2010, **110**, 4417.
- 144 M. V. Kovalenko, M. Scheele and D. V. Talapin, *Science*, 2009, **324**, 1417.
- 145 W. Liu, J.-S. Lee and D. V. Talapin, *J. Am. Chem. Soc.*, 2013, **135**, 1349.
- 146 X. Peng, L. Manna, W. Yang, J. Wickham, E. Scher, A. Kadavanich and A. P. Alivisatos, *Nature*, 2000, **404**, 59.
- 147 J. S. Son, X.-D. Wen, J. Joo, J. Chae, S.-I. Baek, K. Park, J. H. Kim, K. An, J. H. Yu, S. G. Kwon, S.-H. Choi, Z. Wang, Y.-W. Kim, Y. Kuk, R. Hoffmann and T. Hyeon, *Angew. Chem. Int. Ed.*, 2009, **48**, 6861.
- 148 Z. Li and X. Peng, *J. Am. Chem. Soc.*, 2011, **133**, 6578.
- 149 J. Choi, N. Kang, H. Y. Yang, H. J. Kim and S. U. Son, *Chem. Mater.*, 2010, **22**, 3586.
- 150 S. Acharya, M. Dutta, S. Sarkar, D. Basak, S. Chakraborty and N. Pradhan, *Chem. Mater.*, 2012, **24**, 1779.
- 151 L. Jiang, Y.-J. Zhu and J.-B. Cui, *J. Solid State. Chem.*, 2010, **183**, 2358.
- 152 B. Mahler, B. Nadal, C. Bouet, G. Patriarche and B. Dubertret, *J. Am. Chem. Soc.*, 2012, **134**, 18591.

(Review article) Submitted to Journal of Materials Chemistry C

- 153 S. Ithurria, G. Bousquet and B. Dubertret, *J. Am. Chem. Soc.*, 2011, **133**, 3070.
- 154 C. Xu, Y. Zeng, X. Rui, N. Xiao, J. Zhu, W. Zhang, J. Chen, W. Liu, H. Tan, H. H. Hng and Q. Yan, *ACS Nano*, 2012, **6**, 4713.
- 155 Z. Tang, Z. Zhang, Y. Wang, S. C. Glotzer and N. A. Kotov. *Science*, 2006, **314**, 274.
- 156 G. Zhang, W. Wang, X. Lu and X. Li, *Cryst. Growth Des.*, 2009, **9**, 145.
- 157 T. J. Zhu, X. Chen, X. Y. Meng, X. B. Zhao and J. He, *Cryst. Growth Des.*, 2010, **10**, 3727.
- 158 C. Schliehe, B. H. Juarez, M. Pelletier, S. Jander, D. Greshnykh, M. Nagel, A. Meyer, S. Foerster, A. Kornowski, C. Klinke and H. Weller, *Science*, 2010, **329**, 550.
- 159 Z. Wang, C. Schliehe, T. Wang, Y. Nagaoka, Y. C. Cao, W. A. Bassett, H. Wu, H. Fan and H. Weller, *J. Am. Chem. Soc.*, 2011, **133**, 14484.
- 160 J. S. Son, K. Park, S. G. Kwon, J. Yang, M. K. Choi, J. Kim, J. H. Yu, J. Joo and T. Hyeon, *Small*, 2012, **8**, 2394.
- 161 L. Li, Z. Chen, Y. Hu, X. Wang, T. Zhang, W. Chen and Q. Wang, *J. Am. Chem. Soc.*, 2013, **135**, 1213.
- 162 G. D. Moon, S. Ko, Y. Xia and U. Jeong, *ACS Nano*, 2010, **4**, 2307.
- 163 G. D. Moon, S. Ko, Y. Min, J. Zeng, Y. Xia and U. Jeong, *Nano Today*, 2011, **6**, 186.
- 164 H.-F. Shao, X.-F. Qian and Z.-K. Zhu, *J. Solid State Chem.*, 2005, **178**, 3522.
- 165 A. Cabot, R. K. Smith, Y. Yin, H. Zheng, B. M. Reinhard, H. Liu and A. P. Alivisatos, *ACS Nano*, 2008, **2**, 1452.
- 166 Y. Wang, L. Cai and Y. Xia, *Adv. Mater.*, 2005, **17**, 473.
- 167 H. Tan, S. Li and W. Y. Fan, *J. Phys. Chem. B*, 2006, **110**, 15812.
- 168 G. Zhang, Q. Yu, Z. Yao and X. Li, *Chem. Commun.*, 2009, 2317.
- 169 S. H. Kim and B. K. Park, *J. Appl. Phys.*, 2010, **108**, 102808.
- 170 J. Li, X. Tang, L. Song, Y. Zhu and Y. Qian, *J. Cryst. Growth*, 2009, **311**, 4467.
- 171 H. Fan, Y. Zhang, M. Zhang, X. Wang and Y. Qian, *Cryst. Growth Des.*, 2008, **8**, 2838.
- 172 B. Gates, B. Mayers, Y. Wu, Y. Sun, B. Cattle, P. Yang and Y. Xia, *Adv. Funct. Mater.*, 2002, **12**, 679.
- 173 A. K. Samal and T. Pradeep, *J. Phys. Chem. C*, 2009, **113**, 13539.
- 174 K. Wang, H.-W. Liang, W.-T. Yao and S.-H. Yu, *J. Mater. Chem.*, 2011, **21**, 15057.
- 175 H.-W. Liang, S. Liu, Q.-S. Wu and S.-H. Yu, *Inorg. Chem.*, 2009, **48**, 4927.

(Review article) Submitted to Journal of Materials Chemistry C

- 176 G. Tai, B. Zhou and W. Guo, *J. Phys. Chem. C*, 2008, **112**, 11314.
- 177 A. K. Samal and T. Pradeep, *J. Phys. Chem. C*, 2010, **114**, 5871.
- 178 A. Som and T. Pradeep, *Nanoscale*, 2012, **4**, 4537.
- 179 H. Zhu, J. Luo, H. Zhang, J. Liang, G. Rao, J. Li, G. Liu and Z. Du, *CrystEngComm*, 2012, **14**, 251.
- 180 U. Jeong, P. H. C. Camargo, Y. H. Lee and Y. Xia, *J. Mater. Chem.*, 2006, **16**, 3893.
- 181 J. M. Luther, H. Zheng, B. Sadtler and A. P. Alivisatos, *J. Am. Chem. Soc.*, 2009, **131**, 16851.
- 182 H. Li, M. Zanella, A. Genovese, M. Povia, A. Falqui, C. Giannini and L. Manna, *Nano Lett.*, 2011, **11**, 4964.
- 183 S. Jeong, J. H. Han, J.-T. Jang, J.-W. Seo, J.-G. Kim and J. Cheon, *J. Am. Chem. Soc.*, 2011, **133**, 14500.
- 184 V. R. Shinde, T. P. Gujar, T. Noda, D. Fujita, C. D. Lokhande and O.-S. Joo, *J. Phys. Chem. C*, 2009, **113**, 14179.
- 185 J. W. Kim, H.-S. Shim, S. Ko, U. Jeong, C.-L. Lee and W. B. Kim, *J. Mater. Chem.*, 2012, **22**, 20889.
- 186 I. T. Sines, D. D. Vaughn II, A. J. Biacchi, C. E. Kingsley, E. J. Popczun and R. E. Schaak, *Chem. Mater.*, 2012, **24**, 3088.
- 187 M. Mohl, A. Kumar, A. L. M. Reddy, A. Kuhovecz, Z. Konya, I. Kiricsi, R. Vajtai and P. M. Ajayan, *J. Phys. Chem. C*, 2010, **114**, 389.
- 188 J. H. Song, Y. Wu, B. Messer, H. Kind and P. Yang, *J. Am. Chem. Soc.*, 2001, **123**, 10397
- 189 H.-W. Liang, S. Liu, J.-Y. Gong, S.-B. Wang, L. Wang and S.-H. Yu, *Adv. Mater.*, 2009, **21**, 1850.
- 190 H. Zhang, H. Wang, Y. Xu, S. Zhuo, Y. Yu and B. Zhang, *Angew. Chem. Int. Ed.*, 2012, **51**, 1459.
- 191 K. Chang and W. Chen, *Chem. Commun.* 2011, **47**, 4252.
- 192 C. Altavilla, M. Sarno and P. Ciambelli, *Chem. Mater.*, 2011, **23**, 3879.
- 193 J. N. Coleman, M. Lotya, A. O'Neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, I. V. Shvets, S. K. Arora, G. Stanton, H.-Y. Kim, K. Lee, G. T. Kim, G. S. Duesberg, T. Hallam, J. J. Boland, J. J. Wang, J. F. Donegan, J. C. Grunlan, G. Moriarty, A. Shmeliov, R. J. Nicholls, J. M. Perkins, E. M. Grievson, K. Theuwissen, D.

(Review article) Submitted to Journal of Materials Chemistry C

- W. McComb, P. D. Nellist and V. Nicolosi, *Science*, 2011, **331**, 568.
- 194 G. Cunningham, M. Lotya, C. S. Cucinotta, S. Sanvito, S. D. Bergin, R. Menzel, M. S. P. Shaffer and J. N. Coleman, *ACS Nano*, 2012, **6**, 3468.
- 195 B. Luo, Y. Fang, B. Wang, J. Zhou, H. Song and L. Zhi, *Energy Environ. Sci.* 2012, **5**, 5226.
- 196 W. Luo, Y. Xie, C. Wu and F. Zheng, *Nanotechnology*, 2008, **19**, 075602.
- 197 K. Chang and W. Chen, *ACS Nano*, 2011, **5**, 4720.
- 198 S. Ding, J. S. Chen and X. W. Lou, *Chem. Eur. J.*, 2011, **17**, 13142.
- 199 S. K. Das, R. Mallavajula, N. Jayaprakash and L. A. Archer, *J. Mater. Chem.*, 2012, **22**, 12988.
- 200 Y. Idota, T. Kubota, A. Matsufuji, Y. Maekawa and T. Miyasaka, *Science*, 1997, **276**, 1395.
- 201 T. Zhai, L. Li, X. Wang, X. Fang, Y. Bando and D. Golberg, *Adv. Funct. Mater.*, 2010, **20**, 4233.
- 202 X. Fang, Y. Bando, M. Liao, U. K. Gautam, C. Zhi, B. Dierre, B. Liu, T. Zhai, T. Sekiguchi, Y. Koide and D. Golberg, *Adv. Mater.*, 2009, **21**, 2034.
- 203 T. Zhai, X. Fang, M. Liao, X. Xu, L. Li, B. Liu, Y. Koide, Y. Ma, J. Yao, Y. Bando and D. Golberg, *ACS Nano*, 2010, **4**, 1596.
- 204 J.-J. Wang, F.-F. Cao, L. Jiang, Y.-G. Guo, W.-P. Hu and L.-J. Wan, *J. Am. Chem. Soc.*, 2009, **131**, 15602.
- 205 J. S. Jie, W. J. Zhang, Y. Jiang, X. M. Meng, Y. Q. Li and S. T. Lee, *Nano Lett.*, 2006, **6**, 1887.
- 206 R. Zhou, H.-C. Chang, V. Protasenko, M. Kuno, A. K. Singh, D. Jena and H. Xing, *J. Appl. Phys.*, 2007, **101**, 073704.
- 207 X. Fang, S. Xiong, T. Zhai, Y. Bando, M. Liao, U. K. Gautam, Y. Koide, X. Zhang, Y. Qian and D. Golberg, *Adv. Mater.*, 2009, **21**, 5016.
- 208 T. Zhai, M. Ye, L. Li, X. Fang, M. Liao, Y. Li, Y. Koide, Y. Bando and D. Golberg, *Adv. Mater.*, 2010, **22**, 4530.
- 209 G. Konstantatos, L. Levina, J. Tang and E. H. Sargent, *Nano Lett.*, 2008, **8**, 4002.
- 210 G. Xiao, Q. Dong, Y. Wang, Y. Sui, J. Ning, Z. Liu, W. Tian, B. Liu, G. Zou and B. Zou, *RSC Advances*, 2012, **2**, 234.
- 211 D. Wang, C. Hao, W. Zheng, Q. Peng, T. Wang, Z. Liao, D. Yu and Y. Li, *Adv. Mater.*,

(Review article) Submitted to Journal of Materials Chemistry C

- 2008, **20**, 2628.
- 212 J.-J. Wang, Y.-Q. Wang, F.-F. Cao, Y.-G. Guo and L.-J. Wan, *J. Am. Chem. Soc.*, 2010, **132**, 12218.
- 213 J.-J. Wang, J.-S. Hu, Y.-G. Guo and L.-J. Wan, *NPG Asia Mater.*, 2012, **4**, e2.
- 214 D.-J. Xue, J.-J. Wang, Y.-Q. Wang, S. Xin and Y.-G. Guo, *Adv. Mater.*, 2011, **23**, 3704.
- 215 X. Wang, W. Song, B. Liu, G. Chen, D. Chen, C. Zhou and G. Shen, *Adv. Funct. Mater.*, 2013, **23**, 1202.
- 216 B. C. Sales, *Science*, 2002, **295**, 1248.
- 217 M. S. Dresselhaus, G. Chen, M. Y. Tang, R. G. Yang, H. Lee, D. Z. Wang, Z. F. Ren, J. P. Fleurial and P. Gogna, *Adv. Mater.*, 2007, **19**, 1043.
- 218 G. J. Snyder and E. S. Toberer, *Nat. Mater.*, 2008, **7**, 105.
- 219 S. I. Kim, K. Ahn, D.-H. Yeon, S. Hwang, H.-S. Kim, S. M. Lee and K. H. Lee, *Appl. Phys. Express*, 2011, **4**, 091801
- 220 D.-K. Ko, Y. Kang and C. B. Murray, *Nano Lett.*, 2011, **11**, 2841.
- 221 M. Scheele, N. Oeschler, I. Veremchuk, K.-G. Reinsberg, A.-M. Kreuziger, A. Kornowski, J. Broekaert, C. Klinke and H. Weller, *ACS Nano*, 2010, **4**, 4283.
- 222 A. Soni, Z. Yanyuan, Y. Ligen, M. K. K. Aik, M. S. Dresselhaus and Q. Xiong, *Nano Lett.*, 2012, **12**, 1203.
- 223 J. S. Son, M. K. Choi, M.-K. Han, K. Park, J.-Y. Kim, S. J. Lim, M. Oh, Y. Kuk, C. Park, S.-J. Kim and T. Hyeon, *Nano Lett.*, 2012, **12**, 640.
- 224 R. J. Mehta, Y. Zhang, C. Karthik, B. Singh, R. W. Siegel, T. Borca-Tasciuc and G. Ramanath, *Nat. Mater.*, 2012, **11**, 233.
- 225 G. Zhang, B. Kirk, L. A. Jauregui, H. Yang, X. Xu, Y. P. Chen and Y. Wu, *Nano Lett.*, 2012, **12**, 56.
- 226 W. Liang, O. Rabin, A. I. Hochbaum, M. Fardy, M. Zhang and P. Yang, *Nano Res.*, 2009, **2**, 394.
- 227 G. Zhang, H. Fang, H. Yang, L. A. Jauregui, Y. P. Chen and Y. Wu, *Nano Lett.*, 2012, **12**, 3627.
- 228 X. Z. Wu, *Solar Energy*, 2004, **77**, 803.
- 229 A. Romeo, M. Terheggen, D. Abou-Ras, D. L. Batzner, F.-J. Haug, M. Kalin, D. Rudmann and A. N. Tiwari, *Prog. Photovoltaics*, 2004, **12**, 93.

(Review article) Submitted to Journal of Materials Chemistry C

- 230 M. Kemell, M. Ritala and M. Leskela, *Crit. Rev. Solid State Mater. Sci.*, 2005, **30**, 1.
- 231 B. D. Weil, S.T. Connor and Y. Cui, *J. Am. Chem. Soc.*, 2010, **132**, 6642.
- 232 J. Puthussery, S. Seefeld, N. Berry, M. Gibbs and M. Law, *J. Am. Chem. Soc.*, 2011, **133**, 716.
- 233 Y. Yu, P. V. Kamat and M. Kuno, *Adv. Funct. Mater.*, 2010, **20**, 1464.
- 234 C. Steinhagen, V. A. Akhavan, B. W. Goodfellow, M. G. Panthani, J. T. Harris, V. C. Holmberg and B. A. Korgel, *ACS Appl. Mater. Interface*, 2011, **3**, 1781.
- 235 I. Gur, N. A. Fromer, M. L. Geier and A. P. Alivisatos, *Science*, 2005, **310**, 462.
- 236 Z. Feng, Q. Zhang, L. Lin, H. Guo, J. Zhou and Z. Lin, *Chem. Mater.*, 2010, **22**, 2705.
- 237 Q. Guo, G. M. Ford, R. Agrawal and H. W. Hillhouse, *Prog. Photovoltaics*, 2013, **21**, 64.
- 238 Q. Guo, G. M. Ford, H. W. Hillhouse and R. Agrawal, *Nano Lett.*, 2009, **9**, 3060.
- 239 S. Jeong, B.-S. Lee, S. Ahn, K. Yoon, Y.-H. Seo, Y. Choi and B.-H. Ryu, *Energy Environ. Sci.*, 2012, **5**, 7539.
- 240 A. J. Wooten, D. J. Werder, D. J. Williams, J. L. Casson and J. A. Hollingsworth, *J. Am. Chem. Soc.*, 2009, **131**, 16177.
- 241 W. Bi, M. Zhou, Z. Ma, H. Zhang, J. Yu and Y. Xie, *Chem. Commun.*, 2012, **48**, 9162.
- 242 J. Xu, Y.-B. Tang, X. Chen, C.-Y. Luan, W.-F. Zhang, J. A. Zapien, W.-J. Zhang, H.-L. Kwong, X.-M. Meng, S.-T. Lee and C.-S. Lee, *Adv. Funct. Mater.*, 2010, **20**, 4190.
- 243 A. Singh, C. Coughlan, F. Laffir and K. M. Ryan, *ACS Nano*, 2012, **6**, 6977.
- 244 A. Singh, H. Geaney, F. Laffir and K. M. Ryan, *J. Am. Chem. Soc.*, 2012, **134**, 2910.
- 245 Y. Min, G. D. Moon, J. Park, M. Park and U. Jeong, *Nanotechnology*, 2011, **22**, 465604.
- 246 T. Xu and Q. Qiao, *Energy Environ. Sci.*, 2011, **4**, 2700.
- 247 M. D. McGehee, *MRS Bull.*, 2009, **34**, 95.
- 248 X. Fan, M. Zhang, X. Wang, F. Yang and X. Meng, *J. Mater. Chem. A*, 2013, **1**, 8694.
- 249 W. U. Huynh, J. J. Dittmer and A. P. Alivisatos, *Science*, 2002, **295**, 2425.
- 250 Y. Wu and G. Zhang, *Nano Lett.*, 2010, **10**, 1628.
- 251 B. Sun, H. J. Snaith, A. S. Dhoot, S. Westenhoff and N. C. Greenham, *Appl. Phys.*, 2005, **97**, 014914.
- 252 P. Wang, A. Abrusci, H. M. P. Wong, M. Svensson, M. R. Andersson and N. C. Greenham, *Nano Lett.*, 2006, **6**, 1789.
- 253 S. Dayal, N. Kopidakis, D. C. Olson, D. S. Ginley and G. Rumbles, *Nano Lett.*, 2010, **10**,

(Review article) Submitted to Journal of Materials Chemistry C

- 239.
- 254 J. A. Chang, J. H. Rhee, S. H. Im, Y. H. Lee, H.-J. Kim, S. I. Seok, M. K. Nazeeruddin and M. Gratzel, *Nano Lett.*, 2010, **10**, 2609.
- 255 S.-H. Im, C.-S. Lim, J. A. Chang, Y. H. Lee, N. Maiti, H.-J. Kim, Md. K. Nazeeruddin, M. Gratzel and S. I. Seok, *Nano Lett.*, 2011, **11**, 4789.
- 256 E. Hutter and J. H. Fendler, *Adv. Mater.*, 2004, **16**, 1685.
- 257 J. Homola, *Anal. Bioanal. Chem.*, 2003, **377**, 528.
- 258 J. Homola, *Chem. Rev.*, 2008, **108**, 462.
- 259 B. P. Nelson, T. E. Grimsrud, M. R. Lies, R. M. Goodman and R. M. Corn, *Anal. Chem.*, 2001, **73**, 1.
- 260 M. L. Brongersma, J. W. Hartman and H. A. Atwater, *Phys. Rev. B*, 2000, **62**, 16356.
- 261 E. Ozbay, *Science*, 2006, **311**, 189.
- 262 S.-W. Hsu, W. Bryks and A. R. Tao, *Chem. Mater.*, 2012, **24**, 3765.
- 263 J. S. Niezgodna, M. A. Harrison, J. R. McBride and S. J. Rosenthal, *Chem. Mater.*, 2012, **24**, 3294.
- 264 Y. Zhao, H. Pan, Y. Lou, X. Qiu, J. Zhu and C. Burda, *J. Am. Chem. Soc.*, 2009, **131**, 4253.
- 265 I. Kriegel, C. Jiang, J. Rodriguez-Fernandez, R. D. Schaller, D. V. Talapin, E. da Como and J. Feldmann, *J. Am. Chem. Soc.*, 2012, **134**, 1583.
- 266 M.-H. Shao, K. Sasaki and R. R. Adzic, *J. Am. Chem. Soc.*, 2006, **128**, 3526.
- 267 J. K. Nørskov, J. Rossmeisl, A. Logadottir, L. Lindqvist, J. R. Kitchin, T. Bligaard, and H. Jonsson, *J. Phys. Chem. B*, 2004, **108**, 17886.
- 268 M. Winter and R. J. Brodd, *Chem. Rev.*, 2004, **104**, 4245.
- 269 M.-R. Gao, J. Jiang and S.-H. Yu, *Small*, 2012, **8**, 13.
- 270 M.-R. Gao, S. Liu, J. Jiang, C.-H. Cui, W.-T. Yao and S.-H. Yu, *J. Mater. Chem.*, 2010, **20**, 9355.
- 271 J. G. Checkelsky, Y. S. Hor, R. J. Cava and N. P. Ong, *Phys. Rev. Lett.*, 2011, **106**, 196801.
- 272 D. Kong, Y. Chen, J. J. Cha, Q. Zhang, J. G. Analytis, K. Lai, Z. Liu, S. S. Hong, K. J. Koski, S.-K. Mo, Z. Hussain, I. R. Fisher, Z.-X. Shen and Y. Cui, *Nature Nanotech.*, 2011, **6**, 705.
- 273 L. Fu, C. L. Kane and E. J. Mele, *Phys. Rev. Lett.*, 2007, **98**, 106803.

(Review article) Submitted to Journal of Materials Chemistry C

- 274 I. Garate and M. Franz, *Phys. Rev. Lett.*, 2010, **104**, 146802.
- 275 L. Fu and C. L. Kane, *Phys. Rev. Lett.*, 2008, **100**, 096407.
- 276 H. Zhang, C.-X. Liu, X.-L. Qi, X. Dai, Z. Fang and S.-C. Zhang, *Nat. Phys.*, 2009, **5**, 438.
- 277 Y. Xia, D. Qian, D. Hsieh, L. Wray, A. Pal, H. Lin, A. Bansil, D. Grauer, Y. S. Hor, R. J. Cava and M. Z. Hasan, *Nat. Phys.*, 2009, **5**, 398.
- 278 Y. L. Chen, J. G. Analytis, J.-H. Chu, Z. K. Liu, S. -K. Mo, X. L. Qi, H. J. Zhang, D. H. Lu, X. Dai, Z. Fang, S. C. Zhang, I. R. Fisher, Z. Hussain and Z.-X. Shen, *Science*, 2009, **325**, 178.
- 279 D. Hsieh, Y. Xia, L. Wray, D. Qian, A. Pal, J. H. Dil, J. Osterwalder, F. Meier, G. Bihlmayer, C. L. Kane, Y. S. Hor, R. J. Cava and M. Z. Hasan, *Science*, 2009, **323**, 919.
- 280 M. Nath, S. Kar, A. K. Raychaudhuri and C. N. R. Rao, *Chem. Phys. Lett.*, 2003, **368**, 690.
- 281 C. W. Dunnill, H. K. Edwards, P. D. Brown and D. H. Gregory, *Angew. Chem. Int. Ed.*, 2006, **45**, 7060.
- 282 N. C. Gresty, Y. Takabayashi, A. Y. Ganin, M. T. McDonald, J. B. Claridge, D. Giap, Y. Mizuguchi, Y. Takano, T. Kagayama, Y. Ohishi, M. Takata, M. J. Ropsseinsky, S. Margadonna and K. Prassides, *J. Am. Chem. Soc.*, 2009, **131**, 16944.
- 283 Y. Mizuguchi, F. Tomioka, S. Tsuda, T. Yamaguchi and Y. Takano, *Appl. Phys. Lett.*, 2009, **94**, 012503.
- 284 F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Huang, Y.-Y. Chu, D.-C. Yan and M.-K. Wu, *Proc. Natl. Acad. Sci. U.S.A.*, 2008, **105**, 14262.
- 285 B. C. Sales, A. S. Sefat, M. A. McGuire, R. Y. Jin, D. Mandrus and Y. Mozharivskyj, *Phys. Rev. B*, 2009, **79**, 094521.
- 286 S. Medvedev, T. M. McQueen, I. Trojan, T. Palasyuk, M. I. Erements, R. J. Cava, S. Naghavi, F. Casper, V. Ksenofontov, G. Wortmann and C. Felser, *Nat. Mater.*, 2009, **8**, 630.
- 287 Y. Mizuguchi, F. Tomioka, S. Tsuda, T. Yamaguchi and Y. Takano, *J. Phys. Soc. Jpn.*, 2009, **78**, 074712.
- 288 J. Guo, S. Jin, G. Wang, S. Wang, K. Zhu, T. Zhou, M. He and X. Chen, *Phys. Rev. B*, 2010, **82**, 180520(R).
- 289 L. Malavasi and S. Margadonna, *Chem. Soc. Rev.*, 2012, **41**, 3897.

(Review article) Submitted to Journal of Materials Chemistry C

- 290 Y. Zhang, L. P. Hu, T. J. Zhu, J. Xie and X. B. Zhao, *Cryst. Growth Des.*, 2013, **13**, 645.
- 291 P. Laurino, R. Kikkeri and P. H. Seeberger, *Nat. Protoco.*, 2011, **6**, 1209.
- 292 B.-H. Kwon, K. G. Lee, T. J. Park, H. Kim, T. J. Lee, S. J. Lee and D. Y. Jeon, *Small*, 2012, **8**, 3257.

(Review article) Submitted to Journal of Materials Chemistry C

Table 1. Thermodynamic preferences of chalcogenide nanocrystals.

	M (metal)	Thermodynamic Preference (level)	Crystal structure	reason	Materials
Q (=S, Se, Te)		1-D (strong)	Trigonal	Chain-like structure	Se, Te
	IB	1-D (medium)	Hexagonal	High surface energy in (0001) plane	Cu ₂ Q
M₂Q	IB	0-D (strong)	Cubic	Isotropic surface Energy	Cu _{2-x} Q
	IIB IVA	0-D (strong)	Cubic	Isotropic surface energy	ZnQ, CdQ, PbQ
MQ	IIB	1-D (strong)	Hexagonal	High surface energy in (0001) plane	CdQ, ZnQ
	IVA, VIII B	2-D (strong)	Orthorhombic	Layered-structure	GeS, GeSe, SnS, SnSe, FeSe, FeTe
	IB IIB VIII B	3-D (medium)	Cubic	Isotropic surface energy	FeS ₂ , CoS ₂ , NiS ₂ , CuS ₂ , ZnS ₂
MQ₂	IVB VB VIB	2-D (strong)	Hexagonal	Layered-structure	TiQ ₂ , ZrQ ₂ , NbQ ₂ , TaQ ₂ , MoQ ₂ , WQ ₂
	IVB	1-D (medium)	Monoclinic	Chain-like structure	TiS ₃ , ZrS ₃ , ZrSe ₃ , ZrTe ₃ , HfQ ₃
MQ₃	VA	2-D (strong)	Hexagonal	Layered-structure	Bi ₂ Se ₃ , Bi ₂ Te ₃ , Sb ₂ Te ₃
	VA	1-D (strong)	Orthorhombic	Chain-like structure	Bi ₂ S ₃ , Sb ₂ S ₃ , Sb ₂ Se ₃

(Review article) Submitted to Journal of Materials Chemistry C

Table 2. Anisotropic chalcogenide nanocrystals reported to date.

Mechanism	Products	Growth	Shape*	
Intrinsically anisotropic growth	Se, Te, Se_xTe_y	1D	NW [45,46,54,58,59,61-67], NT [57,61], NR [59,60,68], NN [56], NRB [53], NB [57],	
	Bi_2S_3	1D	NR [72]	
	Sb_2Q_3 (Q= S, Se)	1D	NW [74] NRB [73]	
	GeQ (Q= S, Se)	2D	NSt [117]	
	FeQ , FeQ_x (Q= Se, Te)	2D	NSt [121], NF [122]	
	SnQ (Q=S, Se)	2D	NSt [119,120]	
	MS_2 (M= Ti, Zr, Nb, Ta, Mo), TiSe_2	2D	NSt [127,132,133], ND [126]	
	Bi_2Q_3 (Q=Se, Te)	2D	NP [134,135,222,223,224], ND [136] NSt [136], NF[137]	
	Sb_2Te_3	2D	NP [138,139,224]	
	$\text{Bi}_2\text{Te}_{3-x}\text{Se}_x$	2D	NP [222]	
$\text{Bi}_{2-x}\text{Sb}_x\text{Te}_3$	2D	NP [221, 224]		
Surfactant driven growth	Cu_2Q (Q= S, Te), Cu_{2-x}S	1D	NW [79],	
	PbQ (Q= Se, Te)	1D	NW [80,82], NR [80,82]	
	Sb_2Te_3	1D	NB [83]	
	CdSe	2D	NSt [147], ND [148]	
	Cu_{2-x}Se	2D	ND [144]	
	In_2S_3	2D	NSt [150]	
	NiTe_2	2D	NF [151]	
Oriented attachment growth	PbSe	1D	NR [95], NW [96]	
	ZnQ (Q= S, Se)	1D	NR [97], NW [98]	
	CdQ (Q= S, Se, Te)	1D	NW [92-94,99,108]	
	Bi_2Q_3 (Q= Se, Te)	2D	NP [156]	
	CdQ (Q= S, Te)	2D	NSt [155], NP [160]	
	PbQ (Q =S, Te)	2D	NSt [157-159]	
Chemical transformation	Reactant	Product		
	Te	M_xTe_y (M =Ag, Cd, Zn, Pb, Bi, Sb, La, Co)	1D	NW [162,173-177], NT [168-171]NRB [179]
	Te	$\text{Ag}_2\text{Te}-\text{Te}-\text{Ag}_2\text{Te}$	1D	Heterostructured NW [178]
	Se	Ag_2Se	1D	NW [66,172,180]
	Ag_2Te	MTe (M=Cd, Zn, Pb,)	1D	NW [162]
	CdTe	PtTe_2	1D	NT [162]
	CdQ (Q= S, Se)	MQ (M=Pb, Zn)	1D	NR [181,182]

(Review article) Submitted to Journal of Materials Chemistry C

Ag ₂ Se	CdSe	1D	NW [66,180]
Cd(OH) ₂	CdE (E = S, Se, Te)	1D	NT [184,185]
LiMo ₃ Se ₃	Au, Ag, Pt, Pd	1D	NW [188]
Te	Pt, Pd	1D	NT [189], NW [189]
Ti ₂ S	Cu ₂ S, CdS	2D	Toroid [183]
SnSe	SnTe	2D	NSt [186]

* Abbreviations are as follows: nanowire (NW), nanorod (NR), nanotube (NT), nanobelt (NB), nanoneedle (NN), nanoribbon (NRB), nanowire bundle (NWB) for 1D nanostructures, and nanoplate (NP), nanosheet (NSt), nanodisc (ND), and nanoflake (NF) for 2-D nanostructures.

(Review article) Submitted to Journal of Materials Chemistry C

Table 3. Binding energies (in eV) calculated for various ligands to the surfaces of CdE (E=S, Se) crystals. The energies marked with “a” and “b” were calculated from the $\text{Cd}_{15}\text{Se}_{15}$ and $\text{Cd}_{33}\text{Se}_{33}$ clusters, respectively. The elements (Cd, Se, S) placed beside surface notations represent the element terminated at the surfaces.

Wurtzite Cd_xSe_x [Ref. 75]				
Ligand	(000 $\bar{1}$)Cd	(0001)Se	(01 $\bar{1}$ 0)	(11 $\bar{2}$ 0)
PO	1.06a/0.85b	0.66a/0.63b	1.23b	1.37b
PA	1.12a/1.11b	0.66a/0.67b	1.45b	1.26b
CA	0.68a	0.42a	–	–
TMA	0.91a	1.05b	–	–
Wurtzite CdS[Ref. 78]				
	(0001)S	(0001)Cd	(10 $\bar{1}$ 0)	(11 $\bar{2}$ 0)
TOP	3.25	0.50	0.50	0.50
OA	3.75	0.50	0.75	2.65
Zinc Blend CdS[Ref. 78]				
	(001)	(111)S	(111)Cd	(110)
TOP	3.65	1.30	0.50	0.20
OA	3.20	0.3	0.15	1.60

* Abbreviations of the ligands are as follows: Phosphine Oxide (PO), Phosphonic Acid (PA), Carboxylic Acid (CA), Trimethylamine (TMA), Trioctylphosphine (TOP), and Oleic Acid (OA).

(Review article) Submitted to Journal of Materials Chemistry C

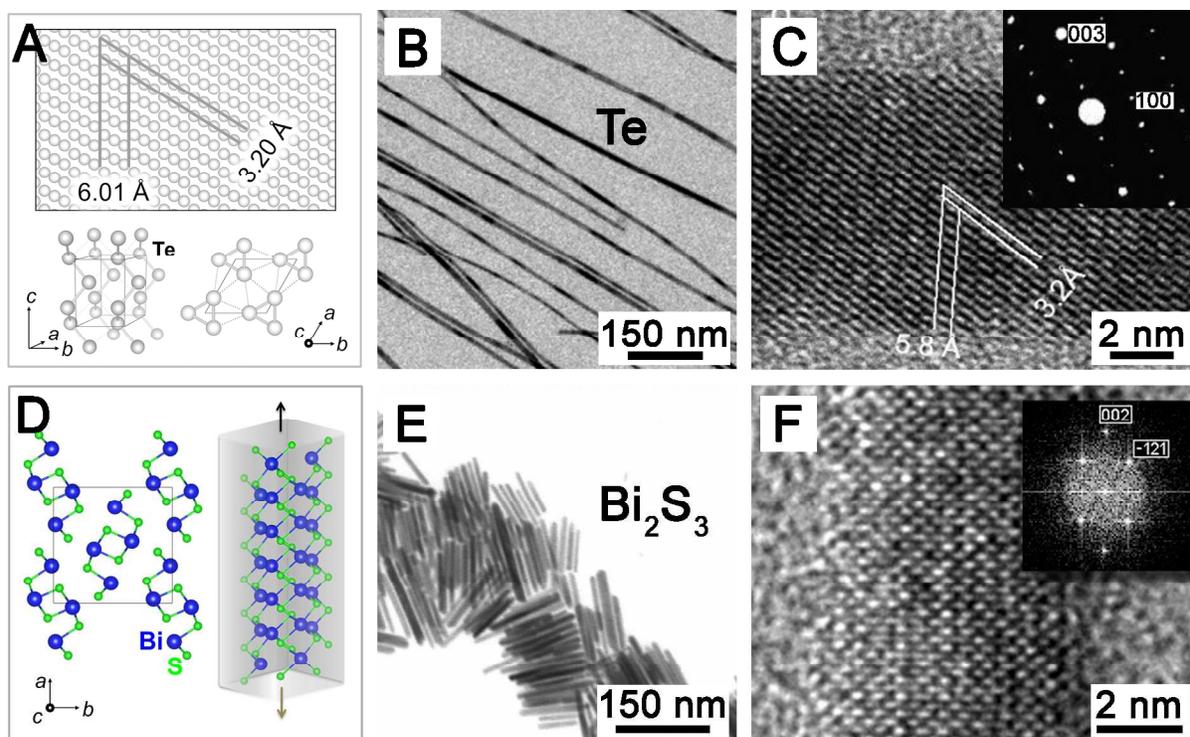


Figure 1. Intrinsically anisotropic growth of 1-D Te, Bi_2S_3 nanocrystals. (A) Tellurium (Te) crystal structure viewed along a -axis, while the insets show perspective and top views of the unit cell. Lattice spacings were obtained from the density-functional theory (DFT) calculations with Grimme's van der Waals correction. Projector augmented wavefunction method (PAW) was used for core level potential, while the PBE-GGA exchange correlation functional is used. (B) TEM and (C) HR-TEM images of t-Te nanowires and the electron diffraction (ED) pattern as an inset.⁶⁷ Adapted with permission from ref. 67, Copyright American Chemical Society. (D) Crystal unit cell of Bi_2S_3 viewed along c axis, [001] direction, The growth direction is noted with arrows along c -axis, (E) TEM and (F) HR-TEM images of Bi_2S_3 nanorods with an ED pattern (inset in F).⁷¹ Adapted from ref. 71 with permission from Wiley VCH.

(Review article) Submitted to Journal of Materials Chemistry C

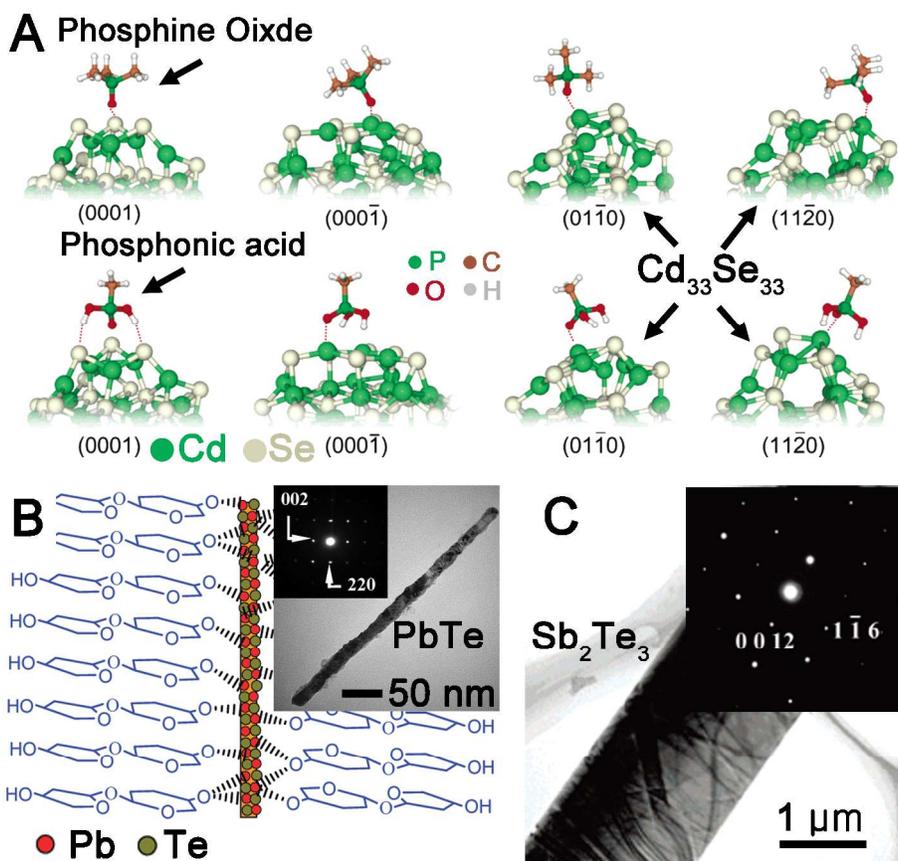


Figure 2. (A) Calculated geometries of phosphine oxide and phosphonic acid bound to the four facets of $\text{Cd}_{33}\text{Se}_{33}$ cluster.⁷⁵ (B) Schematic showing the growth mechanism of PbTe nanowires in the presence of sucrose with TEM images and corresponding ED pattern as an inset; anisotropic growth is due to the selective binding between the hydroxyl group sucrose and Pb atoms.⁸² (C) TEM image of a single Sb_2Te_3 nanobelt with SAED pattern (inset in C).⁸³ Adapted from ref. 75, 82, and 83 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

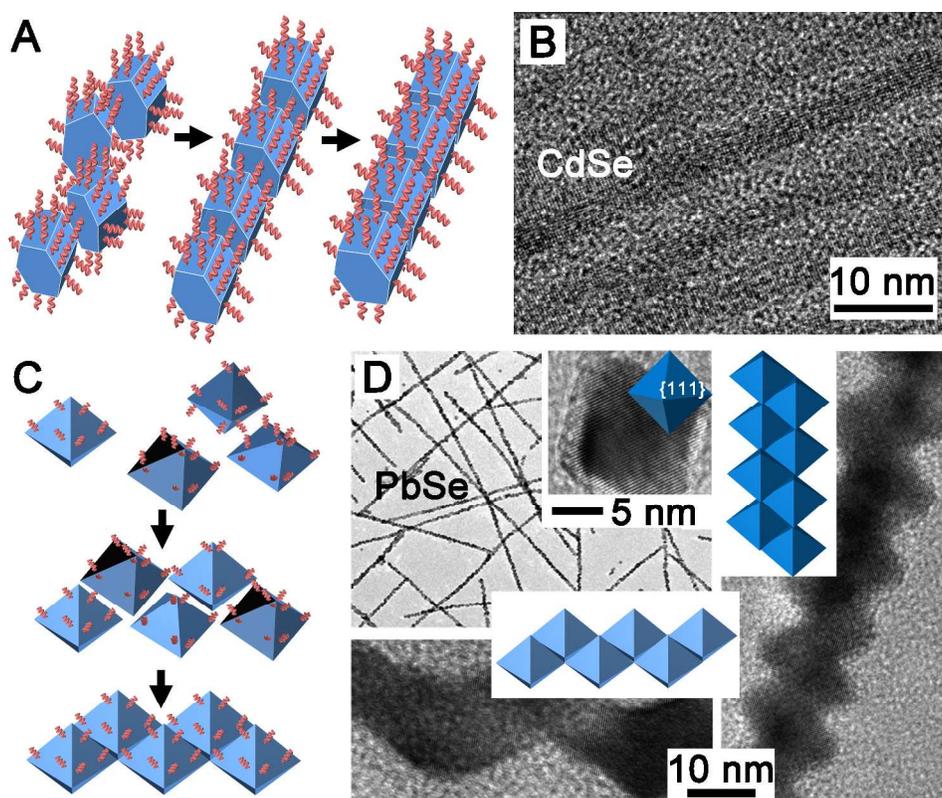


Figure 3. Axial growth by oriented attachment of CdSe, PbSe nanowires. (A) Schematic illustration showing the each growth stage during morphology evolution of CdSe quantum wires. (B)HR-TEM image of CdSe nanowires.¹⁰⁸ Adapted from ref. 108 with permission from IOP publishing. (C) Schematics of segment showing the assembly and growth of octahedral PbSe nanocrystals into zigzag nanowires. (D) TEM and HR-TEM images of octahedral repeat unit and zigzag nanowires depending on the two attachment mode.⁹⁶ (Schemes show the different attachment mode of octahedral PbSe nanocrystals) Adapted from ref. 96 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

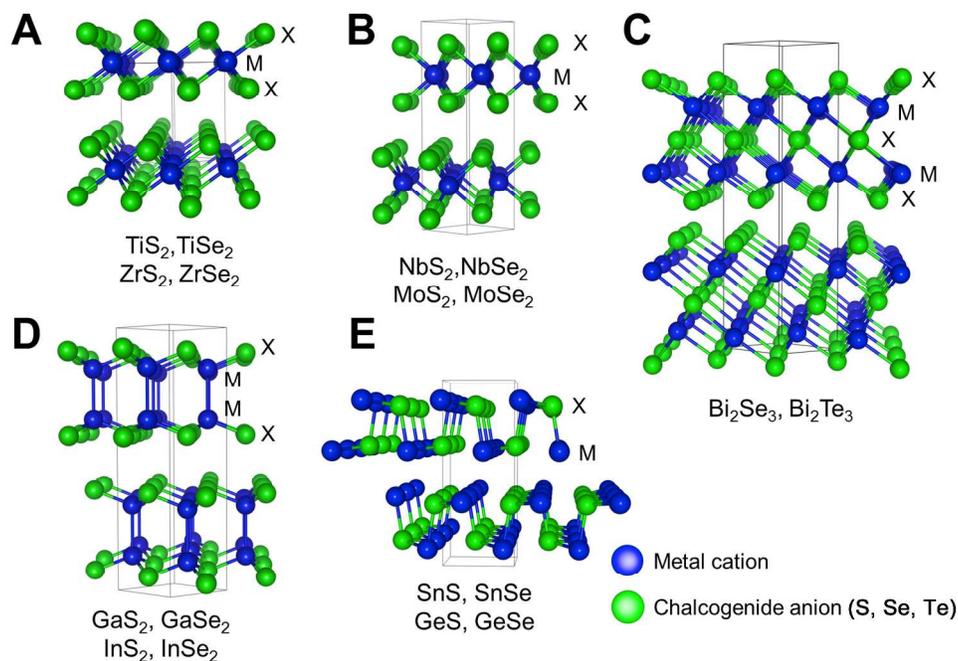


Figure 4. Crystal structures of various MC layered materials: Schematic descriptions of various metal chalcogenide crystals with layered geometry with stoichiometries MX_2 (in A, B, and D), M_2X_3 (in C), and MX (in E).

(Review article) Submitted to Journal of Materials Chemistry C

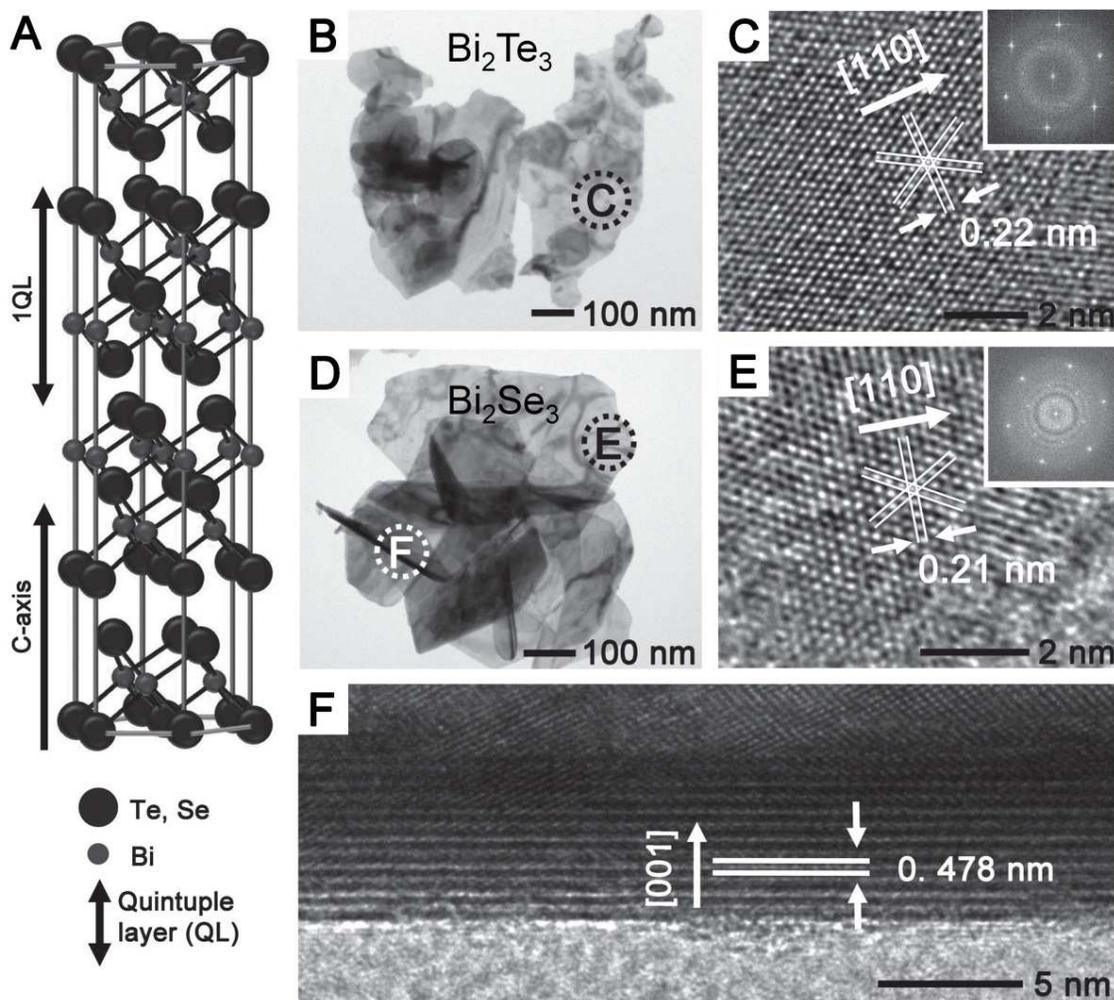


Figure 5. (A) Layered structure of bismuth chalcogenides (Bi_2Te_3 , Bi_2Se_3). Five consecutive atomic planes $[\text{Te}_1(\text{Se}_1)\text{-Bi-Te}_2(\text{Se}_2)\text{-Bi-Te}_1(\text{Se}_1)]$ consisting of one quintuple layer along the c-axis. (B) TEM image of as-synthesized Bi_2Te_3 nanoflakes and (C) HR-TEM image of the area designated by the letter C in panel B. (D) TEM image of as-synthesized Bi_2Se_3 nanoflakes and (E) A HR-TEM image of the area indicated by the E in panel D. (F) HR-TEM image showing a side view of the Bi_2Se_3 nanoflake indicated by the letter F in panel D. The insets in C and D are the corresponding SAED patterns.¹³⁷ Adapted from ref. 137 with permission from Wiley VCH.

(Review article) Submitted to Journal of Materials Chemistry C

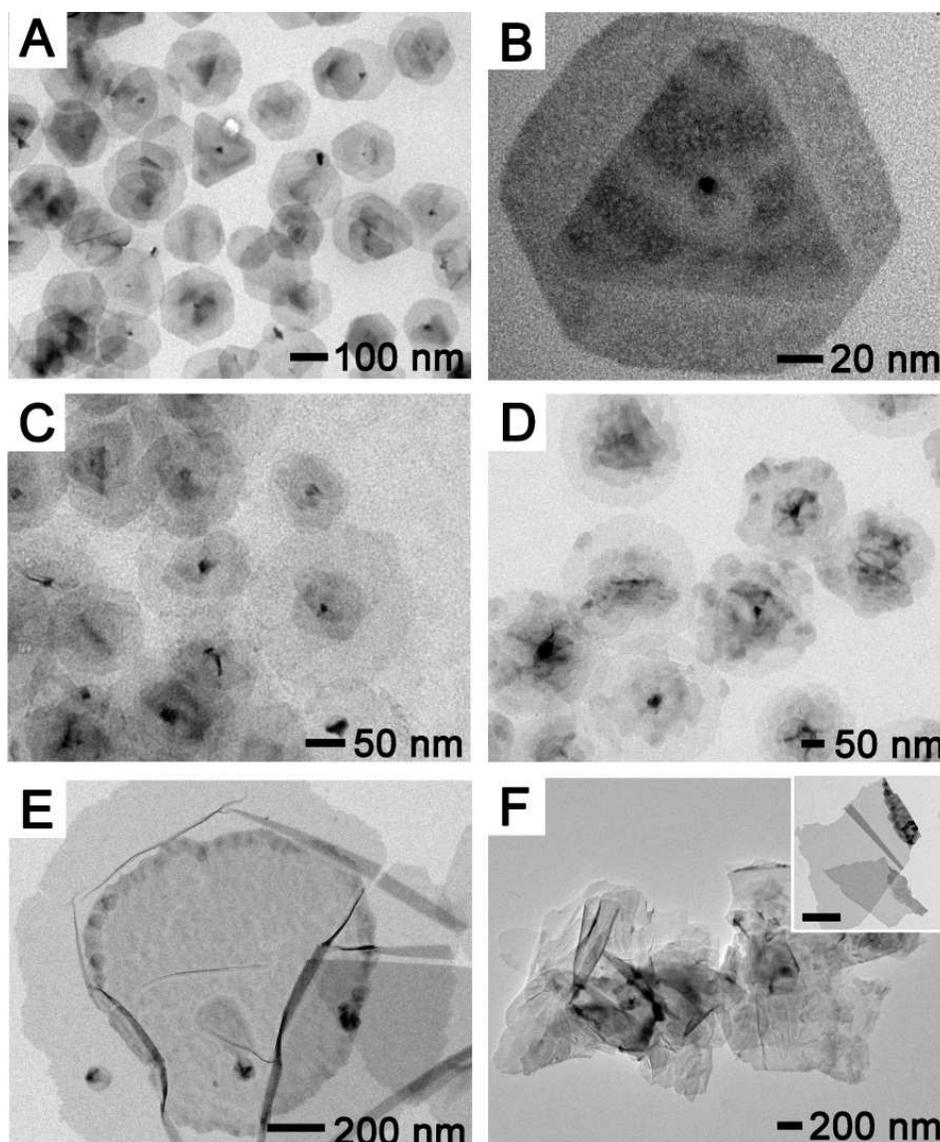


Figure 6. TEM images showing morphological changes of the Bi_2Se_3 nanostructured materials from nanodiscs to nanosheets by controlling the molar ratio of PVP in the mixture with PEI. PVP : PEI = 10:0 (A,B), 9:1 (C), 8:2 (D), 3:7 (E), and 0:10 (F). The inset in F indicates the nanosheet fragments torn off from a wide sheet by applying ultrasonic sound in the suspension (Scale bar = 200 nm).¹³⁶ Adapted from ref. 136 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

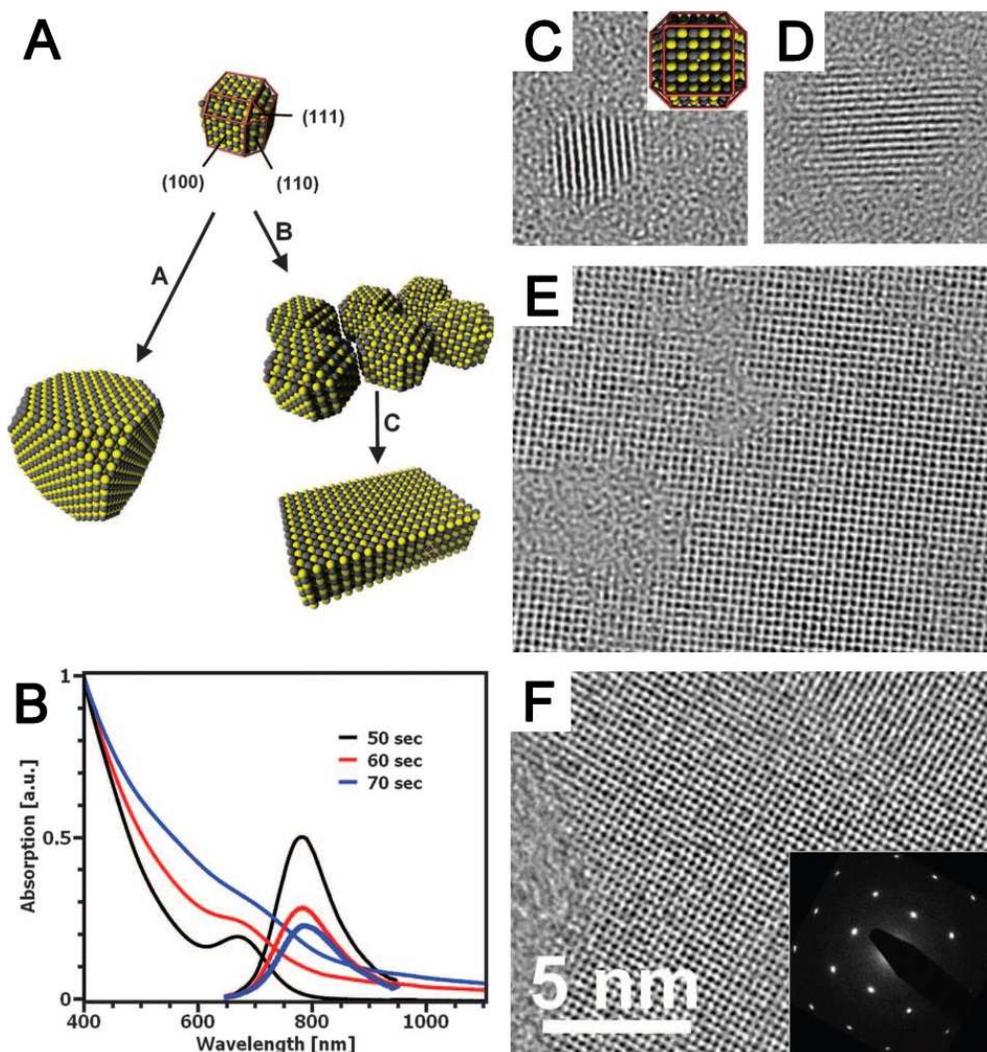


Figure 7. (A) Schematic illustrating the two growth pathways of quasi-single PbS nanocrystals into a large particle (path A) and into a nanosheet (path B, C). (B) Absorption and emission spectra of the PbS nanocrystals according to the reaction time. (C-F) TEM images showing the shape evolution of PbS nanocrystals into a nanosheet by an oriented attachment growth mechanism.¹⁵⁸ Adapted from ref. 158 with permission from American Association for the Advancement of Science.

(Review article) Submitted to Journal of Materials Chemistry C

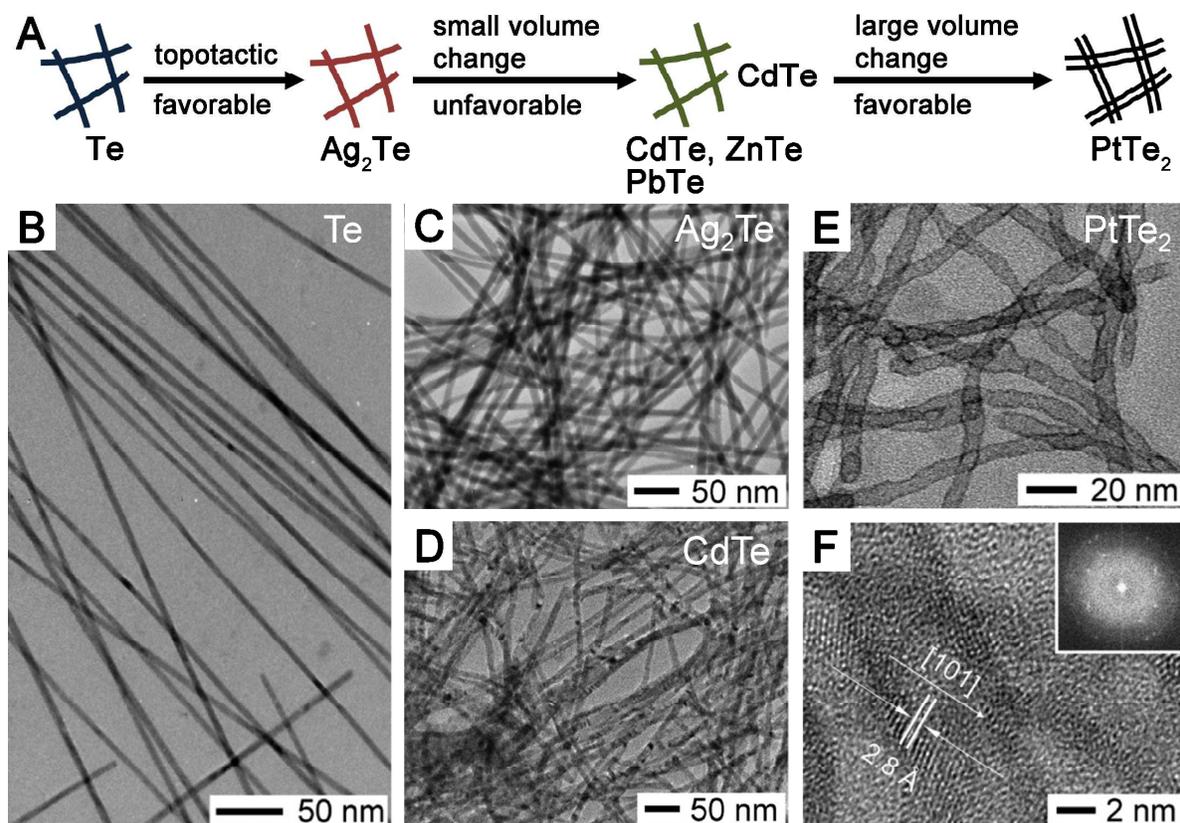


Figure 8. (A) Flow of chemical transformation from ultrathin Te nanowires into various chalcogenide 1-D nanostructured materials. Topotactic transformation from ultrathin Te to Ag₂Te nanowires, which is thermodynamically favorable. Reversible cation exchange reaction for generating metal telluride nanowires (MTe, M=Cd, Zn, Pb) from Ag₂Te nanowires. The reaction is thermodynamically prohibited, hence the use of specific surfactant is needed. Further transformation of CdTe nanowires into PtTe₂ nanotubes through a forward cation exchange reaction. TEM images of ultrathin Te (B), Ag₂Te (C), CdTe nanowires (D). TEM (E) and HR-TEM (F) images of the PtTe₂ nanotubes transformed from CdTe nanowires. The inset shows the Fourier transformed ring pattern of PtTe₂ nanotubes.¹⁶² Adapted from ref. 162 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

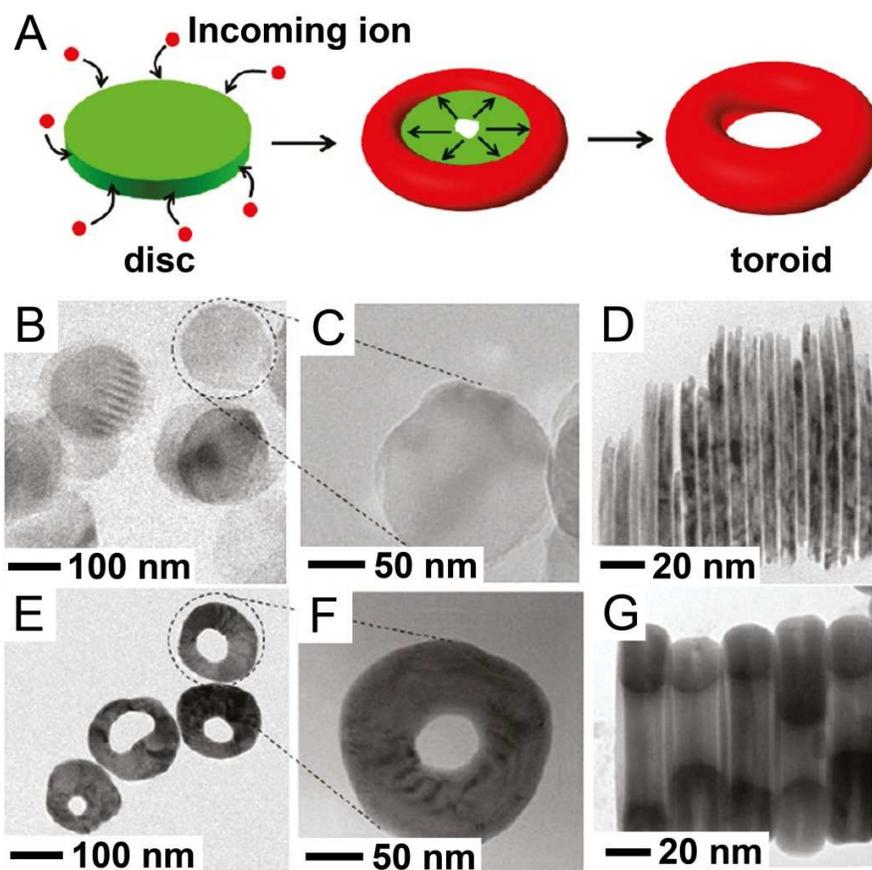


Figure 9. (A) Schematic illustration of the transformation from a Ti₂S nanodisc into a Cu₂S toroid by regioselective reaction of Ti₂S with incoming ions. (B,C) TEM images of Ti₂S nanodisc as a starting material. (D) Cross-sectional TEM image of a stack of Ti₂S nanodiscs. (E,F) TEM images of Cu₂S toroids transformed from Ti₂S nanodiscs. (G) Side view of a stack of Cu₂S toroids.¹⁸³ Adapted from ref. 183 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

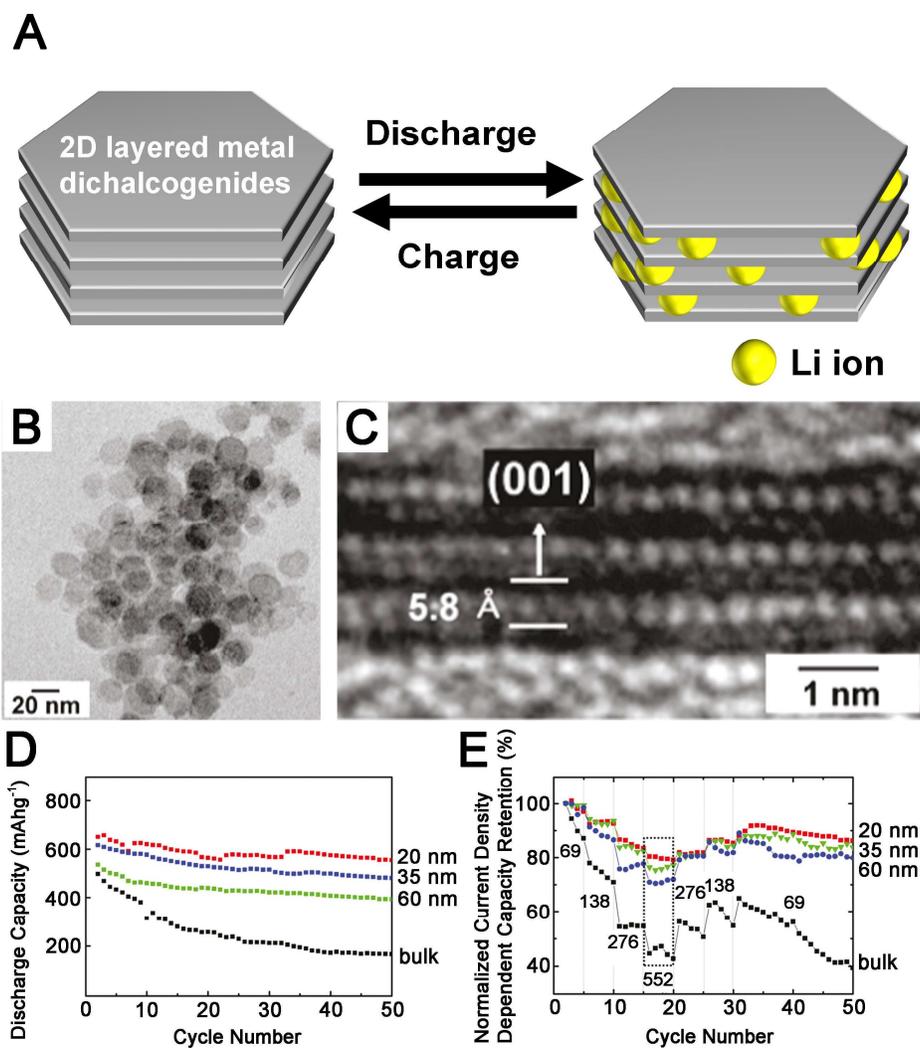


Figure 10. (A) Schematic illustration of the reversible intercalation and exfoliation of Li^+ ions in 2-D layered anodic materials. (B) Top- and (C) side-view TEM images of as-synthesized ZrS_2 nanodiscs. (D) Cycling behaviors of ZrS_2 nanodiscs with different lateral dimensions (20, 35, and 60 nm) and bulk ZrS_2 . (E) Current density-dependent capacity retention profiles of ZrS_2 nanodiscs (20, 35, and 60 nm) and bulk ZrS_2 at current densities of 69, 138, 276, and 552 mAh/g .¹²⁸ Adapted from ref. 128 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

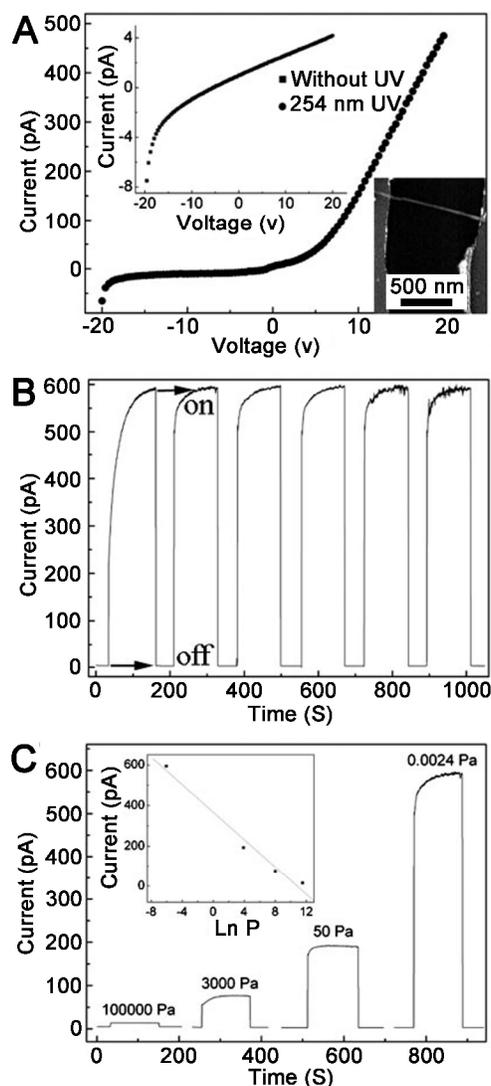


Figure 11. (A) I-V characteristics of an individual single-crystalline Ag_2S nanowire under dark (top-left inset) and UV illumination at 254 nm. The measurement was done at room temperature and a pressure of 2.4×10^{-3} Pa. Bottom-right inset shows a typical SEM image of the device. (B) Time-resolved photocurrents of the device measured at pressure of 2.4×10^{-3} Pa in air at atmospheric pressure. (C) Time-resolved photocurrents measured at different pressures. Linear relations between the logarithmic pressure and the current (inset in panel C).²¹¹ Adapted from ref. 211 with permission from Wiley VCH.

(Review article) Submitted to Journal of Materials Chemistry C

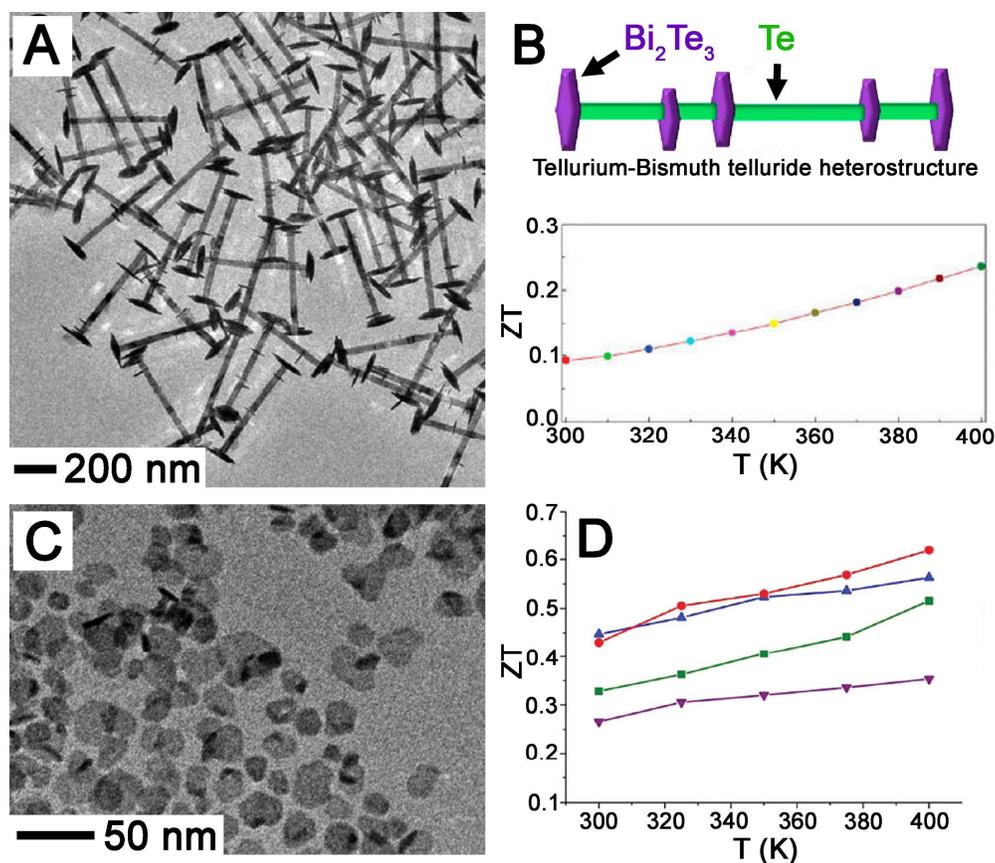


Figure 12. Thermoelectric application of the Te-Bi₂Te₃ 1-D heterostructure and Bi₂Te₃ 2-D nanoplate. (A) TEM image of Te-Bi₂Te₃ heterostructure. (B) Schematic drawing of the Te-Bi₂Te₃ heterostructure and temperature dependence of the thermoelectric figure of merit (ZT) of the sintered bulk nanocomposite pellet. Reproduced with permission.²²⁷ (C) TEM image of the as-synthesized Bi₂Te₃ nanoplates. (D) Temperature dependence of the thermoelectric figure of merit of the Bi₂Te₃ nanoplates bulk pellets. The colors indicate the sintering temperature: 200 °C (green squares), 250 °C (red circles), 300 °C (blue upwards-pointing triangles), and 325 °C (purple downwards-pointing triangles).²²³ Adapted from ref. 227 and 223 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

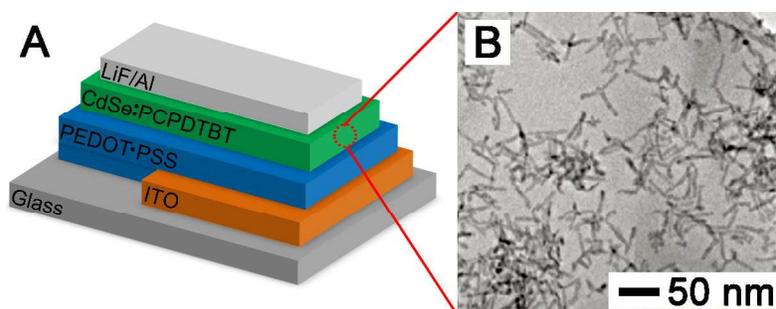
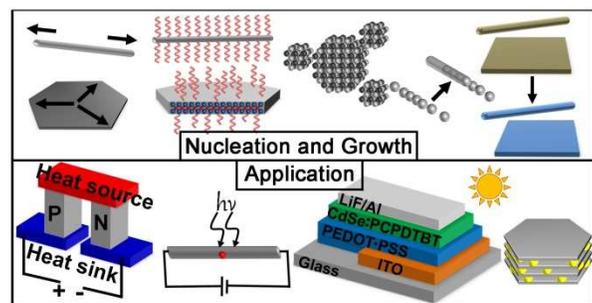


Figure 13. (A) Photovoltaic device configuration of CdSe-PCPDTBT hybrid structure. (B) TEM image of CdSe tetrapod nanocrystals as the component of active layers.²⁵³ Adapted from ref. 253 with permission from American Chemical Society.

(Review article) Submitted to Journal of Materials Chemistry C

Table of Contents Only


This article reviews recent advances in solution-phase synthesis of anisotropic metal chalcogenide nanomaterials (1-D & 2-D) and their practical applications with some challenges in the solution-based synthesis.

(Review article) Submitted to Journal of Materials Chemistry C

Biographical Information



Yuho Min received a B.S. degree in the Dept. of Materials Science and Engineering from Yonsei University in 2010. He is pursuing his Ph.D. degree under the supervision of Prof. Unyong Jeong in the same department. His research interests include synthesis of metal chalcogenide nanomaterials and solid-state device materialization of inorganic nanocrystals for their opto-electronic and thermoelectric applications.

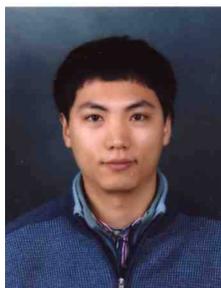

Geon Dae Moon received a B.S. in 2006 and Ph. D. in 2011 in the Dept. of Materials Science and Engineering from Yonsei University under the supervision of Prof. Unyong Jeong. Then, he worked as a postdoctoral fellow at Prof. Yadong Yin's group in the Dept. of Chemistry in University of California, Riverside. Now, he is working as a research associate in the Sustainable Energy Technology Dept., Brookhaven National Laboratory starting from 2013. His research interests include synthesis of metal, metal oxide, and metal chalcogenide nanomaterials along with self-assembly of those inorganic nanostructures for electronic and electrochemical applications.

(Review article) Submitted to Journal of Materials Chemistry C



Chang-Eun Kim received a B.S. degree in the Dept. of Materials Science and Engineering from Yonsei University in 2013. He is pursuing his Ph.D. degree under the supervision of Prof. Aloysius Soon in the same department. His research interests include first-principles description for the phase stability, electronic structure and transport property of narrow-gap semiconductors.




Ji-hwan Lee received a B.S. degree in the Dept. of Material Science and Engineering from Yonsei University in 2013. He is pursuing his Ph. D. degree under the supervision of Prof. Aloysius Soon in the same department. His research interests include density-functional study combined with ab initio thermodynamics of multifunctional interfaces to design new material system for next-generation energy technology.

(Review article) Submitted to Journal of Materials Chemistry C



Aloysius Soon holds a Ph.D. in Physics from the University of Sydney, Australia and joined the Department of Materials Science and Engineering at Yonsei University, Korea as an Assistant Professor in 2010. Prior to that, he was an Alexander von Humboldt postdoctoral fellow at the Fritz-Haber-Institut der Max-Planck-Gesellschaft, Germany under the direction of Prof. Matthias Scheffler. Recently, he was awarded the title of Honorary Research Fellow to pursue joint research at the University of Sydney. His research focuses on the development and application of materials theory and first-principles methods for the fundamental understanding of the chemistry and physics of materials.

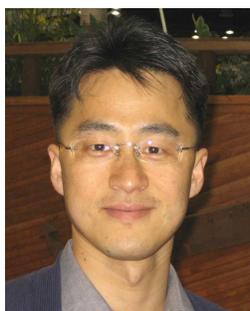

Unyong Jeong received his Ph.D. in Chemical Engineering from POSTECH in Korea. He spent two years as a postdoctoral research associate at University of Washington. He moved to Materials Science and Engineering at Yonsei University in 2006 and now he is an associate professor. His research interest includes production of nanostructured materials, colloids and fibers by electrohydrodynamics, and organic/inorganic hybrid materials for electronic devices.

(Review article) Submitted to Journal of Materials Chemistry C

His current interest in the material synthesis is put on the shape control of metal chalcogenides and dimension control of metal nanowires.