

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Simple Coordination Complex-Derived Three-Dimensional Mesoporous Graphene as an Efficient Bifunctional Oxygen Electrocatalyst

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012Kyung Joo Lee,^a Young Jing Sa,^a Hu Young Jeong,^b Christopher W. Bielawski,^{a,c}
Sang Hoon Joo,^{a,d} and Hoi Ri Moon^{*a}

DOI: 10.1039/x0xx00000x

www.rsc.org/

3D mesoporous graphene (*mesoG*) was synthesized via the thermal conversion of [Ni₂(EDTA)] (EDTA = ethylenediaminetetraacetate). The material is comprised of interconnected 4 nm-sized hollow carbon shells composed of 3 – 4 layers of graphene and exhibits high bifunctional electrocatalytic activity as well as high durability for use in oxygen evolution and reduction reactions.

Due to their numerous potential applications in gas adsorption,¹ energy storage,² and catalysis,³ porous carbon materials have attracted tremendous interest. In particular, given the high porosity of carbon combined with graphitic frameworks, the resulting materials are expected to exhibit excellent electrochemical and mechanical properties^{4,5} as well as high thermal conductivity.⁶ Of the several forms of graphitic porous carbons, 3D porous graphene-like materials are attractive because they are expected to display high conductivities and large surface areas. While ideal graphene is composed of a single layer of *sp*² hybridized carbon atoms with a high theoretical surface area (2630 m² g⁻¹), its strong stacking affinity via the formation of infinite π - π interactions can hamper the full utilization of its intrinsic properties in practical applications.^{4,7} To integrate the functionality of graphene with structural features that prevent undesired stacking, efforts have been directed toward the synthesis of 3D porous graphene-like networks. For instance, Chen *et al.* reported the synthesis of graphene foams via a template-directed chemical vapor deposition (CVD) that utilized nickel foam as both a template and a catalyst.⁸ Similarly, 3D porous graphene networks have been prepared by CVD in the presence of templates such as 3D assembled colloidal silica⁹ and porous MgO¹⁰ along with additional catalysts to facilitate graphitization. However, such template-assisted CVD methods are commonly unsuitable for large-scale syntheses and require cumbersome template preparation steps. An alternative approach is the assembly of materials which are chemically derived from graphene, such as graphene oxide (GO) and reduced graphene oxide (rGO), followed by activation.¹¹ Despite the potential advantage of mass production, such a method might yield lower electrochemical performances caused by damage of the GO



Scheme 1. Schematic representation of the thermal conversion of [Ni₂(EDTA)] into three-dimensional mesoporous graphene, 3D *mesoG*. The processes indicated by red arrows occurred during the one-step heat treatment of [Ni₂(EDTA)].

and rGO surfaces. Another method is the hybridization of graphene with organic or inorganic materials that effectively function as ‘spacers’ between the graphene layers.^{12,13} However, this approach is susceptible to the restacking of 2D graphene layers due to low pillar densities as compared to overall surface area.¹³ Herein, we report that the direct thermal conversion of a Ni^{II} coordination complex followed by etching can yield 3D mesoporous graphene (*mesoG*). The method is cost effective, may be performed on the gram scale, and can proceed without the aid of additional templates, catalysts or CVD techniques (Scheme 1). During the thermal conversion of the Ni^{II} complex under an inert atmosphere, the Ni^{II} ionic centers are transformed *in situ* into 4 nm-sized Ni NPs (Fig. 1a), which act as catalysts that facilitate C-C bond cleavage and enable the formation of amorphous carbon from the organic ligands while also serving as a template for the creation of mesopores. The resulting 3D *mesoG* material is composed of a 3D interconnected structure of hollow carbon shells comprised of 3 – 4 graphene layers. In addition, the material features small, uniform mesopores (~ 4 nm in diameter), a large surface area, and a very high C/O ratio. The 3D *mesoG* exhibits very high activity and durability as a bifunctional electrocatalyst for oxygen reduction and evolution reactions (ORR and OER, respectively), revealing its promise as a non-precious metal electrocatalyst for use in energy conversion and storage devices.¹⁴

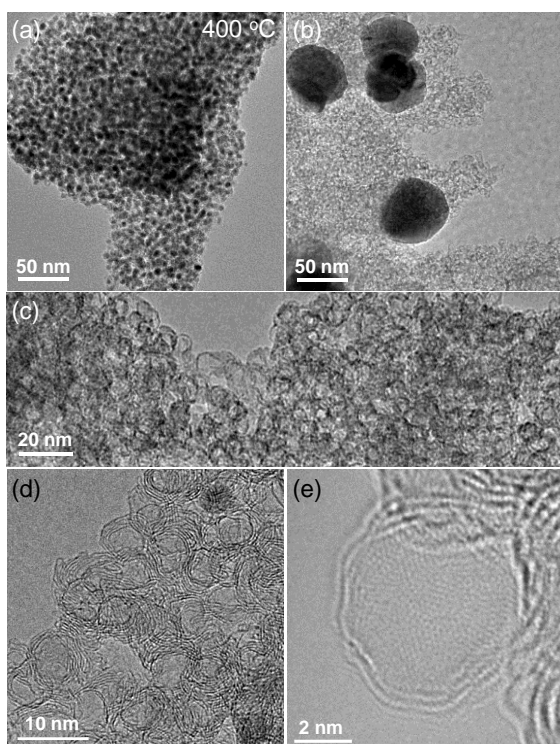


Fig. 1 TEM image of (a) *mesoG*/Ni during the thermal conversion at 400 °C, and (b) *mesoG*/Ni after heat treatment at 1000 °C, and (c–e) 3D *mesoG* at various magnifications.

The Ni^{II} coordination complex used herein can be readily prepared via the coordination of Ni^{II} ions with ethylenediaminetetraacetic acid (H₄EDTA) in the presence of *N,N,N*-triethylamine (TEA), which serves to deprotonate the carboxylic acid. In the corresponding product, [Ni₂(EDTA)],¹⁵ which is a blue powder, the Ni^{II} center is chelated by an EDTA ligand to form six coordination bonds with four oxygen atoms of the carboxylates and two nitrogen atoms of the tertiary amines.

With [Ni₂(EDTA)] in hand, 1.15 g of the complex was heated to 1000 °C at a ramping rate of 10 °C min⁻¹ under a nitrogen flow of 500 mL min⁻¹. After maintaining the temperature of the reaction at 1000 °C for 1 h, the solid was cooled to room temperature, which resulted in the formation of 0.32 g of a black powder. Elemental composition analysis of the resulting powder revealed that during the thermolysis of [Ni₂(EDTA)], most of the H, N, and O were removed, while the Ni and 30% of the C contents remained (*mesoG*/Ni, Table S1 and Fig. S2). Transmission electron microscopy (TEM) (Fig. 1b) revealed that after the thermal treatment, the black powder was composed of 3D carbon materials and ~50 nm-sized Ni NPs (*mesoG*/Ni). The Ni NPs could be removed by a wet etching process to obtain a relatively metal-free carbon material (~0.1 g) where approximately 1 wt% of the Ni remained in the 3D *mesoG* after etching, as determined by thermogravimetric analysis (TGA) under oxygen (Table S1 and Fig. S3). Interestingly, the 3D *mesoG* also contained 1.7 wt% of nitrogen, presumably from the EDTA ligands, and thus can be considered an N-doped carbon. Fig. 1c and d show that the obtained carbon materials consisted of small hollow carbon shells in addition to large shells. A closer observation (Fig. 1e) via atomic resolution TEM (AR-TEM) revealed that these small hollow

carbon shells were composed of 3 – 4 layers of graphene with an inner diameter of ~4 nm, and were interconnected to produce the 3D nanostructured *mesoG*. We note that even after etching the Ni NPs from hollow carbon, the 3D *mesoG* structure did not collapse. Furthermore, elemental composition analysis of the 3D *mesoG* (Table S1) revealed that etching with a strong acid had a negligible effect on the chemical state of the 3D *mesoG*. Scanning electron microscopy (SEM) analysis of the 3D *mesoG* revealed the external microscopic morphology of the integrated graphene shells (see Fig. S4 for an image of this material). Notably, the synthetic method can be scaled and at least tens of grams of the [Ni₂(EDTA)] precursor may be used.

To identify the origin of the formation of the hollow shell and the 3D graphene-like structure, variable temperature X-ray powder diffraction (VT-XRPD) experiments were performed during the treatment of [Ni₂(EDTA)] (Fig. S5a). When the temperature reached 400 °C, a broad signal near $2\theta = 45^\circ$ was detected. Upon further increase of the temperature, the peak at 45° became sharper and were accompanied with the formation of two newly evolved peaks at 52° and 76° , which were characteristic reflections of a cubic Ni⁰ structure (JCPDS file no. 04-0850). When the temperature was further increased to 1000 °C, a very small but clear peak at 26° was observed and a typical (002) reflection of graphitic carbon. Fig. S5b shows the size of Ni NPs at each temperature, estimated by applying the Debye-Scherrer equation to the (111) reflection. Below 600 °C, the sizes of the Ni NPs were less than 5 nm. However, above 700 °C, some of the small nanoparticles began to agglomerate to form larger Ni NPs (plotted as red and blue dots, respectively), as derived from the Debye-Scherrer equation with two deconvoluted peaks of the (111) reflection. Subsequently, when the temperature reached 900 °C, the small Ni NPs ceased to agglomerate and resulted in a single data point of ~35 nm-sized Ni NPs. The number of expected peaks for deconvolution was determined from TEM images obtained at each temperature (Fig. S6). Since the solids heated to less than 300 °C were unstable under the e-beam during TEM analysis, images were obtained for samples treated at 400, 500, 600, 700, 800, 900, and 1000 °C. Similar to the XRPD results, when the temperature was 400 °C, Ni NPs embedded in the carbon matrix were formed. As the temperature increased, the shapes of the Ni NPs became more regular and crystalline, and had diameters less than 5 nm. Meanwhile, owing to the catalytic function of Ni NPs, the organic species from the EDTA began to decompose and subsequently formed *sp*² carbons on the Ni NPs. A similar phenomenon has been observed with the growth of CNTs assisted by Ni catalysts.¹⁶ In the present system where the Ni NPs were embedded within carbon layers, the total directional contact of carbon with Ni NP surfaces results in spherical shells rather than tubular structures. Therefore, the size of the Ni NPs formed *in situ* dictates the inner diameter of the hollow carbon. In the TEM image of the solid treated at 700 °C (Fig. 2c), Ni NPs with diameters larger than 50 nm were observed in the presence of small Ni NPs with diameters of ca. 5 nm. We presume that this was due to the secondary agglomeration of the 4 nm Ni NPs that was initiated upon heating at the temperatures above ~600 °C. The mobility of the Ni NPs can be explained by the melting-point depression in nanoscale materials.¹⁷ While the melting temperature of bulk Ni metal is 1453 °C, metal particles smaller than ~100 nm

can melt at significantly lower temperatures; indeed, the melting point of 4 nm Ni metal particles was calculated to be ~ 700 °C, a temperature at which the Ni NPs began to agglomerate. Therefore, after heating at 1000 °C for 1 h, the 3D *mesoG* coexisted with large Ni NPs. Likewise, the surfaces of the large Ni NPs also act as catalysts to generate large carbon shells, as shown in Fig. S6.

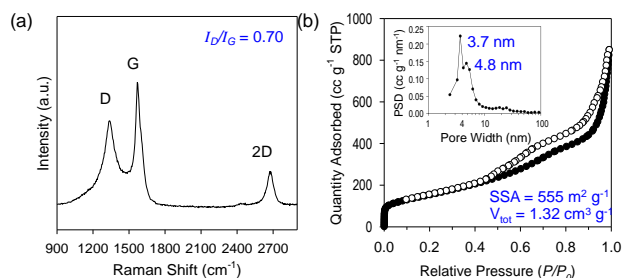


Fig. 2 Structural and electronic characterization of 3D *mesoG*. (a) Raman spectrum. (b) N_2 adsorption-desorption isotherm and the corresponding BJH pore size distribution curve (inset).

To explore the structural and electronic properties of the 3D *mesoG* material, Raman spectroscopy was conducted (Fig. 2a). A broad D band attributed to the disorder-induced mode and a relatively sharp G band attributed to the E_{2g} mode from the sp^2 carbon domain appeared at 1340 and 1575 cm^{-1} , respectively, along with the 2D band at 2676 cm^{-1} . The G peak indicated the presence of crystalline graphitic carbon in the 3D *mesoG*. The ratio between the intensity of the D and G bands (I_D/I_G), which is commonly used as an indicator for the degree of disorder in graphitic materials, was 0.70. This I_D/I_G ratio was comparable to or smaller than those measured for GO and rGO ($I_D/I_G = \sim 1$)¹⁸ as well as CVD-grown multi-wall CNTs ($I_D/I_G = 0.7\sim 1.3$),¹⁹ thus indicating that high quality 3D *mesoG* was formed (Table S2). The broad D peak might originate primarily from the distorted nature of the hexagonal sp^2 carbons because of significant lattice stress arising from high curvature of the 4 nm hollow graphene shell in 3D *mesoG*. As listed in Table S2, elemental analysis of 3D *mesoG* revealed a high C/O ratio of 55, which was much higher than that of some forms of chemically or thermally reduced graphene oxide (rGO) (~ 20).²⁰ Regardless, such a high C/O atomic ratio implies the presence of limited oxygen-containing functionalities, which may lead to improved physical properties. In order to assess the porous structure of 3D *mesoG*, nitrogen adsorption-desorption measurements were conducted. As shown in Fig. 3b, 3D *mesoG* exhibited typical type IV isotherms with an H3 type hysteresis loop over a relative pressure range of $0.42 < P/P_0 < 0.99$, characteristic of a mesoporous material. The Barrett–Joyner–Halenda (BJH) pore size distribution curve (Fig. 3b, inset) indicated that the sizes of the mesopores were centered around 4 nm, which was in good agreement with the TEM analysis. The highly porous nature of 3D *mesoG* gave rise to a relatively large Brunauer–Emmett–Teller (BET) specific surface area (SSA) of 555 $m^2 g^{-1}$, which was comparable to the specific surface area of five-layered graphene calculated from the theoretical SSA of monolayer graphene (2630 $m^2 g^{-1}$). In addition, 3D *mesoG* exhibited a very high total pore volume (V_{tot}) of 1.32 $cm^3 g^{-1}$.

Overall, the characterization data were consistent with the material with large surface area from a readily-accessible Ni

coordination complex. It is noteworthy that it was previously impossible to prepare 3D graphene with such small, monodisperse mesopores without the need for additional pore generation processes, such as the introduction and removal of various templates (e.g., Ni foams⁸ or silica beads⁹). Furthermore, the present method can proceed without the use of reductive gases (e.g., H_2), which is typically required to form the carbons observed within the graphene layers. As such, this method represents a significant advancement in the preparation of 3D graphene materials in terms of simplicity of the synthetic process as well as the quality of the resulting materials.

To utilize the good structural properties displayed by 3D *mesoG*, we investigated its bifunctional electrocatalytic activity in ORR and OER, which are relevant for renewable energy technologies.^{14,21} The activities of Ir/C (20 wt% Ir, Premetek) and Pt/C (20 wt% Pt, Johnson-Matthey) were also evaluated as benchmarks. The polarization curves for the ORR and OER were measured in 0.1 M KOH at 1600 rpm using the rotating disk electrode (RDE) technique (Fig. 3a). For the OER, 3D *mesoG* showed a very high activity that was comparable to that of noble-metal-based Ir/C and was significantly better than that of Pt/C. The potential to drive 10 $mA cm^{-2}$ for 3D *mesoG* was 1.56 V (vs. reversible hydrogen electrode (RHE), overpotential (η) = 330 mV), which was slightly better than that of Ir/C (1.58 V, η = 350 mV) and significantly better than that of Pt/C (1.83 V, η = 600 mV). In the ORR, 3D *mesoG* also showed high activity, which approached that of Pt/C and exceeded that of the Ir/C catalyst. The potentials required to reach $-3 mA cm^{-2}$ during the ORR were 0.76 V, 0.88 V, and 0.70 V for 3D *mesoG*, Pt/C, and Ir/C, respectively. To quantitatively compare the bifunctional activity (oxygen electrode activity) of the catalysts for the OER and ORR, the potential difference to drive 10 $mA cm^{-2}$ and $-3 mA cm^{-2}$ (or the sum of overpotentials at those current densities) was calculated (Fig. 3b and Table S3).²² Remarkably, the 3D *mesoG* material exhibited the highest oxygen electrode activity among the catalysts compared: indeed, the potential difference of the 3D *mesoG* (0.80 V) was lower than that of the noble metal-based Ir/C (0.88 V) and Pt/C (0.95 V) catalysts. It should be also noted that the comparison of the oxygen electrode activities of the reported catalysts indicated that the 3D *mesoG* may be ideally suited for use in carbon-based bifunctional catalysts for the ORR and OER (Table S4) and a promising catalyst for use in regenerative fuel cells as well as rechargeable metal-air batteries. The high bifunctional activity of 3D *mesoG* may originate from its very large surface area, with numerous defect sites due to the high curvature of its structure. In addition, the presence of nitrogen and nickel species in the carbon framework also contributed to the high catalytic activity.²³

Finally, we assessed the structural stability of the 3D *mesoG* material via a series of durability tests in the OER. Specifically, the 3D *mesoG* material as well as Ir/C and Pt/C catalysts were cycled from 1.20 to 1.70 V 100 times (Fig. S7). A comparison of the current densities at 1.70 V before and after the cycling tests revealed that 3D *mesoG* underwent only a 3% decay in the current density, whereas the OER activities of Ir/C and Pt/C catalysts declined by 19% and 75%, respectively (Fig. 3c). Carbon-supported metal nanoparticles are subject to various deactivation processes, such as carbon oxidation, metal dissolution, and Ostwald ripening, which are more pronounced at high oxidative OER potentials (>1.4 V). The superior

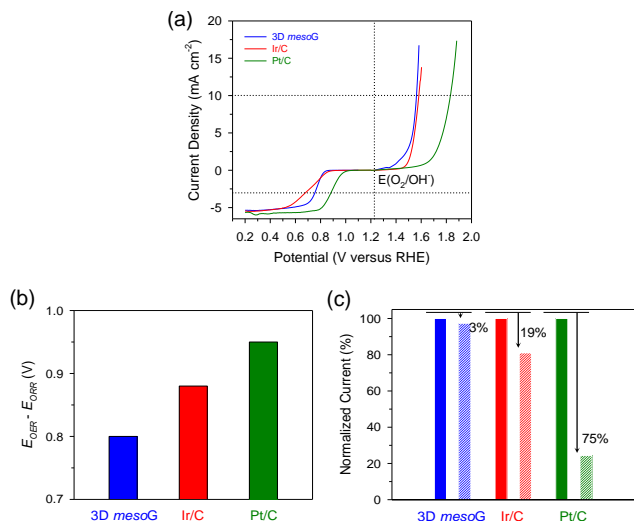


Fig. 3 Electrocatalytic activity and durability of 3D mesoG in OER and ORR. (a) Polarization curves showing ORR and OER activities of 3D mesoG, Ir/C, and Pt/C catalysts. (b) Bar graph showing the potential differences to drive 10 mA cm⁻² for OER and -3 mA cm⁻² for ORR. (c) The changes in relative current densities of 3D mesoG, Ir/C, and Pt/C catalysts for the OER before and after cycling tests.

stability of the 3D mesoG material can be attributed to the highly graphitic carbon framework, which appears in the aforementioned experiments to be more resistant to oxidation than amorphous carbon in Ir/C and Pt/C.

In conclusion, we describe a straightforward and cost effective method to synthesize 3D mesoporous graphene frameworks by thermally converting a NiII molecular coordination compound. The resulting 3D mesoG was composed of 3D interconnected hollow N-doped graphene shells consisting of 3 – 4 layers with small, uniform mesopores of ca. 4 nm. The 3D mesoG material exhibited high bifunctional electrocatalytic activity and durability in the ORR and OER, and in our hands was found to be superior to that of noble metal catalysts such as Pt/C and Ir/C. We believe that, similar to recent studies regarding the conversion of metal-organic frameworks,²⁴ this approach can be extended to a variety of porous graphene frameworks, including heteroatom-doped graphene and utilized as a high-performance material for use in energy conversion and storage applications. Furthermore, we envisage that the conversion of small molecular metal complexes into nanostructured materials can be exploited for the preparation of novel functional materials.

This work was supported by the Basic Science Research Program through the National Research Foundation (NRF) of Korea (NRF-2013R1A1A3010846; NRF-2013R1A1A2012960) as well as the IBS (IBS-R019-D1 to CWB).

Notes and references

^a Department of Chemistry, Ulsan National Institute of Science and Technology (UNIST), UNIST-gil 50, Ulsan 689-798, Republic of Korea. E-mail: hoirimoon@unist.ac.kr

^b UNIST Central Research Facilities (UCRF), Ulsan National Institute of Science and Technology (UNIST), UNIST-gil 50, Ulsan 689-798, Republic of Korea.

^c Center for Multidimensional Carbon Materials, Institute for Basic Science (IBS), Ulsan 689-798, Republic of Korea.

^d School of Energy and Chemical Engineering, Ulsan National Institute of Science and Technology (UNIST), UNIST-gil 50, Ulsan 689-798, Republic of Korea.

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c000000x/

- H. Y. Yang, Z. J. Han, S. F. Yu, K. L. Pey, K. Ostrikov, R. Karnik, *Nat. Commun.* 2013, **4**, 2220.
- (a) X. Ji, K. T. Lee, L. F. Nazar, *Nat. Mater.* 2009, **8**, 500; (b) C. Merlet, B. Rotenberg, P. A. Madden, P.-L. Taberna, P. Simon, Y. Gogotsi, M. Salanner, *Nat. Mater.* 2012, **11**, 306; (c) Y. Zhu, S. Murali, M. D. Stoller, K. J. Ganesh, W. Cai, P. J. Ferreira, A. Pirkle, R. M. Wallace, K. A. Cychoz, M. Thommes, D. Su, E. A. Stach, R. S. Ruoff, *Science*, 2011, **332**, 1537.
- (a) C. Su, K. P. Loh, *Acc. Chem. Res.* 2013, **46**, 2275; (b) D. S. Su, S. Perathoner, G. Centi, *Chem. Rev.* 2013, **113**, 5782; (c) S. Navalon, A. Dhakshinamoorthy, M. Alvaro, H. Garcia, *Chem. Rev.* 2014, **114**, 6179.
- Y. Zhu, S. Murali, W. Cai, X. Li, J. W. Suk, J. R. Potts, R. S. Ruoff, *Adv. Mater.* 2010, **22**, 3906.
- K. S. Kim, Y. Zhao, H. Jang, S. Y. Lee, J. M. Kim, K. S. Kim, J.-H. Ahn, P. Kim, J.-Y. Choi, B. H. Hong, *Nature* 2009, **457**, 706.
- A. A. Balandin, S. Ghosh, W. Bao, I. Calizo, D. Teweldebrhan, F. Miao, C. N. Lau, *Nano Lett.* 2008, **8**, 902.
- M. J. Allen, V. C. Tung, R. B. Kaner, *Chem. Rev.* 2010, **110**, 132.
- Z. Chen, W. Ren, L. Gao, B. Liu, S. Pei, H.-M. Cheng, *Nat. Mater.* 2011, **10**, 424.
- J.-C. Yoon, J.-S. Lee, S.-I. Kim, K.-H. Kim, J.-H. Jang, *Sci. Rep.* 2013, **3**, 1788.
- C. Cui, W. Qian, Y. Yu, C. Kong, B. Yu, L. Xiang, F. Wei, *J. Am. Chem. Soc.* 2014, **136**, 2256.
- (a) Z.-S. Wu, Y. Sun, Y.-Z. Tan, S. Yang, X. Feng, K. Müllen, *J. Am. Chem. Soc.* 2012, **134**, 19532; (b) L. Zhang, F. Zhang, X. Yang, G. Long, Y. Wu, T. Zhang, K. Leng, Y. Huang, Y. Ma, A. Yu, Y. Chen, *Sci. Rep.* 2013, **3**, 1408; (c) C. Wu, X. Huang, G. Wang, L. Lv, G. Chen, G. Li, P. Jiang, *Adv. Funct. Mater.* 2013, **23**, 506.
- (a) K. H. Kim, M. H. Yang, K. M. Cho, Y.-S. Jun, S. B. Lee, H.-T. Jung, *Sci. Rep.* 2013, **3**, 3251; (b) Z. Fan, J. Yan, L. Zhi, Q. Zhang, T. Wei, J. Feng, M. Zhang, W. Qian, F. Wei, *Adv. Mater.* 2010, **22**, 3723; (c) J. W. Burrell, S. Gadipelli, J. Ford, J. M. Simmons, W. Zhou, T. Yildirim, *Angew. Chem. Int. Ed.* 2010, **49**, 8902.
- T. K. Kim, J. Y. Cheon, K. Yoo, J. W. Kim, S. Hyun, H. S. Shin, S. H. Joo, H. R. Moon, *J. Mater. Chem. A* 2013, **1**, 8432.
- (a) S. Park, Y. Shao, J. Liu, Y. Wang, *Energy Environ. Sci.* 2012, **5**, 9331; (b) P. G. Bruce, S. A. Freunberger, L. J. Hardwick, J.-M. Tarascon, *Nat. Mater.* 2012, **11**, 19.
- E. Coronado, M. Drillon, A. Fuytes, D. Beltran, A. Mosset, J. Galy, *J. Am. Chem. Soc.* 1986, **108**, 900.
- M. Kumar, Carbon Nanotubes – Synthesis, Characterization, Applications. In *Carbon Nanotube Synthesis and Growth Mechanism* [Online]; Yellampalli, S., Ed.; InTech, 2011, Ch. 8. <http://www.intechopen.com/books/carbon-nanotubes-synthesis-characterization-applications/carbon-nanotube-synthesis-and-growth-mechanism> (accessed February 5, 2015).
- M. Anna, G. N. Albert, I. K. Esko, *J. Phys.: Condens. Matter* 2013, **15**, S3011.
- V. Georgakilas, M. Otyepka, A. B. Bourlino, V. Chandra, N. Kim, K. C. Kemp, P. Hobza, R. Zboril, K. S. Kim, *Chem. Rev.* 2012, **112**, 6156.
- (a) M. Sveningsson, R.-E. Morjan, O. A. Nerushev, Y. Sato, J. Bäckström, E. E. B. Campbell, F. Rohmund, *Appl. Phys. A* 2001, **73**, 409; (b) K. Kwok, W. K. S. Chiu, *Carbon* 2005, **43**, 437; (c) W. Li, H. Zhang, C. Wang, Y. Zhang, L. Xu, K. Zhu, S. Xie, *Appl. Phys. Lett.* 1997, **70**, 2684.
- C. K. Chun, M. Pumera, *Chem. Soc. Rev.* 2014, **43**, 291.
- R. Cao, J.-S. Lee, M. Liu, J. Cho, *Adv. Energy Mater.* 2012, **2**, 816.
- Y. Gorlin, T. F. Jaramillo, *J. Am. Chem. Soc.* 2010, **132**, 13612.
- Y. Zhao, R. Nakamura, K. Kamiya, S. Nakanishi, K. Hashimoto, *Nat. Commun.* 2013, **4**, 2390.
- (a) T. K. Kim, K. J. Lee, J. Y. Cheon, J. H. Lee, S. H. Joo, H. R. Moon *J. Am. Chem. Soc.* 2013, **135**, 8940. (b) J. H. Lee, Y. J. Sa, T. K. Kim, H. R. Moon, S. H. Joo, *J. Mater. Chem. A* 2014, **2**, 10435. (c) K. J. Lee, T.-H. Kim, T. K. Kim, J. H. Lee, H.-K. Song, H. R. Moon, *J. Mater. Chem. A* 2014, **2**, 14393.