

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Helical mesoporous silica as an inorganic heterogeneous chiral trigger for asymmetric autocatalysis with amplification of enantiomeric excess†

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Tsuneomi Kawasaki,^{a,b,†} Yuko Araki,^a Kunihiro Hatase,^a Kenta Suzuki,^a Arimasa Matsumoto,^a Toshiyuki Yokoi,^c Yoshihiko Kubota,^d Takashi Tatsumi^{c*} and Kenso Soai^{a,b*}

Mesoporous silica has been used as a heterogeneous support of catalysts; however, asymmetric induction by helicity of inorganic mesoporous silica itself has not yet been achieved. *P*- and *M*-Helical mesoporous silica was found to act as a chiral inorganic trigger of asymmetric autocatalysis to afford (*S*) and (*R*)-pyrimidyl alkanol with >99.5% ee, respectively.

Catalytic enantioselective synthesis has attracted much attention in the fields of materials science and pharmaceuticals, because it is a useful method for synthesizing a large amount of a chiral compound from an initial small amount of chiral compound.¹ From an environmental and economic point of view, asymmetric synthesis using heterogeneous inorganic materials is an emerging area, because these catalysts can be separated from a reaction mixture easily and their thermal and mechanical stability allows for the recovery and reuse of the catalyst.^{2,3}

On the other hand, research into well-ordered mesoporous materials has become a “hot area” in materials science⁴ because of their versatile applications in areas such as catalysis, adsorption, and drug delivery systems.⁵ Their extremely large surface area, uniform pore size, and well-defined pore shape enables them to act as selective catalysts. There are some examples of chiral catalyst supported on achiral mesoporous silica.⁶ However, to the best of our knowledge, there has been no report on asymmetric reaction induced by the chirality of inorganic helical mesoporous silica itself. Therefore, the use of mesoporous materials with a chiral inorganic framework presents a challenge in the field of asymmetric catalysis.

One of us synthesized chiral mesoporous silica using *N*-myristoyl alanine as a chiral anionic surfactant, which has a twisted hexagonal rod-like morphology, with dimensions of diameter = 130–180 nm and length 1–6 μm.⁷ Right-handed enriched (*P*)-helical mesoporous silica has been produced from a surfactant derived from D-alanine. In contrast, the L-isomer afforded left-handed enriched (*M*)-helical mesoporous silica (Fig. 1). To the best of our knowledge, there have been no reports on mesoporous silica mediated

asymmetric synthesis, in which the chiral inorganic structure induces the enantioselectivity.


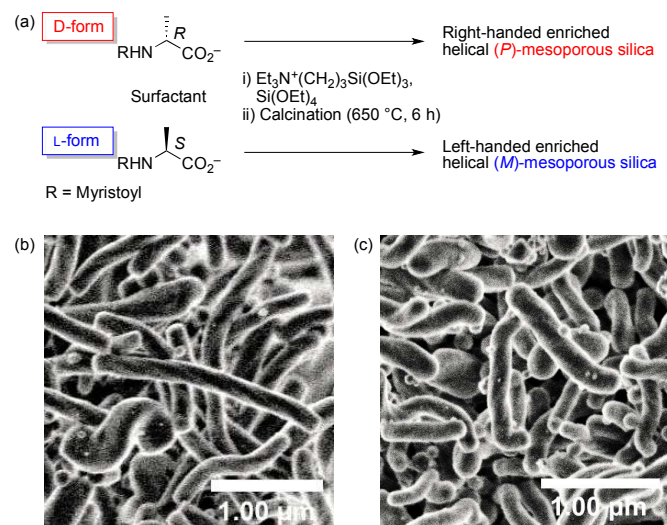


Fig. 1 Helical mesoporous silica. (a) A schematic representation of the stereochemical relationship between a chiral surfactant and the handedness of the helical mesoporous silica, and SEM images of (b) right-handed enriched (*P*)- and (c) left-handed enriched (*M*)-mesoporous silica.

Meanwhile, we have continued to study asymmetric autocatalysis with the amplification of enantiomeric excess (ee)⁸ where a chiral product acts as the chiral catalyst for its own production.⁹ Chiral compounds can act as the source of chirality in the addition reaction of diisopropylzinc (*i*-Pr₂Zn) to aldehydes to give highly enantioenriched alkanols in combination with asymmetric autocatalysis.^{10–14}

Here, we report that chiral mesoporous silica acts as a heterogeneous chiral catalyst in the enantioselective addition of

$i\text{Pr}_2\text{Zn}$ to pyrimidine-5-carbaldehyde **1** to afford, in combination with asymmetric autocatalysis, 5-pyrimidyl alkanol **2** with a high ee (Scheme 1).

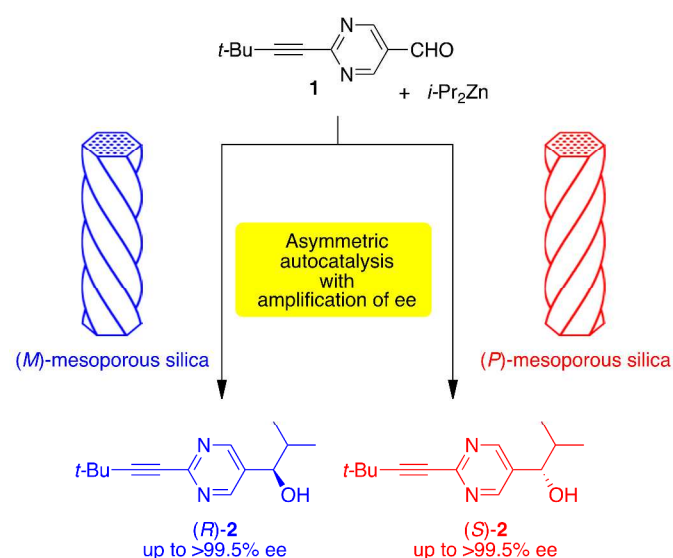

Scheme 1 Highly enantioselective synthesis of the 5-pyrimidyl alkanol **2** using chiral mesoporous silica as a heterogeneous solid catalyst in the reaction between $i\text{-Pr}_2\text{Zn}$ and pyrimidine-5-carbaldehyde **1**.

The results of asymmetric autocatalysis in the presence of helical mesoporous silica⁷ are summarized in Table 1. In the presence of right-handed enriched helical (*P*)-mesoporous silica (Sample A) with approximately 52% ee, (*S*)-5-pyrimidyl alkanol with a 97% ee was obtained in a 92% isolated yield from the reaction of pyrimidine-5-carbaldehyde **1** and $i\text{-Pr}_2\text{Zn}$ (entry 1). When Sample A with a (*P*)-helicity was used as the chiral promoter, the same stereochemical outcome was observed, *i.e.*, 5-pyrimidyl alkanol **2** with *S* chirality was produced in a reproducible manner (entries 2 and 3). In sharp contrast, left-handed enriched (*M*)-mesoporous silica Sample B promoted the formation of (*R*)-pyrimidyl alkanol **2** with an 80% ee in an 85% yield (entry 4). The stereochemical correlation using Sample B was reproducible and afforded 5-pyrimidyl alkanol **2** possessing *R*-chirality (entries 5 and 6). For entries 7 and 8, another sample of helical mesoporous silica, Sample C, was subjected to asymmetric autocatalysis. The correlation between the enrichment of the (*P*)-helicity of the silica and the (*S*)-configuration of alkanol **2** was reproduced well (entries 7 and 8). The formation of (*R*)-**2** was reproducible when chiral (*M*)-enriched mesoporous silica Samples D and E were utilized as the chiral promoter of asymmetric autocatalysis, (entries 9–11). It should be noted that near enantiopure products (*S*)- and (*R*)-**2** with >99.5% ee could be obtained by consecutive asymmetric autocatalysis (entries 8 and 10, respectively).^{8b}

Table 1 Asymmetric autocatalysis induced by helical mesoporous silica^a

Entry	Mesoporous silica ^b			5-Pyrimidyl Alkanol 2		
	Lot #	Chirality	ee ^c (%)	Yield (%) ^d	ee ^e (%)	Config
1 ^f	A	<i>P</i>	52	92	97	<i>S</i>
2	A	<i>P</i>	52	92	92	<i>S</i>
3	A	<i>P</i>	52	91	86	<i>S</i>
4	B	<i>M</i>	19	85	80	<i>R</i>
5	B	<i>M</i>	19	83	82	<i>R</i>
6	B	<i>M</i>	19	78	97	<i>R</i>
7	C	<i>P</i>	39	87	92	<i>S</i>
8	C	<i>P</i>	39	85	96 (>99.5) ^g	<i>S</i>
9	D	<i>M</i>	26	89	86	<i>R</i>
10	D	<i>M</i>	26	93	93 (>99.5) ^g	<i>R</i>
11	E	<i>M</i>	22	91	94	<i>R</i>

^a The molar ratio used was chiral mesoporous silica (SiO_2) : pyrimidine-5-carbaldehyde **1** : $i\text{-Pr}_2\text{Zn}$ = 0.09 : 0.53 : 1.18. ^b Helical mesoporous silica was prepared according to the reported method. ^{7c} The ee of the chiral mesoporous silica was checked using SEM images from each sample (see the ESI†). ^d Isolated yield. ^e The ee was determined using HPLC employing a chiral stationary phase. ^f The typical experimental procedure used is as follows: To a mixture of right-handed enriched (*P*)-mesoporous silica (30 mg) with *ca.* 52% ee and pyrimidine-5-carbaldehyde **1** (9.4 mg, 0.05 mmol), was added a solution of $i\text{-Pr}_2\text{Zn}$ (0.15 mmol, 0.15 mL of 1 M toluene solution) at 0 °C, and the mixture was then stirred for 4 h. After the addition of toluene (4.75 mL), $i\text{-Pr}_2\text{Zn}$ (0.4 mmol, 0.4 mL of a 1 M toluene solution) was added over a period of 30 min at 0 °C. After stirring the mixture for 15 min, a solution of **1** (37.6 mg, 0.2 mmol) in toluene (1.5 mL) was added over a period of 1.5 h. After the mixture was left stirring overnight, toluene (14.4 mL) and a solution of $i\text{-Pr}_2\text{Zn}$ (1.6 mmol, 1.6 mL of 1 M toluene solution) was added successively, and the resulting mixture was stirred for a further 20 min. A solution of **1** (150.6 mg, 0.8 mmol) in toluene (4.0 mL) was then added over a period of 1 h at 0 °C. After stirring for a further 2 h, the reaction was quenched using 1 M hydrochloric acid (5 mL), and neutralized with a saturated sodium hydrogen carbonate solution (15 mL). The mixture was then filtered using Celite, and the filtrate extracted three times using ethyl acetate. The combined organic layers were dried over anhydrous sodium sulfate and evaporated *in vacuo*. Purification of the residue using silica gel column chromatography (hexane/ethyl acetate = 3/1, *v/v*) gave the (*S*)-5-pyrimidyl alkanol **2** (225 mg, 0.968 mmol) with a 97% ee in a yield of 92%. The ee was determined using HPLC employing a chiral stationary phase (Daicel Chiralcel OD-H, 4.6 × 250 mm, eluent: 2-propanol/hexane = 5/95 (*v/v*), flow rate: 1.0 mL min⁻¹, 254 nm UV detector, retention time: 10.1 min for (*S*)-**2**, 15.1 min for (*R*)-**2**). ^g After carrying out a typical experimental procedure, additional rounds of consecutive asymmetric autocatalysis were performed.^{8b}

Asymmetric autocatalysis is a very powerful reaction for detecting low levels of chirality (crypto chirality) in a substance,¹⁵ and therefore, to ensure that the reason that asymmetric induction that occurred was because of the helical structure of the mesoporous silica, thermal analysis (TG-DTA) was performed. As shown in Fig. 2, the organic part completely disappeared around 600 °C. Since the chiral mesoporous silica was prepared by calcining the composite precursor at 650 °C for 6 h, only the chiral inorganic framework would remain to act as the chiral source for the enantioselective reaction.¹⁶

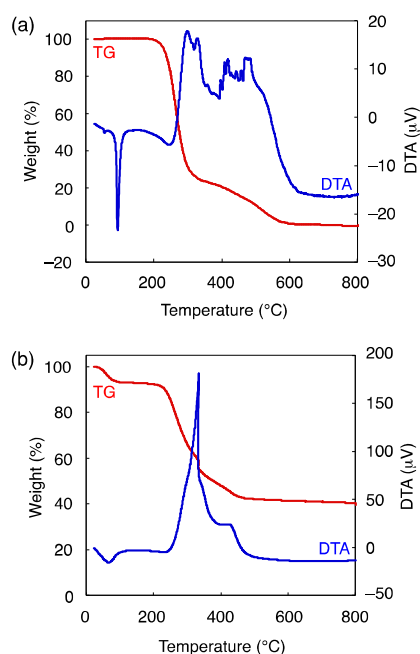


Fig 2 Thermal analysis (TG/DTA) of (a) *N*-myristoyl-L-alanine (5.4 mg, 10 °C/min, air, 30 mL/min) and (b) the surfactant/silica composite (10.1 mg, 10 °C/min, air, 30 mL/min).

The enantioselectivity observed in this reaction can be explained as follows:¹⁷ (1) Asymmetric activation of *i*-Pr₂Zn by the chiral mesoporous silica induces the formation of a chiral zinc species that enables the enantioselective addition to aldehyde **1**. (2) Enantiotopic face selective adsorption of the achiral pyrimidine-5-carbaldehyde **1** to the helical surface of the chiral mesoporous silica enables the addition of *i*-Pr₂Zn onto the preferred face. (3) Enantioselective adsorption of the initially formed zinc alkoxide of pyrimidyl alkanol **2** induces an enantiomeric imbalance in the reaction solution. Then, the induced enantiomeric imbalance is amplified to provide the overwhelming enantioenrichment of product **2** by subsequent asymmetric autocatalysis.^{8b}

In conclusion, a highly enantioselective addition of diisopropylzinc to pyrimidine-5-carbaldehyde **1** was achieved to afford a highly enantioenriched organic compound by utilizing chiral mesoporous silica as a source of chirality in conjunction with asymmetric autocatalysis. We have clearly demonstrated that helical mesoporous silica has the capability, from its large reactive surface, to be responsible for the enantioselective addition of *i*-Pr₂Zn to pyrimidine-5-carbaldehyde **1**. We believe that these results show the potential for using the large reactive surface of chiral mesoporous silica for asymmetric reactions as a chiral inorganic catalyst.

This work was supported by a Grant-in-Aid for Scientific Research from Japan Society for the Promotion of Science (JSPS) and by MEXT-Supported Program for the Strategic Research Foundation at Private Universities, 2012–2016..

Notes and references

^a Department of Applied Chemistry, Tokyo University of Science, Kagurazaka, Shinjuku-ku, Tokyo, 162-8601, Japan. E-mail: soai@rs.kagu.tus.ac.jp

^b Research Center for Chirality, Research Institute for Science and Technology (RIST), Tokyo University of Science, Kagurazaka, Shinjuku-ku, Tokyo, 162-8601, Japan..

^c Chemical Resources Laboratory, Tokyo Institute of Technology, Nagatsuta, Midori-ku, Yokohama 226-8503, Japan. E-mail: ttatsumi@cat.res.titech.ac.jp

^d Division of Materials Science and Chemical Engineering, Yokohama National University, 79-5, Tokiwadai, Hodogaya-ku, Yokohama, 240-8501, Japan.

† Electronic Supplementary Information (ESI) available: See DOI: 10.1039/c000000x/

‡ Present address: Department of Materials Science and Engineering, University of Fukui, Bunkyo, Fukui, 910-8507, Japan.

- (a) *Catalytic Asymmetric Synthesis*, Third Edition (Ed: I. Ojima), John Wiley & Sons Inc, Hoboken, New Jersey, 2010; (b) *Comprehensive Asymmetric Catalysis I-III* (Eds: E. N. Jacobsen, A. Pfaltz and H. Yamamoto), Springer-Verlag, Berlin, 1999.
- (a) C. E. Song and S-g. Lee, *Chem. Rev.*, 2002, **102**, 3495–3524; (b) M. Heitbaum, F. Glorius and I. Escher, *Angew. Chem. Int. Ed.*, 2006, **45**, 4732–4762 and references cited therein.
- (a) P. McMorn and G. J. Hutchings, *Chem. Soc. Rev.*, 2004, **33**, 108–122; (b) K. Soai, M. Watanabe and A. Yamamoto, *J. Org. Chem.*, 1990, **55**, 4832–4835; (c) K. C. W. Chong, J. Sivaguru, T. Shichi, Y. Yoshimi, V. Ramamurthy and J. R. Scheffer, *J. Am. Chem. Soc.*, 2002, **124**, 2858–2859; (d) S. Fujita, H. Sato, N. Kakegawa and A. Yamagishi, *J. Phys. Chem. B*, 2006, **110**, 2533–2540.
- (a) B. Lebeau, A. Galarnau and M. Linden, *Chem. Soc. Rev.*, 2013, **42**, 3661–3662; (b) C. T. Kresge and W. J. Roth, *Chem. Soc. Rev.*, 2013, **42**, 3663–3670; (c) T. Yanagisawa, T. Shimizu, K. Kuroda and C. Kato, *Bull. Chem. Soc. Jpn.*, 1990, **63**, 988–992 and references cited therein.
- Reviews: (a) J. Y. Ying, C. P. Mehnert and M. S. Wong, *Angew. Chem. Int. Ed.*, 1999, **38**, 56–77; (b) M. E. Davis, *Nature*, 2002, **417**, 813–821; (c) D. Trong, D. Desplandier-Giscard, C. Danumah and S. Kaliaguine, *Appl. Catal. A*, 2003, **253**, 545–602; (d) T. Yokoi, Y. Kubota and T. Tatsumi, *Applied Catal. A*, 2012, **421–422**, 14–37; (e) S. Kwon, R. K. Singh, R. A. Perez, E. A. Abou Neel, H.-W. Kim and W. Chrzanowski, *J. Tissue Engineering* 2013, **4**, 1–19; (f) N. Gargiulo, F. Pepe and D. Caputo, *J. Nanoscience Nanotechnology*, 2014, **14**, 1811–1822; (g) L. Wang and F.-S. Xiao, *Green Chem.*, 2015, **17**, 24–39.
- For example, (a) E. Gross, J. H. Liu, S. Alayoglu, M. a Marcus, S. C. Fakra, F. D. Toste, and G. A. Somorjai, *J. Am. Chem. Soc.*, 2013, **135**, 3881–3886; (b) R. Raja, J. M. Thomas, M. D. Jones, B. F. G. Johnson and D. E. W. Vaughan, *J. Am. Chem. Soc.*, 2003, **125**, 14982–14983.
- (a) S. Che, Z. Liu, T. Ohsuna, K. Sakamoto, O. Terasaki and T. Tatsumi, *Nature*, 2004, **429**, 281–284; (b) T. Yokoi, K. Ogawa, D. Lu, J. Kondo, Y. Kubota and T. Tatsumi, *Chem. Mater.*, 2011, **23**, 2014–2016; (c) T. Yokoi, S. Sato, Y. Ara, D. Lu, Y. Kubota and T. Tatsumi, *Adsorption*, 2010, **16**, 577–586.
- (a) K. Soai, T. Shibata, H. Morioka and K. Choji, *Nature*, 1995, **378**, 767–768; (b) I. Sato, H. Urabe, S. Ishiguro, T. Shibata and K. Soai, *Angew. Chem. Int. Ed.*, 2003, **42**, 315–317.
- For the mechanistic analyses of asymmetric autocatalysis see: (a) I. Sato, D. Omiya, H. Igarashi, K. Kato, Y. Ogi, K. Tsukiyama and K. Soai, *Tetrahedron: Asymmetry*, 2003, **14**, 975–979; (b) M. Quaranta, T. Gehring, B. Odell, J. M. Brown and D. G. Blackmond, *J. Am.*

- Chem. Soc.*, 2010, **132**, 15104–15107; (c) G. Ercolani and L. Schiaffino, *J. Org. Chem.*, 2011, **76**, 2619–2626; (d) J.-C. Micheau, C. Coudret, J.-M. Cruz and T. Buhse, *Phys. Chem. Chem. Phys.*, 2012, **14**, 13239–13248; (e) T. Gehring, M. Quaranta, B. Odell, D. G. Blackmond and J. M. Brown, *Angew. Chem. Int. Ed.*, 2012, **51**, 9539–9542; (f) I. D. Gridnev and A. K. Vorobiev, *ACS Catal.*, 2012, **2**, 2137–2149; (g) I. D. Gridnev and A. K. Vorobiev, *Bull. Che. Soc. Jpn.*, 2015, **88**, 333–340.
- 10 Reviews by us: (a) K. Soai, T. Kawasaki and A. Matsumoto, *Acc. Chem. Res.*, 2014, **47**, 3643–3654; (b) T. Kawasaki and K. Soai, *Bull. Chem. Soc. Jpn.*, 2011, **84**, 879–892; (c) K. Soai, T. Kawasaki and A. Matsumoto, *Chem. Record*, 2014, **14**, 70; (d) T. Kawasaki, I. Sato, H. Mineki, A. Matsumoto and K. Soai, *Yuki Gosei Kagaku Kyokaishi (J. Synth. Org. Chem. Jpn.)*, 2013, **71**, 109–123; (e) K. Soai and T. Kawasaki, *Top. Organomet. Chem.*, 2013, **44**, 261–280; (f) T. Kawasaki and K. Soai, *Isr. J. Chem.*, 2012, **52**, 582–590.
- 11 Reviews by others: (a) J.-K. Micheau, C. Coudret and T. Buhse, in *The Soai Reaction and Related Topic* (Eds: G. Palyi, C. Zucchi and L. Caglioti), Accad. Nazl. Sci. Lett. Arti, Artestampa, Modena, 2012, pp. 169–196; (b) T. Gehring, M. Busch, M. Schlageter and D. Weingand, *Chirality*, 2010, **22**, E173–E182; (c) B. Barabas, J. Toth and G. Palyi, *J. Mathematical Chem.*, 2010, **48**, 457–489; (d) G. Lente, *Symmetry*, 2010, **2**, 767–798; (e) J. M. Brown, I. Gridnev and J. Klankermayer, *Top. Curr. Chem.*, 2008, **284**, 35–65; (f) L. Caglioti and G. Palyi, *Chimica Oggi*, 2008, **26**, 41–42; (g) A. J. Bissette and S. P. Fletcher, *Angew. Chem. Int. Ed.*, 2013, **52**, 12800–12826; (h) J. Podlech and T. Gehring, *Angew. Chem. Int. Ed.*, 2005, **44**, 5776–5777.
- 12 Asymmetric autocatalysis initiated with chiral inorganic materials such as amorphous silica, silsesquioxane, synthetic hectorite, sodium chlorate and cinnabar, see: a) I. Sato, K. Kadowaki, H. Urabe, J. Hwa Jung, Y. Ono, S. Shinkai and K. Soai, *Tetrahedron Lett.*, 2003, **44**, 721–724; (b) T. Kawasaki, K. Ishikawa, H. Sekibata, I. Sato and K. Soai, *Tetrahedron Lett.*, 2004, **45**, 7939–7941; (c) T. Kawasaki, T. Omine, K. Suzuki, H. Sato, A. Yamagishi and K. Soai, *Org. Biomol. Chem.*, 2009, **7**, 1073–1075; (d) I. Sato, K. Kadowaki and K. Soai, *Angew. Chem. Int. Ed.*, 2000, **39**, 1510–1512; (e) H. Shindo, Y. Shirota, K. Niki, T. Kawasaki, K. Suzuki, Y. Araki, A. Matsumoto and K. Soai, *Angew. Chem. Int. Ed.*, 2013, **52**, 9135–9138.
- 13 *d* and *l*-Quartz (SiO₂) promoted asymmetric autocatalysis see: K. Soai, S. Osanai, K. Kadowaki, S. Yonekubo, T. Shibata and I. Sato, *J. Am. Chem. Soc.*, 1999, **121**, 11235–11236.
- 14 Spontaneous absolute asymmetric synthesis mediated by achiral silica gel, see: T. Kawasaki, K. Suzuki, M. Shimizu, K. Ishikawa and K. Soai, *Chirality*, 2006, **18**, 479–482.
- 15 (a) T. Kawasaki, Y. Matsumura, T. Tsutsumi, K. Suzuki, M. Ito and K. Soai, *Science*, 2009, **324**, 492–495; (b) T. Kawasaki, H. Tanaka, T. Tsutsumi, T. Kasahara, I. Sato and K. Soai, *J. Am. Chem. Soc.*, 2006, **128**, 6032–6033; (c) T. Kawasaki, C. Hohberger, Y. Araki, K. Hatase, K. Beckerle, J. Okuda and K. Soai, *Chem. Commun.*, 2009, 5621–5623; (d) T. Kawasaki, Y. Okano, E. Suzuki, S. Takano, S. Oji and K. Soai, *Angew. Chem. Int. Ed.*, 2011, **50**, 8131–8133.
- 16 The direction of asymmetric induction has been examined employing *N*-myristoyl-D-alanine and its L-isomer as chiral initiators of asymmetric autocatalysis, respectively (see the ESI†).