

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

CaO nanocrystals grown over SiO₂ microtubes for efficient CO₂ capture: Organogel sets the platform

Received 00th January 20xx,
Accepted 00th January 20xx

Annamalai Prathap,^a M. M. Shaijumon^b and Kana M. Sureshan^{*a}

DOI: 10.1039/x0xx00000x

www.rsc.org/

Materials that can capture and store CO₂ are important. Though CaO is a cheap sorbent, it is inefficient for practical purposes due to sintering and poor diffusion of CO₂ through the surface-CaCO₃ layer. We have developed a high performance, sintering-resistant CaO-based sorbent by uniformly nanofabricating the CaO nanocrystals on SiO₂ microtubes made by organogel templated polymerization.

There is serious concern about excessive levels of the greenhouse gas, CO₂, being spewed out to the atmosphere everyday as it contributes to global warming and the subsequent climate change.¹ At the same time, CO₂ is an important and cheap precursor for the production of several useful chemicals (*e.g.* methanol, dimethyl ether *etc.*).² Also, an efficient method for power production using CO₂ gas has been recently proposed.³ Importantly, Lithium/CO₂ rechargeable battery is an emerging system for efficient energy storage.⁴ Hence CO₂ capture and storage (CCS) is important and materials that can adsorb/absorb CO₂ are of great interest.⁵ The reversibility of the carbonation of CaO to CaCO₃ has prompted researchers to explore quick lime (CaO) as a cheap and recyclable sorbent for CCS.⁶ However, the carbonation reaction is not very efficient due to 'sintering'^{6b,7} (aggregation of CaO crystals/particles upon carbonation resulting in the reduction of the surface area) and the consequent inaccessibility of CaO in the inner part of aggregates for carbonation owing to the poor diffusion of CO₂ through the CaCO₃ layer formed on the surface. It is essential to increase the surface area-to-volume ratio of the active CaO sorbent to minimize the effect of sintering.^{6c} As powdered CaO aggregate upon several cycles of carbonation and calcination, they are also not suitable for practical purpose.⁸ This has led

researchers to use CaO adsorbed on inert matrices such as silica.⁹ Though physical blend of CaO and silica has been used, the efficiency is not satisfactory after a few cycles presumably due to the phase separation into individual phases.¹⁰ Exploiting the use of structured silica as the matrix for the first time, we herein report an efficient sintering-resistant and economically viable sorbent that can be used for the multiple carbonation-calcination cycles.

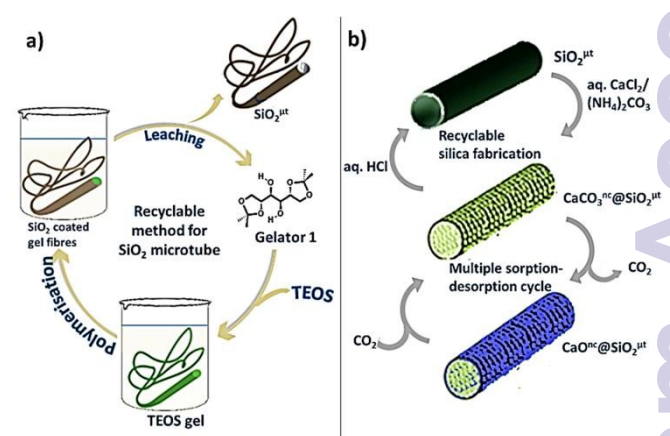


Fig. 1 Schematic proposal for (a) large-scale preparation of hollow silica microtubes using recyclable organogel-templated polymerization; (b) use of silica microtubes as platform for growing CaO nanocrystals and their use as sintering-free sorbent for multi-cycle calcium looping.

We envisioned that, in order to prevent phase separation and thus the ensuing sintering, it is necessary to immobilize the nanosized CaO particles uniformly on a high-surface-area matrix. Also, it has been known CaCO₃ layer of thickness above 50 nm would limit the diffusion of CO₂ through it.^{6b} In this context, we planned to decorate nanoparticles of CaO on micro-structured silica forms. As hollow tubes give maximum surface area due to the availability of inner and outer surfaces for nanofabrication, we planned to grow nanocrystals of CaO (CaO^{nc}) on silica microtubes (SiO₂^{mt}).

^a School of Chemistry, Indian Institute of Science Education and Research Thiruvananthapuram, Kerala, 695016, India. Fax: (+) 0091-4712597427; Tel: +914712599412; E-mail: kms@iisertvm.ac.in. Home page: <http://kms514.wix.com/kmsgroup>

^b School of Physics, Indian Institute of Science Education and Research Thiruvananthapuram, Kerala, 695016, India.

† Electronic Supplementary Information (ESI) available: [Experimental details, TEM, SEM images, SEM-EDAX, IR]. See DOI: 10.1039/b000000x/

Organogels, formed by the entrapment of solvent by the superstructures formed as a result of the self-assembly of low molecular mass organogelators (LMOG), are attractive materials and have been exploited for various applications.^[11] Shinkai *et al.* demonstrated that the microstructures of organogels can be used as templates to synthesize microstructured silica of different shapes¹² by polymerising TEOS on the gel fibres followed by removal of the gelator by calcination. Though elegant, this usual method is not suitable for the large scale preparation of silica tubes. For templating, the attraction between anionic silica species and the gel fibres is important¹³ and hence the gelators exploited for the preparation of silica tubes are complex molecules with cationic moiety in them. Gelations of such special molecules often require a special mixture of solvents (*eg.* mixture of acetic acid and DMSO) and SiO₂ precursor (TEOS) needs to be introduced at a later stage. The usual method of destructive removal (calcination) of the template is not practical for large scale preparation of SiO₂ tubes. For large scale preparation of silica tubes, it is essential to (i) use a simple, cheap and easy-to-prepare gelator as the template, (ii) the gelator should be able to congeal the silica precursor TEOS, (iii) develop a method for recovering and recycling the gelator instead of calcining. Screening of various gelators we have developed in our lab,¹⁴ revealed that 1,2;5,6-di-*O*-isopropylidene mannitol **1** (Fig. 1a) could congeal TEOS without a co-solvent, which makes the envisioned process easy. Also SEM analysis of the xerogel made from TEOS gel of **1** showed fibrillar morphology of the self-assembled gelator (Fig. 2a).

As the gelator **1** is known to interact with anions through hydrogen bonding,¹⁵ we wondered whether the hydrogen bonded gel fibers of **1** can be used as template for the preparation of silica tubes. It is anticipated that the hydrogen bonding interaction between the gelator network and the silanol produced in situ upon hydrolysis of TEOS would bring the template effect.¹⁶ In order to initiate the polymerization, catalytic amounts of benzylamine and water were added to 6 wt% TEOS gel of compound **1**. It was observed that after the templated polymerization, the volatile TEOS and the ethanol produced in the polymerization underwent evaporation to yield only SiO₂-coated gelator fibres. (†ESI Fig. S1). As the gelator **1** is a simple uncharged molecule, the gel template could be extracted with dichloromethane and methanol to obtain hollow silica tubes. The recovered gelator could be reused multiple times for the preparation of SiO₂ tubes. Thus, this method is advantageous over the traditional method of destroying the gelator/template by calcination.

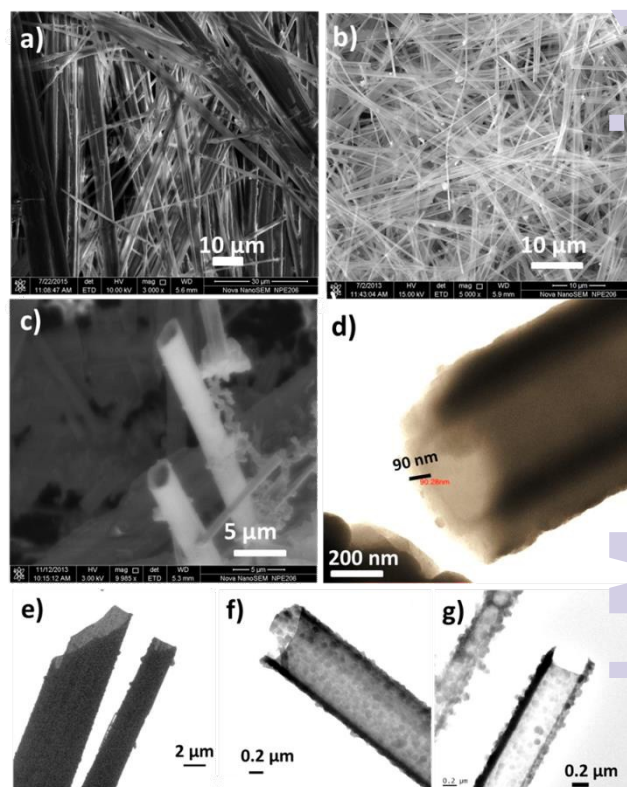


Fig. 2 a) SEM image of xerogel of **1** made from its TEOS gel. (b) SEM image of the silica microtubes made from 6 wt% gel of **1** in TEOS. (c) SEM image showing the hollow tubes. (d) TEM image of the cross section of a silica tube showing a wall thickness of ~90 nm. (e-g) TEM images of silica tubes made from 13 wt%, 10 wt% and 6 wt% gel of **1** in TEOS respectively showing different diameters.

Analysis of the polymerized silica by SEM revealed that the fibrillar morphology as in the organogel is preserved even after transcription to silica and tubes of several micrometres length could be seen (Fig. 2b). Both SEM and TEM analyses indicated that the silica fibres have hollow tubular structure (Fig. 2c-d, †ESI Fig. S2). These tubes have a wall thickness of around 90 nm as evidenced from TEM analysis (Fig. 2d). SEM-EDAX (Energy dispersive X-ray spectroscopy) analysis has shown peaks due to SiO₂ only suggesting that the gelator **1** has been completely removed during washing (†ESI Fig. S3). The IR spectrum of the silica microtubes matched with that of the commercial silica (200-400 mesh) sample (†ESI Fig. S4). The PXRD data of these silica tubes suggested that they are amorphous in nature (†ESI Fig. S5). BET surface area analysis revealed that these silica tubes have large surface area as anticipated. (†ESI Fig. S6). Interestingly, the average diameter of the tubes could be tuned from nanometers to micrometres by changing the concentration of the gelator as suggested by SEM (†ESI Fig. S7) and TEM (Fig. 2e-2g) analyses. Upon increasing the gelator concentration, the gel fibres of large diameters are formed. Templated TEOS polymerization over these fibres leads to the formation of silica tubes of large diameters. For instance, the use of TEOS gels having gelator concentrations of 13 wt%, 10 wt% and 6 wt% as template yielded silica tubes of average diameters of 2 μm (Fig. 2e), 700 nm (Fig. 2f) and 500 nm (Fig. 2g) respectively as evidenced

from TEM analyses. Though inconsequential, the length of the tubes is not amenable to tuning by this method. To the best of our knowledge, this is the first report on the synthesis of size controllable SiO₂ tubes using organogels as the template.

Having achieved a scalable method for large-scale preparation of silica microtubes, without losing the template, we next attempted for growing nanocrystals of CaO on the surfaces of these hollow tubes. Initially, CaCO₃ nanocrystals were grown by keeping a suspension of silica microtubes in calcium chloride solution in a closed desiccator containing solid ammonium carbonate. The *in situ* generated CO₂ gas slowly diffuse into the aqueous solution and the carbonic acid thus generated reacts with CaCl₂ to give CaCO₃.¹⁷ This slow diffusion is important for slow growth and uniform distribution of CaCO₃ over the silica tube surface.

The morphology of the hollow tubes remained unchanged even after the "carbonation" as evidenced from SEM (Fig. 3a) and TEM (Fig. 3b) analyses. Depending on the concentration of CaCl₂ solution and the exposure time, the amount of CaCO₃ formed over the silica tubes could be tuned as evidenced from the weight of the composites made under different conditions (†ESI) and from SEM-EDAX analyses of these materials after calcination to CaO (†ESI Fig. S8). For instance, the more the concentration of CaCl₂ or the more is the exposure time, the more is the CaCO₃ loading. TEM analysis revealed the granular morphology and the distribution of CaO nanocrystals over silica tubes. (†ESI Fig. S10). PXRD analysis of the CaCO₃-coated silica tubes showed the presence of fcc nanocrystals of CaCO₃ (Fig. 3c).¹⁸ SEM-EDAX mapping revealed the uniform distribution of CaO nanocrystals on silica tubes (†ESI Fig. S11). The carbonated tubes were calcined at 800 °C to convert the nanocrystals of CaCO₃ to nanocrystals of CaO on silica tubes. Even after calcination, the tubular morphology is maintained as evidenced from SEM analysis (†ESI Fig. S12). PXRD analysis of the tubes after calcination proved the crystalline nature of CaO (Fig. 3d) on the amorphous silica.

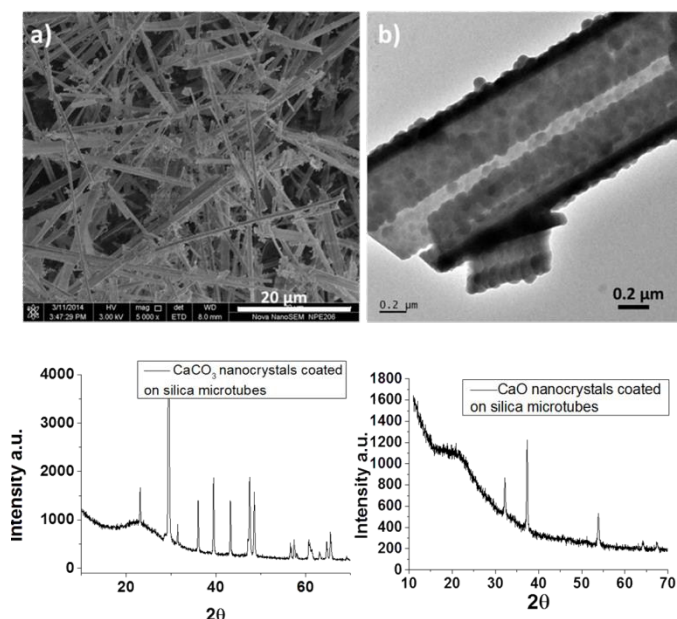


Fig. 3 a) SEM image of silica microtubes after growing CaCO₃ nanocrystals over their surface. b) TEM image of the CaCO₃^{nc}-grown-SiO₂^{mt} microtubes, showing the growth of CaCO₃ nanocrystals on either surface of the SiO₂ tubes. c) PXRD spectrum of CaCO₃-grown on SiO₂ microtubes showing crystalline CaCO₃ over amorphous SiO₂. d) PXRD spectrum of CaO-SiO₂ microtubes showing crystalline CaO over amorphous SiO₂.

The CO₂ sorption and desorption studies were done in a TGA instrument using a CaO^{nc}@SiO₂^{mt} sample having 33%, by weight, of CaO. The carbonation was done at 760 °C and the calcination at 800 °C. The CO₂ uptake was found to be 22 wt% in the first cycle and 10 wt% at the 30th cycle with respect to the whole composite (Fig. 4a). This corresponds to 30 wt% absorption with respect to the active CaO sorbent even at the 30th cycle. The average CO₂ uptake for 30 cycles is 0.37 g per gram of active sorbent (CaO), which is the best among the SiO₂-based CaO sorbents reported so far.^{6b}

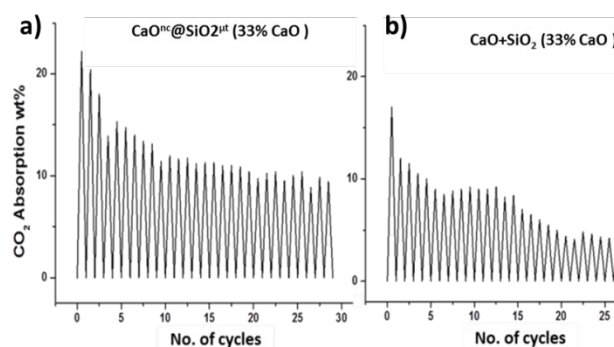


Fig. 4 TGA data showing the CO₂ absorption-desorption capacity over 30 cycles of a) CaO^{nc}@SiO₂^{mt} b) Physically blended SiO₂ and CaO.

From the TGA data, it is clear that the CO₂ uptake capacity of CaO^{nc}@SiO₂^{mt} decreases only gradually unlike a sudden drop in the case of only CaO.¹⁹ In cases of pure CaO (†ESI Fig. S13), and a physical blend of SiO₂ and CaO (Fig. 4b), the CO₂ capture efficiencies were decreased by 34% and 27% respectively, in the second cycle, relative to the first cycle due to sintering. Remarkably, only a relative reduction of 7.6% (1.7 absolute %) was observed in the case of CaO^{nc}@SiO₂^{mt}. After the fifth cycle, the drop in efficiency is less than 1% between two successive cycles and after the 10th cycle the uptake capacity is almost stable. This remarkable 30 wt% absorption with respect to CaO even at the 30th cycle is possible only because of the negligible sintering due to the uniform distribution of CaO nanocrystals over the high surface area silica microtubes. On the other hand, a physical blend of silica and CaO in the same ratio as the tubes showed a sudden decrease to 7% (Fig. 4b) by the 7th cycle and the efficiency kept on decreasing. Usually, owing to the slow diffusion of CO₂ to the bulk of the CaO sorbent, each carbonation-calcination cycle is lengthy (100 min/cycle) and hence are not practically feasible when multi-cycle process is envisioned.²⁰ Remarkably, due to the nanofabrication in our case, the rate of absorption and release of CO₂ is very fast and hence each carbonation-calcination cycle can be done in 20 minutes. Also the absorption happens even at low CO₂ pressure (14 sccm and 5 Psi).

The SEM image of the silica tubes recorded even after 30 cycles clearly shows the robustness and structural integrity of the silica tubes (†ESI Fig. S14). This has motivated us to investigate the recyclability of these silica tubes. For this, the tubes were washed with dilute HCl solution, which dissolved the CaCO₃/CaO to regenerate the pure silica tubes. These regenerated tubes were also morphologically intact as evidenced from SEM analysis (†ESI Fig. S15). These regenerated microtubes could be reused for growing CaO nanocrystals again and for new rounds of carbonation calcination cycles.

In summary, capture and storage of CO₂ is an important issue of current emergency. Though CaO can stoichiometrically and reversibly react with CO₂, CaO-based sorbents are not efficient for practical purpose due to sintering. The most important criterion to prevent the sintering and to increase the capturing capacity is to increase the surface area by manipulating CaO at the nano level with uniform distribution. We have addressed this problem by decorating nanocrystals of CaO on SiO₂ microtubes. SiO₂ microtubes of tuneable thickness were easily prepared via sol-gel transcription method using a cheaply available organogelator as the template and through a method that allows the recovery and recycling of the gelator. We have fabricated nanocrystals of CaO on these silica microtubes and demonstrated its superior efficiency in CO₂ uptake and release. This robust composite could be used for multiple carbonation and calcinations cycles without compromising the efficiency. The robust nature of the silica tubes allows recycling of these microtubes for multiple rounds of nanofabrication with CaO. This is the first use of structured silica for such an application. This report of the development of a high-performance, sintering-free sorbent for calcium looping not only offers a method for possible adoption in practical applications but also demonstrates the importance of supramolecular chemistry in tackling such practical problems.

We thank Mr. Binson Babu for his help in BET analyses. KMS thanks Department of Science and Technology, India for a SwarnaJayanti Fellowship.

Notes and references

- (a) IPCC Special Report on Carbon Dioxide Capture and Storage (Eds.: B. Metz, O. J. G. J. Davidson, H. de Coninck, M. Loos, L. A. Meyer), Cambridge University Press, Cambridge, 2005; (b) J. G. J. Olivier, G. Janssens-Maenhout, J. A. H. W. Peters, J. Wilson, Long-Term Trend in Global CO₂ Emissions. 2011 report. PBL Netherlands Environmental Assessment Agency: The Hague, 2011, 9.
- (a) J. Graciani, K. Mudiyansele, F. Xu, A. E. Baber, J. Evans, S. D. Senanayake, D. J. Stacchiola, P. Liu, J. Hrbek, J. F. Sanz and J. A. Rodriguez, *Science* 2014, **345**, 546; (b) G. A. Olah, G. K. Surya Prakash and A. Goepfert, *J. Am. Chem. Soc.* 2011, **133**, 12881.
- <http://www.acs.org/content/acs/en/pressroom/newsrelease/s/2013/july/harvesting-electricity-from-the-greenhouse-gas-carbon-dioxide.html>
- Y. Liu, R. Wang, Y. Lyu, H. Li and L. Chen, *Energy Environ. Sci.* 2014, **7**, 677.
- (a) D. M. D. Alessandro, B. Smit and J. R. Long, *Angew. Chem. Int. Ed.* 2010, **49**, 6058; (b) J. H. Lee, H. J. Lee, S. Y. Lim, B. G. Kim and J. W. Choi, *J. Am. Chem. Soc.* 2015, **137**, 7210; (c) D. H. Apaydin, E. D. Glowacki, E. Portenkirchner and N. S. Sariciftci, *Angew. Chem. Int. Ed.* 2014, **53**, 6819; (d) M. Wriedt, J. P. Sculley, A. A. Yakovenko, Y. Ma, G. J. Halder, P. B. Balbuena and H. C. Zhou, *Angew. Chem. Int. Ed.* 2012, **51**, 9804; (e) M. Yue, Y. Hoshino, Y. Ohshiro, K. Imamura and Y. Miura, *Angew. Chem. Int. Ed.* 2014, **53**, 2654; (f) R. Vaidyanathan, S. S. Iremonger, G. K. H. Shimizu, P. G. Boyd, S. Alavi and T. K. Woo, *Angew. Chem. Int. Ed.* 2012, **51**, 1826.
- (a) R. Barker, *J. Appl. Chem. Biotechnol.* 1973, **23**, 133; (b) A. M. Kierzkowska, R. Pacciani and C. R. Muller, *ChemSusChem* 2013, **6**, 1130; (c) W. Liu, H. An, C. Qin, J. Yin, G. Wang, B. Feng and M. Xu, *Energy & Fuels* 2012, **26**, 2751.
- R. Barker, *J. Appl. Chem. Biotechnol.* 1974, **24**, 221.
- (a) P. S. Fennell, R. Pacciani, J. S. Dennis, J. F. Davidson and A. N. Hayhurst, *Energy & Fuels* 2007, **21**, 2072; (b) N. H. Florin and A. T. Harris, *Chem. Eng. Sci.* 2009, **64**, 187.
- H. Lu, A. Khan, S. E. Pratsinis and P. G. Smirniotis, *Energy & Fuels* 2009, **23**, 1093.
- (a) J. M. Valverde, A. Perejon and L. A. Perez-Maqueda, *Environ. Sci. Technol.* 2012, **46**, 6401; (b) M. H. Wang, C. G. Lee and C. K. Ryu, *Int. J. Hydrogen Energy* 2008, **33**, 6368.
- (a) P. Terech and R. G. Weiss, *Chem. Rev.* 1997, **97**, 3133; (b) J. H. van Esch and B. L. Feringa, *Angew. Chem. Int. Ed.* 2000, **39**, 2263; (c) N. M. Sangeetha and U. Maitra, *Chem. Soc. Rev.* 2000, **34**, 821; Low Molecular Mass Gelators: Design, Self-assembly, Function. (Ed: F. Fages), *Top. Curr. Chem.* 2005, 256, 1; (d) K. K. Kartha, R. D. Mukhopadhyay and A. Ajayaghosh *Chimia Int. J. Chem.* 2013, **67**, 51.
- (a) Y. Ono, K. Nakashima, M. Sano, Y. Kanekiyo, K. Inoue, J. Hojo and S. Shinkai, *Chem. Commun.* 1998, 1477; (b) J. H. Jung, Y. Ono and S. Shinkai, *J. Chem. Soc., Perkin Trans. 2* 1999, 1289; (c) C. Li, T. Hatano, M. Takeuchi and S. Shinkai, *Chem. Commun.* 2004, 2350; (d) K. Sugiyasu, N. Fujita and S. Shinkai, *J. Mater. Chem.* 2005, **15**, 2747; (e) J. H. Jung, Y. Ono, K. Hanabusa and S. Shinkai, *J. Am. Chem. Soc.* 2000, **122**, 5008; (f) J. H. Jung, Y. Ono and S. Shinkai, *Chem. Eur. J.* 2000, **24**, 4552; (g) J. H. Jung, M. Amaike and S. Shinkai, *Chem. Commun.* 2000, 2343; (h) Y. Ono, K. Nakashima, M. Sano, J. Hojo and S. Shinkai, *J. Mater. Chem.* 2001, **11**, 2412.
- Q. Huo, D. I. Margolese, U. Ciesla, P. Feng, T. E. Gier, P. Sieger, R. Leone, P. M. Petroff, F. Schuth and G. D. Stucky, *Nature* 1998, **368**, 317.
- (a) B. P. Krishnan, S. Ramakrishnan and K. M. Sureshan, *Chem. Commun.* 2013, **49**, 1494; (b) A. Prathap and K. M. Sureshan, *Chem. Commun.* 2012, **48**, 5250; (c) A. Vidyasagar, K. Handore and K. M. Sureshan, *Angew. Chem. Int. Ed.* 2011, **50**, 8021.
- T. Saha, S. Dasari, D. Tewari, A. Prathap, K. M. Sureshan, A. Bera, A. Mukherjee and P. Talukdar, *J. Am. Chem. Soc.* 2015, **136**, 14128.
- K. Suzuki, S. Sato and M. Fujita, *Nat. Chem.* 2010, **2**, 25.
- M. Morfin, C. S. Bohun and J. Wattis, Proceedings of the OCCAM-Fields-MITACS Biomedical Problem Solving Workshop 2009.
- H. Yu, Z. Zhang, K. Y. Win, J. Chan, S. H. Teoh and M. Y. Han, *Chem. Commun.* 2010, **46**, 6578.
- G. S. Grasa and J. C. Abanades, *Ind. Eng. Chem. Res.* 2006, **45**, 8846.
- M. Wang, C. G. Lee and C. K. Ryu, *Int. J. Hydrogen Energy* 2008, **33**, 6368.