

CrystEngComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Evaluation of $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ ($0 \leq x < 0.4$) synthesised via a modified sol-gel method as mediators for magnetic fluid hyperthermia

K. McBride,^a J. Cook^{a,b}, S. Gray^b, S. Felton^b, L. Stella^{a,b}, and D. Poulidi^{a†}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

A range of lanthanum strontium manganates ($\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ - LSMO) where $0 \leq x < 0.4$ were prepared using a modified peroxide sol-gel synthesis method. The magnetic nanoparticle (MNP) clusters obtained for each of the materials were characterised using Scanning Electron Microscopy (SEM), X-ray powder diffraction (XRD) and Infra-Red (IR) spectroscopy in order to confirm the crystalline phases, crystallite size and cluster morphology. The magnetic properties of the materials were assessed using the Superconducting quantum interference device (SQUID) to evaluate the magnetic susceptibility, Curie temperature (T_c) and static hysteretic losses. Induction heating experiments also provided an insight into the magnetocaloric effect for each material. The specific absorption rate (SAR) of the materials was evaluated experimentally and via numerical simulations. The magnetic properties and heating data were linked with the crystalline structure to make predictions with respect to the best LSMO composition for mild hyperthermia ($41^\circ\text{C} \leq T \leq 46^\circ\text{C}$). $\text{La}_{0.65}\text{Sr}_{0.35}\text{MnO}_3$, with crystallite diameter of 82.4 nm, (agglomerate size of $\sim 10 \mu\text{m}$), T_c of 89°C and SAR of $56 \text{ W g}^{-1}\text{Mn}$ at a concentration 10 mg mL^{-1} gave the optimal induction heating results (T_{max} of 46.7°C) and was therefore deemed as most suitable for the purposes of mild hyperthermia, *vide infra*.

Introduction

Magnetic nanoparticles (MNPs) have emerged as promising mediators for localised magnetic hyperthermia treatment and drug delivery.¹ The magnetocaloric effect caused by inducing a radio-frequency alternating magnetic field close to an area containing the MNPs leads to a local increase in temperature. When this local increase in temperature occurs within the range of 41°C to 46°C it is known as mild hyperthermia.² Mild hyperthermia is a promising therapy at the cellular³ and systemic levels, allowing the selective targeting of cancer cells through the exploitation of the characteristic traits of cancer cells whilst minimising the damage to healthy tissue.⁴⁻⁶ The therapeutic use of mild hyperthermia is viewed as an adjunct to conventional chemo- or radio- therapies, allowing them to be more effective and require lower dosages as a result. For MNPs to be considered for mild hyperthermia they should be biocompatible; have a low Curie temperature (T_c), ideally within or close to the therapeutic range of mild hyperthermia (41°C to 46°C); and have a high Specific Absorption Rate (SAR).⁷ SAR is a measure of the ability of a material to absorb energy when exposed to electromagnetic radiation.

The vast majority of magnetic nanoparticles investigated for hyperthermia treatment until recently were iron-based⁸⁻¹⁵

which are biocompatible and have high SARs¹⁶ (of the order of 100 W g^{-1}). However, iron-based materials have high T_c s (ranging from 280°C ¹⁷ to 956°C ¹⁸) meaning that application of the magnetic field may lead to overheating of local tissue¹⁹. This issue has led to a variety of doped composite materials being developed such as ferrites of Pd-Ni⁷, Ni-Cu²⁰, Co-Au²¹ and Co-Zn^{22, 23}. The aim of these studies was to reduce the T_c to within the therapeutic range so as to reduce the likelihood of overheating, whilst optimising the SAR. Prior research into perovskite-based manganate MNPs^{17, 24-30} also shows them to be promising materials. The potential of these materials as mediators for hyperthermia relies on their perovskite structure. Their composition and as such, magnetic properties, can be tailored without significantly changing the perovskite phase. This can occur by simply distorting the crystal, without compromising the stability. Regardless of the crystal structure the resulting material remains single phase as opposed to composite core-shell materials whose stability may be less predictable. Figure 1 illustrates the perovskite structure ABO_3 present in the manganates. Perovskites have a face-centred cubic lattice with A-sites found on the corners, and the B-sites in the centre of the unit cells. The magnetic properties of a perovskite, including the transition temperature, can be tailored by doping the A and/or B site ions.^{31, 32} Altering the magnetic properties of the material may also be achieved by means of altering the method of synthesis. For example, increasing the sintering temperature for $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ from 600 to 1000°C leads to an increase in the grain size from 37 to 163 nm and an increase in T_c from 38°C to 57°C .³³

^a School of Chemistry and Chemical Engineering, Queen's University Belfast, Stranmillis Road, Belfast BT9 5AG, U.K† Email: d.poulidi@qub.ac.uk

^b School of Mathematics and Physics, Queen's University Belfast, University Road, Belfast BT7 1NN, UK

Electronic Supplementary Information (ESI) available: Powder X-ray diffraction data, elemental compositions determined by EDX. See DOI: 10.1039/x0xx00000x

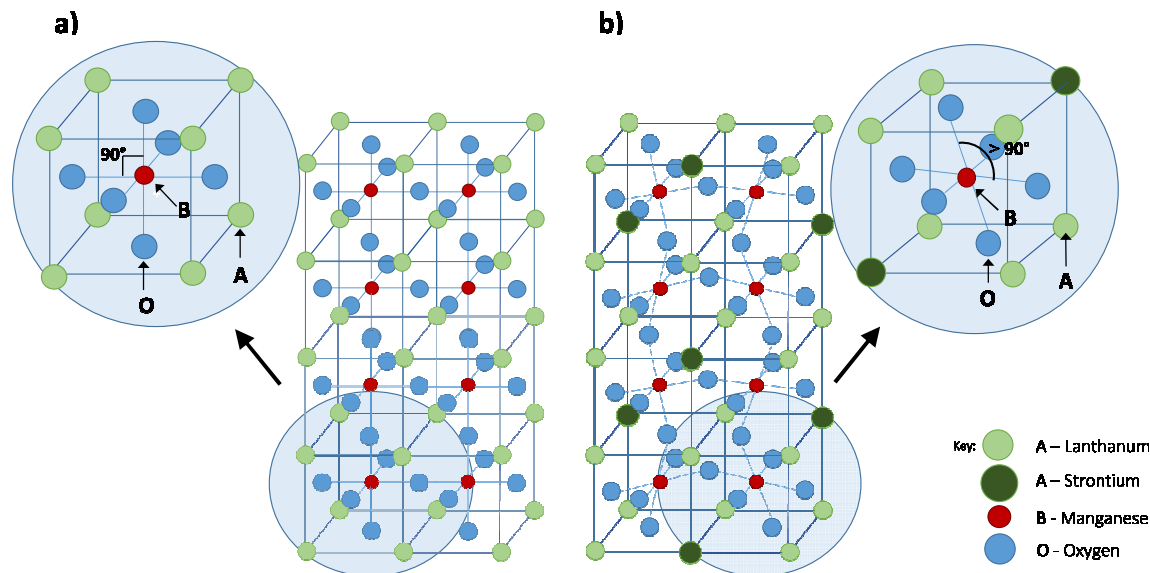


Fig. 1 - Structure of perovskites of the type ABO_3 . Figure 1a shows the undoped parent compound $LaMnO_3$ and Figure 1b shows the distortion caused to the lattice with dopant in $La_{1-x}Sr_xMnO_3$ compounds.

In this work we have investigated the effect of dopant concentration on the magnetic properties (magnetic susceptibility, SAR and T_c) of lanthanum strontium manganates ($La_{1-x}Sr_xMnO_3$) prepared using a modified sol-gel method. This perovskite family has been suggested as a candidate material for MNP mediated hyperthermia treatment.⁶ Previous studies have investigated the effect of the particle size³³ and the effect of altering the composition^{32, 34, 35} on the magnetic properties of the $La_{1-x}Sr_xMnO_3$ (LSMO) MNPs. As composition is varied with dopant, a change in magnetic properties is observed. This paper presents a systematic study of the changes in structure, magnetic susceptibility, hysteresis as well as magnetocaloric effect as a result of the changes in composition. The simultaneous investigation of structural changes and changes to physical properties is not usually seen in the literature.

The $La_{1-x}Sr_xMnO_3$ family is a group of mixed metal oxides of the perovskite structure where La^{3+} or Sr^{2+} ions are the A-site cations with either Mn^{3+} or Mn^{4+} as the B-site cation. The substitution of La^{3+} ions for larger Sr^{2+} ions causes distortion of the local crystal lattice away from the ideal cubic geometry of the parent compound through orthorhombic and rhombohedral structures. This alters the chemical pressure exerted within the lattice, and so alters the bond length of Mn-O and the $Mn^{3+}-O^{2-}-Mn^{4+}$ bond angle. Where this bond angle nears 180° and with decreasing bond length, the extent of e_g orbital overlap increases leading to enhancement of the double-exchange mechanism³⁶. The double-exchange mechanism is a type of magnetic exchange whereby an electron is simultaneously transferred from Mn^{3+} to O^{2-} while an electron is transferred from O^{2-} to Mn^{4+} . Enhancement of the double-exchange mechanism leads to enhancement of magnetic properties such as magnetoresistance and the magnetocaloric effect.³⁶

The dopant ion may also be used to affect the valency of the B-site cation. For example in $La_{1-x}Sr_xMnO_3$ with small levels of Sr^{2+} dopant, the ratio of La^{3+} to Sr^{2+} decreases and so the ratio of Mn^{4+} to Mn^{3+} increases. Increasing the proportion of Mn^{4+} towards a 1:1 ratio favours the double exchange mechanism.³⁷ Mn^{4+} is known to be a non Jahn-Teller active ion because its three valence electrons occupy degenerate t_{2g} orbitals, whereas Mn^{3+} is Jahn-Teller active due to its four valence electrons in a high spin state occupying non-degenerate orbitals.³⁸ This degeneracy causes distortion of the bond lengths in order to minimise the energy of conformation. Therefore, Jahn-Teller distortion will be less effective at increasing the $Mn^{3+}-O^{2-}-Mn^{4+}$ bond angle to 180° with higher levels of Sr^{2+}/Mn^{4+} . This would lead to the restriction of the double exchange mechanism, and hence the magnetocaloric effect would be limited. This correlates to the fact that LSMO in the entire range of $0.1 < x < 0.5$ is in the ferromagnetic phase.³⁷

LSMO is being considered here as a mediator for hyperthermia treatment as this family of materials shows the most promise to tune the T_c within the desired range by varying the level of strontium dopant.³⁹ In preliminary testing, the maximum T_c recorded for $La_{0.75}Sr_{0.25}MnO_3$ was $98^\circ C$ (60 nm)⁴⁰ compared with Fe_3O_4 for which $585^\circ C$ (100 nm) was observed.²⁶ Hence there is more potential to reduce the T_c to within therapeutically acceptable levels using manganates by means of altering the preparation method or composition of the material through doping.^{31, 32} The method of preparation adopted in this work is a modified peroxide sol-gel synthesis⁴¹ which has not been used to synthesise these materials before for the application as mediators for hyperthermia treatment. This facile method of synthesis uses metal oxide and metal carbonate precursors in water, along with hydrogen peroxide

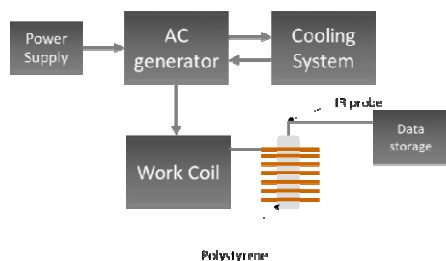


Fig. 2 - Schematic of equipment used for the induction heating experiments.

Table 1 - Lattice parameters and atomic coordinates for (a) Orthorhombic (Pnma) and (b) Rhombohedral (R-3c) which were used to as input parameters for Rietveld analysis.

(a) Orthorhombic (Pnma) lattice parameters and atomic coordinates

$$a = 5.5743, b = 7.695 \text{ and } c = 5.537$$

Atom	Wyckoff Position	x	y	z
La	4c	0.55	0.3	0
Mn	4a	0	0	0
O(1)	4c	-0.011	0.3	-0.1
O(2)	8d	0.309	0	0.2

(b) Rhombohedral (R-3c) lattice parameters and atomic coordinates

$$a = b = 5.5212 \text{ and } c = 13.37908$$

Atom	Wyckoff Position	x	y	z
La	6a	0	0	0.3
Mn	6b	0	0	0
O	18e	0.55	0	0.3

and a small amount of ammonium hydroxide. The Pechini⁴² method has been widely used in this area instead as it uses metal nitrate precursors which are extremely soluble and so form a very stable solution. Upon gelation and aging of this solution it is possible to synthesise highly monodisperse and uniform nanoparticles. The modified peroxide sol-gel method was used here as it avoids the use of EDTA and citric acid as the chelating agents, using hydrogen peroxide instead which leads to water as the only by-product of the reaction. It is deemed to be a safer method of preparation in the lab scale as it does not require the use of highly oxidising nitrate precursors. Further investigation in order to achieve better control of the particle size and particle size distribution is currently underway.

Experimental

Material synthesis

As mentioned previously an aqueous modified sol-gel method was used in this work based on a method developed by Liu *et al.*⁴³ and Chen *et al.*⁴⁴ The powder precursors (obtained from

Sigma Aldrich); lanthanum (III) oxide, $\geq 99.9\%$ (La_2O_3); manganese(II) carbonate, $\geq 99.9\%$ trace metals basis; and strontium carbonate, $\geq 99.9\%$ trace metals basis; were added to 150 ml deionised H_2O in appropriate proportions in order to obtain the desired stoichiometric ratio for the different Sr-doping levels. No thermal pre-treatments were carried out on the powders. While stirring, 100 mL of hydrogen peroxide (30 vol% - Fisher Scientific) was added slowly, followed by addition of 3 ml of ammonium hydroxide NH_4OH (25 vol%, Sigma Aldrich). Hydrogen peroxide worked as a complexation agent in addition to participating in the oxidation of manganese, while the role of ammonia was to peptize the solution into a stable solution. Chen *et al* found that the addition of hydrogen peroxide was necessary in order to obtain a stable solution and xerogel which is why a larger excess of peroxide is used than is needed for simply the oxidation of Mn^{2+} to Mn^{3+} and Mn^{4+} .⁴⁴

After stirring at 70°C for 2 hours, the resulting solution was dried at 90°C until dried gel formation. Finally calcination at 1100°C for 16 hours was used to remove the residual carbon and obtain a crystalline product. After calcination, the xerogel was converted into a powder which contained the three components in the desired stoichiometric level in the perovskite phase. Table 1 shows all the produced samples and sample names to be used for the remainder of the report. The samples were manually ground before characterisation and testing.

Characterisation

The produced samples underwent a series of analysis in order to obtain the necessary information with respect to the crystalline structure, sample morphology and magnetic properties. Structural determination was carried out using XRD (Panalytical X'Pert) and Fourier Transform Infrared Spectroscopy (FTIR Perkin Elmer Spectrum 2). The Scherrer equation using Full-Width at Half Maximum was used to determine the size of the crystallites using the most intense reflection in all cases, which occurred at approximately 32° 2θ . As the Bragg angle is obtained to 4 decimal places, the error propagation of the trigonometric Scherrer function comes to a value of ± 0.1 nm in keeping with the values quoted. X'Pert High Score Plus was used to carry out a Rietveld analysis on the diffraction patterns of the crystalline phases present in the powder samples. The input lattice parameters and atomic coordinates which best matched the experimental data are shown in Tables 1a and 1b. The background was not subtracted and refinement of the atomic coordinates of both phases was undertaken before refining the instrumental parameters. The morphology of the resulting samples was studied using SEM (eSEM - FEI Quanta FEG-Environmental SEM Oxford Ex-ACT). The concentration of dopants in the synthesised materials was then confirmed using eSEM-EDX with the Aztec based XACT system. Atomic percentage was determined using the relative ratio of La to Sr elements in each sample. A cobalt standard was used with the uncertainty for the data values at the $\pm 1\%$ level. The magnetic

Table 2 - Key characterisations on samples presented in this work including the stoichiometry of each sample as determined by EDX analysis, as well as the average crystallite diameter calculating using the Scherrer equation using the most intense peak.

Sample	Sample Name	EDX	XRD	IR	Induction Heating	SEM	M vs T (SQUID)	M V H (SQUID)	EDX Stoichiometry	Crystallite Diameter (nm)
LaMnO ₃	LMO		✓	✓	✓				-----	164.9
La _{0.8} Sr _{0.2} MnO ₃	LSMO20	✓	✓	✓	✓				La _{0.82} Sr _{0.18} MnO ₃	82.4
La _{0.75} Sr _{0.25} MnO ₃	LSMO25	✓	✓	✓	✓				La _{0.76} Sr _{0.24} MnO ₃	82.4
La _{0.7} Sr _{0.3} MnO ₃	LSMO30	✓	✓	✓	✓		✓	✓	La _{0.72} Sr _{0.28} MnO ₃	82.4
La _{0.65} Sr _{0.35} MnO ₃	LSMO35	✓	✓	✓	✓		✓	✓	La _{0.66} Sr _{0.34} MnO ₃	82.4
La _{0.6} Sr _{0.4} MnO ₃	LSMO40	✓	✓	✓	✓	✓	✓	✓	La _{0.62} Sr _{0.38} MnO ₃	61.9

susceptibility and magnetisation hysteresis were measured using a superconducting quantum interference device (SQUID) magnetometer (Quantum Design MPMS XL). Field dependent magnetisation measurements were conducted in the range -10,000 ≤ H ≤ 10,000 Oe, at 100 K and 200 K. Susceptibility measurements were conducted in field cooled (FC) and zero field cooled (ZFC) conditions between 100 and 370 K, at 500 Oe. Non-adiabatic heating experiments were conducted using an RF magnetic field generator (Easyheat 0112) coupled with a water-cooled induction coil (6-turn 12 cm length coil).

A schematic of the induction rig used for the magnetic heating measurements is shown in Figure 2. The generated magnetic field characteristics were frequency: 175 kHz and amplitude: 10.95 kAm⁻¹. Aqueous suspensions of the MNPs of concentrations 5, 10 and 15 mg mL⁻¹ were prepared. The temperature of the aqueous suspension during the induction heating experiments was measured with an IR temperature probe (Optocon AG) FOTEMP 1 coupled to a (Optocon AG) TS2/2 sensor. The heating curves from the induction heating experiments are presented in terms of temperature difference rather than measured temperature to reduce systematic errors. The results obtained from the induction heating measurements were used to calculate the SAR. The corrected slope method was used here to ensure reliable results which can be compared between different experimental set-ups. The SAR was estimated using the following equation⁴⁵:

$$SAR_{corrected\ slope} = \frac{C_w \frac{\Delta T_w}{\Delta t} + L \Delta T_w}{m_{MNP}} \quad (1)$$

where C_w is the Specific Heat Capacity (J g⁻¹ K⁻¹) of water, m_{MNP} is the weight fraction of the magnetically active element, $\Delta T_w / \Delta t$ is the change in temperature against time, and L is the thermal losses of the system (taken from the literature⁴⁵).

It has been recently reported that a temperature increase (3°C in a 10 minute period) may be observed without a magnetic sample present inside the induction coil. This is a result of large currents flowing through the induction coil causing additional convectional heating.⁴⁵ As a result, the temperature of 1 mL of water was also measured under the same conditions to act as a blank experiment in order to correctly attribute heating effects as being due to the magnetocaloric effect of the material. We found that for our

experimental settings, the temperature of the blank reproducibly increased by 3°C in a 10 minute period when the initial temperature was 25°C, in agreement with the literature. The magnetic heating curves here are not scaled to remove the blank heating profile as they would then not be comparable to other published results. However, the blank is taken into consideration when calculating the linear loss parameter for the SAR using Wildeboer *et al's* method⁴⁵. We use the SAR of the blank in Figures 8 and 9 as a guide to compare SARs for the range of materials.

The experimental heating curves were modelled using a simple two-temperature model.⁴⁶ This model is based on the balance between: (i) the energy absorbed by the MNP; (ii) the energy released by the MNP to the solvent; (iii) the heat loss to the environment. This energy balance can be written down as a system of two ordinary differential equations:

$$\begin{cases} f_m C_p^{(m)} \frac{dT_m}{dt} = f_m K_{rf} - f_m g (T_m - T_s), \\ C_p^{(s)} \frac{dT_s}{dt} = f_m g (T_m - T_s) - K_{out} (T_s - T_{room}), \end{cases}$$

where T_m is the temperature of the MNP, T_s is the temperature of the solvent, T_{room} is the temperature of the environment, $C_p^{(m)}$ is the specific heat capacity at constant pressure of the MNP, $C_p^{(s)}$ is the specific heat capacity at constant pressure of the solvent, f_m is the sample concentration of MNPs in water, g is specific heat transfer coefficient, K_{rf} is the specific absorption rate of the MNPs (and not per g_{Mn} as is the SAR), and K_{out} is the specific loss rate of the solvent to the environment. To simplify the calculations, we assume that all the parameters in the equations are temperature independent. In particular, we set $C_p^{(m)} = 1.44706e3 \text{ J kg}^{-1} \text{ K}^{-1}$ and $C_p^{(s)} = 4.2e3 \text{ J kg}^{-1} \text{ K}^{-1}$ (for water). The sample concentration has been set to $f = 10 \text{ mg/g} = 0.01$.

Results and discussion

Crystalline structure and configuration analysis

Table 2 shows the stoichiometry of the synthesised samples as verified by EDX to be in keeping with the desired ratios (the EDX maps of all samples are provided in the Supplementary Information). In Figure 3 the XRD patterns for the LSMO samples can be seen. An increasing proportion of the

Fig. 3 – Rietveld analyses of X-ray Diffraction Patterns of a selection of LSMO materials (a) LMO (b) LSMO25 (c) LSMO35 and (d) LSMO40 to quantify the relative weight percentages of orthorhombic (Pnma) and rhombohedral (R-3c) crystalline phases. The red line below each diffraction pattern is the difference plot which gives an indication of the variation between the calculated and experimental data.

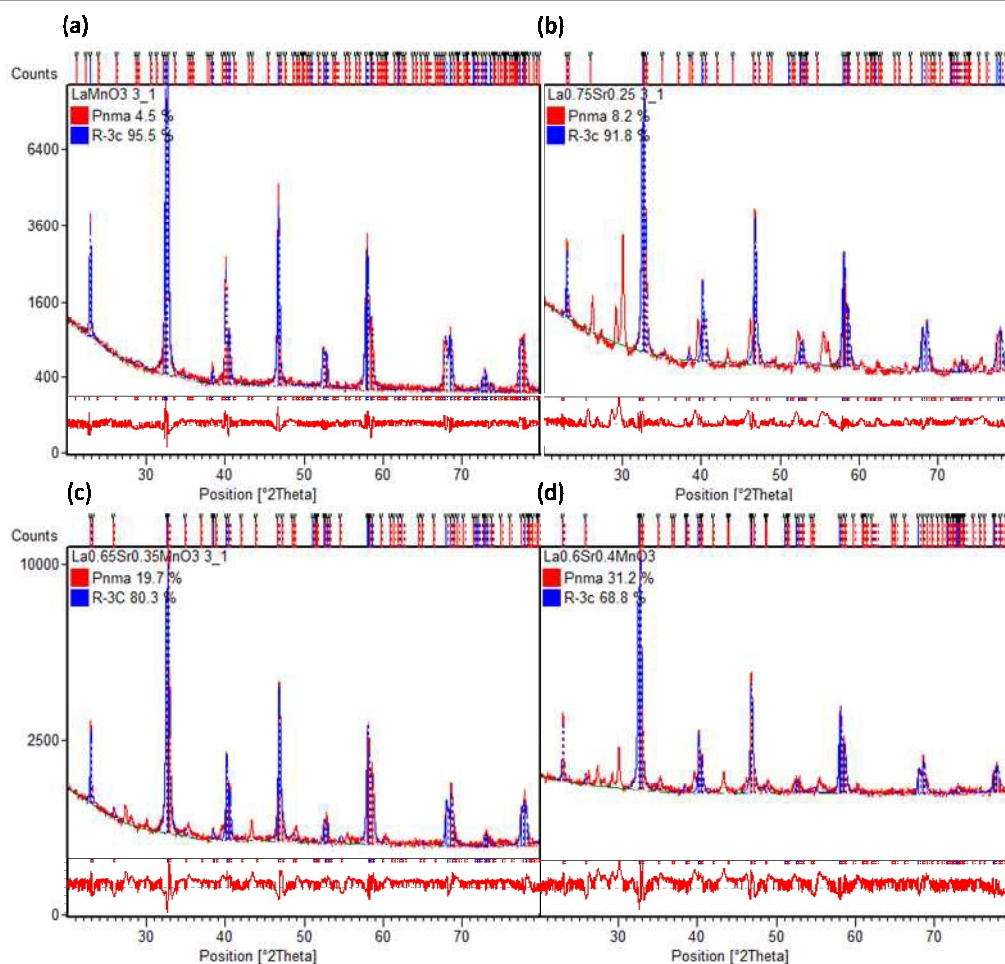


Table 3 – Refined lattice parameters resulting from Rietveld analysis for LMO, LSMO25, LSMO35 and LSMO40. (Gof – Goodness of fit)

Sample	Crystal System	a / Å	b / Å	c / Å	α / °	β / °	γ / °	v / Å	Space group	R _w	R _{exp}	R _{bragg}	Gof	Wt. percent. / %
LMO	Orthorhombic	7.43101	8.4159	5.7144	90	90	90	357.4	Pnma	9.4	4.1	40.3	5.1	4.5
	Rhombohedral	5.52248	5.5225	13.3686	90	90	120	353.1	R-3c					6.2
LSMO25	Orthorhombic	5.43725	7.7984	5.43306	90	90	90	230.4	Pnma	10.7	3.5	4.22	9.3	8.2
	Rhombohedral	5.51461	5.5146	13.3552	90	90	120	351.7	R-3c					2.64
LSMO35	Orthorhombic	5.44815	7.7433	5.46776	90	90	90	230.4	Pnma	8.2	3.8	18.8	4.6	19.7
	Rhombohedral	5.51197	5.5119	13.3546	90	90	120	351.4	R-3c					28.8
LSMO40	Orthorhombic	5.44819	7.7501	5.45624	90	90	90	230.4	Pnma	6.1	2.7	29.45	5.03	31.2
	Rhombohedral	5.51086	5.5109	13.3543	90	90	120	351.2	R-3c					9.57

secondary phase of SrMnO₃ is visible with increasing strontium dopant. Also evident is the increasing intensity of the reflections and (110) in particular, with increasing strontium dopant. Peaks at 28 -30 °2 θ are likely to be due to contamination with agate during manual grinding. Other potential secondary phases which may be present in even

smaller amounts include La₂O₃, MnCO₃ and SrMnO₃.⁴⁷ Previous observations by Zhang *et al.* have shown that for $x < 0.2$ the orthorhombic geometry is typically dominant, followed by a transition to rhombohedral geometry for $0.25 < x < 0.5$.⁴⁸ On initial assessment of the diffraction patterns our data seemed to support this but the presence of more than one phase is

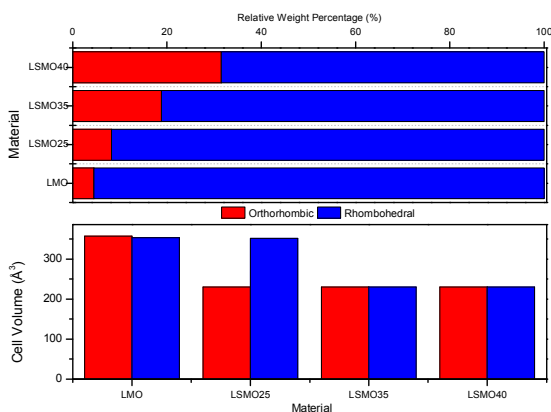


Fig. 4 – Crystal structure comparison of orthorhombic and rhombohedral phases for (a) Relative weight percentages and (b) Unit cell volumes for LMO, LSMO25, LSMO35 and LSMO40.

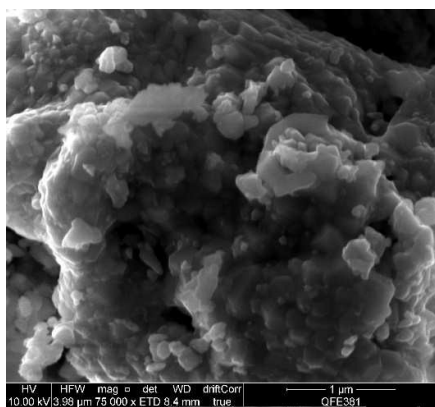


Fig. 5 – Scanning Electron Micrograph of LSMO40.

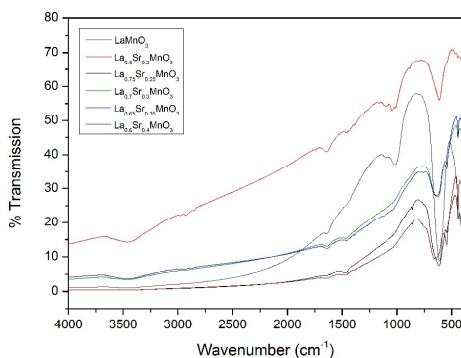


Fig. 6 - IR spectra for a range of the doped LSMO materials where $x = 0.2$ to 0.4 compared to the parent compound LaMnO_3

evident in the shallow transition in magnetic susceptibility *vide infra*. On completion of Rietveld analysis of the samples we found that all samples produced via this modified peroxide sol-gel method contained mixed crystalline phases. The calculated crystalline phases which best fitted the experimental data were found to be orthorhombic (Pnma)⁴⁹ and rhombohedral (R-3c)⁵⁰ crystal structures. The rhombohedral (R-3c) geometry appears to be the dominant crystalline phase for all the

samples presented here (LMO, LSMO25, LSMO35 and LSMO40) in keeping with literature.⁵¹⁻⁵³ Figure 4 shows that with increasing strontium dopant, the relative weight percentage of the orthorhombic (Pnma) crystalline phase increases. This is in keeping with Dokiya *et al* who documented the structural transition of LSMO from rhombohedral (R-3c) to higher orthorhombic and rhombohedral symmetries with increasing strontium dopant or decreasing oxygen content.⁴⁹

Table 3 shows the calculated structural information for the LSMO samples. We can see that the A-site substitution of lanthanum with cationic radius of 1.36 Å for strontium with a larger cationic radius of 1.44 Å does not account for the decrease in cell volume with increasing dopant concentration for both phases. The decrease in cell volume is therefore ascribed to the decreasing ionic radii of the B-site with increasing strontium dopant, which causes Mn³⁺ with cationic radii of 0.645 Å to be replaced by the smaller Mn⁴⁺ with cationic radii of 0.53 Å.⁵⁴ There appears to be little difference in cell volumes for orthorhombic and rhombohedral crystalline phases in each of the LMO, LSMO35 and LSMO40 samples. For LSMO25 however, the cell volume of the rhombohedral structure is 52% greater than for the orthorhombic structure. It is at this point that the relative weight percentage of the rhombohedral phase begins to more rapidly decline, with the orthorhombic phase more rapidly increasing. For both crystal phases we can see a reduction in cell volume of approximately 35% between $x = 0$ and $x = 0.35$. It is in this range that we could expect the material to have enhanced magnetic properties as the decrease in cell volume would lead to shorter bond lengths with greater bonding orbital overlap meaning the double exchange mechanism will be more effective. The change in crystal structure from rhombohedral to orthorhombic geometry also means that γ has decreased from 120° to 90°. In doing so this should mean that a greater proportion of Mn³⁺-O-Mn⁴⁺ bonds are close to 180° for optimal double exchange³⁶. By this rationale LSMO35 and LSMO40 should be able to participate more effectively in the double exchange mechanism and therefore exhibit better magnetocaloric effect. The SEM analysis shown in Figure 5 (LSMO40) indicates that the samples consist of agglomerates of nanoparticles of the order of 10 μm.

Figure 6 shows the FTIR analysis results for the prepared LSMO samples. The presence of octahedral MnO₆ due to the absorption at approximately 600 cm⁻¹ by the Mn-O bond can be seen in all cases. However, there is a positive shift in the wavenumber of this absorption with increasing dopant concentration. Figure 7 depicts the calculated parameters from the XRD and FTIR analysis (crystallite size, average A-site cation radius and Mn-O bond absorption wavenumber) as a function of the dopant concentration. We can see that increasing the dopant concentration (and as a result the average radius of the A-site cation) decreases the crystallite diameter for LSMO and in turn shortens the bond angle β (shown in Table 3) until a geometrical transition (from rhombohedral to orthorhombic) is observed while increasing the Mn-O wavenumber. This increase in wavenumber is evidence of the increasing energy required to manipulate the

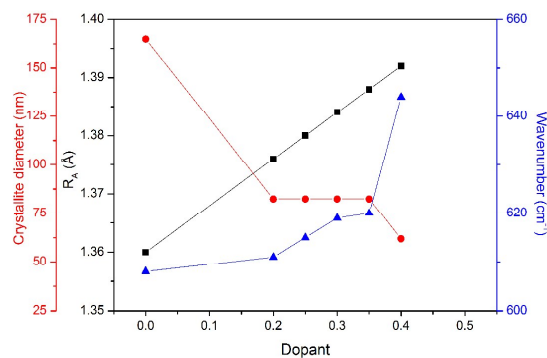


Fig. 7 – The relationship between the average radii of A-site cations (R_A), crystallite diameter and wavenumber for the range of doped LSMO materials. Black squares correspond to R_A , red circles to the crystallite diameter, and blue triangles to the Mn-O wavenumber. Connecting lines are included as a guide to the eye.

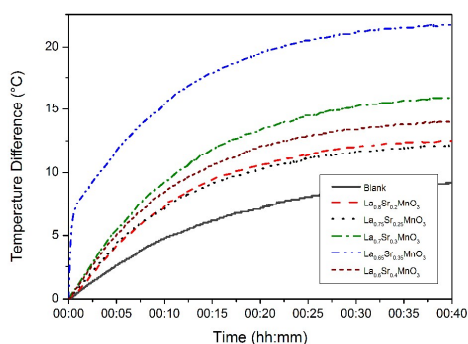


Fig. 8 – Heating curves of the range of doped LSMO materials using aqueous suspension of 10 mg mL^{-1} .

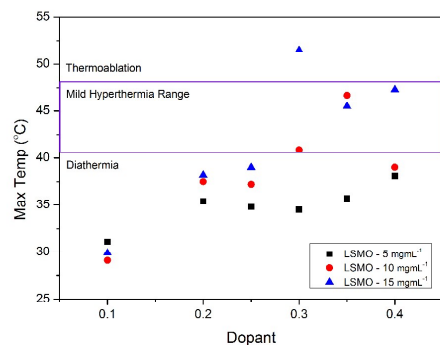


Fig. 9 – Maximum temperatures reached by the range of doped LSMO materials at various suspension concentrations.

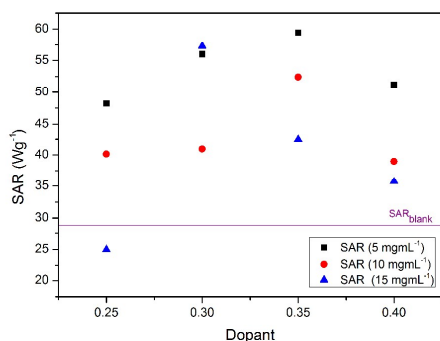


Fig. 10 – Specific Absorption Rates reached by the range of doped LSMO materials.

Mn-O bond in the more distorted octahedron where the geometric transition has occurred to reduce strain. For LSMO samples where $0.2 < x < 0.35$ the crystallite diameter remains constant, yet increasing strain caused by increasing dopant concentration creates greater internal pressure in the perovskite lattice. This internal pressure, based on this rationale is at its maximum for LSMO35, where we begin to see a significant change in the relative weight percentages of the orthorhombic and rhombohedral geometries. As it is in a region of magnetic phase transition in which the optimal magnetocaloric effect may be observed, we may expect the maximum caloric effect for the LSMO35 sample. This hypothesis will be evaluated next when the magnetisation and induction heating experiments are discussed.

Magnetic heating experiments

Figure 8 shows the heating curves for doped LSMO samples where $0.2 < x < 0.35$ for sample concentration of 10 mg mL^{-1} ; we can see that as dopant increases so does the maximum temperature reached by each heating profile until an optimum is reached, after which this maximum temperature of saturation decreases again. Figure 9 shows the saturation temperature achieved for all LSMO samples at the three different concentrations (5 mg mL^{-1} , 10 mg mL^{-1} or 15 mg mL^{-1}); in general increasing the suspension concentration increases the maximum temperature achieved. For example; where $x = 0.3$, the maximum temperature reached increases from 34.5°C at 5 mg mL^{-1} , to 40.9°C at 10 mg mL^{-1} , and to 51.5°C at 15 mg mL^{-1} . The dopant concentration for obtaining the optimal maximum temperature is also a function of the suspension concentration dropping from $x = 0.4$ for 5 mg mL^{-1} (38.1°C) to $x = 0.35$ for 10 mg mL^{-1} (46.7°C) and to 0.3 for 15 mg mL^{-1} (51.5°C). The temperatures of both the blank sample and the parent compound LaMnO_3 increase with time in the AC field by similar amounts. In Figure 10 we can see that the optimal SARs at concentrations of 5 , 10 and 15 mg mL^{-1} are found for samples where $0.3 < x < 0.35$. SARs are higher for the range of doped samples when tested at lower concentrations. As SAR is calculated per gram of the magnetic material, the observed decrease in SAR is expected with increasing sample concentration. The greatest optimal SAR of $59.43 \text{ W g}^{-1} \text{ Mn}$ was obtained at a concentration of 5 mg mL^{-1} where $x = 0.35$. However the maximum temperature achieved by this sample concentration was 35.7°C . Equations 2 and 3 have also been solved numerically and the result for $T_s(t)$ has been fitted to the experimental heating values using a standard least squares regression. The calculated parameters (as discussed

Table 4 – Calculated modelling parameters.

x	K_{rf} W Kg^{-1}	g $\text{W Kg}^{-1} \text{ K}^{-1}$	K_{out} $\text{W Kg}^{-1} \text{ K}^{-1}$	SAR $\text{W g}^{-1} \text{ Mn}$	T_{max} $(^\circ\text{C})$
0.20	12733	56.66	6.006	53.67	35.60
0.25	11507	50.60	5.684	47.97	35.12
0.30	12888	124.01	6.706	53.12	34.61
0.40	13210	104.65	6.052	53.83	35.91

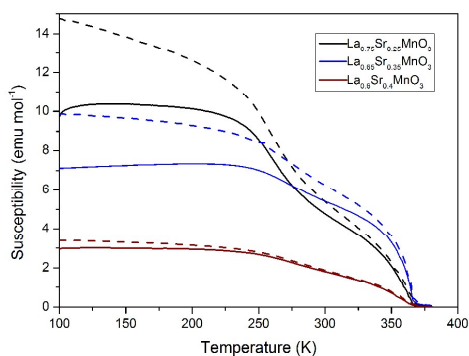


Fig. 11 - Magnetic susceptibility measurements for a selection of LSMO samples (dashed lines represent ZFC and full lines FC measurements).

Fig. 12 - Hysteresis loops for a selection of doped LSMO materials at 100 K (a) Complete field range (-5000 to 5000 Oe) and (b) zoom in from -250 to +250 Oe.

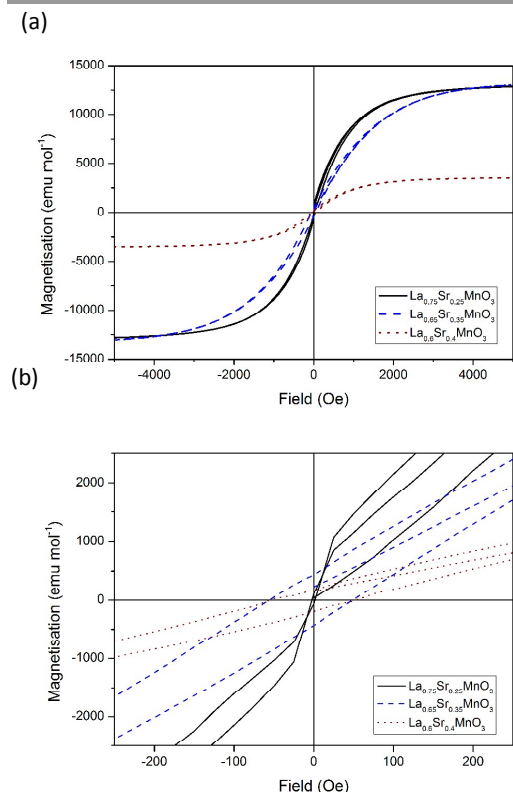


Table 5 - Parametric characterisation of hysteresis for a selection of doped LSMO materials. (M_s - Saturation Magnetisation, H_c - Coercivity, B_r - Remanence, W - Hysteretic Losses and T_c - Curie Temperature)

Sample	M_s	H_c	B_r	W_{100K}	W_{150K}	T_c
	emu/mol	Oe	emu/mol	J/g _{Mn}	J/g _{Mn}	K
LSMO25	12800	25	339	5400	15900	346
LSMO35	13000	75	408	4300	11400	362
LSMO40	3500	50	155	1600	1000	352

previously) as a function of the doping, x , are shown in Table 4. These are in very good agreement with the SARs calculated using Wildeboer *et al.*'s method⁴⁵ shown in Figure 10.

For the efficacy of the hyperthermia treatment as previously stated, the heat generated should be within the mild hyperthermia range of 41 to 46 °C with a high SAR. Based on these two considerations, further work was done using LSMO where $x = 0.35$ and a suspension concentration of 10 mg mL⁻¹ in order to achieve a maximum temperature of 46.7 °C at 10 mg mL⁻¹.

Magnetic measurements

Figure 11 shows the magnetic susceptibility of the materials with respect to temperature. All samples show a ferromagnetic to paramagnetic transition where the zero-field cooled and field cooled curves overlap. The susceptibilities of the LSMO materials in Figure 11 decrease with increasing dopant from $x = 0.25$ to $x = 0.4$. These LSMO materials have a shallow transition region, exhibiting multiplicity as two slight inflections are observed on each graph. This indicates that the LSMO samples contain more than one magnetic phase present. Comparing the susceptibility measurements with the magnetic heating results we can see that the materials with lower susceptibilities produce a greater magnetocaloric effect and vice versa. We would expect to see that since, as the susceptibility of the material decreases, the A.C. hysteretic loss contributions in particular would increase (*vide infra*).

Table 5 shows the corresponding T_c s which were calculated from the susceptibility measurements. The T_c was estimated for each sample using the Arrott plot method. Increasing from $x = 0.25$ to 0.35 for LSMO, we see that T_c increases and then decreases again where $x = 0.40$. The sample where $x = 0.4$ has a higher T_c than the phase diagram would suggest.³⁷ However all calculated T_c s are in keeping with experimental trends reported by Urushibara *et al.*⁴⁰

Figure 12 shows the hysteresis loops recorded for each of the materials for $x=0.25, 0.35$ and 0.4 at 100 K between -5000 and 5000 Oe. The calculated areas of hysteresis are listed in Table 5. These values show a similar trend to that of the susceptibility measurements. Hysteretic losses decrease with increasing dopant from $x = 0.25$ to $x = 0.4$. The decrease in hysteretic losses with increasing dopant can be attributed to the increasing substitution of Jahn-Teller active Mn³⁺ for non Jahn-Teller active Mn⁴⁺. The decrease in Jahn-Teller active ions causes a decrease in the extent of the double exchange mechanism and magnetocaloric effect *vide priori*. Increasing the temperature from 100 to 150 K increases the hysteretic losses three-fold for LSMO25 and LSMO35. However no significant increase in hysteretic losses is calculated for LSMO40.

An inverse trend is observed for LSMO with respect to hysteretic losses and magnetocaloric effect. It must be stressed however that the two types of measurements (i.e. induction heating and static hysteretic losses) are not directly comparable so no further conclusions can be drawn at this stage.

Conclusions

The polycrystalline structure of a family $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ of perovskite-type MNP clusters with different dopant concentrations was evaluated and linked with the magnetic properties of the materials with the aim to make predictions with respect to the best LSMO composition for use as a mild hyperthermia mediator. Taking into consideration the target temperature range and requirement for a low MNP dosage for therapeutic application, whilst maintaining a high SAR it was found that $\text{La}_{0.65}\text{Sr}_{0.35}\text{MnO}_3$ appeared to be the most suitable material. It was found that a transition in the crystalline structure of the perovskite crystal between rhombohedral and orthorhombic increases the magnetocaloric properties of LSMO. FTIR has been shown to be a useful technique in order to compare potential mediators and to predict their magnetocaloric properties. This study presents the magnetic properties (magnetic susceptibility, hysteresis and heating experiment measurements) of the overall sample containing the agglomerated nanoparticles, not the nanoparticles themselves. As we are looking at the magnetic properties of the overall sample as a result of changing the dopant, a TEM study on the nanoparticles would be beyond the scope of this project. Further detailed studies on the stoichiometry of the crystalline phases for the actual magnetic nanoparticles are however planned for future work.

Acknowledgements

Katherine McBride and Suzanne Gray would like to acknowledge financial support from the Department of Education and Learning Northern Ireland (DEL-NI) for a PhD studentship. The authors also acknowledge the help of Professor David Rooney and Christopher McCallum for their help with the induction heating experiments.

Notes and references

- Y. Fukumori and H. Ichikawa, *Advanced Powder Technology*, 2006, **17**, 1-28
- A. Jordan, R. Scholz, P. Wust, H. Föhling and Roland Felix, *J Magn Magn Mater*, 1999, **201**, 413-419 (DOI: 10.1016/S0304-8853(99)00100-0)
- L. Asín, M. R. Ibarra, A. Tres and G. F. Goya, *Pharm. Res.*, 2012, **29**, 1319-1327 (DOI:10.1007/s11095-012-0710-z)
- K. Maier-Hauff, F. Ulrich, D. Nestler, H. Niehoff, P. Wust, B. Thiesen, H. Orawa, V. Budach and A. Jordan, *J. Neurooncol.*, 2011, **103**, 317-324 (DOI:10.1007/s11060-010-0389-0)
- F. K. H. van Landeghem, K. Maier-Hauff, A. Jordan, K. Hoffmann, U. Gneveckow, R. Scholz, B. Thiesen, W. Brück and A. von Deimling, *Biomaterials*, 2009, **30**, 52-57
- A. Jordan, R. Scholz, P. Wust, H. Schirra, Thomas Schiestel, H. Schmidt and R. Felix, *J Magn Magn Mater*, 1999, **194**, 185-196
- O. A. Kuznetsov, O. N. Sorokina, V. G. Leontiev, O. A. Shlyakhtin, A. L. Kovarski and A. A. Kuznetsov, *J Magn Magn Mater*, 2007, **311**, 204-207
- N. A. Brusentsov, V. V. Gogosov, T. N. Brusentsova, A. V. Sergeev, N. Y. Jurchenko, A. A. Kuznetsov, O. A. Kuznetsov and L. I. Shumakov, *J Magn Magn Mater*, 2001, **225**, 113-117
- N. A. Brusentsov, T. N. Brusentsova, E. Y. Filinova, N. Y. Jurchenko, D. A. Kupriyanov, Y. A. Pirogov, A. I. Dubina, M. N. Shumskikh, L. I. Shumakov, E. N. Anashkina, A. A. Shevelev and A. A. Uchevatkin, *J Magn Magn Mater*, 2007, **311**, 176-180
- R. Di Corato, A. Espinosa, L. Lartigue, M. Tharaud, S. Chat, T. Pellegrino, C. Ménager, F. Gazeau and C. Wilhelm, *Biomaterials*, 2014, **35**, 6400-6411
- M. Suto, Y. Hirota, H. Mamiya, A. Fujita, R. Kasuya, K. Tohji and B. Jeyadevan, *J Magn Magn Mater*, 2009, **321**, 1493-1496
- A. Tomitaka, A. Hirukawa, T. Yamada, S. Morishita and Y. Takemura, *J Magn Magn Mater*, 2009, **321**, 1482-1484
- C. S. S. R. Kumar and F. Mohammad, *Adv. Drug Deliv. Rev.*, 2011, **63**, 789-808
- T. Sadhukha, T. S. Wiedmann and J. Panyam, *Biomaterials*, 2014, **35**, 7860-7869
- P. Pradhan, J. Giri, G. Samanta, H. D. Sarma, K. P. Mishra, J. Bellare, R. Banerjee and D. Bahadur, *J. Biomed. Mater. Res.*, 2007, **81B**, 12-22 (DOI:10.1002/jbm.b.30630)
- S. Mornet, S. Vasseur, F. Gasset and E. Duguet, *J. Mater. Chem.*, 2004, **14**, 2161-2175 (DOI:10.1039/B402025A)
- S. Mornet, S. Vasseur, F. Gasset, P. Veverka, G. Goglio, A. Demourgues, J. Portier, E. Pollert and E. Duguet, *Progress in Solid State Chemistry*, 2006, **34**, 237-247
- A. S. Teja and P. Koh, *Progress in Crystal Growth and Characterization of Materials*, 2009, **55**, 22-45
- I. Apostolova and J. M. Wesselinowa, *Solid State Commun.*, 2009, **149**, 986-990
- O. A. Kuznetsov, V. G. Leontiev, V. A. Brukvin, G. N. Vorozhtsov, B. Y. Kogan, O. A. Shlyakhtin, A. M. Yunin, O. I. Tsybin and O. A. Kuznetsov, *J Magn Magn Mater*, 2007, **311**, 197-203
- T. L. Kline, Y. Xu, Y. Jing and J. Wang, *J Magn Magn Mater*, 2009, **321**, 1525-1528
- M. Zeisberger, S. Dutz, R. Müller, R. Hergt, N. Matoussevitch and H. Bönemann, *J Magn Magn Mater*, 2007, **311**, 224-227
- D. S. Nikam, S. V. Jadhav, V. M. Khot, M. R. Phadare and S. H. Pawar, *J Magn Magn Mater*, 2014, **349**, 208-213
- N. K. Prasad, L. Hardel, E. Duguet and D. Bahadur, *J Magn Magn Mater*, 2009, **321**, 1490-1492
- E. Pollert, P. Veverka, M. Veverka, O. Kaman, K. Záveta, S. Vasseur, R. Epherre, G. Goglio and E. Duguet, *Progress in Solid State Chemistry*, 2009, **37**, 1-14.
- S. Vasseur, E. Duguet, J. Portier, G. Goglio, S. Mornet, E. Hadová, K. Knížek, M. Maryško, P. Veverka and E. Pollert, *J Magn Magn Mater*, 2006, **302**, 315-320
- E. Pollert, K. Knížek, M. Maryško, P. Kašpar, S. Vasseur and E. Duguet, *J Magn Magn Mater*, 2007, **316**, 122-125
- O. Kaman, P. Veverka, Z. Jiráček, M. Maryško, K. Knížek, M. Veverka, P. Kašpar, M. Burian, V. Šepelák and E. Pollert, *Journal of Nanoparticle Research*, 2011, **13**, 1237-1252.
- N. D. Thorat, V. M. Khot, A. B. Salunkhe, R. S. Ningthoujam and S. H. Pawar, *Colloids and Surfaces B: Biointerfaces*, 2013, **104**, 40-47
- N. D. Thorat, S. V. Otari, R. A. Bohara, H. M. Yadav, V. M. Khot, A. B. Salunkhe, M. R. Phadare, A. I. Prasad, R. S. Ningthoujam and S. H. Pawar, *Materials Science and Engineering: C*, 2014, **42**, 637-646
- T. K. D. Soma Das and, *Journal of Physics: Condensed Matter*, 2006, **18**, 7629.
- R. Epherre, C. Pepin, N. Penin, E. Duguet, S. Mornet, E. Pollert and G. Goglio, *Journal of Materials Chemistry*, 2011, **21**, 14990-14998.
- G. D. V. Anurag Gaur and, *Journal of Physics: Condensed Matter*, 2006, **18**, 8837.
- P. Žvátora, M. Veverka, P. Veverka, K. Knížek, E. Pollert, V. Král, G. Goglio, E. Duguet, K. Záveta and O. Kaman, *Journal of Solid State Chemistry*, 2013, **204**, 373-379.

- 35 E. Natividad, M. Castro, G. Goglio, I. Andreu, R. Epherre, E. Duguet and A. Mediano, *Nanoscale*, 2012, **4**, 3954-3962 (DOI:10.1039/C2NR30667K).
- 36 C. Zener, *Physical Review*, 1951, **82**, 403.
- 37 V. Markovich, A. Wisniewski and H. Szymczak, in *Handbook of Magnetic Materials*, ed. nonymous, Elsevier, p. 1-201.
- 38 M. Abrashev, V. Ivanov, M. Iliev, R. Chakalov, R. Chakalova and C. Thomsen, *Phys.Status Solidi B*, 1999, **215**, 631-636.
- 39 N. K. Prasad, K. Rathinasamy, D. Panda and D. Bahadur, *J. Biomed. Mater. Res.*, 2008, **85B**, 409-416
- 40 A. Urushibara, Y. Moritomo, T. Arima, A. Asamitsu, G. Kido and Y. Tokura, *Phys. Rev. B*, 1995, **51**, 14103-14109.
- 41 L. Nalbandian, A. Evdou and V. Zaspalis, *Int J Hydrogen Energy*, 2009, **34**, 7162-7172
- 42 M. P. Pechini, *Method of preparing lead and alkaline earth titanates and niobates and coating method using the same to form a capacitor*, Google Patents, 1967.
- 43 S. Liu, X. Tan, K. Li and R. Hughes, *Ceram. Int.*, 2002, **28**, 327-335
- 44 C. H. Chen, H. Kruidhof, H. J. M. Bouwmeester and A. J. Burggraaf, *Materials Science and Engineering: B*, 1996, **39**, 129-132
- 45 R R Wildeboer and P Southern and Q.A.Pankhurst, *J. Phys. D*, 2014, **47**, 495003.
- 46 S. Anisimov, B. Kapeliovich and T. Perelman, *Zh.Eksp.Teor.Fiz*, 1974, **66**, 375-377.
- 47 A. Da Silva, L. d. Conceição, A. Rocco and M. Souza, *Cerâmica*, 2012, **58**, 521-528.
- 48 N. Zhang, W. Yang, W. Ding, D. Xing and Y. Du, *Solid State Commun.*, 1999, **109**, 537-542
- 49 Dokiya, *Proceedings of the Fourth International Symposium on Solid Oxide Fuel Cells (SOFC-IV)*, The Electrochemical Society, 1995.
- 50 D. Green and K. Neumann, *arXiv preprint arXiv:1105.2700*, 2011, .
- 51 A. Møllergård, R. McGreevy and S. Eriksson, *Journal of Physics: Condensed Matter*, 2000, **12**, 4975.
- 52 A. Rostamnejadi, H. Salamati, P. Kameli and H. Ahmadvand, *J Magn Magn Mater*, 2009, **321**, 3126-3131
- 53 Z. F. Zi, Y. P. Sun, X. B. Zhu, Z. R. Yang, J. M. Dai and W. H. Song, *J Magn Magn Mater*, 2009, **321**, 2378-2381
- 54 R. T. Shannon, *Acta Crystallographica Section A: Crystal Physics, Diffraction, Theoretical and General Crystallography*, 1976, **32**, 751-767.