



Photoswitching in nanoporous, crystalline solids: An experimental and theoretical study for azobenzene linkers incorporated in metal-organic frameworks

Journal:	<i>Physical Chemistry Chemical Physics</i>
Manuscript ID:	CP-ART-03-2015-001372.R1
Article Type:	Paper
Date Submitted by the Author:	27-Mar-2015
Complete List of Authors:	<p>Wang, Zhengbang; Karlsruhe Institute of Technology, Institute of Functional Interfaces Heinke, Lars; Karlsruher Institut für Technologie (KIT), Institut für Funktionelle Grenzflächen (IFG) Jelic, Jelena; Technische Universität München, Lehrstuhl für Theoretische Chemie Cakici, Murat; Karlsruhe Institute of Technology (KIT), Institute of Organic Chemistry; Ataturk University, Chemistry Dommaschk, Marcel; Christian-Albrechts-Universität Kiel, Institut für Organische Chemie Maurer, Reinhard; Technische Universität München, Lehrstuhl für Theoretische Chemie Oberhofer, Harald; Technical University Munich, Chemistry Grosjean, Sylvain; Karlsruhe Institute of Technology, Herges, Rainer; Christian-Albrechts-Universität Kiel, Institut für Organische Chemie Braese, Stefan; Karlsruhe Institute of Technology (KIT), Institute of Organic Chemistry Reuter, Karsten; TU Munich, Wöll, Christof; Karlsruhe Institute of Technology, Institute of Functional Interfaces</p>

Photoswitching in nanoporous, crystalline solids: An experimental and theoretical study for azobenzene linkers incorporated in metal-organic frameworks

Zhengbang Wang^a, Lars Heinke^{a,}, Jelena Jelic^b, Murat Cakici^c, Marcel Dommaschk^d, Reinhard J. Maurer^b, Harald Oberhofer^b, Sylvain Grosjean^c, Rainer Herges^d, Stefan Bräse^c, Karsten Reuter^b, Christof Wöll^a*

^a Karlsruher Institut für Technologie (KIT), Institut für Funktionelle Grenzflächen (IFG), Hermann-von-Helmholtz-Platz 1, 76344 Eggenstein-Leopoldshafen, Germany

^b Lehrstuhl für Theoretische Chemie, Technische Universität München, Lichtenbergstr. 4, 85747 Garching, Germany

^c Institute of Organic Chemistry (IOC), Karlsruhe Institute of Technology (KIT), Fritz-Haber-Weg 6, 76131 Karlsruhe, Germany

^d Institute of Organic Chemistry, University Kiel, Otto-Hahn-Platz 4, 24118 Kiel, Germany

KEYWORDS (Word Style “BG_Keywords”).

Azobenzene, photoisomerization, photoswitching in crystalline solids, metal-organic frameworks

ABSTRACT

In this article, we use the popular photoswitchable molecule, azobenzene, to demonstrate that the embedding in a nanoporous, crystalline solid enables a precise understanding of light-induced, reversible molecular motion. We investigate two similar azobenzene-containing, pillared-layer metal-organic frameworks (MOFs): $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$. Experimental results from UV-vis spectroscopy and molecular uptake experiments as well as theoretical results based on density-functional theory (DFT) show that in the $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ MOF structure, the azobenzene side groups undergo photoisomerization when irradiated with UV or visible light. In a very similar MOF structure, $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$, the experimental studies show an unexpected absence of photoisomerization. The DFT calculations reveal that in both MOFs the initial and final states of the photoswitching process (the *trans* and the *cis* conformation) have similar energies, which strongly suggests that the reason for the effective blocking of photoswitching in the AzoBiPy-based MOFs must be related to the switching process itself. More detailed calculations show that in $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ a naphthalene linker from the molecular framework blocks the photoisomerization trajectory which leads from the *trans* to the *cis* conformation. For $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$, as a result of the different geometry, such a steric hindrance is absent.

Metal-organic frameworks (MOFs) are crystalline, porous solids, self-assembled from metal knots and organic linker molecules.¹ Due to their large structural variety, MOFs enable many

different applications, ranging from gas storage and separation² over catalysis³ to potential applications, such as in biomedicine⁴ and sensor techniques⁵. One particularly interesting property of MOFs is the availability of free space, which allows the incorporation of photoswitchable molecules. This may enable the switching of physical or chemical properties in a fully remote-controlled way, i.e. without any (e.g. electrical) contacts. So far, only a few MOFs, which contains linker molecules with photoswitchable azobenzene side groups have been synthesized.⁶⁻¹² Some proof-of-principle studies show how the adsorption capacity of gas molecules, like methane and carbon dioxide, can be varied.^{7, 10} Enabled by the photoswitching of the azobenzene in the MOF structure, other pioneering experiments demonstrated the remote-controlled release of guest molecules.^{11, 12}

In order to have a successful incorporation of photoswitchable molecules into solids, a detailed analysis of the dynamics of the photoswitching process itself is necessary. In this context it should be noted that pure azobenzene ($C_{12}H_{10}N_2$) shows no switching behavior in the condensed, crystalline form.¹³ However, for azobenzene derivatives, like azobenzene functionalized with various halogens,¹⁴ photoswitching can be observed also in the condensed, crystalline phase. When pure azobenzene is in solution, switching can typically be observed with precise dynamics (switching speed, relaxation times, etc.) depending on the properties (viscosity, polarizability, etc.) of the liquid. In the gas phase, switching can also be observed directly.¹⁵ When azobenzene units are embedded into polymers¹⁶ or bound to other materials like graphene¹⁷, photoswitching is often enabled, but the properties are affected by the environment.^{16, 18, 19} Switching is possible only if sufficient space is available within the polymer. A number of studies showed that the switching, i.e. the achieved *cis* percentage, can vary

between more than 80% in rather porous polymers^{20, 21} and virtually zero in densely packed polymers,^{22, 23} where the photoswitching is sterically hindered.

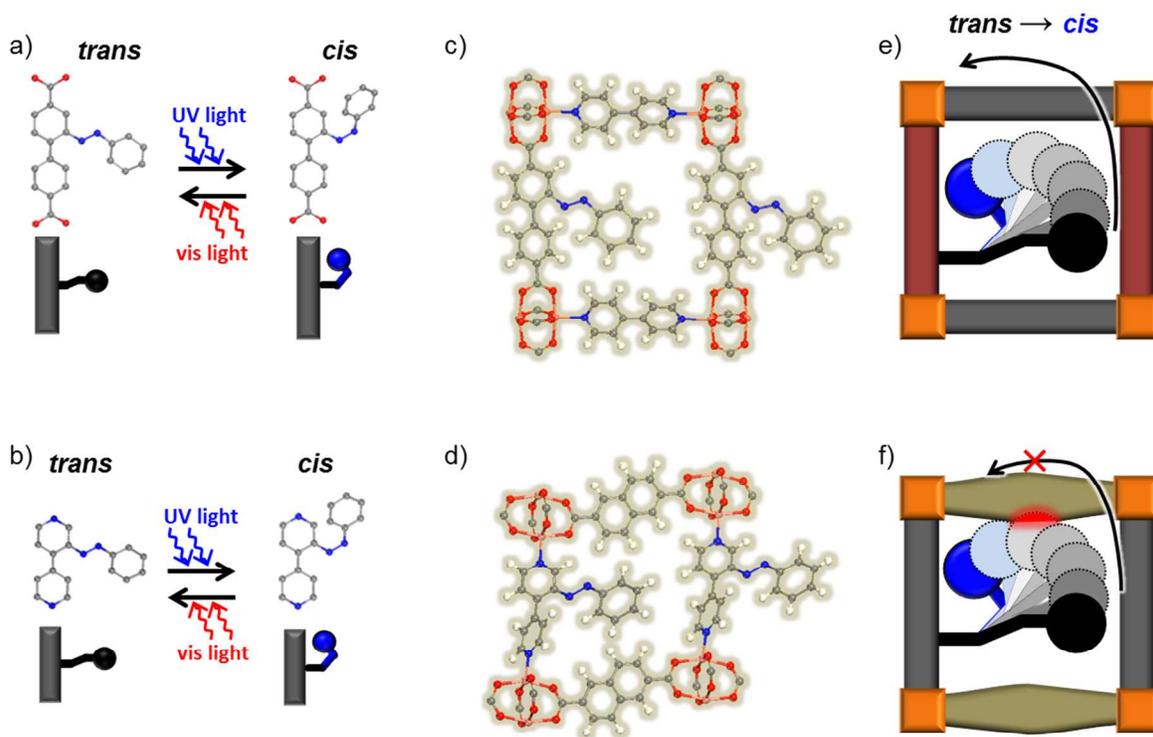


Figure 1: Structure of the azobenzene-containing linkers and MOFs. AzoBPDC (a) and AzoBiPy (b) linkers in the planar *trans* state can be switched to the bent *cis* state by UV light. By irradiation with visible light (or by thermal relaxation), the azobenzene side group goes back to its basic *trans* state. Side views of the structures of MOF Cu₂(AzoBPDC)₂(BiPy) (c) and MOF Cu₂(NDC)₂(AzoBiPy) (d) are shown with the azobenzene side groups in the *trans* state. (The Cu atoms are plotted orange, O red, C grey, N blue and H white.) While the photoisomerization in MOF Cu₂(AzoBPDC)₂(BiPy) is enabled (e), the photoisomerization in MOF Cu₂(NDC)₂(AzoBiPy) is sterically hindered (f).

In this work, we study azobenzene units that have been incorporated into crystalline, nanoporous solids. The use of metal-organic frameworks (MOFs) allows us to perform detailed experimental and theoretical studies of the switching process since the structure of these compounds is well defined. We used thin, epitaxially grown films of two different azobenzene-containing pillared-layer MOF structures which were already published: $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})^9$ and $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})^{11}$, see Figure 1 and SI1 (NDC: 2,6-naphthalenedicarboxylic acid; BiPy: 4,4'-bipyridine; AzoBiPy: 3-azobenzene-4,4'-bipyridine; AzoBPDC: 3-azobenzene 4,4'-biphenyldicarboxylic acid. $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ is also known as Cu-CAU-5.^{6,9}). For these MOF-types, we were able to fabricate well-ordered SURMOFs, which is not always the case.²⁴ These thin surface-mounted MOF films (SURMOFs) were grown on a functionalized solid surface in a layer-by-layer fashion using liquid-phase epitaxy.²⁵ The out-of-plane and in-plane X-ray diffraction (XRD) patterns (Figure SI2) verify the highly crystalline and oriented SURMOF growths (Figure SI2). By exploiting UV-vis spectroscopy, uptake experiments using a quartz crystal microbalance (QCM) and density-functional theory (DFT) calculations, we are able to show that the azobenzene units within the $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ MOF undergo photoisomerization when irradiated with UV light, whereas the other MOF structure cannot be photoswitched due to steric hindrance.

The UV-vis spectra of both linkers recorded in solution (ethanol) and after incorporation into the corresponding MOF films are shown in Figure 2. When irradiated with UV light, the photoswitching of the linker molecules in solution, i.e. the light-induced isomerization of the

azobenzene side groups from the planar *trans* to the bent *cis* state, is clearly visible as a decrease of the $\pi \rightarrow \pi^*$ band (at about 320 nm) and an increase of the $n \rightarrow \pi^*$ band (at about 440 nm; Figure 2a and 2b). The intensity shifts of both bands are generally contributed to the photoswitching process.^{26, 27} By irradiating these solutions with visible light (in this case a 560-nm LED, which usually results in an efficient *cis*-to-*trans* photoisomerization²⁷), the $n \rightarrow \pi^*$ band decreases and the $\pi \rightarrow \pi^*$ band increases again, indicating that the molecules are switched back to the *trans* state. Thus, in ethanolic solution both linker molecules, AzoBiPy and AzoBPDC, are clearly photoswitchable.

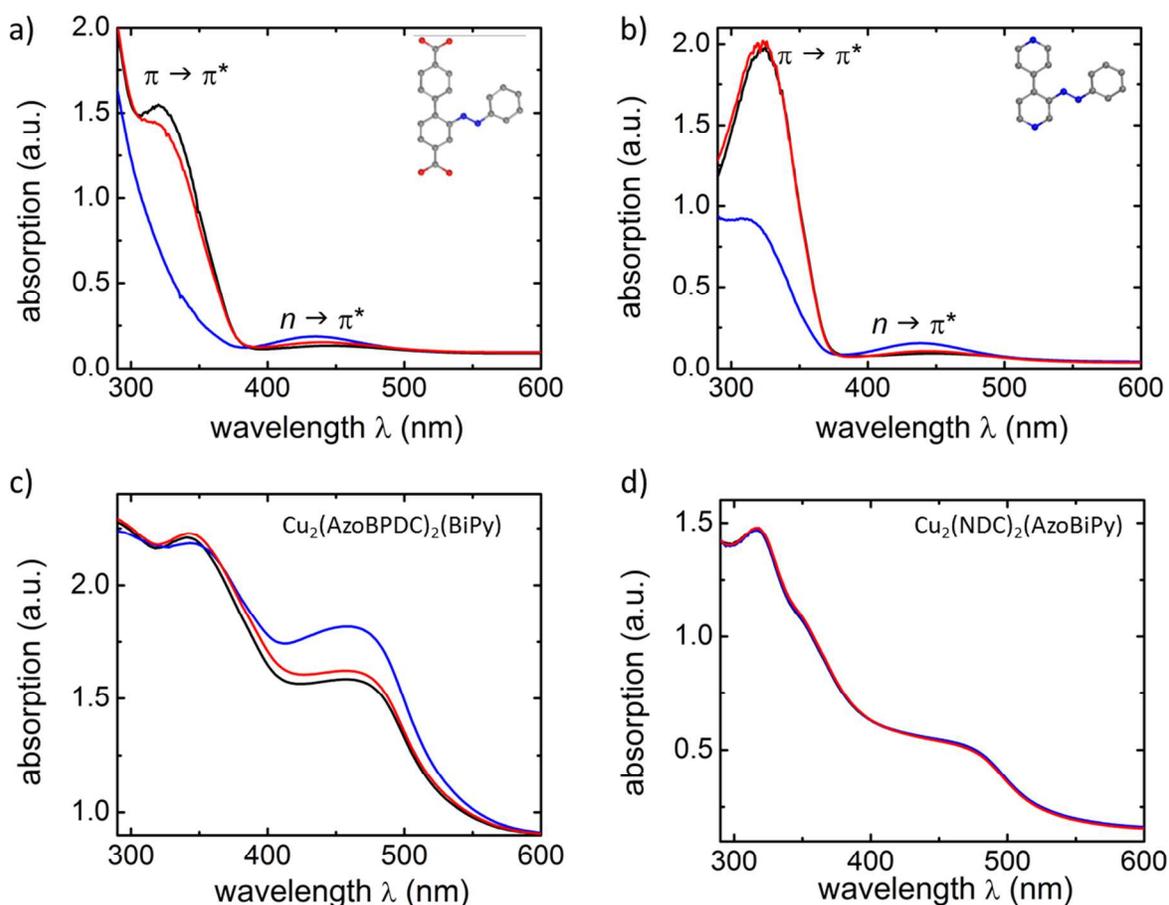


Figure 2: UV-vis spectra of the AzoBPDC (a) and AzoBiPy (b) linker molecules in ethanol solution as well as of the SURMOFs of type $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ (c) and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ (d). Measurements of the pristine sample, i.e. before the samples were exposed to any light (black lines), after UV irradiation for 20 min (blue lines) and after irradiation with visible light for 3 h (red lines) are compared. The spectra in d) are essentially identical.

With azobenzene-linkers incorporated in thin MOF films, the situation is quite different. In this case, only the MOF of type $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ shows comparable shifts of the $\pi \rightarrow \pi^*$ and $n \rightarrow \pi^*$ band intensities when irradiated with UV light (see Fig. 2c). Similar to the linker molecules in solution, irradiation of $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ with visible light results in an $n \rightarrow \pi^*$ band decrease and the $\pi \rightarrow \pi^*$ band increases again. This indicates that the azobenzene moieties in $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ can be switched by UV light from the *trans* to the *cis* state and back again by visible light. However, when thin films of type $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ are irradiated with UV or visible light, no changes in the UV-vis spectra could be observed (see Fig. 2d). Even after irradiating the sample with UV or visible light for long periods of time of up to 12 h, the UV-vis spectrum did not significantly change. This is a clear indication that no photoswitching occurs in $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$.

By means of X-ray diffraction (Fig.SI3), it was shown that the crystallinities of the SURMOF samples are not affected by the UV irradiation.

An independent way to investigate the switching of the azo-based linkers used here is to monitor the effect of the transport of guest molecules inside the MOF. Due to the different conformation in the *trans* and the *cis* state, the corresponding diffusion coefficients and adsorption capacities are expected to be different. A convenient way to study these effects in thin MOF films is to monitor the molecular uptake of small guest molecules using an appropriate sensor. We used 1,4-butanediol as a probe molecule and studied the loading by the corresponding SURMOFs by means of a quartz crystal microbalance (QCM).¹¹ The corresponding results for the uptake by the thin MOF film in the pristine state (*trans*) and by the thin MOF film after UV irradiation are shown in Figure 3. While the UV irradiation resulted in a significant increase of the uptake amount and a decrease of the uptake rate for $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$, no significant change of the uptake was observed for $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ after irradiation with UV light. Thus the uptake data verify the findings from UV-vis spectroscopy that $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ is photoswitchable and can perform isomerization when irradiated with UV light, while $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ cannot.

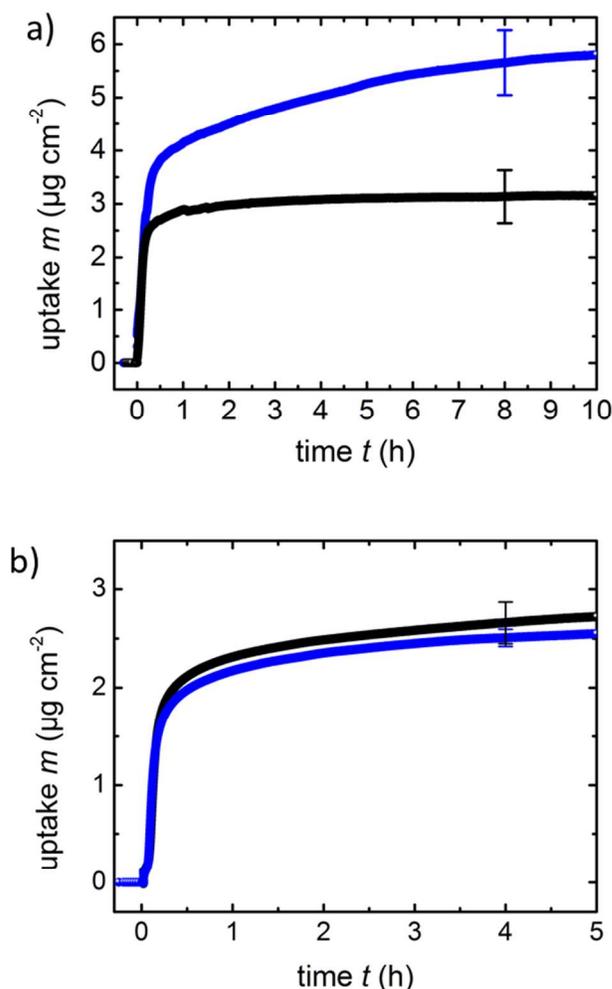


Figure 3: QCM uptake experiments. The uptake of butanediol by $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ (a) and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ (b) was measured without (black) and after (blue) UV irradiation. The uptake amount by $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ doubles when irradiated with UV light, while the uptake by $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ is not significantly influenced by UV irradiation. The small difference in the uptake amount is much smaller than the statistical deviations. The standard deviations of the uptake amounts of the experimental runs are indicated by the error bars at 4 and 8h, respectively.

For a better understanding of why in one MOF structure the photoinduced isomerization is enabled and in the other it is not, we performed DFT calculations for the optimized *trans* and *cis* states in each compound. The geometries of these two states are characterized by values of the dihedral reaction coordinate of $\omega=180^\circ$ (*trans*) and $\omega\sim 20^\circ$ (*cis*), respectively. Like in plain azobenzene, both states are (meta-)stable for the two MOF structures, with *trans* being the ground state at a lower potential energy than the *cis* state ($\Delta E_{\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})}=0.76$ eV and $\Delta E_{\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})}=0.89$ eV). A similarly minute influence of the MOF structures is seen in the vertical excitation energies at the two metastable states as calculated with time-dependent DFT. There is no significant difference when the azobenzene in the two MOF structures are compared to each other or when they are compared to plain azobenzene. With respect to the ground-state energetics, this similarity also extends beyond these two states. As shown in Fig. 4, both MOFs exhibit similar minimum energy pathways along the reaction coordinate ω , i.e. when each time fully optimizing all other degrees of freedom for a given value of ω (black lines in Figs. 4c and d for $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$, respectively).

Since the initial and the final states as well as the minimum energy pathways show no sign for the absence of the photoswitching in $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$, we focus on the dynamics of the process itself. This pertains specifically to the trajectories of the molecular fragments during the course of the photoswitching process. Such investigations would be hardly meaningful in the liquid or in amorphous solids. In contrast, these trajectories are rather well defined in MOFs due to their crystalline nature. Here, we focused on the rotation mechanism, which seems to be the prevailing isomerization mechanism.^{28, 29} In Figure 4a) and b), 2D projections of the corresponding high-dimensional ground-state potential energy hypersurface (PES) are plotted for

the two MOFs. Next to the azobenzene-rotation angle ω as reaction coordinate, these projections also consider a second generalized coordinate q , which describes the relaxation of all other coordinates in the MOFs due to changes in ω . Thereby coordinates $\omega=q$ correspond to the respective *trans* \leftrightarrow *cis* minimum energy pathways, which are discussed above, i.e. all other coordinates can perfectly optimize for each value of ω . Coordinates $q=180^\circ$ (20°) indicate that all other coordinates remain as they are in the *trans* (*cis*) state. As shown in Fig. 4c, the azobenzene group in $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ can be brought from the *trans* to the *cis* energy minimum by a simple rotation along ω with little influence from other degrees of freedom (red line). This means, even if all other coordinates were frozen at the *trans* configuration, a *cis*-like local minimum along ω exists. This minimum can be reached through the photoswitching, after which further relaxation of q directly leads to the actual *cis* state. On the other hand, in $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$, the situation is quite different. Here, only a concerted motion of ω and q could lead to a stable *cis* state. Starting from a structure with q frozen at the *trans* state, a simple rotation along ω alone does not lead to the *cis* state's energetic minimum (red line in Fig. 4d). This qualitative difference in the ground-state energetics is a result of the steric hindrance for the rotation of the azo bond. Whereas in $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ this rotation can proceed relatively unhindered, the PES of $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ requires a substantial reorganization of other (MOF-) degrees of freedom in order to avoid collision with neighboring NDC linkers of the framework. For a successful switching, energy would need to be transferred within the excitation lifetime (typically in the order of pico-seconds²⁶) from the photo-excited ω mode to other modes, including modes of the MOF itself. The experimentally observed absence of switching capability in the $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ framework suggests that the photo-excitation and relaxation in the azobenzene is too fast for this rearrangement to happen. Therefore, it is the

$\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ framework itself that blocks the photoisomerization of the azobenzene side group.

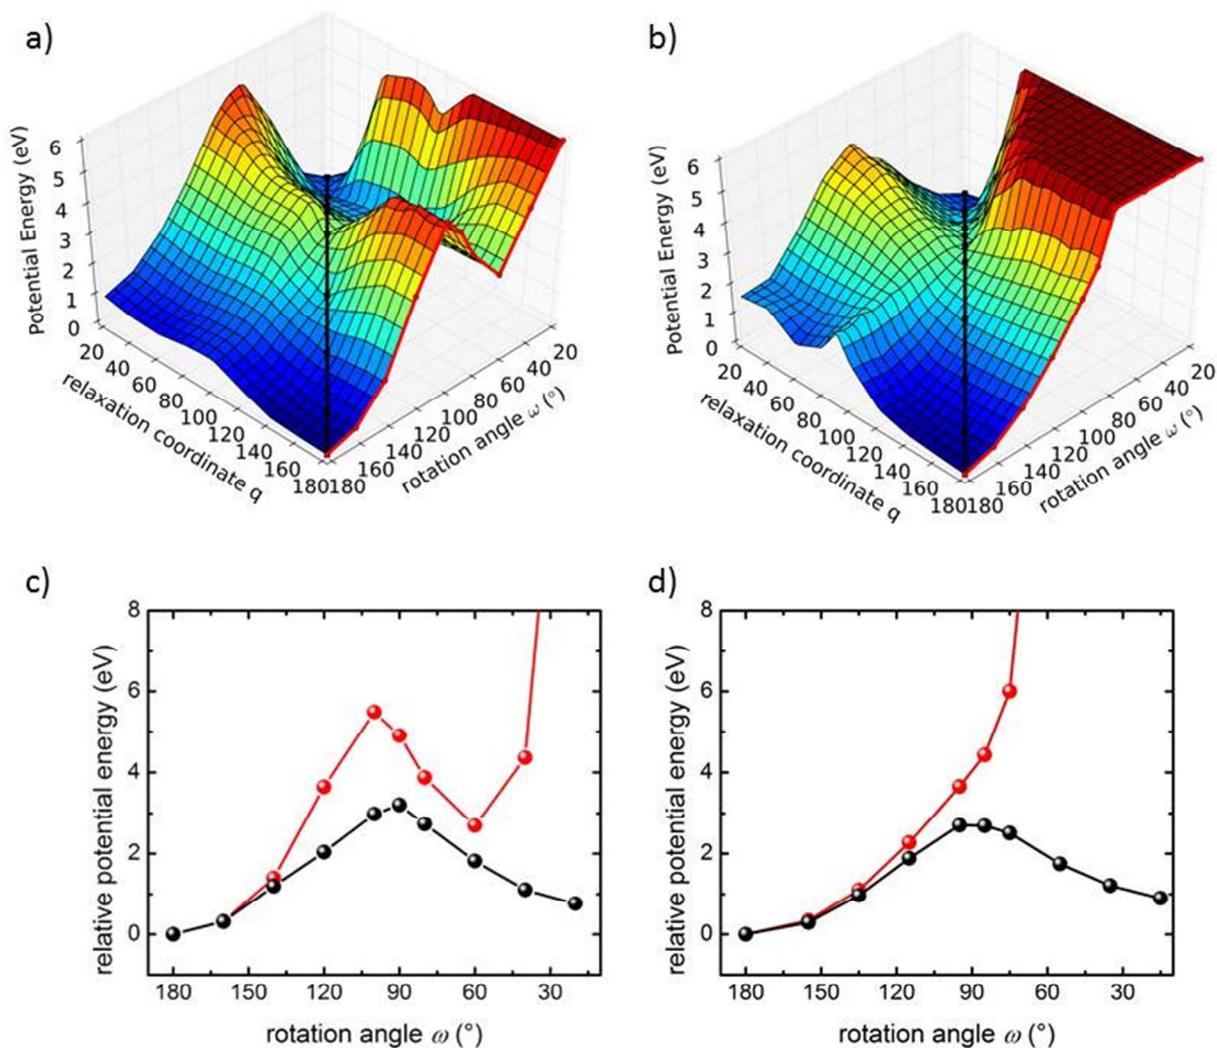


Figure 4: Calculated ground-state potential energy during the rotational isomerization of the azobenzene side group in $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ (a) and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ (b). The high-dimensional potential energy surface (PES) is plotted as a function of the azobenzene rotation angle ω , i.e. the photo-driven reaction coordinate, and a generalized coordinate q ,

representing all other degrees of freedom in the MOF. The energy during the rotation around the azo bond is plotted for the unrelaxed ($q=180$, red) and fully relaxed ($q=\omega$, black) MOF structure for $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$ (c) and $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ (d), see text. Both pathways are also marked in figures (a) and (b), respectively.

It can be inferred that photoswitching in $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$ should be enabled by modifying the linker in such a way that there is more free space around the azobenzene moiety. This can be achieved, for instance, by extending the linear backbone of the AzoBiPy linker by one phenyl ring resulting in AzoBiPyB linker (see Supporting Information 2). It was shown by UV-vis spectroscopy and QCM uptake experiments that pillared-layer MOFs containing AzoBiPyB (this means MOFs of type $\text{Cu}_2(\text{BDC})_2(\text{AzoBiPyB})$) enables photoswitching (see SI4 and SI5).

In conclusion, the incorporation of photoactive compounds into MOFs enables the fabrication of functional, smart materials, where properties such as the uptake of guest molecules can be remote-controlled. However, for the design of such materials, it is not sufficient to study whether the corresponding *cis* and *trans* states known from gas-phase or solution are compatible with the MOF-structure. Instead, the entire trajectories of the switching unit have to be considered. In this paper, we exemplified this for the photoswitching in two similar, azobenzene-containing pillared-layer MOFs. By means of UV-vis spectroscopy and QCM uptake experiments, we

showed that the photoswitching is enabled in one MOF structure, while it is not possible in the other. DFT calculations indicate that steric hindrance along the switching trajectory oppresses the photoisomerization process in the non-switching MOF. The results obtained here demonstrate that the highly crystalline structure of MOFs allows for straightforward experimental and theoretical investigations of photoswitching. In the future, we plan to perform such studies also in a time-resolved fashion to gain deeper insights into the photoswitching process.

Methods

Sample Syntheses

The investigated MOF films were prepared by liquid-phase epitaxy (LPE) on a functionalized solid substrate in a well-defined layer-by-layer fashion.²⁵ These thin MOF films, called surface-mounted MOFs (SURMOFs), are oriented and highly-crystalline. SURMOFs are prepared in a well-defined layer-by-layer fashion by the sequential immersion of the substrate in each of the two reactant solutions, i.e. the solutions of the metal complexes and of the organic linker molecules in ethanol. For $\text{Cu}_2(\text{AzoBPDC})_2(\text{BiPy})$, the solutions were 0.5 mM copper acetate as well as 0.1 mM BiPy and AzoBPDC. For $\text{Cu}_2(\text{NDC})_2(\text{AzoBiPy})$, the solutions were 0.5 mM copper acetate as well as 0.1 mM NDC and AzoBiPy in ethanol. After each immersion step, the substrate was rinsed with ethanol to remove any unreacted, weakly adsorbed reactants. To nucleate the growth on the substrate surface (here: 150nm gold on a silicon wafer) and to control

the SURMOF's crystal orientation, the substrate surface was functionalized with an 11-mercapto-1-undecanol self-assembled monolayer (MUD SAM). Here, all samples were synthesized in 80 cycles.

UV-vis Spectroscopy

The UV-vis spectra were recorded by means of a Cary5000 spectrometer with a UMA unit from Agilent. The linker molecules were studied in ethanolic solution in transmission mode. The UV-vis spectra of the SURMOFs on the gold substrate were measured in reflection with an angle of 20° to the normal.

UV irradiation was performed with a 365-nm LED with a power of 150 mW. The visible light irradiation was performed with a 560-nm LED with 100 mW. The distance between the sample and the LED was about 10 cm.

Uptake experiments using a quartz crystal microbalance

The uptake of the guest molecules by the thin MOF films was studied by using a quartz crystal microbalance (QCM).^{11, 30} The QCM cell is connected to a gas flow system with Argon as carrier gas. With this gas flow system, it is possible to switch instantly between a pure Argon flow and a Argon flow enriched with the guest molecule, here 1,4-butanediol, at room temperature (25°C). This results in a butanediol partial pressure of roughly 1 Pa. All QCM experiments were performed at a constant temperature of 30°C, which is precisely controlled by the Q-Sense setup. Before each experiment, the samples were activated in a pure argon flow at 65°C overnight.

Computational details

All DFT calculations were performed with the all-electron code FHI-aims.^{31,32} The MOF structures were fully relaxed (residual forces below 10^{-4} eV/Å) in periodic boundary conditions and Γ -point sampling of the Brillouin zone. All relaxations and single point energy calculations were conducted non spin-polarized with the PBE generalized gradient exchange-correlation (XC) functional.³³ Electron orbitals and density were expanded in a numeric atomic orbital basis at the “tier1” level using “light” integration grids. Convergence checks with respect to basis set and integration grid size, spin-polarization and XC-functional (against hybrid functional calculations) showed no appreciable influence of these factors on the relative ground-state energetics used to identify the steric hindrance. Dispersion interactions were accounted for using the correction scheme of Tkatchenko and Scheffler.³⁴ The time-dependent DFT calculations were performed with TURBOMOLE^{35,36} based on the B3LYP hybrid functional with an optimized triple-zeta basis (def-TZVPP).

ASSOCIATED CONTENT

Supporting Information: MOF structures, X-ray diffractograms, the synthesis description of AzoBiPyB as well as UV-vis and QCM data of the photoswitching in $\text{Cu}_2(\text{bdc})_2(\text{AzoBiPyB})$.

This material is available free of charge via the Internet at <http://pubs.acs.org>

AUTHOR INFORMATION

Corresponding Author

* Lars.Heinke@KIT.edu

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

ACKNOWLEDGMENT

Z.W. is grateful for a PhD fellowship donated by the China Scholarship Council (CSC). L.H. is indebted to the Baden-Württemberg Stiftung for the financial support of this research project by the Eliteprogramm for Postdocs. J.J., R.J.M., H.O. and K.R. gratefully acknowledge support through the Solar Technologies Go Hybrid initiative of the State of Bavaria.

REFERENCES

1. H. C. Zhou, J. R. Long and O. M. Yaghi, *Chemical Reviews*, 2012, **112**, 673-674.
2. J. R. Li, R. J. Kuppler and H. C. Zhou, *Chemical Society Reviews*, 2009, **38**, 1477-1504.
3. J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chemical Society Reviews*, 2009, **38**, 1450-1459.
4. P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Ferey, R. E. Morris and C. Serre, *Chemical Reviews*, 2012, **112**, 1232-1268.
5. L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. Van Duyne and J. T. Hupp, *Chemical Reviews*, 2011, **112**, 1105-1125.

6. A. Modrow, D. Zargarani, R. Herges and N. Stock, *Dalton Transactions*, 2011, **40**, 4217-4222.
7. A. Modrow, D. Zargarani, R. Herges and N. Stock, *Dalton Transactions*, 2012, **41**, 8690-8696.
8. S. Bernt, M. Feyand, A. Modrow, J. Wack, J. Senker and N. Stock, *European Journal of Inorganic Chemistry*, 2011, 5378-5383.
9. A. Modrow, M. Feyand, D. Zargarani, R. Herges and N. Stock, *Zeitschrift für anorganische und allgemeine Chemie*, 2012, **638**, 2138-2143.
10. J. Park, D. Q. Yuan, K. T. Pham, J. R. Li, A. Yakovenko and H. C. Zhou, *J. Am. Chem. Soc.*, 2012, **134**, 99-102.
11. L. Heinke, M. Cakici, M. Dommaschk, S. Grosjean, R. Herges, S. Bräse and C. Wöll, *Acs Nano*, 2014, **8**, 1463-1467.
12. J. Brown, B. L. Henderson, M. D. Kiesz, A. C. Whalley, W. Morris, S. Grunder, H. Deng, H. Furukawa, J. I. Zink, J. F. Stoddart and O. M. Yaghi, *Chemical Science*, 2013, 10.1039/C1033SC21659D
13. M. Tsuda and K. Kuratani, *Bull. Chem. Soc. Jpn.*, 1964, **37**, 1284-1288.
14. O. S. Bushuyev, A. Tomberg, T. Frišćić and C. J. Barrett, *J. Am. Chem. Soc.*, 2013, **135**, 12556-12559.
15. L. Duarte, R. Fausto and I. Reva, *Physical Chemistry Chemical Physics*, 2014, **16**, 16919-16930.
16. A. Natansohn and P. Rochon, *Chemical Reviews*, 2002, **102**, 4139-4175.
17. Y. Feng, H. Liu, W. Luo, E. Liu, N. Zhao, K. Yoshino and W. Feng, *Sci. Rep.*, 2013, **3**.
18. Y. Imai, K. Naka and Y. Chujo, *Macromolecules*, 1999, **32**, 1013-1017.
19. S. Deshmukh, L. Bromberg, K. A. Smith and T. A. Hatton, *Langmuir*, 2009, **25**, 3459-3466.
20. T. Kondo, K. Yoshii, K. Horie and M. Itoh, *Macromolecules*, 2000, **33**, 3650-3658.
21. M. Ueda, H. B. Kim, T. Ikeda and K. Ichimura, *Chem. Mat.*, 1992, **4**, 1229-1233.
22. P.-c. Che, Y.-n. He and X.-g. Wang, *Chinese Journal of Polymer Science*, 2012, **30**, 478-486.
23. K. Kinashi and Y. Ueda, *Molecular Crystals and Liquid Crystals*, 2006, **445**, 223-230.
24. O. Shekhah, H. Wang, T. Strunskus, P. Cyganik, D. Zacher, R. Fischer and C. Wöll, *Langmuir*, 2007, **23**, 7440-7442.
25. O. Shekhah, H. Wang, S. Kowarik, F. Schreiber, M. Paulus, M. Tolan, C. Sternemann, F. Evers, D. Zacher, R. A. Fischer and C. Wöll, *J. Am. Chem. Soc.*, 2007, **129**, 15118-15119.
26. H. M. D. Bandara and S. C. Burdette, *Chemical Society Reviews*, 2012, **41**, 1809-1825.
27. E. Uchida and N. Kawatsuki, *Polymer Journal*, 2006, **38**, 724-731.
28. A.-H. Gao, B. Li, P.-Y. Zhang and J. Liu, *Computational and Theoretical Chemistry*, 2014, **1031**, 13-21.
29. J. C. Corchado, M. Luz Sanchez, I. F. Galvan, M. Elena Martin, A. Munoz-Losa, R. Barata-Morgado and M. A. Aguilar, *Journal of Physical Chemistry B*, 2014, **118**, 12518-12530.
30. L. Heinke and C. Wöll, *Physical Chemistry Chemical Physics*, 2013, **15**, 9295-9299.
31. X. Ren, P. Rinke, V. Blum, J. Wieferink, A. Tkatchenko, A. Sanfilippo, K. Reuter and M. Scheffler, *New Journal of Physics*, 2012, **14**.

32. V. Blum, R. Gehrke, F. Hanke, P. Havu, V. Havu, X. Ren, K. Reuter and M. Scheffler, *Computer Physics Communications*, 2009, **180**, 2175-2196.
33. J. P. Perdew, K. Burke and M. Ernzerhof, *Physical Review Letters*, 1996, **77**, 3865-3868.
34. A. Tkatchenko and M. Scheffler, *Physical Review Letters*, 2009, **102**.
35. M. v. Arnim and R. Ahlrichs, *Journal of Computational Chemistry*, 1998, **19**, 1746-1757.
36. F. Weigend, *Physical Chemistry Chemical Physics*, 2006, **8**, 1057-1065.