

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

***P,O*-Phosphinophenolate Zinc(II) Species: Synthesis, Structure
and Use in the Ring-Opening Polymerization (ROP) of Lactide, ϵ -
Caprolactone and Trimethylene carbonate.**

Christophe Fliedel,^{†‡} Vitor Rosa,^{†‡} Filipa M. Alves,[#] Ana. M. Martins,[#] Teresa Avilés^{†*} and
Samuel Dagorne^{‡*}

[‡] Institut de Chimie de Strasbourg (UMR 7177), CNRS-Université de Strasbourg, 1 rue
Blaise Pascal, 67000 Strasbourg, France.


[†] LAQV, REQUIMTE, Departamento de Química, Faculdade de Ciências e Tecnologia da
Universidade Nova de Lisboa, Caparica, 2829-516, Portugal.

[#] Centro de Química Estrutural, Instituto Superior Técnico, Universidade de Lisboa, Av.
Rovisco Pais, 1049-001 Lisboa, Portugal.

Corresponding author: dagorne@unistra.fr

Table of Contents Only

Structurally diverse phosphinophenolate Zn(II) heteroleptic and homoleptic compounds are reported, some of which efficiently mediating the controlled ROP of lactide, ϵ -caprolactone and trimethylene carbonate under living and immortal conditions.

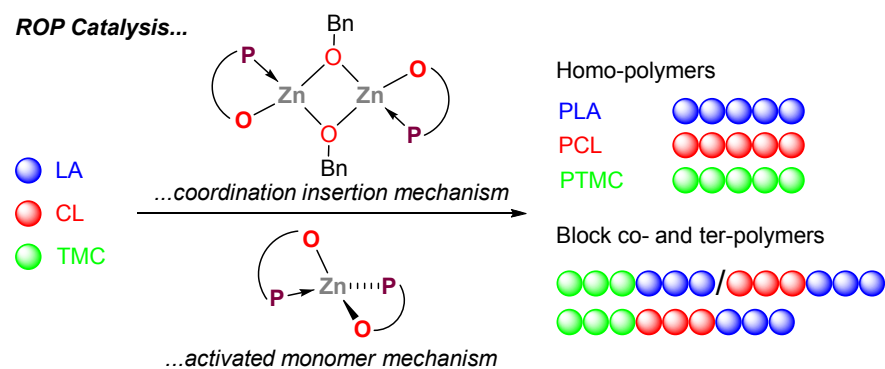

Abstract. The *P,O*-type phosphinophenol proligands (**1**·H, 2-PPh₂-4-Me-6-Me-C₆H₂OH; **2**·H, 2-PPh₂-4-Me-6-^tBu-C₆H₂OH) readily react with one equiv. of ZnEt₂ to afford in high yields the corresponding Zn(II)-ethyl dimers of the type [(κ²-*P,O*)Zn-Et]₂ (**3** and **4**) with two μ-O_{Ph} bridging oxygens connecting the two Zn(II) centers, as determined by X-ray diffraction (XRD) studies in the case of **3**. Based on diffusion-ordered NMR spectroscopy (DOSY), both species **3** and **4** retain their dimeric structures in solution. The alcoholysis reaction of Zn(II) alkyls **3** and **4** with BnOH led to the high yield formation of the corresponding Zn(II) benzyloxide species [(κ²-*P,O*)Zn-OBn]₂ (**5** and **6**) isolated in a pure form as colorless solids. The centrosymmetric and dimeric nature of Zn(II) alkoxides **5** and **6** in solution was deduced from DOSY NMR experiments and multinuclear NMR data. Though heteroleptic species **5** is stable in solution, its analogue **6** is instable in CH₂Cl₂ solution at room temperature to slowly decompose to the corresponding homoleptic species **8** via the transient formation of (κ²-*P,O*)₂Zn₂(μ-OBn)(μ-κ¹:κ¹-*P,O*) (**6'**). Crystallization of compound **6** led to crystals of **6'**, as established by XRD analysis. The reaction of ZnEt₂ with two equiv. of **1**·H and **2**·H allowed access to the corresponding homoleptic species of the type (*P,O*)₂Zn (**7** and **8**). All gathered data are consistent with compound **7** being a dinuclear species in the solid state and in solution. Data for species **8**, which bears a sterically demanding *P,O*-ligand, are consistent with a mononuclear species in solution. The Zn(II) alkoxide species **5** and the [Zn(*P,O*)₂]-type compounds **7** and **8** were evaluated as initiators of the ring-opening polymerization (ROP) of lactide (LA), ε-caprolactone (ε-CL) and trimethylene carbonate (TMC). Species **5** is a well-behaved ROP initiator for the *homo*-, *co*- and *ter*-polymerization of all three monomers with the production of narrow disperse materials under living and immortal conditions. Though species **7** and **8** are ROP inactive on their own, they readily polymerize LA in the presence of a nucleophile such as BnOH to produce narrow disperse PLA, presumably via an activated-monomer ROP mechanism.

Introduction

Aliphatic polyesters and polycarbonates such as polylactic acid (PLA), poly(ϵ -caprolactone) (PCL) and poly(trimethylene carbonate) (PTMC) are of current importance as biodegradable and bioassimilable materials and, as such, have already found a wide array of applications spanning from their use in food packaging to biomedicine (as excipients in controlled drug delivery and bone tissue prosthesis components, for example).¹ The thermoplastic properties of PLA and PCL also position such materials as possible biodegradable alternatives to petrochemically-sourced thermoplastic polyolefins. The resulting properties of these materials are favorably impacted by their well-defined nature, including controlled polymer chain length and, in the case of PLA, stereoregularity.^{1,2} In this regard, the controlled ring-opening polymerization (ROP) of lactide (LA), ϵ -caprolactone (ϵ -CL) and trimethylene carbonate (TMC) by discrete ligand-supported metal alkoxide initiators constitutes the method of choice for the production of well-defined PLA, PCL and PTMC, respectively.² For instance, PLA is industrially produced *via* ROP of L-LA, a dimer of the renewable resource L-lactic acid, using Sn(Oct)₂ as the ROP initiators.³ Over the past fifteen years, numerous complexes of oxophilic metals, primarily Mg(II)-, Ca(II)-, Ti(IV)-, Zr(IV)-, Zn(II)-, Al(III)-, Ga(III)-, In(III)-, Bi(III)-based derivatives, have been investigated as ROP initiators for catalytic performance improvement and the production of stereoregular PLA material.^{2,4} In general, ROP performances of ligand-based metal complexes are greatly impacted by the nature of the ancillary ligand(s). To date, studies on metal-based ROP initiators overwhelmingly involve the use of *N*- or/and *O*-based hard donor polydentate anionic ligand (as supporting/ancillary ligands) for metal stabilization.^{2,4} In contrast, metal complexes bearing softer heteroatom-based Lewis bases (such as phosphine, thioether donors) have been little explored in cyclic esters/carbonates ROP despite the potential positive influence of such softer donor ligands on polymerization catalysis performance. For instance,

earlier studies on various group 4 metal chelates concluded on the beneficial effect of chelating ligands incorporating softer L donors, such as phosphorus and sulfur, on olefin polymerization activity.⁵ Also, we earlier showed that cationic Al(III) complexes bearing bidentate phosphino-phenolate ligands of type **A** (Chart 1) are effective initiators in the ROP of propylene oxide and ϵ -CL,^{6a} while Lamberti, Mazzeo and co-workers reported on the use of thioether-phenolate Zn(II), Mg(II) and Al(III) species for the effective and controlled ROP of ϵ -CL and lactide.^{6b-c,7}

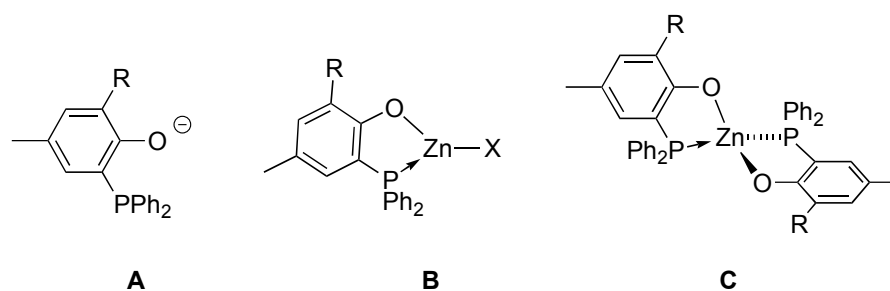


Chart 1. *P,O*-phosphinophenolate ligands **A** and associated (*P,O*)Zn chelates **B** and **C**

As ROP initiators of cyclic esters/carbonates, Zn(II)-based species are of particular interest since Zn is a cheap, readily available and biocompatible metal source, the latter feature being of utmost importance for the application of the derived biomaterials in biomedicine.⁸ This, together with the suitability of bidentate phosphinophenolate ligands **A** in Al(III)-mediated ROP catalysis in our previous studies,^{6a} prompted us to extend our investigations to phosphinophenolate organozinc(II) species of type **B** and **C** (Chart 1) for use in cyclic esters/carbonates ROP. Unsurprisingly, though a couple of phosphino/phosphido Zn(II) compounds have been reported to mediate the ROP of LA and ϵ -CL,⁹ the vast majority of Zn(II) ROP initiators are supported by *N*- or/and *O*-based ligands, some of the latter being among the most effective metal-based initiators known so far in the ROP of LA and ϵ -CL.^{2f,8} Anionic *P,O* ligands of type **A** are readily accessible and their coordination chemistry has been studied with various transition metal centres and the derived *P,O* metal complexes have

been widely studied as olefin oligomerization/polymerization catalysts.¹⁰ Type **A** ligands seem well-suited for the synthesis of ligand-supported Zn(II) ROP initiators as they combine a hard phenolate donor, for an expected strong attachment to the Zn(II) metal center, with a soft phosphine donor that may form a more labile Zn-P coordination bond (yet stabilized through chelate formation) likely to dissociate under ROP conditions, a favorable feature for high catalytic activity. Here we report on the synthesis and structural characterization of phosphino-phenolate Zn(II) complexes and their subsequent use in the controlled and immortal ROP of LA, ϵ -CL and TMC. Taking advantage of the good ROP activity and control exhibited in homo-polymerisation, the production of PCL/PTMC-*co*-PLA copolymers and PTMC-*co*-PCL-*co*-PLA ter-polymers was also achieved.

Results and discussion

Phosphinophenol protio-ligands (1-H and 2-H). Phosphinophenol protio-ligands bearing methyl and ^tBu *ortho*-substituents, **1-H** and **2-H** respectively (Scheme 1) were used to sterically hinder the Zn(II) metal centre upon complexation and thus disfavor excessive aggregation, a well-established tendency of Zn(II) alkyl/alkoxide compounds. The phosphines **1-H** and **2-H** were synthesized according to a literature procedure and their identity was confirmed by NMR analysis.¹¹ In particular, the ³¹P{¹H} NMR spectra of **1-H** and **2-H** both exhibit a singlet resonance at δ -28.9 and -31.7 ppm (CDCl₃), respectively, in line with the presence of a triaryl phosphine group. In the case of **2-H**, single crystals suitable for X-ray diffraction (XRD) studies could be grown from a saturated EtOAc/hexane mixture and subsequently analyzed through XRD, confirming its molecular structure (Figure 1). In the solid-state, the P-C-C-O chelating backbone is nearly planar as expected [O1-C2-C1-P1 torsion angle of 3.3(2)°] and the phosphorus center adopts a slightly distorted tetrahedral geometry with similar C_{Phenyl}-P-C_{Phenyl} and C_{Phenol}-P-C_{Phenyl} bond angles [103.33(8)-104.11(8)°]. The structural data for **2-H** are similar to those of the other few XRD-characterized *P,O* phosphinophenol species.^{10c,12}


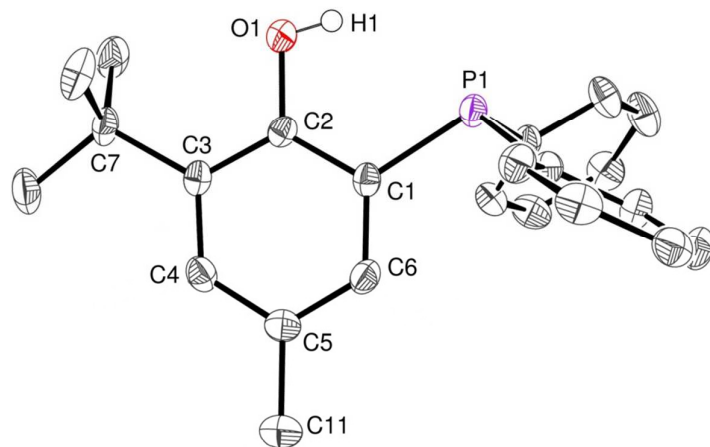


Figure 1. ORTEP drawing of the molecular structure of proligand **2**·H. Thermal ellipsoids are set at the 50% probability level. Hydrogens are omitted for clarity except the crystallographically observed O-H1 hydrogen. Selected bond distances (Å): P1-C1 1.827(2), O1-C2 1.372(2), and angles (deg): O1-C2-C3 118.1(2), P1-C1-C6 124.0 (1), P1-C1-C2 117.3(1).

Heteroleptic Phosphinophenolate Zn(II) alkyls/alkoxides 3-6. Access to the [(*P,O*)-ZnEt]-type Zn(II) ethyl complexes **3** and **4** (Scheme 1) was readily achieved by reaction of ZnEt₂, acting both as a base and a metal source, with a stoichiometric amount of the corresponding ligand precursor (**1**·H and **2**·H, respectively, Scheme 1). Analytically pure compounds **3** and **4** were isolated as colorless solids in good yields (82 and 86% yield, respectively) upon precipitation from the reaction solvent (CH₂Cl₂) and after a pentane wash of the collected solids. Both Zn(II) alkyl complexes are poorly soluble in common organic solvents (precluding ¹³C NMR analysis), suggesting that both species **3** and **4** form aggregates in solution. The ¹H NMR spectra of **3** and **4** display the expected resonances for one ZnCH₂CH₃ moiety (δ -0.28 and 0.69 for **3**; -0.05 and 0.74 for **4**; Figures S1 and S2, ESI). The ³¹P{¹H} NMR singlet signals for **3** and **4** [δ -30.3 (**3**) and -31.0 (**4**) in CDCl₃] resonate at a similar chemical shift to that of the corresponding free proligands [δ -28.9 (**1**·H) and -31.7

(2·H) ppm], possibly reflecting a weak Zn(II)-P coordination bond due to the oxophilic character of the Zn(II) centers. In the case of complex **3**, a dimeric [(*P,O*)-ZnEt]₂ structure is proposed in solution on the basis of diffusion-ordered NMR spectroscopy (DOSY) analysis (CDCl₃, room temp.), which yielded a hydrodynamic radius of 6.01 Å for **3** and thus an estimated molecular volume of 909 Å³ in solution (ESI – Figure S9 and Table S2). The latter matches well the estimated volume of dimer **3** in the solid-state (936 Å³, see ESI – Figure S14).¹³ It is thus probable that species **3** adopts a dimeric structure in solution similar to that observed in the solid state (Figure 2). The analogous NMR features for **3** and **4** suggest that both complexes adopt a comparable structure in solution.

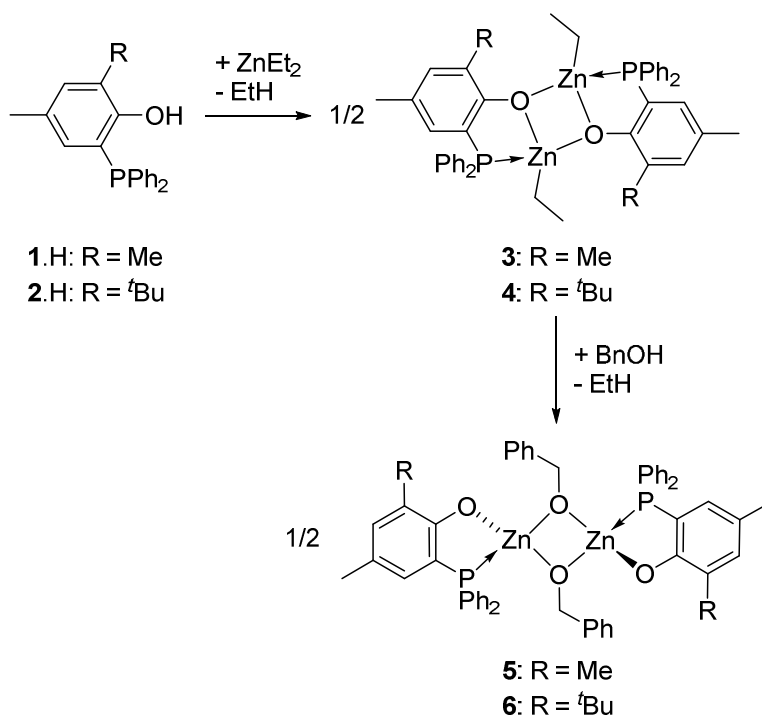

Scheme 1. Synthesis of the phosphine-phenolate (*P,O*)-supported zinc(II) alkyl (**3** and **4**) and alkoxide (**5** and **6**) complexes.

The solid state molecular structure of complex **3** could be unambiguously established through XRD studies (Figure 2; ESI - Table S1) and constitutes the first *P,O*-zinc alkyl complex to be structurally characterized.¹⁴ Complex **3** crystallizes as a centrosymmetric dimer

with each Zn(II) center adopting a significantly distorted tetrahedral geometry. This is due to a rather acute *P,O*-ligand bite angle [$\text{O1-Zn1'-P1} = 80.31(1)^\circ$] and the geometrical constraints imposed upon dimer formation. For instance, the small O-Zn-O bond angles [$82.6(2)^\circ$] of the Zn_2O_2 core are compensated for by rather large P1'-Zn1-C21 and O1'-Zn1-C21 bond angles [$133.3(2)^\circ$ and $130.0(3)^\circ$, respectively]. Each metal center bears a κ^2 -chelating *P,O*-phosphino phenolate ligand, a $\mu\text{-O}$ bridging phenolate connecting the two Zn(II) centers, and an ethyl group. The Zn-P and Zn-C_{alkyl} bond lengths [$2.458(3)$ Å and $1.985(8)$ Å, respectively] are in the expected ranges for related Zn-phosphine/phosphido compounds [Zn-P : $2.598(2)$ - $2.390(1)$ Å; $\text{Zn-C}_{\text{alkyl}}$: $2.147(2)$ - $1.941(6)$ Å].¹⁴

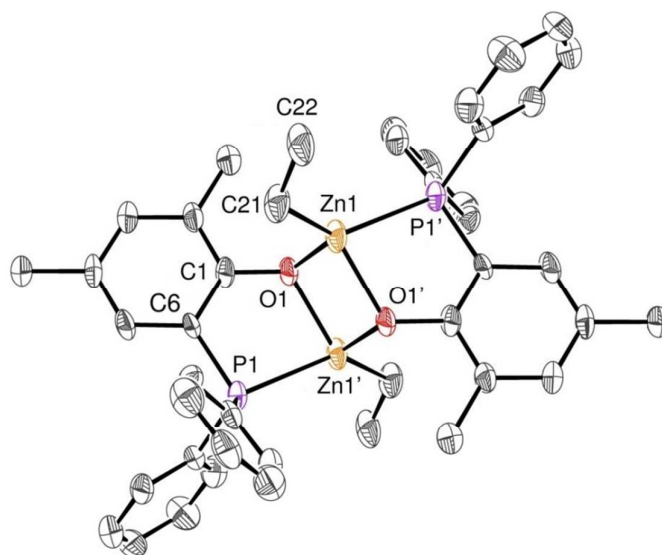



Figure 2. ORTEP drawing of the molecular structure of **3**. Thermal ellipsoids are set at the 50% probability level. Hydrogen atoms are omitted for clarity. Selected bond distances (Å): Zn1-P1' 2.458(3), Zn1-O1' 2.069(5), Zn1-C21 1.985(8), Zn1-O1 2.058(6), O1-C1 1.358(6), P1-C6 1.796(7) and angles (deg): O1-Zn1'-P1 80.31(1), O1-Zn1-C21 113.6(3), P1'-Zn1-C21 133.3(2), O1-Zn1-P1' 103.8(1), O1'-Zn1-C21 130.0(3), O1-Zn1-O1' 82.6(2).

The corresponding zinc alkoxide derivatives of the type $[(P,O)\text{Zn-OCH}_2\text{Ph}]_2$ (**5** and **6**, Scheme 1) were prepared in good yield (88-91%) *via* an alcoholysis reaction between the

[(*P,O*)ZnEt]₂ complexes **3** and **4** and 2 equiv. of BnOH at room temperature in CH₂Cl₂ (Scheme 1). Complexes **5** and **6** were isolated as colorless solids and their formulation deduced from elemental analysis and NMR data (ESI - Figures S3 and S4). The ¹H NMR data for these species agree with the presence of one Zn-OBn moiety per phosphinophenolate ligand and with overall centrosymmetric structures (C_i symmetry). In particular, the ¹H NMR spectra only contain one set of signals for the *P,O* ligand while the presence of two ¹H NMR resonances for the methylene benzyl group indicates inequivalent Zn-OCHH'Ph methylene protons in **5** and **6**. These data are in line with the proposed dimeric structure for **5** and **6** (presumably through two μ -O-benzyloxy bridges) proposed in Scheme 1. DOSY NMR measurements support a dimeric structure for species **5** and **6**. Hydrodynamic radii of 6.00 Å and 6.04 Å were estimated for species **5** and **6**, respectively, (CDCl₃, room temp.) corresponding to calculated molecular volumes of 905 Å³ and 921 Å³ (see ESI – Figures S10, S11 and Table S2). In the case of species **5**, the experimental value well with the calculated volume for a model molecule (923 Å³; estimated from a Chem 3D optimized geometry; ESI – Figure S15 and S16). Besides, the molecular volumes for **5** and **6** are close to that measured for the [(*P,O*)-ZnEt]₂ dimer **3** (V_{DOSY} = 909 Å³ and V_{X-ray} = 936 Å³), whose molecular structure was XRD-established. Therefore, *P,O*-supported zinc alkyls (**3** and **4**) and alkoxides (**5** and **6**) likely display a similar level of aggregation in solution under the studied conditions.

Though heteroleptic species **5** is stable for days in solution (CD₂Cl₂, room temp.), the more sterically encumbered analogue **6** is unstable in CD₂Cl₂ and slowly converts over the course of several days to the corresponding homoleptic Zn species **8** (along with presumed [Zn(OBn)₂]_n-type aggregate species)¹⁵ via the formation of dinuclear Zn species **6'** (Scheme 2), as deduced from ¹H and ³¹P{¹H} NMR monitoring experiments (³¹P{¹H} NMR data: Figure 3; ¹H NMR data: ESI – Figures S8B). Based on ¹H NMR data, 50% of complex **6** is converted to **6'** after 2 days. Complex **6** is completely consumed within 4 days with the

presence of compound **6'** and homoleptic species **8** as the major product (in a 1/2 **6'**/**8** ratio). The absence of species **8** after 2 days of reaction while it is the major product after 4 days strongly suggests that **8** is produced from dinuclear species **6'**. A nearly quantitative formation of **8** is observed after 8 days.

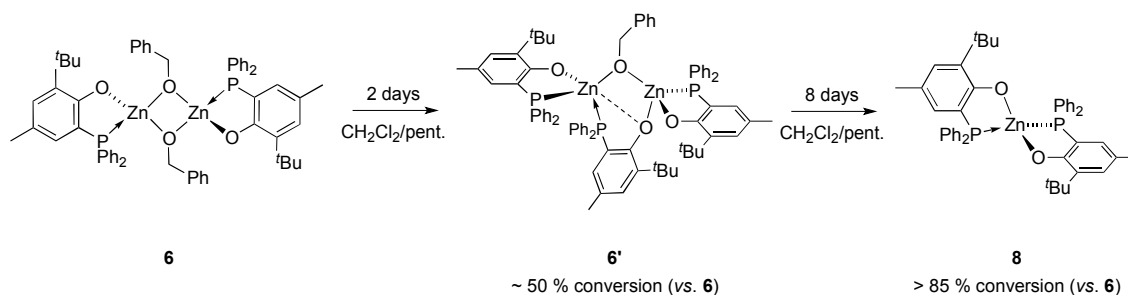

Scheme 2. Conversion of heteroleptic species **6** to homoleptic species **8** via the transient formation of **6'**.

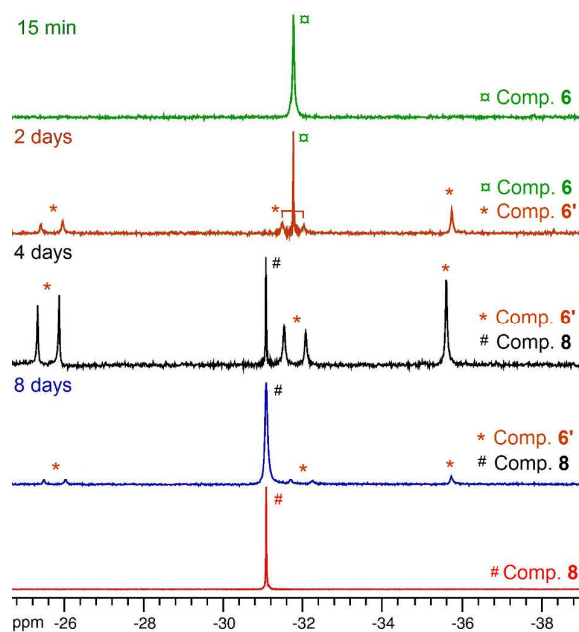
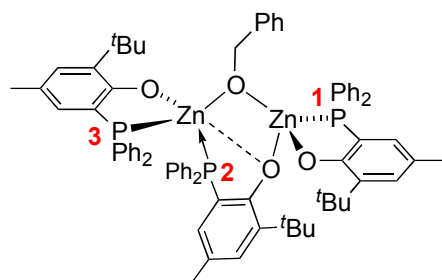
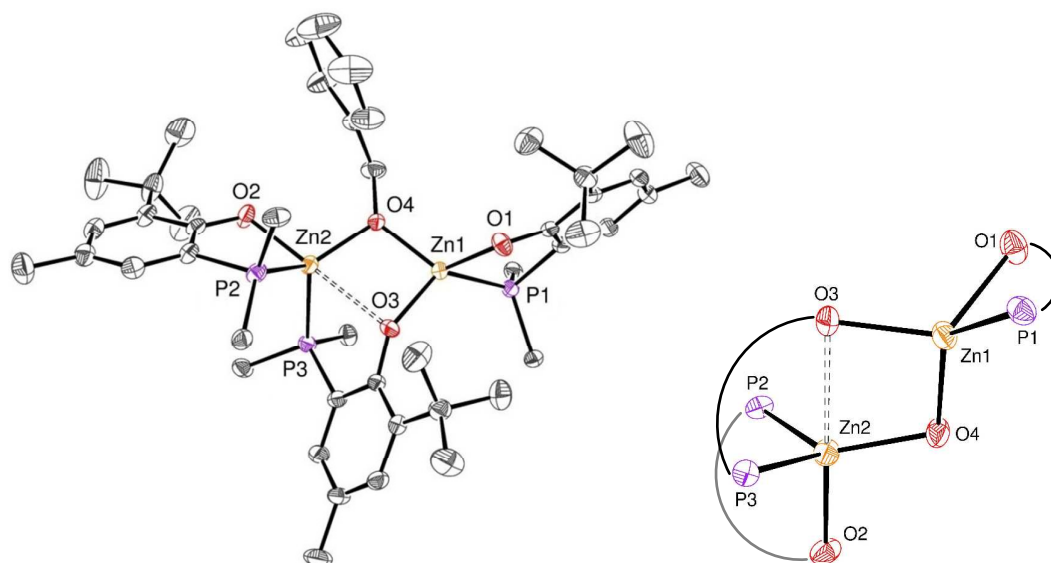


Figure 3. $^{31}\text{P}\{^1\text{H}\}$ NMR (162 MHz, CD_2Cl_2 , RT) monitoring of the conversion of heteroleptic species **6** to homoleptic **8** via the formation of species **6'**. Conditions: $[\mathbf{6}]_0 = 10 \text{ mM}$, CD_2Cl_2 , room temperature. For comparison, the $^{31}\text{P}\{^1\text{H}\}$ NMR spectrum of analytically pure compound **8** (bottom spectrum) prepared and isolated from the reaction of ZnEt_2 and 2 equiv. of ligand **2-H**.

The identity of species **6'** and **8** was established through independent synthesis and characterization data (*vide infra* for the synthesis of compound **8**). Analytically pure complex **6'** was isolated in 41% yield by crystallization of compound **6** (1/1 CH₂Cl₂/pentane, -35 °C, 2 days) allowing XRD, ¹H and ³¹P{¹H} NMR characterization. Note that, according to ¹H NMR analysis, the remaining CH₂Cl₂/pentane mother liquor consisted of complex **8**, trace amount of species **6'** and [Zn(OBn)₂]_n species, in line with the conversion of **6** to **8** discussed above. No exploitable ¹³C{¹H} NMR data for **6'** could however be obtained due to its low solubility in common organic solvents. In the solid state and as depicted in Figure 4, species **6'** consists of a dinuclear Zn(II) species containing only one benzyloxy moiety for three *P,O* bidentate ligands (*vs.* a 1/1 ratio in the parent compound **6**). The Zn(II) centers in **6'** are connected to one another through a μ -O-benzyloxy moiety and a μ - κ^1 : κ^1 -*P,O* bridging phosphinophenolate ligand. A close Zn2...O3 contact [2.465(2) Å] may also be noted with a distance well below the sum of the corresponding VdW radii (2.91 Å), yet too long to be considered as a Zn-O dative bond (typically ranging from 2.10 to 2.25 Å).¹⁶ Nevertheless, such a contact possibly explains the observed trigonal pyramidal geometry at Zn(2), with the P2, P3 and O4 atoms occupying the equatorial positions (the central Zn2 atom lies only 0.316 Å outside the P2-P3-O4 mean plane) while the O2 and O3 atoms (from the κ^2 -*P,O*- and μ - κ^1 : κ^1 -*P,O* ligand, respectively) are in the apical positions. In contrast, the Zn1 centre may be described as four-coordinate with a distorted tetrahedral geometry due to the bidentate κ^2 -*P,O*-chelation of a *P,O* ligand [bite angle = 84.25(7)°] and the bonding with the μ - κ^1 : κ^1 -*P,O* ligand through O3. Overall, the bonding distances in **6'** are in the expected ranges with Zn-P bond lengths [2.370(9)-2.411(9) Å] comparable to those found in related Zn phosphino complexes [Zn-P: 2.322(1)-2.678(2) Å].^{16,17} Also, the terminal and bridging Zn-O bond distances in complex **6'** are in line with those found in the literature [Zn-O_{Terminal}: 2.336(5)-1.844(4) Å; Zn-(μ -O_{alkoxide})-Zn: 2.148(5)-1.976(5) Å].¹⁷


**6'****Chart 2.** Labelling of the phosphorus atoms in the Zn(II) complex **6'**

The NMR data for species **6'** agree with its solid-state structure being retained in CD₂Cl₂ solution at room temperature (ESI – Figures S5A-C). In particular, the ³¹P{¹H} NMR (CD₂Cl₂) spectrum of **6'** features three sets of resonances (ESI – Figure S5C): a sharp singlet (δ -35.6 ppm; P1 in Chart 2) and two doublets assigned to the two P atoms coordinated on the same Zn(II) center and *cis* to one another (δ -31.8 ppm, $^2J_{P,P} = 87$ Hz; -25.6 ppm, P2 and P3 in Chart 2). The ¹H NMR spectrum of species **6'** is consistent with the presence of one benzyloxide group for three phosphinophenolate entities.

**Figure 4.** Left: ORTEP drawing of the molecular structure of **6'**. Thermal ellipsoids are set at the 50% probability level. Hydrogen atoms are omitted and only the *ipso*-carbon of each P-phenyl ring is

represented for clarity. Selected bond distances (Å): Zn1-P1 2.370(9), Zn1-O1 1.949(2), Zn1-O3 1.934(2), Zn1-O4 1.933(2), Zn2-P2 2.411(9), Zn2-O2 1.983(3), Zn2-P3 2.411(7), Zn2-O3 2.465(2), Zn2-O4 1.941(2) and angles (deg): P1-Zn1-O1 84.25(7), O3-Zn1-O4 88.46(9), P1-Zn1-O3 124.9 (7), O1-Zn1-O4 115.9(9), P2-Zn2-O2 81.59(7), P2-Zn2-P3 116.8(3), P2-Zn2-O4 127.3(7), P3-Zn2-O4 109.9(7), O2-Zn2-O3 179.8(8), P3-Zn2-O3 71.27(5). Right: Zoom on the coordination spheres around Zn1 and Zn2.

Homoleptic Phosphinophenolate Zn(II) species 7 and 8. The synthesis of the homoleptic compounds $[Zn(P,O)_2]$ (**7** and **8**, Scheme 3) was also performed for their subsequent use in ROP catalysis as well-defined Lewis acids. Thus, the reaction of $ZnEt_2$ with 2 equiv. of phosphinophenols **1-H** and **2-H** (CH_2Cl_2 , room temp.) led to the quantitative formation of the corresponding bis-(phosphinophenolate) Zn(II) complexes **7** and **8**, respectively, which were isolated in high yield as colorless solids. The structures of both species were deduced from NMR data, elemental analysis and, in the case of **7**, through XRD studies.

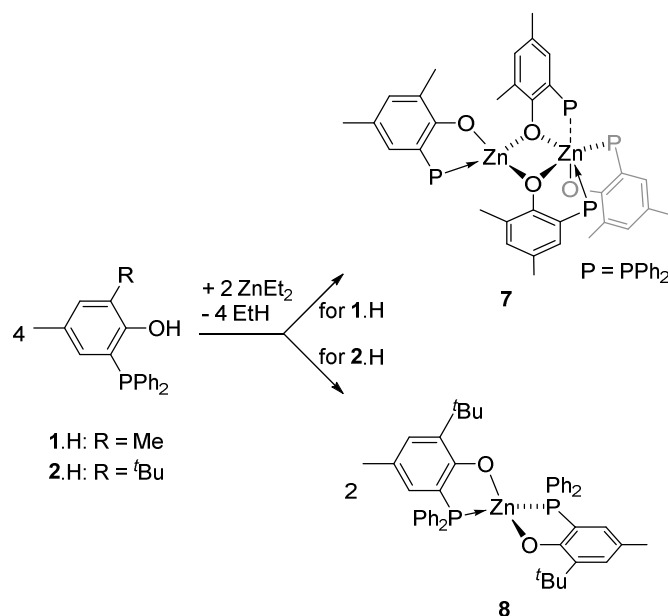

Scheme 3. Synthesis of the homoleptic bis(phosphine-phenolate) (P,O)-supported zinc(II) complexes **7** and **8**.

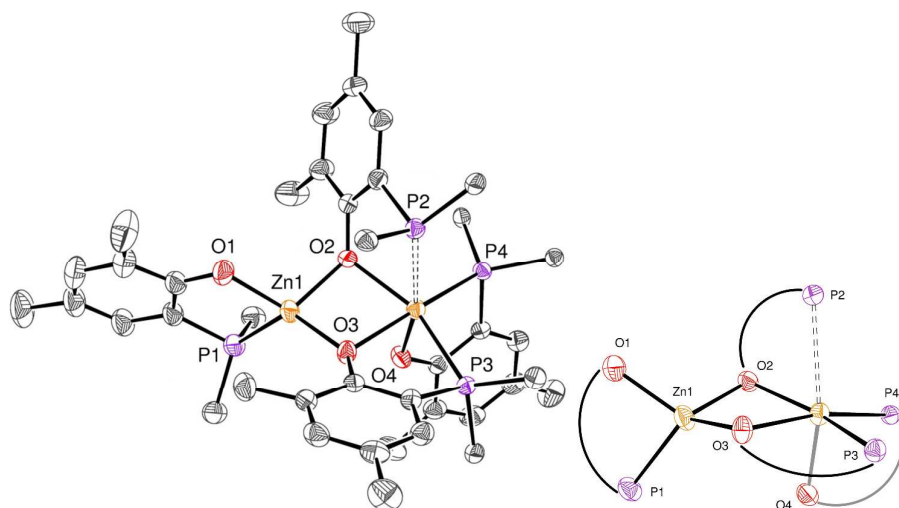


Figure 5. *Left:* ORTEP drawing of the molecular structure of **7**. Thermal ellipsoids are set at the 50% probability level. Hydrogen atoms are omitted and only the *ipso*-carbons of the PPh_2 rings are represented for clarity. Selected bond distances (\AA) around Zn1: Zn1-P1 2.393(9), Zn1-O1 1.936(1), Zn1-O2 1.973(2), Zn1-O3 1.946(2) and around Zn2: Zn2-P2 2.690(6), Zn2-O2 2.116(1), Zn2-P3 2.531(7), Zn2-O3 2.201(2), Zn2-P4 2.543(8), Zn2-O4 2.005(2) and angles (deg) around Zn1: P1-Zn1-O1 86.77(6), O2-Zn1-O3 87.52(7) and around Zn2: P2-Zn2-O2 73.72(5), P2-Zn2-P3 97.43(2), P3-Zn2-O4 94.68(5), O4-Zn2-O2 92.81(7), P4-Zn2-O3 168.05(5). *Right:* a zoom on the different coordination environment for Zn1 and Zn2.

In the solid state, as depicted in Figure 5, the homoleptic Zn(II) complex **7** crystallizes as a dinuclear species with the two Zn(II) centres being connected *via* two μ -O-phenolate bridges. Though the formation of species **7** formally arises from the assembly of two $[Zn(P,O)_2]$ molecules, species **7** is not dimeric as reflected by the different coordination environment of the two Zn(II) centres. While Zn1 adopts a tetrahedral geometry similar to that observed in dimer $[(P,O)\text{-ZnEt}]_2$ (**3**), the Zn2 metal centre lies in a slightly distorted octahedral environment due to the coordination of three bidentate P,O ligands. The three phosphorus ligands P2, P3 and P4 coordinate to Zn2 in a *fac*-fashion and the corresponding Zn-P bond distances [$Zn2\text{-P3} = 2.531(7)$, $Zn2\text{-P4} = 2.543(8)$, $Zn2\text{-P2} = 2.690(6)$ \AA] are significantly

longer than the Zn1-P1 bond distance [2.393(9) Å] and those observed in related species **3** and **6**. The Zn-P bond distances in **7** also lie in the upper range of Zn-P bond lengths [Zn-P: 2.322(1)-2.678(2) Å], certainly reflecting the electronic saturation of the Zn2 centre in **7**.¹⁷ The assembly of two four-coordinate Zn species such as [Zn(*P,O*)₂] entities may be expected to yield two penta-coordinate Zn(II) centres in the solid state: in the present case, the different coordination environment of Zn1 vs. Zn2 in the solid state structure of **7** may relate to the (small) preference of Zn(II) species for a four-coordinate tetrahedral environment.

The ¹H NMR data for complex **7** exhibit one set of broadened signals for the *P,O* ligands (ESI – Figure S6A). The ³¹P{¹H} NMR spectrum for **7** contains three resonances: a sharp singlet (δ -30.3 ppm) and two broad resonances (δ -18.7 and -37.2 ppm; ESI – Figure S6B). To gain further insight, low temperature ¹H and ³¹P{¹H} NMR experiments were performed but the low solubility of species **7** (precipitation as the NMR sample was cooled down) precluded the obtainment of exploitable data. Nevertheless, DOSY NMR data for **7** suggest a comparable level of aggregation in solution (CD₂Cl₂, room temp.) and in the solid state. As shown in Figure S12 (ESI), the molecular volume of **7** in solution (V_{DOSY} = 1358 Å³, hydrodynamic radius = 6.87 Å; ESI – Table S2) is similar to that estimated from solid state data (V_{X-ray} = 1303 Å³; ESI – Figure S17). The ¹H, ¹³C{¹H} and ³¹P{¹H} NMR data for complex **8** (CD₂Cl₂, room temp.) exhibit one set of resonances for the Zn-coordinated *P,O* ligands and are in line with the proposed structure for **8** (ESI – Figures S7A-C). DOSY NMR data for **8** (CD₂Cl₂, room temp., hydrodynamic radius = 6.04 Å, V_{DOSY} = 922 Å³, ESI – Figure S13 and Table 2) are consistent with a monomeric structure for species **8**: a geometrical optimization of a model molecule of **8** (ESI – Figure S18) led to a calculated volume (987 Å³; ESI – Figure S19), close to that experimentally determined in solution. Altogether, the solution data for species **7** and **8** at room temperature agree with a dinuclear

structure for **7** while species **8** is a $[Zn(P,O)_2]$ -type mononuclear species, which is certainly due a superior steric protection of the Zn(II) centre by the *P,O* bidentate ligand **2** vs. **1**.

ROP of *rac*-LA, ϵ -CL and TMC by species **5.** The Zn(II) benzyloxide dimer **5** efficiently initiates *rac*-LA, ϵ -CL and TMC ROP. The results are summarized in Table 1. The combination of Zn alkoxide analogue **6** with lactide also resulted into the production of narrowly disperse and chain-length controlled PLA with a ROP efficiency similar to that observed with **5**. However, the lack of stability of **6** in solution (*vide supra*) casts doubt onto the nature of the ROP-active initiator(s) and the ROP results with species **6** are thus not reported herein.

Using **5** as a ROP initiator, the quantitative conversion of 100 equiv. *rac*-LA to extremely narrow disperse and atactic PLA may be achieved within 2 h at room temperature ($1 < PDI < 1.05$; entry 1, Table 1) as deduced from SEC and NMR data (ESI – Figure S20). A good agreement between the expected and experimental chain-lengths [$M_n(\text{theo})$ vs. $M_n(\text{corr})$] is also observed (Figure 6), in line with a controlled ROP process and the formation of chain-length controlled PLA. Additional data consistent with a well-behaved ROP process include a first-order dependence on *rac*-LA concentration ($k_{\text{obs}} = 0.0282 \text{ min}^{-1}$, Figure 6) and MALDI-TOF mass spectrometric data consistent with OB $_n$ -end-capped PLA materials (ESI – Figure S23). A coordination-insertion ROP mechanism is thus assumed for this system with the Zn-OB $_n$ group acting as the initiating moiety, and, unlike what was earlier observed in related (*P,O*)Al-based ROP initiators,^{6a} with the apparent non-involvement of the *P,O* ligand as an initiating group.¹⁸ A polymerization run under standard conditions (100 equiv. *rac*-LA, $[M]_0 = 1 \text{ M}$, room temp., 2 h) in THF afforded PLA with a 40% conversion (vs. 97% conv. in CH_2Cl_2), suggesting a monomer/solvent competition. Complex **5** was also found to quantitatively polymerize 100 equiv. of *rac*-LA in bulk conditions within 20 min. (130 °C, no

solvent; entry 3, Table 1), yet with substantial loss of PLA chain length control and a broader PDI. The ROP of *rac*-LA initiated by **5** was also carried out under immortal conditions in the presence of benzyl alcohol acting as an external chain-transfer agent, yielding the nearly quantitative conversion of 500 equiv. of *rac*-LA within 7 h to well-defined and narrow disperse PLA (entry 2, Table 1) as deduced from SEC data (ESI – Figure S23).¹⁹

Likewise, species **5** also effectively initiates the controlled ROP of ϵ -CL to afford chain-length-controlled, narrow disperse and OBn-end-capped PCL (entries 4 and 5, Table 1), as deduced from SEC and MALDI-TOF analyses (ESI – Figures S21 and S25). Kinetic data for species **5** (Figure 6, ESI – Figure S28) agree with a controlled ROP process proceeding slightly faster than with *rac*-LA ($k_{\text{obs}} = 0.0372 \text{ min}^{-1}$).

The use of well-defined metal alkoxide complexes for the controlled ROP of TMC remain rare and, in particular, only a few Zn-based discrete species have been reported so far.^{4i,8c,20} The performance of Zn(II) alkoxide species **5** for the ROP of TMC was therefore evaluated (entries 6 and 7, Table 1). Compound **5** efficiently polymerizes 100 equiv. TMC at room temperature (2 h, CH₂Cl₂) with the high yield production of well-defined and OBn-end-capped PTMC material. All data (SEC, MALDI-TOF, kinetic studies: Figure 6 and ESI – Figures S22, S26, S29) agree with controlled polymerization reactions under living and immortal conditions. It may be noted that the ROP of TMC initiated by species **5** is slower than those of *rac*-LA and ϵ -CL ($k_{\text{obs}} = 0.0171 \text{ min}^{-1}$, Figure 6).

Table 1. ROP of *rac*-LA, ϵ -CL and TMC initiated by the (*P,O*)-Zn alkoxide species **5** and homoleptic [Zn(*P,O*)₂] complexes **7** and **8**.[□]

Run	Init.	Monomer	Zn/M/BnOH	time (min)	Conv ^a (%)	M_n^b (corr.)	M_n^c (theo.)	PDI ^d
1	5	<i>rac</i> -LA	1/100/0	120	97	13690	13980	1.02

2	5	<i>rac</i> -LA	1/500/4	450	99	14190	14270	1.02
3 ^e	5	<i>rac</i> -LA	1/100/0	20	97	50520	13980	1.63
4	5	ϵ -CL	1/100/0	120	99	10400	11300	1.03
5	5	ϵ -CL	1/500/4	450	99	13254	11300	1.11
6	5	TMC	1/100/0	120	87	8030	8880	1.13
7	5	TMC	1/500/4	450	99	14560	10110	1.16
8	7	<i>rac</i> -LA	1/100/1	180	51	4140	7350	1.06
9	8	<i>rac</i> -LA	1/100/1	180	83	6900	11950	1.05

□ Conditions: CH_2Cl_2 , $[\text{M}]_0 = 1 \text{ M}$, room temp., M_n values are given in $\text{g}\cdot\text{mol}^{-1}$. ^a Determined by ¹H NMR. ^b Determined by GPC using polystyrene standards and applying the appropriate correcting factor (0.58, 0.56 or 0.88 for PLA, PCL and PTMC, respectively).²¹ ^c Calculated according to the conversion ($M_{LA} = 144.13 \text{ g}\cdot\text{mol}^{-1}$, $M_{CL} = 114.14 \text{ g}\cdot\text{mol}^{-1}$, $M_{TMC} = 102.09 \text{ g}\cdot\text{mol}^{-1}$). ^d Determined by GPC. ^e ROP run in bulk conditions, 130 °C.

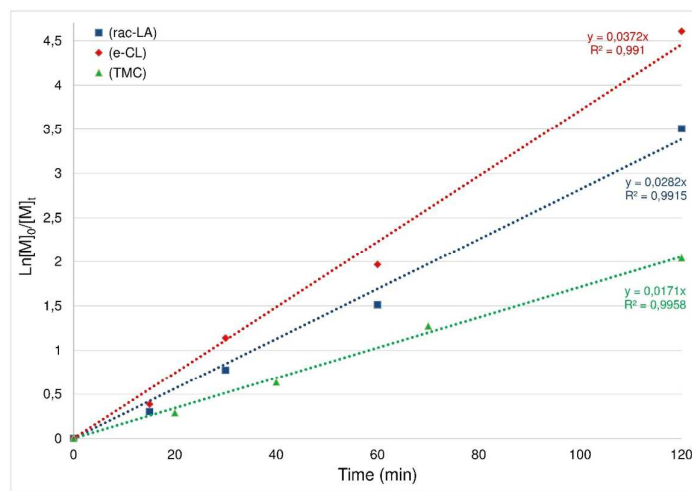


Figure 6. Semilogarithmic plots of *rac*-LA (blue), ϵ -CL (red) and TMC (green) conversion versus time for complex **5**. Reaction conditions: $[\text{Zn}]/[\text{M}]_0 = 100$, $[\text{M}]_0 = 1 \text{ M}$, CH_2Cl_2 , room temp.

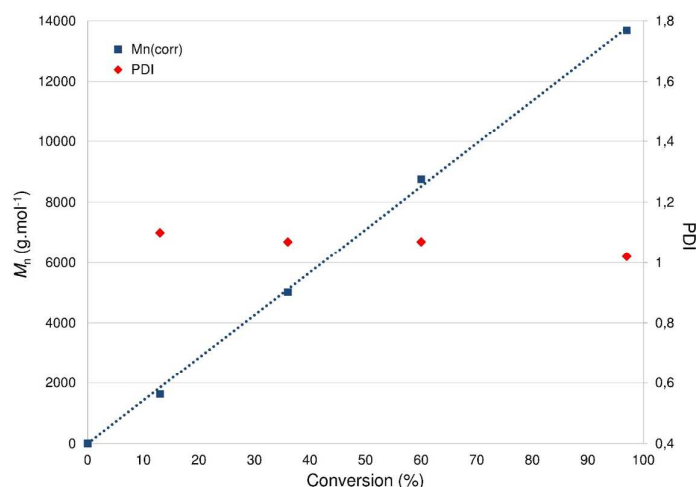


Figure 7. Linear dependence of M_n and PDI [M_w/M_n] of PLA versus monomer (*rac*-LA) conversion with **5** as a catalyst. Reaction conditions: $[Zn]/[LA]_0 = 100$, $[LA]_0 = 1$ M, CH_2Cl_2 , room temp.

ROP of *rac*-LA by the Zn(II) species **7 and **8**.** The homoleptic Zn(II) species **7** and **8** were also tested for lactide ROP activity. Both **7** and **8** are inactive in the ROP of *rac*-LA under the standard conditions used for ROP initiator **5** (100 equiv., CH_2Cl_2 , room temp., 2 h), further confirming the Zn-bonded *P,O* ligand is not an effective initiating group in these systems. However, the combination of an external nucleophile such as BnOH and compound **7/8** initiates the ROP of *rac*-LA at room temperature to afford narrow disperse and slightly heterotactic-enriched PLA material ($P_r = 0.58$ and 0.64 for **7** and **8**, respectively), albeit with lower M_n values than expected (entries 8 and 9, Table 1). The **7/8** and BnOH initiating mixture is less active than discrete Zn alkoxide species **5** with 51%/83% consumption of 100 equiv. *rac*-LA after 3 h of reaction (entries 8 and 9 vs. 1, Table 1). Kinetic data for **7/BnOH** and **8/BnOH** (ESI – Figure S30) are consistent with a pseudo-first order reaction relative to monomer and with the ROP mediated by **8/BnOH** proceeding roughly twice faster than that by **7/BnOH** ($k_{obs} = 0.0099$ vs. 0.0041 min⁻¹). Such a difference in ROP activity between **7** and **8** is certainly related to the more reactive/accessible Zn centre in mononuclear species **8** (vs. in dinuclear species **7**) for monomer activation. MALDI-TOF spectrometric analysis of a PLA

sample produced via ROP of *rac*-LA with a **7**/BnOH mixture agrees with the exclusive formation of OBn-end-capped PLA material with equally-separated peaks by 144 u.a. (ESI – Figure S27). This, together with the absence of reaction between species **7** or **8** and 1 equiv. of BnOH as monitored through a NMR scale reaction (CD₂Cl₂, 2h, room temp.), rules out a ROP proceeding *via* coordination-insertion mechanism from an *in situ* generated Zn-OBn initiator. It seems likely the **7/8** and BnOH two-component mixture polymerizes lactide *via* an “activated monomer” mechanism with the Zn compounds **7/8** acting as a well-defined Lewis acid for monomer activation and BnOH as an external nucleophile source.¹⁸ The ROP initiation then occurs *via* a nucleophilic attack of BnOH at a Zn(II)-activated lactide.

Co- and ter-Polymerization of L-LA, ϵ -CL and TMC by species 5. The excellent ROP control and activity in the homo-polymerization of *rac*-LA, ϵ -CL and TMC of compound **5** was further exploited to access diblock PCL-*b*-PLLA and PTMC-*b*-PLLA co-polymers and triblock PTMC-*b*-PCL-*b*-PLLA *ter*-polymers *via* sequential ROP. Such PLA-based *co*- and *ter*-polymers may improve and tune the properties of PLA.²² For instance, the brittleness of PLLA (the commercial form of PLA) may be improved upon incorporation of a softer and flexible PTMC segment, as in PTMC-*b*-PLLA.

Species **5** mediates the sequential ROP of TMC and/or PCL and L-LA to produce in high conversion the corresponding narrow disperse *co*- and *ter*-polymers as determined from SEC and NMR data (ESI – Figures S31-34). The results are summarized in Table 2. The sequential additions of the desired monomer were carefully NMR monitored to ensure complete or nearly complete consumption prior to the addition of the subsequent monomer. Note that the order of monomer addition is crucial for these ROPs to proceed: when L-LA was first polymerized, the subsequent ROP of TMC or ϵ -CL did not proceed (CH₂Cl₂, room temp.). The *in situ* generated Zn-PLLA chains somehow disfavor PCL and PTMC chain

growth and thus L-LA was added last in all ROP runs. Though little is known about the reactivity of TMC *vs.* cyclic esters under co-polymerization conditions, the present observations with CL and LA are in line with various metal-mediated CL/LA co-polymerization studies where the greater reactivity of LA *vs.* CL under co-polymerization conditions is well-established.²³

Table 2. Block *co*- and *ter*-polymerization of L-LA and ϵ -CL and/or TMC initiated by complex **5**.^{□□}

Entry	Init.	Zn/TMC/ ϵ -CL/ L-LA	TMC	Time (h)		Conv ^a (%)	M_n^b (GPC)	M_n^c (corr.)	M_n^d (theo.)	PDI ^e
				ϵ -CL	L-LA					
1	5	1/100/0/100	2	-	4	94	63770	41570	23270	1.09
2	5	1/0/100/100	-	2.5	4	87	54050	30940	22830	1.05
3	5	1/100/100/100	2.5	3	4	97	87790	54940	35070	1.13

[□] Conditions: CH₂Cl₂, [M]₀ = 1 M, room temp, M_n values are given in g.mol⁻¹. ^a Determined by ¹H NMR. ^b Determined by GPC using polystyrene standards. ^c Determined by GPC using polystyrene standards and applying the appropriate correcting factor for the ¹H NMR determined (PLA, PCL and PTMC fractions: 0.58, 0.56 and 0.88, respectively)²¹ according to the conversion of each monomer. ^d Calculated according to the conversion of each monomer. ^e Determined by GPC.

Conclusion

The coordination chemistry of bidentate *P,O* anionic ligands to Zn(II) allowed access through alkane elimination reactions to structurally diverse (*P,O*)-Zn species ranging from dimeric Zn(II) alkyl/alkoxide species (**3-6**) to homoleptic complexes of the type $[\text{Zn}(\text{P},\text{O})_2]$ (**7** and **8**). As deduced from combined solid state and solution structural data, the level of aggregation observed in the solid state (in favor of dinuclear species) and in solution are similar. The use of sterically bulky *P,O* ligands such as **2.H** reduces aggregation in the homoleptic series (mononuclear **8** vs. dinuclear **7**). Steric hindrance seems to be of importance in the lack of stability of heteroleptic Zn(II) alkoxide complex **6** (to yield homoleptic species **8**): as a comparison, the less encumbered analogue **5** is stable under identical conditions. The lability of the Zn-phosphine bond may also favor ligand exchange reactions yielding homoleptic species **8** from $[(\text{P},\text{O})\text{Zn}-\text{OBn}]_2$ Zn(II) alkoxide **6**. When compared to the present $[(\text{P},\text{O})\text{ZnOR}]_2$ systems, $[(\text{LX})\text{Zn}-\text{OBn}]_2$ species (LX = N-/O-based anionic ligand) are typically much more robust.^{2f} Nevertheless, the Zn(II) alkoxide species **5** is a well-behaved ROP initiator of LA, ϵ -CL and TMC with the production of narrow disperse materials under living and immortal conditions, with catalytic activities comparing well with the majority of Zn(II)-based ROP species thus far developed. Interestingly, the homoleptic species $[\text{Zn}(\text{P},\text{O})_2]$ **7** and **8** may act as discrete ligand-supported Zn(II) Lewis acids able to promote the ROP of lactide in the presence of an external nucleophile such as BnOH. The lability of the Zn-phosphine bonds in **7** and **8** certainly facilitates monomer activation under ROP conditions. Future studies with **7** and **8**/alcohol bi-component mixtures may focus on the addition of a Brønsted base for activation of the initiating/propagating alcohol (dual approach of catalytic ROP) for higher performance ROP catalysts.²⁴

Experimental section

General Procedures

All experiments were performed under N₂ by using standard Schlenk techniques or in a nitrogen-filled glovebox. Toluene and pentane were collected after passing through drying columns through a solvent purification system and stored over activated molecular sieves (4 Å) for 24 h in a glovebox before use. THF was distilled over the Na–benzophenone complex and stored over activated molecular sieves (4 Å) for 24 h in a glovebox before use. CH₂Cl₂, CD₂Cl₂ and CDCl₃ were distilled from CaH₂, degassed under a N₂ flow, and stored over activated molecular sieves (4 Å) in a glovebox before use. Anhydrous BnOH (99.8%) was purchased from Aldrich and stored over activated molecular sieves (4 Å) for 24 h in a glovebox before use. All deuterated solvents were obtained from Eurisotop (Groupe CEA, Saclay, France). *rac*-Lactide and L-Lactide (98% purity) were purchased from Aldrich and sublimed once before use. Trimethylene carbonate (purchased from Boehringer) was recrystallized twice from dry Et₂O and ε-Caprolactone was distilled from CaH₂ prior to use. All other chemicals were purchased from Aldrich and were used as received. The NMR spectra were recorded on Bruker AC 300, 400 or 500 MHz NMR spectrometers with Teflon-valved J. Young NMR tubes at ambient temperature otherwise specified. ¹H and ¹³C chemical shifts were determined by reference to the residual ¹H and ¹³C solvent peaks. The diffusion-ordered NMR spectroscopy (DOSY) experiments were performed with a Bruker 600 MHz NMR spectrometer. Elemental analyses for all compounds were performed at the Service de Microanalyse of the Université de Strasbourg (Strasbourg, France). GPC analyses were performed on a system equipped with a Shimadzu RID10A refractive index detector with HPLC grade THF as an eluent (with molecular masses and PDIs calculated by using polystyrene standards). These were adjusted with appropriate correction factors for the *M_n* values. MALDI-TOF-MS analyses were performed at the Service de Spectrométrie de Masse

de l'Institut de Chimie de Strasbourg and run in a positive mode: samples were prepared by mixing a solution of the polymers in CH_2Cl_2 ($0.5 \text{ mg } 100 \text{ mL}^{-1}$); 2,5-dihydroxybenzoic acid was used as the matrix in a volume ratio of 5:1. Proligands **1**·H and **2**·H were prepared according to literature methods.¹¹

*Synthesis of [(P,O)ZnEt]₂ complexes **3** and **4***

Compound 3: A precooled CH_2Cl_2 (10 mL, $-35 \text{ }^\circ\text{C}$) solution of ZnEt_2 (161.3 mg, 1.31 mmol, 1 equiv.) was slowly added to a solution of the proligand **1**·H (400 mg, 1.31 mmol, 1 equiv.) in CH_2Cl_2 (10 mL) at $-35 \text{ }^\circ\text{C}$. A white precipitate formed rapidly. The reaction mixture was then allowed to warm to RT and stirred overnight. A white solid was separated by sedimentation and removing of the solvent *via* a pipette. The colorless solid was isolated after washing twice with pentane (2 x 10 mL) and drying under reduced pressure (86% yield). Anal. calcd (%) for $\text{C}_{44}\text{H}_{46}\text{O}_2\text{P}_2\text{Zn}_2$ (799.56): C 66.10, H 5.80; found: C 65.91, H 5.84. The low solubility of complexes **3** and **4**, related to its dimeric structure, precluded the obtainment of ^{13}C NMR data. ^1H NMR (400 MHz, CDCl_3): δ (ppm) = -0.28 (2H, q, $^3J = 7.2 \text{ Hz}$, ZnCH_2CH_3), 0.69 (3H, t, $^3J = 7.2 \text{ Hz}$, ZnCH_2CH_3), 2.13 (3H, s, *o*- CH_3), 2.21 (3H, s, *p*- CH_3), 6.68 (1H, br. s, Ar), 6.98 (1H, br. s, Ar), 7.38-7.41 (10H, m, Ar). $^{31}\text{P}\{^1\text{H}\}$ NMR (162 MHz, CDCl_3): δ (ppm) = -30.3 (s).

Compound 4: synthesized following the same procedure than for **3** with the use of ZnEt_2 (177.2 mg, 1.44 mmol, 1 equiv.), proligand **2**·H (500 mg, 1.44 mmol, 1 equiv.), with the final isolation of species **4** as an analytically pure solid (82% yield). Elemental analysis calcd (%) for $\text{C}_{50}\text{H}_{58}\text{O}_2\text{P}_2\text{Zn}_2$ (883.72): C 67.96, H 6.62; found: C 67.83, H 6.55. ^1H NMR (400 MHz, CDCl_3): δ (ppm) = -0.05 (2H, q, $^3J = 8.0 \text{ Hz}$, ZnCH_2CH_3), 0.74 (3H, t, $^3J = 8.0 \text{ Hz}$, ZnCH_2CH_3), 1.26 (9H, s, *o*- $\text{C}(\text{CH}_3)_3$), 2.12 (3H, s, *p*- CH_3), 6.77 (1H, d, $^3J = 6.0 \text{ Hz}$, Ar), 7.08 (1H, br. s, Ar), 7.27-7.62 (10H, m, Ar).

Synthesis of [(P,O)Zn(OBn)]₂ complexes 5 and 6 and of the [(2)₂Zn₂(μ-OBn)(μ-2)] dinuclear species 6'

Compound 5: A precooled CH₂Cl₂ (5 mL, -35 °C) solution of BnOH (65 μL, 0.625 mmol, 2 equiv.) was slowly added to a suspension of complex **3** (250 mg, 0.313 mmol, 1 equiv.) in CH₂Cl₂ (15 mL) at -35 °C. The cloudy colorless suspension progressively changed color to light yellow. The reaction mixture was then allowed to warm to RT and stirred overnight. A colorless solid was separated by sedimentation and the solvent was removed *via* a pipette. The colorless solid was isolated after washing twice with pentane (2 x 10 mL) and drying under reduced pressure (88% yield). Anal. data calcd (%) for C₅₄H₅₀O₄P₂Zn₂ (955.70): C 67.87, H 5.27; found: C 67.76, H 5.39. ¹H NMR (400 MHz, CD₂Cl₂): δ (ppm) = 2.02 (3H, s, Ph-CH₃), 2.11 (3H, s, Ph-CH₃), 4.57 and 4.68 (1H and 1H, AB spin system, broad, OCH₂Ph), 6.53 (1H, br. s, Ar), 6.93-7.12 (13H, m, Ar), 7.27-7.47 (3H, m, Ar). ¹³C{¹H} NMR (75 MHz, CD₂Cl₂): δ = 17.5 (Me), 20.6 (Me), 68.5 (OCH₂Ph), 123.8 (C arom), 126.8 (C arom), 127.5 (C arom), 128.3 (C arom), 128.9 (C arom), 130.2 (C arom), 130.4 (C arom), 133.8 (C arom), 135.3 (C arom), 144.4 (C_{quat}). ³¹P{¹H} NMR (162 MHz, CD₂Cl₂): δ (ppm) = -31.6 (s).

Compound 6: synthesized following the same procedure than for **5** with BnOH (75.3 μL, 0.724 mmol, 2 equiv.), complex **4** (320 mg, 0.362 mmol, 1 equiv.), yielding species **6** as an analytically solid (91% yield). Anal. data calcd (%) for C₆₀H₆₂O₄P₂Zn₂ (1039.86): C 69.30, H 6.01; found: C 69.12, H 5.99. ¹H NMR (400 MHz, CDCl₃): δ (ppm) = 1.53 (9H, s, *o*-C(CH₃)₃), 2.18 (3H, s, *p*-CH₃), 4.46 and 4.77 (1H and 1H, AB spin system, ²J = 11.2 Hz, OCH₂Ph), 6.63 (1H, d, ²J = 5.6 Hz, Ar), 6.91 (1H, br, Ar), 7.20 (3H, t, ²J = 7.2 Hz, Ar), 7.27 (5H + CDCl₃, br, Ar), 7.31-7.39 (6H, m, Ar), 7.43-7.50 (1H, m, Ar). ³¹P{¹H} NMR (162 MHz, CDCl₃): δ (ppm) = -31.6 (s).

Complex 6' $[(\kappa^2-2)_2\text{Zn}_2(\mu\text{-OBn})(\mu\text{-}\kappa^1:\kappa^1-2)]$. Dinuclear species **6'** was serendipitously prepared via crystallization of a saturated solution (1/1 CH_2Cl_2 /pentane, -35°C) of compound **6** (15% yield). Complex **6'** can be isolated in 41% yield by harvesting the crystals formed after 2 days. Crystallization process: pentane vapor diffusion into a saturated CH_2Cl_2 solution of complex **6**. The structure of species **6'** was XRD determined and the collected crystals allow characterization *via* ^1H , $^{31}\text{P}\{^1\text{H}\}$ NMR spectroscopy and elemental analysis. Anal. data calcd (%) for $\text{C}_{76}\text{H}_{79}\text{O}_4\text{P}_3\text{Zn}_2$ (1280.15): C 71.31, H 6.22; found: C 71.11, H 6.28. ^1H NMR (400 MHz, CD_2Cl_2): δ (ppm) = 0.93 (9H, s, 1 *o*- $\text{C}(\text{CH}_3)_3$), 1.45 (18H, s, 2 *o*- $\text{C}(\text{CH}_3)_3$), 2.15 (6H, s, 2 *p*- CH_3), 2.20 (3H, s, 1 *p*- CH_3), 4.47 and 4.82 (1H and 1H, AB spin system, $^2J = 11.2$ Hz, 1 OCH_2Ph), 6.28 (2H, br, Ar), 6.41 (1H, br, Ar), 6.72 (3H, br, Ar), 6.90-6.99 (8H, m, Ar), 7.05-7.07 (8H, d, $^2J = 8$ Hz, Ar), 7.15-7.17 (2H, d, $^2J = 7.6$ Hz, Ar), 7.30-7.36 (6H, m, Ar), 7.40-7.45 (8H, m, Ar), 7.57-7.62 (2H, m, Ar), 7.71 (1H, br, Ar). $^{31}\text{P}\{^1\text{H}\}$ NMR (162 MHz, CD_2Cl_2): δ (ppm) = -35.6 (s), -31.8 (d, $^2J_{\text{P,P}} = 87$ Hz), -25.6 (d, $^2J_{\text{P,P}} = 87$ Hz).

Synthesis of $[\text{Zn}(\text{P},\text{O})_2]$ complexes 7 and 8

Compound 7. A precooled CH_2Cl_2 (10 mL, -35°C) solution of ZnEt_2 (80.6 mg, 0.653 mmol, 1 equiv.) was slowly added to a solution of the proligand **1**·H (400 mg, 1.31 mmol, 2 equiv.) in CH_2Cl_2 (10 mL) at -35°C . The reaction mixture was then allowed to warm to RT and stirred overnight. The volatiles were removed under reduced pressure, and the residue was washed twice with pentane (2 x 10 mL), affording after drying a light yellow crystalline solid (90% yield). Anal. data calcd (%) for $\text{C}_{40}\text{H}_{36}\text{O}_2\text{P}_2\text{Zn}$ (676.05): C 71.07, H 5.37; found: C 71.23, H 5.56. ^1H NMR (400 MHz, CDCl_3): δ (ppm) = 2.32 (6H, s, 2 *o*- CH_3), 2.48 (6H, s, 2 *p*- CH_3), 6.88 (2H, br. s, Ar), 7.14 (2H, br. s, Ar), 7.30 (4H, d, $^3J = 7.6$ Hz, Ar), 7.38 (4H, t, $^3J = 6.8$ Hz, Ar), 7.60-7.92 (12H, m, Ar). $^{31}\text{P}\{^1\text{H}\}$ NMR (162 MHz, CDCl_3): δ (ppm) = -18.7 (br), -30.3 (s), -37.2 (br).

Compound 8: synthesized following the same procedure than for **7** with ZnEt₂ (95.7 mg, 0.775 mmol, 1 equiv.), proligand **2**·H (540 mg, 1.55 mmol, 2 equiv.), yielding a white solid (82%). Anal. data calcd (%) for C₄₆H₄₈O₂P₂Zn (760.22): C 72.68, H 6.36; found: C 72.55, H 6.47. ¹H NMR (500 MHz, CD₂Cl₂): δ (ppm) = 1.46 (18H, s, 2 *o*-C(CH₃)₃), 2.16 (6H, s, 2 *p*-CH₃), 6.85 (2H, br. s, Ar), 7.13 (2H, d, ³J = 2.5 Hz, Ar), 7.32 (8H, t, ³J = 7.5 Hz, Ar), 7.43 (6H, t, ³J = 7.5 Hz, Ar), 7.47 (6H, br. m, Ar). ¹³C{¹H} NMR (125 MHz, CD₂Cl₂): δ = 20.4 (Me), 29.1 (^tBu), 35.3 (^tBu), 111.9 (C_{quat}, J_{C-P} = 27.75 Hz), 123.0 (C_{quat}), 128.9 (C arom), 129.8 (C_{quat}, J_{C-P} = 21.25 Hz), 130.3 (C arom), 130.4 (C arom), 131.9 (C arom), 133.4 (C arom), 139.4 (C arom), 148.2 (C_{quat}), 169.9 (C_{quat}, J_{C-P} = 10.90 Hz). ³¹P{¹H} NMR (162 MHz, CD₂Cl₂): δ (ppm) = -31.1 (s).

General procedure for the ROP of LA, ε-CL and TMC by species 5, 7 and 8

In a glovebox, the initiator was charged in a vial equipped with a TeflonTM-tight screw-cap and a monomer solution ([M]₀ = 1 M, THF or CH₂Cl₂) was added *via* a syringe all at once. The solution was vigorously stirred the appropriate time and at room temperature. When the desired time was reached, aliquots were taken and analyzed by ¹H NMR spectroscopy to estimate the conversion. The reaction mixture was exposed to air and volatiles removed under vacuum, the resulting solid was then washed several times with MeOH, dried in *vacuo* until constant weight and subsequently analyzed by ¹H NMR and SEC. In some cases, a MALDI-TOF-MS analysis was performed.

For ROPs under immortal conditions, an identical procedure to that above was used but with the initial addition of a monomer solution ([M]₀ = 1 M, CH₂Cl₂) containing the desired amount of benzylic alcohol (BnOH) onto complex **5**.

For sequential *co*- and *ter*-polymerization runs, a similar general procedure was followed with an addition of the incoming monomer after full or nearly full consumption of the previous monomer (as monitored by ¹H NMR).

Acknowledgments

We thank Dr. Lydia BreLOT and Corinne Bailly for X-Ray diffraction studies. We are also grateful to the *Fundação para a Ciência e Tecnologia* (FCT), Portugal for funding project PTDC/QUI-QUI/099873/2008 and fellowships SFRH/BPD/73253/2010 (C.F.) and SFRH/BPD/44262/2008 (V.R.). The University of Strasbourg and the CNRS are gratefully acknowledged for financial support.

Supporting Information

NMR data of all Zn complexes, DOSY measurements details for compounds **3**, **5**, **6**, **7** and **8**, optimized geometries (Chem 3D) and associated parameters for complexes **6** and **8** are provided in the ESI. SEC traces, MALDI-TOF spectra of polymers, selected ROP kinetic data, ¹H NMR spectra of selected isolated polymers and a summary of crystallographic data for compounds **2H**, **3**, **6'** and **7** are also provided in the ESI. The crystal data of compounds **2H**, **3**, **6'** and **7** can be obtained free of charge from the Cambridge Crystallographic Data Centre, 12 Union Road, Cambridge CB2 1EZ (fax: +44-1223-336-033; e-mail: deposit@ccdc.cam.ac.uk), reference numbers CCDC-1046464-1046467.

References

1. (a) M. S. Lindblad, Y. Liu, A.-C. Albertsson, E. Ranucci and S. Karlsson, *Adv. Polym. Sci.* 2002, **157**, 139; (b) M. Vert, *Biomacromolecules* 2005, **6**, 538; (c) L. S. Nair and C. T. Laurencin, *Prog. Polym. Sci.* 2007, **32**, 762; (d) E. S. Place, J. H. Georges, C. K. Williams and M. M. Stevens, *Chem. Soc. Rev.* 2009, **38**, 1139.
2. Selected reviews: (a) B. J. O'Keefe, M. A. Hillmeyer and W. B. Tolman, *J. Chem. Soc., Dalton Trans.* 2001, 2215; (b) O. Dechy-Cabaret, B. Martin-Vaca and D. Bourissou, *Chem. Rev.* 2004, **104**, 6147; (c) J. Wu, T.-L. Yu, C.-T. Chen and C.-C. Lin, *Coord. Chem. Rev.* 2006, **205**, 602; (d) A. P. Dove, *Chem. Commun.* 2008, 6446; (e) R. H. Platel, L. M. Hodgson and C. K. Williams, *Polym. Rev.* 2008, **48**, 11; (f) C. A. Wheaton, P. G. Hayes and B. J. Ireland, *Dalton Trans* 2009, 4832; (g) A. Arbaoui and C. Redshaw, *Polym. Chem.* 2010, **1**, 801; (i) J.-C. Buffet and J. Okuda, *Polym. Chem.* 2011, **2**, 2758; (j) A. Sauer, A. Kapelski, C. Fliedel, S. Dagorne, M. Kol and J. Okuda, *Dalton. Trans.* 2013, **42**, 9007; (k) S. Dagorne, M. Normand, E. Kirillov and J.-F. Carpentier, *Coord. Chem. Rev.* 2013, **257**, 1869.
3. (a) P. R. Gruber, E. S. Hall, J. J. Kolstad, M. L. Iwen, R. D. Benson and R. L. Borchardt (Cargill Incorporated) US Patent, 5 258 488, 1993; (b) P. R. Gruber, J. J. Kolstad, E. S. Hall, R. S. Eichen Conn and C. M. Ryan (Cargill Incorporated) US Patent, 6 143 863, 2000.
4. For recent and representative examples of metal-mediated ROPs of cyclic esters/carbonates, see : (a) A. Pilone, K. Press, I. Goldberg, M. Kol, M. Mazzeo and M. Lamberti, *J. Am. Chem. Soc.* 2014, **136**, 2940; (b) A. Meduri, T. Fuoco, M. Lamberti, C. Pellechia and D. Pappalardo, *Macromolecules* 2014, **47**, 534; (c) M. D. Jones, S. L. Hancock, P. McKeown, P. Schäfer, A. Buchard, L. H. Thomas, M. F. Mahon and J. P. Lowe, *Chem. Commun.* 2014, **50**, 15967; (d) N. Maudoux, T. Roisnel, J.-F. Carpentier and Y. Sarazin, *Organometallics* 2014, **33**, 5630; (e) J. S. Klitzke, T. Roisnel, E. Kirillov, O. de L. Casagrande Jr. and J.-F. Carpentier, *Organometallics* 2014, **33**, 5693; (f) Y. Huang, W. Wang, C.-C. Lin, M. P. Blake, L. Clark, A. D. Schwarz and P. Mountford, *Dalton Trans.*, 2013, **42**, 9313; (g) R. A. Collins, J. Unruangsri, P. Mountford, *Dalton Trans.*, 2013, **42**, 759; (h) R. L. Webster,

- N. Noroozi, S. G. Hatzikiriakos, J. A. Thomson and L. L. Schafer, *Chem. Commun.* 2013, **49**, 57; (i) F. Hild, N. Neehaul, F. Bier, M. Wirsum, C. Gourlaouen and S. Dagorne, *Organometallics* 2013, **32**, 587; (j) C. Bakewell, A. J. White, N. J. Long and C. K. Williams, *Inorg. Chem.* 2013, **52**, 12561; (k) V. Balasanthiran, M. H. Chisholm, C. B. Durr and J. C. Gallucci, *Dalton Trans.* 2013, **42**, 11234; (l) I. Yu, A. Acosta-Ramirez and P. Mehrkhodavanti, *J. Am. Chem. Soc.* 2012, **134**, 2057; (m) C. Bakewell, T.-P.-A. Cao, N. Long, X. F. Le Goff, A. Auffrant and C. K. Williams, *J. Am. Chem. Soc.* 2012, **134**, 2057; (n) P. Horeglad, G. Szczepaniak, M. Dranka and J. Zachara, *Chem. Commun.* 2012, **48**, 1171; (o) C. Romain, B. Heinrich, S. Bellemin-Laponnaz and S. Dagorne, *Chem. Commun.* 2012, **48**, 2213; (p) L. Azor, C. Bailly, L. Brelot, M. Henry, P. Mobian and S. Dagorne, *Inorg. Chem.* 2012, **51**, 10876; (q) E. L. Whitelaw, G. Loraine, M. F. Mahon and M. D. Jones, *Dalton Trans.* 2011, **40**, 11469; (r) C. Y. Li, C. Y. Tsai, C. H. Lin and B. T. Ko, *Dalton Trans.* 2011, **40**, 1880; (s) A. Otero, A. Lara-Sánchez, J. Fernández-Baeza, C. Alonso-Moreno, J. A. Castro-Osma, I. Márquez-Segovia, L. F. Sánchez-Barba, A. M. Rodríguez and J. C. Garcia-Martinez, *Organometallics* 2011, **30**, 1507; (t) D. J. Darensbourg, O. Karroonnirun and S. J. Wilson, *Inorg. Chem.* 2011, **50**, 6775; (u) M. P. Blake, A. D. Schwarz and P. Mountford, *Organometallics* 2011, **30**, 1202; (v) W.-H. Sun, M. Shen, W. Zhang, W. Huang, S. Liu and C. Redshaw, *Dalton Trans.* 2011, **40**, 2645; (w) M. Shen, W. Huang, W. Zhang, X. Hao, W.-H. Sun and C. Redshaw, *Dalton Trans.* 2010, **39**, 9912; (x) M. Bouyahyi, T. Roisnel and J.-F. Carpentier, *Organometallics* 2010, **29**, 491; (y) F. Hild, P. Haquette, L. Brelot and S. Dagorne, *Dalton Trans.* 2010, **39**, 533; (z) A. D. Schwarz, Z. Y. Chu and P. Mountford, *Organometallics* 2010, **29**, 1246.
5. (a) D. C. H. Oakes, B. S. Kimberley, V. C. Gibson, D. J. Jones, A. J. P. White and D. J. Williams, *Chem. Commun.* 2004, 2174; (b) L. Lavanant, A. Silvestru, A. Faucheux, L. Toupet, R. F. Jordan and J.-F. Carpentier, *Organometallics* 2005, **24**, 5604; (c) C. Wang, Z. Ma, X.-L. Sun, Y. Gao, Y.-H. Guo, Y. Tang and L.-P. Shi, *Organometallics* 2006, **25**, 3259; (d) R. J. Long, V. C. Gibson and A. J. P. White, *Organometallics* 2008, **27**, 235.
6. (a) M. Haddad, M. Laghzaoui, R. Welter and S. Dagorne, *Organometallics* 2009, **28**, 4584; (b) M. Lamberti, I. D'Auria, M. Mazzeo, S. Milione, V. Bertolasi and D.

-
- Pappalardo, *Organometallics* 2012, **31**, 5551; (c) A. Pilone, M. Lamberti, M. Mazzeo, S. Milione and C. Pellechia, *Dalton Trans.* 2013, **42**, 13036.
7. For a recent overview on the use of Al(III) species in the ROP of cyclic polar monomers, see: S. Dagorne and C. Fliedel, *Top. Organomet. Chem.* 2013, **41**, 125.
 8. For recent examples of Zn(II) complexes for the controlled ROP cyclic esters/carbonates, see: (a) Z. M. Bo, M. Wang, H. Xie, P. Li, L. Li, S. Li and D. Cui, *Chem. Commun.* 2014, **50**, 11411; (b) C. Fliedel, D. Vila-Viçosa, M. J. Calhorda, S. Dagorne and T. Avilés, *ChemCatChem.* 2014, **6**, 1357; (c) C. Fliedel, S. Mameri, S. Dagorne and T. Avilés, *Appl. Organometal. Chem.* 2014, **28**, 504; (d) H. Wang and H. Ma, *Chem. Commun.* 2013, **49**, 8686; (e) G. Schnee, C. Fliedel, T. Avilés and S. Dagorne, *Eur. J. Inorg. Chem.* **2013**, 3699; (f) C. Romain, V. Rosa, C. Fliedel, F. Bier, F. Hild, R. Welter, S. Dagorne and T. Avilés, *Dalton Trans.* 2012, **41**, 3377; (g) V. Poirier, T. Roisnel, J.-F. Carpentier and Y. Sarazin, *Dalton Trans.* 2011, **40**, 523.
 9. (a) I. D'Auria, M. Lamberti, M. Mazzeo, S. Milione, G. Roviello and C. Pellechia, *Chem. Eur. J.* 2012, **18**, 2349; (b) L.-C. Liang, W.-Y. Lee, T.-L. Tsai, Y.-L. Hsu and T.-Y. Lee, *Dalton Trans.* 2010, **39**, 8748.
 10. Selected examples: (a) P. Tao, H.-L. Mu, J.-Y. Liu and Y.-S. Li, *Organometallics*, 2013, **32**, 4805; (b) R. J. Long, V. C. Gibson, A. J. P. White and D. J. Williams, *Inorg. Chem.* 2006, **45**, 511; (c) J. Heinicke, M. He, A. Dal, H.-F. Klein, O. Hetche, W. Keim, U. Flörke and H. J. Haupt, *Eur. J. Inorg. Chem.* 2000, 431; (d) J. Pietsch, P. Braunstein and Y. Chauvin, *New J. Chem.* 1998, 467; (e) W. Keim, *Angew. Chem. Int. Ed. Engl.* 1990, **29**, 235.
 11. (a) T. B. Rauchfuss, *Inorg. Chem.* 1977, **16**, 2966; (b) C. A. Willoughby, R. R. Duff, Jr., W. M. Davis and S. L. Buchwald, *Organometallics* 1996, **15**, 472.
 12. (a) J. Heinicke, R. Kadyrov, M. K. Kindermann, M. Koesling and P. G. Jones, *Chem. Berich.* 1996, **129**, 1547; (b) D. J. Jones, V. C. Gibson, S. M. Green, P. J. Maddox, A. J. P. White and D. J. Williams, *J. Am. Chem. Soc.* 2005, **127**, 11037.

13. N. Giuseppone, J.-L. Schmitt, L. Allouche and J.-M. Lehn, *Angew. Chem., Int. Ed.* 2008, **47**, 2235.
14. For other XRD-established molecular structures of phosphine-stabilized zinc alkyl complexes, see: (a) E. E. Wilson, A. G. Oliver, R. P. Hughes and B. L. Ashfeld, *Organometallics*, 2011, **30**, 5214-5221; (b) A. Murso and D. Stalke, *Dalton Trans.*, 2004, 2563; (c) L.-C. Liang, W.-Y. Lee and C.-H. Hung, *Inorg. Chem.*, 2003, **42**, 5471; (d) J. Dekker, J. W. Munninghoff, J. Boersma and A. L. Spek, *Organometallics*, 1987, **6**, 1236.
15. For well-characterized Zn-OR aggregates, see, for instance : Q. Li, K. Nie, B. Xu, Y. Yao, Y. Zhang and Q. Shen, *Polyhedron*, 2012, **31**, 58) et (M. A. Dreher, M. Krumm, C. Lizandara-Pueyo and S. Polarz, *Dalton Trans.*, 2010, **39**, 2232.
16. For representative solid state structures of Zn species bearing a Zn-O dative bond, see: (a) A. Ozarowski, H. M. Lee and A. Balch, *J. Am. Chem. Soc.* 2003, **125**, 12606; (b) S. Aboukacem, W. Tyrra and I. Pantenburg, *Z. Anorg. Allg. Chem.*, 2003, **629**, 1569; (c) D. Wang, K. Wurst and M. R. Buchmeiser, *J. Organomet. Chem.* 2004, **689**, 2123; (d) Q. Li, K. Nie, B. Xu, Y. Yao, Y. Zhang and Q. Shen, *Polyhedron* 2010, **31**, 58.
17. For structures of phosphine-stabilized Zn(II) inorganic species, see: (a) L.-C. Liang, H.-Y. Shih, H.-S. Chen and S.-T. Lin, *Eur. J. Inorg. Chem.*, 2012, 298-305; (b) A. Krezel, R. Latajka, G. D. Bujacz and W. Bal, *Inorg. Chem.*, 2003, **42**, 1994; (c) D. J. Darensbourg, M. S. Zimmer, P. Rainey and D. L. Larkins, *Inorg. Chem.* 2000, **39**, 1578; (d) D. J. Darensbourg, J. R. Wildeson, J. C. Yarbrough and J. H. Reibenspies, *J. Am. Chem. Soc.* 2000, **122**, 12487; (e) D. J. Darensbourg, M. S. Zimmer, P. Rainey and D. L. Larkins, *Inorg. Chem.* 1998, **37**, 2852; (f) D. Weiß, A. Schier and H. Schmidbaur, *Z. Naturforsch., B: Chem. Sci.* 1998, **53**, 1307; (g) J. Podlahova, B. Kratochvil and J. Podlaha, *J. Chem. Soc., Dalton Trans.*, 1985, 2393.
18. T. Endo, General Mechanisms in Ring-Opening Polymerization. In *Handbook of Ring-Opening Polymerization*; P. Dubois, O. Coulembier, J.-M. Raquez, Eds.; Wiley-VCH Verlag GmbH & Co. KGaA: Weinheim, 2009, pp 53-64.

-
19. For reviews on immortal metal-catalyzed ROP of cyclic esters and carbonates, see: (a) T. Aida and S. Inoue, *Acc. Chem. Res.* 1996, **29**, 39; (b) N. Ajellal, J.-F. Carpentier, C. Guillaume, S. M. Guillaume, M. Helou, V. Poirier, Y. Sarazin and A. Trifonov, *Dalton Trans.* 2010, **39**, 8363.
20. For selected recent examples, see refs 4i and 8c and: (a) B. Liu, T. Roisnel, L. Maron, J.-F. Carpentier and Y. Sarazin, *Chem. Eur. J.* 2013, **19**, 3986; (b) F. Hild, L. Brelot and S. Dagorne, *Organometallics* 2011, **30**, 5457.
21. (a) I. Barakat, P. Dubois and P. Teyssié, *J. Polym. Sci. Part A: Polym Chem.* 1993, **31**, 505; (b) D. Delcroix, B. Martin-Vaca, D. Bourissou and C. Navarro, *Macromolecules* 2010, **43**, 8828.
22. (a) A. P. Pêgo, A. A. Poot, D. W. Grijpma and J. Feijen, *J. Control. Release* 2003, **87**, 69; (b) T. Tyson, A. Finne-Wistrand and A.-C. Albertsson, *Biomacromolecules* 2009, **10**, 149; (c) Z. Zhang, D. W. Grijpma and J. Feijen, *J. Control. Release* 2006, **112**, 57.
23. See, for instance: (a) H. R. Kricheldorf, K. Bornhorst and H. Hachmann-Thiessen, *Macromolecules* 2005, **38**, 5017; (b) F. Stassin and R. Jérôme, *J. Polym. Sci., Part A: Polym. Chem.* 2005, **43**, 2777; (c) D. Pappalardo, L. Annunziata and C. Pellecchia, *Macromolecules* 2009, **42**, 6056.
24. E. Piedra-Arroni, A. Amgoune and D. Bourissou, *Dalton Trans.* 2013, **42**, 9024.