

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).


Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/dalton

Graphical abstract

Thermal decomposition of $\text{MB}_{12}\text{H}_{12}$ ($\text{M}=\text{Mg}, \text{Ca}$) forms H-deficient monomers $\text{MB}_{12}\text{H}_{12-x}$ containing icosahedral B_{12} skeletons and followed by the formation of $(\text{MB}_y\text{H}_z)_n$ polymers.

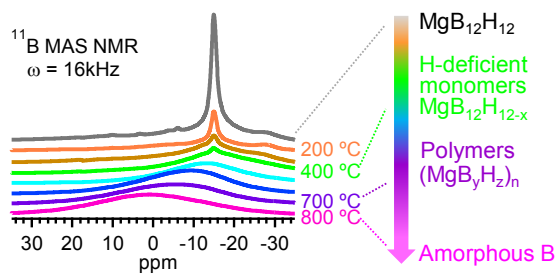



Facile Synthesis of Anhydrous Alkaline Earth Metal Dodecaborate $\text{MB}_{12}\text{H}_{12}$ ($\text{M} = \text{Mg}, \text{Ca}$) from $\text{M}(\text{BH}_4)_2$

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Liqing He,^a Hai-Wen Li,^{*b,c} Nikolay Tumanov,^d Yaroslav Filinchuk,^d Etsuo Akiba^{a,b,c}

Metal dodecaborate $\text{M}_{2/n}\text{B}_{12}\text{H}_{12}$ is one of the dehydrogenation intermediates of metal borohydride $\text{M}(\text{BH}_4)_n$ with a high hydrogen density of approximately 10 mass%, the latter is a potential hydrogen storage material. It is therefore in great need to synthesize anhydrous $\text{M}_{2/n}\text{B}_{12}\text{H}_{12}$ in order to investigate the thermal decomposition of $\text{M}_{2/n}\text{B}_{12}\text{H}_{12}$ and to understand its role in the dehydrogenation and rehydrogenation of $\text{M}(\text{BH}_4)_n$. In this work, anhydrous alkaline earth metal dodecaborates $\text{MB}_{12}\text{H}_{12}$ ($\text{M} = \text{Mg}, \text{Ca}$) have been successfully synthesized by sintering of $\text{M}(\text{BH}_4)_2$ ($\text{M} = \text{Mg}, \text{Ca}$) and $\text{B}_{10}\text{H}_{14}$ with stoichiometric molar ratio of 1:1. Thermal decomposition of $\text{MB}_{12}\text{H}_{12}$ shows multistep pathways with the formation of H-deficient monomers $\text{MB}_{12}\text{H}_{12-x}$ containing icosahedral B_{12} skeletons and followed by the formation of $(\text{MB}_x\text{H}_y)_n$ polymers. Comparison on the thermal decomposition of $\text{MB}_{12}\text{H}_{12}$ and $\text{M}(\text{BH}_4)_2$ suggests that different behaviours of the anhydrous $\text{MB}_{12}\text{H}_{12}$ and those formed from the decomposition of $\text{M}(\text{BH}_4)_n$.

Introduction

Hydrogen, known as an environment-friendly energy carrier, can be stored in chemical materials in the form of hydrides. Among various kinds of hydrides, borohydrides with high volumetric and gravimetric hydrogen densities such as LiBH_4 (H capacity: 18.5 mass% and 122 kg H_2/m^3), $\text{Mg}(\text{BH}_4)_2$ (14.9 mass% and 147 kg H_2/m^3) and $\text{Ca}(\text{BH}_4)_2$ (11.6 mass% and 124 kg H_2/m^3), have been considered as potential hydrogen storage materials.¹⁻⁴ Most of borohydrides show a stepwise decomposition accompanied with a formation of intermediates containing polyanions, such as $[\text{B}_2\text{H}_6]^{2-}$, $[\text{B}_3\text{H}_8]^-$ and/or $[\text{B}_{12}\text{H}_{12}]^{2-}$. The decomposition mechanism significantly depends on the dehydrogenation temperature and hydrogen backpressure as well as the particle size of borohydrides.⁵⁻¹⁷ The intermediates containing small clusters like $[\text{B}_2\text{H}_6]^{2-}$ and $[\text{B}_3\text{H}_8]^-$ were found to be beneficial for the rehydrogenation to the corresponding borohydrides.^{13, 16, 18} The $[\text{B}_{12}\text{H}_{12}]^{2-}$ intermediate, despite its formation is still controversial, having strong B-B bonds in a stable icosahedral boron cage, has been widely regarded as an obstacle for the rehydrogenation to $\text{M}(\text{BH}_4)_n$.^{7, 10, 19-21} Fundamental investigation on the thermal

decomposition of metal dodecaborate $\text{M}_{2/n}\text{B}_{12}\text{H}_{12}$, therefore, is in great need to elucidate its role in the dehydrogenation and rehydrogenation of borohydrides.

$\text{M}_{2/n}\text{B}_{12}\text{H}_{12}$ is generally synthesized using wet chemistry processes, followed by a careful dehydration under vacuum slightly above 120 °C.^{22, 23} Higher temperatures cause the hydrolysis, and lower do not allow to remove water completely, thus failing in synthesizing some anhydrous alkaline earth metal dodecaborates such as $\text{MgB}_{12}\text{H}_{12}$.²⁴ Under such condition, we have recently developed a novel solvent-free synthesis method, i.e. sintering of $\text{M}(\text{BH}_4)_n$ with $\text{B}_{10}\text{H}_{14}$, by which high purity anhydrous alkali metal dodecaborates $\text{M}_2\text{B}_{12}\text{H}_{12}$ ($\text{M} = \text{Li}, \text{Na}, \text{K}$) have been successfully synthesized.²⁵

In this work, we have applied our recently developed sintering process to the syntheses of anhydrous alkaline earth metal dodecaborates $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$. Anhydrous $\text{MB}_{12}\text{H}_{12}$ have been successfully synthesized by sintering of $\text{M}(\text{BH}_4)_2$ and $\text{Ca}(\text{BH}_4)_2$ with $\text{B}_{10}\text{H}_{14}$, based on the equation (1): $\text{M}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14} \rightarrow \text{MB}_{12}\text{H}_{12} + 5\text{H}_2$ ($\text{M} = \text{Mg}, \text{Ca}$) (1) Thermal decomposition behaviours of the thus synthesized anhydrous $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ were carefully investigated using thermogravimetry (TG), mass spectrometry (MS), X-ray diffraction (XRD), Raman spectra and solid-state magic angle spinning (MAS) nuclear magnetic resonance (NMR) spectra. Furthermore, the decomposition processes of $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ are compared with those for products formed during the dehydrogenation of $\text{Mg}(\text{BH}_4)_2$ and $\text{Ca}(\text{BH}_4)_2$, in order to elucidate their roles in the dehydrogenation of borohydrides.

Experimental

Commercial $\text{B}_{10}\text{H}_{14}$ (99%, Wako), $\gamma\text{-Mg}(\text{BH}_4)_2$ (95%, Aldrich) and $\text{Ca}(\text{BH}_4)_2$ (95%, Aldrich) were all stored in a glove box under Ar

^a Department of Mechanical Engineering, Faculty of Engineering, Kyushu University, Fukuoka 819-0395, Japan.

^b International Research Center for Hydrogen Energy, Kyushu University, Fukuoka 819-0395, Japan. E-mail: li.haiwen.305@m.kyushu-u.ac.jp. Tel.: +81-92-802-3226. Fax: +81-92-802-3235.

^c WPI International Institute for Carbon-Neutral Energy Research (WPI-I2CNER), Kyushu University, Fukuoka 819-0395, Japan.

^d Institute of Condensed Matter and Nanosciences, Université catholique de Louvain, Louvain-la-Neuve 1348, Belgium.

† Electronic Supplementary Information (ESI) available: MS spectra of $\text{Mg}(\text{BH}_4)_2$, XRD patterns and Raman spectra of $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ heated to respective temperatures. See DOI: 10.1039/x0xx00000x

gas and used without further purification. Starting materials of $\text{Mg}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ and $\text{Ca}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ were firstly mechanically milled at room temperature using a planetary ball mill (Fritsch P-7) with 10 steel balls (7 mm in diameter) in a hardened steel vial (30 cm³ in volume) under 0.1 MPa Ar for 5 h (15 min milling, 5 min pausing). Subsequently, the ball milled samples of $\text{Mg}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ and $\text{Ca}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ were sealed into stainless steel crucibles for sintering at 300 °C for 1 h and at 380 °C for 2 h, respectively.

Powder XRD patterns were recorded by Rigaku Ultima IV X-ray diffractometer with Cu-K α radiation, and the accelerating voltage/ tube current were set as 40 kV/ 40 mA. The sample powders were placed on a glass plate sealed by Scotch tape to prevent exposure to air during the measurement. Powder XRD patterns of the as-synthesized $\text{MgB}_{12}\text{H}_{12}$ were measured in a glass capillary, on MAR345 diffractometer, with Mo K α rotating anode generator and a focusing mirror. The synchrotron radiation powder XRD pattern for the as-synthesized $\text{CaB}_{12}\text{H}_{12}$ was measured on the Materials Science Beamline X04SA at the Swiss Light Source (transmission geometry in capillary, MYTHEN detector, $\lambda = 1.00117$ Å). A variable temperature experiment on the sample of $\text{CaB}_{12}\text{H}_{12}$ was carried out at the Materials Science Beamline X04SA, SLS, using the wavelength of 0.77619 Å. The sample was loaded in a glass capillary, and was heated in 20 °C steps from room temperature to 400 °C, and then cooled down to the ambient temperature. A number of diffraction patterns was collected at each temperature point to follow both time and temperature dependences of the transformations.

Raman spectra were obtained from RAMAN-11 VIS-SS (Nanophoton) using a green laser with 532 nm wavelength. Thermal decomposition was examined by TG with a heating rate of 5 °C/min under a 200 ml/min flow of He gas. The gas released during TG measurement was analysed by quadrupole mass spectrometer coupled with TG. Solid-state MAS NMR spectra were recorded using a Bruker Ascend-600 spectrometer at room temperature. NMR sample preparations were always done in a glove box filled with purified Ar gas and dry N₂ gas was used for sample spinning. ¹¹B MAS NMR spectra were obtained at excitation pulses of 6.5 μs ($\pi/2$ pulse) and with strong ¹H decoupling pulses. ¹¹B NMR chemical shifts were referenced to BF_3OEt_2 ($\delta = 0.00$ ppm).

Results and discussion

1. Synthesis of anhydrous $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$

Figure 1 shows XRD pattern and Raman spectra of $\text{Mg}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ after sintering at 300 °C for 1 h. The observed broad peak between $2\theta = 3^\circ$ and 15° (between $2\theta = 10^\circ$ and 18° using Cu-K α radiation as shown in Figure S1) is distinct from the starting materials of $\text{Mg}(\text{BH}_4)_2$ and $\text{B}_{10}\text{H}_{14}$, as well as the amorphous $\text{Mg}(\text{BH}_4)_2$,²⁶ and could be ascribed to the formation of amorphous $\text{MgB}_{12}\text{H}_{12}$ theoretically predicted by First-principle Calculations.²⁷ In the Raman spectra, two peaks ascribed to B-H bending and stretching vibrations of $[\text{B}_{12}\text{H}_{12}]^{2-}$ are observed at 751 and 2569 cm⁻¹, respectively, together with

the high level of baseline due to the fluorescent effect. Furthermore, no trace of O-H bond of water is observed in the Raman spectra, which proves the successful synthesis of the anhydrous $\text{MgB}_{12}\text{H}_{12}$.

Anhydrous $\text{CaB}_{12}\text{H}_{12}$ is also synthesized by sintering of $\text{Ca}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ at 380 °C for 2 h, its XRD and Raman data are shown in Figure 2. Three representative diffraction peaks at $2\theta = 9.3^\circ$, 9.5° and 10.5° originating from $\text{CaB}_{12}\text{H}_{12}$ with a monoclinic (C2/c) crystal structure,²⁸ are clearly observed in the XRD patterns. An impurity with an unknown structure was indexed in the orthorhombic crystal system ($a = 13.580(2)$, $b = 12.264(1)$, $c = 4.2495(4)$ Å) and our preliminary analysis suggests space group symmetry *Pcab* or *Pbab*. Our in-situ diffraction experiments show that the second crystalline phase disappears from the diffraction pattern after heating to 400 °C, see Figure 2c. In Raman spectra, vibration peaks assigned to B-H bending and stretching modes of $[\text{B}_{12}\text{H}_{12}]^{2-}$ are observed at 585, 751 and 2485, 2547 cm⁻¹, respectively.²⁹ No O-H vibration peak of water is detected in Raman spectra, which indicates the successful synthesis of the anhydrous $\text{CaB}_{12}\text{H}_{12}$.

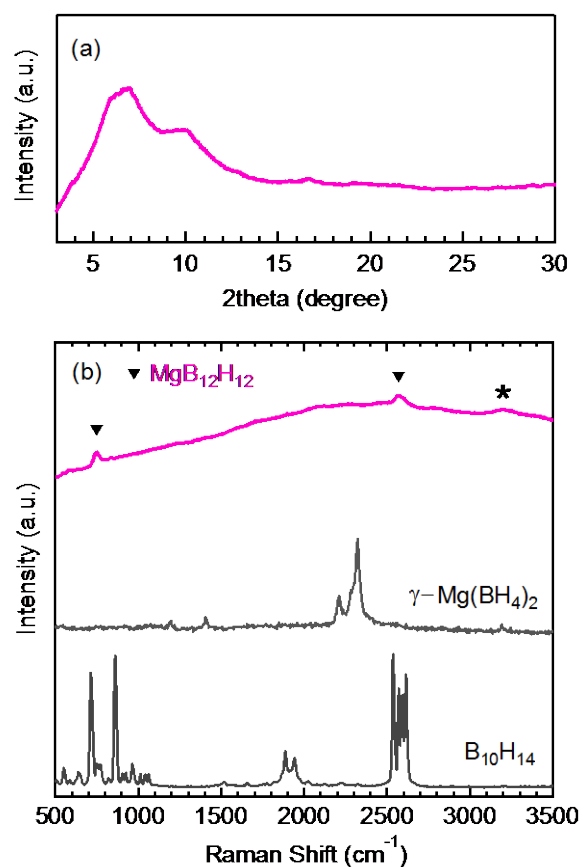


Figure 1. (a) XRD pattern (Mo K α) and (b) Raman spectra of 5 h ball milled $\text{Mg}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ followed by sintering at 300 °C for 1 h. Starting materials of $\text{Mg}(\text{BH}_4)_2$ and $\text{B}_{10}\text{H}_{14}$ are also shown as references, asterisk indicates the systematic error.

The successful syntheses of the anhydrous $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ are further proved by solid state ^{11}B MAS NMR spectra, shown in Figure 3. The main resonances at -15.0 and -14.0 ppm are assigned to $[\text{B}_{12}\text{H}_{12}]^{2-}$ in $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$, respectively.²⁸ $[\text{B}_{10}\text{H}_{10}]^{2-}$ (-28.3 ppm for Mg, -26.3 ppm for Ca),⁸ 30 $[\text{BH}_4]^-$ (-41.9 ppm for Mg, -32.2 ppm for Ca)²⁷ and unknown phases (-6.0 and -46.3 ppm) are detected in the synthesized $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ samples as impurities. In addition, the synthesized anhydrous $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ samples display homogenous yellow color, which is different from the white starting materials. All the above mentioned results, therefore, consistently indicate that sintering of metal borohydrides $\text{M}(\text{BH}_4)_2$ with $\text{B}_{10}\text{H}_{14}$ is a facile method to synthesize anhydrous alkaline earth metal dodecaborates.

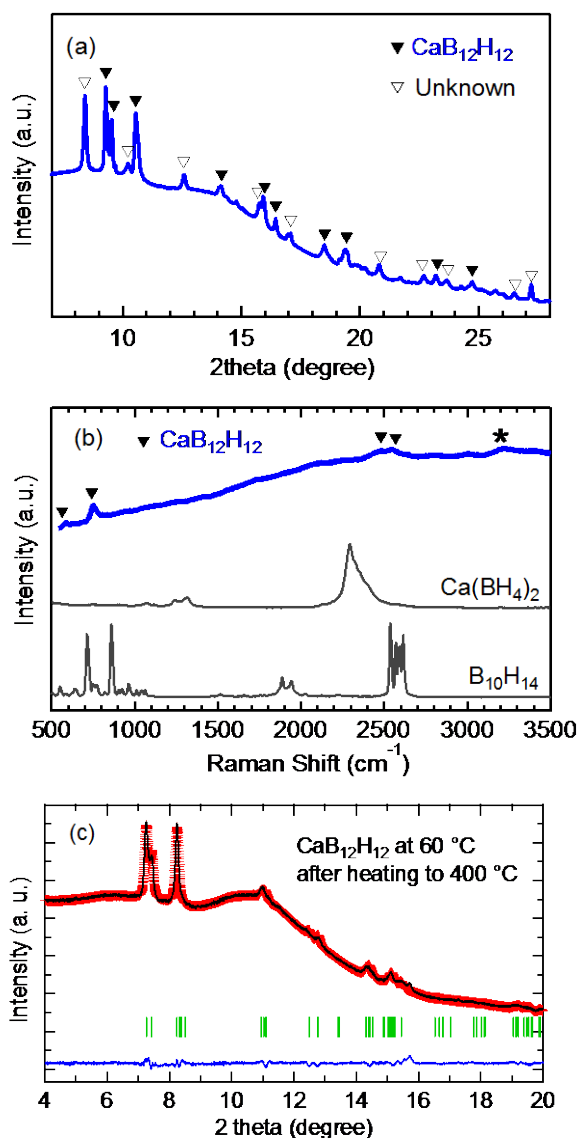


Figure 2. (a) Synchrotron XRD ($\lambda = 1.00117 \text{ \AA}$) pattern and (b) Raman spectra of 5 h ball milled $\text{Ca}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ followed by sintering at 380 °C for 2 h. Asterisk indicates the systematic error. (c) Rietveld refinement plot for $\text{CaB}_{12}\text{H}_{12}$ at 60 °C after heating to 400 °C. Red crosses and black line show the experimental and calculated data, respectively. Blue line is the difference profile, and green marks indicate Bragg positions of $\text{CaB}_{12}\text{H}_{12}$.

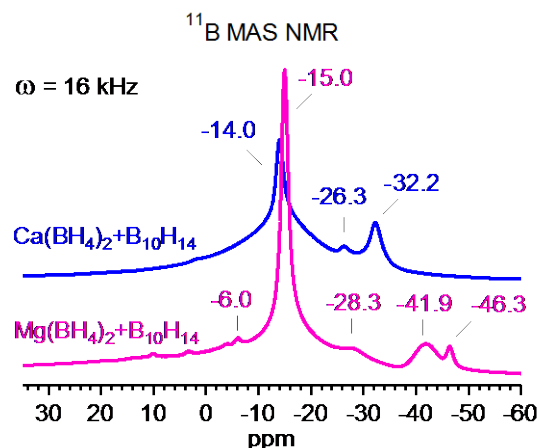


Figure 3. ^{11}B MAS NMR spectra of synthesized samples from $\text{M}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ (M = Mg: 5 h ball milling followed by sintering at 300 °C for 1 h; M = Ca: 5 h ball milling followed by sintering at 380 °C for 2 h).

2. Thermal decomposition of anhydrous $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$

(1) $\text{MgB}_{12}\text{H}_{12}$

Thermal decomposition behaviour of the anhydrous $\text{MgB}_{12}\text{H}_{12}$ examined by TG and MS are shown in Figure 4. Only hydrogen is detected by MS, indicating the weight loss upon heating is originated from the dehydrogenation of $\text{MgB}_{12}\text{H}_{12}$. The dehydrogenation starts at approximately 190 °C, reaching 5.6 mass% or approximately 77% of the theoretical hydrogen content in $\text{MgB}_{12}\text{H}_{12}$ when heated up to 800 °C. The decomposition pathway is multistep, as shown in TG and MS results.

In order to elucidate the decomposition pathway of anhydrous $\text{MgB}_{12}\text{H}_{12}$, the sample was heated to fixed temperatures and subsequently cooled down to room temperature, and the changes were followed systematically by XRD, Raman and solid state ^{11}B NMR. The results are shown in Figure S1 and Figure 5, respectively. When the temperature is increased up to 200 °C, the main resonance at -15.0 ppm attributed to $\text{MgB}_{12}\text{H}_{12}$ becomes weak, while the peak intensity for $\text{Mg}(\text{BH}_4)_2$ and $\text{MgB}_{10}\text{H}_{10}$ impurities do not change obviously. This indicates that the decomposition of $\text{MgB}_{12}\text{H}_{12}$ starts at 190 °C, prior to that of $\text{Mg}(\text{BH}_4)_2$ as shown in Figure S2. When the temperature is increased up to 400 °C, the broad diffraction peak between $2\theta = 10^\circ$ and 18° disappears, and the B-H stretching mode of $\text{MgB}_{12}\text{H}_{12}$ at 2569 cm^{-1} becomes almost invisible, the main resonance of $\text{MgB}_{12}\text{H}_{12}$ at -15.0 ppm reduces significantly without any change in the chemical shift, which consistently indicate that a major part of B-H bond in the icosahedral $[\text{B}_{12}\text{H}_{12}]^{2-}$ has been broken to release hydrogen. The released amount reaches 2.1 mass% at 400 °C, suggesting that the decomposition product is probably H-deficient $\text{MgB}_{12}\text{H}_{12-x}$ ($x = 3.5$) that keeps the icosahedral B_{12} skeletons.¹² When the temperature is further increased to 500, 600 and 700 °C, the released amount of hydrogen reaches 3.2, 3.8 and 4.6 mass% and the major resonance of $[\text{B}_{12}\text{H}_{12}]^{2-}$ at -15.0 ppm shifts to -13.1, -9.4 and -5.6 ppm. It suggests that $\text{MgB}_{12}\text{H}_{12-x}$ continuously releases hydrogen accompanied with the

polymerization of the icosahedral B_{12} skeletons and the formation of $(MgB_yH_z)_n$ polymers,^{31, 32} insoluble in water and DMSO. When the sample is heated up to 800 °C, the major resonance shifts to 0.9 ppm, indicating the formation of amorphous boron at 800 °C. The temperature is higher than that (600 °C) reported for $MgB_{12}H_{12}$ /Carbon nanocomposite,³³ suggesting that the carbon nanocomposite may contribute to the reduction of the decomposition temperature.

Based on the abovementioned experimental results, thermal decomposition pathway of anhydrous $MgB_{12}H_{12}$ could be briefly summarized as the following steps:

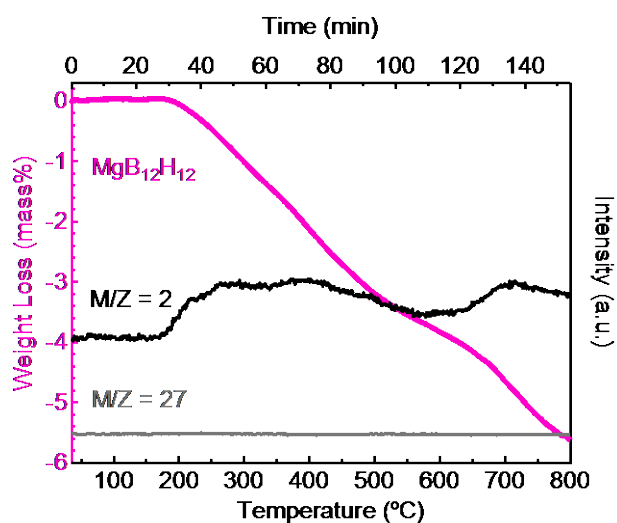





Figure 4. TG curve and MS signals of the synthesized $MgB_{12}H_{12}$ (mass numbers of 2 and 27 represent H_2 and B_2H_6).

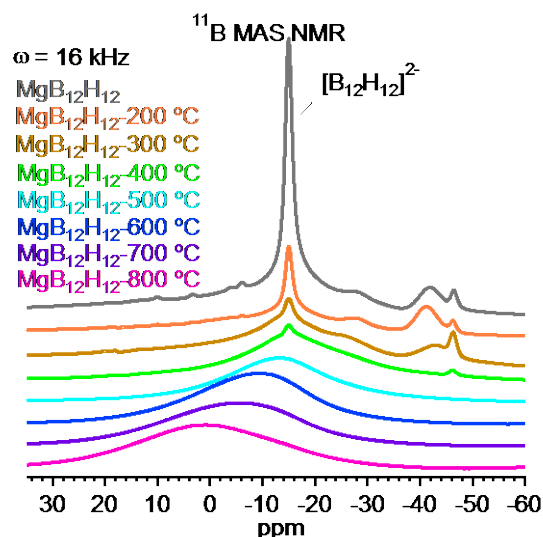


Figure 5. ^{11}B MAS NMR spectra of $MgB_{12}H_{12}$ as synthesized and heated up to respective temperatures.

It is worth emphasizing that the thermal decomposition behaviour of the synthesized $MgB_{12}H_{12}$ is fairly different from that formed during the dehydrogenation of $Mg(BH_4)_2$. The synthesized $MgB_{12}H_{12}$ exhibits a lower decomposition onset temperature and a wider decomposition temperature range of 190 ~ 800 °C than $Mg(BH_4)_2$. Also, the synthesized $MgB_{12}H_{12}$ decomposes into amorphous boron rather than MgB_2 formed as the decomposition product from $Mg(BH_4)_2$ at 600 °C.³⁴ Taking into account the controversial discussions about the formation of $MgB_{12}H_{12}$ during the dehydrogenation of $Mg(BH_4)_2$, those differences may result from the following two possibilities: a) the concurrent formation of MgH_2 and $MgB_{12}H_{12}$ during the dehydrogenation of $Mg(BH_4)_2$, since MgH_2 facilitates the formation of MgB_2 from $MgB_{12}H_{12}$ as predicted by First-principles calculations;⁹ b) $MgB_{12}H_{12}$ does not form as a stable dehydrogenation intermediate of $Mg(BH_4)_2$ as reported recently.¹⁴

(2) $CaB_{12}H_{12}$

Thermal decomposition behaviour of anhydrous $CaB_{12}H_{12}$ is systematically studied and the TG and MS results are shown in Figure 6. Only hydrogen is detected by MS, indicating the weight loss upon heating comes from the dehydrogenation of $CaB_{12}H_{12}$. The dehydrogenation starts at ca. 320 °C and reaches 2.5 mass% (approximately 38% of theoretical hydrogen capacity in $CaB_{12}H_{12}$), comparable to the reported value of 1.5 mass% at 600 °C.²⁸ The reaction has multiple steps when heated up to 750 °C.

The XRD patterns, Raman spectra and solid-state ^{11}B MAS NMR spectra of the anhydrous $CaB_{12}H_{12}$ heated to fixed temperatures and subsequently cooled down to room temperature are shown in Figures S3 and 7, respectively. When $CaB_{12}H_{12}$ is heated up to 400 °C, no obvious changes of Raman spectra and the major resonance for $CaB_{12}H_{12}$ are seen, whereas the diffraction peaks of the unknown phase and the resonance at -32.2 ppm originates from the residual $Ca(BH_4)_2$ nearly disappears at 375 °C. This indicates that the weight loss below 400 °C is responsible for the dehydrogenation of the residual $Ca(BH_4)_2$ and the unknown phase, suggesting that the impurities do not directly influence the decomposition of $CaB_{12}H_{12}$. When $CaB_{12}H_{12}$ is heated up to 500 °C, diffraction peaks and Raman spectra attributed to $CaB_{12}H_{12}$ disappear, the major resonance at -14.0 ppm becomes significantly weaker and overlaps with a broad resonance between 0 and -13 ppm, suggesting that the dehydrogenation of $CaB_{12}H_{12}$ to $CaB_{12}H_{12-x}$ as well as a polymerization of $CaB_{12}H_{12-x}$ to water and DMSO insoluble $(CaB_yH_z)_n$ polymers starts close to 500 °C.^{31, 32} When $CaB_{12}H_{12}$ is further heated up to 600 °C and 750 °C, the major resonance shifts to -11.2 and -7.0 ppm, indicating the continuous polymerization of $(CaB_yH_z)_n$, similar to that of $MgB_{12}H_{12}$ heated up to 500 ~ 700 °C. Unlike $MgB_{12}H_{12}$, no obvious NMR spectra originated from amorphous boron is observed when $CaB_{12}H_{12}$ is heated up to 750 °C, whereas CaB_6 has been demonstrated as the main dehydrogenation product of $Ca(BH_4)_2$ above 330 °C.^{14, 20, 35}

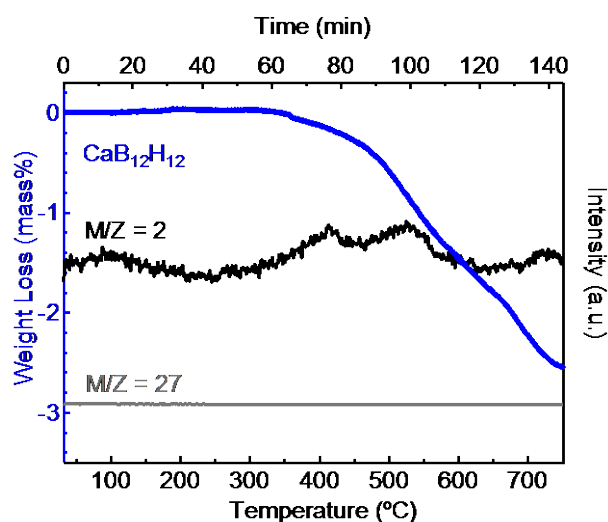


Figure 6. TG curve and MS signals of the synthesized $\text{CaB}_{12}\text{H}_{12}$ (mass numbers of 2 and 27 represent H_2 and B_2H_6).



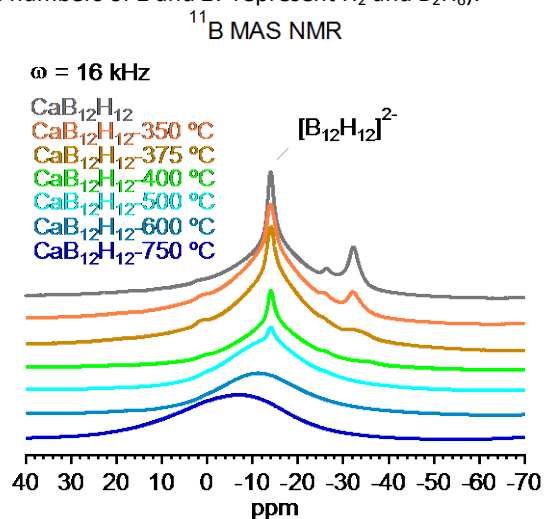


Figure 7. ^{11}B MAS NMR spectra of $\text{CaB}_{12}\text{H}_{12}$ as synthesized and heated up to respective temperatures.

The decomposition pathway of the anhydrous $\text{CaB}_{12}\text{H}_{12}$ is briefly summarized as the following steps (below 750°C):



Similar to that of $\text{MgB}_{12}\text{H}_{12}$, the decomposition behaviour of the synthesized $\text{CaB}_{12}\text{H}_{12}$ does not seem to directly correlate with the dehydrogenation of $\text{Ca}(\text{BH}_4)_2$, suggesting that: a) CaH_2 forming in the decomposition of $\text{Ca}(\text{BH}_4)_2$ facilitates the transformation of $\text{CaB}_{12}\text{H}_{12}$ to produce CaB_6 that is not detected when $\text{CaB}_{12}\text{H}_{12}$ is heated even up to 750°C ;^{9, 28} or b) $\text{CaB}_{12}\text{H}_{12}$ does not form as a stable dehydrogenation intermediate of $\text{Ca}(\text{BH}_4)_2$ as reported recently.¹⁶

In summary, the thermal decomposition of $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ reveal two steps of 1) dehydrogenation to produce H-deficient $\text{MB}_{12}\text{H}_{12-x}$ and 2) polymerization of $\text{MB}_{12}\text{H}_{12-x}$ to form $(\text{MB}_y\text{H}_z)_n$, which is the main step to form amorphous boron, regarded as the major obstacle for rehydrogenation. The uncorrelated thermal decomposition behaviours of metal

dodecaborates and metal borohydrides emphasize the importance of systematic investigations of various possible dehydrogenation intermediates and the corresponding metal borohydrides, in order to determine the exact dehydrogenation and rehydrogenation mechanisms for metal borohydrides.

Conclusions

Anhydrous alkaline earth metal dodecaborates $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ have been successfully synthesized through sintering of ball milled $\text{M}(\text{BH}_4)_2 + \text{B}_{10}\text{H}_{14}$ ($\text{M} = \text{Mg}, \text{Ca}$). This study again proves that sintering of borohydrides with $\text{B}_{10}\text{H}_{14}$ is a facile method to synthesize anhydrous metal dodecaborates. Systematic investigations of thermal decomposition demonstrate that both $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ firstly release hydrogen to form H-deficient $\text{MB}_{12}\text{H}_{12-x}$ with the icosahedral B_{12} skeletons, followed by a polymerization process to produce $(\text{MB}_y\text{H}_z)_n$. The anhydrous $\text{MgB}_{12}\text{H}_{12}$ is amorphous and it decomposes into amorphous boron at 800°C , whereas $\text{CaB}_{12}\text{H}_{12}$ may require much higher temperature to complete the decomposition. The lower electronegativity of Ca than that of Mg is considered to be responsible for the higher stability of $\text{CaB}_{12}\text{H}_{12}$ than that of $\text{MgB}_{12}\text{H}_{12}$.³⁶ On the other hand, thermal decomposition of the synthesized $\text{MgB}_{12}\text{H}_{12}$ and $\text{CaB}_{12}\text{H}_{12}$ does not seem directly correlate with the dehydrogenation of $\text{Mg}(\text{BH}_4)_2$ and $\text{Ca}(\text{BH}_4)_2$, suggesting the great importance of further investigation on the correlation between decomposition of possible dehydrogenation intermediates and of the corresponding metal borohydrides.

Acknowledgements

We would like to sincerely thank Assoc. Prof. M. Yamauchi and Asst. Prof. M. Watanabe in I2CNER for their great help on ^{11}B MAS NMR measurement. This study was partially supported by JSPS KAKENHI Grant Number 25709067, JSPS Invitation Fellowship for Research in Japan (Short-Term), FNRS and the International Institute for Carbon Neutral Energy Research (WPI-I2CNER), sponsored by the Japanese Ministry of Education, Culture, Sports, Science and Technology.

Notes and references

1. S.-i. Orimo, Y. Nakamori, J. R. Eliseo, A. Züttel and C. M. Jensen, *Chemical Reviews*, 2007, **107**, 4111-4132.
2. H.-W. Li, Y. Yan, S.-i. Orimo, A. Züttel and C. M. Jensen, *Energies*, 2011, **4**, 185-214.
3. L. H. Rude, T. K. Nielsen, D. B. Ravnsbaek, U. Bösenberg, M. B. Ley, B. Richter, L. M. Arnbjerg, M. Dornheim, Y. Filinchuk, F. Besenbacher and a. T. R. Jensen, *physica status solidi (a)*, 2011, **208**, 1754-1773.
4. H.-W. Li, J. Wang and Ping Chen, *MRS Bulletin*, 2013, **38**, 480-487.
5. S.-i. Orimo, Y. Nakamori, N. Ohba, K. Miwa, M. Aoki, S.-i. Towata and A. Züttel, *Applied physics letters*, 2006, **89**, 021920-021920-021923.

6. N. Ohba, K. Miwa, M. Aoki, T. Noritake, S.-i. Towata, Y. Nakamori, S.-i. Orimo and A. Züttel, *Physical Review B*, 2006, **74**, 075110.
7. H.-W. Li, K. Kikuchi, Y. Nakamori, N. Ohba, K. Miwa, S. Towata and S. Orimo, *Acta Materialia*, 2008, **56**, 1342-1347.
8. S.-J. Hwang, R. C. Bowman, J. W. Reiter, J. Rijssenbeek, G. L. Soloveichik, J.-C. Zhao, H. Kabbour and C. C. Ahn, *The Journal of Physical Chemistry C*, 2008, **112**, 3164-3169.
9. V. Ozolins, E. Majzoub and C. Wolverton, *Journal of the American Chemical Society*, 2009, **131**, 230-237.
10. C. Bonatto Minella, S. Garroni, D. Olid, F. Teixidor, C. Pistidda, I. Lindemann, O. Gutfleisch, M. D. Baró, R. d. Bormann and T. Klassen, *The Journal of Physical Chemistry C*, 2011, **115**, 18010-18014.
11. Y. Yan, H.-W. Li, H. Maekawa, K. Miwa, S.-i. Towata and S.-i. Orimo, *The Journal of Physical Chemistry C*, 2011, **115**, 19419-19423.
12. M. P. Pitt, M. Paskevicius, D. H. Brown, D. A. Sheppard and C. E. Buckley, *Journal of the American Chemical Society*, 2013, **135**, 6930-6941.
13. M. Chong, A. Karkamkar, T. Autrey, S.-i. Orimo, S. Jalisatgi and C. M. Jensen, *Chemical Communications*, 2011, **47**, 1330-1332.
14. Y. Yan, A. Remhof, D. Rentsch and A. Züttel, *Chemical Communications*, 2015, **51**, 700-702.
15. M. Riktor, M. Sørby, J. Muller, E. Bardají, M. Fichtner and B. Hauback, *Journal of Alloys and Compounds*, 2015, **632**, 800-804.
16. Y. Yan, A. Remhof, D. Rentsch, A. Züttel, S. Giri and P. Jena, *Chemical Communications*, DOI: 10.1039/C5CC03605D.
17. G. Xia, Q. Meng, Z. Guo, Q. Gu, H. Liu, Z. Liu and X. Yu, *Acta Materialia*, 2013, **61**, 6882-6893.
18. H.-W. Li, T. Matsunaga, Y. Yan, H. Maekawa, M. Ishikiriya and S.-i. Orimo, *Journal of Alloys and Compounds*, 2010, **505**, 654-656.
19. Y. Kim, S.-J. Hwang, J.-H. Shim, Y.-S. Lee, H. N. Han and Y. W. Cho, *The Journal of Physical Chemistry C*, 2012, **116**, 4330-4334.
20. H.-W. Li, E. Akiba and S.-i. Orimo, *Journal of Alloys and Compounds*, 2013, **580**, S292-S295.
21. C. B. Minella, C. Pistidda, S. Garroni, P. Nolis, M. D. Baró, O. Gutfleisch, T. Klassen, R. d. Bormann and M. Dornheim, *The Journal of Physical Chemistry C*, 2013, **117**, 3846-3852.
22. I. B. Sivaev, V. I. Bregadze and S. Sjöberg, *Collection of Czechoslovak chemical communications*, 2002, **67**, 679-727.
23. J.-H. Her, W. Zhou, V. Stavila, C. M. Brown and T. J. Udovic, *The Journal of Physical Chemistry C*, 2009, **113**, 11187-11189.
24. X. Chen, Y.-H. Liu, A.-M. Alexander, J. C. Gallucci, S.-J. Hwang, H. K. Lingam, Z. Huang, C. Wang, H. Li, Q. Zhao, U. S. Ozkan, S. G. Shore and J.-C. Zhao, *Chemistry - A European Journal*, 2014, **20**, 7325-7333.
25. L. He, H.-W. Li, S.-J. Hwang and E. Akiba, *The Journal of Physical Chemistry C*, 2014, **118**, 6084-6089.
26. V. Ban, A.V. Soloninin, A.V. Skripov, J. Hadermann, A. Abakumov and Y. Filinchuk, *The Journal of Physical Chemistry C*, 2014, **118**, 23402-23408.
27. A. D. Kulkarni, L.-L. Wang, D. D. Johnson, D. S. Sholl and J. K. Johnson, *The Journal of Physical Chemistry C*, 2010, **114**, 14601-14605.
28. V. Stavila, J.-H. Her, W. Zhou, S.-J. Hwang, C. Kim, L. A. M. Ottley and T. J. Udovic, *Journal of Solid State Chemistry*, 2010, **183**, 1133-1140.
29. N. Nogi and S. Tanaka, *Journal of Solid State Chemistry*, 2006, **179**, 2927-2933.
30. S. Hermanek, *Chemical Reviews*, 1992, **92**, 325-362.
31. S.-J. Hwang, R. C. Bowman Jr, C. Kim, J. A. Zan and J. W. Reiter, *Journal of Analytical Science & Technology*, 2011, **2**, A159-A162.
32. Y. Yan, A. Remhof, S.-J. Hwang, H.-W. Li, P. Mauron, S.-i. Orimo and A. Züttel, *Physical Chemistry Chemical Physics*, 2012, **14**, 6514-6519.
33. A. Remhof, Y. Yan, D. Rentsch, A. Borgschulze, C. M. Jensen and A. Züttel, *Journal of Materials Chemistry A*, 2014, **2**, 7244-7249.
34. H.-W. Li, K. Kikuchi, T. Sato, Y. Nakamori, N. Ohba, M. Aoki, K. Miwa, S.-i. Towata and S.-i. Orimo, *Materials transactions*, 2008, **49**, 2224-2228.
35. Y. Kim, D. Reed, Y.-S. Lee, J. Y. Lee, J.-H. Shim, D. Book, and Y. W. Cho, *The Journal of Physical Chemistry C*, 2009, **113**, 5865-5871.
36. Y. Nakamori, K. Miwa, A. Ninomiya, H. Li, N. Ohba, S.-i. Towata, A. Züttel and S.-i. Orimo, *Physical Review B*, 2006, **74**, 045126.