

Faraday Discussions

Accepted Manuscript



This manuscript will be presented and discussed at a forthcoming Faraday Discussion meeting. All delegates can contribute to the discussion which will be included in the final volume.

Register now to attend! Full details of all upcoming meetings: <http://rsc.li/fd-upcoming-meetings>



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Faraday Discussions**Oxygen Deficient Layered Double Perovskite as an Active Cathode
for CO₂ Electrolysis Using Solid Oxide Conductor**

Tae Ho Shin ^{a,*}, Jae-Ha Myung ^a, Maarten Verbraeken ^a, Guntae Kim ^b, and John T. S. Irvine ^{a,*}

^a *School of Chemistry, University of St Andrews, KY16 9ST, Scotland, UK*

^b *Dept. of Chemical and Energy Engineering, Ulsan National Institute of Science and Technology (UNIST), Korea*

Corresponding Author

Dr. Tae Ho Shin (Birth: March 28, 1976)

School of Chemistry

University of St Andrews, St Andrews, Fife, KY16 9ST, UK

Tel: +44-759-676-2424

E-mail: ths@st-andrews.ac.uk, ceramist95@gmail.com

Abstract

A-site ordered $\text{PrBaMn}_2\text{O}_{5+\delta}$ was investigated as a potential cathode for CO_2 electrolysis using $\text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM) electrolyte. The A-site ordered layered double perovskite, $\text{PrBaMn}_2\text{O}_{5+\delta}$, was found to enhance electrocatalytic activity for CO_2 reduction on the cathode side since it supports mixed valent transition metal cations such as Mn, which could provide high electrical conductivity and maintain a large oxygen vacancy content, contributing to fast oxygen ion diffusion. It was found that during the oxidation of the reduced $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5 phase) to $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6 phase), a reversible oxygen switchover in the lattice takes place. In addition, here the successful CO_2 electrolysis was measured in LSGM electrolyte with this novel oxide electrode. It was found that $\text{PrBaMn}_2\text{O}_{5+\delta}$, layered perovskite cathode exhibits a performance with a current density of 0.85 A cm^{-2} at 1.5 V and 850°C and electrochemical property also was evaluated by impedance spectroscopy.

1. Introduction

With growth of renewable energy technologies, it is necessary to store vast amounts of energy by, e.g., converting electricity overcapacity to chemical energy in the form of compounds such as hydrogen, methane, or methanol. In particular, the variety products from high temperature electrolysis can be used as feedstocks for chemical synthesis or converted into highly dense electric power; it would provide a means of storing renewable electricity in a convenient, high energy-density form. Recently, hydrogen has attracted attention as an alternative mediator for energy conversion and storage because of its high gravimetric energy density and zero carbon emission¹⁻⁵. However, the utilization of hydrogen has been limited due to the practical engineering and economic limitations with respect to its generation and distribution⁶. On the other hand hydrocarbon fuels and carbon monoxide cost-effectively match the existing energy infrastructure well because of their similarity to current fossil fuels; they would be effective energy carriers in a period of transition toward zero carbon emission⁷⁻⁹. Recycling or reuse of CO₂ could be an effective approach for accessing a new form of energy carrier and enabling a carbon-neutral cycle. In particular, electrochemical reduction of CO₂ into CO fuel with renewable electricity has been proposed as an alternative method to store this energy, overcoming the inherent problems with intermittency and geographical distribution of renewable energy sources¹⁰⁻¹³.

Solid oxide electrolysis cells (SOECs) have recently attracted a great deal of interest as a highly efficient electrolyser and a green energy technology. Current developments are mainly based upon steam electrolysis for hydrogen production. However, reduction of CO₂ using a highly efficient solid oxide electrolyser is also feasible. This would be an alternative to carbon capture and advanced utilization of CO₂^{14,15}. Solid oxide electrolysers with oxygen ion conducting electrolytes are able to separately produce CO and O₂ from CO₂ ($\text{CO}_2 \rightarrow 1/2\text{O}_2 + \text{CO}$) at high and intermediate temperature (500-900°C) with high efficiencies (as they are not limited by the Carnot cycle). Both products, CO and O₂ may be useful in industrial processes. The electrolysis of CO₂ in a solid oxide device is analogous to high temperature steam electrolysis by SOEC, i.e. CO₂ molecules are electrochemically reduced into CO at the cathode (fuel electrode) and oxygen ion are transported through the oxygen-ion conducting electrolyte to the anode (oxygen electrode) where gaseous O₂ is produced and released. High temperature solid oxide electrolysis reduces electricity demand, and offers fast electrode kinetics, reducing the overall cell internal resistance

as a consequence and increasing electrolysis efficiency. Due to the operating conditions in SOEC using CO_2 , cathode materials require stability in a wide $p\text{O}_2$ and temperature range, and additionally need to be tolerant towards carbon coking. To date, SOEC predominantly comprise materials and techniques from solid oxide fuel cells (SOFCs), but operated in reverse modes. This means that electrode materials have not been tailored specifically for use in electrolysis conditions, which can differ substantially from fuel cell conditions. Long term stability of solid oxide electrode materials is still one of the important challenging issues for both SOEC and SOFC for commercialisation into the energy market.

Currently, high temperature electrolysis of CO_2 has been mainly performed using Ni-YSZ cermet cathodes in oxygen ion conducting SOEC. However, Ni is easily deactivated by reoxidation or carbon formation when it is directly exposed to CO/CO_2 or hydrocarbon atmosphere¹⁶⁻¹⁸. Therefore, a significant reduction atmosphere is required to flow over the Ni surface base electrode to avoid oxidation of Ni to NiO, which would cause a loss of electronic conductivity and the failure of the electrode. In the most serious circumstance, the electrode fails mechanically as a result of deposited coke or re-oxidation¹⁹. Consequently, redox stability and reversibility have recently been emphasised as important requirements for the cathode (fuel electrode) material in SOEC. So far, several conductive perovskite oxides have been reported as potential anode materials in SOFC, which may also be useful as cathode materials in SOEC. For more sturdy and superior materials in durable SOFC/SOEC systems, various mixed ionic and electronic conducting (MIEC) oxides have been explored. Among these, researchers have mainly demonstrated that $\text{La}(\text{Sr})\text{MO}_3$ ($\text{M} = \text{Cr}, \text{Mn}, \text{Fe}, \text{Ti}$) perovskite oxides²⁰⁻²² can, in principle, be good fuel electrode materials with sufficient electronic conductivity. For instance, the efficient electrolysis of CO_2 based on a ceramic cathode, $\text{La}(\text{Sr})\text{Mn}(\text{Cr})\text{O}_3$ (LSCM) perovskite oxide have been recently demonstrated^{20, 23-25}. However, electrochemical performance of the ceramic electrodes is still smaller than that using a Ni based electrode, due to insufficient electrical conductivity and low electrocatalytic activity. LSCM suffers from a drop in conductivity under the reducing SOEC cathode conditions.

Recently we have succeeded in synthesising the oxygen deficient layered phase, $\text{PrBaMn}_2\text{O}_{5+\delta}$ under reducing atmosphere. Whereas polycrystalline samples sintered in air adopt the cubic ABO_3 perovskite structure, the A-site ordered layered perovskite $\text{PrBaMn}_2\text{O}_{5+\delta}$, can be grown under reducing conditions. Furthermore, it was found that the double perovskite, $\text{PrBaMn}_2\text{O}_{5+\delta}$ exhibits high electrical conductivity and excellent redox and coking tolerance when used as an anode for an SOFC²⁶. In this work, $\text{PrBaMn}_2\text{O}_{5+\delta}$, employed as a potential ceramic cathode for CO_2 electrolysis SOEC with configuration of

PrBaMn₂O_{5+δ} | La doped Ceria (LDC) | La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O₃ (LSGM) | La(Sr)Fe(Co)O₃. The performance of the PrBaMn₂O_{5+δ} cathode and the electrochemical process of high temperature electrolysis of CO₂ in a cell using LSGM as the electrolyte were investigated and evaluated.

2. Experimental

The Pr_{0.5}Ba_{0.5}MnO_{3-δ} was prepared using the conventional solid-state reaction method and then A-site ordered layered PrBaMn₂O_{5+δ} is obtained by in-situ annealing Pr_{0.5}Ba_{0.5}MnO_{3-δ} in reducing conditions using 5% H₂ at temperatures higher than 800°C. The crystalline phase characterization of the oxide powder was performed by X-ray diffraction (PANalytical Empyrean, Mo K α radiation and Cu K α 1 radiation). Thermal gravimetric analysis (TGA) was carried out on a NETZSCH TG 209 instrument (NETZSCH Geraetebau GmbH, Selb, Germany) with a heating & cooling rate of 2-5 °C/min to evaluate the oxygen loss and incorporation on redox cycling in air and 5% H₂ on the compositions synthesized and dilatometry was also performed at 100°C to 800°C with a heating/cooling rate of 2 °C min⁻¹ in air and 5 % H₂ to characterize the thermo-physical properties. Electrical conductivity was measured on the sintered pellets by the standard four terminal DC method or Van Der Pauw method up to 900°C in ambient air. A current of 50 mA (model: Keithley 220, Keithley Instruments Inc., U.S.A.) was applied in both directions, and resistance was calculated as a gradient of potential vs. current. This conductivity details was previously reported²⁶.

For solid oxide electrolyser experiments, a configuration of PrBaMn₂O_{5+δ} | LDC | La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O₃ (LSGM) | La(Sr)Fe(Co)O₃ was fabricated using 200 μ m thick LSGM electrolyte supports. Commercially available powder, La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O_{3-δ} (LSGM, 99.9% Kceracell co., Ltd, South Korea) was used for the preparation of electrolyte. The LSGM electrolyte supports were prepared by dry-pressing powder into a circular green body followed by high-temperature sintering in air at 1450°C for 6hrs and mechanical polishing until 2 cm diameter and 200 μ m thick electrolyte supports were obtained. Electrodes were deposited onto the faces of the LSGM electrolyte disk by screen-printing inks of the respective powders, followed by sintering at 1100°C for 30 min (thickness of screen printed electrode, < 25 μ m). The active area of the cells, equal to the area to the cathode area (PrBaMn₂O_{5+δ}), was 0.5 cm² and the area of the anode was same.

To evaluate the electrochemical properties, I - V curves and impedance were measured using a four terminal configuration with silver mesh/wire as the electrode current collectors. In order to perform electrochemical testing in fuel cell mode, dried CO_2/CO (70:30 vol) mixture was supplied into the cathode with 100 ml min^{-1} flow rate while the anode side was exposed to constant oxygen flow as an oxidant gas (100 ml min^{-1}). The cell was maintained in each condition for at least one hour to get steady state, before carrying out any electrochemical tests. AC impedance spectroscopy was recorded using using an IM6 Electrochemical Workstation (Zahner, Germany) with frequency ranged from 0.1 Hz to 100 kHz with amplitude of 10 mV.

3. Results and Discussion

The disordered cubic perovskite $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ was prepared by typical solid state reaction. To avoid the complete oxidization of Mn^{3+} to Mn^{4+} , which would favour the formation of BaMnO_3 , the powder was calcined in an atmosphere with lower oxygen partial pressure (using a mixture of Ar/Air) below the synthesis temperature ($< 1300^\circ\text{C}$). A-site ordering in the layered manganite perovskite would be partially hindered by the formation of the hexagonal related perovskite BaMnO_3 . Fig 1 shows the XRD pattern for the cubic disordered perovskite (Fig 1a), prepared by solid state reaction at 1200°C in air; reduction in 5% H_2 leads to A-site ordering and hence doubling of the unit cell, giving a layered phase with tetragonal symmetry (Fig 1b). The XRD pattern of disordered cubic perovskite shown in Fig 1a, suggests the presence of a small amount secondary hexagonal phase, as similarly observed in a previous study in which the powder was prepared by Pechini synthesis at lower temperature²⁶. However, they are not serious impurities but single phase of $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ was mainly indicated. Furthermore, the A-site ordered layered perovskite $\text{PrBaMn}_2\text{O}_{5+\delta}$ could also be grown by annealing the disordered phase in reducing atmosphere in accordance with previous results²⁶. To fully understand the phase changes during redox cycling, we checked the phase transition from disordered cubic $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ phase (O3) to oxygen deficient layered $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) by in-situ variable temperature/atmosphere X-ray diffraction (Mo $K\alpha_1/K\alpha_2$), whilst performing reduction – oxidation cycles. Fig 2(a-c) shows Rietveld refinement profiles of $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ phase (O3), $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) and $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) from in-situ XRD data at 800°C in various atmospheres.. The refined unit cells parameters and refinement statistics are summarized

in Table 1; Table 2 shows selected bond distances and angles.

The in-situ high temperature X-ray diffraction study confirms cubic symmetry for the disordered O3 phase at 800°C. Upon reduction at 800°C, the A-site ordered O5 phase emerges with tetragonal symmetry, causing a relative shrinkage of the c-axis as compared to the a-axis. Refinement is successful using the $P4/mmm$ spacegroup. Subsequent re-oxidation of the A-site ordered O5 phase at 800°C results in the emergence of the double perovskite, $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) phase. This O6 phase also has tetragonal symmetry with spacegroup $P4/mmm$. Re-oxidation of the O5 phase causes a decrease in tetragonality as evidenced by the drop in $2a/c$ ratio from 1.018 to 1.005. Despite this, direct evidence of A-site ordering and thus doubling of unit cell in both O5 and O6 phased from the XRD data is the (001) reflection found at $2\theta \approx 5^\circ$ as shown in Fig 2b and 2c. Despite the weak intensity of the (001) reflection due to small contrast between Pr^{3+} and Ba^{2+} , its emergence on redox cycling is significant. .

The fully oxidised ordered O6 phase shows A-site ordering along the c-axis, with a stacking pattern of alternating $\text{BaO} - \text{MnO}_2 - \text{PrO} - \text{MnO}_2 - \text{BaO}$ layers. As expected from perovskite materials, Mn is six coordinated, whereas both Ba and Pr are twelve coordinated. The MnO_6 octahedron is slightly distorted, causing the Mn and O2 sites to be closer to Pr than to Ba. The reduced O5 variant has an identical stacking sequence but additionally exhibits oxygen vacancy ordering, with the O3 site vacant, resulting in Pr layers without oxygen ions, shown in Fig. 3. In this structure Mn becomes square pyramidally coordinated, whereas Pr is now 8 coordinated to O2. Ba becomes less coordinated to O2, as the latter moves closer to Pr. The lattice volume is increased due to Mn reduction as shown in Table 1 and 2.

Due to the reduction of $\text{Mn}^{3+}/\text{Mn}^{4+}$ in the O3/O6 phases to $\text{Mn}^{2+}/\text{Mn}^{3+}$ in O5 the Mn-O bond length at 800°C increases from 1.89 – 2.03 to 2.04 – 2.07 Å. It is expected that the oxygen deficient PrO_x layer provides a channel for fast oxygen transport and therefore A-site ordering is in fact enhancing the oxygen mobility, albeit only in two dimensions²⁷. The coexistence of Mn oxidation states is further expected to give rise to electronic conductivity, which is a requirement for any SOEC/SOFC electrode material. The mixed valence of transition metals such as Mn could give rise to different Mn-O bond length at various oxygen partial pressure conditions; the swollen Mn-O bonding length (ca. 2.046 Å) of the oxygen deficient phase could be expected from the reduced oxidation state of Mn (Mn^{3+} or Mn^{2+}). The vacancy would be mainly located between reduced $\text{Mn}^{3+}/\text{Mn}^{2+}$ state cations, between pairs of square pyramidal MnO_5 . Thus oxygen vacancy ordering provides a mechanism to reduce the coordination number of the

smaller Pr^{3+} ion without reducing the coordination number of the larger Ba^{2+} ion. Under reducing conditions, oxygen atoms in the PrO_x plane can be partially or entirely removed, creating many oxygen vacant sites in the crystal sites. This might illustrate the close coupling between A-site ordering and oxygen vacancy ordering²⁷.

What makes the layered perovskite-manganese oxide $\text{PrBaMn}_2\text{O}_{5+\delta}$ a promising candidate for high oxygen mobility is its remarkable variability in oxygen content under redox conditions. It was generally found that for $\text{ReBaMn}_2\text{O}_{5+\delta}$ ($\text{Re} = \text{Pr}, \text{Nd}, \text{La}, \text{Gd}$) the oxidation of the reduced (O5) phase $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6), in the case of $\text{ReBaMn}_2\text{O}_{5+\delta}$, a reversible oxygen switchover in the lattice takes place. The reversibility of the phase change during redox cycle was also established by thermal analysis. The fully oxygen charged $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) had been reduced in 5% H_2 /95%Ar at elevated temperature up to 800°C and cooled in 5% H_2 /95%Ar to room temperature (2.5°C min^{-1}) and re-oxidized up to 700°C in air. Fig 4 shows the thermogravimetric analysis (TGA) in which a weight gain of ca. 3.58 wt% was observed on both reduction and re-oxidation corresponding to a loss/uptake of 1 formula unit of oxygen ($\delta=1$). This symmetry between reduction and oxidation cycles suggests excellent reversibility, which is in agreement with our previously reported dilatometry data²⁶.

Since $\text{PrBaMn}_2\text{O}_{5+\delta}$ shows superior redox reversibility as well as potential electrochemical performance as oxide anode for SOFC, application of $\text{PrBaMn}_2\text{O}_{5+\delta}$ for a potential cathode in CO_2 electrolysis using solid oxide ion conductor, LSGM, was further studied. Fig 5a shows the temperature dependent I - V curves for CO_2 electrolysis between 750°C and 850°C under the following gas feed conditions: air on the anode side and a mixture of 70% CO_2 / 30% CO on the cathode side with 100 ml min^{-1} . It was found that $\text{PrBaMn}_2\text{O}_{5+\delta}$ is very effective for CO_2 electrolysis with a remarkable cathodic current density of 0.84 A cm^{-2} at 1.55 V and 850°C. At lower temperature (750°C), it seems that there was no significant current flow at lower voltages suggesting a slow electrolysis reaction, which might be explained by the large overpotential on the cathode side; the cell voltage sharply increased with increasing current density at initial low current range. Fig 5b shows the I - V curve at 850°C, during current cycling, which was measured with increasing current up to the maximum current range and subsequent decreasing current, leaving long stabilisation times at every current step to attempt to attain equilibrium. However, it was observed that voltage recovery was slow and strongly time dependent. As shown in Fig 5b, initial OCV (0.825 V) was slightly increased to 1.141 V after current cycling; the initial OCV was however

recovered over time. The increased OCV after cycling could be related with momentary carbon deposition or carbon monoxide adsorption on the catalyst surface, as 1.14 V is very close to the theoretical OCV value for carbon fuel; Slow surface kinetics of $\text{PrBaMn}_2\text{O}_{5+\delta}$ might explain such desorption/adsorption CO/CO_2 or carbon species. Alternatively, poor catalytic activity for carbon oxidation or a Ba carbonation reaction might play a role too. The slow chemical kinetics are not fully understood at this stage, but a more detailed analysis using *in-situ* exhausts gas analysis, catalyst additives and *in-situ* surface analysis would be helpful to shed further light on the issue in future work. In particular, stable catalytic activity of $\text{PrBaMn}_2\text{O}_{5+\delta}$ for CO_2 could be improved with other catalyst additives, whereas B-site doping may help stabilize the Ba from carbonisation.

For the detailed reaction mechanisms, ac impedance spectra were measured. Fig. 6 shows complex impedance plots under open circuit conditions for internal resistance of the cell $\text{PrBaMn}_2\text{O}_{5+\delta} | \text{LDC} | \text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM) $| \text{La}(\text{Sr})\text{Fe}(\text{Co})\text{O}_3$. In general, it is necessary to have a reference electrode to separate anode and cathode losses. However, it should be recognized that improper placement of the reference electrode and working electrodes will give erroneous value; thus, exactly separating each electrode can be difficult even in symmetric electrode geometry in thin electrolyte support cell, when the kinetics of the two electrode are significantly different²⁸⁻³⁰. As shown in Fig. 6(a), it is significant that the ohmic resistance in both impedance spectra are approximately the same, and almost exactly one-half of the total ohmic resistance of the cell, showing that the reference electrode is sampling the potential at the centre of the electrolyte. Thus, it can be roughly inferred that total polarization resistance was clearly dominated by cathodic electrode ($\text{PrBaMn}_2\text{O}_{5+\delta}$) because cathodic impedance spectra was similar to the total cell impedance. It is obvious that at least two semicircles are present in the impedance plot. Considering the response frequencies of the two parallel RQ circuits, the resistance at higher frequency (R_{p1}) could be assigned to a charge transfer process, whereas the lower frequency process (R_{p2}) seems related to a diffusion process of the cathodic reaction. The contribution of R_{p2} is much larger than that of the surface reaction step (R_{p1}), and so the observed impedance may indicates a slow CO_2 diffusion, which may be due to slow chemical surface adsorption/desorption and/or slow surface-diffusion processes for CO_2 reduction on the surface of $\text{PrBaMn}_2\text{O}_{5+\delta}$ at lower temperature. Although fast oxygen ion mobility would be expected due to a large concentration of ordered oxide ion vacancies in $\text{PrBaMn}_2\text{O}_{5+\delta}$, it shows lower surface activity for CO_2 reduction at lower temperature. However, fairly good performances were still achieved at temperature higher than 800°C and its surface activity for CO_2 may be improved if other

catalytic additives are effectively employed. Due to improve surface activity, various metal catalyst additives are now under study, and the results will be reported in the future. Fig. 7 shows SEM micrographs of the cathode of the $\text{PrBaMn}_2\text{O}_{5+\delta}$ | LDC | $\text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM) | $\text{La}(\text{Sr})\text{Fe}(\text{Co})\text{O}_3$ cell before and after CO_2 electrolysis. There appears to be some limited coking on the top surface that might be explained by Boudouard reaction at high temperature with CO_2/CO mixture or slow response of $\text{PrBaMn}_2\text{O}_{5+\delta}$ for the chemical surface adsorption/desorption of CO_2 molecules; however, there were no serious surface morphology changes. It was therefore concluded that A-site ordered layered perovskite, $\text{PrBaMn}_2\text{O}_{5+\delta}$, could be used as a potential cathode in solid oxide electrolysis with excellent redox tolerance.

4. Conclusion

In summary, $\text{PrBaMn}_2\text{O}_{5+\delta}$ was successfully prepared as single phase cathode material from disordered O3 perovskite phase after reduction treatment. The reduction to obtain layered $\text{PrBaMn}_2\text{O}_{5+\delta}$ can be performed in-situ during SOEC/SOFC testing to limit processing steps. An in-situ high temperature X-ray diffraction study confirmed the phase changes under reducing and oxidising conditions, showing that the A-site ordered layered perovskite can be formed from disordered cubic phase under reducing condition at 800°C with reversible phases change between $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) and $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) during redox cycles. The superior redox ability of $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) was also observed by thermogravimetric methods, showing a reversible weight change during redox cycling corresponding to a change in oxygen stoichiometry of $\delta=1$.

Moreover, the reduction of CO_2 via elevated-temperature ($750 - 850^\circ\text{C}$) electrolysis using an SOEC with LSGM as the electrolyte was studied using $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) cathode. High current density (0.845 A cm^{-2}) was obtained at 850°C and electrolysis potential of 1.55 V for a cell using the $\text{PrBaMn}_2\text{O}_{5+\delta}$ | LDC | $\text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM) | $\text{La}(\text{Sr})\text{Fe}(\text{Co})\text{O}_3$. As a result, this study revealed that $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) is a potential cathode material for SOEC.

Acknowledgements

We thank EPSRC (EP/I022570/1, EP/K015540/1, EP/I038950/1) and the Royal Society (Wolfson Research Merit award) for support.

References

1. J. L. Bernal-Agustín and R. Dufo-López, *International Journal of Hydrogen Energy*, 2008, **33**, 6401.
2. J. O. M. Bockris and T. N. Veziroglu, *International Journal of Hydrogen Energy*, 2007, **32**, 1605.
3. S. H. Jensen, P. H. Larsen and M. Mogensen, *International Journal of Hydrogen Energy*, 2007, **32**, 3253.
4. W. Doenitz, R. Schmidberger, E. Steinheil and R. Streicher, *International Journal of Hydrogen Energy*, 1980, **5**, 55.
5. A. O. Isenberg, *Solid State Ionics*, 1981, **3–4**, 431.
6. E. H. Seymour, L. Murray and R. Fernandes, *International Journal of Hydrogen Energy*, 2008, **33**, 3015.
7. L. Schlapbach, *Nature*, 2009, **460**, 809.
8. L. Wang and R. T. Yang, *Energy & Environmental Science*, 2008, **1**, 268.
9. B. Sakintuna, F. Lamari-Darkrim and M. Hirscher, *International Journal of Hydrogen Energy*, 2007, **32**, 1121.
10. S. D. Ebbesen and M. Mogensen, *Journal of Power Sources*, 2009, **193**, 349.
11. N. Q. Minh and M. B. Mogensen, *Electrochemical Society Interface*, 2013, **22**, 55.
12. C. Graves, S. D. Ebbesen and M. Mogensen, *Solid State Ionics*, 2011, **192**, 398.
13. K. Xie, Y. Zhang, G. Meng and J. T. S. Irvine, *Journal of Materials Chemistry*, 2011, **21**, 195.
14. C. Graves, S. D. Ebbesen, S. H. Jensen, S. B. Simonsen and M. B. Mogensen, *Nat Mater*, 2015, **14**, 239.
15. D. M. Bierschenk, J. R. Wilson and S. A. Barnett, *Energy & Environmental Science*, 2011, **4**, 944.
16. E. P. Murray, T. Tsai and S. A. Barnett, *Nature*, 1999, **400**, 649.
17. P. Huang, A. Horky and A. Petric, *Journal of the American Ceramic Society*, 1999, **82**, 2402.
18. B. C. H. Steele, I. Kelly, H. Middleton and R. Rudkin, *Solid State Ionics*, 1988, **28–30**, 1547.
19. S. McIntosh and R. J. Gorte, *Chemical Reviews*, 2004, **104**, 4845.
20. X. L. Yue and J. T. S. Irvine, *Journal of the Electrochemical Society*, 2012, **159**, F442.
21. S. Wang, H. Tsuruta, M. Asanuma and T. Ishihara, *Advanced Energy Materials*, 2015, **5**, n/a.
22. Y. Li, J. Zhou, D. Dong, Y. Wang, J. Z. Jiang, H. Xiang and K. Xie, *Physical Chemistry Chemical Physics*, 2012, **14**, 15547.
23. X. Yue and J. T. S. Irvine, *Electrochemical and solid-state letters*, 2012, **15**, B31.
24. X. L. Yue and J. T. S. Irvine, *Solid State Ionics*, 2012, **225**, 131.
25. F. Bidrawn, G. Kim, G. Corre, J. T. S. Irvine, J. M. Vohs and R. J. Gorte, *Electrochemical and Solid-State Letters*, 2008, **11**, B167.
26. S. Sengodan, S. Choi, A. Jun, T. H. Shin, Y.-W. Ju, H. Y. Jeong, J. Shin, J. T. S. Irvine and G. Kim, *Nat Mater*, 2015, **14**, 205.
27. M. T. Anderson, J. T. Vaughey and K. R. Poeppelmeier, *Chemistry of Materials*, 1993, **5**, 151.
28. S. McIntosh and R. J. Gorte, *Chemical reviews*, 2004, **104**, 4845.
29. S. B. Adler, *Journal of the Electrochemical Society*, 2002, **149**, E166.
30. S. McIntosh, J. Vohs and R. Gorte, *Journal of the Electrochemical Society*, 2003, **150**, A1305.

Table 1 Refined structural parameters for $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (O3), $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) and $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) obtained by simultaneous fitting of *in-situ* high temperature XRD data at 800°C

	$\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (O3) in air	$\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) in H_2	$\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) in air
Space group	<i>Pm -3m (Cubic)</i>	<i>P4/nmm (Tetra)</i>	<i>P4/mmm (Tetra)</i>
a=b (Å)	3.93593(5)	4.02405(9)	3.93985(9)
c (Å)	-	7.90618(24)	7.84136(24)
2a/c		1.018	1.005
V (Å³)	60.9735(13)	128.024(6)	121.717(5)
λ (Å) Mo Kα1	0.0793	0.7093	0.7093
λ (Å) Mo Kα2	0.7136	0.7136	0.7136
R_p %	7.93	6.43	6.06
R_{wp} %	11.19	8.30	8.01

Table 2 Selected interatomic distances and angles of $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (O3), $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) and $\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) obtained by simultaneous fitting of *in-situ* high temperature XRD data at 800°C

	$\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (O3) in air	$\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) in H_2	$\text{PrBaMn}_2\text{O}_{6-\delta}$ (O6) in air
Distance (Å)			
Mn-O1	1.96796(2) 6	2.067(5) × 1	2.03072(6) × 1
Mn-O2	-	2.0405(18) × 4	1.97022(4) × 4
Mn-O3	-	-	1.88996(6) × 1
Mn-O (average)	1.96796	2.0458	1.96693
Angles (°)			
Mn-O1-Mn	180	180	180
Mn-O2-Mn	-	160.83(57)	178.01680(10)
Mn-O3-Mn	-	-	180
O1-Mn-O3	180	-	180
O2-Mn-O2	180	160.83(57)	178.01680(10)

Figure 1

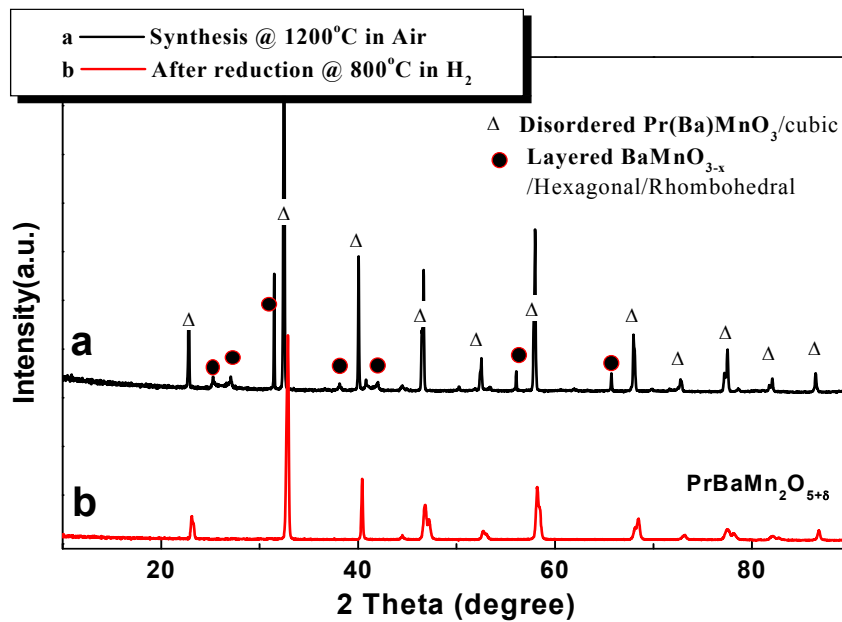
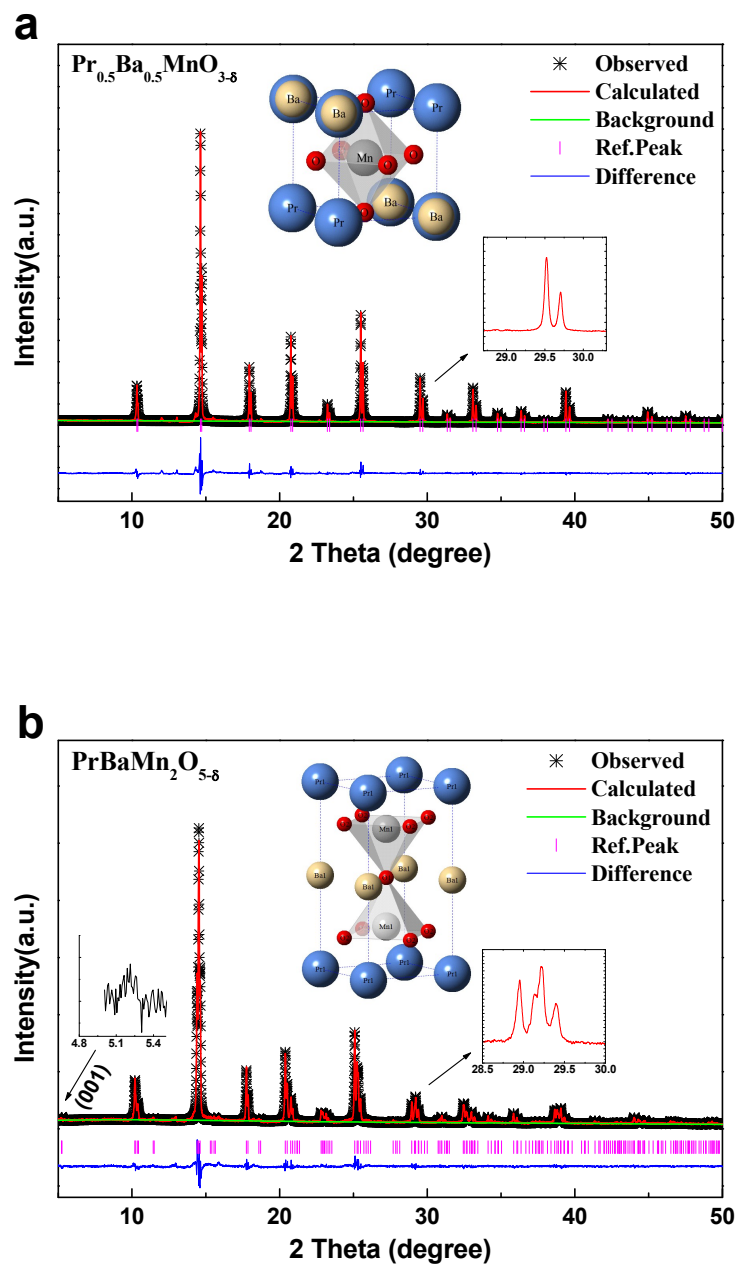


Fig 1. X-ray diffraction patterns of $\text{Pr}_{0.5}\text{Ba}_{0.5}\text{MnO}_3$ (O3) prepared by solid state reaction at 1200°C in air, and (b) $\text{PrBaMn}_2\text{O}_{5+\delta}$ (O5) was obtained by reducing as-prepared powder (a) in 5% H_2 at 800°C for 4hr. (Cu $K\alpha$ radiation)

Figure 2.



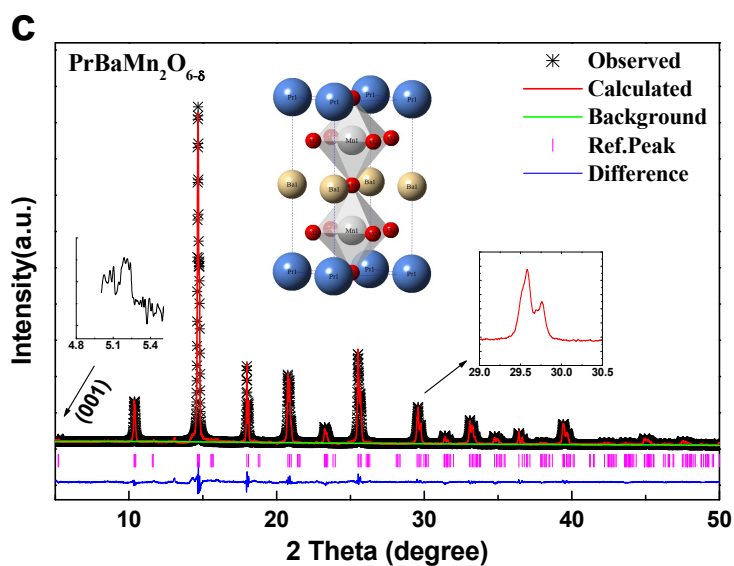


Figure 2. Rietveld-refined XRD profiles of (a) Pr_{0.5}Ba_{0.5}MnO₃ (O3), (b) PrBaMn₂O_{5+δ} (O5) and (c) PrBaMn₂O_{6-δ} (O6) obtained by simultaneous fitting of *in-situ* high temperature XRD data at 800°C in air, 5%H₂ and air, respectively. (Mo Kα1, Kα2 radiation)

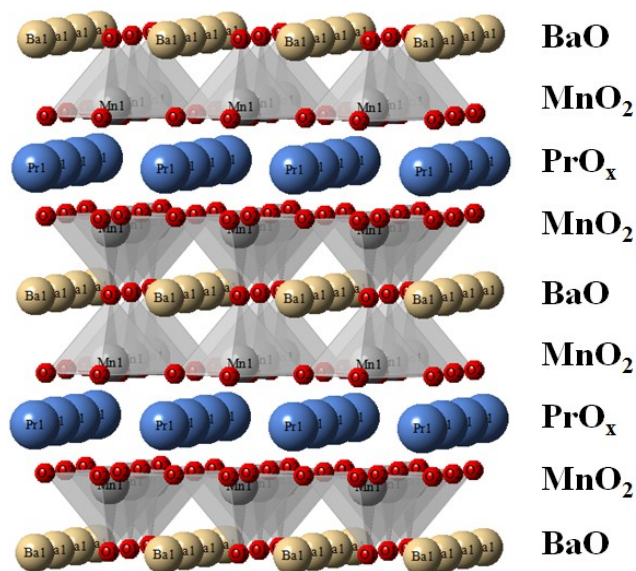


Figure 3. A schematic drawing of crystal structure model determined for A-site ordering layered PrBaMn₂O_{5+δ} (O5) and oxygen vacancy ordering in oxygen deficient O5 phase by Rietveld-refined XRD profile.

Figure 4.

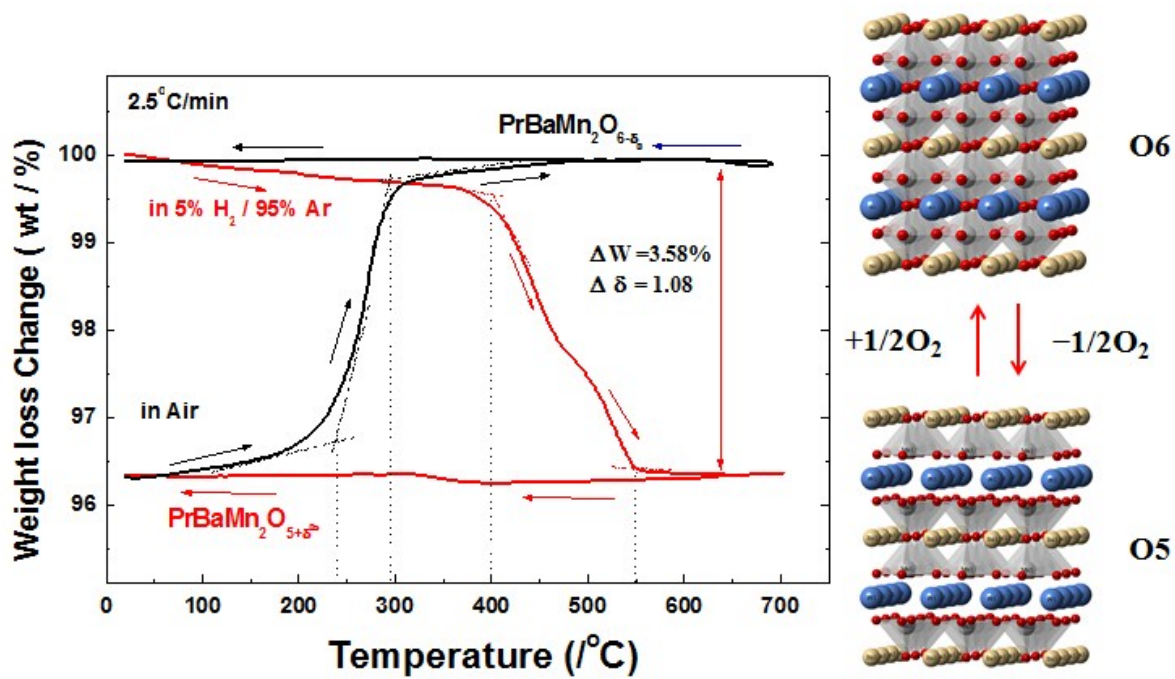


Figure 4. . TGA curves of $\text{PrBaMn}_2\text{O}_{5+\delta}$ in 5% H_2/Ar from room temperature to 700 $^{\circ}\text{C}$ to room and in re-oxidation cycle from room temperature to 700 $^{\circ}\text{C}$.

Figure 5.

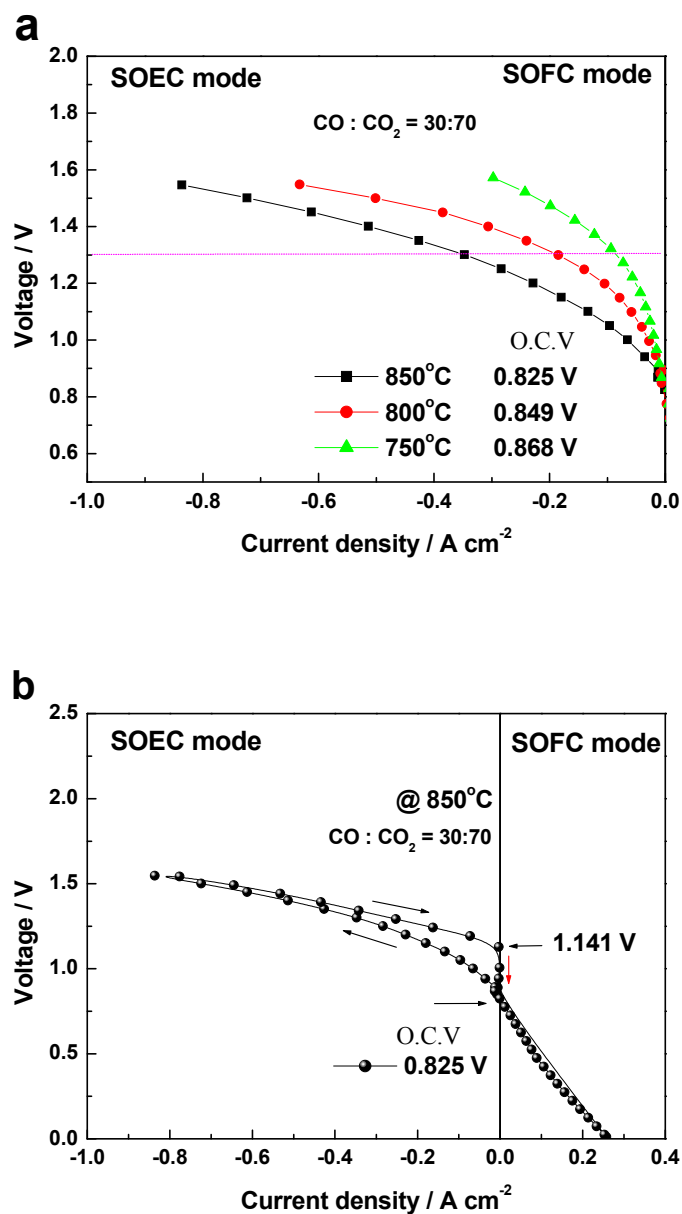


Figure 5. . (a) Temperature dependent $I-V$ curves for CO₂ electrolysis under gas feed conditions with elevating temperature (750~850°C) with the cell configuration of PrBaMn₂O_{5+δ} | LDC | La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O₃ (LSGM) | La(Sr)Fe(Co)O₃ and (b) the $I-V$ curves, voltages during steadily current cycling at 850°C.

Figure 6.

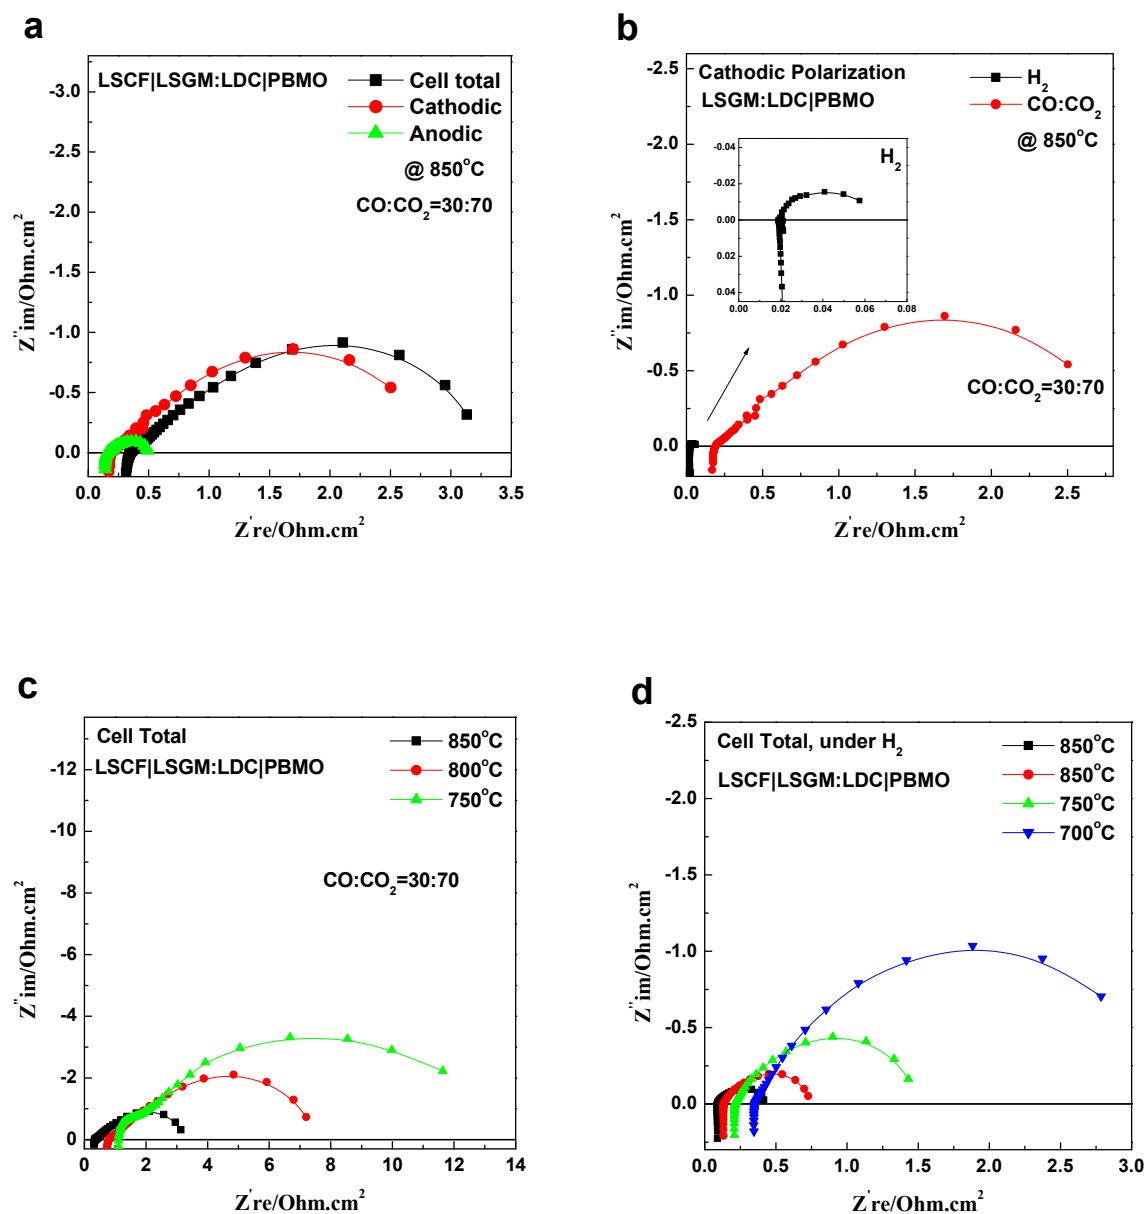


Figure 6. Nyquist plot of cell $\text{PrBaMn}_2\text{O}_{5+\delta} | \text{LDC} | \text{La}_{0.9}\text{Sr}_{0.1}\text{Ga}_{0.8}\text{Mg}_{0.2}\text{O}_3$ (LSGM) | $\text{La}(\text{Sr})\text{Fe}(\text{Co})\text{O}_3$ under open circuit : (a) impedance plot of cells, cathodic and anode under 70% vol CO_2 gas fuel condition at 850°C, (b) comparison of cathodic impedance plot under H_2 with 70% vol CO_2 , (c) temperature dependant impedance plot of the total cell under 70% vol CO_2 gas fuel, (d) temperature dependant impedance plot of the total cell under H_2 gas fuel.

Figure 7

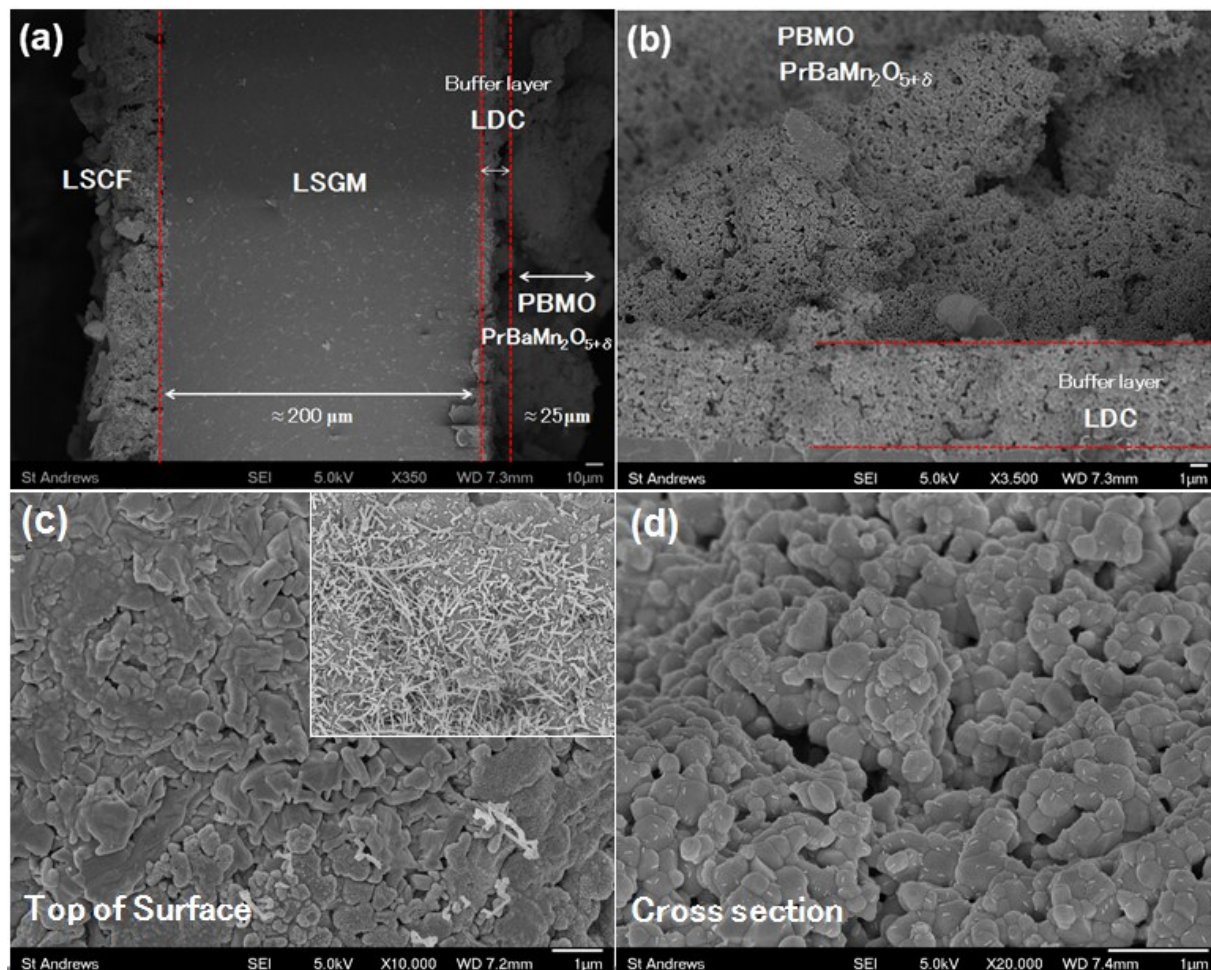


Figure 7. SEM images of a cell cell PrBaMn₂O_{5+δ} | LDC | La_{0.9}Sr_{0.1}Ga_{0.8}Mg_{0.2}O₃ (LSGM) | La(Sr)Fe(Co)O₃ after electrochemical test, a) cross section of the cell and b) cathode parts include PrBaMn₂O_{5+δ} | LDC, c) the top of surface, d) high magnification of cathode.