

Green Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/greenchem



Journal Name

COMMUNICATION

Highly efficient visible-light-driven CO₂ reduction to CO using a Ru(II)–Re(I) supramolecular photocatalyst in an aqueous solution

Received 00th January 20xx,
Accepted 00th January 20xx

Akinobu Nakada,^a Kazuhide Koike,^{b,c} Kazuhiko Maeda^a and Osamu Ishitani^{*a,c}

DOI: 10.1039/x0xx00000x

www.rsc.org/

In an aqueous solution, [Ru(dmb)₂-(BL)-Re(CO)₃Cl]²⁺ (BL = bridging ligand) most efficiently photocatalyzed reduction of CO₂ to CO under visible-light irradiation using 2-(1,3-dimethyl-2,3-dihydro-1H-benzimidazol-2-yl)benzoic acid (BI(CO₂H)H) as a water-soluble sacrificial reductant ($\Phi_{\text{CO}} = 13\%$, TON = 130). Since BI(CO₂H)H could efficiently produce one-electron-reduced species of [Ru(diimine)₃]²⁺-type complexes under visible-light irradiation even in an aqueous solution, that is one of the main reasons why the photocatalytic system induced the highly efficient CO₂ reduction. This result strongly indicates that BI(CO₂H)H should be the useful reductant for evaluating authentic abilities of various photocatalytic systems in water as well.

The photocatalytic reduction of CO₂ using water as a reductant and sunlight as an energy source is a promising technology for solving the serious problems of global warming and energy and carbon-resource shortages. Although various photocatalytic systems involving transition-metal complexes as a photosensitizer and/or a catalyst have been reported^{1, 2} besides semiconductor photocatalyst,³ most of the systems using metal complexes have been tested only in organic solvents with a sacrificial reductant. For the future practical implementation of photocatalytic reduction technology, photocatalytic reactions must proceed using water as the reductant in aqueous solution. As the first step toward this objective, efficient photocatalysts for CO₂ reduction that can function in an aqueous solution should be developed, even if they require a sacrificial reductant. Several photocatalytic systems based on a metal-complex catalyst with a [Ru(bpy)₃]²⁺-type photosensitizer (bpy = 2,2'-bipyridine) in aqueous

solutions have been tested for CO₂ reduction⁴⁻¹² and for hydrogen evolution from water¹³⁻¹⁹ in the presence of ascorbate ion (asc⁻) as a sacrificial reductant. Unfortunately, most of these systems exhibited very low efficiency, durability, and selectivity for CO₂ reduction.

Ru(II)–Re(I) supramolecular photocatalysts constructed with both a Ru photosensitizer and a Re catalyst units can efficiently and selectively reduce CO₂ to CO in a dimethylformamide (DMF) and triethanolamine (TEOA) mixed solution; they also exhibit high durability.²⁰⁻²⁶ In particular, the use of 1,3-dimethyl-2-phenyl-2,3-dihydro-1H-benzo[d]imidazole (BIH) as a sacrificial reductant achieved an extraordinarily high quantum yield of CO formation ($\Phi_{\text{CO}} = 45\%$) by suppression of the back electron transfer from one-electron-reduced species (OERS) of the photocatalyst to one-electron-oxidized species (OEOS) of the reductant because of the fast deprotonation of the OEOS.²⁵

We recently reported selective photocatalytic CO₂ reduction to formic acid in an aqueous solution using a Ru(II)–Re(I) supramolecular photocatalyst and asc⁻ as a reductant.⁴ In this system, however, the efficiency of the CO₂ reduction was much lower than that using 1-benzyl-1,4-dihydronicotinamide (BNAH) as a reductant in the DMF–TEOA mixed solution. Although asc⁻ is, to our best knowledge, the only reported reductant that can be used in aqueous solution for photocatalytic CO₂ reduction using a [Ru(bpy)₃]²⁺-type photosensitizer, back electron transfer from the reduced photosensitizer to the OEOS of asc⁻ is efficient because of the stability of the OEOS, and the final product of the oxidized ascorbate (dehydroascorbic acid) accepts the electron from the reduced photosensitizer and/or reaction intermediates.^{4, 16, 18, 19} Moreover, we observed that asc⁻ accelerated a photochemical ligand-substitution reaction of the Ru(II) photosensitizer, which caused deactivation of the photocatalytic system.⁴ These properties of asc⁻ as an inhibitor should make it difficult to evaluate the “real” photocatalytic activities of the systems constructed with such metal complexes in an aqueous solution.

^a Department of Chemistry, Graduate School of Science and Engineering, Tokyo Institute of Technology, 2-12-1-NE-1 O-okayama, Meguro-ku, Tokyo 152-8550, Japan. E-mail: ishitani@chem.titech.ac.jp; Fax: +81 3 5734 2284; Tel: +81 3 5734 2240

^b National Institute of Advanced Industrial Science and Technology, 16-1 Onogawa, Tsukuba 305-8569, Japan.

^c CREST, Japan Science and Technology Agency (JST), 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan.

† Electronic Supplementary Information (ESI) available: Experimental details, photophysical data, results of ¹³C labeling experiments, ¹H NMR observation of the reductant, and UV-vis absorption changes. See DOI: 10.1039/x0xx00000x

Herein, we report 2-(1,3-dimethyl-2,3-dihydro-1*H*-benzimidazol-2-yl)benzoic acid (BI(CO₂H)H, Chart 1) as a suitable water-soluble reductant for the photocatalytic CO₂ reduction; this reductant efficiently quenched the excited state of the Ru(II) photosensitizer unit, giving the OERS of the photosensitizer with a high yield. When this reductant was used, a Ru(II)–Re(I) supramolecular photocatalyst (**RuRe**, Chart 1) functioned as an efficient ($\Phi = 13\%$) and durable (TON = 130) photocatalyst for CO₂ reduction, selectively giving CO even in an aqueous solution.

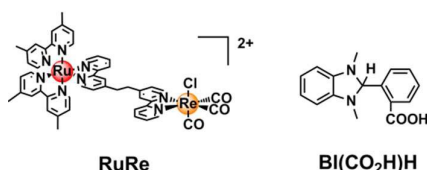


Chart 1 The Ru(II)–Re(I) supramolecular photocatalyst **RuRe** and the reductant BI(CO₂H)H used in this study.

As the first step in investigating the photocatalytic reaction, we evaluated the solubility of BI(CO₂H)H in aqueous solutions: to dissolve BI(CO₂H)H in an aqueous solution, more than an equal amount of NaOH should be added to the solution. This indicates that BI(CO₂H)H dissolves as the carboxylate ion, BI(CO₂[−])H. The pH at the equivalence point was 8.9 for 10 mM BI(CO₂H)H. Because bubbling of the solution containing BI(CO₂H)H (10 mM) with CO₂ induced precipitation of BI(CO₂H)H even in the presence of 0.1 M NaOH, the concentration of CO₂ in the solution should be controlled for the photocatalytic reaction. Suitable conditions were achieved using the following procedure: a CO₂-saturated NaOH (0.1 M) aqueous solution was mixed with the same amount of an aqueous solution containing BI(CO₂H)H (20 mM) and NaOH (0.1 M), which was bubbled with Ar, giving a solution at pH = 9.8 in which all of the added BI(CO₂H)H was completely dissolved.

In a typical run of the photocatalytic reaction, an aqueous solution containing **RuRe** (0.05 mM), BI(CO₂H)H (10 mM), NaOH (0.1 M), and CO₂ was irradiated at $\lambda_{\text{ex}} > 500$ nm using a high-pressure Hg lamp combined with a K₂CrO₄ (30% w/w, $d = 1$ cm) filter. The Ru photosensitizer unit of **RuRe** was selectively excited because BI(CO₂[−])H and the Re catalyst unit could not absorb the $\lambda > 500$ -nm light (Fig. S1, ESI[†]). The irradiation-time dependences of CO, formate, and H₂ production are shown in Fig. 1a. CO was the main product, and the turnover number of CO formation (TON_{CO}) based on the amount of photocatalyst used after 6 h of irradiation reached 130. The quantum yield of the photocatalytic CO formation was 13% under the optimized conditions using 480-nm monochromatic light (see Supporting Information). To the best of our knowledge, this value is 5.6 times greater than that of best reported for photocatalytic CO₂ reduction in an aqueous solution under visible-light irradiation.¹¹ H₂ was also produced as a by-product during irradiation with long induction periods of up to 3 h. Fig. 1b shows the UV–vis absorption spectra of the reaction solution after irradiation, where the peak at

approximately 460 nm is attributed to the MLCT absorption band of the Ru(II) unit. This result indicates that the Ru photosensitizer unit decomposed during the induction period. [Ru^{II}(bpy)₂(X)(Y)]ⁿ⁺-type complexes have been reported to function as catalysts for photocatalytic formation of H₂ in solutions containing water.²⁷ The decomposition product(s) of the Ru unit can therefore be reasonably assumed to catalyze H₂ evolution after 3 h of irradiation.

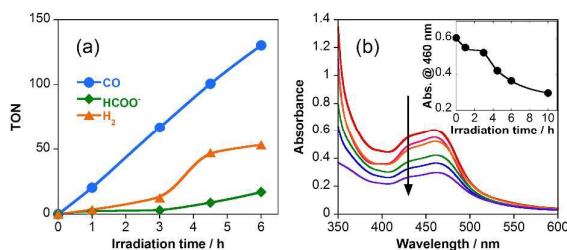


Fig. 1 (a) Time-dependent production of CO (blue), HCOO[−] (green), and H₂ (orange) in the photocatalytic reaction using **RuRe**. A 4 mL of NaOH (0.1 M) aqueous solution containing **RuRe** (0.05 mM) and BI(CO₂[−])H (10 mM) was irradiated at $\lambda_{\text{ex}} > 500$ nm under a CO₂ atmosphere. (b) UV–vis absorption changes during the photocatalytic reaction. The inset shows time-dependent absorbance changes at 460 nm.

Table 1 summarizes the results of the photocatalytic reaction and its control experiments. As previously described, the irradiation to **RuRe** in the presence of BI(CO₂[−])H under a CO₂ atmosphere photocatalytically produced CO as the main product (entry 1, Table 1). On the other hand, in the control experiments without irradiation, **RuRe**, BI(CO₂[−])H, or CO₂, i.e., under an Ar atmosphere, did not give any CO₂ reduction products (entries 2–5). Notably, much less CO was produced with larger amounts of H₂ and formate when only a mononuclear model complex of the Ru photosensitizer unit, [Ru(dmb)₂(mmb)]²⁺ (**Ru**, dmb = 4,4′-dimethyl-2,2′-bipyridine; mmb = 4-methyl-2,2′-bipyridine), was used instead of **RuRe** (entry 6). The formation of H₂ and formate is attributable to products obtained from the photocatalytic reaction system consist of **Ru** as a redox photosensitizer and the decomposition product(s) of the **Ru** as the catalyst. A mononuclear model complex of the Re catalyst unit, Re{4,4′-(CH₂PO₃H₂)₂bpy}(CO)₃Cl (**Re**), did not drive CO₂ reduction (entry 7) because **Re** cannot absorb the irradiated light. A mixed system of two mononuclear model complexes **Ru** and **Re** did not work well (entry 8). This strongly suggests that the strategy of the supramolecular photocatalysts, i.e., connecting a photosensitizer and a catalyst with an appropriate chemical bonding, is useful for constructing various efficient photocatalytic systems not only in organic solutions^{20, 24} but also in an aqueous solution.⁴

To clarify carbon sources of the produced CO and formate, we conducted ¹³CO₂ labeling experiments. GC-mass spectra (Fig. S2, ESI[†]) show carbon monoxide and formic acid and/or formate produced by the photocatalytic reactions using **RuRe** under a ¹³CO₂ (99%, 609 mmHg) atmosphere and under an ordinary CO₂ atmosphere. These results clearly indicate that 93% of CO was obtained by CO₂ reduction. On the other hand, almost no formate was produced from CO₂. The formate might

be produced by the partial decomposition of $\text{BI}(\text{CO}_2^-)\text{H}$; the oxidation products of $\text{BI}(\text{CO}_2^-)\text{H}$ are described in greater detail below. The carbonyl ligands of $\text{Re}(\text{bpy})(\text{CO})_3\text{Cl}$ have been reported to be gradually substituted by ^{13}CO during photocatalytic reduction of $^{13}\text{CO}_2$,²⁸ and the amount of ^{12}CO produced in the photocatalytic reduction was only 3.7 times the molar equivalents of **RuRe** added. Therefore, the similar


ligand exchange between the carbonyl ligands and the produced CO on the Re center should proceed in the photocatalytic reduction of $^{13}\text{CO}_2$ in the presence of **RuRe**; this exchange should be the main carbon source of the produced ^{12}CO . Another carbon source of ^{12}CO might be the contaminant, i.e., $^{12}\text{CO}_2$ in the used $^{13}\text{CO}_2$ gas (the ^{13}C content was 99%).

Table 1 Photocatalytic reaction and control experiments.^a

| entry | complex ^b | $\text{BI}(\text{CO}_2^-)\text{H}^c$ | $h\nu^d$ | CO_2 | product / μmol | | |
|-------|--|--------------------------------------|----------|---------------|---------------------------|-----------------|--------------|
| | | | | | CO | HCOO^- | H_2 |
| 1 | RuRe | o | o | o | 13.5 | 0.6 | 2.5 |
| 2 | RuRe | o | x | o | N.D. | N.D. | < 0.1 |
| 3 | RuRe | o | o | x | N.D. | N.D. | 0.5 |
| 4 | RuRe | x | o | o | N.D. | N.D. | N.D. |
| 5 | x | o | o | o | N.D. | N.D. | < 0.1 |
| 6 | Ru^e | o | o | o | 1.0 | 4.5 | 19.9 |
| 7 | Re^f | o | o | o | N.D. | N.D. | < 0.1 |
| 8 | Ru^e + Re^f | o | o | o | 1.5 | 0.4 | 1.0 |

^aFour milliliters of the reaction solutions were irradiated for 3 h. ^bThe complex concentration was 0.05 mM. ^cThe $\text{BI}(\text{CO}_2^-)\text{H}$ concentration was 10 mM. ^d $\lambda_{\text{ex}} > 500$ nm. ^e $[\text{Ru}(\text{dmb})_2(\text{mmb})]^{2+}$ (dmb = 4,4'-dimethyl-2,2'-bipyridine, mmb = 4-methyl-2,2'-bipyridine). ^f $\text{Re}(\text{4,4'-(CH}_2\text{PO}_3\text{H}_2)_2\text{bpy})(\text{CO})_3\text{Cl}$.

We evaluated the reducing power of $\text{BI}(\text{CO}_2^-)\text{H}$ in the aqueous solution using cyclic voltammetry, where irreversible oxidation waves of $\text{BI}(\text{CO}_2^-)\text{H}$ and asc^- were observed (Fig. S3, ESI[†]). The peak potential of $\text{BI}(\text{CO}_2^-)\text{H}$ was negatively shifted by 340 mV compared to that of asc^- ; therefore, $\text{BI}(\text{CO}_2^-)\text{H}$ has much stronger reducing power compared with that of asc^- , which is one of the properties that makes $\text{BI}(\text{CO}_2^-)\text{H}$ a suitable sacrificial reductant for the photocatalytic CO_2 reaction in aqueous solution. Actually, $\text{BI}(\text{CO}_2^-)\text{H}$ served as an efficient quencher of emission from the ³MLCT excited state of the Ru photosensitizer unit of **RuRe** in an aqueous solution (eq. 1 and Fig. S4, ESI[†]). The emission quenching rate constant (k_q) was determined as $4.6 \times 10^9 \text{ M}^{-1}\text{s}^{-1}$ from the slope of the linear Stern–Volmer plots (Fig. S4 inset, ESI[†]), eq. 2, and the emission lifetime of **RuRe** ($\tau_{\text{em}} = 366 \text{ ns}$, Fig. S5, ESI[†]). Notably, the k_q value was similar to the diffusion-controlled rate constant in water ($7.4 \times 10^9 \text{ M}^{-1}\text{s}^{-1}$ at 25 °C), and the k_q with ascorbate instead of $\text{BI}(\text{CO}_2^-)\text{H}$ was $2.4 \times 10^7 \text{ M}^{-1}\text{s}^{-1}$.





$$\frac{I_0}{I} = 1 + k_q\tau[\text{BI}(\text{CO}_2^-)\text{H}] \quad (2)$$


The first reduction potentials ($E^{1/2}$) of **Ru** and $\text{Re}(\text{dmb})(\text{CO})_3\text{Cl}$ measured in MeCN were -1.73 V and -1.71 V vs. Ag/AgNO_3 , respectively (Fig. S6, ESI[†]).²⁹ Therefore, the intramolecular electron transfer from the OERS of the Ru unit to the Re unit (eq. 3) should be thermodynamically favourable. Taking into account this fact and the results of the control experiments described previously, we can conclude that the CO_2 reduction proceeded on the Re unit.



¹H NMR spectra of the reaction solution (Fig. S7, ESI[†]) show that $\text{BI}(\text{CO}_2^-)\text{H}$ was converted into a two-electrons-oxidized compound $\text{BI}^+(\text{CO}_2^-)$ in 79% yield after photocatalytic reaction for 22.5 h (eq. 4). Other smaller signals possibly associated with the formation of the hydrolysis product of $\text{BI}(\text{CO}_2^-)\text{H}$ (eq. 5) were also observed. Another possible product is the fragment(s) of $\text{BI}(\text{CO}_2^-)\text{H}$ generated by the elimination of formate detected after the photocatalytic reaction.

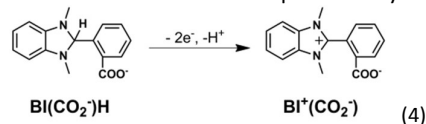

On the basis of the quantitative analysis with the ¹H NMR spectra, the amount of $\text{BI}^+(\text{CO}_2^-)$ produced was very similar to the combined amounts of CO and H_2 produced during the photocatalytic reaction (Fig. 2). This similarity clearly indicates that $\text{BI}(\text{CO}_2^-)\text{H}$ acted as a two-electron donor for the photocatalytic formation of CO and H_2 because both require two-electron reduction. Given the results of both the $^{13}\text{CO}_2$ labeling experiments and the ¹H NMR analysis, we conclude that the material balance of the photocatalytic CO formation is as shown in eq. 6:



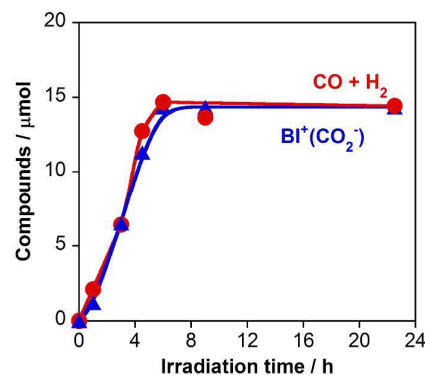


Fig. 2 Amounts of CO + H₂ (red) and BI⁺(CO₂⁻) (blue) produced during the photocatalytic reaction: A 2 mL of D₂O solution containing RuRe (0.05 mM), BI(CO₂⁻)H (10 mM), and NaOD (0.1 M) was irradiated at λ_{ex} > 500 nm under a CO₂ atmosphere.

As previously described, the photocatalysis of RuRe ($\Phi_{\text{CO}} = 13\%$, TON = 130) when BI(CO₂⁻)H was used as the reductant was substantially improved compared to the reported performance of a Ru(II)–Re(I) supramolecular system with asc⁻ ($\Phi_{\text{HCOOH}} = 0.2\%$, TON_{HCOOH} = 25). The reasons for the low photocatalytic activities in the case of asc⁻ were described in the Introduction; one of them is the efficient back electron transfer from the reduced Ru(II) photosensitizer unit to the oxidized asc⁻. To clarify the improvement of the photochemical reduction process of the Ru photosensitizer unit by BI(CO₂⁻)H, we monitored the UV–vis absorption spectral changes of an aqueous solution containing the mononuclear model complex Ru and BI(CO₂⁻)H during irradiation under an Ar atmosphere. A new absorption peak at λ_{max} = 510 nm, which is attributed to the OERS of Ru, was observed during the irradiation (Fig. S8, ESI[†]). Notably, no such accumulation of the OERS was observed in the case where asc⁻ (200 mM) was used instead of BI(CO₂⁻)H (10 mM).⁴ Because the quenching efficiencies of emission from the excited Ru photosensitizer unit in the experiments were similar in both cases (94% by 10 mM of BI(CO₂⁻)H and 87%⁴ by 200 mM of asc⁻), the efficiency of the back electron transfer from the OERS of Ru to the oxidized BI(CO₂⁻)H should be much lower compared to that in the case where asc⁻ was used. This is one of the main reasons why BI(CO₂⁻)H remarkably improved the quantum yield for CO₂ reduction compared to that achieved with asc⁻.}

Another significant difference between the cases where BI(CO₂⁻)H and asc⁻ were used is the main product of CO₂ reduction: CO in the case of BI(CO₂⁻)H and formate in the case of asc⁻. Kaneko and co-workers reported that, in the electrocatalytic CO₂ reduction with Re(bpy)(CO)₃Br as a catalyst in an aqueous solution, formic acid was the main product during the electrolysis at -1.3 V vs. SCE, whereas CO became the main product at more negative applied potentials.³⁰ This result might indicate that the electron-supply rate to the Re catalyst affects distribution of the reduction products; i.e., formate might become a main product under a slow electron-supply condition. If this is true, we can understand the difference of the main product between the

photocatalytic systems in which BI(CO₂⁻)H and asc⁻ are used as the reductants. The formation speed of the OERS of the Ru(II) photosensitizer unit was much lower in the case where asc⁻ was used than in the BI(CO₂⁻)H system, which should cause slow electron supply to the Re catalytic unit.

Conclusions

A Ru(II)–Re(I) binuclear complex exhibited high photocatalytic activity with 13% quantum yield for CO₂ reduction to CO even in aqueous solution. The new sacrificial reductant BI(CO₂⁻)H enabled the efficient production of the reduced photosensitizer unit, which allowed us to observe the real photocatalytic activities of the Ru(II)–Re(I) supramolecular photocatalyst in water. We believe that the water-suitable Ru(II)–Re(I) supramolecular photocatalyst can be used in a Z-scheme hybrid system^{31,32} with a semiconductor photocatalyst for CO₂ reduction, where water is used as an electron donor.

Acknowledgement

This work was partially supported by a Grant-in-Aid for Scientific Research on Innovative Areas “Artificial photosynthesis (AnApple)” (No. 24107005) from the Japan Society for the Promotion of Science (JSPS).

References

1. A. J. Morris, G. J. Meyer and E. Fujita, *Acc. Chem. Res.*, 2009, **42**, 1983–1994.
2. G. Sahara and O. Ishitani, *Inorg. Chem.*, 2015, **54**, 5096–5104.
3. J. Mao, K. Li and T. Peng, *Catal. Sci. Technol.*, 2013, **3**, 2481–2498.
4. A. Nakada, K. Koike, T. Nakashima, T. Morimoto and O. Ishitani, *Inorg. Chem.*, 2015, **54**, 1800–1807.
5. A. H. A. Tinnemans, T. P. M. Koster, D. H. M. W. Thewissen and A. Mackor, *Recl. Trav. Chim. Pays-Bas*, 1984, **103**, 288–295.
6. J. L. Grant, K. Goswami, L. O. Spreer, J. W. Otvos and M. Calvin, *J. Chem. Soc., Dalton Trans.*, 1987, 2105–2109.
7. C. A. Craig, L. O. Spreer, J. W. Otvos and M. Calvin, *J. Phys. Chem.*, 1990, **94**, 7957–7960.
8. E. Kimura, X. Bu, M. Shionoya, S. Wada and S. Maruyama, *Inorg. Chem.*, 1992, **31**, 4542–4546.
9. E. Kimura, S. Wada, M. Shionoya and Y. Okazaki, *Inorg. Chem.*, 1994, **33**, 770–778.
10. K. Mochizuki, S. Manaka, I. Takeda and T. Kondo, *Inorg. Chem.*, 1996, **35**, 5132–5136.
11. D. J. Boston, C. Xu, D. W. Armstrong and F. M. MacDonnell, *J. Am. Chem. Soc.*, 2013, **135**, 16252–16255.
12. N. Ikuta, S. Y. Takizawa and S. Murata, *Photochem. Photobiol. Sci.*, 2014, **13**, 691–702.
13. G. M. Brown, B. S. Brunschwig, C. Creutz, J. F. Endicott and N. Sutin, *J. Am. Chem. Soc.*, 1979, **101**, 1298–1300.
14. S. Fukuzumi, T. Kobayashi and T. Suenobu, *Angew. Chem. Int. Ed.*, 2011, **50**, 728–731.
15. Y. Sano, A. Onoda and T. Hayashi, *Chem. Commun.*, 2011, **47**, 8229–8231.

16. M. Guttentag, A. Rodenberg, R. Kopelent, B. Probst, C. Buchwalder, M. Brandstätter, P. Hamm and R. Alberto, *Eur. J. Inorg. Chem.*, 2012, **2012**, 59-64.
17. B. Shan, T. Baine, X. A. N. Ma, X. Zhao and R. H. Schmehl, *Inorg. Chem.*, 2013, **52**, 4853-4859.
18. M. Guttentag, A. Rodenberg, C. Bachmann, A. Senn, P. Hamm and R. Alberto, *Dalton Trans.*, 2013, **42**, 334-337.
19. C. Bachmann, B. Probst, M. Guttentag and R. Alberto, *Chem. Commun.*, 2014, **50**, 6737-6739.
20. B. Gholamkhash, H. Mametsuka, K. Koike, T. Tanabe, M. Furue and O. Ishitani, *Inorg. Chem.*, 2005, **44**, 2326-2336.
21. S. Sato, K. Koike, H. Inoue and O. Ishitani, *Photochem. Photobiol. Sci.*, 2007, **6**, 454-461.
22. K. Koike, S. Naito, S. Sato, Y. Tamaki and O. Ishitani, *J. Photochem. Photobiol. A: Chem.*, 2009, **207**, 109-114.
23. H. Takeda and O. Ishitani, *Coord. Chem. Rev.*, 2010, **254**, 346-354.
24. Y. Tamaki, K. Watanabe, K. Koike, H. Inoue, T. Morimoto and O. Ishitani, *Faraday Disc.*, 2012, **155**, 115-127.
25. Y. Tamaki, K. Koike, T. Morimoto and O. Ishitani, *J. Catal.*, 2013, **304**, 22-28.
26. E. Kato, H. Takeda, K. Koike, K. Ohkubo and O. Ishitani, *Chem. Sci.*, 2015, **6**, 3003-3012.
27. J.-M. Lehn and R. Ziessel, *J. Organomet. Chem.*, 1990, **382**, 157-173.
28. J. Hawecker, J.-M. Lehn and R. Ziessel, *Helv. Chim. Acta*, 1986, **69**, 1990-2012.
29. The reduction potentials of the complexes could not be measured in an aqueous solution because of competing hydrogen evolution on the working electrode.
30. T. Yoshida, K. Tsutsumida, S. Teratani, K. Yasufuku and M. Kaneko, *J. Chem. Soc., Chem. Commun.*, 1993, 631-633.
31. K. Sekizawa, K. Maeda, K. Domen, K. Koike and O. Ishitani, *J. Am. Chem. Soc.*, 2013, **135**, 4596-4599.
32. F. Yoshitomi, K. Sekizawa, K. Maeda and O. Ishitani, *ACS Appl. Mater. Interfaces*, 2015, **7**, 13092-13097.

Table of Contents

Even in an aqueous solution, a Ru(II)–Re(I) supramolecular photocatalyst worked well for CO₂ reduction. A water-soluble reductant BI(CO₂)H should be useful for evaluation of authentic abilities of various photocatalytic systems.

