

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2015,

Accepted 00th January 2015

DOI: 10.1039/x0xx00000x

www.rsc.org/

Versatile method for the synthesis of porous nanostructured thin films of conducting polymers and their composites

LingFeng Dai,^a Yuan He,^a Xiang Huang,^a Xin Cui,^a Shihui Wang,^a Dongtao Ge,^{*a} Nifang Zhao,^b Yue Li,^b Yanan Sun^a and Wei Shi^{*a}

Porous nanostructure of FeCl₃ prepared by a simple evaporation process was used simultaneously as a template and oxidant to synthesize porous nanostructured thin films of almost all major classes of conducting polymers (CPs) and their composite.

Among the numerous polymer materials that have been investigated for organic electronics, supercapacitors, biosensors, and electromagnetic shielding, conducting polymers (CPs) may be the most important ones due to their unique and attractive properties such as wide range of electrical conductivity, high mechanical flexibility and thermal stability, and more importantly, low cost.¹⁻⁶ For practical applications in aforementioned fields, CPs often need to be processed into films. However, film-forming ability of CPs is usually hindered by their poor processability. To prepare high quality CP films, various methods, including spin-coating,⁷ dip-coating,⁸ drop-coating,⁹ electrochemical deposition,¹⁰⁻¹² binary system deposition,¹³ dilute polymerization,^{14,15} Langmuir-Blodgett technique,¹⁶ and vapor phase polymerization,¹⁷⁻¹⁹ have been developed. Although all of these methods can obtain CP films, only a few of them are able to result in nanostructured film directly. In fact, nanostructured, especially porous nanostructured CP films, are highly desirable for various emerging applications in material science and nanodevices because of their high specific surface areas, which often enables a good access of ion and electron to the active surfaces and leads to an enhanced performance. Nevertheless, current existing methods for preparing nanostructured CP films, such as electrochemical deposition,²⁰⁻²² dilute polymerization,^{14,15} binary system deposition,¹³ and soft²³ and hard template-assisted method,²⁴⁻²⁶ usually have limitations ranging from limited substrate materials, time-consumption, cost effectiveness, the use of toxic organic solvents, reproducibility to lack of scalability. Therefore, a new method that can circumvent these problems, at least to some extent, is still needed.

On the other hand, from the application perspective, CP-based nanocomposite films are probably even more important than pure nanostructured CP films. To date, various nanostructured CP composite films, including CP/polymer and CP/inorganics nanocomposite films, have been prepared for applications in supercapacitors,²⁷⁻²⁹ rechargeable lithium batteries,^{30,31} artificial

muscles,³² actuators,³³ biosensors,^{34,35} organic photovoltaics³⁶ and organic light-emitting diodes.³⁷ However, to the best of our knowledge, there are no reports so far on the preparation of porous nanostructured thin films of CPs, CP/polymer composites and CP/inorganics composites respectively by using only one method.

In this communication, a simple and versatile method was developed to prepare porous nanostructured films of CPs, CP/polymer composites and CP/inorganics composites. As depicted in Fig. 1a, the method used porous nanostructure of FeCl₃ as template, which was simply prepared by solvent evaporation from FeCl₃ solution that dropped directly on to various substrates (step 1). Then the resulting FeCl₃ nanostructure simultaneously acted as a template and oxidant to initiate the polymerization of CP monomers.

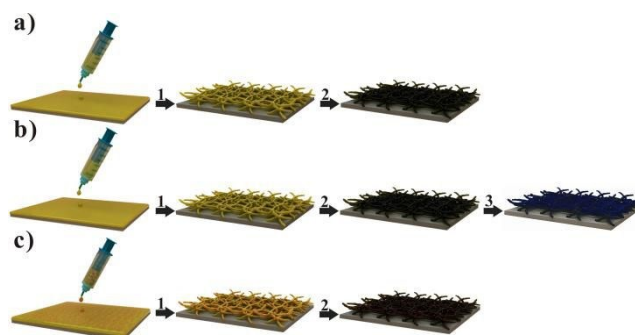


Fig. 1 Schematic representations for the formation of porous nanostructured thin films of a) CPs (step 1: evaporation of the solvent from FeCl₃ solution; step 2: polymerization of CP monomer). b) CP/polymer composites (step 1 and 2 are the same as above except that the polymerization time of the step 2 is reduced to some extent, step 3: polymerization of another monomer by the residual FeCl₃). c) CP/inorganics composites (step 1: formation of porous FeCl₃/inorganics nanocomposite by evaporation of the solvent from a solution containing FeCl₃ and inorganics, step 2: formation of porous CP/inorganics nanocomposite by using FeCl₃ that contained in FeCl₃/inorganics nanocomposite to oxidize CP monomer).

During the reaction, FeCl₃ was gradually consumed and the porous nanostructure of CP reproduced and replaced the FeCl₃ nanostructure (step 2). For obtaining porous CP/polymer nanocomposite film (Fig. 1b), the step 2 should be paused after a certain period of time, the residual FeCl₃ could be further used to

initiate the polymerization of another monomer, thus resulting in the formation of the CP/polymer nanocomposite film (step 3). For preparing CP/inorganics nanocomposite film, as shown in Fig. 1c, the desired inorganics could be introduced during the step 1 by dissolving them in the FeCl_3 solution. After evaporating the solvent, porous nanostructured FeCl_3 /inorganics composite film was obtained (step 2). Then the composite film was used as template and oxidant to further oxidize the monomers of CPs. With the consuming of the FeCl_3 , CP/inorganics composite film was formed (step 3). Therefore, three kinds of important CP related porous nanostructured thin films, i.e., CP films, CP/polymer composite film, and CP/inorganics composite film, could be prepared using this method. This versatility, plus other obvious advantages, such as simple and cost-effective formation process of FeCl_3 template, no limitation of substrate materials, without the use of toxic organic solvent, and easy to scale up, make this method very attractive in preparing high quality and multifunctional CP related nanostructured thin films for various practical applications.

It is well known that FeCl_3 is a commonly used oxidant for preparing a large number of CP nanostructures.³⁸⁻⁴⁵ However, as far as we know, there are no reports to date on using porous FeCl_3 nanostructure as a CP nanomaterial template. In fact, template-assisted synthesis is probably the most important method for the synthesis of CP nanostructures, but often requires harsh reaction conditions to remove hard-templates such as anodic aluminium oxide (AAO).²⁴⁻²⁶ In the present work, porous nanostructured FeCl_3 was used as both oxidant and template, this effect conveniently results in its simultaneous reduction to FeCl_2 , which is easily dissolved in water. Therefore, no harsh template-removal conditions were required. Furthermore, FeCl_3 is cheap and easy to obtain, which are essential features for a template that can be used only once.

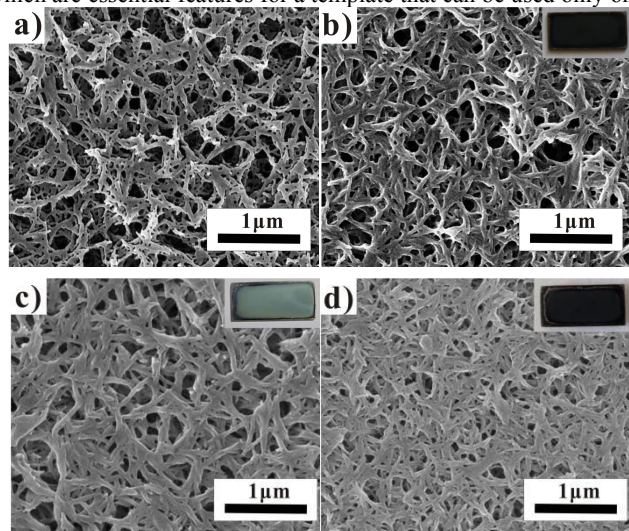


Fig. 2 a) SEM image of the porous nanostructured FeCl_3 thin film obtained by evaporating ethanol from 0.05 M ethanol solution of FeCl_3 at 45 °C. b) SEM image of the porous nanostructured PPy thin film obtained by exposure of the nanostructured FeCl_3 (in Fig. 2a) to pyrrole vapor at 60 °C for 1 h (inset: digital photo of PPy film on titanium). c) SEM image of porous nanostructured PANI thin film obtained by exposure of the nanostructured FeCl_3 to aniline vapor at 60 °C for 1 h (inset: digital photo of PANI film on titanium). d) SEM image of porous nanostructured PEDOT thin film obtained by exposure of the nanostructured FeCl_3 to EDOT vapor at 60 °C for 1 h (inset: digital photo of PEDOT film on titanium).

Considering these factors, we suppose the nanostructured FeCl_3 we prepared is a desirable template for the synthesis of porous nanostructured thin films of CPs and CP composites.

Porous nanostructured FeCl_3 thin film can be formed by evaporation of ethanol from ethanol solution of FeCl_3 that dropped on various substrate materials. Fig. 2a shows the SEM image of the

FeCl_3 film's surface microstructure on metal titanium substrate. The film had a homogeneous, fine-porous network nanostructure comprising branches of ~90nm thickness. Energy dispersive X-ray spectroscopy (EDS) revealed the structure contained only Fe and Cl elements (Fig. S1, ESI[†]), confirming the formation of FeCl_3 film. To study the formation mechanism of the FeCl_3 porous nanostructure, the effects of drying temperature and FeCl_3 concentration on the FeCl_3 morphology were investigated. We found no homogeneous porous nanostructures formed at drying temperatures below 30 °C (Fig. S2, ESI[†]). However above 60 °C, FeCl_3 film with dendritic morphology was formed that easily fractured (Fig. S3, ESI[†]), and only between 40 to 50 °C could porous nanostructured morphologies with homogeneous pores be prepared (Fig. S4, ESI[†]). On the other hand, at a fixed drying temperature of 45 °C, the nanostructure backbone thickness increased from ~90 to 130 nm with increasing of FeCl_3 concentration from 0.05 to 0.10 M (Fig. S5, ESI[†]). Based on the above, we suggest that solvent evaporation plays a key role in the formation of the porous FeCl_3 nanostructure. During the evaporation process, the flow of the generated ethanol steam creates the porous FeCl_3 nanostructure. The porosity varied with the amount of ethanol steam (determined by drying temperature) and FeCl_3 concentration, i.e. when both were low, lower porosity of thicker-branched FeCl_3 nanostructure was obtained. Since the CP nanostructure was obtained by replication of the porous FeCl_3 nanostructure, the ability to adjust FeCl_3 nanostructure by temperature and concentration offers an important means for controlling CP nanostructure morphology.

Because FeCl_3 is highly water soluble, the CP synthesis step could not be carried out in aqueous solution. Therefore, we used chemical vapor deposition (CVD) to synthesize CP using polypyrrole (PPy) synthesis as the first example. Polymerization of pyrrole was initiated by exposing the porous FeCl_3 nanostructure to pyrrole vapor at 60 °C. Fig. 2b shows the SEM image of the porous PPy nanostructure synthesized using the FeCl_3 shown in Fig. 2a for a template. The obtained PPy closely maintained the original morphology of the FeCl_3 nanostructure. The FTIR spectrum of the porous PPy nanostructure (Fig. S6, ESI[†]) shows the characteristic PPy peaks such as the asymmetric and symmetric ring stretching at 1560 and 1471 cm^{-1} , the C–N stretching vibration at 1197 cm^{-1} , and C–C out-of-plane ring deformation vibration at 927 cm^{-1} , which collectively confirm the formation of PPy. The conductivity of the porous PPy nanostructure was measured to be ~0.3 S cm^{-1} using four-probe technique at room temperature. In addition, analysis of the surface wettability of the porous PPy nanostructure revealed superhydrophilic behavior, where the contact angle of a water droplet on PPy surface was almost 0° (Fig. S7, ESI[†]). It should be pointed out that surface wettability of the PPy film is important for practical applications, particularly in promoting immobilization of hydrophilic probe molecule in sensors and enhancing the penetration and diffusion ability through the film in energy storage/conversion systems. Therefore, it is envisaged that the porous nanostructured PPy thin film may find applications in biosensors and energy storage systems.

As mentioned earlier, FeCl_3 is commonly used as an oxidant to polymerize the monomers of various CPs. The present study also established that similar porous nanostructures of polyaniline (PANI) and poly (3,4-ethylenedioxythiophene) (PEDOT) were obtainable on titanium substrates using the FeCl_3 template method (Fig. 2c and d), the formation of which was confirmed by FTIR spectra (Fig. S8, ESI[†]). The conductivity of the porous nanostructured films of PANI and PEDOT were ~0.8 and ~0.2 S cm^{-1} , respectively. These results show the method provides a general route for preparing porous nanostructures of almost all major classes of CPs.

Currently, CP nanostructures are usually formed electrochemically on the surface of conductive substrates, or chemically in the body of the solution.^{46,47} In the present work, the porous nanostructure of FeCl₃ can be coated directly on various substrate materials regardless of their conductivity, and thus so can the porous CP nanostructure. We have successfully deposited porous nanostructured PPy thin films on a large variety of substrates, including conducting substrates (for example, titanium, Au-coated Si wafer, and Si wafer) and non-conducting substrates (for example, glass, polyethylene terephthalate (PET), poly (phenylene sulfide) (PPS)) using the FeCl₃-templated method (Fig 3, 4 and Fig. S9, ESI †). There is no apparent difference in the coating morphology for either conductive or non-conducting substrates. Therefore, we suppose that the FeCl₃-templated method is a simple and versatile method for the deposition of almost any CP film on almost any substrate. Interestingly, the PPy nanostructured film formed on PET substrate could be easily bent (Fig. 3), exhibiting excellent flexibility. This property renders the PPy coating suitable for potential applications in flexible electronics.

It is obvious that the thickness of the CP film depends on the thickness of the FeCl₃ layer. Therefore, transparent CP films should be obtained by forming a thinner layer of FeCl₃ nanostructure. Fig. 4a shows the digital photo of the transparent PPy film that coated on coverslip glass. It was measured by UV/Vis spectroscopy that the PPy film has a greater than 90% light transmittance within the visible region (Fig. 4b). The transparency of the PPy film is also demonstrated by the clearly visible Xiamen University logo placed under the glass coverslip. The conductivity of the PPy transparent film was measured to be about 1 S cm⁻¹, which is sufficient for applications in electrostatic dissipation, magnetics shielding, and secondary electrodes. Such conducting, transparent film has great implications for potential applications in flexible organic electronics, optoelectronics, sensors, and energy storage devices.

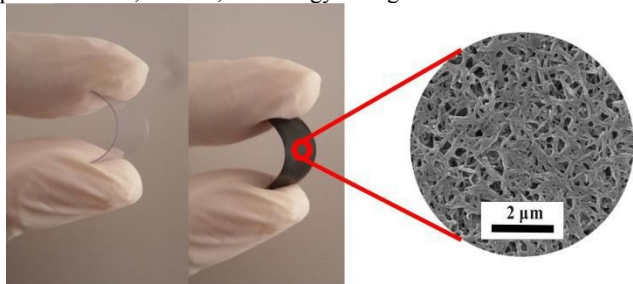


Fig. 3 Photo of the PET substrate and the PPy film formed on it (left) and SEM image of the microstructure of the PPy film (right).

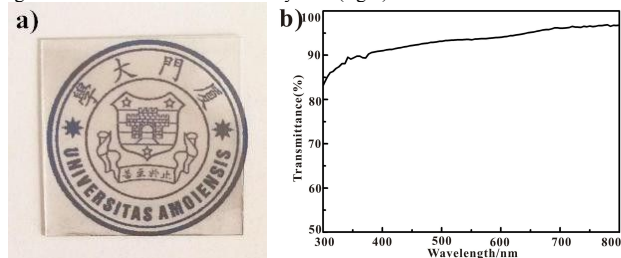


Fig. 4 a) Digital photo of the transparent nanostructured PPy thin film coated on glass coverslip. b) UV/Vis-spectroscopy of transparent nanostructured PPy thin film coated on coverslip glass.

Besides porous nanostructured CP film, porous CP/polymer nanocomposite film also can be prepared by using FeCl₃ nanostructure as oxidant to oxidize two different monomers successively. Fig. 5a exhibits the SEM image of microstructure of PPy/PEDOT nanocomposite film, which was prepared by using FeCl₃ to first oxidize pyrrole vapor to PPy and then EDOT vapor to

PEDOT. The FTIR spectrum (Fig. S10a, ESI †) confirms the formation of the PPy/PEDOT. To further prove the versatility of the method for the preparation of CP/polymer nanocomposite, another interesting polymer, polydopamine (PDA) was incorporated into PPy to form porous PPy/PDA nanocomposite film. Fig. 5b shows the SEM image of porous PPy/PDA film, which was synthesized by first oxidizing vapor of pyrrole monomers to PPy and then oxidizing dopamine monomers in aqueous solution to PDA. The FTIR spectrum proves the formation of the PPy/PDA (Fig. S10b, ESI †). Recently, PDA has been intensively investigated as functional coating for numerous applications due to its ability to adhere to wide range of organic and inorganic materials.^{48,49} However, few reports focus on the formation of CP/PDA nanocomposites. Here, we show that the CP/PDA nanocomposite film can be prepared easily by the present FeCl₃-template method. It is well known that PPy has good conductivity and biocompatibility, but is difficult to be modified due to the lack of specific interaction on the surface. While the additional functional groups from PDA can address this problem easily. Therefore, the combination of PDA with PPy significantly improves the processability and functionality of PPy, making the porous PPy/PDA nanocomposite film very attractive for potential applications in biomedical science and organic electronics.

Finally, we demonstrate the introduction of CaCl₂ into PPy as an example to illustrate the formation of the porous CP/inorganics nanocomposite film. Porous FeCl₃/CaCl₂ composite nanostructure (Fig. 6a) was obtained by evaporating ethanol from a solution containing specified amounts of dissolved FeCl₃ and CaCl₂. The presence of CaCl₂ in the resultant template nanostructure was confirmed by EDS (Fig. 6b), and fine porous nanostructured morphologies were produced with CaCl₂ content as high as 30 wt.%. Fig. 6c shows the SEM image of the obtained PPy/CaCl₂ nanocomposite, where exposure of the CaCl₂/FeCl₃ nanocomposite to the pyrrole vapor for 1 h still produced the desired porous nanostructured morphology.

During the past decade, biomedical applications for PPy have attracted much attention.⁵⁰⁻⁵² A promising example is the use of PPy as a coating material for dental and orthopedic implants.^{53,54} However, PPy exhibits poor osteoconductive properties and thus does not bond directly to living bone; this impedes patient healing and might ultimately result in long-term failure of the implant. Introduction of Ca²⁺ to the implants has proved an effective way to increase its osteoconductivity,⁵⁵⁻⁵⁷ where Ca²⁺ induces the deposition of apatite on the implant surface and promotes attachment and proliferation of osteoblasts, and superior osseointegration bonding between implant and bone.⁵⁸⁻⁶⁰ However, since PPy is insoluble and infusible, it is difficult to introduce Ca²⁺ into PPy nanostructure by conventional methods.

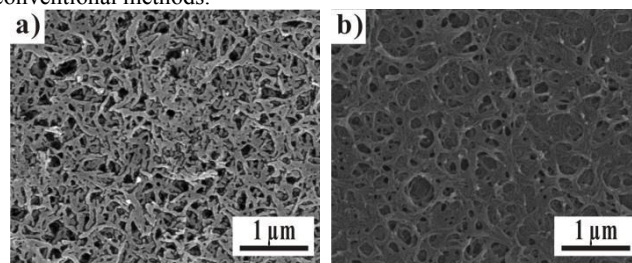


Fig. 5 SEM images of the porous nanostructured thin film of a) PPy/PEDOT and b) PPy/PDA.

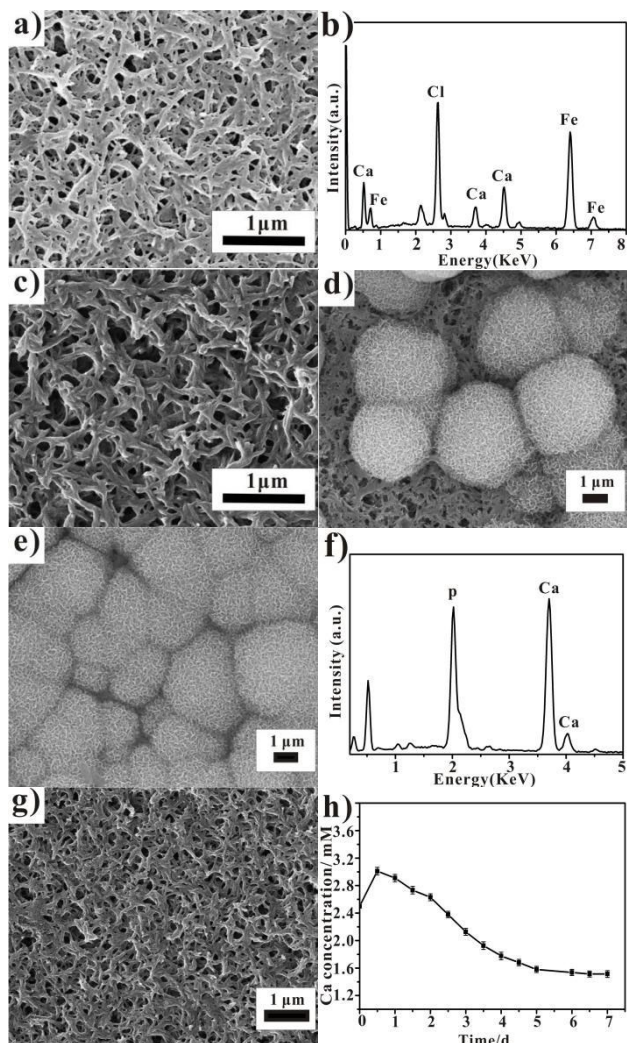


Fig. 6 (a) SEM image of the porous nanostructured thin film of $\text{FeCl}_3/\text{CaCl}_2$ composite (with wt.10% of CaCl_2). (b) EDS spectrum of $\text{FeCl}_3/\text{CaCl}_2$ nanocomposite thin film in Fig. 3a. (c) SEM image of the porous nanostructured thin film of PPy/CaCl_2 composite. (d) apatite particles formed on PPy/CaCl_2 nanocomposite after soaking in SBF for 48 h. (e) apatite particles formed on PPy/CaCl_2 nanocomposite after soaking in SBF for 96 h. (f) EDS spectrum of the apatite particles in Fig. 3e. (g) SEM image of the PPy nanostructure without CaCl_2 after soaking in SBF for 120 h. (h) variation in Ca^{2+} concentration of SBF with soaking of porous PPy/CaCl_2 nanostructured thin film.

In the present work, introduction of Ca^{2+} into the porous PPy nanostructure to form PPy/CaCl_2 nanocomposite was easily accomplished. To evaluate its apatite-forming ability, the PPy/CaCl_2 nanocomposite was soaked in simulated body fluid (SBF).⁶¹⁻⁶³ Fig. 6d and e shows the SEM images of the PPy/CaCl_2 nanocomposite surface after soaking in SBF for 48 and 96h respectively. As shown in Fig. 6d, after 48 h, some of the PPy/CaCl_2 nanocomposite surface became covered by spherical particles, and after 96 h, the whole surface was completely covered (Fig. 6e). EDS results indicated that the particles predominantly contained calcium and phosphorus (Fig. 6f) and the ratio of Ca/P was 1.2, thus confirming the particles were bone-like apatite. Notably, no apatite particles formed on porous PPy nanostructure lacking CaCl_2 even after soaking in SBF for 120 h (Fig. 6g). Concentration of Ca^{2+} was monitored by inductively coupled plasma mass spectrometry (ICP-MS) after the PPy/CaCl_2 nanostructure was placed in SBF. Fig. 6h shows Ca^{2+} concentration first increased and then decreased gradually until a steady state was reached. The increase of the Ca^{2+} was ascribed to the release of Ca^{2+} from the PPy/CaCl_2 nanostructure to the SBF, and the following

decrease of Ca^{2+} to the deposition of apatite from SBF to the surface of the nanostructure film. Therefore, we reasonably postulate that the introduction of CaCl_2 to PPy produced pronounced apatite-forming ability. Noted that besides CaCl_2 , other inorganics also might be introduced into FeCl_3 to establish more kinds of porous CP/inorganics nanocomposite films.

Conclusions

In summary, we have developed an attractive oxidative template method for synthesizing CP-based porous nanostructured thin films. Porous nanostructure of one of the most commonly used oxidants for CP monomers, FeCl_3 , was used for the first time as template to accomplish the synthesis. Compared to other methods, our method offers following advantages. First, FeCl_3 is cheap and easy to obtain, which are essential features for a template that can be used only once. In addition, the formation process of nanostructured FeCl_3 template is short and simple, involving only physical evaporation and no additional chemical reactions. Second, it is a general method to prepare porous nanostructured thin films of almost all major classes of CPs on almost any substrate. Third, besides porous nanostructured CP films, porous nanostructured thin films of CP/polymer and CP/inorganics composites also can be formed, making the FeCl_3 -template method to be the only method so far for simultaneously preparing three kinds of CP-based porous nanostructured thin films, i.e. porous CP, CP/polymer, and CP/inorganics nanostructured thin films. We believe this versatile method could significantly broaden our ability to obtain porous nanostructured thin films of CP and CP-based nanocomposites for use in various fields such as organic electronics, energy storage devices, and biomedical science.

Notes and references

^aDepartment of Biomaterials, College of Materials, Xiamen University, Xiamen, 361005, China, Tel&Fax: +86 592 2188502. Email address: gedi@xmu.edu.cn; shiwei@xmu.edu.cn

^bDepartment of Materials Science and Engineering, College of Materials, Xiamen University, Xiamen, 361005, China.

Electronic Supplementary Information (ESI) available: Experimental section and data section, which includes EDS spectrum of FeCl_3 , SEM images of FeCl_3 nanostructures obtained at different conditions, digital photos of PPy thin films on various substrates, contact angle of water on PPy nanostructured film, FTIR spectra of PPy, PANI, PEDOT, PPy/PEDOT and PPy/PDA. See DOI: 10.1039/c000000x/

Acknowledgments

This work was supported by the National Nature Science Foundation of China (31271009, 81271689), the Fundamental Research Funds for the Central Universities (No. 2011121001), the Natural Science Foundation of Fujian Province (2011J01331), and the Program for New Century Excellent Talents in University, and the Program for New Century Excellent Talents in Fujian Province University.

- 1 A. Facchetti, *Chem. Mater.*, 2011, 23, 733-758.
- 2 G. A. Snook, P. Kao, and A. S. Best, *J. Power Sources*, 2011, 196, 1-12.
- 3 M. Gerard, A. Chaubey, and B. D. Malhotra, *Biosens. Bioelectron.*, 2002, 17, 345-359.

- 4 P. Saini and M. Arora, *New Polymers for Special Applications*, ed. A. D. Gomes, Intech, Croatia, 2012, 71-112.
- 5 P. Saini, V. Choudhary, N. Vijayan and R.K. Kotnala, *J. Phys. Chem C*, 2012, 116, 13403-13412.
- 6 P. Saini, M. Arora, G. Gupta, B. K. Gupta, V. N. Singh and V. Choudhary, *Nanoscale*, 2013, 5, 4330-4346.
- 7 M. L. Machala, L. Muller-Meskamp, S. Gang, S. Olthof, and K. Leo, *Org. Electron.*, 2011, 12, 1518-1526.
- 8 Z. Y. Hu, J. J. Zhang, S. Z. Xiong, and Y. Zhao, *Org. Electron.*, 2012, 13, 142-146.
- 9 C. T. Li, C. P. Lee, Y. Y. Li, M. H. Yeh, and K. C. Ho, *J. Mater. Chem. A*, 2013, 1, 14888-14896.
- 10 X. Y. Cui, J. F. Hetke, J. A. Wiler, D. J. Anderson, and D. C. Martin, *Sensor. Actuat. A-phys.*, 2001, 93, 8-18.
- 11 X. Luo and X. T. Cui, *Acta. Biomater.*, 2011, 7, 441-446.
- 12 A. Baba and W. Knoll, *Adv Mater.*, 2003, 15, 1015-1019.
- 13 J. M. D'Arcy, H. D. Tran, V. C. Tung, A. K. Tucker-Schwartz, and R. P. Wong, *PNAS*, 2010, 107, 19673 - 19678.
- 14 N. R. Chiou, C. Lu, J. Guan, L. J. Lee, and A. J. Epstein, *Nat. Nanotechnol.*, 2007, 2, 354-357.
- 15 N. R. Chiou and A. J. Epstein, *Adv. Mater.*, 2005, 17, 1679 - 1683.
- 16 S. Yang, L. Fan, and S. Yang, *J. Phys. Chem. B*, 2004, 108, 4394 - 4404.
- 17 J. M. D'Arcy, M. F. El-Kady, P. P. Khine, L. H. Zhang, S. H. Lee, N. R. Davis, D. S. Liu, M. T. Yeung, S. Y. Kim, and C. L. Turner, *ACS Nano*, 2014, 8, 1500-1510.
- 18 J. P. Lock, S. G. Im, and K. K. Gleason, *Macromolecules*, 2006, 39, 5326-5329.
- 19 J. L. Yagüe, A. M. Coclite, C. Petruczuk, and K. K. Gleason, *Macromol. Chem. Phys.*, 2013, 214, 302-312.
- 20 F. Hui, B. Li, P. G. He, J. Hu, and Y. Z. Fang, *Electrochem. Commun.*, 2009, 11, 639-642.
- 21 M. Li, Z. X. Wei, and L. Jiang, *J. Mater. Chem.*, 2008, 18, 2276-2280.
- 22 W. Shi, P. F. Liang, D. T. Ge, J. X. Wang, and Q. Q. Zhang, *Chem. Commun.*, 2007, 2414-2416.
- 23 P. Saini and M. Arora, *J. Mater. Chem. A*, 2013, 1, 8926-8934.
- 24 W. Shi, Y. Y. Ma, D. T. Ge, and H. R. Jiang, *J. Membrane. Sci.*, 2010, 354, 86-92.
- 25 K. Wang, H. P. Wu, Y. N. Meng, and Z. X. Wei, *Small*, 2014, 10, 14 - 31.
- 26 H. D. Tran, D. Li, and R. B. Kaner, *Adv Mater.*, 2009, 21, 1487-1499.
- 27 W. Lei, P. He, S. S. Zhang, F. Q. Dong, and Y. J. Ma, *J. Power. Sources*, 2014, 266, 347-352.
- 28 S. H. Li, D. K. Huang, J. C. Yang, B. Y. Zhang, X. F. Zhang, G. Yang, M. K. Wang, and Y. Shen, *Nano. Energy*, 2014, 9, 309-317.
- 29 G. A. Snook, P. Kao, and A. S. Best, *J. Power Sources*, 2011, 196, 1-12.
- 30 Y. Kiya, A. Iwata, T. Sarukawa, J. C. Henderson, and H. D. Abruna, *J. Power Sources*, 2007, 173, 522-530.
- 31 M. M. Sun, S. C. Zhang, T. Jiang, L. Zhang, and J. H. Yu, *Electrochem Commun.*, 2008, 10, 1819-1822.
- 32 W. Zheng, J. M. Razal, P. G. Whitten, R. Ovalle-Robles, G. G. Wallace, R. H. Baughman, and G. M. Spinks, *Adv. Mater.*, 2011, 23, 2966-2970.
- 33 A. Liu, L. Zhao, H. Bai, H. X. Zhao, X. H. Xing, and G. Q. Shi, *ACS. Appl. Mater. Inter.*, 2009, 1, 951-955.
- 34 S. Brahim, D. Narinesingh, and A. Guiseppi-Elie, *Biosens. Bioelectron.*, 2002, 17, 53-59.
- 35 Y. C. Tsai, S. C. Li, and S. W. Liao, *Biosens. Bioelectron.*, 2006, 22, 495-500.
- 36 J. D. Kwon, P. H. Kim, J. H. Keum, and J. S. Kim, *Sol. Energ. Mat. Sol. C.*, 2004, 83, 311-321.
- 37 J. P. Singh, U. Saha, R. Jaiswal, R. S. Anand, A. Srivastava, and T. H. Goswami, *J. Nanopart. Res.*, 2014, 16:2693.
- 38 C. R. Martin, L. S. Van Dyke, Z. H. Cai, and W. B. Liang, *J. Am. Chem. Soc.*, 1990, 112, 8976-8977.
- 39 H. J. Ding, M. X. Wan, and Y. Wei, *Adv. Mater.*, 2007, 19, 465-469.
- 40 Y. Zhu, D. Hu, M. X. Wan, L. Jiang, and Y. Wei, *Adv. Mater.*, 2007, 19, 2092-2096.
- 41 M. Ikegame, K. Tajima, and T. Aida, *Angew. Chem. Int. Ed.*, 2003, 42, 2154-2157.
- 42 J. Li, H. Q. Tang, A. Q. Zhang, X. T. Shen, and L. H. Zhu, *Macromol. Rapid Commun.*, 2007, 28, 740-745.
- 43 M. Chen, X. L. Fang, S. H. Tang, and N. F. Zheng, *Chem. Commun.*, 2012, 48, 8934-8936.
- 44 M. J. Antony and M. Jayakannan, *J. Phys. Chem. B*, 2007, 111, 12772-12780.
- 45 N. Nuraje, K. Su, N. Yang, and H. Matsui, *ACS nano*, 2008, 2, 502-506.
- 46 C. Li, H. Bai, and G. Q. Shi, *Chem. Soc. Rev.*, 2009, 38, 2397 - 2409.
- 47 M. X. Wan, *Adv. Mater.*, 2008, 20, 2926-2932.
- 48 H. Lee, S. M. Dellatore, W. M. Miller, and P. B. Messersmith, *Science*, 2007, 318, 426-430.
- 49 M. E. Lyng, R. van der Westen, A. Postma, and B. Städler, *Nanoscale*, 2011, 3, 4916-4928.
- 50 N. K. Guimard, N. Gomez, and C. E. Schmidt, *Prog. Polym. Sci.*, 2007, 32, 876-892.
- 51 R. Ravichandran, S. Sundarajan, J. R. Venugopal, S. Mukherjee, and S. Ramakrishna, *J. R. Soc. Interface*, 2010, 7, 559-579.
- 52 S. Nambiar and J. T. W. Yeow, *Biosens. Bioelectron.*, 2011, 26, 1825-1832.
- 53 E. D. Giglio, M. R. Guascito, L. Sabbatini, and G. Zambonin, *Biomaterials*, 2001, 22, 2609-2616.
- 54 S. Sirivisoort, R. Pareta, and T. J. Webster, *Nanotechnology*, 2011, 22, 085101.
- 55 T. Kawaia, C. Ohtsukia, M. Kamitakaharaa, T. Miyazakib, M. Taniharaa, Y. Sakaguchic, and S. Konagaya, *Biomaterials*, 2004, 25, 4529-4534.
- 56 T. Miyazaki, M. Imamura, E. Ishida, M. Ashizuka, and C. Ohtsuki, *J. Mater. Sci. Mater. Med.*, 2009, 20, 157-161.
- 57 I. A. Kim and S. H. Rhee, *J. Biomater. Sci. Polym. Ed.*, 2010, 21, 1127-1141.
- 58 K. L. Kilpadi, P. L. Chang, and S. L. Bellis, *J. Biomed. Mater. Res.*, 2001, 57, 258-267.
- 59 K. M. Woo, J. Seo, R. Zhang, and P. X. Ma, *Biomaterials*, 2007, 28, 2622-2630.
- 60 H. Yuan, Y. Li, J. D. de Bruijn, K. de Groot, and X. Zhang, *Biomaterials*, 2000, 21, 1283-1290.
- 61 T. Kokubo, *Biomaterials*, 1991, 12, 155-163.
- 62 T. Kokubo and H. Takadama, *Biomaterials*, 2006, 27, 2907-2915.
- 63 A. Oyane, H. M. Kim, T. Furuya, T. Kokubo, T. Miyazaki, and T. Nakamura, *J. Biomed. Mater. Res.*, 2003, 65A, 188-195.