

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## ARTICLE

# Visible light driven photocatalytic elimination of organic- and microbial pollutions by rutile-phase titanium dioxides: new insights on the dynamic relationship between morpho-structural parameters and photocatalytic performance

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

G. Veréb<sup>1,2,\*</sup>, T. Gyulavári<sup>1</sup>, Zs. Pap<sup>1,3,4</sup>, L. Baia<sup>4,5</sup>, K. Mogyorósi<sup>1</sup>, A. Dombi<sup>1</sup>, K. Hernádi<sup>1,6</sup>,

The characteristic properties and the resulted photocatalytic efficiencies of rutile-phase titanium dioxides were investigated in the present study. A series of rutile with different primary particle sizes (5.2-290 nm) were produced by a sol-gel method followed by calcination and were characterized by XRD, DRS, TEM, XPS, EPR, IR and N<sub>2</sub> adsorption. Their photocatalytic efficiencies were determined in the decomposition of phenol, and in the inactivation of *E. coli* bacteria under visible light irradiation. The results were compared with the photocatalytic performance of commercial Aldrich rutile and Aeroxide P25 powders. Of the non-commercial products, the TiO<sub>2</sub> with the smallest particle size displayed the highest efficiency, while the surface-normalized photocatalytic performance was significantly higher for the larger rutile particles. This can be explained by the red shift of light absorption at higher calcination temperatures. Although Aldrich rutile and the corresponding laboratory-made photocatalyst exhibited similar structural features (e.g. particle size, specific surface area, morphology and light absorption), the latter proved to be less efficient despite its Ti<sup>3+</sup> content (while Aldrich rutile contains only Ti<sup>4+</sup>). The main reason of much higher photocatalytic performance was the presence of Ti-O-O- entities on the surface of Aldrich rutile. On the basis of these results, in the case of rutile-phase titanium dioxide, the presence of Ti-O-O- entities was more beneficial, than the presence of Ti<sup>3+</sup> and low-binding-energy oxygen (which indicates defects) in relation with the photocatalytic performance under visible light irradiation.

## 1. Introduction

Photocatalysis is a promising and environmentally friendly approach in water-, air- and surface cleaning technologies. The most widely investigated semiconductor is TiO<sub>2</sub><sup>1-3</sup>, which occurs in three different crystal forms: anatase, rutile and brookite (in theoretical studies fluorite - as a highly visible light active phase - is also mentioned<sup>4,5</sup>). Anatase is described often as the most active phase<sup>6-8</sup>, and therefore it is the most widely investigated one, although it can be excited only by UV photons (the band gap for anatase is 3.2 eV (~387 nm) for rutile is 3.02 eV (~410 nm)<sup>9</sup>). On the other hand rutile is more stable<sup>6,10</sup>, can be efficient in visible light induced photocatalytic processes<sup>6,10-12</sup> because of the lower band gap and can be more efficient than anatase in photocatalytic disinfection processes as it is described by *Caratto et al.*<sup>13</sup>. In our previous publication<sup>14</sup>

Aldrich rutile also showed much higher disinfection performance (under visible light irradiation) than commercial, anatase-phase, doped titanium dioxide (Kronos VLP7000), which has significantly higher performance in photocatalytic decomposition of phenol. The high disinfection performance of rutile grows the potential of utilization of this phase for indoor air- and surface cleaning processes. However, the size-dependence and desired surface specificities has not been investigated in details in the literature.

Aldrich rutile demonstrated the mentioned high disinfection property<sup>14</sup> despite its large average primer particle size (~315 nm) and very low (3 m<sup>2</sup>g<sup>-1</sup>) specific surface area. Generally high specific surface area is preferred in photocatalytic processes, but Amano and Nakata<sup>15</sup> described an improved photocatalytic activity for large rutile particles, which was

explained by the increased lifetime of the photogenerated charge carriers. Large particle size can also be beneficial in disinfection processes, although no clear experimental evidences can be found in the literature.

The main aim of the present study was to investigate the liaison between the specific surface area (and/or surface properties) and the photocatalytic performances of rutile. Therefore, in the first instance nanosized (~5 nm) non-doped rutile was obtained, followed by a calcination at different temperatures (400-1000 °C), resulting a series of rutile photocatalysts with finely tuned specific surface areas (1-197 m<sup>2</sup>g<sup>-1</sup>). The photocatalytic performance was determined under visible light irradiation using phenol and *E.coli* bacteria as model contaminants. The Investigated photocatalysts were characterized by XRD, DRS, TEM, XPS, EPR, IR and N<sub>2</sub> adsorption.

## 2. Experimental

### 2.1. Materials

For the synthesis of different rutile photocatalysts, Ti(O-nBu)<sub>4</sub> (Sigma-Aldrich, reagent grade, 97%), HCl (Sigma-Aldrich; 37%) and ultrapure water (Millipore Milli-Q) were used.

For the determination of the photocatalytic efficiencies, phenol (Spektrum 3D; analytical grade) and *E. coli* K12 bacteria were applied as model water contaminants. Photocatalytic experiments were carried out in NaCl (Spektrum 3D; analytical grade) solutions.

The reference TiO<sub>2</sub> photocatalysts were commercially available Aeroxide P25 (produced by Evonik Industries) and Aldrich rutile.

### 2.2. Methods and instrumentation

#### 2.2.1. Structural characterization of the TiO<sub>2</sub>-s

A Rigaku diffractometer was applied for X-ray diffraction (XRD) measurements ( $\lambda$ Cu K $\alpha$  = 0.15406 nm, 30 kV, and 15 mA, in the 20-40° (2 $\theta$ ) regime). The average diameters of the particles were derived by using the Scherrer equation. The weight fractions of anatase and rutile were calculated from the peak areas of the anatase and rutile peaks at 25.3° (2 $\theta$ ) and 27.5° (2 $\theta$ ), respectively.

The DR spectra of the samples ( $\lambda$  = 220-800 nm) were measured on a Jasco-V650 diode array computer-controlled (SpectraManager Software) spectrophotometer equipped with an integration sphere (ILV-724).

TEM micrographs were recorded on a Philips CM 10 instrument operating at 100 kV, using Formvar-coated copper grids.

The specific surface areas of the catalysts were determined by N<sub>2</sub> adsorption at 77 K, using a Micromeritics gas adsorption analyzer (Gemini Type 2375). The specific surface area was calculated via the BET method.

XPS measurements were performed on a Specs Phoibos 150 MCD instrument, with monochromatized Al K $\alpha$  radiation (1486.69 eV) at 14 kV and 20 mA, and a pressure lower than 10<sup>-9</sup> mbar. Samples were mounted on the sample holder with the use of double-


sided adhesive carbon tape. High-resolution Ti2p and O1s spectra were recorded in steps of 0.05 eV for the analyzed samples. The data obtained were analyzed with CasaXPS software. All peaks were deconvoluted by using the Shirley background and Lorentzian-Gaussian line shapes. The value of the Gaussian-Lorentzian ratio applied was 30.

The FT-IR measurements were made with a Bruker Equinox 55 spectrometer with an integrated FRA 106 Raman Module. Samples were ground with KBr and pressed into thin pellets (thickness  $\approx$  0.3 mm). IR spectra were recorded with a spectral resolution of 2 cm<sup>-1</sup>.

EPR measurements were performed on powder samples using an EPR spectrometer ADANI PS 8400 system (ADANI Company, Minsk, Republic of Belarus) in the X-band. The samples were introduced in quartz tubes of 2 mm inner diameter. The EPR measurements were performed for all samples with the same conditions and using the same amount of powder.

#### 2.2.2. Determination of photocatalytic efficiencies

The photocatalytic decomposition of phenol was carried out in a special photoreactor which was an open double-walled glass vessel, surrounded by a thermostating jacket at 25.0 °C. Around the vessel 4 conventional energy-saving compact fluorescence lamps (24-W; Düwi 25920/R7S lamps) were mounted<sup>14</sup>. The spectrum of the light emitted by the lamps was slightly modified by circulating 1 M NaNO<sub>2</sub> (Molar Chemicals, min. 99.13%) aqueous solution in the thermostating jacket. This cut-off solution absorbed UV photons below 400 nm, providing solely visible light irradiation for the TiO<sub>2</sub>-s (Fig. 1.).

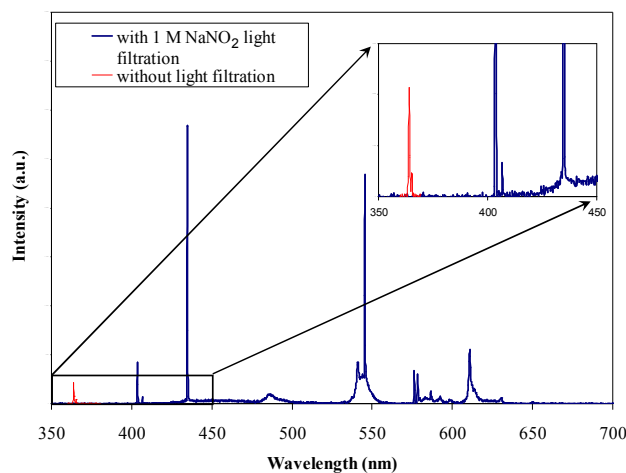

**Fig. 1.** Emission spectra of the conventional energy-saving compact fluorescence lamps (with and without NaNO<sub>2</sub> cut-off filtration)

The TiO<sub>2</sub> suspensions (V=100 mL; c<sub>TiO<sub>2</sub></sub>=1.0 g L<sup>-1</sup>) which contained 0.1 mM phenol as model contaminant were sonicated for 5 min before the photocatalytic tests and then stirred with a magnetic stirrer, and air was purged through the reaction mixture (pH=6) during the experiments. Changes in phenol concentration were followed with an Agilent 1100 series HPLC system equipped with a Lichrospher RP 18 column, a methanol:water = 35:65 mixture being applied as eluent (detection was carried out at 210 nm). The initial

degradation rates were calculated from the slopes of the decay curves ( $t = 0$ )<sup>16</sup>.

Disinfection efficiencies were investigated in the same photoreactor as that in which the phenol decomposition experiments were carried out. The photocatalysts were added to a 0.9% NaCl solution and homogenized by ultrasonication, and an *E. coli* K12 bacteria suspension was then inoculated into it; this suspension was prepared as follows. The bacterial culture was grown at 37 °C in 0.9% NaCl solution containing 1% Tripton (Reanal, analytical grade) and 0.5% Yeast extract (Scharlau, analytical grade) as nutrients. The culture was incubated for 24 h and then purified twice with a 0.9% saline solution by centrifugation (4000 rpm, 2 min) to eliminate the nutrients; the sediment was re-suspended in 0.9% NaCl solution. The initial colony forming unit level in the investigated solution (pH~7) was set to be  $10^4$  CFU/mL. During the photocatalytic disinfection experiments, samples were plated on agar gels (Merck, analytical grade) and the grown colonies were counted after a 24-h incubation at 37 °C in the dark.

### 3. Results and discussion

#### 3.1. Synthesis of rutile TiO<sub>2</sub>-s

Nanosized rutile was produced by the hydrolysis of Ti(O-*n*Bu)<sub>4</sub> under highly acidic conditions. The synthesis method is very sensitive to the H<sup>+</sup> concentration as it is described by Tang *et al.*<sup>17</sup>. They concluded that the optimal interval is about Ti(O-*n*Bu)<sub>4</sub>:H<sup>+</sup>:H<sub>2</sub>O ~ 1:2-3:50. Higher or lower acid concentrations can result in the crystallization of anatase (at nearly neutral pH, amorphous TiO<sub>2</sub> is formed by the hydrolysis of Ti(O-*n*Bu)<sub>4</sub>)<sup>17</sup>. In our synthesis, the Ti(O-*n*Bu)<sub>4</sub>:H<sup>+</sup>:H<sub>2</sub>O ratio of 1:2:50 resulted in a mixture of anatase and rutile. At a ratio of 1:3:50, the TiO<sub>2</sub> produced was pure rutile. Tang *et al.* applied nitric acid to ensure the necessary H<sup>+</sup> concentration, but in the present study hydrochloric acid was applied to avoid N doping of the TiO<sub>2</sub>, because it induces interpretation errors of the obtained results, due to the additional visible light activity<sup>18-23</sup>. 15.7 mL hydrochloric acid was added in 44.6 mL Milli-Q water, and 21.3 mL Ti(O-*n*Bu)<sub>4</sub> was then added to the solution dropwise (1 mL min<sup>-1</sup>). The solution was aged for 15 min under magnetic stirring. After the termination of homogenization, two clear layers appeared, an upper (yellowish) organic phase and a lower colorless sol, which was isolated in a separating funnel. The sol was aged for 24 h in a water bath at 40 °C. The temperature of the solution in this step is a critical condition in the synthesis. Higher temperatures result in faster crystallization, but the formation of anatase is to be expected above 60 °C<sup>24</sup>. The higher thermodynamic stability of rutile leads to a lower activation energy, which results in the preferred formation of rutile at lower temperatures. During the 24-h thermal treatment (in a water bath at 40 °C), a white precipitate appeared in the sol, which indicated the crystallization of TiO<sub>2</sub>. The suspension was dried at 40 °C in a drying oven, and then ground in an agate mortar. The sample was washed by centrifugation 4 times in Milli-Q water. After the purification of this TiO<sub>2</sub> (designated Rutile-O), it was dried at 40 °C, and again ground in an agate mortar.

#### 3.2. Preparation of the series of rutile samples with different particle sizes

Rutile-O was calcined (*Thermolyne 21100* tube furnace) at increasing temperatures to produce rutile samples with increasing particle sizes. Since the presence of O vacancies and Ti<sup>3+</sup> on the surface of TiO<sub>2</sub> nanoparticles is generally beneficial for high photocatalytic performance<sup>11, 12, 25, 26</sup>, a special calcination method (named as “RHSE - Rapid heating, short exposure”) was applied (Fig. 2.) in the present study<sup>27, 28</sup> which results the appearance of these species. The temperatures applied were 400, 600, 700, 800, 900 and 1000 °C, producing TiO<sub>2</sub> samples designated Rutile-RHSE-400-1000. After the calcination, the samples were again ground in an agate mortar.

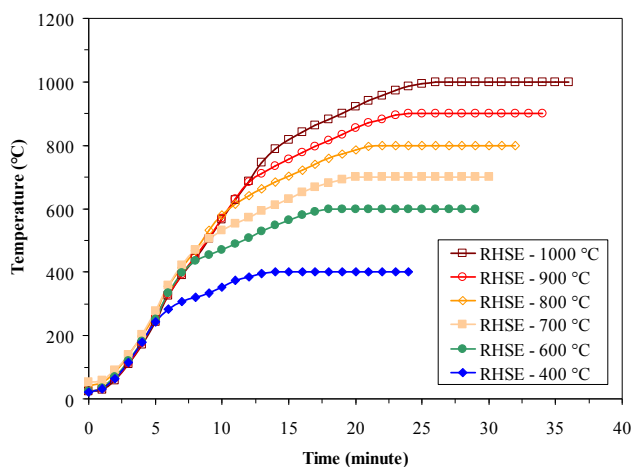


Fig. 2. Heating profile of the different calcination temperatures (RHSE: rapid heating short exposure – more details are given in an earlier publication<sup>28</sup>)

#### 3.3. Characterization of the photocatalysts

Each of the photocatalysts was characterized by X-ray diffraction (XRD) measurements (Fig. 3. shows typical diffraction data of titanium dioxides).

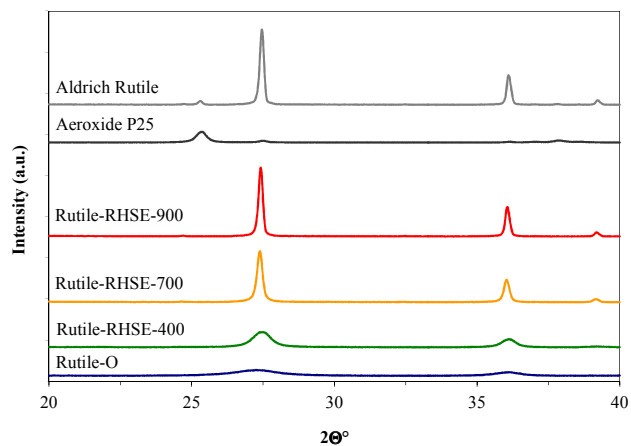


Fig. 3. XRD patterns of laboratory-made and commercial reference TiO<sub>2</sub>-s




**Table 1.** Structural parameters of the investigated photocatalysts (crystal phase content, particle size and specific surface area), initial reaction rates determined for phenol decomposition under VIS irradiation, and initial reaction rates normalized to 1 m<sup>2</sup> of surface.

	Anatase (wt %)	Rutile (wt %)	DA (nm)	DR (nm)	Specific surface area (m <sup>2</sup> g <sup>-1</sup> )	r <sub>0, phenol</sub> (10 <sup>-10</sup> M s <sup>-1</sup> )	r <sub>0, phenol</sub> (10 <sup>-12</sup> mol m <sup>-2</sup> s <sup>-1</sup> ) Surface normalized
Rutile-O	<1	>99	-	5,2	197	8,7	4,4
Rutile-RHSE-400	<1	>99	-	12,9	62	3,2	5,2
Rutile-RHSE-600	<1	>99	-	39,1	34	3,1	9,1
Rutile-RHSE-700	<1	>99	-	69,3	12	3,1	25,8
Rutile-RHSE-800	<1	>99	-	135 <sup>TEM</sup>	7	2,0	28,6
Rutile-RHSE-900	<1	>99	-	245 <sup>TEM</sup>	3	1,9	63,3
Rutile-RHSE-1000	<1	>99	-	290 <sup>TEM</sup>	1	1,8	175,0
Aldrich rutile	4	96	315 <sup>TEM</sup>	315 <sup>TEM</sup>	3	41,6	1386,7
Aeroxide P25	90	10	25,4	40,0	49	12,3	25,1

The main crystalline phase of the prepared TiO<sub>2</sub>-s was rutile (>99 wt. %). The average diameters of the particles, estimated by using the Scherrer equation (when it is lower than 100 nm), are presented in Table 1. Rutile-O contained very small nanoparticles (D~5 nm) and, as expected, the average particle size increased (13-290 nm) with rising calcination temperature (400-1000 °C). The primary particle sizes and phase distributions of commercial reference photocatalysts are also presented in Table 1. Aeroxide P25 contains 90 wt. % anatase and 10 wt. % rutile (D<sub>anatase</sub> = 25.4 nm and D<sub>rutile</sub> = 40 nm), while Aldrich rutile contains mainly (96 wt. %) rutile (D~315 nm).

Transmission electron microscopic (TEM) images (Fig. 4.) were taken to determine the particle size (when it is higher than 100 nm), the size distribution and the morphology of the particles.

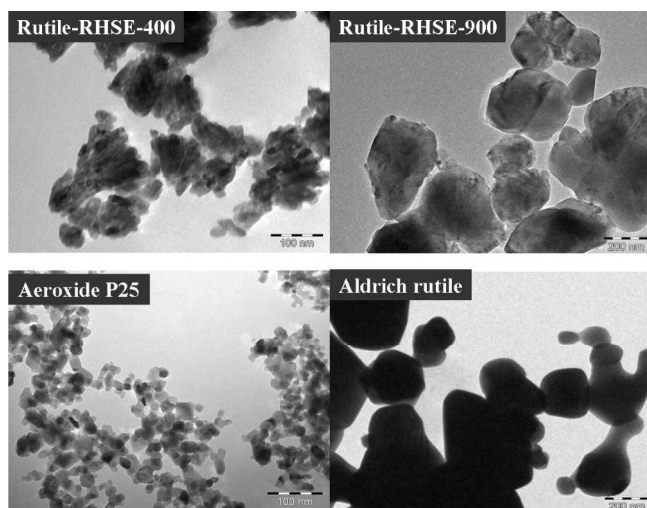


**Fig. 4.** TEM images of selected photocatalysts

The laboratory-prepared rutile particles were mostly rounded, edgeless and polydisperse (e.g. Rutile-RHSE-900 contains particles with D = 100-400 nm). The micrographs of Aldrich rutile and Rutile-RHSE-900 revealed very similar morphology and particle

size distribution. Aeroxide P25 contained spherical and polyhedral (faceted) particles too.

The specific surface areas of the laboratory-made rutile titanias varied within a wide range (1-197 m<sup>2</sup> g<sup>-1</sup>, Table 1). Non-calcined Rutile-O exhibited the highest value (197 m<sup>2</sup> g<sup>-1</sup>), which decreased concomitantly with the temperature raising. It should be noted that Rutile-RHSE-900 and Aldrich rutile demonstrated the same specific surface area: ~3 m<sup>2</sup> g<sup>-1</sup>.

To investigate the light absorption properties of the synthesized photocatalysts, diffuse reflectance spectra were recorded (Fig. 5).

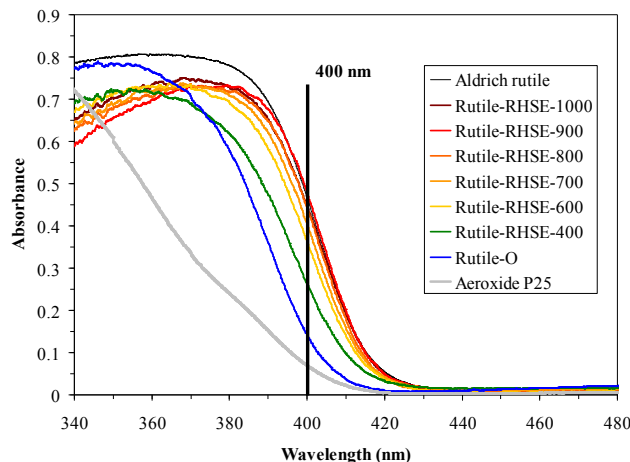

**Fig. 5.** DR spectra of investigated TiO<sub>2</sub>-s

As the calcination temperature was increased, the light absorption of the produced rutile TiO<sub>2</sub>-s underwent a red shift (similar effect was demonstrated by Silva and Faria<sup>29</sup>). Interestingly, Rutile-RHSE-900 and Rutile-RHSE-1000 displayed very similar light absorption properties to those of Aldrich rutile. Consequently, the increased visible light absorption of the TiO<sub>2</sub>-s calcined at higher temperatures is expected to be accompanied by higher photocatalytic activity under visible light irradiation.

### 3.4. Photocatalytic decomposition of phenol

The phenol decay curves in Fig. 6. show that Aldrich Rutile has high efficiency relative to the laboratory-made TiO<sub>2</sub>-s and Aeroxide P25. The initial degradation rates are listed in Table 1.

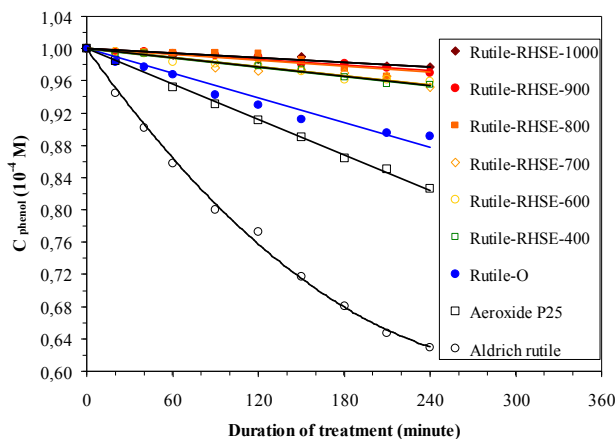


Fig. 6. Photocatalytic decomposition of phenol solutions

The photocatalytic experiments revealed the highest rate of phenol degradation for Rutile-O among the laboratory-made TiO<sub>2</sub>-s. Interestingly, the light absorption edge gradually shifted into the visible region (see Fig. 5.) as the calcination temperature was increased. Furthermore, an increase in the primary particle size (5–290 nm) and a decrease in the specific surface area (from 197 to 1 m<sup>2</sup> g<sup>-1</sup>) were also observed. A comparison of the photocatalytic activities with the above-mentioned properties indicates the following important observations:

- The photocatalytic activity decreased slightly on elevation of the calcination temperature because of the lower specific surface area.
- The surface-normalized rate of degradation of phenol (mol s<sup>-1</sup> m<sup>-2</sup>) varied oppositely the previous trend (Table 1). This could be due to the more efficient visible light absorption (see Fig. 5.) of the TiO<sub>2</sub>-s calcined at higher temperatures.

Aldrich rutile has ~22 times higher photocatalytic efficiency than that of Rutile-RHSE-900, despite these TiO<sub>2</sub>-s having very similar specific surface area, particle size and morphology (rounded, edgeless shape, and highly polydispersed size distribution). The light absorption properties of these photocatalysts are also nearly the same.

The photocatalytic performances of the laboratory-made TiO<sub>2</sub>-s were compared with that of the most commonly used reference TiO<sub>2</sub>, Aeroxide P25. Rutile-O TiO<sub>2</sub> and Aeroxide P25 gave rise to similar phenol decomposition yields under visible light irradiation. The relatively high efficiency of Aeroxide P25 is very interesting, considering the fact that it contains mainly (~90%) anatase, which cannot be activated by visible light. There are some different explanations for this high efficiency in the literature. Balázs *et al.*<sup>30</sup> reported that polyhedral nanoparticles have higher photocatalytic activity than spherical ones, and Aeroxide P25 contains polyhedral particles whereas Aldrich rutile and the laboratory-made photocatalysts do not (see Fig. 4.). Another explanation is provided by Rajashekhar and Devi<sup>31</sup> and by Ohno *et al.*<sup>32</sup>: they describe a

special synergetic effect of anatase and rutile nanoparticles in Aeroxide P25, which can result in the high activity of this type of TiO<sub>2</sub>. However this synergetic effect is doubted by Ohtani *et al.*<sup>33</sup>.

### 3.5. Photocatalytic disinfection of E. coli-contaminated water

For the visible light irradiation of TiO<sub>2</sub> and *E. coli*-containing suspensions (50 μL) were plated on agar gels and the grown colonies were counted after a 24-h incubation at 37 °C in the dark. The results of these disinfection experiments are summarized in Fig. 7. All of the experiments were repeated twice, and the averages are presented.

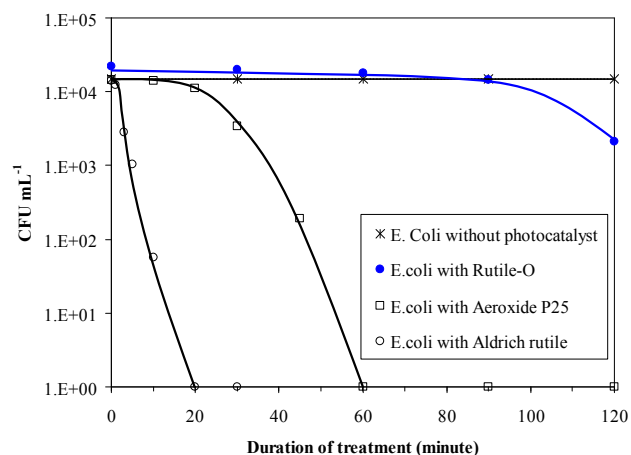


Fig. 7. Photocatalytic E.coli disinfection experiments

The grown colonies are illustrated in a photo (see Fig. 8.) in the case of Rutile-O. More than 90% of the *E. coli* cells were killed after 2 h of irradiation in the presence of this TiO<sub>2</sub> with its very small nanoparticles (~5 nm).

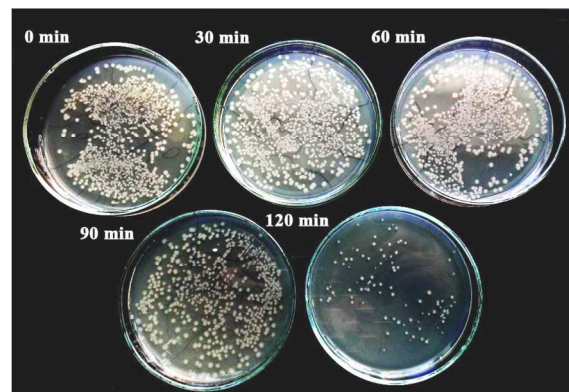


Fig. 8. E.coli colonies grown in photocatalytic disinfection experiment with laboratory-made Rutile-O

None of the other (calcined) laboratory-made rutile photocatalysts exhibited any disinfection properties after the 120-min irradiation. Aeroxide P25 totally sterilized the water after 60 min, while Aldrich Rutile (with large nanoparticles ~315 nm) did so after 20 min whereas Rutile-RHSE-900 (with a similar particle size and the same specific surface area as those of Aldrich rutile) was not active at all. In experiments with the TiO<sub>2</sub>-s without irradiation, no antibacterial effect was seen.

### 3.6. Discussion

Aldrich rutile with large particle size (~315 nm) showed the highest disinfection performance. Unfortunately, the rutile with the smallest particle size (among the obtained rutile samples) exhibited a significantly lower disinfection performance. Moreover the larger rutiles did not show any disinfection property. This means that the particle size of rutile is not a crucial factor in visible light induced photocatalytic disinfection. Furthermore, Aldrich rutile and self-made Rutile-RHSE-900 TiO<sub>2</sub> with similar structural properties (specific surface area, particle size, shape and size distribution)

demonstrated very different photocatalytic activities. Accordingly a close correlation was not observed between these structural parameters and the photocatalytic efficiency of rutile-phase titanium dioxides.

In an attempt to explain the great difference in photocatalytic efficiency, X-ray photoelectron, and IR spectroscopic and EPR examinations were also carried out on these two samples.

X-ray photoelectron spectra (Ti2p, O1s) are presented in Fig. 9.

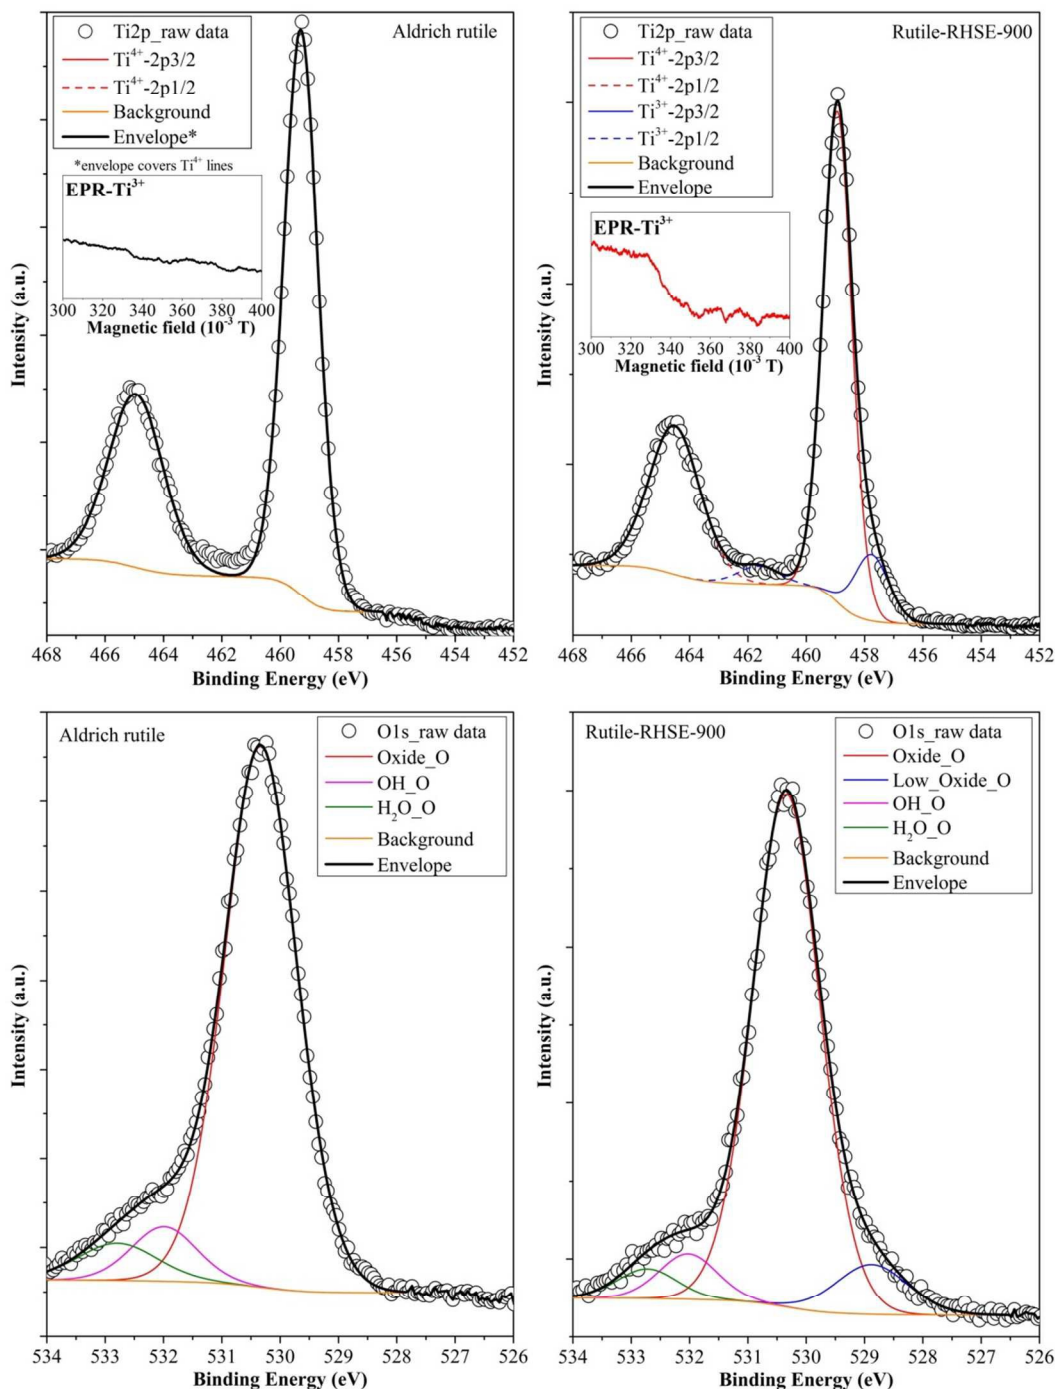


Fig. 9. Ti2p and O1s XP spectra of Aldrich rutile and Rutile-RHSE-900

The surface of the Aldrich Rutile does not appear unusual. In the Ti2p XPS spectrum only  $Ti^{4+}$  was detected, while the O1s spectrum revealed the usual components: oxide oxygen from  $TiO_2$  (530.3 eV), surface OH group oxygen (532 eV), and oxygen from  $H_2O$  (532.8 eV). As the Rutile-RHSE-900 was made by the rapid heat treatment method<sup>27, 28, 34</sup>, we expected the appearance of new spectral features. Indeed, in the Ti2p XPS spectrum a small amount of  $Ti^{3+}$  was observed (13 at. %: peaks at 457.3 eV and 461.9 eV), along with  $Ti^{4+}$  (87 at. %: peaks at 459.1 eV and 464.8 eV)<sup>27</sup>. The O1s spectrum of this material indicated a low binding energy oxygen species (at 528.8 eV, 12 at. %). On the basis of recent publications<sup>27, 28</sup>, this interesting form of oxygen was ascribed to the presence of oxygen defects, or to oxygen atoms adjacent to reduced Ti sites (i.e.  $Ti^{3+}$ ). This is reinforced by the fact that  $Ti^{3+}$  and the low binding energy oxygen are interdependent entities: if one them appears in a surface composition, so does the other. In the cases of the other fast heat-treated  $TiO_2$ -s (in which the predominant crystal phase was anatase), the presence of this special species was earlier observed to enhance the photocatalytic activity (UV – phenol degradation) as it is described in our previous study<sup>27</sup>. In the present study (rutile - VIS - phenol degradation), the presence of this species did not enhance the photocatalytic performance: a drastic inhibition was registered. Consequently the specific roles of  $Ti^{3+}$  and O vacancies needs further investigations as it is also emphasized by Su et al. in their excellent review article<sup>35</sup> about the complexity of this topic.

To get further evidence, EPR measurements were carried out, which proved the presence of  $Ti^{3+}$  in Rutile-RHSE-900<sup>36,37</sup> (see the inset of Fig 9.). As it can be seen, until now, there are no clear evidences concerning the higher photocatalytic activity. The explanation regarding this issue, must be surface related, as the photocatalytic properties are surface quality dependent phenomena.

Hence, IR measurements were carried out and were presented in Fig. 10. The usual features were noted for both samples, the most important being the broad band centered at  $3400\text{ cm}^{-1}$ , with a sharp band at  $1623\text{ cm}^{-1}$ , which can be attributed to the stretching and bending vibrations of the surface OH group<sup>27</sup>.

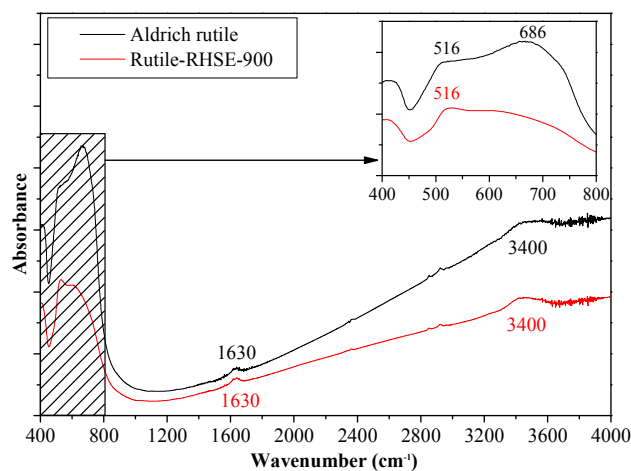


Fig. 10. IR spectra of Aldrich rutile and Rutile-RHSE-900 samples

In the inset of Fig. 10., the Ti-O-Ti bond stretching vibrations can be identified at  $519\text{ cm}^{-1}$  for the rutile phase<sup>38</sup>. The samples presented

similar peaks of  $CO_2$  at  $2380\text{ cm}^{-1}$ . The only difference between the IR spectra is the appearance of a new band for Aldrich Rutile at  $687\text{ cm}^{-1}$ , which corresponds to Ti-O-O- bond stretching vibrations<sup>8, 39-41</sup>. This indicates an oxygen-rich surface on the catalyst, which could be an electrophilic entity. Since rutile is activated in visible light (as shown by the DRS spectra) and the charge carriers are formed as usual, this “peroxidized” surface can attract electrons, which can then be easily captured by molecular oxygen, resulting finally in higher radical generation (high hydroxyl radical generation was proved in our earlier publication<sup>14</sup> in case of visible light activated Aldrich rutile). Shankar and co-workers<sup>40</sup>, and Zou and co-workers<sup>41</sup> also reported enhanced photocatalytic activity in their Ti-O-O-groups containing, laboratory prepared titanium-dioxides.

#### 4. Conclusions

A method for the synthesis of nanosized ( $\sim 5\text{ nm}$ ), pure rutile-phase, non-doped  $TiO_2$  was developed (Rutile-O), by the hydrolysis of  $Ti(O-nBu)_4$  in HCl solution, and crystallization in a water bath at low temperature ( $40\text{ }^\circ\text{C}$ ). A series of rutile with increasing particle size (12.9, 39.1, 69.3, 135, 245 and 290 nm) were produced by the calcination of Rutile-O at different temperatures ( $400\text{-}1000\text{ }^\circ\text{C}$ ).

The DR spectra indicated that the light absorption was shifted into the visible region on increase of the calcination temperature, which may explain the significantly increased surface-normalized photocatalytic performance of the calcined  $TiO_2$ -s.

The results of XRD, DRS, BET and TEM characterization methods demonstrated that Aldrich rutile and the laboratory-made Rutile-RHSE-900 have very similar properties, such as particle size, specific surface area, morphology and light absorption, but they differ significantly in photocatalytic efficiency (for either phenol decomposition or disinfection). A close correlation was not observed between these structural parameters and the photocatalytic efficiency of rutile

The present work highlighted that surface properties causes much higher differences in photocatalytic performances than specific surface area, and the importance of the presence of  $Ti^{3+}$  was re-evaluated. It emerged from XPS and EPR measurements that the presence of  $Ti^{3+}$  and low-binding-energy oxygen on rutile does not enhance the photocatalytic performance (under visible light irradiation). However, the IR measurements revealed that Aldrich rutile has an oxygen-rich surface (Ti-O-O- entities), which can result in higher radical generation efficiency under (despite it's low specific surface area:  $\sim 3\text{ m}^2\text{g}^{-1}$ ). The presented results pointed out that the presence of Ti-O-O- entities is more preferable than the presence of  $Ti^{3+}$  in relation with the photocatalytic performance of rutile under visible light irradiation. Based on these results a next challenge is to prepare rutile-phased titanium dioxide with high specific surface area, containing Ti-O-O groups on the surface

#### Acknowledgments

This research was supported by the European Union and the State of Hungary, co-financed by the European Social Fund in the framework of TÁMOP 4.2.4. A/2-11-1-2012-0001 'National Excellence Program'. This work was partially co-financed by the Swiss



Contribution (SH/7/2/20). This work was supported for the Romanian authors by a grant of the Romanian National Authority for Scientific Research, CNCS–UEFISCDI, project number PN-II-ID-PCE-2011-3-0442. KM is grateful for the financial support of the János Bolyai Research Scholarship of the Hungarian Academy of Sciences. The authors are indebted to Evonik Industries for supporting our work by supplying TiO<sub>2</sub>-s for these studies.

The authors are grateful for the research group of László Manczinger (*Department of Microbiology; University of Szeged*) for the helpful contribution in microbial experiments.

## Notes and references

<sup>1</sup>Research Group of Environmental Chemistry, Institute of Chemistry, University of Szeged, H-6720, Szeged, Tisza Lajos krt. 103., Hungary

<sup>2</sup>Department of Process Engineering; Faculty of Engineering, University of Szeged, H-6725, Szeged, Moszkvai krt. 9, Hungary

<sup>3</sup>Faculty of Chemistry and Chemical Engineering, Babes-Bolyai University, RO-400028, Arany János 11, Cluj-Napoca, Romania

<sup>4</sup>Faculty of Physics, Babes-Bolyai University, RO-400084, M. Kogălniceanu 1, Cluj-Napoca, Romania

<sup>5</sup>Institute for Interdisciplinary Research on Bio-Nano-Sciences, RO-400271, Treboniu Laurian 42, Cluj-Napoca, Romania

<sup>6</sup>Department of Applied and Environmental Chemistry University of Szeged, H-6720, Rerrich tér 1, Szeged, Hungary

\*Corresponding author, tel/fax: +36-62-544338

E-mail address: verebg@chem.u-szeged.hu

1. R. Zha, R. Nadimicherla and X. Guo, *RSC Adv.*, 2015, **5**, 6481-6488.
2. M. Li, S. Zhang, Y. Peng, L. Lv and B. Pan, *RSC Adv.*, 2014, **5**, 7363-7369.
3. W. Sun, H. Liu, J. Hu and J. Li, *RSC Adv.*, 2015, **5**, 513-520.
4. M. Abbasnejad, E. Shojaee, M. R. Mohammadzadeh, M. Alaei and R. Maezono, *Appl. Phys. Lett.*, 2012, **100**, 261902.
5. Y. Wang, H. Zhang, P. Liu, X. Yao and H. Zhao, *RSC Advances*, 2013, **3**, 8777.
6. J. Orlikowski, B. Tryba, J. Ziebro, A. W. Morawski and J. Przepiórski, *Catalysis Communications*, 2012, **24**, 5-10.
7. M. A. Fox and M. T. Dulay, *Chem. Rev.*, 1993, **93**, 341-357.
8. V. Etacheri, M. K. Seery, S. J. Hinder and S. C. Pillai, *Adv. Funct. Mater.*, 2011, **21**, 3744-3752.
9. S. Banerjee, J. Gopal, P. Muraleedharan, A. Tyagi and B. Rai, *Curr. Sci.*, 2005, **90**, 1378-1383.
10. S. Yin, H. Hasegawa, D. Maeda, M. Ishitsuka and T. Sato, *J. Photochem. Photobiol., A*, 2004, **163**, 1-8.
11. K.-C. Huang and S.-H. Chien, *Appl. Catal., B*, 2013, **140-141**, 283-288.
12. H. Nagai, S. Aoyama, H. Hara, C. Mochizuki, I. Takano, N. Baba and M. Sato, *J. Mater. Sci.*, 2008, **44**, 861-868.
13. V. Caratto, B. Aliakbarian, A. A. Casazza, L. Setti, C. Bernini, P. Perego and M. Ferretti, *Mater. Res. Bull.*, 2013, **48**, 2095-2101.
14. G. Veréb, L. Manczinger, G. Bozsó, A. Sienkiewicz, L. Forró, K. Mogyorósi, K. Hernádi and A. Dombi, *Appl. Catal., B*, 2013, **129**, 566-574.
15. F. Amano and M. Nakata, *Appl. Catal., B*, 2014, **158-159**, 202-208.
16. G. Veréb, Z. Ambrus, Z. Pap, Á. Kmettykó, A. Dombi, V. Danciu, A. Cheesman and K. Mogyorósi, *Applied Catalysis A: General*, 2012, **417-418**, 26-36.
17. Z. Tang, J. Zhang, Z. Cheng and Z. Zhang, *Mater. Chem. Phys.*, 2002, **77**, 314-317.
18. P. Wu, R. Xie, J. A. Imlay and J. K. Shang, *Appl. Catal., B*, 2009, **88**, 576-581.
19. J. A. Rengifo-Herrera, J. Kiwi and C. Pulgarin, *J. Photochem. Photobiol., A*, 2009, **205**, 109-115.
20. P. Wu, J. A. Imlay and J. K. Shang, *Biomaterials*, 2010, **31**, 7526-7533.
21. J. A. Rengifo-Herrera, K. Pierzchała, A. Sienkiewicz, L. Forró, J. Kiwi and C. Pulgarin, *Appl. Catal., B*, 2009, **88**, 398-406.
22. H. U. Lee, S. C. Lee, S. Choi, B. Son, S. M. Lee, H. J. Kim and J. Lee, *Chemical Engineering Journal*, 2013, **228**, 756-764.
23. D. Dolat, S. Mozia, B. Ohtani and A. W. Morawski, *Chemical Engineering Journal*, 2013, **225**, 358-364.
24. M. Gopal, W. J. M. Chan and L. C. DeJonghe, *J. Mater. Sci.*, 1997, **32**, 6001-6008.
25. Q. P. Wu and R. van de Krol, *J. Am. Chem. Soc.*, 2012, **134**, 9369-9375.
26. M. Y. Xing, J. L. Zhang, F. Chen and B. Z. Tian, *Chemical Communications*, 2011, **47**, 4947-4949.
27. Z. Pap, E. Karacsonyi, Z. Cegled, A. Dombi, V. Danciu, I. C. Popescu, L. Baia, A. Oszko and K. Mogyorosi, *Appl. Catal., B*, 2012, **111**, 595-604.
28. Z. Pap, V. Danciu, Z. Cegled, A. Kukovecz, A. Oszko, A. Dombi and K. Mogyorosi, *Appl. Catal., B*, 2011, **101**, 461-470.
29. C. G. Silva and J. L. Faria, *Photochemical & Photobiological Sciences*, 2009, **8**, 705.
30. N. Balazs, K. Mogyorosi, D. F. Sranko, A. Pallagi, T. Alapi, A. Oszko, A. Dombi and P. Sipos, *Appl. Catal., B*, 2008, **84**, 356-362.
31. K. E. Rajashekhar and L. G. Devi, *J. Mol. Catal. A: Chem*, 2013, **374**, 12-21.
32. T. Ohno, K. Sarukawa and M. Matsumura, *J. Phys. Chem. B*, 2001, **105**, 2417-2420.
33. B. Ohtani, O. O. Prieto-Mahaney, D. Li and R. Abe, *J. Photochem. Photobiol., A*, 2010, **216**, 179-182.
34. K. Mogyorosi, E. Karacsonyi, Z. Cegled, A. Dombi, V. Danciu, L. Baia and Z. Pap, *J. Sol-Gel Sci. Technol.*, 2013, **65**, 277-282.
35. J. Su, X. Zou and J.-S. Chen, *RSC Advances*, 2014, **4**, 13979.
36. R. F. Howe and M. Grätzel, *J. Phys. Chem.*, 1985, **89**, 4495-4499.
37. V. M. Khomeenko, K. Langer, H. Rager, A. Fett, *Physical Chemistry Minerals*, 1998, **25**, 338-346.
38. T. Busani and R. A. B. Devine, *Semicond. Sci. Technol.*, 2005, **20**, 870-875.
39. M. R. Ayers and A. J. Hunt, *Mater. Lett.*, 1998, **34**, 290-293.
40. M. V. Shankar, T. Kako, D. Wang and J. Ye, *J. Colloid Interface Sci.*, 2009, **331**, 132-137.
41. J. Zou, J. Gao and F. Xie, *J. Alloys Compd.*, 2010, **497**, 420-427.