



**Photoluminescence and afterglow of deep red emitting  
 $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$**

Journal:	<i>RSC Advances</i>
Manuscript ID	RA-ART-12-2015-025686.R1
Article Type:	Paper
Date Submitted by the Author:	03-Jan-2016
Complete List of Authors:	Müller, Matthias; Münster University of Applied Sciences, Department of Chemical Engineering Volhard, Max-Fabian; Münster University of Applied Sciences, Department of Chemical Engineering Jüstel, Thomas; Münster University of Applied Sciences, Department of Chemical Engineering
Subject area & keyword:	Optical materials < Materials



Journal Name

ARTICLE

## Photoluminescence and afterglow of deep red emitting SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup>

Matthias Müller, Max-Fabian Volhard, and Thomas Jüstel\*

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

This work deals with the photoluminescence (PL) properties of SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> and SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup>,Dy<sup>3+</sup>. For this purpose a series of powder samples of SrSc<sub>2</sub>O<sub>4</sub> with various concentrations of Eu<sup>2+</sup> and Dy<sup>3+</sup> were prepared. The samples were synthesised via high temperature solid state route. Phase purity was investigated by conducting X-ray powder diffractometry. The PL properties of all prepared samples were elucidated by recording PL and PL excitation spectra. Furthermore, the temperature behaviour of the PL of SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> was investigated from 100 to 500 K. Diffuse reflectance spectra were recorded to investigate the optical properties of Eu<sup>2+</sup> doped SrSc<sub>2</sub>O<sub>4</sub>. Additionally, persistent luminescence of SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> and SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup>,Dy<sup>3+</sup> was investigated. To this end PL lifetime measurements were conducted. SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> shows an emission band in the deep red spectral range. Moreover, it turned out that the red emission of SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> shows persistent luminescence, too.

### 1. Introduction

Today, materials which show red photoluminescence (PL) or persistent luminescence are of great interest for various applications. Their uses as phosphor in light emitting diodes or as fluorescence probe in bio-imaging are only two potential fields of application for those materials. For this reason, many research groups are investigating different host compounds and various dopants to find new red emitting materials.<sup>1,2,3</sup> Often, Eu<sup>2+</sup> is taken as a dopant to obtain red emission.<sup>3,4</sup> Since the emission of Eu<sup>2+</sup> is due to interconfigurational *d-f*-transition, the energy of the emission strongly depends on the host material. Therefore, the emission band of Eu<sup>2+</sup> can be shifted from ultraviolet (UV) to deep red range of the electromagnetic spectrum by changing the chemical environment.<sup>5</sup>

For instance, in a material providing a surrounding with little covalent character like BaAlF<sub>5</sub>, the Eu<sup>2+</sup> emission occurs in the UV range at about 361 nm.<sup>6</sup> With increasing covalent interaction the emission band of Eu<sup>2+</sup> can be located all over the visible spectrum. In CaAl<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> the emission band of Eu<sup>2+</sup> is located in the blue spectral range at about 436 nm.<sup>7</sup> Green emission of Eu<sup>2+</sup> can be observed in oxides and oxy-nitrides like SrAl<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> ( $\lambda_{em, max} \approx 512$  nm) and  $\beta$ -SiAlON:Eu<sup>2+</sup> ( $\lambda_{em, max} \approx 535$  nm). Red *5d-4f*-emission of Eu<sup>2+</sup> is commonly observed in nitrides and sulphides. For example, Sr<sub>2</sub>Si<sub>5</sub>N<sub>8</sub>:Eu<sup>2+</sup> possesses an emission band at about 620 nm. Eu<sup>2+</sup> doped sulfides such as CaS:Eu<sup>2+</sup> or SrS:Eu<sup>2+</sup> show emission at about 650 and 615 nm, respectively.

So far, not many red emitting luminescent materials on the basis of Eu<sup>2+</sup>-doped oxides are known and even less showing persistent luminescence in the deep red spectral range.<sup>1</sup> Most of the red or infrared emitting persistent phosphors are sulphide based compounds doped with lanthanide ions.<sup>8</sup> Especially in the red region, this group of compounds provides a variety of different emission wavelengths. Unfortunately, such compounds usually are extremely sensitive against moisture and thus chemically unstable. Therefore, further efforts like encapsulation and surface modification are necessary to protect these compounds from degradation. A chemically more stable group of compounds are oxides. Usually, oxides are impervious against moisture. However, most oxides which show red persistent luminescence are doped with Cr<sup>3+</sup>.

SrSc<sub>2</sub>O<sub>4</sub> was firstly described and its structure solved by Carter and Feigelson in 1964.<sup>9</sup> Later Gaume et al reported on the spectroscopic properties of Yb<sup>3+</sup>-doped SrSc<sub>2</sub>O<sub>4</sub>.<sup>9</sup> To the best of our knowledge there is no report concerning the PL properties of Eu<sup>2+</sup> doped SrSc<sub>2</sub>O<sub>4</sub>. Therefore, a series of powder samples of SrSc<sub>2</sub>O<sub>4</sub> with various contents of Eu<sup>2+</sup> and Dy<sup>3+</sup> was prepared. SrSc<sub>2</sub>O<sub>4</sub> crystalizes in the orthorhombic crystal system with space group *Pnam*. In SrSc<sub>2</sub>O<sub>4</sub> the Sr<sup>2+</sup> ions are surrounded by eight O<sup>2-</sup> ions. The ionic radius of 8-fold coordinated Sr<sup>2+</sup> is 1.26 Å. 8-fold coordinated Eu<sup>2+</sup> and Dy<sup>3+</sup> exhibit ionic radii of 1.25 Å and 1.027 Å.<sup>10</sup> Therefore, it is assumed that the Eu<sup>2+</sup> and Dy<sup>3+</sup> ions tend to occupy the Sr<sup>2+</sup> sites.

### 2. Experimental

The SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup> and SrSc<sub>2</sub>O<sub>4</sub>:Eu<sup>2+</sup>,Dy<sup>3+</sup> samples as investigated in this work were synthesized by high temperature solid state

Department of Chemical Engineering, Münster University of Applied Sciences, Stegerwaldstrasse 39, 48565 Steinfurt, Germany, \*E-mail: tj@fh-muenster.de

reaction. Therefore, high purity educts  $\text{SrCO}_3$  (Aldrich, 99.9%),  $\text{Sc}_2\text{O}_3$  (Treibacher Industrie AG, 99.99%),  $\text{Eu}_2\text{O}_3$  (Treibacher Industrie AG, 99.99%), and  $\text{Dy}_2\text{O}_3$  (Treibacher Industrie AG, 99.99%) were weighted in stoichiometric amounts and were thoroughly blended in acetone in an agate mortar. After drying at ambient temperatures, the obtained powder blends were calcined at 1400 °C for 12 h in Mo boats in a reducing hydrogen atmosphere (Westfalen, 99.999%). After calcination, red sinter bodies were obtained which were ground to a fine  $\mu$ -powder.

Phase purity of the synthesized samples was investigated using X-ray powder diffractometry (XRD). XRD patterns were collected on a Rigaku MiniFlex II diffractometer working in Bragg-Brentano geometry using  $\text{Cu K}\alpha$  radiation. Step width and integration time were set to 0.02° and 1 s, respectively.

Particle size and morphology were investigated using scanning electron microscopy (SEM). Therefore, the scanning electron microscope Zeiss EVO MA10 equipped with a  $\text{LaB}_6$ -cathode was used. Pressure in the sample chamber was  $5 \times 10^5$  Pa and acceleration voltage was 8 kV.

PL as well as PL excitation (PLE) spectra were recorded on an Edinburgh Instruments FSL900 spectrometer equipped with a Xe arc lamp (450 W) and a cooled (-20 °C) single-photon counting photomultiplier (Hamamatsu R2658P). Obtained PL spectra were corrected by applying a correction file obtained from a tungsten incandescent lamp certified by the National Physics Laboratory U.K.

Persistent luminescence decay (PLD) curves were recorded after exciting the samples for 15 min with an excitation wavelength of  $\lambda_{\text{ex}} = 525$  nm. Absolute luminance and radiance was measured using the optical power meter 1830-C of Newport Corporation equipped with a Si-detector.

Temperature dependent PL measurements from 100 to 500 K were performed using the Oxford Instruments cryostat MicrostatN2. Liquid nitrogen was used as a cooling agent. Temperature stabilization time was 60 s and tolerance was set to  $\pm 3$  K.

Diffuse reflectance (DR) spectra were recorded on an Edinburgh Instruments FS900 spectrometer equipped with a Xe arc lamp (450 W), a cooled (-20 °C) single-photon counting photomultiplier (Hamamatsu R928) as well as a teflon-coated integration sphere.  $\text{BaSO}_4$  (99.998%, Sigma-Aldrich) was used as a reflectance standard.

### 3. Results and Discussion

The collected XRD patterns as well as the ICDD reference card of  $\text{SrSc}_2\text{O}_4$  are depicted in Fig. 1 for comparison purposes. The diffractograms prove the formation of the orthorhombic  $\text{SrSc}_2\text{O}_4$  phase without any impurity phases. In addition, with increasing  $\text{Eu}^{2+}$  doping concentration no significant shift of the reflexes is observed. The diffractograms confirm the used synthesis route for the preparation of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$ .

Morphology of the surface as well as particle size of the prepared samples were investigated by using SEM. Fig. 2 shows the obtained image of  $\text{SrSc}_2\text{O}_4$ . The prepared powders

of  $\text{SrSc}_2\text{O}_4$  are in micrometer range. Further, the particles are heavily cracked by crushing them in the agate mortar.

Reflectance behaviour of the doped and undoped  $\text{SrSc}_2\text{O}_4$  powder samples was investigated by recording DR spectra.  $\text{BaSO}_4$  was used as a reflectance standard. The obtained spectra are illustrated in Fig. 3. Undoped  $\text{SrSc}_2\text{O}_4$  shows about 70%

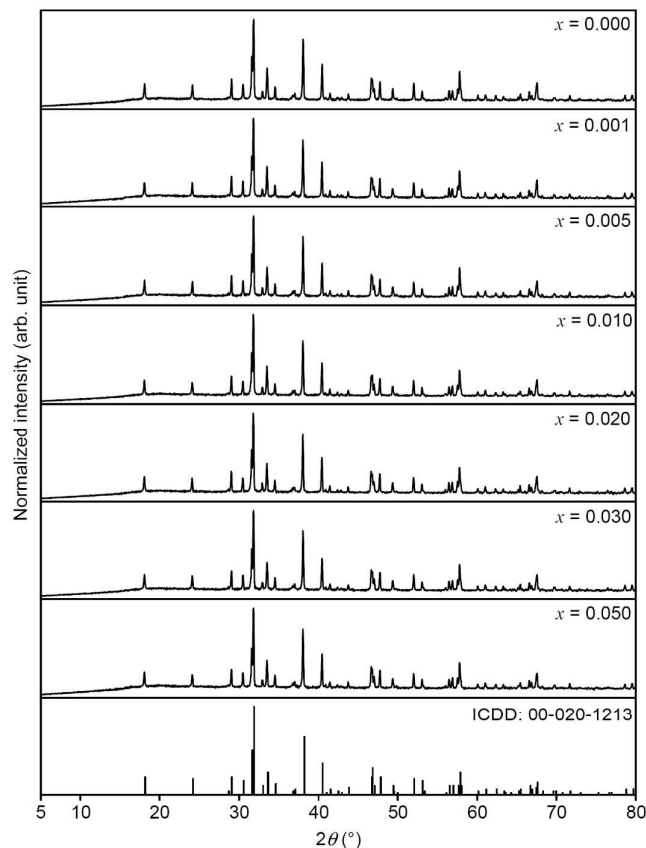


Fig. 1 XRD patterns of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various doping concentrations and ICDD reference card of  $\text{SrSc}_2\text{O}_4$ .

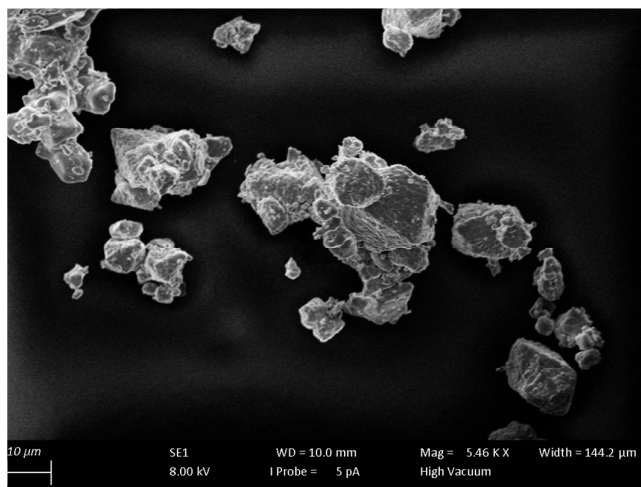


Fig. 2 SEM photograph of  $\text{SrSc}_2\text{O}_4$ .

reflectance compared to  $\text{BaSO}_4$ , which is in line with the white to greyish body colour. This greying is ascribed to Mo impurities caused by the Mo foil used during the high temperature annealing. The  $\text{Eu}^{2+}$  doped  $\text{SrSc}_2\text{O}_4$  samples show strong absorption bands at about 320 and 475 nm. These bands are assigned to transitions from the  $^8\text{S}([\text{Xe}]4f^7)$  ground state to the

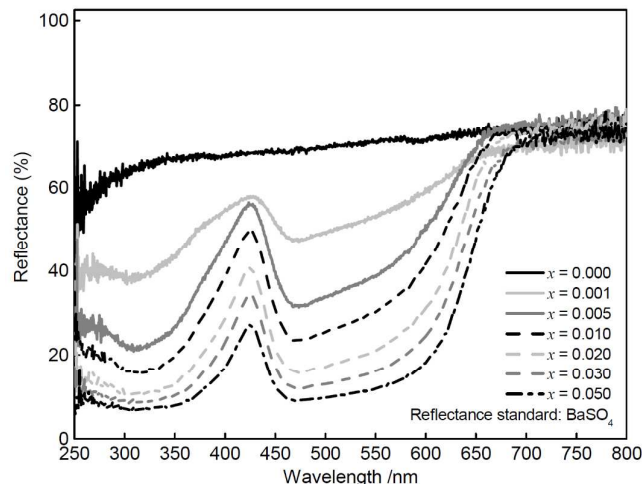


Fig. 3 DR spectra of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various doping concentrations.

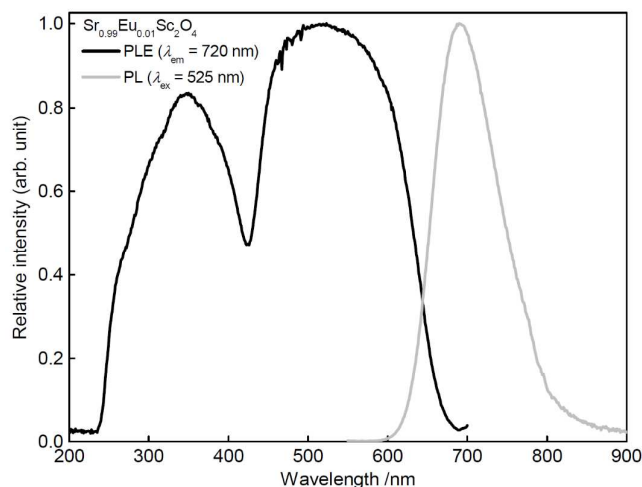


Fig. 4 Room temperature PL and PLE spectra of  $\text{Sr}_{0.98}\text{Eu}_{0.02}\text{Sc}_2\text{O}_4$ .

$5d$  multiplet. With increasing  $\text{Eu}^{2+}$  concentration this absorption increases and broadens towards the long wavelength range. Therefore, the body colour of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  is shifted from light pink to red violet.

PL as well as PLE spectra of  $\text{Sr}_{0.98}\text{Eu}_{0.02}\text{Sc}_2\text{O}_4$  are depicted in Fig. 4. The PLE spectrum was recorded monitoring the  $\text{Eu}^{2+}$  emission at  $\lambda = 720$  nm. The obtained PLE spectrum shows a broad band which consists of various unresolved bands. This band originates from the transition of the  $^8\text{S}$  ground state to the excited states  $^6\text{P}$  and  $^8\text{P}([\text{Xe}]4f^65d^1)$ .<sup>11</sup> PL of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  was measured upon excitation of  $\lambda_{\text{ex}} = 525$  nm. The obtained spectrum shows a broad band in the deep red

range of the visible spectrum. This emission band ranges from about 595 to 840 nm with a maximum at about 687 nm and a full width half maximum of about 103 nm ( $2098\text{ cm}^{-1}$ ). Hence, the PL maximum of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  is located in the first bio-imaging window.

The PLE spectra obtained from  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with  $x = 0.02$ , 0.03, and 0.05 are depicted in Fig. 5. The PLE maximum shifts towards longer wavelengths with increasing  $\text{Eu}^{2+}$  concentration. In addition to that, the PLE spectra broaden with increasing  $\text{Eu}^{2+}$

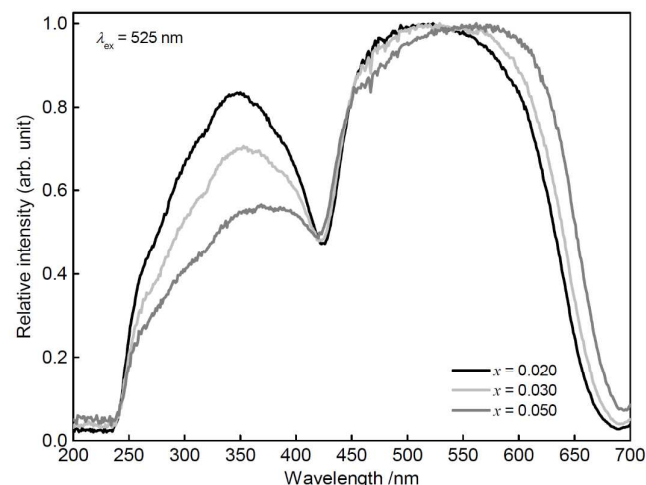


Fig. 5 Room temperature PLE spectra of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various  $\text{Eu}^{2+}$  concentrations.

Table 1 Excitation bands, crystal field splitting, and centroid shift of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various  $\text{Eu}^{2+}$  concentrations

Sample (x)	$\lambda_{\text{ex}}$ range (nm)	crystal field splitting ( $\text{cm}^{-1}$ )	centroid wavenumber ( $\text{cm}^{-1}$ )
0.02	238 ... 697	27670	26596
0.03	237 ... 689	27680	25381
0.05	235 ... 685	27954	23810

concentration. The shift of the excitation maximum is mainly ascribed to a change in covalency. This is verified by calculating the centroid wavenumber of the excitation bands. The results are summarized in Table 1. With increasing  $\text{Eu}^{2+}$  concentration the calculated energy of the centroid wavenumbers decrease. This observation reflects an increase in the covalency of the bonds of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  and is attributed to the higher alkalinity of  $\text{Eu}^{2+}$  compared to  $\text{Sr}^{2+}$ . To investigate the broadening of the excitation band in more detail, the crystal field splitting of the  $d$ -orbitals of  $\text{Eu}^{2+}$  was calculated (see Table 1). With increasing  $\text{Eu}^{2+}$  concentration crystal field splitting increases, too. Since  $\text{Eu}^{2+}$  is slightly smaller than  $\text{Sr}^{2+}$ , the incorporation of  $\text{Eu}^{2+}$  into  $\text{SrSc}_2\text{O}_4$  leads to a smaller Sr site and thus to higher crystal field splitting of the  $d$ -orbitals.

PL spectra of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with  $x = 0.001$ , 0.005, 0.010, 0.020, 0.030, and 0.050 are illustrated in Fig. 6. The spectra were recorded using an excitation wavelength of  $\lambda_{\text{ex}} = 525$  nm. No  $\text{Eu}^{3+}$  emission was observed. Therefore, it is assumed that

the concentration of  $\text{Eu}^{2+}$  corresponds to the amount which was weighed out. With increasing  $\text{Eu}^{2+}$  concentration the PL maximum shifts from 688 to 702 nm. In addition to that, with increasing doping concentration the PL intensity of  $\text{Sr}_{1-x}\text{Eu}_x\text{ScO}_4$  increases up to an  $\text{Eu}^{2+}$  content of  $x = 0.005$ . At higher concentrations the PL intensity decreases due to concentration quenching (inset Fig. 6).

To investigate the mechanism of the energy transfer responsible for concentration quenching, van Uitert's approach was applied:<sup>12</sup>

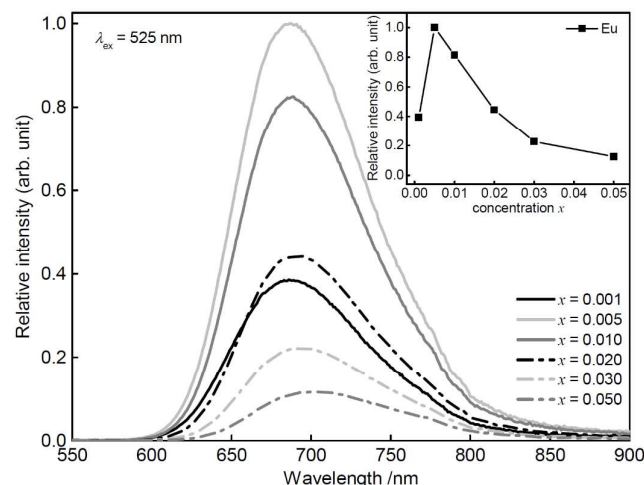


Fig. 6 PL spectra of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various  $\text{Eu}^{2+}$  concentrations. Inset: Integrated PL intensity in dependence of the  $\text{Eu}^{2+}$  concentration.

$$\frac{I}{x} = \frac{k}{1 + Ax^{\vartheta}} \quad (1)$$

Here,  $I$  is the intensity,  $k$  as well as  $A$  are constants, and  $x$  is the concentration of  $\text{Eu}^{2+}$ .  $\vartheta = 3$  corresponds to exchange interaction whereas  $\vartheta = 6, 8,$  and  $10$  corresponds to dipole-dipole, dipole-quadrupole, and quadrupole-quadrupole interaction, respectively. Fig. 7 depicts the experimental data and the fitting curves. The best fitting is obtained for  $\vartheta = 6$  indicating that the mechanism of concentration quenching occurs *via* dipole-dipole interaction. This result is quite reasonable since the transitions of excitation and emission of  $\text{Eu}^{2+}$  are quantum mechanically allowed.

Furthermore, the critical distance  $R_c$  between the  $\text{Eu}^{2+}$  ions was calculated.  $R_c$  is defined as the distance, at which the probability of energy transfer equals the probability of radiative transition. To estimate the critical distance  $R_c$  between  $\text{Eu}^{2+}$  ions in  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  Dexter's formula for dipole-dipole interaction can be used:<sup>13</sup>

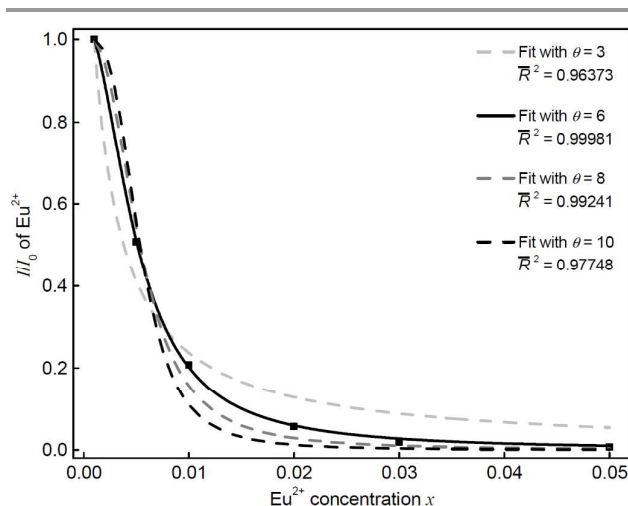


Fig. 7 Dependence of  $I/I_0$  on the  $\text{Eu}^{2+}$  concentration.

$$R_c^6 = 0.63 \times 10^{28} \frac{Q_A}{E^4} \int F_S(E) F_A(E) dE \quad (2)$$

In this equation  $Q_A$  is the absorption cross section of  $\text{Eu}^{2+}$  and  $E$  is the energy of maximum spectral overlap.  $\int F_S(E) F_A(E) dE$  represents the spectral overlap of the normalized PL ( $F_S(E)$ ) and PLE ( $F_A(E)$ ) spectrum of  $\text{Eu}^{2+}$ .  $Q_A$  is  $4.8 \times 10^{-16} f_d$ . Here,  $f_d$  is the oscillator strength of the electronic transitions of  $\text{Eu}^{2+}$  and was taken as 0.02. The spectral overlap integral was calculated to be  $0.03 \text{ eV}^{-1}$ . Plugging these values into eqn 2  $R_c$  is calculated to be  $20.3 \text{ \AA}$ .

In order to examine the temperature behaviour of the PL of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  PL spectra were recorded from 100 to 500 K. The resulting spectra are illustrated in Fig. 8. With increasing temperature the PL intensity gradually decreases. Moreover, the emission maximum shifts from 692 to 680 nm. Due to extending equilibrium distance between  $\text{Eu}^{2+}$  and its surrounding oxygen ligands with increasing temperature, crystal field splitting of the  $d$ -orbitals of  $\text{Eu}^{2+}$  decreases. As a consequence the energetic distance between the  $d$  and  $f$ -orbitals increases and the emission maximum is shifted towards higher energy. The inset of Fig. 8 depicts the integrated PL intensity of the investigated sample. Fitting these data points with a Fermi-Dirac distribution yields the activation energy  $E_A$  for thermal quenching.

$$I(T) = \frac{I_0}{1 + B \times e^{-\frac{E_A}{kT}}} \quad (3)$$

In eqn 3  $I(T)$  is the PL intensity at a certain temperature and  $I_0$  is the PL intensity at zero Kelvin.  $B$  is the frequency factor for thermal quenching,  $k = 8.617 \times 10^{-5} \text{ eV K}^{-1}$  is the Boltzmann constant, and  $T$  is the temperature. Parameters  $I_0$  and  $B$  were derived from the fitting function and are about 0.97 and 2945, respectively. From this  $E_A$  was calculated to be 0.25 eV. By applying  $E_A$  to the following formula,  $T_{1/2}$  can be calculated:

$$T_{1/2} = \frac{-E_A}{k \times \ln\left(\frac{1}{B}\right)} \quad (4)$$

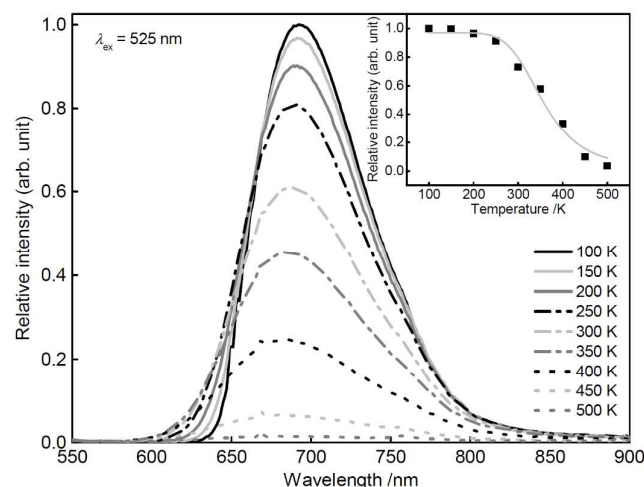


Fig. 8 PL spectra of  $\text{Sr}_{0.995}\text{Eu}_{0.005}\text{Sc}_2\text{O}_4$  from 100 to 500 K. Inset: Integrated PL intensity in dependence of the temperature.

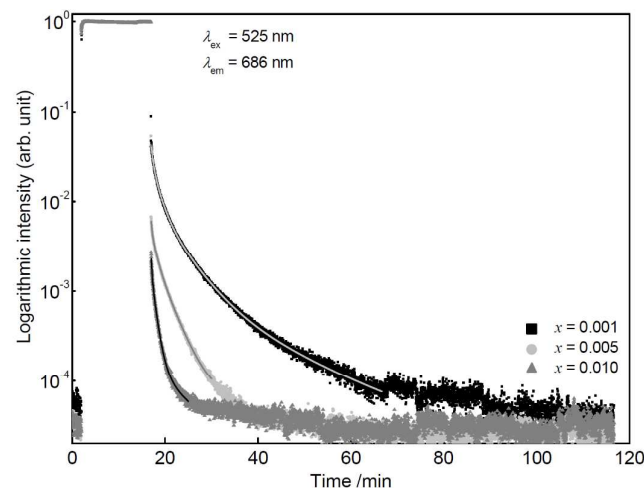


Fig. 9 PLD curves of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with various doping concentrations.

$T_{1/2}$  is the temperature where PL intensity of a luminescent centre decreases to one-half of its maximal intensity. For the herein investigated  $\text{Sr}_{0.995}\text{Eu}_{0.005}\text{Sc}_2\text{O}_4$  sample  $T_{1/2}$  was calculated to be 357 K.

To investigate the persistent luminescence properties of  $\text{Eu}^{2+}$  doped  $\text{SrSc}_2\text{O}_4$ , luminescent lifetime measurements were conducted. For that purpose, the investigated samples were charged for 15 min with an excitation wavelength of  $\lambda_{\text{ex}} = 525$  nm. Fig. 9 shows the obtained PLD curves of  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  with  $x = 0.001, 0.005,$  and  $0.010$ . The longest afterglow duration was found for  $\text{Sr}_{0.999}\text{Eu}_{0.001}\text{Sc}_2\text{O}_4$ . The corresponding PLD curve can be best fitted with the following equation:

$$I = A_1 \cdot e^{-\frac{t}{\tau_1}} + A_2 \cdot e^{-\frac{t}{\tau_2}} + A_3 \cdot e^{-\frac{t}{\tau_3}} + A_4 \cdot e^{-\frac{t}{\tau_4}} \quad (5)$$

Here,  $I$  is the PL intensity,  $A_1, A_2, A_3,$  and  $A_4$  are fitting parameters, and  $t$  is the time.  $\tau_1, \tau_2, \tau_3,$  and  $\tau_4$  are the partial luminescence lifetimes of the exponential components. The average luminescence lifetime can be obtained using eqn 6:

$$\tau = \frac{A_1\tau_1^2 + A_2\tau_2^2}{A_1\tau_1 + A_2\tau_2} \quad (6)$$

Partial lifetimes and their corresponding emission fractions as well as the calculated average lifetime  $\tau$  are summarized in Table 2. With increasing  $\text{Eu}^{2+}$  content the PL lifetime of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  decreases and the PLD curve becomes tri-exponential.

It is well known that additional incorporation of  $\text{Dy}^{3+}$  into  $\text{Eu}^{2+}$  doped materials can lead to long lasting persistent phosphors.<sup>14</sup> In order to investigate the influence of  $\text{Dy}^{3+}$  co-doping on the afterglow duration, additional luminescence lifetime measurements were performed on  $\text{Sr}_{0.998}\text{Eu}_{0.001}\text{Dy}_{0.001}\text{Sc}_2\text{O}_4$  and  $\text{Sr}_{0.994}\text{Eu}_{0.001}\text{Dy}_{0.005}\text{Sc}_2\text{O}_4$ . Fig. 10 illustrates the PLD curves of co-doped  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}, \text{Dy}^{3+}$ . Analogous to  $\text{Eu}^{2+}$ , with increasing  $\text{Dy}^{3+}$  concentration the afterglow duration decreases. Another possibility to enhance

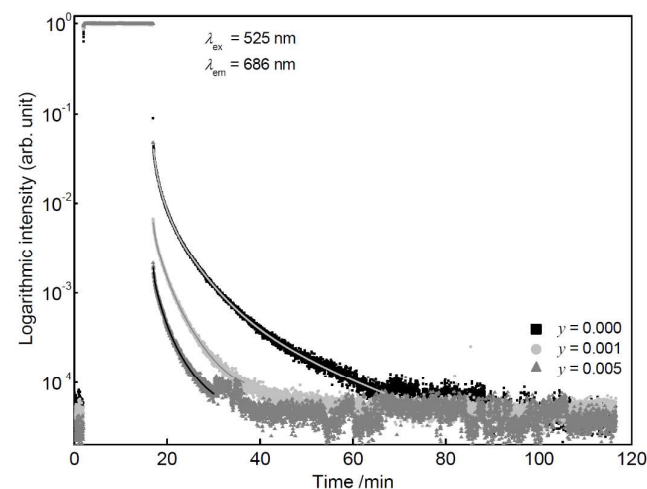


Fig. 10 PLD curves of  $\text{Sr}_{0.999-y}\text{Eu}_{0.001}\text{Dy}_y\text{Sc}_2\text{O}_4$  with different concentrations of  $\text{Dy}^{3+}$ .

the afterglow duration of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  could be co-doping with  $\text{Cr}^{3+}$ .<sup>15</sup> Further experiments should be performed to investigate the influence of  $\text{Cr}^{3+}$  co-doping on the persistent luminescence properties of  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$ .

Fig. 11a depicts the luminance in dependence of the time. For comparison the solid line visualises the luminance value  $0.32 \text{ mcd} \times \text{m}^{-2}$  which is the minimum value commonly used for safety signage.<sup>16</sup> The dashed line illustrates the limit of the sensitivity of the dark-adapted eye. For the  $\text{Sr}_{0.999}\text{Eu}_{0.001}\text{Sc}_2\text{O}_4$  sample  $0.32 \text{ mcd} \times \text{m}^{-2}$  is reached after about 6 min. Absolute radiance is plotted in Figure 11b. The absolute radiance values obtained after charging the sample for 15 min are considerably smaller compared to other deep red emitting persistent phosphors.<sup>17,18</sup>

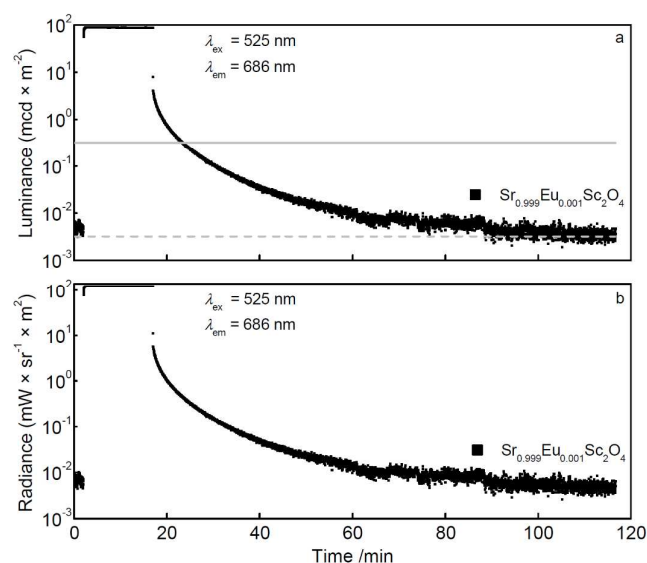


Fig. 11 Persistent luminescence curves of  $\text{Sr}_{0.999}\text{Eu}_{0.001}\text{Sc}_2\text{O}_4$ : luminance a) and radiance b) of the  $\text{Eu}^{2+}$  emission.

Table 2 Persistent luminescence lifetimes  $\tau$  as well as partial lifetimes  $\tau_1$ ,  $\tau_2$ ,  $\tau_3$ , and  $\tau_4$  and the emission fractions  $\text{frac}_1$ ,  $\text{frac}_2$ ,  $\text{frac}_3$ , and  $\text{frac}_4$  of  $\text{Eu}^{2+}$  in  $\text{Sr}_{1-x}\text{Eu}_x\text{Sc}_2\text{O}_4$  and  $\text{Sr}_{1-x}\text{Eu}_x\text{Dy}_y\text{Sc}_2\text{O}_4$

Sample (x, y)	$\tau_1$ (s)	$\text{frac}_1$ (%)	$\tau_2$ (s)	$\text{frac}_2$ (%)	$\tau_3$ (s)	$\text{frac}_3$ (%)	$\tau_4$ (s)	$\text{frac}_4$ (%)	$\tau$ (s)
0.001, 0.000	21.7	4.8	88.3	27.4	293.6	47.3	1007.4	20.6	371
0.005, 0.000	10.4	2.3	57.9	18.7	193.6	79.0			164
0.010, 0.000	9.6	6.2	56.1	59.7	283.8	34.1			131
0.001, 0.001	16.2	3	93.7	32.0	271.1	65.0			207
0.001, 0.005	9.2	2.0	84.8	32.2	257.0	65.9			197

## 4. Conclusions

$\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  powder samples were prepared and its PL properties were investigated, also time and temperature dependent.  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  shows a broad emission band in the deep red region of the spectrum with a maximum at about 687 nm. This deep red lying emission band is quite rare for oxidic host materials doped with  $\text{Eu}^{2+}$ .<sup>1</sup> Further, no  $\text{Eu}^{3+}$  emission was observed. The highest PL intensity was found for a  $\text{Eu}^{2+}$  concentration of  $x = 0.005$ . At a higher  $\text{Eu}^{2+}$  concentration the PL intensity decreases due to concentration quenching caused by energy transfer between  $\text{Eu}^{2+}$  ions, likely resulting in energy migration to defect states. It turned out that in  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  energy transfer between  $\text{Eu}^{2+}$  ions is of a resonance type and occurs *via* dipole-dipole interaction. The critical distance  $R_c$  was calculated to be about 20.3 Å. Temperature dependent PL measurements revealed a  $T_{1/2}$  value of 357 K. Additionally, it was found that  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  shows deep red persistent luminescence after charging it with an excitation wavelength of  $\lambda_{\text{ex}} = 525$  nm. The longest afterglow duration was found for the sample  $\text{Sr}_{0.999}\text{Eu}_{0.001}\text{Sc}_2\text{O}_4$ . This sample reaches the value of

0.32  $\text{mcd} \times \text{m}^{-2}$  after about 6 min what is considerably shorter than for comparable materials.<sup>17,18</sup> No increase in afterglow duration could be observed if  $\text{SrSc}_2\text{O}_4:\text{Eu}^{2+}$  was additionally doped by  $\text{Dy}^{3+}$ . For this reason, it would be worth the effort to try to increase the afterglow duration by doping with additional ions like  $\text{Cr}^{3+}$ .

## Acknowledgements

The authors are grateful to Merck KGaA Darmstadt, Germany for generous financial support.

## References

- D. Deng, H. Yu, Y. Li, Y. Hua, G. Jia, S. Zhao, H. Wang, L. Huang, Y. Li, C. Li and S. Xu, *J. Mater. Chem. C*, 2013, **1**, 3194.
- a) K. Song, J. Zhang, Y. Liu, C. Zhang, J. Jiang, H. Jiang and H.-B. Qin, *J. Phys. Chem. C*, 2015, **119**, 24558–24563; b) R. Yu, N. Xue, T. Wang, Z. Zhao, J. Wang, Z. Hei, M. Li, H. Mi Noh and J. Hyun Jeong, *Ceram. Int.*, 2015, **41**, 6030–6036.

- 3 P. Pust, V. Weiler, C. Hecht, A. Tücks, A. S. Wochnik, A.-K. Henß, D. Wiechert, C. Scheu, P. J. Schmidt and W. Schnick, *Nat. Mater.*, 2014, **13**, 891–896.
- 4 a) R.-J. Xie, N. Hirosaki, T. Suehiro, F.-F. Xu and M. Mitomo, *Chem. Mater.*, 2006, **18**, 5578–5583; b) S. Tezuka, Y. Sato, T. Komukai, Y. Takatsuka, H. Kato and M. Kakihana, *Appl. Phys. Express*, 2013, **6**, 72101.
- 5 a) S. H. M. Poort, H. M. Reijnhoudt, H. O. T. van der Kuip and G. Blasse, *J. Alloy. Compd.*, 1996, **241**, 75–81; b) S. H. M. Poort and G. Blasse, *J. Lumin.*, 1997, **72-74**, 247–249.
- 6 W. Zhang, R. Hua, T. Liu, J. Zhao, L. Na and B. Chen, *Mater. Res. Bull.*, 2014, **60**, 247–251.
- 7 a) C. Chang, J. Xu, L. Jiang, D. Mao and W. Ying, *Mater. Chem. Phys.*, 2006, **98**, 509–513; b) B. Zhang, C. Zhao and D. Chen, *Luminescence*, 2010, **25**, 25–29.
- 8 a) J. Zhang, Y.-L. Liu and S.-q. Man, *J. Lumin.*, 2006, **117**, 141–146; b) X. Duane, S. Huang, F. You and K. Kang, *J. Rare Earths*, 2009, **27**, 43–46; c) S. K. Singh, *RSC Adv*, 2014, **4**, 58674–58698.
- 9 J. R. Carter and R. S. Feigelson, *J. Am. Ceram. Soc.*, 1964, **47**, 141–144.
- 10 R. D. Shannon, *Acta Crystall. A-Crys.*, 1976, **A32**, 751–767.
- 11 a) G. Blasse, *Phys. Stat. Sol. B*, 1973, **55**, K131-K134; b) G. Blasse and B. C. Grabmaier, *Luminescent Materials*, Springer-Verlag, Berlin/Heidelberg, 1st edn., 1994.
- 12 L. G. van Uitert, *J. Electrochem. Soc.*, 1967, **114**, 1048.
- 13 a) D. L. Dexter, *J. Chem. Phys.*, 1953, **21**, 836; b) G. Blasse, *Philips Res. Rep.*, 1969, **24**, 131–144.
- 14 a) I. P. Sahu, D. P. Bisen, N. Brahme and M. Ganjir, *Luminescence*, 2015, **30**, 1318–1325; b) B. K. Gupta, A. Kumar, P. Kumar, J. Dwivedi, G. N. Pandey and G. Kedawat, *J. Appl. Phys.*, 2015, **117**, 243104; c) P. Wang, X. Xu, D. Zhou, X. Yu and J. Qiu, *Inorg. Chem.*, 2015, **54**, 1690–1697.
- 15 a) H. Ryu and K. S. Bartwal, *J. Alloy. Compd.*, 2008, **464**, 317–321; b) J. Ueda, K. Kuroishi and S. Tanabe, *Appl. Phys. Express*, 2014, **7**, 62201.
- 16 K. van den Eeckhout, D. Poelman and P. Smet, *Materials*, 2013, **6**, 2789–2818.
- 17 J. Xu, S. Tanabe, A. D. Sontakke and J. Ueda, *Appl. Phys. Lett.*, 2015, **107**, 81903.
- 18 Y. Zhuang, J. Ueda and S. Tanabe, *Appl. Phys. Express*, 2013, **6**, 52602.





Under ambient light



Under 366 nm illumination

