

**Iron Catalyzed CO₂ Hydrogenation to Formate Enhanced by
Lewis Acid Co-Catalysts**

| | |
|-------------------------------|---|
| Journal: | <i>Chemical Science</i> |
| Manuscript ID: | SC-EDG-04-2015-001467.R1 |
| Article Type: | Edge Article |
| Date Submitted by the Author: | 14-May-2015 |
| Complete List of Authors: | Zhang, Yuanyuan; Brown University, Chemistry MacIntosh, Alex; Brown University, Chemistry Wong, Janice; Yale University, Department of Chemistry Bielinski, Elizabeth; Yale University, Department of Chemistry Williard, Paul; Brown University, Department of Chemistry Mercado, Brandon; Yale University, Department of Chemistry Hazari, Nilay; Yale University, Department of Chemistry Bernskoetter, Wesley; Brown University, Chemistry |
| | |

Iron Catalyzed CO₂ Hydrogenation to Formate Enhanced by Lewis Acid Co-Catalysts

Yuanyuan Zhang,^{a,†} Alex D. MacIntosh,^{a,†} Janice L. Wong,^b Elizabeth A. Bielinski,^b Paul G. Williard,^a Brandon Q. Mercado,^b Nilay Hazari^{b,*} and Wesley H. Bernskoetter^{a,*}

^a*The Department of Chemistry, Brown University, Providence, RI 02912*

^b*The Department of Chemistry, Yale University, New Haven, CT 06520*

e-mail: nilay.hazari@yale.edu; wb36@brown.edu

Abstract

A family of iron(II) carbonyl hydride complexes supported by either a bifunctional PNP ligand containing a secondary amine, or a PNP ligand with a tertiary amine that prevents metal-ligand cooperativity, were found to promote the catalytic hydrogenation of CO₂ to formate in the presence of Brønsted base. In both cases a remarkable enhancement in catalytic activity was observed upon the addition of Lewis acid (LA) co-catalysts. For the secondary amine supported system, turnover numbers of approximately 9,000 for formate production were achieved, while for catalysts supported by the tertiary amine ligand, nearly 60,000 turnovers were observed; the highest activity reported for an earth abundant catalyst to date. The LA co-catalysts raise the turnover number by more than an order of magnitude in each case. In the secondary amine system, mechanistic investigations implicated the LA in disrupting an intramolecular hydrogen bond between the PNP ligand N-H moiety and the carbonyl oxygen of a formate ligand in the catalytic resting state. This destabilization of the iron-bound formate accelerates product extrusion, the rate-limiting step in catalysis. In systems supported by ligands with the tertiary amine, it was demonstrated that the LA enhancement originates from cation assisted substitution of formate for dihydrogen during the slow step in catalysis.

[†] These authors made equal contribution.

Introduction

The increasing volatility in price and the negative environmental impact associated with fossil fuel utilization for energy and commodity chemical production continues to spur basic research into the exploitation of renewable carbon resources.¹ CO₂ is an attractive target for transitioning the chemical industry to sustainable feedstocks, due to its incredible abundance, cheap availability and low toxicity.² Formic acid is an especially interesting CO₂ reduction product given its use in numerous agrochemicals and preservatives,³ as well as its potential role as a material for chemical hydrogen storage (CHS) in renewable energy applications.⁴ The utilization of formic acid as a CHS material requires reversible hydrogenation/dehydrogenation between CO₂ and formic acid, a reaction with a small thermodynamic preference (7 kcal/mol) toward CO₂ and H₂ in the gas phase.⁵ Consequently, most catalysts for the hydrogenation of CO₂ to formic acid rely on exogenous base to form formate, which drives the reaction.⁶ The most effective of these catalysts employ precious metals such as ruthenium,⁷ rhodium,⁸ and iridium,⁹ and turnover numbers (TONs) of approximately 3.5×10^6 and turnover frequencies (TOFs) near 150,000 h⁻¹ have been achieved at elevated pressures and temperatures (49-59 atm; 120-220 °C).¹⁰ These findings demonstrate the remarkable potential for catalytic CO₂ hydrogenation to formate, but also motivate the development of earth abundant catalytic systems, which are expected to enhance the sustainability and economic feasibility of this transformation.

Although homogeneous catalysts for CO₂ hydrogenation to formate containing first-row transition metals were first described in 1976,¹¹ TONs were low. As a result for many decades significantly more attention was devoted to the study of heterogeneous catalysts containing first-row transition metals.¹² However, in recent years, the development of homogenous catalysts has been reinvigorated by the discovery of several more active cobalt and iron based systems.¹³ For example, Fujita *et al.* reported a Cp*Co (Cp* = η^5 -C₅Me₅) complex supported by a dihydroxy-

bipyridine ligand that is capable of 59 turnovers to formate in aqueous bicarbonate,¹⁴ while Linehan and coworkers described an even more impressive TON of 9400 using $(\text{Me}_2\text{PCH}_2\text{CH}_2\text{PMe}_2)_2\text{CoH}$, although the use of a costly and strong base (Verkade's base) is required for high conversion.¹⁵ During the same time period, Beller and coworkers described both cobalt and iron catalysts supported by tetraphosphine ligands, with the $[\text{P}(o\text{-C}_6\text{H}_4\text{PPh}_2)_3\text{Fe}]^{2+}$ congener affording the highest TON for an iron catalyst to date.¹⁶ This *in situ* generated system afforded 1897 turnovers to formate in methanol/water with excess NEt_3 under 60 atm of CO_2/H_2 at 100 °C.^{16b} Another noteworthy iron system was reported by Milstein and coworkers who showed that a complex supported by pincer ligand with a pyridine backbone could give 708 turnovers under remarkably mild pressures (8-10 atm) in 2M aqueous NaOH.¹⁷ Collectively these discoveries establish that earth abundant metals are capable of promoting CO_2 hydrogenation, but their activities lag far beyond those of precious metal catalysts.

Our laboratories recently identified iron catalysts for formic acid dehydrogenation (FADH), the reverse of CO_2 hydrogenation, which surpass even precious metal catalysts in activity.¹⁸ The iron(II) formate carbonyl hydride species, $(^{\text{R}}\text{PNP})\text{Fe}(\text{H})\text{CO}(\text{HCO}_2)$ ($^{\text{R}}\text{PNP} = \text{HN}\{\text{CH}_2\text{CH}_2(\text{PR}_2)\}_2$; R = ⁱPr (**HCO₂-1a**), R = Cy (**HCO₂-1b**)), bearing a bifunctional amido ligand give 1×10^6 turnovers for FADH with a TOF near 200,000 h^{-1} (Figure 1). Slightly diminished performance was also observed using the five-coordinate iron(II) species, $((^{\text{R}}\text{PNP})\text{Fe}(\text{H})\text{CO}$; R = ⁱPr (**1a**), R = Cy (**1b**)), which readily form **HCO₂-1a** and **HCO₂-1b** upon exposure to formic acid. The impressive activity is dependent on the presence of a Lewis acid (LA) co-catalyst, such as LiBF_4 , which preliminary mechanistic studies indicate aids in the decarboxylation of an iron-formate intermediate. Herein we report the development of a collection of iron complexes based on this PNP ligand motif, which catalyze the hydrogenation

of CO₂ to formate with TONs approaching 60,000, far greater than any previously described earth abundant metal catalyst. These high TONs are only achieved in the presence of a LA co-catalyst and we describe detailed mechanistic studies which elucidate the crucial role of the LA.

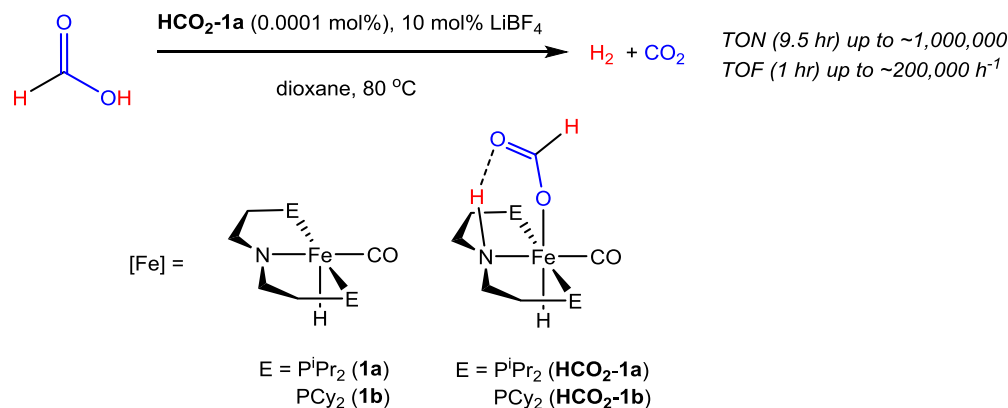


Figure 1. Iron-LA co-catalyzed dehydrogenation of formic acid.

Results and Discussion

CO₂ Hydrogenation Activity of (^RPNP)Fe(H)CO. The mildly endergonic profile of CO₂ hydrogenation to formic acid has led researchers to employ a wide variety of exogenous bases to drive this reaction. Given the limited stability of **1a** and **1b** in aqueous environments,¹⁹ our initial catalytic experiments focused on identifying suitable bases with moderate to good solubility in organic solvents. A brief screen of bases using **1b** in THF and a combined 69 atm of CO₂/H₂ (1:1) at 80 °C indicated that Cs₂CO₃ and 1,8-diazabicycloundec-7-ene (DBU) were among the most effective bases in promoting formate production (Table S1). For subsequent investigations, DBU was selected as the base of choice owing to its higher solubility in THF and moderately better TON compared to Cs₂CO₃. The TON of 78 observed using DBU indicates that **1b** is, at best, a modest catalyst for CO₂ reduction by itself. However, addition of LiBF₄ dramatically improved the conversion.²⁰ Conducting catalytic reactions using **1a** and **1b** in the presence of a LA (2:1 ratio of DBU:LiBF₄) afforded a *ca* 3-4 fold increase in TON, with the -PCy₂ substituted **1b** showing a slightly higher conversion (Table 1). A screen of LiBF₄ loadings between

DBU:LiBF₄ ratios of 150:1 to 2:1 showed an onset of saturation behavior below 6:1 (Table S2), thus a DBU:LA ratio of 7.5:1 was employed as the benchmark co-catalyst loading for most catalytic experiments reported here. This loading balances the higher conversions at increased LA loadings with possible complications arising from solubility limitations.

Table 1. Lewis acid enhancement of CO₂ hydrogenation catalyzed by **1a** and **1b**.^a

$$\text{CO}_2 + \text{H}_2 \xrightarrow[1500\text{eq DBU, THF, } 80^\circ\text{C, 16 h}]{0.78 \mu\text{mol } \mathbf{1a/1b}} \text{H}-\text{C}(=\text{O})-\text{O}^- \quad \text{DBUH}^+$$

| Entry | Catalyst | DBU/LiBF ₄ | TON ^b | Yield (%) ^c |
|-------|-----------|-----------------------|------------------|------------------------|
| 1 | 1a | no LiBF ₄ | 240 | 16 |
| 2 | 1b | no LiBF ₄ | 430 | 28 |
| 3 | 1a | 2/1 | 1010 | 67 |
| 4 | 1b | 2/1 | 1220 | 82 |

^aReaction conditions: 69 atm of CO₂:H₂ (1:1), 0.78 μmol of **1a** or **1b** in 5 mL THF (*ca.* 0.015 M), 180 mg DBU at 80 °C. ^bFormate production quantified by ¹H NMR spectroscopy; reported values are the average of three trials. ^cReported yields are based on DBU:formate of 1:1.

In our previous work on LA enhanced FADH we screened a large range of Lewis acidic salts and identified LiBF₄ as the optimum co-catalyst.¹⁸ A more limited examination of LAs was conducted for the CO₂-to-formate reaction with an emphasis on using readily available alkali metal salts (Table 2). Entries 2-4 show the superior performance of the trifluoromethanesulfonate anion (OTf) compared to BF₄⁻ or Cl⁻. In the case of Cl⁻, an inhibition of the reaction compared to no added LA was observed, likely due to coordination of Cl⁻ to the iron catalyst. Additional comparison of the three lightest alkali metal OTf salts (entries 4-6) indicated good TON for all species, with a slightly higher conversion for the Li cation.

The incongruous reaction conditions employed across most iron and cobalt catalyzed CO₂ hydrogenation reactions make a definitive comparison of catalyst activity challenging. The *ca.* 3,000 TON observed for the LiOTf/**1b** catalyzed CO₂-to-formate reaction (Table 2; entry 4) is higher than any other iron mediated system to date and it functions under comparable reaction conditions to the [P(*o*-C₆H₄PPh₂)₃Fe]²⁺ catalyst described by Beller.^{16b} The LA/Fe co-catalyzed

reaction is also far more active than cobalt catalysts when DBU is employed as the common base, although higher TONs are achieved with cobalt under different reaction conditions.¹⁵

Table 2. Lewis acid screening for CO₂ hydrogenation catalyzed by **1b**.^a

$$\text{CO}_2 + \text{H}_2 \xrightarrow[5000\text{eq DBU, LA, THF, } 80^\circ\text{C, 24 h}]{0.78 \mu\text{mol } \mathbf{1b}} \text{H}-\text{C}(=\text{O})-\text{O}^- \text{ DBUH}^+$$

| Entry | LA | DBU/LA | TON ^b | Yield (%) ^e |
|----------|-------------------|--------|-------------------|------------------------|
| 1 | no LA | no LA | 880 | 17 |
| 2 | LiCl ^d | 7.5/1 | 190 | 4 |
| 3 | LiBF ₄ | 7.5/1 | 2250 | 45 |
| 4 | LiOTf | 7.5/1 | 3070 ^c | 61 |
| 5 | NaOTf | 7.5/1 | 2520 | 50 |
| 6 | KOTf | 7.5/1 | 2680 | 54 |

^aReaction conditions: 69 atm of CO₂:H₂ (1:1), 0.78 μmol of **1b** in 5 mL THF (ca. 0.015 M), 600 mg DBU (3.94 mmol) at 80 °C. ^bFormate production quantified by ¹H NMR spectroscopy. ^cReported value is the average of two trials. ^dLiCl was not fully soluble at ambient temperature under these conditions. ^eReported yields are based on DBU:formate of 1:1.

Synthesis and Characterization of [^RPN^{Me}PFe] Complexes. A potentially important feature of **1** is that it can undergo reactions in which there is metal-ligand cooperation²¹ due to the ability of the PNP ligand to be in either a protonated or deprotonated form.^{18-19,22} Beller and coworkers have recently reported the synthesis of MeN{CH₂CH₂(PⁱPr₂)₂}₂ and its coordination to iron as part of control experiments relating to catalytic nitrile and ester hydrogenation.²³ To further explore the role of the bifunctional ligand we were interested in comparing the activity for CO₂ hydrogenation of iron complexes supported by both ^RPN^HP and ^RPN^{Me}P ligands. In our hands both the isopropyl and cyclohexyl versions of ^RPN^{Me}P were coordinated to FeCl₂ by stirring in THF solution to give excellent yields of (^RPN^{Me}P)FeCl₂ (Figure 2). Each species displays a set of broad peaks between ca -5 and 75 ppm in the ¹H NMR spectrum, indicative of a paramagnetic substance. The molecular structure of (ⁱPrPN^{Me}P)FeCl₂ was confirmed by X-ray diffraction (Figure S16) and exhibited a distorted square pyramidal geometry (τ = 0.37).²⁴ Treatment of these iron(II) dichloride species with sodium borohydride in MeCN/EtOH afforded the six-coordinate (^RPN^{Me}P)Fe(H)BH₄ species (Figure 2). The structure of the PⁱPr₂ congener

was characterized by X-ray diffraction as depicted in Figure S17. The data were of sufficient quality that all hydrogen atoms, including those bound to iron and boron, were located in the difference map and clearly indicate a κ^2 -coordination of the BH_4 ligand.

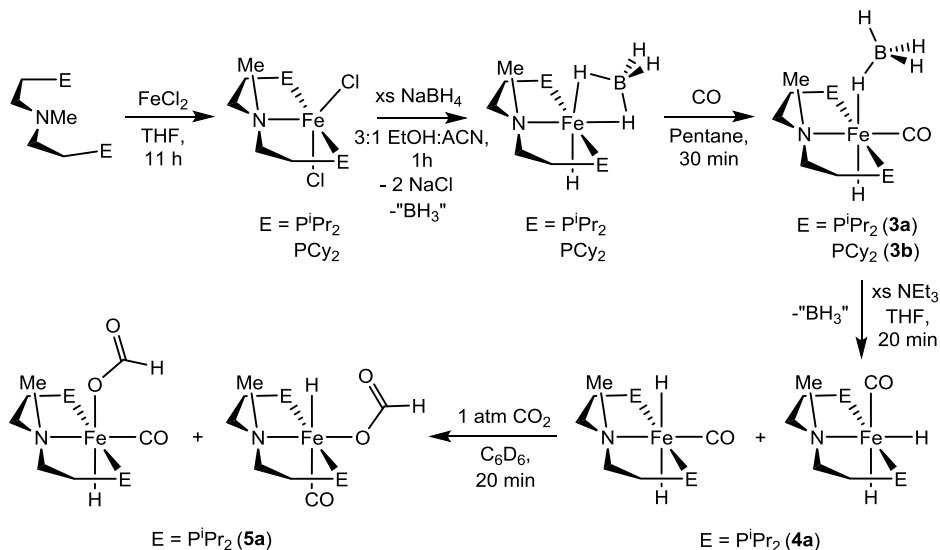


Figure 2. Synthesis of $[\text{RPN}^{\text{Me}}\text{PF}]$ complexes.

The $(\text{RPN}^{\text{Me}}\text{P})\text{Fe}(\text{H})\text{BH}_4$ species each react readily with 1 atm of CO to yield $(\text{RPN}^{\text{Me}}\text{P})\text{Fe}(\text{H})\text{CO}(\text{BH}_4)$ ($\text{R} = i\text{Pr}$ (**3a**), $\text{R} = \text{Cy}$ (**3b**)) as yellow compounds (Figure 2). The highest purity materials were obtained from syntheses conducted in pentane over short reaction times (30-45 minutes). ^1H NMR spectra of **3a** and **3b** in benzene- d_6 each display an iron-hydride resonance near -20 ppm and a very broad borohydride signal around -2.5 ppm. The broad resonance of the BH_4 fragment is typical of κ^1 -coordinated species and suggests a rapid interchange of the bound B-H bond on the NMR timescale.²⁵ The P^iPr_2 congener, **3a**, again provided a solid state structure from X-ray diffraction experiments (Figure S18), which confirms the κ^1 -coordination of BH_4 and the binding of CO ligand *trans* to the tertiary amine.

The thermal stability of **3a** in benzene or THF was limited. Even upon standing under an N_2 atmosphere for 1 hour, new Fe-H resonances began to appear in the ^1H NMR spectrum. These resonances, along with signals in the ^{31}P NMR spectrum, are consistent with those previously

described by Beller and coworkers for the *cis* and *trans* dihydride isomers of $(i\text{PrPN}^{\text{Me}}\text{P})\text{Fe}(\text{H})_2\text{CO}$ (**4a**).^{23,26} The conversion of **3a** to **4a** appears to be influenced by solvent and exposure to vacuum, with use of THF and lower pressures enhancing formation of the iron(II) dihydride species. Pure samples of **4a** were obtained by treatment of **3a** with a large excess of NEt_3 and crystallization from pentane at low temperature. Crystal samples of **4a** obtained at $-30\text{ }^\circ\text{C}$ consistently afforded a molecular structure of the *cis* dihydride isomer (Figure S19), including characterization of two polymorphs of the material.²⁷ However, solutions prepared from the crystalline material consistently show a 3:1 ratio favoring the *trans* dihydride isomer. EXSY NMR experiments (mixing time 800 ms at $22\text{ }^\circ\text{C}$) do not display correlations indicative of rapid isomer interconversion on the NMR timescale, but the consistent ratio from multiple samples suggests isomerization likely occurs over longer time periods.

The addition of 1 atm of CO_2 to **4a** generated the iron formate complex **5a** as a 5:1 mixture of two isomers (Figure 2). The major isomer of **5a** exhibits an Fe-H resonance at -23.89 ppm ($^3J_{\text{P-H}} = 52$ Hz) and a formate C-H peak at 9.22 ppm in the ^1H NMR spectrum along with a signal at 84.81 ppm in the $^{31}\text{P}\{^1\text{H}\}$ NMR spectrum. The minor isomer displays similar resonances, which are illustrated in the Electronic Supplementary Information. A structural assignment of the isomers of **5a** was based on a combination of 2D NOESY, ^{13}C O isotopic labeling and X-ray diffraction experiments. Cooling a diethyl ether solution of **5a** to $-35\text{ }^\circ\text{C}$ yielded small yellow needles which weakly diffracted X-rays. While the data was marginal (requiring all hydrogens not bound to iron to be calculated) the refinement did afford a satisfactory solution with the molecular structure depicted in Figure S20. The crystalized isomer of **5a** contains a *meridional* chelate ligand with the formate moiety positioned proximal to the N-Me substituent. The Fe-H bond is located *trans* to the formate ligand and *cis* to the iron-carbonyl.

Additional structural evidence was obtained from 2D NOESY NMR spectra (23 °C, 300 ms mixing time) which indicated a through space correlation between the Fe-H and N-CH₃ resonances for at least one of the isomers of **5a**, though overlap between the isomers obviated assignment for this correlation to a specific isomer. Still, the NOESY NMR data indicated that the Fe-H and N-CH₃ fragments are on the same face of the iron coordination environment for one isomer, presumably the one not identified by X-ray diffraction.²⁸ Isotopic labeling of **5a** with ¹³CO afforded ²J_{C-H} coupling constants between the bound ¹³CO and Fe-H of 19.5 and 23.9 Hz for the major and minor isomers, respectively. The larger coupling constant for the minor isomer indicates a *trans* disposition of these fragments, which along with the NOESY NMR data and X-ray diffraction study is consistent with the isomers depicted in Figure 2. This collection of data also suggests the structure determined by X-ray diffraction is the major isomer.

CO₂ Hydrogenation Activity of [RPN^{Me}PFe] Complexes. With several [RPN^{Me}PFe] complexes in hand, the metal-hydride containing species (^{iPr}PN^{Me}P)Fe(H)BH₄, **3a** and **4a** were each screened for CO₂ hydrogenation under the conditions described for **1b**/LiOTf in Table 2. Although (^{iPr}PN^{Me}P)Fe(H)BH₄ proved to be an ineffective catalyst with a TON = 52 (a conversion comparable to the reaction without iron catalyst), both **3a** and **4a** afforded very high conversions with TONs of 7660 and 6900, respectively (Table 3). The observed formate yields were in excess of the equivalents of DBU employed; however, stabilization of multiple formate ions by a single DBU via homoconjugation has been previously observed.^{15b,29} The dramatic improvement in catalyst performance using the N-methylated ligand necessitated trials at lower catalyst and higher DBU loadings to better elucidate their optimum performance. Given the comparable activity of **3a** and **4a** in preliminary experiments, the relative ease in obtaining **3a** made it a more convenient choice for exploratory catalytic trials (Table 3). Only when the

catalyst loading was dropped to 0.30 μmol and the DBU/Fe ratio raised to *ca* 40,000 did the yield of formate decrease below the concentration of DBU employed. At *ca* 80,000 equivalents of base per iron an impressive 42,347 turnovers to formate were observed. Further enhancement of the conversion to nearly 60,000 TON was achieved by raising the LiOTf co-catalyst loading to 5/1 with base, however, at this loading not all of the LiOTf appeared to dissolve and further increasing LiOTf amounts did not enhance the conversion. The central role of the LA co-catalyst was demonstrated in a control experiment where the absence of LiOTf drops the TON to a meager 2,790. Overall, this remarkably active catalyst system affords TONs more than an order of magnitude greater than any previously reported iron catalysts.

Table 3. CO₂ hydrogenation catalyzed by **3a**.^a

$$\text{CO}_2 + \text{H}_2 \xrightarrow[\text{DBU, LiOTf, THF, 80 }^\circ\text{C, 24h}]{0.30-0.78 \mu\text{mol } \mathbf{3a/4a}} \text{H}-\text{C}(=\text{O})-\text{O}^- \quad \text{DBUH}^+$$

| Catalyst | [Fe] (μmol) | DBU/Fe | DBU/LiOTf | TON ^b | Yield (%) ^d |
|-----------|--------------------------|--------|-----------|---------------------|------------------------|
| 3a | 0.78 | 5,000 | 7.5/1 | 7,660 | >99 |
| 4a | 0.78 | 5,000 | 7.5/1 | 6,900 | >99 |
| 3a | 0.30 | 39,800 | 7.5/1 | 34,030 | 85 |
| 3a | 0.30 | 79,600 | 7.5/1 | 42,350 ^c | 53 |
| 3a | 0.30 | 79,600 | 5/1 | 58,990 ^c | 74 |
| 3a | 0.30 | 79,600 | No LiOTf | 2,790 | 4 |

^aReaction conditions: 69 atm of CO₂:H₂ (1:1), 0.30 or 0.78 μmol of **3a** or **4a** in 5 mL or 10 mL THF at 80 °C for 24 hours. ^bFormate production quantified by ¹H NMR spectroscopy. ^cReported values are average of two trials. ^dReported yields are based on DBU:formate of 1:1.

Table 4 provides a comparison of each of the iron CO₂ hydrogenation catalysts described herein.³⁰ Each trial was conducted under 69 atm of CO₂:H₂ (1:1) with 0.30 - 0.78 μmol catalyst, and 79,600 equiv. of DBU with a 7.5:1 loading of base to LiOTf in THF at 80 °C. Under these conditions the secondary amine containing complexes **1a** and **1b** (entries 2 and 3) improve their TONs to 6,030 and 8,910, respectively, over 24 hours. Trials conducted at longer reaction times did not improve the conversion indicating the catalysts had completely deactivated after 1 day.

Table 4. Comparison of iron catalysts for CO₂ hydrogenation to formate.^a


| Entry | Catalyst | DBU/LiOTf ^f | TOF (1h) ^b | TON (24h) ^{b,c} | Yield (%) ^d |
|-------|-----------|------------------------|-----------------------|--------------------------|------------------------|
| 1 | 1a | 7.5/1 | 1,290 | 6,030 | 8 |
| 2 | 1b | 7.5/1 | 1,830 | 8,910 | 11 |
| 3 | 2a | 7.5/1 | 680 | 1,500 | 2 |
| 4 | 3a | 7.5/1 | 18,050 | 42,350 | 53 |
| 5 | 3b | 7.5/1 | 20,490 | 46,110 | 58 |
| 6 | 4a | 7.5/1 | 18,410 | 38,970 | 49 |
| 7 | 5a | 7.5/1 | 23,190 | 46,130 | 58 |

^aReaction conditions: 69 atm of CO₂:H₂ (1:1), 0.3 μmol of catalyst in 10 mL THF (*ca.* 0.01 M), 3.600 g DBU at 80 °C. ^bFormate production quantified by ¹H NMR spectroscopy. TOF was measured after first hour including a temperature equilibration period (< 10 min). ^cReported values are average of two trials. ^dReported yields are based on DBU:formate of 1:1.

Use of the borohydride analog, (ⁱPrPNP)Fe(H)CO(BH₄) (**2a**), a feasible precatalyst for **1a**, showed dramatically lower activity (entry 4).^{25c} While the secondary amine [^RPNPFe] complexes are highly active catalysts with respect to most previously reported iron and cobalt catalysts, they pale in comparison to the tertiary amine [^RPN^{Me}PFe] systems. As noted above, **3a** delivers a remarkable 42,350 conversions to formate over 24 hours (entry 5). Much like the analogous secondary amine supported catalyst, the cyclohexyl phosphine substituted **3b** (entry 7) offers a small enhancement over the isopropyl phosphine counterpart. Use of the iron(II) dihydride carbonyl species **4a** in place of the borohydride precursor (entries 4 and 6) afforded very similar TONs and TOFs (TOF were measured after the first hour of reaction). This is consistent with a rapid conversion of **3a** to **4a** under catalytic conditions, with both species then proceeding via a common mechanism for CO₂ hydrogenation (*vide infra*).¹ Use of **5a** as a catalyst (entry 7) gave activity comparable to **3a** and **4a**, consistent with it being an intermediate in catalysis using **3a** or

4a. It is notable that for all the $[\text{RPN}^{\text{Me}}\text{PFe}]$ catalysts (entries 4-7) almost half the total conversion occurs during the first hour of the reaction. Again, no additional conversion was observed for experiments conducted for longer than 24 hours. This is indicative of highly active catalysts whose overall productivity declines significantly as the reaction proceeds.

Mechanistic Considerations of $(\text{RPNP})\text{Fe}(\text{H})\text{CO}/\text{Li}^+$ Catalyzed CO_2 Hydrogenation. We were interested in understanding the role of the LA in systems supported by both $\text{RPN}^{\text{H}}\text{P}$ and $\text{RPN}^{\text{Me}}\text{P}$ ligands and the increased activity of the tertiary amine supported species. The rate influencing role of the LA co-catalyst was first explored by studying the elementary reaction steps in isolation via NMR spectroscopy in systems with the bifunctional $\text{RPN}^{\text{H}}\text{P}$ ligand. On the basis of our related studies,¹⁸ a plausible pathway for CO_2 hydrogenation starting from **1** could proceed via 1) 1,2-addition of H_2 across the Fe-N bond, followed by 2) insertion of CO_2 into an Fe-H, and then 3) N-H deprotonation accompanied by formate extrusion to regenerate **1** (Scheme 1). Since the activities of **1a** and **1b** were comparable, $-\text{P}^i\text{Pr}_2$ substituted **1a** was selected for NMR experiments due to its simplified spectra.

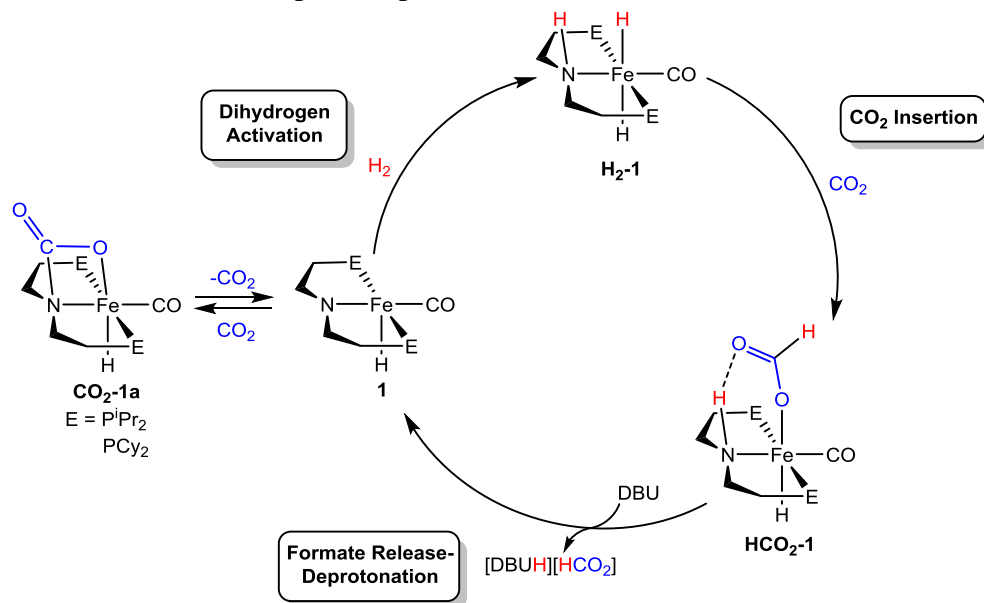

Scheme 1. Proposed mechanism for $(\text{RPNP})\text{Fe}(\text{H})\text{CO}/\text{Li}^+$ catalyzed CO_2 hydrogenation.

The H_2 activation reaction can be observed directly by addition of H_2 to **1a** in THF or

benzene solution, and results in near instantaneous bleaching of the dark red color and a corresponding appearance of NMR signals previously described for (ⁱPrPNP)Fe(H)₂CO (**H₂-1a**).¹⁸ Though **H₂-1a** was not isolable in the absence of an H₂ atmosphere, CO₂ insertion was immediately observed upon addition of 1 atm of CO₂ to an *in situ* generated solution of **H₂-1a** (Figure 3). Careful examination of the NMR spectra over the first 15 minutes following CO₂ addition revealed sufficient signals to account for the formation of two products. Two triplet Fe-H resonances were observed in the ¹H NMR spectrum, at -25.43 and -25.83 ppm and ³¹P NMR spectra exhibited peaks at 95.40 and 93.99 ppm. The more upfield resonance in each of these pairs was assigned to **HCO₂-1a**, which was previously prepared by addition of formic acid to **1a**.¹⁸ Over the course of 1 hour the resonances originating from the second product diminished with concomitant growth in the signals for **HCO₂-1a**. The reaction sequence was repeated using ¹³CO₂ in order to gain insight into the transient product which afforded two enhanced resonances in the ¹³C NMR spectrum at 165.37 and 174.81 ppm. ¹H-¹³C HSQC NMR spectra showed correlation between the resonance at 174.81 ppm and the formate C-H resonance of **HCO₂-1a** at 9.51 ppm in the ¹H-dimension; however, no one-bond correlations were observed for the signal at 165.37 ppm. This indicated that the transient species was not simply an isomer of **HCO₂-1a**. Instead complex **CO₂-1a** is the formal product of CO₂ addition across the Fe-N bond, and separate experiments show that this species may also be obtained as the sole product from the reaction of CO₂ to **1a**. Definitive characterization of **CO₂-1a** was established by single crystal X-ray diffraction as depicted in Figure S21. To the best of our knowledge, addition of CO₂ across an Fe-NR₂ bond has not previously been reported, but the transformation is closely related to the more commonly observed cycloaddition of CO₂ to transition metal imides and CO₂ insertion into transition metal amides.³¹ Though **CO₂-1a** has limited stability to vacuum, small quantities of

pure material were isolated by low temperature crystallization from pentane solution under N_2 . Notably, addition of 1 atm of H_2 to CO_2 -**1a** affords HCO_2 -**1a** cleanly over 6-8 hours at ambient temperature with no observable intermediates. If these results are extrapolated to the catalytic conditions, this suggests that formation CO_2 -**1a** is likely of minimal consequence to CO_2 hydrogenation, but may serve as a reversibly formed off-cycle catalytic intermediate.

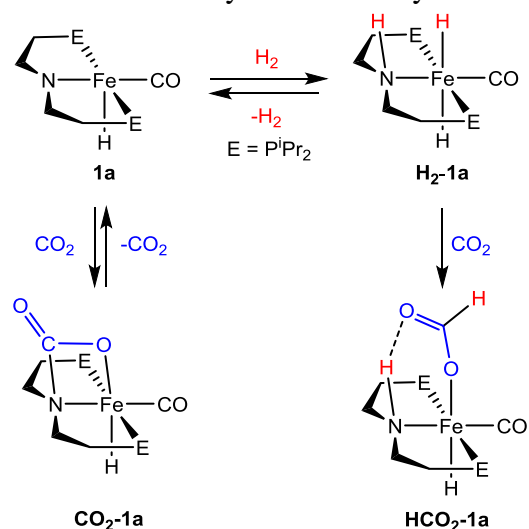


Figure 3. Reactions of **1a** with CO_2 and H_2 .

Overall, the rapidity of **H₂-1a** and **HCO₂-1a** formation (even under temperature and pressure conditions far more mild than the catalytic reaction) suggests that extrusion of formate and/or N-H deprotonation from **HCO₂-1a** are likely key to the rate of $(^RPNP)Fe(H)CO/Li^+$ catalyzed CO_2 hydrogenation. This was supported by *in situ* NMR spectroscopy of a catalytic reaction under modified conditions (1:3:40 ratio of **HCO₂-1a**: $LiBF_4$:DBU in THF under 2 atm of CO_2/H_2 at ambient temperature) which showed ^{31}P and 1H NMR resonances approximate to **HCO₂-1a** as the primary organometallic species. To better assign these resonances and gain further insight into roles of Fe, Li^+ and DBU in this portion of the reaction, a series of stoichiometric NMR scale reactions was performed (Figure S1). First, samples of **HCO₂-1a** were independently treated with 1 equiv. of DBU and $LiBF_4$ in $THF-d_8$. The sample treated with base showed no reaction, but the NMR spectra of the sample containing LA exhibited several changes

indicative of an interaction between **HCO₂-1a** and Li⁺. LiBF₄ addition resulted in a ~1.5 ppm upfield shift of the ³¹P NMR resonance and a corresponding downfield shift of ~0.2 ppm for the Fe-H peak in the ¹H NMR spectrum (Figures S1). A more dramatic upfield movement of the N-H resonance from 8.52 to 5.74 ppm was also observed. This change in chemical shift is consistent with a disruption of the hydrogen bonding interaction between the secondary amine and the bound formate, an interaction which has been predicted by computational analysis.¹⁸⁻¹⁹ While an exact structure for the Li-bound **HCO₂-1a** complex has not been established, ⁷Li NMR spectroscopy exhibited a resonance at -2.12 ppm which is consistent with a Li-O interaction.³² Subsequent addition of 1 equiv of DBU to the Li⁺/**HCO₂-1a** complex produced only a minimal change in the ³¹P NMR spectrum, and a very modest shift of the N-H proton resonance back downfield to 6.20 ppm. This indicates that DBU does not significantly alter the hydrogen bonding interaction. Notably, no conversion to **1a** and free formate was detected by NMR spectroscopy.

The stoichiometric experiments suggest a three component equilibrium exists between **HCO₂-1a**, Li⁺/**HCO₂-1a**, and DBU/Li⁺/**HCO₂-1a** complexes (Figure 4). The inability to observe separate NMR resonances for these species (even at -80 °C) suggests that equilibration is rapid. The relative upfield N-H ¹H NMR chemical shift also indicates a thermodynamic preference for the Li⁺/**HCO₂-1a** and DBU/Li⁺/**HCO₂-1a** complexes. However, it is important to consider that the conditions of these stoichiometric NMR experiments are far removed from the prevailing Li⁺ and DBU concentrations under catalytic conditions.

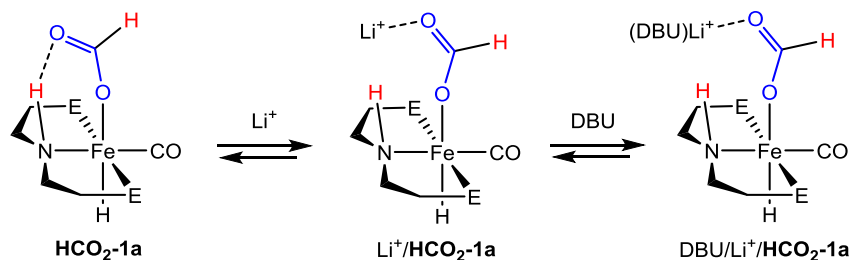


Figure 4. Reversible activation of **HCO₂-1a** by Li cation and DBU.

In order to better model the catalytic reaction a J. Young NMR tube was charged with DBU/LiBF₄/**HCO₂-1a** in a 40:3:1 ratio. Initial NMR spectra were nearly identical to those for the stoichiometric DBU/Li⁺/**HCO₂-1a** mixture (Figure S2). Addition of 1.5 atm each of H₂ and CO₂ produced a gradual downfield shift in the N-H resonance along with the growth of a new peak near 9.30 ppm assigned to the free formate product. After 2 hours the conversion was complete and the N-H resonance remained at ~7.80 ppm. This experiment is consistent with a reaction model where the initial resting state of the catalyst is dominated by the Li⁺ and DBU bound forms of **HCO₂-1a**, but as DBU is consumed and the product ammonium formate reduces the available Li⁺ concentration via equilibration between the salts, the resting state equilibrium shifts toward the pure **HCO₂-1a** complex.

Overall, the combination of data collected from the NMR experiments point toward the extrusion of formate from iron and/or the deprotonation of the N-H bond as the limiting steps of (^RPNP)Fe(H)CO/Li⁺ co-catalyzed CO₂ hydrogenation. The addition of LA appears to enhance catalysis primarily by assisting removal of the anionic formate and making the N-H fragment more available for DBU deprotonation through disruption of its hydrogen bond.


Mechanistic Considerations for [^RPN^{Me}PFe] catalysts. The mechanism of CO₂ hydrogenation for the [^RPN^{Me}PFe] catalysts was investigated through a series of NMR spectroscopy experiments. The similar catalytic performance of the iron borohydride and

dihydride catalysts, **3a** and **4a** (Table 4), as well as the synthesis of **4a** from **3a** in the presence of base, suggests that both catalysts function via the same mechanism. It is likely that **3a** simply serves as a precatalyst, which rapidly forms **4a** upon exposure to the high concentrations of DBU present at the initiation of the reaction. This hypothesis was supported by *in situ* monitoring using NMR spectroscopy of a catalytic reaction using **3a** or **4a** with 3 and 40 equiv. of LiBF₄ and DBU, respectively, under 1.5 atm each of H₂ and CO₂ (Figures S3-S6). In both cases, catalytically active (ⁱPrPN^{Me}P)Fe(H)CO(HCO₂) (**5a**) (see Table 4), was observed as the resting state during formate production, although some residual **3a** remained in the experiment using the iron borohydride catalyst.

The iron formate catalyst resting state for the [^RPN^{Me}PFe] systems parallels that observed for the secondary amine complexes, suggesting that formate extrusion still limits the rate of catalysis. In the case of **1a** and **1b**, our mechanistic experiments demonstrated that the Li⁺ co-catalyst assisted with this step, in part, by disrupting an intramolecular hydrogen bond between the formate and amide ligand. The role of Li⁺ was similarly probed for the [^RPN^{Me}PFe] system through stoichiometric NMR experiments. A sample of **5a** in THF-*d*₈ was first treated with 5 equiv of DBU under 1 atm H₂ and monitored for 16 hours at ambient temperature, resulting in no observable formation of free formate or the iron dihydride complex **4a**. However, addition of 3 equiv of LiBF₄ immediately afforded full conversion to **4a** and extrusion of a formate ion (Figure S12 & S13). This observation is consistent with LA assistance of formate release from the iron coordination sphere, likely via stabilization of the anionic formate by the Li⁺ center. Further evidence for this interaction was obtained by the addition of 3 equiv of LiBF₄ to a THF-*d*₈ solution of **5a**, which immediately shifted the Fe-H ¹H NMR resonances upfield by approximately 0.5 ppm and dramatically broadened both these signals and the peaks

corresponding to the formate C-H protons. A broadening and upfield shift of signals was also observed in the ^{31}P NMR spectrum, suggestive of a reversible coordination of Li^+ to **5a** (Figures S14 & S15).

The mechanistic information available suggests a pathway for $[\text{RPN}^{\text{Me}}\text{PFe}]$ catalyzed CO_2 hydrogenation which shares some common features with the secondary amine containing $[\text{RPNPFe}]$ catalyst (Scheme 2), including the insertion of CO_2 into an Fe-H bond followed by rate limiting formate extrusion. Yet the absence of a bifunctional amide moiety requires distinct mechanisms for the elementary reaction steps of H_2 activation and deprotonation by DBU. It is proposed that for the $[\text{RPN}^{\text{Me}}\text{PFe}]$ catalysts, Li^+ facilitates the displacement of formate by dihydrogen to generate a transient iron(II) dihydrogen cationic complex, which is then deprotonated by DBU to regenerate the iron(II) dihydride species. No spectroscopic evidence for the iron(II) dihydrogen cationic complex has been observed during catalysis, but several closely related iron complexes have been observed by others and implicated as intermediates in CO_2 hydrogenation.^{3d,13a,33} Given the prior precedent, a formate release/ H_2 deprotonation sequence was deemed more likely than an Fe-H deprotonation/ H_2 oxidative addition pathway, which would require the intermediacy of a zerovalent iron species.

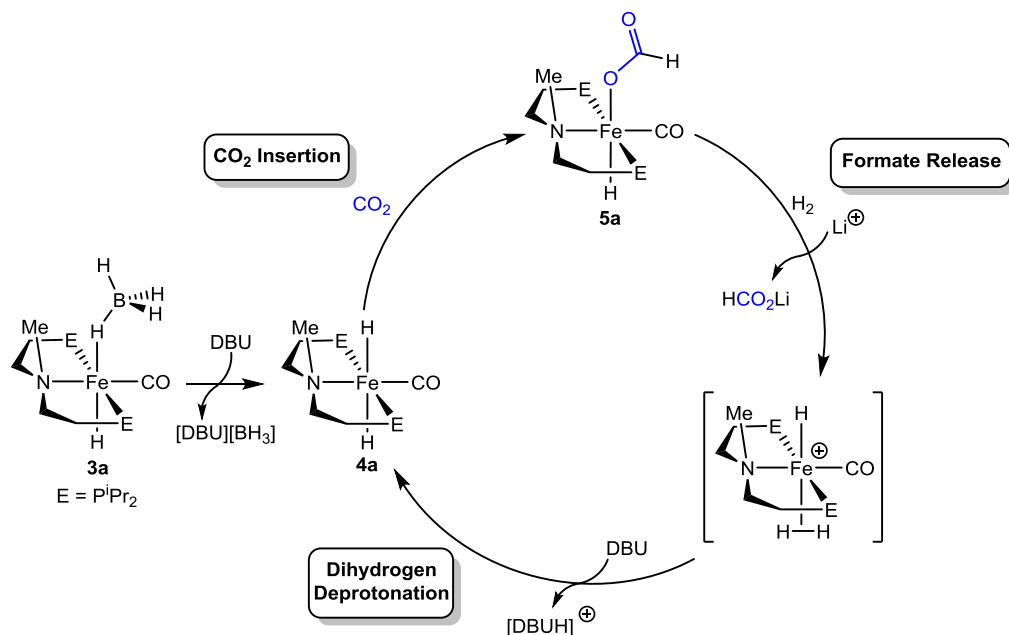

Scheme 2. Proposed pathway for catalytic CO₂ hydrogenation using (ⁱPrPN^{Me}P)Fe(H)CO(BH₄).

Conclusions

The catalytic activity of a family of PNP supported iron hydrides, containing either secondary or tertiary amines was investigated. In both cases dramatic improvements in TON and TOF were observed when LA co-catalysts were present. Our best system, involving the tertiary amine supported complex (ⁱPrPN^{Me}P)Fe(H)CO(BH₄), achieved approximately 60,000 turnovers, more than an order of magnitude greater than other iron catalysts and far superior to any earth abundant metal catalysts reported to date. In systems containing a secondary amine ligand, NMR spectroscopy identified the catalyst resting state as (^RPNP)Fe(H)CO(HCO₂) and suggested a key role for LA was disrupting a stabilizing hydrogen bond between N-H and Fe-O₂CH moieties in this species. Mechanistic consideration of the [^RPN^{Me}PFe] catalysts afforded a model whereby (^RPN^{Me}P)Fe(H)CO(BH₄) was activated by base to produce a (^RPN^{Me}P)Fe(H)₂CO species which rapidly inserts CO₂. The resulting formate complex, (ⁱPrPN^{Me}P)Fe(H)CO(HCO₂), was identified as the catalytic resting state. In this case, the primary role of LA was its assistance in a formate for dihydrogen substitution which yields a transient cationic iron(II) dihydrogen complex.

Subsequent deprotonation of the dihydrogen fragment by DBU regenerates $(^R\text{PN}^{\text{Me}}\text{P})\text{Fe}(\text{H})_2\text{CO}$. This pathway for CO_2 hydrogenation resulted in remarkable activity, providing approximate TOFs of $20,000 \text{ h}^{-1}$. Given that most precious and earth abundant metal catalysts are postulated to operate via similar mechanisms for CO_2 hydrogenation, it is possible that the use of LA co-catalysts could dramatically enhance performance across of a range of other CO_2 reduction systems. Such improvements in CO_2 hydrogenation at iron may enable these or related catalyst systems to produce even higher value products, such as methanol, under optimized conditions. Targeting these CO_2 functionalization products, as well as further elucidating the structure-reactivity relationships in the $[\text{RPN}^{\text{Me}}\text{PFe}]$ system are the foci of on-going efforts in our laboratories.

Acknowledgements. This material is based upon work supported by the National Science Foundation through the Centre for the Capture and Conversion of CO_2 (C^4) (CHE-1240020). N.H. and W.H.B are fellows of the Alfred P. Sloan Foundation.

Supporting Information Available. Experimental details and characterizing data, X-ray CIFs, and selected NMR spectra. These data are available free of charge via the Internet.

References

- (a) Dincer, I. *Energ. Policy* **1999**, *27*, 845; (b) Lewis, N. S.; Nocera, D. G. *Proc. Natl. Acad. Sci. U.S.A.* **2006**, *103*, 15729; (c) Dimitratos, N.; Lopez-Sanchez, J.; Hutchings, G. *Top. Catal.* **2009**, *52*, 258.
- (a) *Feedstocks for the Future*; Bozell, J.; Patel, M. K. Eds.; ACS Symposium Series 921; American Chemical Society; Washington, DC, 2006; (b) *Renewable Raw Materials: New Feedstocks for the Chemical Industry*; Ulber, R. Sell, D.; Hirth, T. Eds; Wiley-VCH: Weinheim, 2011; (c) *Carbon Dioxide as Chemical Feedstock*. Aresta, M. Ed. Wiley-VCH: Weinheim, 2011; (d) Bhanage, B. M.; Arai, M. Eds *Transformation and Utilization of Carbon Dioxide*, Springer: 2014.
- (a) Jessop, P. G.; Ikariya, T.; Noyori, R. *Chem. Rev.* **1995**, *95*, 259; (b) Jessop, P. G.; Joo, F.; Tai, C.-C. *Coord. Chem. Rev.* **2004**, *248*, 2425; (c) Federsel, C.; Jackstell, R.; Beller, M. *Angew. Chem. Int. Ed.* **2010**, *49*, 6254; (d) Ziebart, C.; Beller, M. In *Transformation and Utilization of Carbon Dioxide.*; Bhanage, B. M., Arai, M., Eds.; Springer: Berlin, 2014; (e) Kang, P.; Chen, Z.; Brookhart, M.; Meyer, T. J. *Top. Catal.* **2015**, *58*, 30; (f) Knopf, I.; Cummins, C. C. *Organometallics* **2015**, *34*, 1601.
- (a) Enthaler, S.; von Langermann, J.; Schmidt, T. *Energy Environ. Sci.* **2010**, *3*, 1207; (b) Grasemann, M.; Laurency, G. *Energy Environ. Sci.* **2012**, *5*, 8171.
- Yasaka, Y.; Wakai, C.; Matubayasi, N.; Nakahara, M. *J. Phys. Chem. A* **2010**, *114*, 3510.
- An alternative strategy to drive the reaction, which is both more costly and conceptually different, is to use a sacrificial silane or borane. Hydrolysis of a siloxy or boroxo species subsequently generates formic acid. For examples using first row transition metals see: (a) Shintani, R.; Nozaki, K. *Organometallics* **2013**, *32*, 2459; (b) Motokura, K.; Kashiwame, D.; Miyaji, A.; Baba, T. *Org. Lett.* **2012**, *14*, 2642.
- (a) Laurency, G.; Joó, F.; Nadasdi, L. *Inorg. Chem.* **2000**, *39*, 5083; (b) Elek, J.; Nadasdi, L.; Papp, G.; Laurency, G.; Joó, F. *Appl. Catal. A* **2003**, *255*, 59; (c) Federsel, C.; Jackstell, R.; Boddien, A.; Laurency, G.; Beller, M. *ChemSusChem* **2010**, *3*, 1048; (d) Boddien, A.; Gärtner, F.; Federsel, C.; Sponholz, P.; Mellmann, D.; Jackstell, R.; Junge, H.; Beller, M. *Angew. Chem. Int. Ed.* **2011**, *50*, 6411; (e) Drake, J. L.; Manna, C. M.; Byers, J. A. *Organometallics* **2013**, *32*, 6891; (f) Huff, C. A.; Sanford, M. S. *ACS Catal.* **2013**, *3*, 2412; (g) Moret, S.; Dyson, P. J.; Laurency, G. *Nat. Commun.* **2014**, *5*; (h) Filonenko, G. A.; van Putten, R.; Schulpen, E. N.; Hensen, E. J. M.; Pidko, E. A. *ChemCatChem* **2014**, *6*, 1526.
- (a) Gassner, F.; Leitner, W. *J. Chem. Soc., Chem. Commun.* **1993**, 1465; (b) Leitner, W.; Dinjus, E.; Gassner, F. In *Aqueous-Phase Organometallic Catalysis, Concepts and Applications*; Cornils, B., Herrmann, W. A., Eds.; Wiley-VCH: Weinheim, **1998**; p 486.
- (a) Joo, F.; Joo, F.; Nadasdi, L.; Elek, J.; Laurency, G.; Nadasdi, L. *Chem. Commun.* **1999**, 971; (b) Himeda, Y.; Onozawa-Komatsuzaki, N.; Sugihara, H.; Arakawa, H.; Kasuga, K. *Organometallics* **2004**, *23*, 1480; (c) Schmeier, T. J.; Dobereiner, G. E.; Crabtree, R. H.; Hazari, N. *J. Am. Chem. Soc.* **2011**, *133*, 9274; (d) Azua, A.; Sanz, S.; Peris, E. *Chem. Eur. J.* **2011**, *17*, 3963; (e) Fernández-Alvarez, F. J.; Iglesias, M.; Oro, L. A.; Polo, V. *ChemCatChem* **2013**, *5*, 3481; (f) Hull, J. F.; Himeda, Y.; Wang, W.-H.; Hashiguchi, B.; Periana, R.; Szalda, D. J.; Muckerman, J. T.; Fujita, E. *Nat. Chem.* **2012**, *4*, 383; (g) Maenaka, Y.; Suenobu, T.; Fukuzumi, S. *Energy Environ. Sci.* **2012**, *5*, 7360.
- (a) Tanaka, R.; Yamashita, M.; Nozaki, K. *J. Am. Chem. Soc.* **2009**, *131*, 14168; (b) Tanaka, R.; Yamashita, M.; Chung, L. W.; Morokuma, K.; Nozaki, K. *Organometallics* **2011**, *30*, 6742.
- Inoue, Y.; Izumida, H.; Sasaki, Y.; Hashimoto, H. *Chem. Lett.* **1976**, 863.
- Hansen J. B. *Handbook of Heterogeneous Catalysis*, Vol. 4; Ertl G., Knötzing H., Weitkamp, J., Eds.; VCH: 1997.
- (a) Fong, H.; Peters, J. C. *Inorg. Chem.* **2015**, In Press; (b) Rivada-Wheelaghan, O.; Dauth, A.; Leitus, G.; Diskin-Posner, Y.; Milstein, D. *Inorg. Chem.* **2015**, In Press.
- Badie, Y. M.; Wang, W.-H.; Hull, J. F.; Szalda, D. J.; Muckerman, J. T.; Himeda, Y.; Fujita, E. *Inorg. Chem.* **2013**, *52*, 12576.
- (a) Jeletic, M. S.; Mock, M. T.; Appel, A. M.; Linehan, J. C. *J. Am. Chem. Soc.* **2013**, *135*, 11533; (b) Jeletic, M. S.; Helm, M. L.; Hulley, E. B.; Mock, M. T.; Appel, A. M.; Linehan, J. C. *ACS Catal.* **2014**, *4*, 3755.
- (a) Federsel, C.; Boddien, A.; Jackstell, R.; Jennerjahn, R.; Dyson, P. J.; Scopelliti, R.; Laurency, G.; Beller, M. *Angew. Chem. Int. Ed.* **2010**, *49*, 9777; (b) Ziebart, C.; Federsel, C.; Anbarasan, P.; Jackstell, R.; Baumann, W.; Spannenberg, A.; Beller, M. *J. Am. Chem. Soc.* **2012**, *134*, 20701; (c) Federsel, C.; Ziebart, C.; Jackstell, R.; Baumann, W.; Beller, M. *Chem. Eur. J.* **2012**, *18*, 72.
- Langer, R.; Diskin-Posner, Y.; Leitus, G.; Shimon, L. J. W.; Ben-David, Y.; Milstein, D. *Angew. Chem. Int. Ed.* **2011**, *50*, 9948.
- Bielinski, E. A.; Lagaditis, P. O.; Zhang, Y.; Mercado, B. Q.; Würtele, C.; Bernskoetter, W. H.; Hazari, N.; Schneider, S. *J. Am. Chem. Soc.* **2014**, *136*, 10234.

19. Bielinski, E. A.; Förster, M.; Zhang, Y.; Bernskoetter, W. H.; Hazari, N.; Holthausen, M. C. *ACS Catal.* **2015**, *5*, 2404.
20. To the best of our knowledge the use of Lewis acids to improve CO₂ hydrogenation to formate is conceptually novel. Previously Leitner and coworkers have used Brønsted acids to improve TONs in the hydrogenation of CO₂ to methanol. See: Wesselbaum, S.; von Stein, T.; Klankermayer, J.; Leitner, W. *Angew. Chem. Int. Ed.* **2012**, *51*, 7499.
21. (a) Fan, L.; Foxman, B. M.; Ozerov, O. V. *Organometallics* **2004**, *23*, 326; (b) Grützmacher, H. *Angew. Chem. Int. Ed.* **2008**, *47*, 1814; (c) Hetterscheid, D. G. H.; van der Vlugt, J. I.; de Bruin, B.; Reek, J. N. H. *Angew. Chem. Int. Ed.* **2009**, *48*, 8178; (d) Scheuermann, M. L.; Fekl, U.; Kaminsky, W.; Goldberg, K. I. *Organometallics* **2010**, *29*, 4749; (e) Gunanathan, C.; Milstein, D. *Acc. Chem. Res.* **2011**, *44*, 588; (f) Schneider, S.; Meiners, J.; Askevold, B. *Eur. J. Inorg. Chem.* **2012**, *2012*, 412.
22. Chakraborty, S.; Brennessel, W. W.; Jones, W. D. *J. Am. Chem. Soc.* **2014**, *136*, 8564.
23. (a) Bornschein, C.; Werkmeister, S.; Wendt, B.; Jiao, H.; Alberico, E.; Baumann, W.; Junge, H.; Junge, K.; Beller, M. *Nat. Commun.* **2014**, *5*, 4111; (b) Werkmeister, S.; Junge, K.; Wendt, B.; Alberico, E.; Jiao, H.; Baumann, W.; Junge, H.; Gallou, F.; Beller, M. *Angew. Chem. Int. Ed.* **2014**, *53*, 8722.
24. Addison, A. W.; Rao, T. N.; Reedijk, J.; van Rijn, J.; Verschoor, G. C. *J. Chem. Soc., Dalton Trans.* **1984**, 1349.
25. (a) Marks, T. J.; Kolb, J. R. *Chem. Rev.* **1977**, *77*, 263; (b) Langer, R.; Iron, M. A.; Konstantinovski, L.; Diskin-Posner, Y.; Leitner, G.; Ben-David, Y.; Milstein, D. *Chem. Eur. J.* **2012**, *18*, 7196; (c) Koehne, I.; Schmeier, T. J.; Bielinski, E. A.; Pan, C. J.; Lagaditis, P. O.; Bernskoetter, W. H.; Takase, M. K.; Würtele, C.; Hazari, N.; Schneider, S. *Inorg. Chem.* **2014**, *53*, 2133.
26. Similar spectra have been observed for the cyclohexyl congener, **3b**, but no attempt has been made to isolate (^{Cy}PN^{Me}P)Fe(H)₂CO.
27. The metrical parameters of each polymorph of **4a** are quite similar. The cifs for both polymorphs are provided in the Supporting Information.
28. No exchange correlations between isomers of **5a** were observed under these conditions.
29. (a) Munshi, P.; Main, A. D.; Linehan, J. C.; Tai, C.-C.; Jessop, P. G. *J. Am. Chem. Soc.* **2002**, *124*, 7963; (b) Getty, A. D.; Tai, C.-C.; Linehan, J. C.; Jessop, P. G.; Olmstead, M. M.; Rheingold, A. L. *Organometallics* **2009**, *28*, 5466.
30. In the absence of iron catalyst, only 0.1% conversion to formate was observed under these conditions.
31. Chakraborty, S.; Blacque, O.; Berke, H. *Dalton Trans.* **2015**, *44*, 6560.
32. (a) Reich, H. J.; Borst, J. P.; Dykstra, R. R.; Green, P. D. *J. Am. Chem. Soc.* **1993**, *115*, 8728; (b) Masiker, M. C.; Mayne, C. L.; Boone, B. J.; Orendt, A. M.; Eyring, E. M. *Magn. Reson. Chem.* **2010**, *48*, 94.
33. (a) Gilbertson, J. D.; Szymczak, N. K.; Tyler, D. R. *Inorg. Chem.* **2004**, *43*, 3341; (b) Gilbertson, J. D.; Szymczak, N. K.; Crossland, J. L.; Miller, W. K.; Lyon, D. K.; Foxman, B. M.; Davis, J.; Tyler, D. R. *Inorg. Chem.* **2007**, *46*, 1205; (c) Lee, Y.; Kinney, R. A.; Hoffman, B. M.; Peters, J. C. *J. Am. Chem. Soc.* **2011**, *133*, 16366.