

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Thermodynamic Synthesis of Solution Processable Ladder Polymers

Jongbok Lee,¹ Bharath Bangalore Rajeeva,² Tianyu Yuan,^{1,3} Zi-Hao Guo,¹ Yen-Hao Lin,¹

Mohammed Al-Hashimi,⁴ Yuebing Zheng,² and Lei Fang^{*1,3}

¹Department of Chemistry, Texas A&M University, 3255 TAMU, College Station, TX 77843, USA


²Department of Mechanical Engineering, Materials Science and Engineering Program, and Texas Materials Institute, The University of Texas at Austin, Austin, Texas 78712, USA

³Materials Science & Engineering Department, Texas A&M University, 3255 TAMU, College Station, TX 77843, USA

⁴Department of Chemistry, Texas A&M University at Qatar, P.O. Box 23874, Doha, Qatar

Email: fang@chem.tamu.edu

ABSTRACT: The synthesis of a carbazole-derived, well-defined ladder polymer was achieved under thermodynamic control by employing reversible ring-closing olefin metathesis. This unique approach featured mild conditions and excellent efficiency, affording the ladder polymer backbone with minimum level of unreacted defects. Rigorous NMR analysis on a ¹³C isotope-enriched product revealed that the main-chain contained less than 1% of unreacted precursory vinyl groups. The rigid conformation of the ladder-type backbone was confirmed by photophysical analysis, while the extended rod-like structure was visualized under scanning tunneling microscope. Excellent solubility of this polymer in common organic solvents allowed for feasible processing of thin films using solution-casting techniques. Atomic force microscopy and grazing incident X-ray scattering revealed a uniform and amorphous morphology of these films, in sharp contrast to the polycrystalline thin films of its small molecular counterpart.

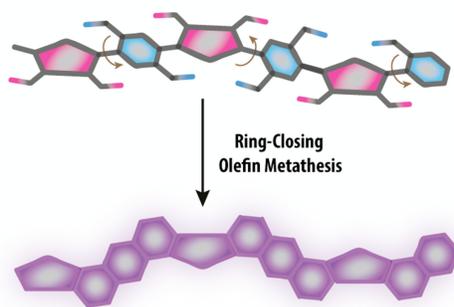

INTRODUCTION

Fully conjugated ladder polymers with coplanar, sp^2 atom-rich backbones represent a captivating class of macromolecules, on account of their well-defined rigid structures, intriguing syntheses, and promising potential in materials applications.¹⁻⁵ By definition,⁶ ladder polymers have a distinctive architecture, whereby the chain consists of an uninterrupted sequence of rings, fused together in a way that adjacent rings share two or more atoms in common, resulting in a constrained chain conformation.⁷⁻⁹ Possessing a backbone of fused aromatic rings, a fully conjugated ladder polymer is intrinsically free of possible torsional disorders that are resulted from σ -bond rotations in between the monomeric units. Without the interruption from these conformational disorders, as a result, its coherent π -conjugation length of a coplanar ladder backbone is much more extended.¹⁰ Such a well-defined conformation would afford a faster intra-chain charge/phonon transport,^{11, 12} and a longer exciton diffusion length compared to conjugated polymers with free rotating torsional motions.¹³ This argument is further corroborated by the unparalleled electronic and thermal conductivity of graphene nanoribbons,^{14, 15} which can be viewed as insoluble ladder polymers composed of only sp^2 carbon atoms. Combining the advantages of conventional polymeric materials such as solution processability and structural versatility, ladder polymers emerge as promising candidates for the next-generation synthetic organic materials with breakthrough performances.

The synthesis of a well-defined ladder polymer, however, is a challenging task because of (i) the potential structural defects originated from moderately efficient ring-closing reactions, and (ii) the often poor solubility of structurally rigid intermediates or products. In an effort to overcome these obstacles, a highly efficient synthetic method and a rationally designed structural characteristic that enables solubility need to be achieved and integrated simultaneously. On one

hand, kinetically controlled annulation reactions such as Scholl oxidation and electrophilic cyclization have been widely used¹⁶⁻²⁴ in the preparation of conjugated ladder polymers from pre-organized polymer precursors, affording a number of materials with fascinating optical and electronic properties. On the other hand, thermodynamically controlled annulation reactions, in principle, can offer unique advantages in the synthesis of well-defined ladder polymers: It enables the opportunities of “error-checking” and “proof-reading”²⁵ while pushing the reversible equilibrium to the most stable position. As a result, during the post-polymerization ring-closing step, one could prevent the potential formation of unreacted defects and inter-chain cross-linking, which could be detrimental to the desired materials properties. Despite the early examples and a few subsequent advances involving imine condensation,^{18, 26, 27} this promising strategy has not been extensively explored up to date. Herein, we report the synthesis of a fully conjugated ladder polymer with an extremely low level of unreacted defects, by taking advantage of thermodynamically controlled ring-closing olefin metathesis (RCM) reaction. The carefully

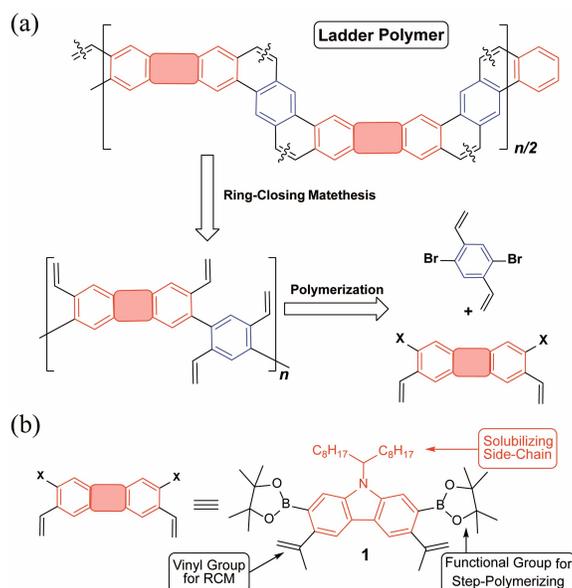



Figure 1. (a) A general retrosynthetic analysis for the designed ladder polymer; (b) Structural formula of the carbazole-derived monomer **1**.

designed structure rendered good solubility of the ladder polymer in common organic solvents, which allowed for excellent solution processability, and extensive solution- and solid-state characterization.

RESULTS AND DISCUSSION

We envisioned that RCM reaction held²⁸⁻³³ the promise for the synthesis of conjugated ladder polymers, because (i) it can produce C=C double bond by releasing about 28 kcal/mol of enthalpy in forming a stable aromatic benzene ring,^{31,33} and (ii) its mild condition enables a wide substrate scope and excellent functional group tolerance.³⁴ Given a properly designed precursor, RCM reaction should lead to an uncross-linked, stable, and conjugated ladder polymer with minimum unreacted defects.

Guided by these principles, a synthetic route (Figure 1a) was designed and executed. This synthesis involved two essential steps: First, step-growth polymerization of two divinyl-functionalized monomers affords a conjugated polymer with pre-organized pendant vinyl groups. In the second step, RCM reaction forms the bridging aromatic rings and hence leads to a coplanar ladder polymer. Carbazole unit was employed as the primary building block in this design (Figure 1b), motivated by the following facts: Firstly, it is inexpensive and feasible to prepare functionalized carbazole derivatives with excellent regioselectivity.^{35,36} For example, in the designed carbazole precursor **1**, two boronic ester functions were installed on the 2,7-positions for the step-growth polymerization step while the 3,6-positions were functionalized with vinyl groups for RCM annulation. Secondly, the presence of an easy-to-alkylate nitrogen position on carbazole unit allows for the installation of an α -branched alkyl group (1-octylnonyl in this case) to enhance the solubility of the rigid ladder polymer product. Such a side-chain would extend in a perpendicular direction with respect to the π -system, so that solubility could be

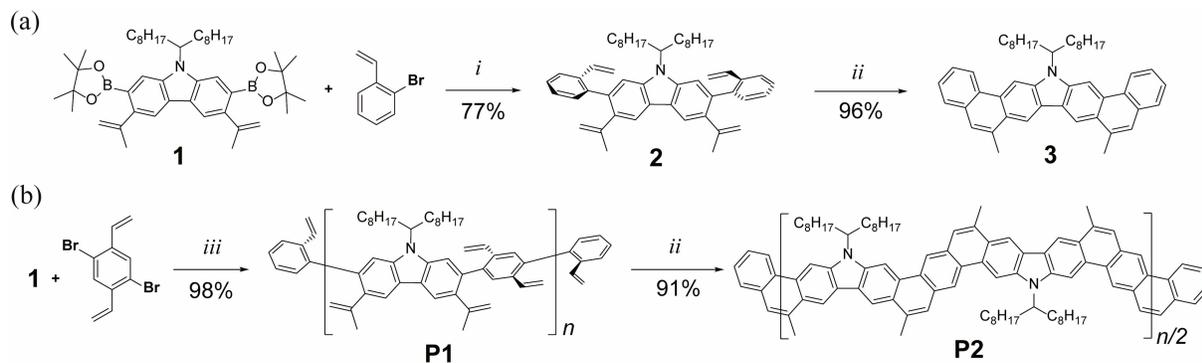

Scheme 1. (a) Synthesis of small molecular model compound **3**; (b) synthesis of ladder polymer **P2**. Reaction conditions: *i*) Pd(PPh₃)₄, K₂CO₃, aliquat 336, BHT, PhMe, H₂O, 100 °C, 24 h. *ii*) Grubbs' 2nd generation catalyst, PhMe, reflux, 6 h. *iii*) Pd(PPh₃)₄, K₂CO₃, aliquat 336, BHT, PhMe, H₂O, 100 °C, 24 h; then 2-bromostyrene and 2-vinylphenylboronic acid.

drastically enhanced by breaking the potentially too strong intermolecular π - π stacking interactions.^{37, 38} Finally, carbazole-containing organic materials have demonstrated high performance in applications associated with photovoltaics^{39, 40} and light emitting diodes.^{41, 42} Thus, successful synthesis of ladder polymers derived from carbazole can be readily translated into applications in these fields.

Precursor **1** was synthesized from 2,7-dibromocarbazole in 60% overall yields on a ~ 3 grams scale (see ESI). Before exploring the synthesis of the target polymer, a small molecular model compound **3** was synthesized to validate the strategy and to assist future characterization (Scheme 1a). 2-Bromostyrene and compound **1** were cross-coupled by Suzuki reaction to give a tetra-vinyl derivative **2**. Butylated hydroxytoluene (BHT) was used in this reaction as a radical scavenger to inhibit free-radical polymerization of the styrene derivatives. During the subsequent RCM step, it was critical to achieve quantitative conversion of the vinyl groups. This was particularly important for the later-on synthesis of polymer **P2** (Scheme 1b). A subset of

conditions for the RCM reaction was tested on **2** (Table S1, ESI). In the most efficient method identified, the catalyst was added with a syringe pump over 4 hr at reflux temperature to give product **3** in 96% isolated yield. According to liquid chromatogram (see ESI), the conversion of the RCM reaction was close to quantitative. In this transformation, reversible nature of RCM prevented undesired side reactions such as intermolecular cross olefin metathesis of vinyl groups, and afforded the thermodynamically most stable product in a nearly quantitative conversion. The structure of **3** was characterized unambiguously by ^1H - ^1H NOESY NMR spectroscopy (Figure S6, ESI) and single crystal X-ray diffraction (Figure 2a). The crystal structure clearly demonstrated that the annulated aromatic rings extended in a coplanar geometry. The 1-octylonyl side-chain was perpendicular to the π -backbone in the solid state. As a result, the potential strong intermolecular π - π stacking interactions were suppressed, leading to its good solubility in common organic solvents, such as chloroform, tetrahydrofuran, and toluene. In the ^1H NMR spectra of **2** and **3** (Figure 3a), as expected, the vinyl peaks at 5.0 - 7.0 ppm in **2** disappeared in **3** after the RCM reaction, while other peaks shifted downfield. Moreover, after RCM, IR spectrum of **3** revealed the disappearance of the alkenyl C-H and C=C stretching peaks originally present in the spectrum of **2** (Figure S4, ESI).

The comparison of optical properties between **2** and **3** clearly illustrated (Figure 2b) the impact of aromatic ring-closure on the electronic structures. UV-vis absorption spectrum of the annulated compound **3** was red-shifted compared to that of **2** because of the more extended conjugation and a covalently enforced coplanar π -electron system. Moreover, both the absorption and emission spectra of **3** showed distinctive vibrational progressions that were indicative of a rigid conjugated system with insignificant conformational fluctuation.⁴³ Interestingly, the absorption spectrum of **3** showed a weak, symmetrically forbidden HOMO-LUMO transition

similar to that of C_{60} .⁴⁴ Time-dependant density functional theory (TDDFT) [B3LYP/6-

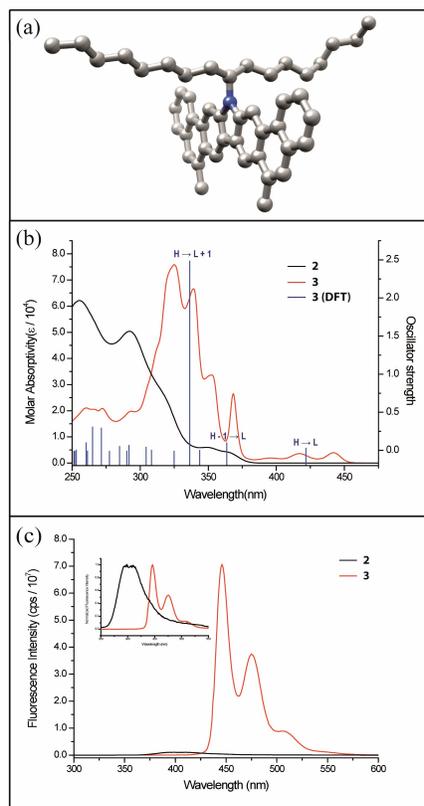


Figure 2. (a) Solid-state structure of compound **3** obtained from single-crystal X-ray diffraction; (b) UV-vis absorption spectra of compound **2** (black) and **3** (red) in $CHCl_3$, with the TDDFT calculated electronic transitions of **3** shown as blue bar; (c) Fluorescent emission spectra of **2** (black) and **3** (red) with absolute intensity scale. Inset is the same spectra with normalized intensity.

311G(d,p)] was performed to obtain the calculated electronic transitions of **3**, which were in excellent agreement with the experimental data (Figure 2b). Furthermore, the fluorescent emission spectrum of **3** (Figure 2c) was also red-shifted and enhanced in terms of intensity relative to that of **2**. This phenomenon corroborated again the extended π -conjugation of **3**. Overall, the successful synthesis and unambiguous characterization of the small molecular model

compound provided a firm basis for the preparation and investigation of ladder polymer **P2** using a similar strategy.

The synthetic route to the target ladder-type polymer **P2** is outlined in Scheme 1b. The step-growth Suzuki polymerization between **1** and 1,4-dibromo-2,5-divinylbenzene afforded a conjugated polymer with pendant vinyl groups, which was then end-capped by subsequent addition of 2-bromostyrene and 2-vinylphenylboronic acid to give **P1**. The end-capping groups not only quenched the active bromide and boronic ester functions, but also provided complementary vinyl groups for the polymer chain ends to undergo RCM reaction in the next step. BHT was again added as a radical scavenger in this step to prevent vinyl cross-linking between the polymer chains. The reaction was carried out on a 1 g scale to afford **P1** in 98% yield. The crude polymer was collected by precipitation from methanol, followed by washing with acetone. Further purification was accomplished using preparative size exclusion chromatography (SEC) with CHCl_3 as the eluent to remove the low molecular weight oligomers, affording a narrowly distributed batch of **P1** in 75% isolated yield. SEC analysis of the purified **P1** revealed a molecular weight ($M_n = 20 \text{ kg/mol}$, $\text{PDI} = 1.88$) that was comparable to that of polymers used as high performance organic solar cell donor materials⁴⁵⁻⁴⁹ (Figure S2, ESI).

In the subsequent RCM step, the optimized condition screened from the synthesis of **3** was employed to convert **P1** into the ladder-type product **P2** in 91% yield. The resulting product **P2** was purified by precipitation and Soxhlet extraction. The molecular weight of **P2** ($M_n = 15 \text{ kg/mol}$, $\text{PDI} = 2.00$) was slightly smaller than its precursor **P1** because the higher molecular weight fraction was partially removed during these purification steps due to its lower solubility at high concentration (Figure S3, ESI). Despite the lower solubility of **P2** compared to **P1**, it was still feasible to prepare a solution of purified **P2** in CHCl_3 at a concentration of 5 mg/ml. This

good solubility allowed for extensive NMR investigation, SEC analysis, and solution processing into thin films.

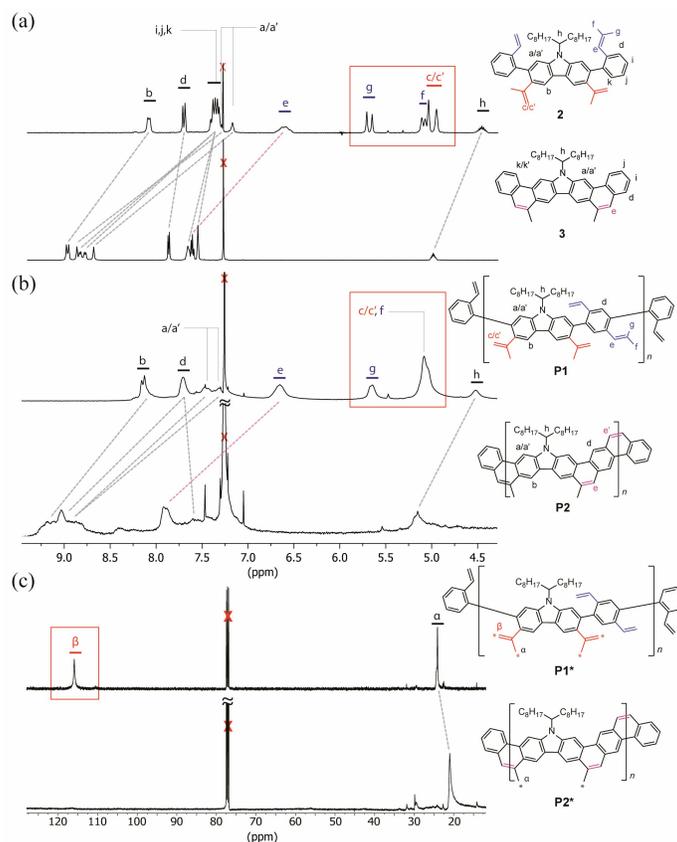


Figure 3. (a) Partial ^1H NMR spectra of **2** and **3**. Dotted lines represent the change of chemical shift of each resonance peak after RCM reaction. Proton resonance peaks for *c*, *c'*, *f* and *g* in the box all disappeared after converting **2** into **3**; (b) Partial ^1H NMR spectra of **P1** and **P2** showing the similar change of chemical shift. Proton resonance peaks for the terminal vinyl groups *c*, *c'*, *f*, and *g* in the box all disappeared after the RCM reaction; (c) ^{13}C NMR spectra of **P1*** (S/N = 94 after 413 scans) and **P2*** (S/N = 367 after 17816 scans). The carbons labeled with “*” are 99% ^{13}C isotope enriched. ^{13}C resonance peaks for the terminal vinyl carbon β in the box disappeared after the RCM reaction.

The comparison of ^1H NMR spectra of **P1** and **P2** resembled that of model compounds **2** and **3**: The resonance peaks associated with the terminal protons on the vinyl groups disappeared after RCM (Figure 3b). In addition, IR spectra of **P2** also showed the disappearance of the alkenyl C–H and C=C stretching after RCM, similar to that of **3** (Figure S5, ESI). Despite these promising results, however, the possibility of unreacted vinyl groups in **P2** could not be ruled out by these characterization methods. ^1H NMR resonance signals were too broad to be useful for a rigorous quantification of defects, especially if the amount of unreacted vinyl groups was less than 5%. Such a structural defect, however, could be critical to the electronic, optical, and mechanical properties of conjugated ladder polymers.⁵⁰⁻⁵² In this context, ^{13}C isotope labeling method⁵³ was employed to track the terminal vinyl carbons using much sharper ^{13}C NMR resonance peaks. Therefore, a much sensitive analysis of the unreacted defects of **P2** could be performed. The same synthetic procedures afforded ^{13}C labeled **P1***, in which a methyl carbon α and the terminal alkenyl carbon β are 99% ^{13}C isotope enriched (Figure 3c). ^{13}C NMR spectrum of **P1*** showed the two expected intense sharp peaks for these ^{13}C isotope enriched carbons at 116.0 ppm and 24.1 ppm with good signal/noise ratio (S/N = 94 after 413 scans). **P1*** was then subjected to the optimized RCM condition to afford **P2***. The resonance signal associated with the terminal vinyl carbon at 116.0 ppm disappeared completely while the peak at 21.0 ppm retained an excellent signal/noise ratio (S/N = 367 after 17816 scans). This result corroborated that the unreacted vinyl defect in **P2*** was less than 1%. Considering that the degree of polymerization of **P2** and **P2*** was around 23 ~ 27, the average possible defect site in a single polymer chain was in fact much less than one. Based on these numbers, we can conclude that most of the polymer chains should be free of defect but their might still be a small fraction of the polymer chains possessing one or more unreacted defects.

UV-vis absorption and fluorescent emission spectra of **P1** and **P2** were recorded in CHCl_3 solution (Figure 4a,b). Similar to that of **3**, both absorption and emission spectra of **P2** were red-shifted compared to that of **P1**, as a result of the much more delocalized and larger conjugated π -system. In addition, HOMO-LUMO transition of **P2** was weak and optically forbidden, similar to that of **3**. Meanwhile, the almost zero wavelength difference (Figure S30, ESI) between HOMO-LUMO transition of absorption and LUMO-HOMO transition of emission and distinctive vibrational progression were in accordance with the highly rigid nature of **P2** backbone, which prevented any significant conformational change between the excited and the ground states.⁴³ Unlike the unstructured and low emission of **P1** (quantum yield < 1%), the emission spectrum of **P2** was composed of well-structured vibrational progressions with much higher quantum yield (15%). Furthermore, it was observed that solid-state UV-vis absorption of **P1** was red-shifted compared to that in the solution phase. Such a red-shift can be attributed to solid-state packing-induced coplanarization of **P1** backbone, similar to that of the well studied regioregular poly(3-alkylthiophene).^{54, 55} In contrast, the solution-phase and solid-state absorption spectra of **P2** were almost identical because **P2** in solution was already coplanar and rigid, hence solid-state packing could not change the spectra by alternating its conformation (Figure 4c,d). These photophysical observations suggested that ladder polymer **P2** possessed a highly rigid backbone and well-extended π -conjugation.

It is expected that sp^2 atom rich, aromatic ladder-type polymers have a backbone that is stable at high temperatures, resembling fused ring carbon materials like carbon nanotubes and graphene nanoribbons.^{56, 57} Thermogravimetric analysis (TGA, Figure S32, S33, ESI) of **P1** showed a clear weight loss in the range of 380 ~ 480 °C, corresponding to the thermal cleavage of the sp^3 1-octylnonyl side-chains. Upon further increasing the temperature the non-ladder type

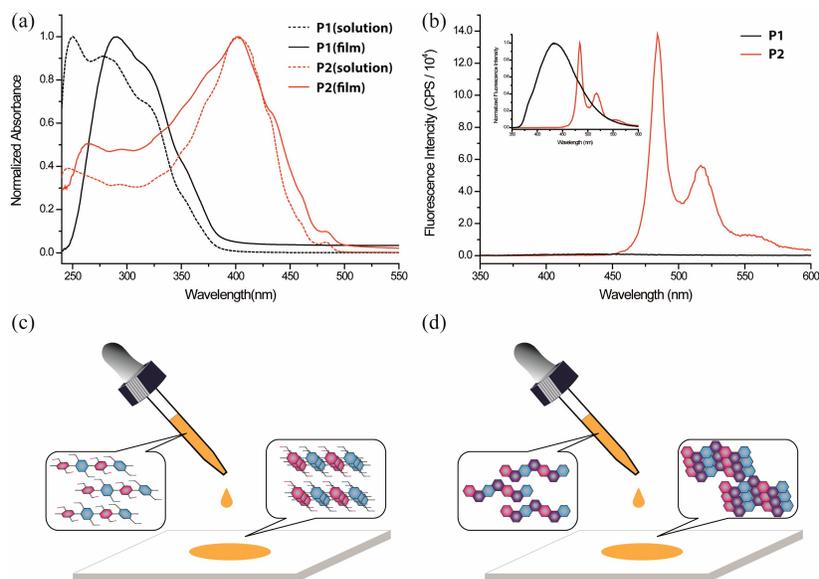


Figure 4. (a) UV-vis absorption spectra of **P1** (black) and **P2** (red) in CHCl_3 and as thin films; (b) Fluorescence emission spectra of **P1** (black) and **P2** (red) in CHCl_3 with absolute intensity scale. Inset is the same spectra with normalized intensity. Graphical illustration of the conformational change of (c) **P1** and (d) **P2** between in solution and in the solid state.

backbone of **P1** saw a continuous weight lost, affording only a 34% carbonization yield at 900 °C. In comparison, polymer **P2** also experienced a weight loss due to the alkyl chain cleavage at around 348 ~ 480 °C. The remaining backbone, however, was stable up to 900 °C, giving a carbonization yield of 52%. The result is in good agreement with the weight percentage of the aromatic backbone (57%). The high thermal stability of the **P2** backbone was a result of its ladder-type nature and promised its potential in applications as pre-functionalized precursors for sp^2 carbon materials.^{58, 59} Differential scanning calorimetric (DSC, Figure S34, S35, ESI) analysis of **P1** showed an irreversible exothermic transition at 129 °C. This transition was attributed to a thermal triggered cross-linking reaction between the vinyl groups, which indeed converted **P1** into an insoluble material after just one heating cycle. In comparison, **P2** possessed

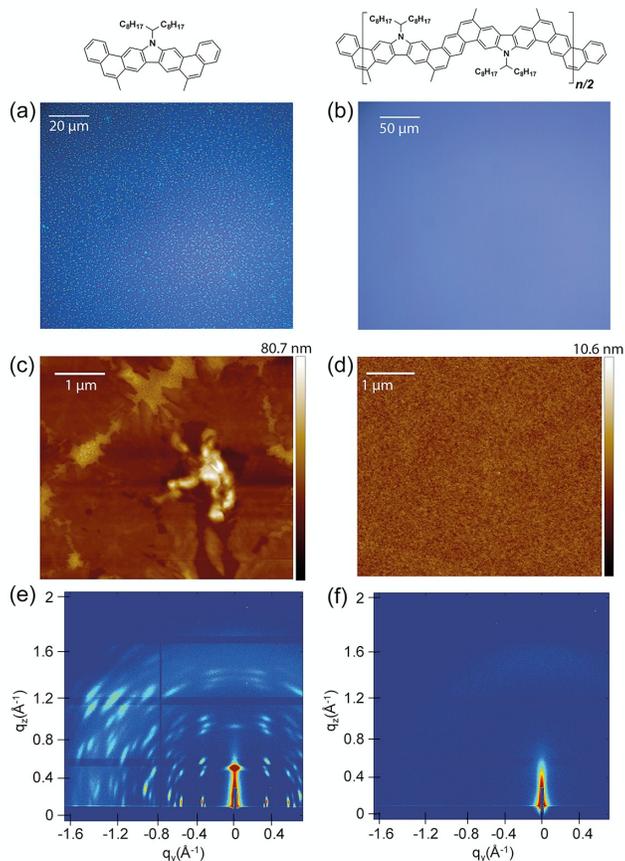


Figure 5. Film morphology comparison of **3** and **P2**. The thin films were deposited on UV-Ozone cleaned silicon wafers by spin-casting solutions (2mg/ml in toluene) at a rate of 2000 rpm. (a) Optical microscope image of **3** with observed microcrystals (1 ~ 3 μm) and (b) that of **P2** with no optical feature; (c) AFM images of microcrystals of **3** (RMS = 5.39 nm) and (d) amorphous morphology of **P2** (RMS = 0.45 nm); (e) GIWAXS patterns of **3** and (f) **P2**. Both samples were measured at an incident angle of 0.2° and 30 second exposure time, and both images have the same color scale.

a thermally stable backbone, showing no thermal transition before its side-chain cleavage temperature in the DSC measurement.

Solution processing of **P2** into thin films would be a key step for future exploration of its applications. Compared to its small molecular counterpart **3**, polymeric **P2** was expected to possess better processability for uniform thin films. Thin film morphologies of **3** and **P2** on SiO₂ substrates were investigated after spin-casting or solution-shearing casting from solutions in toluene (Figure 5). For small molecule **3**, both methods afforded polycrystalline thin films, which were composed of randomly distributed microcrystals with sizes in the range of 1 - 3 μm . Atomic force microscopy (AFM) revealed a very rough surface for this polycrystalline film with root mean square (RMS) roughness of 5.39 nm. In contrast, **P2** can be processed into uniform thin films by either method. No observable feature can be identified under optical microscope. AFM image demonstrated an amorphous morphology with much lower roughness (RMS = 0.45 nm). Grazing incidence wide-angle X-ray scattering (GIWAXS) revealed highly crystalline scattering peaks for the thin film of **3** and no observable diffraction feature for that of **P2** (Figure 5e,f). These results suggested that the polymer chains were packed in an amorphous manner on SiO₂ substrates despite its rigid backbone. The excellent film formation ability of **P2** enables future investigation of its material properties.

In order to further characterize the solid-state dimension, conformation, and self-assembly of **P2**, scanning tunneling microscopic (STM) images were recorded on highly ordered pyrolytic graphite (HOPG) (Figure 6). A solution of **P2** (0.3 mg/ml) in chloroform was drop-casted onto heated HOPG substrate and analyzed by STM. The image exhibited uniform and fully extended rod-like morphology, indicating self-assembly of the rigid polymer chain of **P2** on HOPG substrate.^{20, 60} The highly ordered self-assembly was likely a result of the strong π - π interaction between HOPG substrate and the aromatic ladder-type backbone.^{61, 62} These rods under STM showed alternating sections of high and low signal with a periodic length at around

1.27 nm. According to the single crystal structure of **3** and DFT calculation of model oligomers resembling **P2**, the feature length of each repeating unit on **P2** was close to 1.26 nm, matching well with the experimental result. The periodic distance between the rods under STM was around 0.7 nm, while the width of calculated polymer backbone without alkyl chain is close to 0.68 nm. Taking consideration of the additional contribution to the width from the side-chains, it is likely that the neighbouring **P2** rods were partially stacked, in a manner similar to the literature reported graphene nanoribbons.⁶⁰ In a sharp contrast, STM analysis of **P1** showed no ordered feature, probably a result of low surface interaction between the non-ladder backbone and the HOPG substrate (Figure S38, S39, ESI).

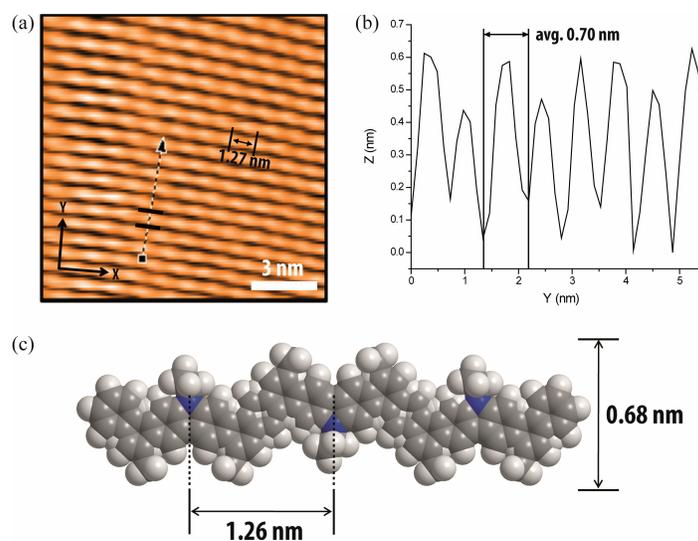


Figure 6. (a) STM image of **P2** on highly-ordered pyrolytic graphite; (b) Section profile along the arrow line drawn in (a). The STM image was obtained with a tunneling current set point of 0.9 nA and sample bias of 50 mV. The distance between consecutive convex spots along the X-axis is 1.27 nm, and average distance between peaks along the Y-axis is 0.70 nm. (c) Theoretical dimensions of a oligomeric model **P2** backbone from DFT calculation (B3LYP/6-311G).

CONCLUSION

In conclusion, a highly efficient synthetic approach to a conjugated ladder-type polymer has been established on the basis of thermodynamically controlled ring-closing olefin metathesis reaction. The resulting polymer possesses highly rigid backbone with less than one defect per chain on average, meanwhile maintaining good solubility and solution processability. The feasible and versatile nature of this method enables an efficient and impactful way to the synthesis of novel polymer materials with desirable features that will potentially be useful for thin film devices.

EXPERIMENTAL SECTION

Synthesis of P1. To a 100 mL Schlenk flask was added **1** (1.03 g, 1.40 mmol), 1,4-dibromo-2,5-divinylbenzene (0.40 g, 1.40 mmol), Pd(PPh₃)₄ (0.16 g, 10 mol%), K₂CO₃ (1.16 g, 8.40 mmol), Aliquat 336 (0.65 mL, 0.35 mmol), and several crystals of BHT under N₂. Degassed toluene (40 mL) and water (8 mL) were added and further degassed 3 times by freeze-pump-thaw. The reaction mixture was stirred at 100 °C for 24 h in dark, before it was cooled down to room temperature. 2-Bromostyrene (0.77 mL, 5.60 mmol) was added into the flask, and the mixture was stirred at 100 °C for 24 h. After 24 h, 2-vinylphenylboronic acid (1.73 g, 11.2 mmol) was added into the flask, and the mixture was stirred at 100 °C for another 24 h. The resulting product was precipitated from methanol, filtered, and washed with acetone. The solid was dried under vacuum to afford **P1** (0.84 g, 98%, $M_n = 10$ kg/mol, PDI = 2.78 by SEC). **P1** was further purified by preparative recycling SEC to remove oligomers to afford a purified batch with higher M_n and lower PDI (0.64 g, 75%, $M_n = 20$ kg/mol, PDI = 1.88 by SEC).

Synthesis of P2. To a 100 mL Schlenk flask was added **P1** (120 mg, 0.20 mmol) and Grubbs' 2nd generation catalyst (8 mg, 5 mol%) under N₂. Subsequently, degassed toluene (12 mL) was added, and the reaction mixture was stirred at reflux temperature. Immediately, another portion of Grubbs' 2nd generation catalyst (26 mg, 15 mol%) in degassed toluene (8 mL) was added for 4 h using syringe pump. After that, the reaction mixture was stirred for an additional 2 h at reflux temperature before cooling down to room temperature. The resulting product was then precipitated from methanol and filtered. The product was further washed *via* Soxhlet extraction with acetone and hexane, before extracted with chloroform. The chloroform solution was filtered and condensed under reduced pressure. The desired product was precipitated from methanol. The precipitate was filtered and dried under vacuum to afford **P2** (100 mg, 91%, $M_n = 15$ kg/mol, PDI = 2.00 by SEC).

Electronic Supplementary Information (ESI) available:

Detailed experimental procedures, characterization data, NMR spectra, and crystallographic data (CIF). see DOI:

Acknowledgements

This work was supported by the National Priorities Research Program award (NPRP7-285-1-045) from the Qatar National Research Fund. The authors thank Dr. Nattamai Bhuvanesh for X-ray crystallography support, Dr. Vladimir Bakhmoutov for NMR spectroscopy support, Dr. Xu Zhou, Fang-Dong Zhuang, and Dr. Jian Pei (Peking University) for fluorescence quantum yield measurement, and Dr. Joseph Strzalka (Argonne National Laboratory) for GIWAXS film characterization support. Use of the Advanced Photon Source at Argonne National Laboratory was supported by the U. S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-06CH11357.

References

1. F. E. Arnold and R. L. Van Deusen, *Macromolecules*, 1969, 2, 497-502.
2. A.-D. Schluter, *Adv. Mater.*, 1991, 3, 282-291.
3. U. Scherf and K. Müllen, *Makromol. Chem. Rapid. Commun.*, 1991, 12, 489-497.

4. A. L. Briseno, S. C. B. Mannsfeld, P. J. Shamberger, F. S. Ohuchi, Z. Bao, S. A. Jenekhe and Y. Xia, *Chem. Mater.*, 2008, 20, 4712-4719.
5. J. D. Plumbhof, T. Stöferle, L. Mai, U. Scherf and R. F. Mahrt, *Nat. Mater.*, 2014, 13, 247-252.
6. J. K. Richard G. Jones, Robert Stepto, Edward S. Wilks Michael Hess, Tatsuki Kitayama, W. Val Metanomski, *Compendium of polymer terminology and nomenclature IUPAC recommendations 2008*, The Royal Society of Chemistry, Cambridge, UK, 2008.
7. S. Liu, Z. Jin, Y. C. Teo and Y. Xia, *J. Am. Chem. Soc.*, 2014, 136, 17434-17437.
8. M. B. Goldfinger, K. B. Crawford and T. M. Swager, *J. Am. Chem. Soc.*, 1997, 119, 4578-4593.
9. M. Carta, R. Malpass-Evans, M. Croad, Y. Rogan, J. C. Jansen, P. Bernardo, F. Bazzarelli and N. B. McKeown, *Science*, 2013, 339, 303-307.
10. F. C. Grozema, P. T. van Duijnen, Y. A. Berlin, M. A. Ratner and L. D. A. Siebbeles, *J. Phys. Chem. B*, 2002, 106, 7791-7795.
11. P. Prins, F. C. Grozema, J. M. Schins, S. Patil, U. Scherf and L. D. A. Siebbeles, *Phys. Rev. Lett.*, 2006, 96.
12. E. J. Dell, B. Capozzi, K. H. DuBay, T. C. Berkelbach, J. R. Moreno, D. R. Reichman, L. Venkataraman and L. M. Campos, *J. Am. Chem. Soc.*, 2013, 135, 11724-11727.
13. M. Samiullah, D. Moghe, U. Scherf and S. Guha, *Phys. Rev. B*, 2010, 82, 205211.
14. Y.-W. Son, M. L. Cohen and S. G. Louie, *Nature*, 2006, 444, 347-349.
15. X. Li, X. Wang, L. Zhang, S. Lee and H. Dai, *Science*, 2008, 319, 1229-1232.
16. A. Tsuda and A. Osuka, *Science*, 2001, 293, 79-82.
17. Z. H. Chen, J. P. Amara, S. W. Thomas and T. M. Swager, *Macromolecules*, 2006, 39, 3202-3209.
18. R. L. Van Deusen, *J. Polym. Sci., Part B: Polym. Phys.*, 1966, 4, 211-214.
19. A. D. Schluter, M. Löffler and V. Enkelmann, *Nature*, 1994, 368, 831-834.
20. X. Yang, X. Dou, A. Rouhanipour, L. Zhi, H. J. Räder and K. Müllen, *J. Am. Chem. Soc.*, 2008, 130, 4216-4217.
21. U. Scherf and K. Müllen, *Polymer*, 1992, 33, 2443-2446.
22. U. Scherf, *J. Mater. Chem.*, 1999, 9, 1853-1864.
23. S. A. Patil, U. Scherf and A. Kadashchuk, *Adv. Funct. Mater.*, 2003, 13, 609-614.
24. S. Qiu, P. Lu, X. Liu, F. Shen, L. Liu, Y. Ma and J. Shen, *Macromolecules*, 2003, 36, 9823-9829.
25. S. J. Rowan, S. J. Cantrill, G. R. L. Cousins, J. K. M. Sanders and J. F. Stoddart, *Angew. Chem. Int. Ed.*, 2002, 41, 898-952.
26. M. M. Durban, P. D. Kazarinoff, Y. Segawa and C. K. Luscombe, *Macromolecules*, 2011, 44, 4721-4728.
27. Y. X. Yao and J. M. Tour, *Macromolecules*, 1999, 32, 2455-2461.
28. R. H. Grubbs, S. J. Miller and G. C. Fu, *Acc. Chem. Res.*, 1995, 28, 446-452.
29. T. J. Donohoe, A. J. Orr and M. Bingham, *Angew. Chem. Int. Ed.*, 2006, 45, 2664-2670.
30. A. Iuliano, P. Piccioli and D. Fabbri, *Org. Lett.*, 2004, 6, 3711-3714.
31. M. C. Bonifacio, C. R. Robertson, J. Y. Jung and B. T. King, *J. Org. Chem.*, 2005, 70, 8522-8526.
32. S. K. Collins, A. Grandbois, M. P. Vachon and J. Côté, *Angew. Chem. Int. Ed.*, 2006, 45, 2923-2926.
33. N. A. Vermeulen, O. Karagiari, A. A. Sarjeant, C. L. Stearn, J. T. Hupp, O. K. Fahra and J. F. Stoddart, *J. Am. Chem. Soc.*, 2013, 135, 14916-14919.
34. T. M. Trnka and R. H. Grubbs, *Acc. Chem. Res.*, 2001, 34, 18-29.
35. J. F. Morin and M. Leclerc, *Macromolecules*, 2001, 34, 4680-4682.
36. N. Blouin and M. Leclerc, *Acc. Chem. Res.*, 2008, 41, 1110-1119.
37. Y. Zhou, T. Kurosawa, W. Ma, Y. Guo, L. Fang, K. Vandewal, Y. Diao, C. Wang, Q. Yan, J. Reinspach, J. Mei, A. L. Appleton, G. I. Koleilat, Y. Gao, S. C. B. Mannsfeld, A. Salleo, H. Ade, D. Zhao and Z. Bao, *Adv. Mater.*, 2014, 26, 3767-3772.
38. H. Langhals, *Helv. Chim. Acta*, 2005, 88, 1309-1343.
39. S. H. Park, A. Roy, S. Beaupre, S. Cho, N. Coates, J. S. Moon, D. Moses, M. Leclerc, K. Lee and A. J. Heeger, *Nature Photon.*, 2009, 3, 297-302.
40. J. Li and A. C. Grimsdale, *Chem. Soc. Rev.*, 2010, 39, 2399-2410.
41. Y. Zou, T. Ye, D. Ma, J. Qin and C. Yang, *J. Mater. Chem.*, 2012, 22, 23485-23491.
42. Z. M. Hudson, Z. Wang, M. G. Helander, Z. H. Lu and S. Wang, *Adv. Mater.*, 2012, 24, 2922-2928.
43. J. Gierschner, J. Cornil and H. J. Egelhaaf, *Adv. Mater.*, 2007, 19, 173-191.
44. Z. Wei-ya, X. Si-shen, Q. Sheng-fa, W. Gang and Q. Lu-xi, *Journal of Physics: Condensed Matter*, 1996, 8, 5793.
45. J. W. Kingsley, P. P. Marchisio, H. Yi, A. Iraqi, C. J. Kinane, S. Langridge, R. L. Thompson, A. J. Cadby, A. J. Pearson, D. G. Lidzey, R. A. L. Jones and A. J. Parnell, *Sci. Rep.*, 2014, 4, 5286.

46. W. Li, L. Yang, J. R. Tumbleston, L. Yan, H. Ade and W. You, *Adv. Mater.*, 2014, 26, 4456-4462.
47. Y. Liang, D. Feng, Y. Wu, S.-T. Tsai, G. Li, C. Ray and L. Yu, *J. Am. Chem. Soc.*, 2009, 131, 7792-7799.
48. Y. Liang, Z. Xu, J. Xia, S.-T. Tsai, Y. Wu, G. Li, C. Ray and L. Yu, *Adv. Mater.*, 2010, 22, E135-E138.
49. S. Wakim, S. Beaupre, N. Blouin, B.-R. Aich, S. Rodman, R. Gaudiana, Y. Tao and M. Leclerc, *J. Mater. Chem.*, 2009, 19, 5351-5358.
50. A. C. Grimsdale and K. Müllen, *Macromol. Rapid. Commun.*, 2007, 28, 1676-1702.
51. S. Y. Cho, A. C. Grimsdale, D. J. Jones, S. E. Watkins and A. B. Holmes, *J. Am. Chem. Soc.*, 2007, 129, 11910-11911.
52. U. Scherf and E. J. W. List, *Adv. Mater.*, 2002, 14, 477-487.
53. H. Roex, P. Adriaensens, D. Vanderzande and J. Gelan, *Macromolecules*, 2003, 36, 5613-5622.
54. T.-A. Chen, X. Wu and R. D. Rieke, *J. Am. Chem. Soc.*, 1995, 117, 233-244.
55. A. R. Aiyar, J.-I. Hong, R. Nambiar, D. M. Collard and E. Reichmanis, *Adv. Funct. Mater.*, 2011, 21, 2652-2659.
56. K. Kim, W. Regan, B. Geng, B. Alemán, B. M. Kessler, F. Wang, M. F. Crommie and A. Zettl, *Phys. Status Solidi Rapid Res. Lett.*, 2010, 4, 302-304.
57. T. Yamamoto, K. Watanabe and E. Hernández, in *Carbon Nanotubes*, eds. A. Jorio, G. Dresselhaus and M. Dresselhaus, Springer Berlin Heidelberg, 2008, vol. 111, ch. 5, pp. 165-195.
58. J. P. McGann, M. Zhong, E. K. Kim, S. Natesakhawat, M. Jaroniec, J. F. Whitacre, K. Matyjaszewski and T. Kowalewski, *Macromol. Chem. Phys.*, 2012, 213, 1078-1090.
59. P. Bajaj and A. K. Roopanwal, *J. Macromol. Sci., Polym. Rev.*, 1997, 37, 97-147.
60. A. Narita, X. Feng, Y. Hernandez, S. A. Jensen, M. Bonn, H. Yang, I. A. Verzhbitskiy, C. Casiraghi, M. R. Hansen, A. H. R. Koch, G. Fytas, O. Ivasenko, B. Li, K. S. Mali, T. Balandina, S. Mahesh, S. De Feyter and K. Müllen, *Nature Chem.*, 2014, 6, 126-132.
61. Y. B. Zheng, B. K. Pathem, J. N. Hohman, J. C. Thomas, M. Kim and P. S. Weiss, *Adv. Mater.*, 2013, 25, 302-312.
62. D. den Boer, M. Li, T. Habets, P. Iavicoli, A. E. Rowan, R. J. M. Nolte, S. Speller, D. B. Amabilino, S. De Feyter and J. A. A. W. Elemans, *Nature Chem.*, 2013, 5, 621-627.