

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

π -Extended [12]Cycloparaphenylenes: from a Hexaphenylbenzene Cyclohexamer to its Unexpected C_2 -symmetric Congener

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Florian E. Golling^{a,b}, Silvio Osella^c, Martin Quernheim^a, Manfred Wagner^a, David Beljonne^c, Klaus Müllen^{a,*}

The synthesis of π -extended [12]cycloparaphenylene (CPP) derivatives from a kinked triangular macrocycle is presented. Depending on the reaction conditions for reductive aromatization, either a hexaphenylbenzene cyclohexamer or its C_2 -symmetric congener was obtained. Their structures were confirmed by NMR spectroscopy or X-ray crystallographic analysis. With the support of DFT calculations, a mechanistic explanation for the unexpected formation of the oval shaped bis(cyclohexadiene)-bridged C_2 -symmetric macrocycle is provided. The here employed congested hexaphenylbenzene mode of connectivity in conjunction with a non-strained precursor improves oxidative cyclodehydrogenation toward the formation of ultrashort carbon nanotubes (CNT)s. Thus, this strategy can pave the way for new conceptual approaches of a solution-based bottom-up synthesis of CNTs.

Introduction

Carbon nanotubes (CNT)s have gained a great deal of attention over the last decades due to their attractive physical and electronic properties.¹ Special emphasis has been put on the controlled synthesis of CNTs, since their electronic features sensitively depend on size and shape (edge structure, chirality).² Cycloparaphenylenes (CPP)s are envisioned as precursors for a concise bottom-up synthesis of carbon nanobelts, i. e., ultrashort CNTs.^{3,4} On surfaces, CPPs,⁵ besides other templates,⁶ have been successfully used for the growth of diameter-defined CNTs, whereas the advancement in solution-based approaches continues to be limited.⁷

To reach this goal, several π -extended CPPs⁸ and structurally closely related derivatives⁹ have been synthesized over the last years. However, a necessary degree of axial π -extension of these structures, from a CPP to a nanobelt precursor (Fig. 1), was not accomplished to enable a solution-based bottom-up synthesis. In contrast, [9]cyclo-1,4-naphthylene¹⁰ and a [10]CPP dimer,¹¹ are sufficiently π -extended and can thus be regarded as carbon nanobelt precursors, but dehydrogenation of the products was not reported.

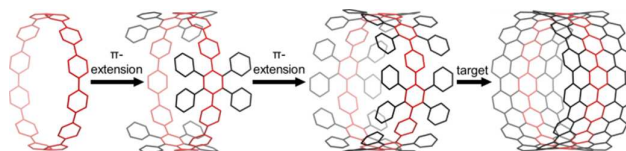


Fig. 1. schematic modes of π -extension: CPP (left), insufficiently π -extended CPP (second left), fully π -extended CPP to give a nanobelt precursor (second right), and CNT (right).

Previously, we attempted a π -extension of CPPs using hexaphenylbenzene (HPB) as the general building block, which can be converted to hexa-*peri*-hexabenzocoronene (HBC) via oxidative cyclodehydrogenation. This concept has been widely employed for the bottom-up synthesis of 1D- and 2D-structures, such as graphene nanoribbons (GNR)¹² and nanographenes.¹³ To obtain π -lengthened CPPs (3D), HPB was embedded into a macrocycle to give a cyclic hexaphenylbenzene trimer ([3]CHPB) and its corresponding larger homologues.¹⁴ A further addition of phenyl rings afforded polyphenylene cylinders (PPC)s, such as **1**, following the parallelogram motif (frame A, Fig. 2).¹⁵ A complete cyclodehydrogenation could not be achieved. Thus, the macrocycles have been redesigned with a different connectivity, which is entirely based on the congested HPB motif (frame B, Figure 2), where one bridging-phenylene moiety is shared by two hexaphenylbenzenes. This structural motif leads to a lower degree of rotational freedom of the attached phenyl groups, which is favorable for the desired cyclodehydrogenation.

^a Max-Planck-Institut für Polymerforschung, Ackermannweg 10, 55128 Mainz (Germany).

^b Graduate School Materials Science in Mainz, Staudinger Weg 9, 55128 Mainz (Germany).

^c Chimie des Matériaux Nouveaux & Centre d'Innovation et de Recherche en Matériaux Polymères, Université de Mons- UMONS/Materia Nova, Place du Parc 20, 7000 Mons (Belgium)

Electronic Supplementary Information (ESI) available: Experimental protocols, crystallographic data for **3** and **5**, ¹H NMR, ¹³C NMR, 2D NMR, MALDI-TOF MS, as well as computational details. CCDC 1033267, CCDC 1033268. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/x0xx00000x

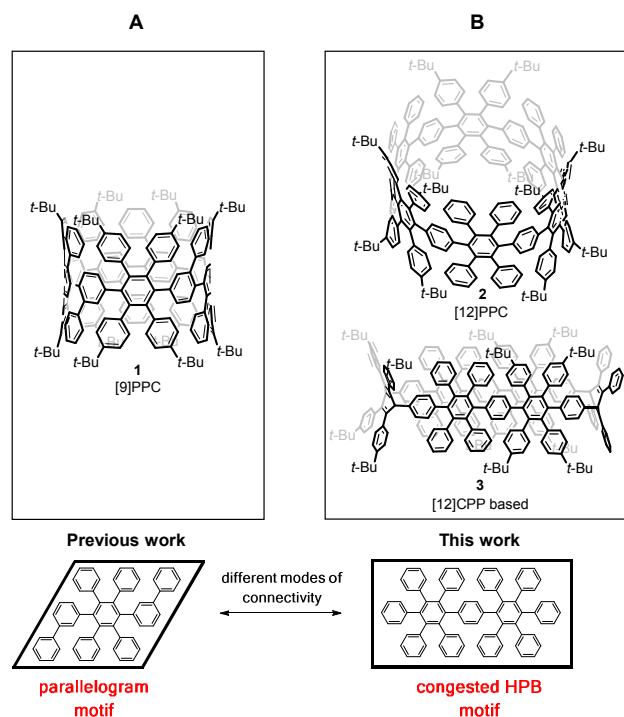


Fig. 2. Two different modes of connectivity. Previous work (left): CNT synthesis *via* the parallelogram motif A (left) using [9]PPC 1 and [15]PPC (not shown); in this work (right): CNTs were approached *via* the congested HPB motif B.


Herein, we present the synthesis of PPCs that entirely consist of congested hexaphenylbenzene moieties. A congested cyclic hexaphenylbenzene hexamer ([6]CCHPB) **2** and its oval-shaped C_2 -symmetric congener **3** were synthesized *via* Suzuki coupling and subsequent reductive aromatization. The oxidative cyclodehydrogenation of both structures was investigated and a hitherto unprecedented degree of cyclodehydrogenation for PPC systems was achieved.

Results and discussion

For the synthesis of the new macrocycles [6]CCHPB **2** and **3** (Scheme 1), we applied a Suzuki-mediated cyclization introduced by Bertozzi and Jasti^{3a} together with a strategy, developed in our group, to convert structurally related, linear polyphenylene (PP) precursors into GNRs,^{12b, 16} using oxidative cyclodehydrogenation.¹⁷ Therefore, the *para*-HPB diboronate, employed for linear PPs, was exchanged with the kinked diboronate **4**. Two different precursors, **6** and **7**, were then foreseen to give the triangular macrocycle **8**, as the kink angles of the three V-shaped units in **6** and **7** add up to $\sim 210^\circ$.¹⁴ Tetraphenyl and *tetrakis*(4-*t*-butylphenyl) were introduced in an alternating fashion to provide solubility and render cyclodehydrogenation possible.


As shown in Scheme 1, the unique “di-kinked” diboronate **7** and its “mono-kinked” counterpart **6** are synthesized *via* Suzuki coupling. For each approach, a fourfold excess of either diboronate **4** or dibromide **5** was used. Dibromide **6** and diboronate **7** could be obtained in yields of 35 %, and 40 % respectively. The macrocyclization of these two building blocks was achieved by Suzuki coupling in diluted media (0.1 mmol) to give **8** in 32 % yield;

side products such as higher linear homologues could be separated by recycling GPC.

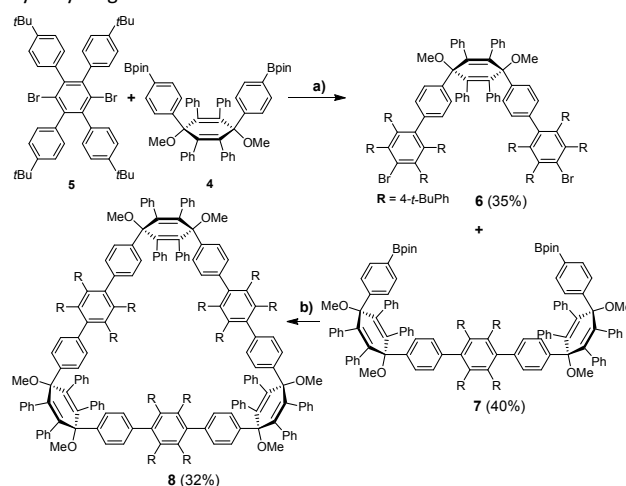


Scheme 1. Synthesis of Triangular Macrocycle **8**. a) Pd(PPh₃)₄, Cs₂CO₃, 100 °C, 2 d, (toluene/H₂O); b) Pd(PPh₃)₄, Cs₂CO₃, 100 °C, 2 d, (toluene/H₂O).

An initial demethoxylation of **8** was achieved under reductive conditions that had previously been applied in our group: low-valent titanium was generated *in situ* and reacted with the triangular macrocycle **8** to give **2** in 46 % (Scheme 2). The applied conditions are very effective at inducing reductive aromatization, but require elevated temperatures (80 °C). To unambiguously characterize cyclohexamer **2**, 2D NMR experiments (section 4.1, ESI†) were carried out. Single crystals of **2** were obtained after slow diffusion of MeCN into DCM. However, the obtained crystals did not yield sufficient reflections to resolve the structure.

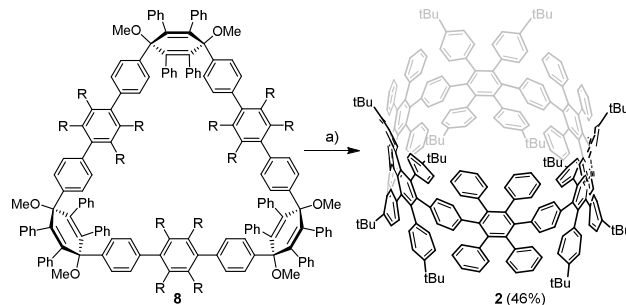

Scheme 2. Synthesis of the [6]CCHPB **2**. a) TiCl₄, LiAlH₄, 80 °C, 3 d (THF).

Therefore, we performed density functional theory (DFT) calculations of **2** with the B3LYP hybrid functional¹⁸ and the 6-31G(d) Pople basis set¹⁹. The fully optimized geometry revealed a torsional angle between neighboring phenylene units of about 90° (Fig. 3, right), in an alternating fashion within the CPP ring. Interestingly, in comparison to PPC **1** (Fig. 2, left), which is based on an odd membered CPP ring with an ellipsoidal structure, cyclohexamer **2** exhibits a circular-shaped structure.

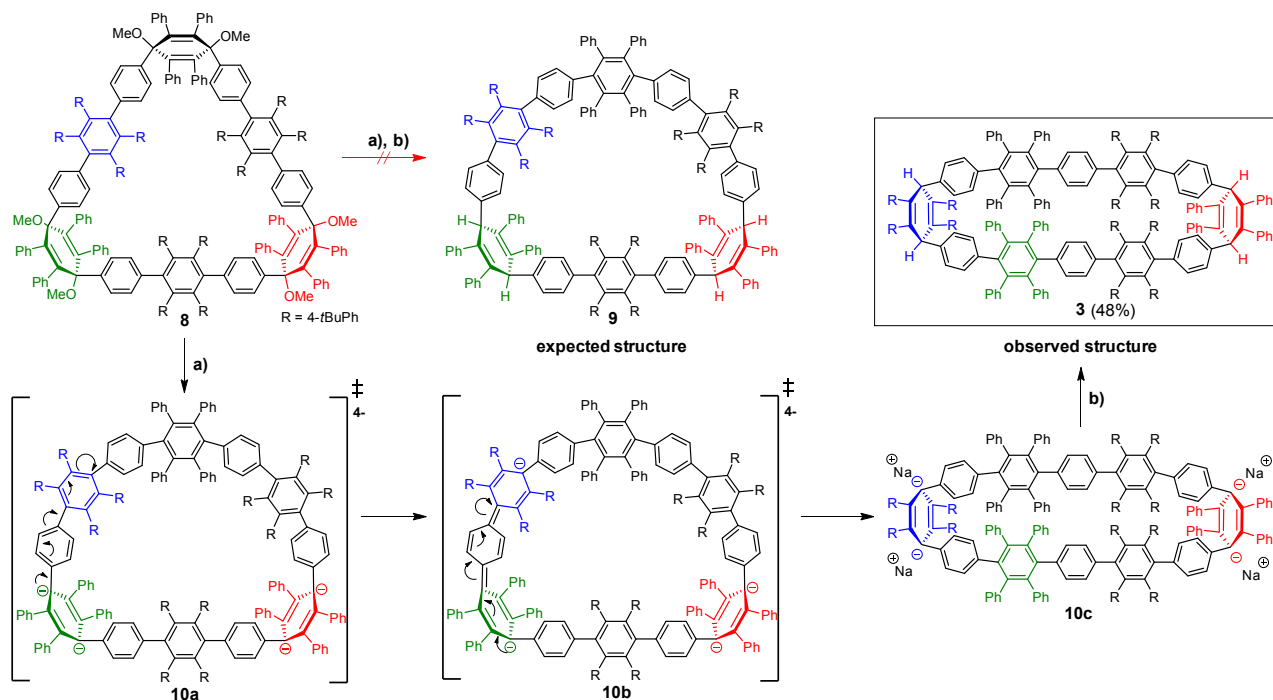

In the second approach, a milder reduction of compound **8** with sodium naphthalenide (NaNp) ($-78\text{ }^{\circ}\text{C}$ vs. $80\text{ }^{\circ}\text{C}$) was attempted (Scheme 3). To our surprise, we did not obtain the expected [6]CCHPB **2**, but rather a macrocycle containing four additional hydrogen atoms (Scheme 3). This was first indicated by the blue color of the reaction solution, hinting at the formation of anionic species, which can stem from an overreduction of the cyclohexadiene moieties, as reported in the literature.^{3q} Therefore, the reaction was quenched with a proton source (MeOH) to trap the charged intermediate, while the use of iodine to quench the reaction or lowering the temperature did not afford any characterizable product. By mass spectrometry, we inferred that the obtained structure possesses four additional hydrogen atoms in comparison to [6]CCHPB **2**. We expected that the reductive aromatization had not overcome ring strain at temperatures of $-78\text{ }^{\circ}\text{C}$, but rather came to a halt after *in situ* formation of a tetraanionic species, which was then preserved by protonation. For this structure, only one of the three 3,6-dimethoxycyclohexadienes was reduced, when applying the above described conditions to give one phenylene moiety instead of the expected three, as shown in Scheme 3. Astonishingly, single crystal X-ray crystallography (Fig. 5)

revealed the formation of **3** instead of the expected structure **9**.

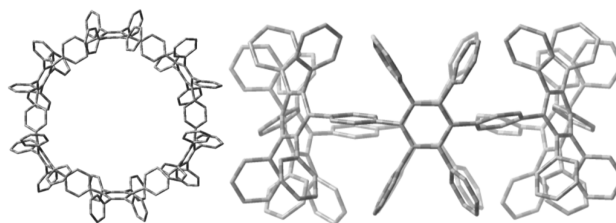


Fig. 3. Optimized geometry of **2** top (left) and side (right) view, as calculated at the B3LYP/6-31G(d) level of theory. Hydrogen atoms are omitted for clarity.

The formation of **3** can be explained by taking into account the mechanistic details of the aromatization: a stepwise two-electron reduction is proposed in the literature,^{3a} forming a radical under loss of one methoxy group. After the second one-electron transfer, a monoanion is formed, which leads to an expulsion of the remaining methoxy group under concomitant aromatization, affording a phenylene moiety from the previous 3,6-dimethoxycyclohexadiene. Based on the obtained product **3**, we propose a mechanism *via* a tetraanionic species with subsequent charge migration from the 3,6-bridging cyclohexadiene moiety to the *tetrakis*(*t*-butylphenyl)-substituted phenylene ring (Scheme 3),

compound **10c**. In detail, the reductive aromatization follows the above mechanism for one of the three cyclohexadiene moieties. Reduction of the second and third cyclohexadiene units does not yield the neutral hydrocarbon **2** but proceeds instead to tetraanion **10c** (Scheme 3). Migration of the anionic charges in intermediate **10a** and **10b**, as shown by arrows in Scheme 3, gives the thermodynamically more favorable C_2 -symmetric tetraanion **10c**.²⁰ Protonation “freezes” the anionically charged structure, leading to the oval-shaped compound **3**.

To support this mechanistic hypothesis, we performed DFT calculations for the different macrocycles shown in Scheme 3. Interestingly, the tetraanion **10** was not found as a stable intermediate, but rather spontaneously evolved into the C_2 -symmetric tetraanion **10c**. On the other hand, the neutral counterpart of the anionic structures (namely **8a**, **9**, and **3**; for all structures the methoxy groups are substituted by hydrogen atoms to reduce computational cost) were obtained as stable structures. To account for the observed charge migration, we compared the relative strain energies of **3**, **8a**, and **9** (Fig. 4). The calculations reveal an increase of strain energy by ~ 24.3 kcal/mol when going from **8** to **9**. This originates from the presence of one additional phenylene moiety obtained after reductive aromatization of **8**; hence a strain relief toward the starting material **8a** is not feasible. On the other hand, a thermodynamically more favorable geometry with a reduced relative strain energy of ~ 2.5 kcal/mol can be reached through a charge migration along one phenylene unit from **10a** over **10b** to its protonated form **3**, as depicted in Scheme 3.

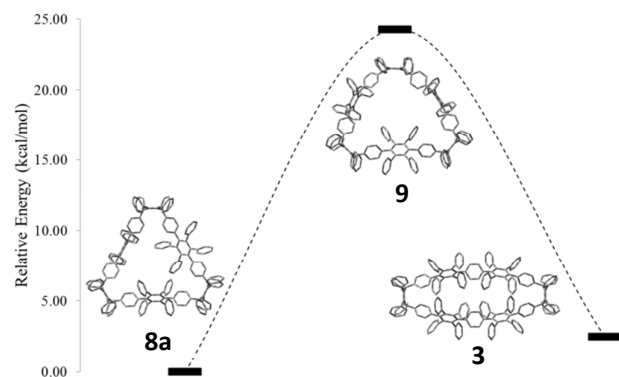


Fig. 4. Comparison of strain energies of **8a**, **9**, and **3**, using DFT calculations at the B3LYP/6-31G(d) level of theory. For all structures, methoxy groups are substituted by hydrogen atoms. Hydrogen atoms are omitted for clarity.

To support the postulated resonance form of the tetraanionic intermediate **3a**, the size of the holes of macrocycle **3** (neutral structure) and **10c** (tetraanionic intermediate) were studied. The computed geometry optimization suggests an increase of the oval opening from 8.2 Å to 12.2 Å, respectively (opening of the neutral structure **9** is 13 Å), which is shown in Fig. 5. Thus, the equilibrium structure of the tetraanionic intermediate **10c** is shifted toward **3** in comparison to **9**. To understand whether the strain release is accompanied by a redistribution of charge over the entire aromatic system, a charge analysis for **11** ($2e^-$) and **10c** ($4e^-$) was performed: the dianionic structure **11** is considered as a starting point and shows that the charges are mainly localized over the cyclohexadiene moieties where the hydrogen atoms have been removed. For **10c**, the calculations reveal that the main part of the charges ($\sim 2e^-$) is strongly localized over the cyclohexadiene moieties

of the macrocycle, while the remaining partial charges ($\sim 2e^-$) are delocalized over the substituted phenyl rings of the belt (Fig. 16, ESI \ddagger), leading to an oval shaped macrocycle. These findings additionally corroborate the postulated form of the tetraanionic intermediate **10c** in opposition to **10a**. The proposed charge migration based on DFT calculations is also supported for a dianionic species after formation of one phenylene moiety (Fig. 10 and Fig. 15, ESI \ddagger). An over-reduction of [6]CCHPB **2** to give the tetraanion **10c**, which can be trapped by a proton source, has not been observed experimentally.

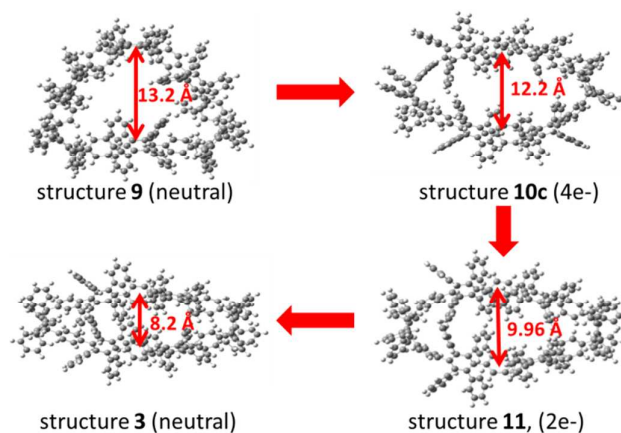


Fig. 5. Geometric analysis of structures **9**, **10c**, **11** and **3** to understand the equilibrium structure of tetraanion **10c**, using DFT calculations at the B3LYP/6-31G(d) level of theory. Structure **11** is twice negatively at one cyclohexadiene moiety, whereas the other contains contains to hydrogen atoms, analogously to the other structures.

Single crystals of **3** were obtained after slow vapor diffusion of MeCN into a solution of DCM. The crystal structure confirmed the oval-shaped nature (Fig. 6) of **3**. Pentaphenylene units (labeled in red) are bridged by two 3,6-substituted cyclohexa-1,4-dienes (labeled in blue). The pentaphenylene moieties are slightly bent (Fig. 6b) as the sp^3 -carbons cannot be fully torn out of plane due to angle constraints (Fig. 3, ESI \ddagger). Additionally, the crystal structure reveals the inherent design pattern: tetraphenyl and *tetrakis*-(4-*t*-butylphenyl) substituents are attached to the central ring in an alternating fashion.

As compounds **2** and **3** were designed in order to serve as direct precursors for a solution-based bottom-up synthesis of CNTs, we subjected both molecules to oxidative cyclodehydrogenation conditions using $FeCl_3$ at room temperature.¹⁵ For **2**, a loss of 20 hydrogen atoms of a possible 96 was observed by MALDI-MS, at which the cyclodehydrogenation came to a halt, despite prolonged reactions times. In contrast to our previous results, here we could, for the first time, determine the degree of cyclodehydrogenation due to isotopically resolved mass peaks. For the barely strained C_2 -symmetric congener **3**, of the 96 hydrogen atoms to obtain a CNT a loss of 60 could be observed (see Scheme S3, p. S92). The detailed analysis of the mass spectra hints at the formation of ribbon-like sidewall structures (Section 7.2, ESI \ddagger), rendering cyclodehydrogenation of the pentaphenylene sidewalls reasonable. However, since the structural analysis is based on mass spectrometry, well known side reactions for Scholl reactions, such as rearrangements, cannot be ruled out. Prolonged reaction times led to chloro-*de-t*-butylations; oxidative aromatization of the

cyclohexadiene moieties was not observed, even with other reagents at elevated temperature (DDQ, 120 °C).

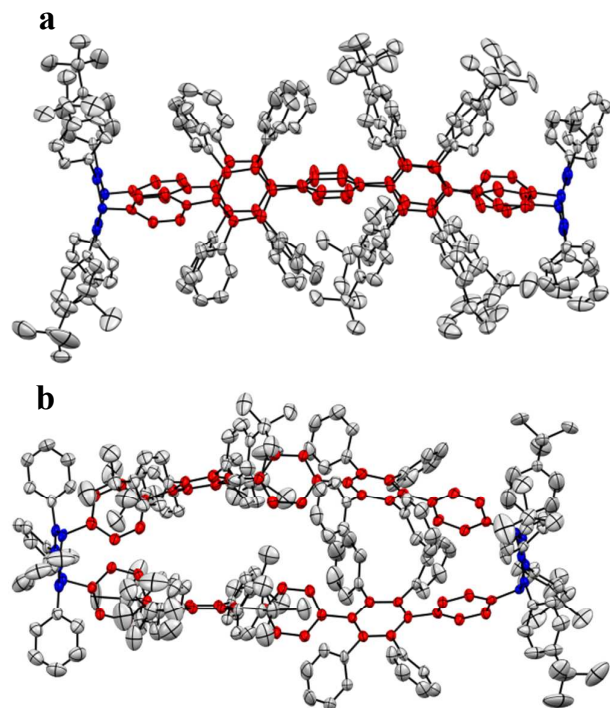


Fig. 6. Crystal structure of **3**. ORTEP drawing at 50% probability level. All hydrogen atoms are omitted for clarity. Phenylene moieties are labelled in red. 3,6-bridging cyclohexa-1,4-dienes are labelled in blue. Front view (a) and top view (b).

Conclusions

In summary, we presented the bottom-up synthesis of a [12]CPP based nanobelt precursor [6]CCHPB **2** and its unexpected weakly-strained C_2 -symmetric congener **3**. Their structural features are based on congested hexaphenylbenzene units, i.e., two hexaphenylbenzenes are bridged by one shared phenylene unit. The surprising synthesis of **3** occurred due to the use of the milder reducing agent NaNP, whereas low valent titanium was applied for the synthesis of the congested HPB **2**. We assume that two different products were obtained because of the high difference of thermal energy (ΔT 160 °C), giving rise to a kinetic control of the reaction. The mechanistic explanation for the astonishing charge migration during reductive aromatization of **3** was confirmed by DFT calculations. The inherent congested HPB structural feature leads to reduced rotational freedom for both macrocycles in comparison to the previously prepared PPCs such as **1**. Finally, we attempted oxidative cyclodehydrogenation which resulted in a loss of 20 H and 60 H for **2** and **3**, respectively. The higher loss for **3** may be assigned to the barely strained pentaphenylenes. The above discussed findings suggest that the oxidative cyclodehydrogenation runs more smoothly if a) the congested HPB structural motif in comparison to the parallelogram approach is applied, as this mode of connectivity restricts rotation of the π -extended macrocycle, thus avoiding mismatched structural arrangements possible for **1** (parallelogram vs. trapezoid); and b) a minimum of strain is present in the cyclic

system, observed for **3** in comparison to **2**. Thus, the synthesis of such non-strained precursors which can be pre-cyclodehydrogenated close to the target structure and are then being converted to strained geometries could open up new concepts for a concise bottom-up synthesis of carbon nanobelts.

Acknowledgements

We would like to acknowledge funding from DFG project MU 334/36-1. We thank Dr. Schollmeyer (University of Mainz) for X-ray crystal structure analysis. F.E.G. is a recipient of a fellowship through the Excellence Initiative (DFG/GSC 266). F.E.G. thanks A. N. Skabeev and J. W. Krumpfer for helpful discussions. This work was supported by the European Commission through the Marie Curie projects GENIUS (PITN-2010-GA-264694). The work in Mons is partly supported by the Belgian National Fund for Scientific Research (FNRS), the FNRS/FRFC 'PHOTOGRAPH' PDR project and the Belgian Science Policy Office (IAP 7/05). DB is a FNRS Research Director.

References

- (a) M. S. Dresselhaus, G. Dresselhaus, J. C. Charlier and E. Hernández, *Philos. Trans. R. Soc. London* 2004, **362**, 2065-2098; (b) D. Jariwala, V. K. Sangwan, L. J. Lauhon, T. J. Marks and M. C. Hersam, *Chem. Soc. Rev.*, 2013, **42**, 2824-2860.
- S. Louie, in *Carbon Nanotubes*, eds. M. Dresselhaus, G. Dresselhaus and P. Avouris, Springer Berlin Heidelberg, 2001, vol. 80, ch. 6, p. 113-145.
- (a) R. Jasti, J. Bhattacharjee, J. B. Neaton and C. R. Bertozzi, *J. Am. Chem. Soc.*, 2008, **130**, 17646-17647; (b) H. Takaba, H. Omachi, Y. Yamamoto, J. Bouffard and K. Itami, *Angew. Chem. Int. Ed.*, 2009, **48**, 6112-6116; (c) H. Omachi, S. Matsuura, Y. Segawa and K. Itami, *Angew. Chem. Int. Ed.*, 2010, **49**, 10202-10205; (d) S. Yamago, Y. Watanabe and T. Iwamoto, *Angew. Chem. Int. Ed.*, 2010, **49**, 757-759; (e) T. Iwamoto, Y. Watanabe, Y. Sakamoto, T. Suzuki and S. Yamago, *J. Am. Chem. Soc.*, 2011, **133**, 8354-8361; (f) T. J. Sisto, M. R. Golder, E. S. Hirst and R. Jasti, *J. Am. Chem. Soc.*, 2011, **133**, 15800-15802; (g) Y. Segawa, P. Senel, S. Matsuura, H. Omachi and K. Itami, *Chem. Lett.*, 2011, **40**, 423-425; (h) Y. Segawa, S. Miyamoto, H. Omachi, S. Matsuura, P. Šenel, T. Sasamori, N. Tokitoh and K. Itami, *Angew. Chem. Int. Ed.*, 2011, **50**, 3244-3248; (i) E. Kayahara, Y. Sakamoto, T. Suzuki and S. Yamago, *Org. Lett.*, 2012, **14**, 3284-3287; (j) J. Xia and R. Jasti, *Angew. Chem. Int. Ed.*, 2012, **51**, 2474-2476; (k) J. Xia, J. W. Bacon and R. Jasti, *Chem. Sci.*, 2012, **3**, 3018-3021; (l) E. R. Darzi, T. J. Sisto and R. Jasti, *J. Org. Chem.*, 2012, **77**, 6624-6628; (m) H. Isobe, S. Hitosugi, T. Yamasaki and R. Iizuka, *Chem. Sci.*, 2013, **4**, 1293-1297; (n) E. Kayahara, T. Iwamoto, T. Suzuki and S. Yamago, *Chem. Lett.* 2013, **42**, 621-623; (o) A.-F. Tran-Van, E. Huxol, J. M. Basler, M. Neuburger, J.-J. Adjizian, C. P. Ewels and H. A. Wegner, *Org. Lett.*, 2014, **16**, 1594-1597; (p) E. Kayahara, V. K. Patel and S. Yamago, *J. Am. Chem. Soc.*, 2014, **136**, 2284-2287; (q) P. J. Evans, E. R. Darzi and R. Jasti, *Nat. Chem.*, 2014, **6**, 404-408; (r) N. Kubota, Y. Segawa and K. Itami, *J. Am. Chem. Soc.*, 2015, **137**, 1356-1361; (s) H. Ueno, T. Nishihara, Y. Segawa and K. Itami, *Angew. Chem. Int. Ed.*, 2015, **54**, 3707-3711; (t) H. Ito, Y. Mitamura, Y. Segawa and K. Itami, *Angew. Chem. Int. Ed.*, 2015, **54**, 159-163; (u) V. K.

- Patel, E. Kayahara and S. Yamago, *Chem. Eur. J.* 2015, **21**, 5742-5749.
- 4 (a) Y.-T. Wu and J. S. Siegel, *Chem. Rev.*, 2006, **106**, 4843-4867; (b) V. M. Tsefrikas and L. T. Scott, *Chem. Rev.*, 2006, **106**, 4868-4884; (c) R. Jasti and C. R. Bertozzi, *Chem. Phys. Lett.*, 2010, **494**, 1-7; (d) H. Omachi, Y. Segawa and K. Itami, *Acc. Chem. Res.*, 2012, **45**, 1378-1389; (e) U. H. F. Bunz, S. Menning and N. Martin, *Angew. Chem. Int. Ed.*, 2012, **51**, 7094-7101; (f) S. Yamago, E. Kayahara and T. Iwamoto, *Chem. Rec.* 2014, **14**, 84-100; (g) T. Nishiuchi and M. Iyoda, *Chem. Rec.*, 2015, **15**, 329-346; (h) S. E. Lewis, *Chem. Soc. Rev.*, 2015, **44**, 2221-2304.
- 5 H. Omachi, T. Nakayama, E. Takahashi, Y. Segawa and K. Itami, *Nat Chem*, 2013, **5**, 572-576.
- 6 (a) X. Yu, J. Zhang, W. Choi, J.-Y. Choi, J. M. Kim, L. Gan and Z. Liu, *Nano Lett.*, 2010, **10**, 3343-3349; (b) J. R. Sanchez-Valencia, T. Dienel, O. Groning, I. Shorubalko, A. Mueller, M. Jansen, K. Amsharov, P. Ruffieux and R. Fasel, *Nature*, 2014, **512**, 61-64.
- 7 (a) E. H. Fort, P. M. Donovan and L. T. Scott, *J. Am. Chem. Soc.*, 2009, **131**, 16006-16007; (b) M. A. Petrukhnina and L. T. Scott, Fragments of Fullerenes and Carbon Nanotubes; John Wiley & Sons, Inc.: Hoboken, NJ, USA, 2011; (c) L. T. Scott, E. A. Jackson, Q. Zhang, B. D. Steinberg, M. Bancu and B. Li, *J. Am. Chem. Soc.*, 2012, **134**, 107-110.
- 8 (a) H. Omachi, Y. Segawa and K. Itami, *Org. Lett.*, 2011, **13**, 2480-2483; (b) T. J. Sisto, X. Tian and R. Jasti, *J. Org. Chem.*, 2012, **77**, 5857-5860; (c) J. Xia, M. R. Golder, M. E. Foster, B. M. Wong and R. Jasti, *J. Am. Chem. Soc.*, 2012, **134**, 19709-19715; (d) T. Iwamoto, E. Kayahara, N. Yasuda, T. Suzuki and S. Yamago, *Angew. Chem. Int. Ed.*, 2014, **53**, 6430-6434; (e) C. Huang, Y. Huang, N. G. Akhmedov, B. V. Popp, J. L. Petersen and K. K. Wang, *Org. Lett.*, 2014, **16**, 2672-2675; (f) A. Yagi, G. Venkataramana, Y. Segawa and K. Itami, *Chem. Commun.*, 2014, **50**, 957-959.
- 9 (a) Z. He, X. Xu, X. Zheng, T. Ming and Q. Miao, *Chem. Sci.*, 2013, **4**, 4525-4531; (b) S. Hitosugi, T. Yamasaki and H. Isobe, *J. Am. Chem. Soc.*, 2012, **134**, 12442-12445; (c) S. Hitosugi, W. Nakanishi, T. Yamasaki and H. Isobe, *Nat. Commun.*, 2011, **2**, 492; (d) T. Matsuno, S. Kamata, S. Hitosugi and H. Isobe, *Chem. Sci.*, 2013, **4**, 3179-3183; (e) K. Matsui, Y. Segawa and K. Itami, *J. Am. Chem. Soc.*, 2014, **136**, 16452-16458; (f) K. Matsui, Y. Segawa, T. Namikawa, K. Kamada and K. Itami, *Chemical Science*, 2013, **4**, 84-88; (g) E. Kayahara, T. Iwamoto, H. Takaya, T. Suzuki, M. Fujitsuka, T. Majima, N. Yasuda, N. Matsuyama, S. Seki and S. Yamago, *Nat. Commun.*, 2013, **4**, 2694.
- 10 A. Yagi, Y. Segawa and K. Itami, *J. Am. Chem. Soc.*, 2012, **134**, 2962-2965.
- 11 Y. Ishii, S. Matsuura, Y. Segawa and K. Itami, *Org. Lett.*, 2014, **16**, 2174-2176
- 12 (a) V. S. Iyer, K. Yoshimura, V. Enkelmann, R. Epsch, J. P. Rabe and K. Müllen, *Angew. Chem. Int. Ed.*, 1998, **37**, 2696-2699; (b) X. Yang, X. Dou, A. Rouhanipour, L. Zhi, H. J. Räder and K. Müllen, *J. Am. Chem. Soc.*, 2008, **130**, 4216-4217; (c) Y. Fogel, L. Zhi, A. Rouhanipour, D. Andrienko, H. J. Räder and K. Müllen, *Macromolecules*, 2009, **42**, 6878-6884; (d) L. Dossel, L. Gherghel, X. L. Feng and K. Müllen, *Angew. Chem. Int. Ed.*, 2011, **50**, 2540-2543; (e) M. G. Schwab, A. Narita, Y. Hernandez, T. Balandina, K. S. Mali, S. De Feyter, X. Feng and K. Müllen, *J. Am. Chem. Soc.*, 2012, **134**, 18169-18172; (f) T. H. Vo, M. Shekhirev, D. A. Kunkel, M. D. Morton, E. Berglund, L. Kong, P. M. Wilson, P. A. Dowben, A. Enders and A. Sinitskii, *Nat. Commun.*, 2014, **5**, 3189; (g) A. Konishi, Y. Hirao, K. Matsumoto, H. Kurata, R. Kishi, Y. Shigeta, M. Nakano, K. Tokunaga, K. Kamada and T. Kubo, *J. Am. Chem. Soc.*, 2013, **135**, 1430-1437; (h) A. Narita, X. Feng, Y. Hernandez, S. A. Jensen, M. Bonn, H. Yang, I. A. Verzhbitskiy, C. Casiraghi, M. R. Hansen, A. H. R. Koch, G. Fytas, O. Ivashenko, B. Li, K. S. Mali, T. Balandina, S. Mahesh, S. De Feyter and K. Müllen, *Nat. Chem.*, 2014, **6**, 126-132; (i) K. Ozaki, K. Kawasumi, M. Shibata, H. Ito and K. Itami, *Nat. Commun.*, 2015, **6**, 6251.
- 13 (a) V. S. Iyer, M. Wehmeier, J. D. Brand, M. A. Keegstra and K. Müllen, *Angew. Chem. Int. Ed.*, 1997, **36**, 1604-1607; (b) S. M. Draper, D. J. Gregg and R. Madathil, *J. Am. Chem. Soc.*, 2002, **124**, 3486-3487; (c) M. Kastler, J. Schmidt, W. Pisula, D. Sebastiani and K. Müllen, *J. Am. Chem. Soc.*, 2006, **128**, 9526-9534; (d) M. Takase, V. Enkelmann, D. Sebastiani, M. Baumgarten and K. Müllen, *Angew. Chem. Int. Ed.*, 2007, **46**, 5524-5527; (e) X. Feng, V. Marcon, W. Pisula, M. R. Hansen, J. Kirkpatrick, F. Grozema, D. Andrienko, K. Kremer and K. Müllen, *Nat Mater*, 2009, **8**, 421-426; (f) A. C. Whalley, K. N. Plunkett, A. A. Gorodetsky, C. L. Schenck, C.-Y. Chiu, M. L. Steigerwald and C. Nuckolls, *Chem. Sci.*, 2011, **2**, 132-135; (g) K. N. Plunkett, K. Godula, C. Nuckolls, N. Tremblay, A. C. Whalley and S. Xiao, *Org. Lett.*, 2009, **11**, 2225-2228; (h) C. Dou, S. Saito, K. Matsuo, I. Hisaki and S. Yamaguchi, *Angew. Chem. Int. Ed.*, 2012, **51**, 12206-12210; (i) Y. Tokudome, T. Fukushima, A. Goto and H. Kaji, *Org. Electron.*, 2011, **12**, 1600-1605; (j) M. Takase, T. Narita, W. Fujita, M. S. Asano, T. Nishinaga, H. Benten, K. Yoza and K. Müllen, *J. Am. Chem. Soc.*, 2013, **135**, 8031-8040; (k) K. Kawasumi, Q. Zhang, Y. Segawa, L. T. Scott and K. Itami, *Nat. Chem.*, 2013, **5**, 739-744; (l) H. Arslan, F. J. Uribe-Romo, B. J. Smith and W. R. Dichtel, *Chem. Sci.*, 2013, **4**, 3973-3978.
- 14 T. Nishiuchi, X. Feng, V. Enkelmann, M. Wagner and K. Müllen, *Chem. Eur. J.*, 2012, **18**, 16621-16625.
- 15 (a) F. E. Golling, M. Quernheim, M. Wagner, T. Nishiuchi and K. Müllen, *Angew. Chem. Int. Ed.*, 2014, **53**, 1525-1528; (b) M. Quernheim, F. E. Golling, W. Zhang, M. Wagner, H.-J. Räder, T. Nishiuchi and K. Müllen, *Angew. Chem. Int. Ed.*, 2015, **54**, 10341-10346.
- 16 (a) M. Müller, V. S. Iyer, C. Kübel, V. Enkelmann and K. Müllen, *Angew. Chem.*, 1997, **109**, 1679-1682; (b) M. Müller, C. Kübel, F. Morgenroth, V. S. Iyer and K. Müllen, *Carbon*, 1998, **36**, 827-831; (c) M. Müller, V. S. Iyer, C. Kübel, V. Enkelmann and K. Müllen, *Angew. Chem. Int. Ed.*, 1997, **36**, 1607-1610.
- 17 (a) A. A. O. Sarhan and C. Bolm, *Chem. Soc. Rev.*, 2009, **38**, 2730-2744; (b) M. Grzybowski, K. Skonieczny, H. Butenschön and D. T. Gryko, *Angew. Chem. Int. Ed.*, 2013, **52**, 9900-9930; (c) M. Grzybowski, K. Skonieczny, H. Butenschön and D. T. Gryko, *Angew. Chem.*, 2013, **125**, 10084-10115.
- 18 P. J. Stephens, F. J. Devlin, C. F. Chabalowski and M. J. Frisch, *J. Phys. Chem.*, 1994, **98**, 11623-11627.
- 19 V. A. Rassolov, M. A. Ratner, J. A. Pople, P. C. Redfern and L. A. Curtiss, *J. Comput. Chem.*, 2001, **22**, 976-984.
- 20 A. Sekiguchi, K. Ebata, C. Kabuto and H. Sakurai, *J. Am. Chem. Soc.* 1991, **113**, 1464-1465; (b) A. Falceto, D. Casanova, P. Alemany and S. Alvarez, *Chem. Eur. J.* 2014, **20**, 14674-14689.