


Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/chemicalscience



Journal Name

ARTICLE

Self-cleaning MOF: Realization of Extreme Water Repellence in Coordination Driven Self-Assembled Nanostructures

Syamantak Roy,^a Venkata M. Suresh,^a and Tapas Kumar Maji*^a

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Bio-inspired self-cleaning surfaces have found industrial applications in oil-water separation, stain resistant textiles, anti-biofouling paints in ships etc. Interestingly, self-cleaning metal-organic framework (MOF) materials having high water contact angles and corrosion resistance have not been realized so far. To address this issue, we have used the fundamentals of self-assembly to expose hydrophobic alkyl chains on MOF surface. This decreases the surface free energy and hence increases hydrophobicity. Coordination directed self-assembly of dialkoxyoctadecyl-*oligo*-(*p*-phenyleneethynylene)dicarboxylate (**OPE-C₁₈**) with Zn^{II} in DMF/H₂O mixture leads to a three dimensional supramolecular porous framework {Zn(OPE-C₁₈)₂·2H₂O} (**NMOF-1**) with nanobelt morphology. Inherently superhydrophobic and self-cleaning **NMOF-1** has high thermal and chemical stability. The periodic arrangement of 1D Zn-OPE-C₁₈ chains with octadecyl alkyl chains projecting outward reduces the surface free energy leading to superhydrophobicity in **NMOF-1** (contact angle; 160-162°). The hierarchical surface structure thus generated, enables **NMOF-1** to mimic the lotus leaf in its self-cleaning property with an unprecedented tilt angle of 2°. Additionally, superhydrophobicity remains intact over a wide pH range (1-9) and under high ionic concentrations. We believe that such a development in this field will herald a new class of materials capable of water repellent applications.

Introduction

The progress in scientific research has witnessed the efforts of scientists to mimic the intricate and precise design of nature for fabricating novel functional materials.¹⁻⁶ In this context, the "Lotus Effect" has incurred immense interest for designing biomimetic self-cleaning materials.⁷⁻¹⁰ It involves easy rolling of water droplets over the lotus leaf. The leaf surface shows characteristic micro and nanoscale roughness with a "re-entrant texture" which is determined to be a prerequisite for such water repellence.¹¹⁻¹⁵ This multiscale or hierarchical roughness reduces the surface free energy, increases the static contact angle (CA) (>150°) and reduces the tilt angle (<10°) leading to superhydrophobic surfaces with self-cleaning properties.¹⁶⁻¹⁸ Therefore, the shape, size, rigidity and ordering with combined surface micro and nanostructure are the guiding principles for the design of artificial self-cleaning materials.¹⁹⁻²² Towards this, carbon nanotubes (CNTs),^{23,24} lithographic patterning,²⁵⁻²⁸ aligned polymer nanofibers,²⁹⁻³¹ self-assembled monolayer (SAM) modified surfaces^{32,33} have been successfully designed as superhydrophobic surfaces with very high CAs. In this context, superhydrophobic metal-organic


frameworks (MOFs)³⁴⁻⁴⁶ would provide the advantage of both inherent porosity and surface water repellence. This could lead to applications of this material in oil-water separation membranes, waste water treatments and fuel purification technology.⁴⁷⁻⁵⁰

Recently, MOFs have been studied for superhydrophobic applications either via post-synthetic modification (PSM) by fluoroalkyl chains or by generating external surface corrugation.⁵¹⁻⁵⁸ Kitagawa et al. proposed a novel method of synthesizing superhydrophobic MOF materials by generating external surface corrugation derived from aromatic surface groups.⁵² However, it lacked the basic requirements for practical applicability i.e. solution processability and self-cleaning property. In this context, coordination driven self-assembly of rigid π -conjugated organic linker, containing long hydrophobic alkyl chains⁵⁹⁻⁶⁰ would provide solution processable nanoMOF (NMOF)⁶¹⁻⁶⁵ structures. Here, the surface free energy will be dictated by the alkyl chains decorating the NMOF surface and create low adhesion of water droplet to it. We therefore conjectured that coordination driven self-assembly of *oligo*-(*p*-phenyleneethynylene) dicarboxylate with alkoxyoctadecyl (C₁₈) chains (**OPE-C₁₈**)^{66,67} would generate a supramolecular NMOF structure which would be promising for superhydrophobic self-cleaning applications.

In this article, we report the rational design and synthesis of a self-cleaning nanoscale supramolecular 3D porous framework {Zn(OPE-C₁₈)₂·2H₂O} (**NMOF-1**) with inherent

^a Molecular Materials Laboratory, Chemistry and Physics of Materials Unit, Jawaharlal Nehru Centre for Advanced Scientific Research, Jakkur, Bangalore-560064, India

Electronic Supplementary Information (ESI) available: [experimental details and characterizations]. See DOI: 10.1039/x0xx00000x

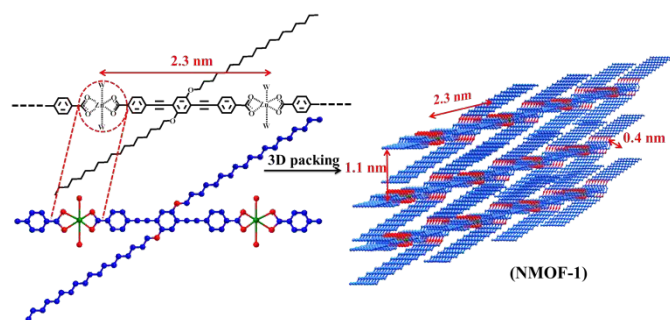

Scheme 1. Bottom-up approach for the fabrication of a self-cleaning MOF nanostructure by coordination driven self-assembly between Zn^{II} and **OPE-C₁₈**

superhydrophobicity based on the self-assembly of **OPE-C₁₈** and Zn^{II} (Scheme 1). The micro-spaces between **NMOF-1** micro-particles are capable of creating solid-air-water composite interface to develop high moisture resistance. The nanoscale roughness is created by the presence of periodic alkyl chains to generate a hierarchical structure with pH tolerability. Our design is an easy and straightforward bottom-up approach for the construction of superhydrophobic MOF nanostructures with remarkably low sliding angles and excellent self-cleaning properties extendable to large areas. To the best of our knowledge, fabrication of self-cleaning MOFs and an in-depth analysis of their characteristic surface structure are yet to be reported.

Results and Discussion

NMOF-1 has been synthesized by stirring **H₂OPE-C₁₈** and $\text{Zn}(\text{OAc})_2 \cdot 2\text{H}_2\text{O}$ in DMF/ H_2O mixed solvent system in the presence of triethylamine at room temperature.⁶⁸ Coordination of Zn^{II} to **OPE-C₁₈** is evidenced by the spontaneous formation of colloidal turbidity on addition of the aqueous $\text{Zn}(\text{OAc})_2$ solution. The reaction mixture is stirred for 2 hours at room temperature and centrifuged. EDAX analysis of the resulting colloid showed the presence of Zn^{II} (Fig. S1) and CHN analysis suggests a molecular formula of $\{\text{Zn}(\text{OPE-C}_{18})_2 \cdot 2\text{H}_2\text{O}\}$ (**NMOF-1**), thereby proposing 1:1 coordination of Zn^{II} ion with **OPE-C₁₈**. FT-IR spectrum of **NMOF-1** shows strong peaks at 1595 cm^{-1} and 1413 cm^{-1} , corresponding to asymmetric and symmetric stretching vibrations of carboxylate groups and the difference (Δ value) is found to be 182 cm^{-1} (Fig. S2). This suggests a bidentate coordination mode of Zn^{II} metal ion to **OPE-C₁₈** (Scheme 1). The presence of a broad peak at 3460 cm^{-1} confirms the presence of Zn^{II} bound coordinated water molecules. These results suggest a hexacoordination environment around Zn^{II} ion with four oxygens from two carboxylate groups of **OPE-C₁₈** and two coordinated water molecules. Thermogravimetry analysis further indicates its stability up to 340°C (Fig. S3). N_2 adsorption isotherm at 77 K of **NMOF-1** shows type II uptake profile (Fig. S4). However, CO_2 adsorption isotherm at 195 K showed a gradual uptake of CO_2 with increasing pressure (Fig. 1a). The final amount is observed to be 35 cc/g at $p = 1\text{ atm}$ which corresponds to 1 molecule of CO_2 per formula unit of **NMOF-1**. The permanent porosity indicates the presence of a porous 3D structural organization in **NMOF-1** (Scheme 1). Powder X-ray diffraction (PXRD) suggests high crystallinity of **NMOF-1** (Fig. 1b). Indexing of PXRD provided insights into its

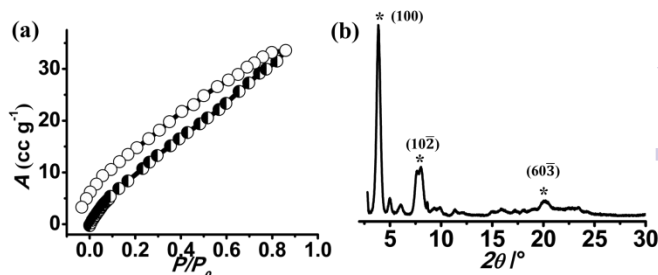


Fig 1. (a) CO_2 (at 195 K) adsorption isotherm of de-solvated **NMOF-1**. (b) PXRD pattern of **NMOF-1**.

packing. Modelling through the Crysfire software⁶⁸ suggests monoclinic crystal system of **NMOF-1** with a cell volume of 2197 \AA^3 and cell parameters of $a = 29.40(5)\text{ \AA}$, $b = 4.146(7)\text{ \AA}$ and $c = 22.81(5)\text{ \AA}$. A close equivalence of experimental and indexing results indicates the accuracy of calculation (Table S1). The (100) peak at 3.9° ($d = 23\text{ \AA}$) corresponds to the repeating distance of Zn^{II} centres connected by **OPE-C₁₈**, suggesting the formation of 1D coordination chain. Therefore the coordination of the terminal carboxylate groups of **OPE-C₁₈** to Zn^{II} extends **NMOF-1** in 1D (Scheme 1). Diffraction peak (603) at 20.2° ($d = 4.4\text{ \AA}$) indicates weak π - π interactions between **OPE-C₁₈** unit of 1D chains that resulted in 2D layers. Such stacking of the 2D layers is reinforced by the orientation of adjacent alkyl chains indicated by the (102) peak at 8° ($d = 11\text{ \AA}$). The long alkyl chains interact via van der Waals forces to extend the packing into a 3D supramolecular framework. This generates a supramolecular porous structure extended via lamellar packing between adjacent **OPE-C₁₈** units of two successive **NMOF-1** layers (Scheme 1). Interestingly, **NMOF-1** retained its structural integrity even at higher temperatures as evident from temperature dependant PXRD measurements (Fig. S5). Measurements were carried out at three different temperatures; PXRD analysis at 100°C , 200°C and 300°C showed that the characteristic peaks of **NMOF-1** are retained at all temperatures. This result clearly reveals exceptional thermal stability of **NMOF-1**.

Morphology transformation

The nanomorphology of **NMOF-1** is investigated using field emission scanning electron microscopy (FESEM), transmission electron microscopy (TEM) and atomic force microscopy (AFM). FESEM, TEM and AFM revealed the presence of belt-like nanostructures of **NMOF-1** (Fig. 2a, b, j, k, S6). The nanobelts offered a length of 700 nm - 1000 nm and a width of 200 nm - 300 nm . The height profile analysed from AFM was found to be about 80 nm and as shown in Scheme S2, the length of **NMOF-1** nanobelts is composed of the 1D chains of ZnOPE-C_{18} . The width of the belts is formed by the weak π - π interactions between the 1D chains forming the 2D layer of the nanobelts. Finally the height of the nanobelts is formed by the 3D packing of **NMOF-1** via the interaction of the alkyl chains. Interestingly, when the reaction time was increased to 6 hours, nanoscrolls of **NMOF-1** were observed. FESEM and TEM measurements further confirmed the formation of the nanoscrolls from the nanobelts (Fig. 2e-i, S7). Intermediate reaction times offered semi-scrolled nanostructures having a

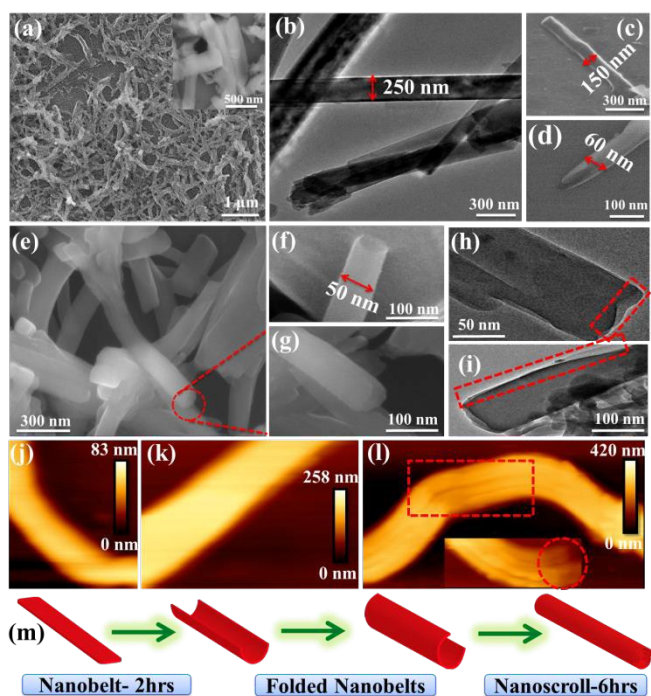


Fig. 2 (a) FESEM image (Inset: nanobelts at higher magnification) and (b) TEM image of **NMOF-1** nanobelts. (c, d) FESEM images of semi-scrolled nanobelts. (e, f, g) FESEM and (h, i) TEM images of nanoscrolls at different magnifications showing the changes in cross section upon scrolling. AFM image of (j, k) nanobelt and (l) nanoscroll (Inset: single nanoscroll showing opening at the mouth). (m) Schematic showing the possible morphological transformation of nanobelts to nanoscrolls in **NMOF-1**.

reduced width (Fig. 2c, d, S8). Upon complete transformation the nanoscrolls showed a length of 400–800 nm and a width of 40–100 nm. AFM height profile of nanoscrolls showed a value of about 270 nm (Fig. S9). The increase in height for nanoscrolls is attributed to the scrolling effect. These results suggest the scrolling of belt occurs in a longitudinal direction leaving long alkyl chains at the surface of the nanobelts and nanoscrolls. As the reaction progresses, the belts start to scroll up to minimize the repulsive forces between the alkyl chains of **OPE-C₁₈** and solvents in the reaction medium (Fig. 2m, Scheme S2). To study the effect of dynamicity of the alkyl chains on the surface, nanoscrolls of **NMOF-1** were allowed to stand in acetonitrile, a less polar solvent than water. After 4 days of standing in solution, partially unscrolled structures of **NMOF-1** taking the shape of nano-containers were observed on FESEM analysis (Fig. S10). A decrease in the hydrophobic interactions between the alkyl chains in a less polar solvent allows the scrolls to relax and open up along the long-alkyl chain direction therefore resulting in a new morphology of **NMOF-1**.

Superhydrophobicity and surface analysis

The presence of alkyl chains and its dynamicity along the surface and pores of the nanostructures further motivated us to study the hydrophobic properties of **NMOF-1**. To investigate the polarity of the self-assembly and supramolecular organization, we carried out water and benzene adsorption experiments at room temperature. The water adsorption isotherms of **NMOF-1** showed negligible uptake at the low

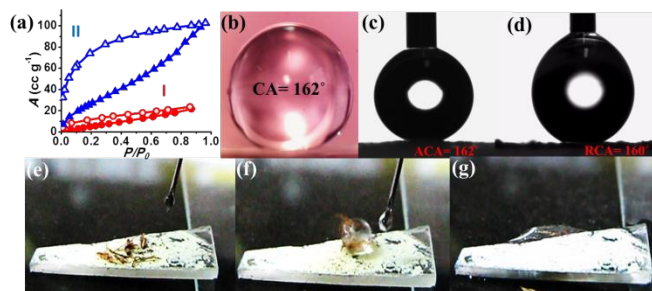


Fig. 3 (a) Solvent vapor adsorption isotherms of **NMOF-1** at 298K: I: Water (red) and II: benzene (blue), P_0 is the saturated vapour pressure; 3.17 kPa (Water) and 12.60 kPa (Benzene) at 298K. Water contact angles of **NMOF-1** coated substrate: (b) Static contact angle, (c) advancing contact angle and (d) receding contact angle. (e-g) Video snapshots of self-cleaning experiment showing the removal of dirt from surface

pressure region with a gradual uptake at higher pressures, finally reaching to 20 mL at $P/P_0 = 1.0$. This suggests hydrophobic nature of the framework (Fig. 3a). The hydrophobicity of the pore surface was further validated by the benzene adsorption isotherms showing an uptake of 102 cc/g (Fig. 3a) which corresponds to ~ 1 benzene molecule per formula unit of **NMOF-1**. Therefore, its pore can be utilized for polar/non-polar solvent separations.

For surface characterizations, the free organic linker (**H₂OPE-C₁₈**) was initially investigated for superhydrophobicity. The contact angle was determined to be 140–147° proving the hydrophobicity of **H₂OPE-C₁₈** (Fig. S11). However, superhydrophobicity was not realized. Hydrophobicity of the **NMOF-1** surface was then investigated by coating its ethanolic dispersion on a glass substrate. The nanoscale structure of **NMOF-1** makes it highly solution processable and easy to coat on glass. Water contact angles were measured on **NMOF-1** coated glass substrates and were determined to be 160–162° in a circle fitting mode (Fig. 3b). These high contact angle values are the highest reported for MOFs without any post-synthetic modifications of the pore as well as the external surface (Table 1). Therefore, to gain insight into this superhydrophobic property of **NMOF-1**, FESEM and AFM analysis was performed. FESEM of coated **NMOF-1** shows uniform distribution of spherical particles with size in the range 10–30 μm (Fig. S12). The occurrence of such particles generates the micro-roughness with trapped air pockets in between them. This distribution is ideal for hydrophobic applications. To investigate further, non-contact mode AFM imaging of **NMOF-1** was performed. 2D AFM images authenticated the presence of spherical particles of **NMOF-1** (Fig. 4a). The particles show needle like protrusions in the nanoscale regime. The 3D AFM image shows the height of the spheres in the range of 300–500 nm (Fig. 4b). 3D AFM image of a single sphere validates the presence of spikes 50–100 nm wide with an inter-spacing of 10–50 nm having height of 200–300 nm (Fig. 4c, d). These descriptions confirm the presence of hierarchical surface roughness. Such periodic existence of large and small particles generates areas containing peaks and troughs throughout the surface (Fig. 4b, d). This is commonly known as the “hills and valley” type surface terrain with trapped air pockets in between. The hills and valley are

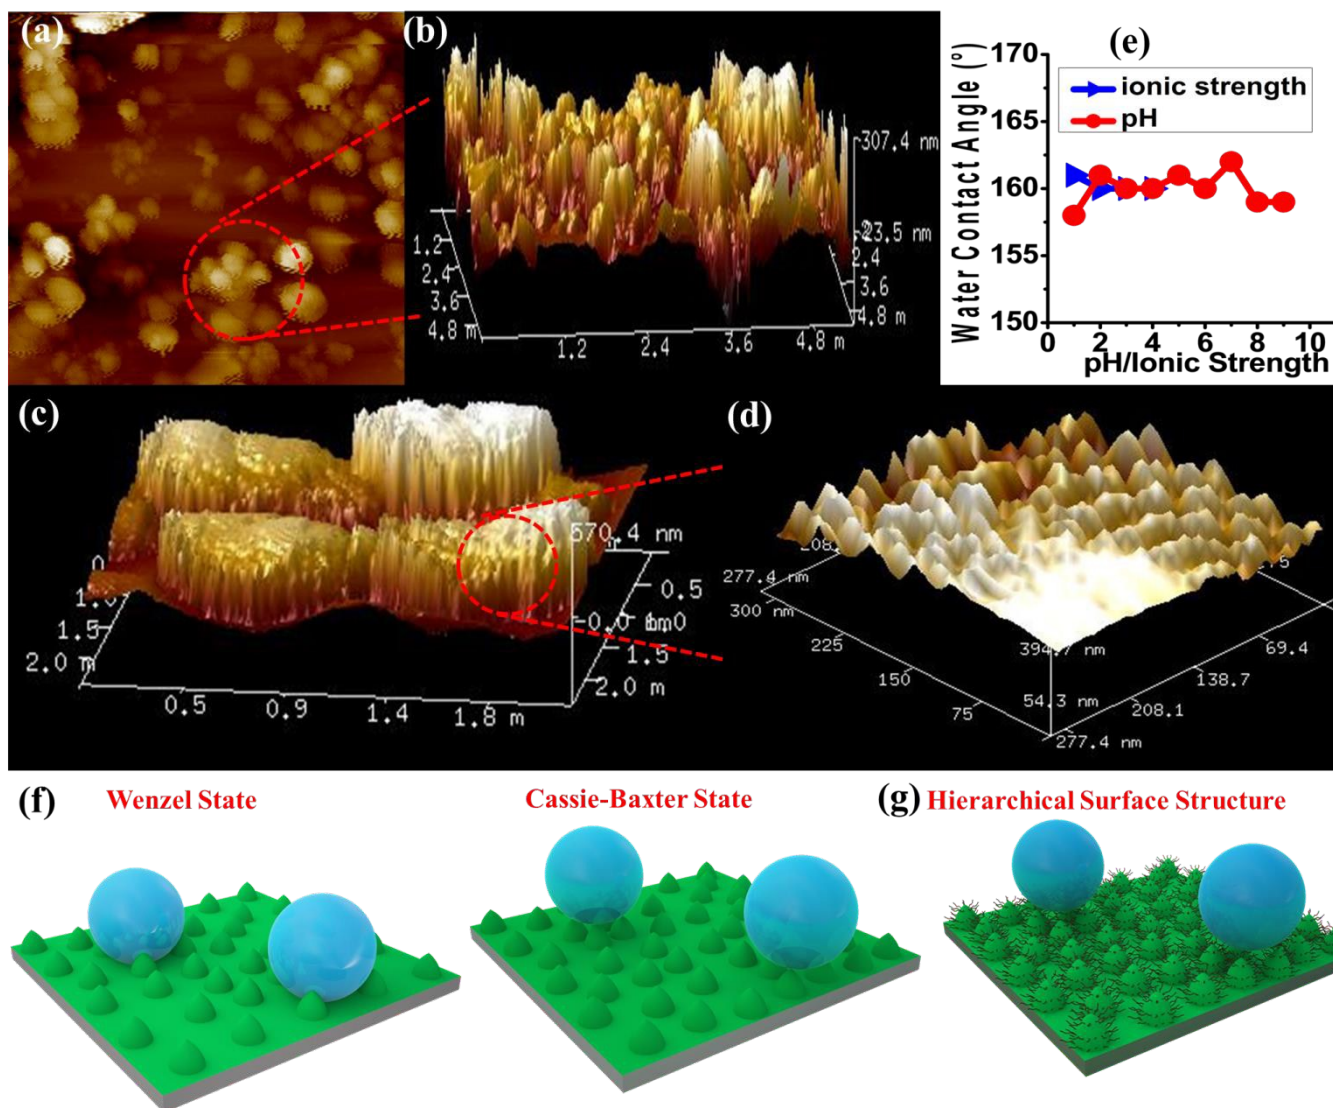


Fig. 4 (a) 2D-AFM image of **NMOF-1** micro-particles on coated glass surface and (b) corresponding 3D-AFM. (c) 3D-AFM image of four adjacent microspheres of **NMOF-1** and (d) corresponding high magnified image showing continuous nano-roughness present on each micro-particle. (e) Plots showing changes in CA with pH/ionic strength. (f) Schematic showing the different states used to explain surface water repellence: left: Wenzel state or the wetting state, right: Cassie-Baxter state or the superhydrophobic state (A transition from the Wenzel to the Cassie-Baxter model occurs when we consider that rough textures on a surface trap air-pockets in between) and (g) Incorporation of hierarchical surface for the generation of the self-cleaning effect in **NMOF-1**.

observed even in the nanoscale regime. The Cassie-Baxter model^{69,70} (Fig. 4f) predicts that such surface roughness will lead to a superhydrophobic structure. The uniformity in micro/sub-microscale roughness of **NMOF-1** therefore provides an ideal surface for super-hydrophobic and self-cleaning applications.

Self-cleaning property

The advancing and receding contact angles of **NMOF-1** were measured to be 162° and 160° respectively, leading to a very small contact angle hysteresis of 2° (Fig. 3c, d). This further prompted us to investigate its self-cleaning property (Fig. S13). It was examined by placing dust particles on the **NMOF-1** coated glass surface. The water droplets indeed rolled off the surface carrying the dust particles along with it (Fig. 3e-g). The whole experiment was video recorded. (Video S1, S2).

However, for any practical applications of **NMOF-1**, it must be stable under a variety of extreme conditions such as high acidic and basic conditions and also solutions of high ionic strength. An experiment was designed where aqueous solutions of different pH were used to measure contact angles. Interestingly, the glass surface with **NMOF-1** coating showed amazing stability with high contact angles in the entire acidic pH range (1-6) and also under mildly basic conditions (up to pH=9). The contact angle varied from its original value only slightly in the entire range (pH=1 to 9). Also under high ionic strength solutions, contact angles showed only a minimal change (I=1-4) (Fig 4e, S14).

The supramolecular packing of **NMOF-1** leaves the alkyl chains of **OPE-C₁₈** both between the 2D layers as well as on the external surface (Scheme S2). On coating the glass surface spherical organizations of **NMOF-1** nanobelts were observed which creates air pockets in between two successive particles.

This prevents the wetting of the surface. Also the periodic alignment of alkyl chains on the surface creates nano-spaced roughness generating a hierarchical surface structure which assists easy rolling of water droplets on it (Figure 4g, Video S1, S2). Likewise, the presence of long alkyl chains on the surface of **NMOF-1** shields the framework from decomposing under such extreme conditions rendering it as a highly stable self-cleaning material. The PXRD peaks showed good correspondence before and after the self-cleaning experiment (Fig. S15) indicating the robustness of **NMOF-1** in such applications. The results were compared to other reported MOFs and have been tabulated in Table 1.

Table 1. Reported superhydrophobic MOFs in the literature highlighting the comparison of contact angles, stability in the pH range and self-cleaning properties with the current work

MOF	CA(°)	PSM	Self-cleaning	pH stability range	Reference
MOFF-2	151±1	No	-	-	53
MOFF-3	135±2	No	-	-	53
MIL-53(Al)-AM4	>150	Yes	-	-	51
MIL-53(Al)-AM6	>150	Yes	-	-	51
NH ₂ -MIL-53(Al)	151-169	Yes	-	-	55
PESD-1	>150	No	-	-	52
NMOF-1	160-162	No	Yes	1-9	Current Work

Conclusions

In conclusion, a novel ligand design strategy has been exploited for the fabrication of an inherently superhydrophobic and self-cleaning nanoscale metal-organic framework **NMOF-1**. The control of reaction parameters has generated nanobelts and nanoscroll morphologies. The micro/nanoscale surface roughness generated was also cultivated for superhydrophobic and self-cleaning application of **NMOF-1** which is unique in MOF chemistry. Its exceptional stability under extreme acidic, basic and ionic conditions renders its applicability as a pH stable self-cleaning and luminescent material. The shape-shifting porous hybrids can also be utilized for a host of dimension dependent applications like optical waveguiding, charge transport etc. Exploitation of supramolecular organization and nanomorphology of MOFs for large area coating and its in-depth surface analysis is done for the first time in this work. This could potentially open up new avenues in the design of superhydrophobic self-cleaning MOF materials without tedious post-synthetic modifications and usher in a new class of materials meeting industrial needs.

Acknowledgements

The authors thank Prof. C. N. R. Rao and Prof K. S. Narayan for AFM Lab facilities, Prof Satish Kailas for tribology lab facilities.

The authors acknowledge Selvi (FESEM), Usha (TEM), Mahesh and Swati (AFM) for microscopic measurements and Shubha for contact angle measurements. S.R thanks UGC (Govt. Of India) and V.M.S thanks CSIR (Govt. of India) for fellowship.

- W. J. P. Barnes, *Science*, 2007, **318**, 203.
- W.-J. Chung, J.-W. Oh, K. Kwak, B. Y. Lee, J. Meyer, E. Wang, A. Hexemer and S.-W. Lee, *Nature*, 2011, **478**, 364.
- P. H. J. Kouwer, M. Koepf, A. A. Le Sage, M. V. Jaspers, A. M. van Buul, Z. H. Eksteen-Akeroyd, T. Woltinge, E. Schwartz, H. J. Kitto, R. Hoogenboom, S. J. Picken, R. J. M. Nolte, E. Mendes and A. E. Rowan, *Nature*, 2013, **493**, 651.
- K. Schacht, T. Jüngst, M. Schweinlin, A. Ewald, J. Groll and T. Scheibel, *Angew. Chem., Int. Ed.*, 2015, **54**, 2816.
- L. Wen, Y. Tian and L. Jiang, *Angew. Chem., Int. Ed.*, 2015, **54**, 3387.
- P. K. Vemula and G. John, *Acc Chem Res.*, 2008, **41**, 769.
- R. Blossley, *Nat. Mater.*, 2003, **2**, 301.
- S. Srinivasan, V. K. Praveen, R. Philip and A. Ajayaghosh, *Angew. Chem., Int. Ed.*, 2008, **47**, 5750.
- K. M. Wisdom, J. A. Watson, X. Qu, F. Liu, G. S. Watson and C.-H. Chen, *Proc. Natl. Acad. Sci. U. S. A.*, 2013, **110**, 7992.
- J. Zhang, A. Wang and S. Seeger, *Adv. Funct. Mater.*, 2014, **24**, 1074.
- X.-M. Li, D. Reinhoudt and M. Crego-Calama, *Chem. Soc. Rev.*, 2007, **36**, 1350.
- K. Liu, X. Yao and L. Jiang, *Chem. Soc. Rev.*, 2010, **39**, 3240.
- P. Roach, N. J. Shirtcliffe and M. I. Newton, *Soft Matter*, 2008, **4**, 224.
- T. Sun, L. Feng, X. Gao and L. Jiang, *Acc. Chem. Res.*, 2005, **38**, 644.
- B. Xin and J. Hao, *Chem. Soc. Rev.*, 2010, **39**, 769.
- C. Neinhuis and W. Barthlott, *Ann Botany*, 1997, **79**, 667.
- R. Makiura, S. Motoyama, Y. Umemura, H. Yamanaka, O. Sakata and H. Kitagawa, *Nat. Mater.*, 2010, **9**, 565.
- A. Tuteja, W. Choi, G. H. McKinley, R. E. Cohen and M. F. Rubner, *MRS Bulletin*, 2008, **33**, 752.
- A. Tuteja, W. Choi, M. Ma, J. M. Mabry, S. A. Mazzella, G. C. Rutledge, G. H. McKinley and R. E. Cohen, *Science*, 2007, **318**, 1618.
- B. P. Dyett, A. H. Wu and R. N. Lamb, *ACS Appl. Mater. Interfaces.*, 2014, **6**, 18380.
- T. L. Liu and C.-J. C. Kim, *Science*, 2014, **346**, 1096.
- T. Verho, C. Bower, P. Andrew, S. Franssila, O. Ikkala and R. H. A. Ras, *Adv. Mater.*, 2011, **23**, 673.
- X. Dong, J. Chen, Y. Ma, J. Wang, M. B. Chan-Park, X. Liu, L. Wang, W. Huang and P. Chen, *Chem. Commun.*, 2012, **48**, 10660.
- Y. C. Jung and B. Bhushan, *ACS Nano*, 2009, **3**, 4155.
- J. Feng, M. T. Tuominen and J. P. Rothstein, *Adv. Funct. Mater.*, 2011, **21**, 3715.
- Y. Lai, C. Lin, H. Wang, J. Huang, H. Zhuang and L. Sun, *Electrochem. Commun.*, 2008, **10**, 387.
- S. P. R. Kobaku, A. K. Kota, D. H. Lee, J. M. Mabry and A. Tuteja, *Angew. Chem., Int. Ed.*, 2012, **51**, 10109.
- F. L. Geyer, E. Ueda, U. Liebel, N. Grau and P. A. Levkin, *Angew. Chem., Int. Ed.*, 2011, **50**, 8424.
- N.-R. Chiou, C. Lu, J. Guan, L. J. A. Lee and J. Epstein, *Nat. Nanotech.*, 2007, **2**, 354.
- L. Feng, S. Li, H. Li, J. Zhai, Y. Song, L. Jiang and D. Zhu, *Angew. Chem., Int. Ed.*, 2012, **41**, 1221.
- D. Zahner, J. Abagat, F. Svec, J. M. J. Fréchet and P. A. Levkin, *Adv. Mater.*, 2011, **23**, 3030.
- N. Belman, K. Jin, Y. Golan, J. N. Israelachvili and N. S. Pesika, *Langmuir*, 2012, **28**, 14609.
- J. Genzer and K. Efimenko, *Science*, 2000, **290**, 2130.

- 34 S. Kitagawa, R. Kitaura and S.-i. Noro, *Angew. Chem., Int. Ed.*, 2004, **43**, 2334.
- 35 T. K. Maji, R. Matsuda and S. Kitagawa, *Nat. Mater.*, 2007, **6**, 142.
- 36 H. Li, M. Eddaoudi, M. O'Keeffe and O. M. Yaghi, *Nature*, 1999, **402**, 276.
- 37 Z. R. Herm, B. M. Wiers, J. A. Mason, J. M. van Baten, M. R. Hudson, P. Zajdel, C. M. Brown, N. Masciocchi, R. Krishna and J. R. Long, *Science*, 2013, **340**, 960.
- 38 S. M. Cohen, *Chem. Sci.*, 2010, **1**, 32.
- 39 S. Roy, A. Chakraborty and T. K. Maji, *Coord. Chem. Rev.*, 2014, **273-274**, 139.
- 40 R. Haldar, R. Matsuda, S. Kitagawa, S. J. George and T. K. Maji, *Angew. Chem., Int. Ed.*, 2014, **53**, 11772.
- 41 Z. Zhang, H. T. H. Nguyen, S. A. Miller and S. M. Cohen, *Angew. Chem., Int. Ed.*, 2015, **54**, 6152.
- 42 R. A. Fischer, *Angew. Chem., Int. Ed.*, 2014, **53**, 5716.
- 43 J. Heine and K. Müller-Buschbaum, *Chem. Soc. Rev.*, 2013, **42**, 9232.
- 44 Y. K. Seo, J. W. Yoon, J. S. Lee, Y. K. Hwang, C. H. Jun, J. S. Chang, S. Wuttke, P. Bazin, A. Vimont, M. Daturi, S. Bourrelly, P. L. Llewellyn, P. Horcajada, C. Serre and G. Férey, *Adv. Mater.*, 2012, **24**, 806.
- 45 Y. He, B. Li, M. O'Keeffe and B. Chen, *Chem. Soc. Rev.* 2014, **43**, 5618.
- 46 G. K.H. Shimizu, J. M. Taylor and S. Kim, *Science*, 2013, **341**, 354.
- 47 A. K. Kota, G. Kwon, W. Choi, J.M Mabry and A. Tuteja, *Nat. Commun.*, 2012, **3**, 1025.
- 48 K. He, H. Duan, G. Y. Chen, X. Liu, W. Yang and D. Wang, *ACS Nano.*, 2015, **9**, 9188.
- 49 L. Ren, Y. Ahn and B. E. Logan, *Environ. Sci. Technol.*, 2014, **48**, 4199.
- 50 I. M. Atadashi, M. K. Aroua and A. A. Aziz, *Renew Energy.*, 2011, **36**, 437.
- 51 J. G. Nguyen and S. M. Cohen, *J. Am. Chem. Soc.*, 2010, **132**, 4560.
- 52 K. P. Rao, M. Higuchi, K. Sumida, S. Furukawa, J. Duan and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2014, **53**, 8225.
- 53 T.-H. Chen, I. Popov, O. Zenasni, O. Daugulis and O. S. Miljanic, *Chem. Commun.*, 2013, **49**, 6846.
- 54 C. Serre, *Angew. Chem., Int. Ed.*, 2012, **51**, 6048.
- 55 T. T. Y. Tan, M. R. Reithofer, E. Y. Chen, A. G. Menon, T. S. A. Hor, J. Xu and J. M. Chin, *J. Am. Chem. Soc.*, 2013, **135**, 16272.
- 56 B. Liu, M. Ma, D. Zacher, A. Bétard, K. Yussenko, N. M- Nolte, C. Wöll and R. A. Fischer, *J. Am. Chem. Soc.*, 2011, **133**, 1734.
- 57 C. Yang, U. Kaipa, Q. Z. Mather, X. Wang, V. Nesterov, A. F. Venero and M. A. Omary, *J. Am. Chem. Soc.*, 2011, **133**, 18094.
- 58 A. Bétard, S. Wannapaiboon and R. A. Fischer, *Chem. Commun.*, 2012, **48**, 10493.
- 59 V. M. Suresh, S. Chatterjee, R. Modak, V. Tiwari, A. B. Patel, T. K. Kundu and T. K. Maji, *J. Phys. Chem. C*, 2014, **118**, 12241.
- 60 V. M. Suresh, S. J. George and T. K. Maji, *Adv. Funct. Mater.*, 2013, **23**, 5585.
- 61 L. He, Y. Liu, J. Liu, Y. Xiong, J. Zheng, Y. Liu and Z. Tang, *Angew. Chem., Int. Ed.*, 2013, **52**, 3741.
- 62 Y. Liu and Z. Tang, *Adv. Mater.*, 2013, **25**, 5819.
- 63 X. Liu, L. He, J. Zheng, J. Guo, F. Bi, X. Ma, K. Zhao, Y. Liu, R. Song and Z. Tang, *Adv. Mater.*, 2015, **27**, 3273.
- 64 Y. Li, J. Tang, L. He, Y. Liu, Y. Liu, C. Chen and Z. Tang, *Adv. Mater.*, 2015, **27**, 4075.
- 65 M. Zhao, K. Deng, L. He, Y. Liu, G. Li, H. Zhao and Z. Tang, *J. Am. Chem. Soc.*, 2014, **136**, 1738.
- 66 T. A. Makal, X. Wang and H.-C. Zhou, *Cryst. Growth. Des.*, 2013, **13**, 4760.
- 67 U. H. F. Bunz, *Chem. Rev.*, 2000, **100**, 1605.
- 68 See Supporting Information.
- 69 A. B. D. Cassie and S. Baxter, *Trans. Faraday Soc.*, 1944, **40**, 546.
- 70 R. N. Wenzel, *Ind. Eng. Chem.*, 1936, **28**, 988.