

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Chemical Science

EDGE ARTICLE

A bioscaffolding strategy for hierarchical zeolites with a nanotube-trimodal network

Guannan Li,^a Haibo Huang,^a Bowen Yu,^b Yun Wang,^a Jiawei Tao,^a Yingxu Wei,^b Shougui Li,^a Zhongmin Liu,^{*b} Yan Xu^{*a} and Ruren Xu^a

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Hierarchical zeolite monoliths with multimodal porosity is of paramount importance as it opens up new horizons for advanced applications. So far, hierarchical zeolites based on nanotube scaffolds have never been reported. Inspired by the organization of biominerals, we have developed a novel precursor scaffolding-solid phase crystallization strategy for hierarchical zeolites with a unique nanotube scaffolding architecture and nanotube-trimodal network, where biomolecular self-assembly (BSA) provides scaffolding blueprint. By vapor-treating Sil-1 seeded precursor scaffolds, zeolite **MFI** nanotube scaffolds are self-generated, during which evolution phenomena such as segmented voids and solid bridges are observed, manifesting likely the Kirdendall effect in a solid-phase crystallization system. The nanotube walls are made of intergrown single crystals rendering good mechanical stability. The inner diameter of the nanotube is tunable between 30–90 nm by varying the thickness of precursor layers. Macropores enclosed by cross-linked nanotubes can be modulated by the choice of BSA. Narrow mesopores are formed by intergrown nanocrystals. Hierarchical ZSM-5 monoliths with nanotube (90 nm), micropore (0.55 nm), mesopore (2 nm) and macropore (700 nm) exhibit superior catalytic performance in the methanol-to-hydrocarbon (MTH) conversion compared to conventional ZSM-5. BSA remains intact after crystallization, allowing higher level of organization and functionalization of zeolite nanotube scaffolds. The current work may afford a versatile strategy for hierarchical zeolite monoliths with nanotube scaffolding architectures and a nanotube-multimodal network leading to self-supporting and active zeolite catalysts, and for applications beyond.

Introduction

Zeolites are microporous aluminosilicates of paramount importance in refineries and petrochemical industry as size- and shape-selective catalysts due to their ordered micropores, acid strength and thermal/hydrothermal stability. But the sole presence of micropores with window opening smaller than 1 nm often causes restricted access and diffusion limitations that adversely affects their catalytic activity.¹ Among others, hierarchical zeolites that integrate the catalytic activity of zeolitic micropores with the transport advantage and the external reactivity of an auxiliary network of interconnected multimodal porosity prove to be effective in both established and emerging applications.² Hierarchical zeolites refer to zeolitic materials having at least two levels of porous hierarchy. Mesoporosity can be integrated by either templating approach

or by leaching of framework atoms.³ Macroporosity is commonly generated by replication of macroporous scaffolds, by evaporation of volatile products, and by aggregation of large zeolite crystals.⁴ These macropores are large and broad with pore openings in micrometer scale, making them less useful for intended applications. Zeolite **MFI** crystals with intracrystalline macropores of 250–500 nm have recently been fabricated *via* steam-assisted crystallization of mesoporous silica.⁵

Transforming laboratory zeolites to industry catalysts is no easy task. Among others, zeolite powders must be shaped with an aid of additives including binders. This is not only costly but causing a series of problems including dilution of active species, diffusion limitation, pore blockage and inaccessibility to interior active sites.⁶ Depositing zeolite films on porous supports is further challenged by easy loss of zeolite films due to different thermal expansion coefficients. It is therefore of great importance to develop self-supporting hierarchical zeolite catalysts with desired porous hierarchy, good mass/heat transfer rates, low pressure drop and adequate mechanical strength.⁷ The concept of self-supporting zeolite catalysts was first demonstrated *via* a micro-macroporous Sil-1 with broad macropores centred at 500 μm using polyurethane foam.^{4a} A series of landmark development follows including a micro-mesoporous ZSM-5 using carbon aerogel,⁸ a micro-

^a State Key Lab of Inorganic Synthesis and Preparative Chemistry, Jilin University, Changchun, 130012, China. E-mail: yanxu@jlu.edu.cn

^b National Engineering Laboratory for Methanol to Olefins, Dalian National Laboratory for Clean Energy, Dalian Institute of Chemical Physics, Dalian, 116023, China. E-mail: liuzm@dicp.ac.cn

*Corresponding authors.

† Electronic Supplementary Information (ESI) available: SEM, TEM, XRD, FTIR, TG, EDS, XPS, UV spectrum, N₂ sorption isotherm, NH₃-TPD, Hg intrusion porosimetry, MTH conversion and product selectivity. See DOI:10.1039/x0xx00000x


EDGE ARTICLE

macroporous ZSM-5 with macropores of 3-8 μm by silica gel transformation method,⁹ and a micro-macroporous Sil-1 with macropores of 10-50 μm by ice templating method.¹⁰ The recent development of a self-supporting tetramodal ZSM-5 monolith containing two macropores (0.2-1.7 μm and 24-33 μm), intracrystalline mesopores centred at 53 nm and zeolitic micropores sets a new record in hierarchical zeolites research.¹¹ ZSM-5 microtubes with trimodal porosity exhibit improved stability in the methanol-to-gasoline conversion.¹² However, the ZSM-5 microtubes are discrete with inner tube diameter of 2-4 μm , which are too large to be best utilized; besides, the microtube formation mechanism remains elusive. A supported hierarchical zeolite **MFI** displaying a trimodal network of zeolitic micropores (0.55 nm), intercrystalline mesopores (10 nm) and macropores (200-300 nm) yields superior performance in the methanol-to-olefin conversion compared to its conventional analogue.^{6a}

Inspired by the organization of biominerals, we have developed a novel precursor scaffolding-solid phase crystallization strategy for hierarchical zeolites with a unique nanotube scaffolding architecture and nanotube-trimodal network using BSA as a scaffolding blueprint, which extends the regime of bioscaffold-mediated mineralization research.¹³ The strategy is conceptualized using bacterial cellulose (BC) aerogel, and the versatility is confirmed using chitosan (Ch) aerogel. The challenges for constructing stable zeolite nanotube scaffolds using BSA are overcome by first transforming BSA to a precursor scaffold both as a precursor source as well as a scaffolding template, followed by concurrent zeolite crystallization and nanotube formation *via* seeded solid phase crystallization. Zeolite nanotubes are self-generated, where BSA nanofibers are found running along the inner corridor of the nanotubes forming a wire-in-nanotube geometry. The evolution phenomena of zeolite nanotubes including ion diffusion pairs, segmented voids and solid bridges is in a good agreement with the Kirkendall effect.¹⁴ Applying this strategy, ZNTS ZSM-5, TS-1 and Sil-1 have been obtained with narrow macropores (700 nm), narrow mesopores (2 nm), zeolitic micropores (0.55 nm) and uniform nanotubes with tunable inner diameter between 30-90 nm by varying the thickness of precursor layer. The macroporosity can be modulated by the choice of BSA. Self-supporting ZNTS ZSM-5 catalyst exhibits superior catalytic performance in the MTH conversion compared to conventional ZSM-5.

Results and Discussion

As illustrated in Scheme 1, the precursor scaffolding-solid phase crystallization strategy for ZNTS involves three principle steps: (1) formation of precursor scaffolds from BSA by confined deposition, (2) concurrent zeolite crystallization and nanotube formation, and (3) BSA removal. For easy illustration, the nanofabrication of ZNTS ZSM-5 using BC is discussed in details. Experimental details are provided in the Supporting Information. The precursor scaffold of BC@ASO is prepared from reaction mixtures with a typical composition of 42TEOS:1ATSB:10NH₃·H₂O:11CTAB:178EtOH:0.6BC. The

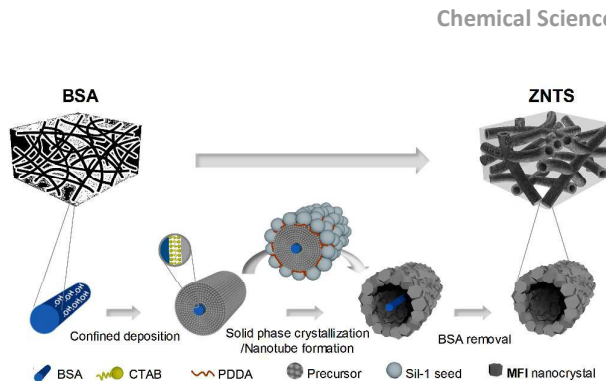

Scheme 1 Nanofabrication of ZNTS by the precursor scaffolding-solid phase crystallization strategy.

formation of BC@ASO is challenged by the following: (i) BC has electronegative surface while aluminosilicates are polyanions, (ii) the polycondensation of TEOS is a rapid process that further facilitates the condensation of ATSB, and (iii) the diffusion of TEOS and ATSB is slow due to the percolating network of hydrogen-bonded BC nanofibers with internal voids filled with solvents (Fig. S1). The confined deposition of aluminosilicates around BC is accomplished with an aid of self-assembled a layer of surfactant, CTAB. The compatibility between the diffusion rate and the rate of polycondensation of TEOS and ATSB is critical for deposition uniformity. This can be achieved by first soaking BC in ethanol containing a stoichiometric amount of TEOS, ATSB and CTAB at RT to allow thorough penetration, followed by addition of ammonia at 0 °C to switch-on the polycondensation. BC@ASO has smooth surface and uniform thickness with an average diameter of 200 nm (Fig. 1a). The thickness of the aluminosilicate layer can be tuned between 80-200 nm by varying the concentration of

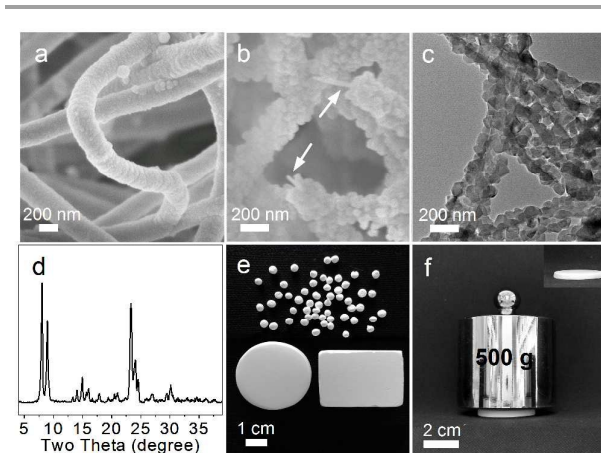


Fig. 1 (a) SEM of BC@ASO precursor scaffold. (b) Cross-sectional view of BC@ZSM-5 by SEM showing a wire-in-nanotube geometry with BC (arrow) in the core of the nanotube. (c) Sideview of BC@ZSM-5 showing interconnected nanotube by TEM. (d) XRD pattern of ZNTS ZSM-5. (e) Photograph of ZNTS ZSM-5 showing tailorable geometry. (f) Photograph of ZNTS ZSM-5 showing negligible volume change after mechanical pressing.

TEOS and ATSB, and the number of deposition cycles.

Concurrent zeolite crystallization and nanotube formation occur during the vapor treatment of the SiI-1 seeded BC@ASO under autoclaving conditions. SiI-1 seeds have uniform size with an average diameter of around 50 nm (Fig. S2a, S2b). Seeding is driven by electrostatic interactions with an aid of a positive polyelectrolyte, PDDA.¹⁵ Partial seeding due to electrostatic repulsion can be overcome by using low molecular-weight PDDA together with small electrolytes such as NaCl.¹⁶ Seeding uniformity is crucial, and it can be accomplished by meticulous experimental design (Fig. S2c, S2d). The seeded BC@ASO is transformed to BC@ZSM-5 nanotube scaffolds made of highly crystallized ZSM-5 nanocrystals (JCPDS 044-0002, ~95%.) after 72 h of the vapor treatment at 140 °C, where BC nanofibers are found running along the inner corridor of the nanotubes based on the SEM, TEM and FTIR analyses (Fig. 1b-1d, S3). Amorphous silica at $2\theta=20^\circ$ and crystalline impurities are absent based on the XRD analysis (Fig. 1d). The challenges to preserve the scaffolding architecture can be overcome by treating the seeded precursor scaffolds using the vapor of 1EDA:12TEA:13H₂O under autoclaving conditions, which is a modified steam-assisted crystallization method.¹⁷ White spongy monoliths of ZNTS ZSM-5 with tailorable geometry and adequate mechanical strength are recovered from BC@ZSM-5 by calcination at 550 °C (Fig. 1e, 1f, S3, S4).

ZNTS ZSM-5 has a nanotube scaffolding architecture based on cross-linked ZSM-5 nanotubes of uniform thickness (Fig. 2a-2c). The nanotube wall is made of a single layer of intergrown nanocrystals of ZSM-5 with an approximate size of 70 nm (Fig. 2c). HRTEM shows uniform lattice fringes with a *d*-spacing of 0.99 nm corresponding to *d*₀₂₀ of ZSM-5, suggesting the single crystal nature of ZSM-5 nanocrystals (Fig. 2d). Adjacent

nanocrystals of ZSM-5 intergrow based on the HRTEM analysis, rendering the nanotube high mechanical stability (Fig. 2d Inset). ²⁹Si MAS NMR spectrum shows a prominent resonance at -110 ppm and shoulder peaks between -100 ppm and -105 ppm, featuring cross-linked Q⁴ units [Si(OSi)₄], and Q³ units [(HO)Si(OSi)₃, (AlO)Si(OSi)₃] with a Q⁴/Q³ ratio of 1.95 (Fig. S5a). No Q² units are found in ZNTS ZSM-5. The sharp and symmetrical peak at 53 ppm on the ²⁷Al MAS NMR spectrum indicates tetrahedral Al³⁺, and no octahedral Al³⁺ is detected (Fig. S5b). ZNTS ZSM-5 with Si/Al ratio of 125 to ∞ has been obtained based on ICP.

The porosity of ZNTS ZSM-5 is examined by N₂ sorption and Hg intrusion porosimetry measurements (Fig. 3a, 3b). It exhibits a typical type I isotherm with a sharp uptake at *P*/*P*₀ < 0.1, revealing zeolitic micropores centred at 0.55 nm based on the Horvath-Kawazoe (HK) method (Fig. 3a, Inset). A hysteresis at *P*/*P*₀ = 0.50-0.75 is attributed to the capillary condensation in small mesopores. A H3 type hysteresis loop at *P*/*P*₀ = 0.75-1.0 implies the presence of cylindrical mesopores. The mesopore size distribution calculated by the BJH method from the adsorption branch reveals narrow mesopores centred at 2 nm formed by intergrown nanocrystals of ZSM-5 and mesopores centred at 90 nm attributed to ZSM-5 nanotubes (Fig. 3a, Inset). Narrow macropores are found between 400-900 nm based on the Hg intrusion porosimetry measurements (Fig. 3b, Inset). The BET surface area is calculated to be 380 m²g⁻¹ and the total pore volume is 0.40 cm³g⁻¹ including 0.15 cm³g⁻¹ of micropores and 0.25 cm³g⁻¹ of mesopores. The nanotube scaffolding architecture is anisotropic based on the low magnification SEM (Fig. 3c, 3e), and the nanotube connectivity is evidenced by the laser scanning confocal microscopy (LSCM) images of ZNTS ZSM-5 dyed with fluorescent rhodamine B (Fig. 3d, 3f). ZNTS ZSM-5 is hierarchically porous, where the nanotube-trimodal connectivity can be deduced from the unique construction, and the greater BET surface area of ZNTS ZSM-5 than conventional ZSM-5.

Notably, the macropores of ZNTS ZSM-5 downshift dramatically during the nanofabrication (Fig. S6a, S6b). The greater outer diameter of ZSM-5 nanotubes (~300 nm) than the diameter of the BC@ASO fibers (~200 nm) reduces the effective opening of macropores (Fig. 2b, 1a). Deposition of aluminosilicates causes reassembly of the hydrogen-bonded network of BC nanofibers, responsible for the downshift of the macropores of BC@ASO compared to BC. This is accompanied by the loss of crystalline order of BC due to cellulose regeneration in strong alkaline medium (Fig. S6c).¹⁸ The nanofabrication causes negligible volume change of the spongy monoliths from BC to ZNTS ZSM-5 (Fig. S6c Inset).

It is worth taking note that the inner diameter of the ZSM-5 nanotube is around 90 nm, which is significantly greater than the average diameter of BC being around 27 nm (Fig. 2b, 1b, S1). It implies that ZSM-5 nanotubes are generated by mechanisms beyond simple replication of BC nanofibers. Hollow nanostructures can be generated due to different atomic diffusion rates of core and shell species, leading to void nucleation at the core/shell interface. The Kirkendall effect has

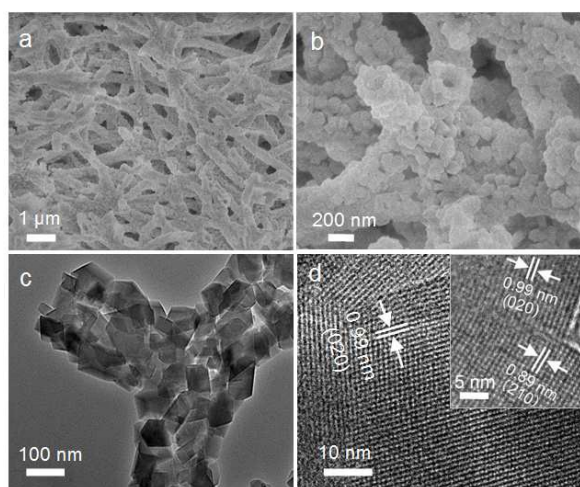


Fig. 2 Characterizing ZNTS ZSM-5: (a) Low magnification SEM showing nanotube scaffolding architecture. (b) High magnification SEM showing ZSM-5 nanotubes. (c) High magnification TEM showing nanotubes connectivity. (d) HRTEM showing the single crystal nature of ZSM-5. Inset: HRTEM showing the intergrowth between the adjacent nanocrystals of ZSM-5.

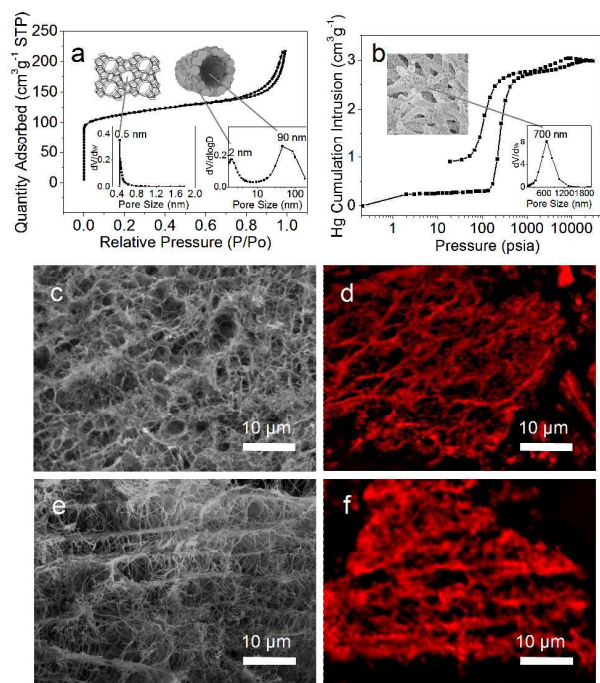


Fig. 3 Characterizing the scaffolding architecture of ZNTS ZSM-5: (a) N₂ sorption isotherm and micropore, mesopore and nanotube. (b) Hg intrusion porosimetry measurements and macropore profile. (c,e) Low magnification SEM and (d,f) LSCM images showing the anisotropic structure and the nanotubes connectivity, respectively.

been applied to explaining the self-generation of hollow nanostructures of varying geometry and compositions.¹⁹ In a typical Kirkendall process, interim phenomena including segmented voids and solid bridges are usually found between core and shell, indicating a net outward diffusion and diffusion path, respectively.^{19b} The average diameter of the Kirkendall hollow spheres is often smaller than initial solid spheres.²⁰

The evolution of ZSM-5 nanotube is tracked to unravel the formation mechanism. The Sil-1 seeded BC@ASO are solid fibers with BC nanofibers in the core (Fig. 4a, 4b). After 6 h of the vapor treatment, segmented voids are observed at the interface of the Sil-1 seeds and the amorphous aluminosilicates (Fig. 4c, 4d). As it proceeds, an interrupted tube with segmented voids and solid bridges become evident based on the high magnification TEM and SEM (Fig. 4e, 4f). The evolution of ZSM-5 nanotube is accompanied by an increase in crystal dimensions as well as the crystallinity from ~10% at 0 h to ~95% at 72 h (Fig. 4a, 4g, S7a), suggesting that crystallization drives the nanotube formation. The corresponding FTIR spectrum shows that the absorption band centred at 550 cm⁻¹, associated with the asymmetric stretching mode of the double five-rings of MFI structure, picks up intensity with time (Fig. S7b). The optical density ratio of the 550 cm⁻¹ band to the 455 cm⁻¹ band at 72 h is around 0.73, close to that of MFI structure, confirming well crystallized ZSM-5 phase.

The average inner diameter of the nanotube (~90 nm) is about 45% of the average diameter of BC@ASO (~200 nm). This ratio is within the size ratio range of 40-70% reported for hollow nanoparticles evolved *via* the Kirkendall effect.²⁰ To determine whether Al³⁺ ions have diffused into the Sil-1 seeds to replace Si⁴⁺ ions, XPS spectra were recorded on the untreated and the Ar-ion-sputtered nanocrystals of ZSM-5, and the Sil-1 seed. The presence of Al³⁺ ions on the surface and in the core of ZSM-5 nanocrystals is indicated by the Al 2p_{3/2} peak at 74.5 eV with a slight decrease in intensity (Fig. S8). It indicates that outbound diffusion of Al³⁺ ions coupled with inward diffusion of Si⁴⁺ ions take place driven by ion-exchange, which contributes to the evolution of ZSM-5 nanotubes.

The observations of ion diffusion pairs, segmented voids, solid bridges and the size reduction of the nanotube suggest that the evolution of the ZSM-5 nanotube is likely a manifestation of the Kirkendall effect in a solid phase crystallization system. The inner diameter of the ZSM-5 nanotube can be tuned between 30-90 nm by varying the thickness of the aluminosilicate layer (Fig. S9, S10, Table S1).

The feasibility of the current strategy is manifested by the successful fabrication of ZNTS TS-1 (Si/Ti ratio: 115 to ∞, crystallinity: ~92%) and ZNTS Sil-1 (crystallinity: ~97%) from the Sil-1 seeded precursor scaffolds of BC@TSO and BC@SO,

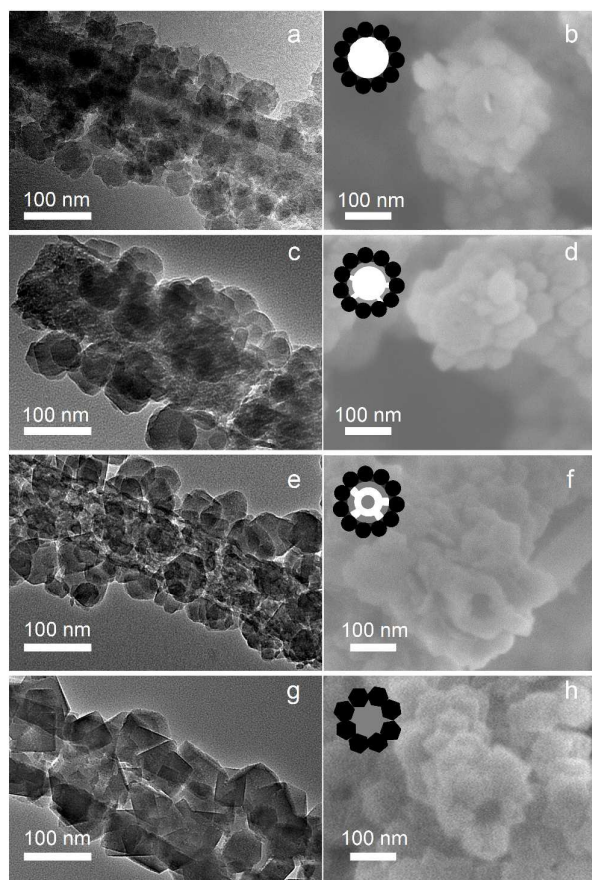


Fig. 4 Tracking the evolution of ZSM-5 nanotube using high magnification TEM and SEM: (a,b) 0 h. (c,d) 6 h. (e,f) 18 h. (g,h) 72 h.

respectively (Fig. S11a, S11b). Ti^{4+} ions in ZNTS TS-1 are found exclusively in a tetrahedral environment based on the sole and strong absorption at 220 nm on the UV-vis spectrum, confirming that amorphous precursor has transformed to crystalline TS-1 phase (Fig. S11c).²¹ The zeolitic micropores, textural mesopores, nanotubes and macropores are revealed by the sorption measurements (Fig. S12). The signature nanotube scaffolding architecture is evidenced by the high magnification TEM and SEM (Fig. S12 Insets). The micropore volumes of ZNTS TS-1 and ZNTS Sil-1 are similar to that of **MFI**, further confirming that the microporous structure of **MFI** is retained in the respective ZNTS (Table S2). ZNTS TS-1 and ZNTS Sil-1 exhibit greater BET surface areas than corresponding zeolite analogue,^{10,4b} implying the nanotube-trimodal connectivity.

The versatility of the current strategy is further examined for the nanofabrication of ZNTS Sil-1 (Ch) using Ch aerogel (Fig. S13). It exhibits the signature scaffolding architecture of ZNTS based on cross-linked nanotubes with tube walls made of intergrown nanocrystals of Sil-1 (Fig. S14). The porous hierarchy is featured with zeolitic micropores (0.55 nm), textural mesopores (2 nm), nanotubes (inner diameter: 100 nm) and macropores (centre: 2 μm). Notably, the macropores of ZNTS Sil-1 (Ch) are larger than those of ZNTS Sil-1 from BC@SO (Fig. S14d, S12b₂), indicating that the macropore profile can be modulated by the choice of BSA. The textural properties of ZNTS Sil-1 (Ch) are summarized in Table S3.

ZNTS ZSM-5 with a stable nanotube scaffolding architecture and nanotube-trimodal connectivity may prove to be a promising self-supporting zeolite catalyst. The MTH conversion was examined over self-supporting monolith of ZNTS ZSM-5 in a fixed-bed stainless reactor. For comparison, a conventional ZSM-5 powder with similar dimension, crystallinity and Si/Al ratio was used as a reference (Fig. S15a, S15b).²² The NH_3 -TPD profiles of both ZNTS ZSM-5 and the conventional ZSM-5 show two peaks centred at 180 °C and 405 °C, corresponding to weak and strong acidity, respectively (Fig. S15c). It indicates their very close acid strength and acid concentration.

Both of the ZSM-5 catalysts present approximately 100% of initial methanol conversion, however, the stability varies. The catalyst lifetime of ZNTS ZSM-5 is longer than that of the conventional ZSM-5 (Fig. S16a). Likely, the multiple interconnected micro-compartments formed by the cross-linked ZSM-5 nanotubes with effective openings at micrometer scale enable easy diffusion of methanol and hydrocarbon products. Under the same reactant-catalyst contact time, ZNTS ZSM-5 exhibits different product selectivity compared to the conventional ZSM-5 powder (Fig. S16b). The relatively low selectivity for aromatics of ZNTS ZSM-5 indicates that H-transfer reaction responsible for coke formation has been suppressed. This is further confirmed by the coke formation rate of 1.0 $\text{mgh}^{-1}\text{g}^{-1}$ for ZNTS ZSM-5 and 1.5 $\text{mgh}^{-1}\text{g}^{-1}$ for the conventional ZSM-5 based on the TG analysis of the used catalysts (Fig. S15d). Given the similar catalyst dimension, acidity, crystallinity and micropore volume between the two catalysts, we believe that the unique nanotube scaffolding

architecture is the key reason for the excellent catalyst stability of ZNTS ZSM-5. The cause for coke formation is likely associated with the large nanocrystal size of ZSM-5 in ZNTS ZSM-5 resulting in long diffusion path within zeolitic micropores, which needs to be further examined.

ZNTS ZSM-5 is a spongy monolith with an approximate density of 0.187 g cm^{-3} and porosity of 89 %, which makes it a promising choice as self-supporting hierarchical catalysts with transport advantages and added separation capability.

Conclusions

In summary, we have developed a novel precursor scaffolding-solid phase crystallization strategy for hierarchical zeolites with a unique nanotube scaffolding architecture and nanotube-trimodal network. This is the first demonstration of hierarchical zeolites based on interconnected nanotubes, where the zeolite nanotube is self-generated with tunable geometry. The macroporosity can be modulated by the choice of BSA. ZNTS ZSM-5 exhibits structure-enabled catalytic performance superior to conventional ZSM-5 in the MTH conversion. Self-generation of zeolite nanotubes keeps BSA intact after crystallization that allows higher level of mesoscale organization and functionalization of zeolite nanotube scaffolds. The precursor scaffolding-solid phase crystallization strategy of the current work may afford a versatile strategy for a new family of hierarchical zeolites with signature nanotube scaffolding architectures and a nanotube-multimodal network. On-going research is in progress to establish more quantitative relationship between the diffusion rate, the reactive site and the porous hierarchy, and the catalytic performance that will ultimately enable rational design of hierarchical zeolites for hierarchical catalysis and other advanced applications.

Acknowledgements

The authors are grateful to the financial support: NNSF China 21171067 & 21373100, Talent Funds 802110000412 and Tang Aoqing Professor Funds 450091105161, to Professor J.H. Yu for valuable advises, Professor X.J. Ji for macropore size measurements and Professor C.F. Wu for LSCM imaging analysis.

Notes and references

- (a) A. Corma, *Chem. Rev.*, 1997, **97**, 2373; (b) J. Pérez-Ramírez, C. Christensen, K. Egeblad, C. Christensen and J. Groen, *Chem. Soc. Rev.* 2008, **37**, 2530; (c) Y. Li, X. Li, J. Liu, F. Duan and J. Yu, *Nat. Commun.*, 2015, **6**, 8328.
- (a) M. Choi, K. Na, J. Kim, Y. Sakamoto, O. Terasaki and R. Ryoo, *Nature*, 2009, **461**, 246; (b) V. Valtchev, E. Balanzat, V. Mavrodinova, I. Diaz, J. Fallah and J. Goupil, *J. Am. Chem. Soc.*, 2011, **133**, 18950; (c) D. P. Serrano, J. M. Escola and P. Pizarro, *Chem. Soc. Rev.*, 2013, **42**, 4004.
- (a) M. Ogura, S. Shinomiya, J. Tateno, Y. Nara, M. Nomura, E. Kikuchi and M. Matsukata, *Appl. Catal. A*, 2001, **219**, 33; (b) M. Hartmann, *Angew. Chem. Int. Ed.*, 2004, **43**, 5880; (b) J. Groen, T.

- Bach, U. Ziese, A. Donk, K. Jong, J. Moulijn and J. Pérez-Ramírez, *J. Am. Chem. Soc.*, 2005, **127**, 10792.
- 4 (a) Y. Lee, J. S. Lee, Y. S. Park and K. B. Yoon, *Adv. Mater.*, 2001, **13**, 1259; (b) L. Chen, X. Li, G. Tian, Y. Li, J. C. Rooke, G. Zhu, S. Qiu, X. Yang and B. Su, *Angew. Chem. Int. Ed.* 2011, **50**, 11156; (c) V. Valtchev, B. Schoeman, J. Hedlund, S. Mintova and J. Sterte, *Zeolites*, 1996, **17**, 408.
- 5 A. G. Machoke, A. M. Beltrán, A. Inayat, B. Winter, T. Weissenberger, N. Kruse, R. Güttel, E. Spiecker and W. Schwieger, *Adv. Mater.*, 2015, **27**, 1066.
- 6 (a) S. Mitchell, N. Michels, K. Kunze and J. Pérez-Ramírez, *Nat. Chem.*, 2012, **4**, 825; (b) C. Parlett, K. Wilson and A. Lee, *Chem. Soc. Rev.*, 2013, **42**, 3876; (c) D. Verboekend and J. Pérez-Ramírez, *ChemSusChem*, 2014, **7**, 753.
- 7 (a) S. Lopez-Orozco, A. Inayat, A. Schwab, T. Selvam and W. Schwieger, *Adv. Mater.*, 2011, **23**, 2602; (b) B. M. Weckhuysen and J. Yu, *Chem. Soc. Rev.*, 2015, **44**, 7022.
- 8 Y. Tao, H. Kanoh and K. Kaneko, *J. Am. Chem. Soc.*, 2003, **125**, 6044.
- 9 Q. Lei, T. Zhao, F. Li, L. Zhang and Y. Wang, *Chem. Commun.*, 2006, 1769.
- 10 H. Mori, K. Aotani, N. Sano and H. Tamon, *J. Mater. Chem.*, 2011, **21**, 5677.
- 11 B. Li, Z. Hu, B. Kong, J. Wang, W. Li, Z. Sun, X. Qian, Y. Yang, W. Shen, H. Xu and D. Zhao, *Chem. Sci.*, 2014, **5**, 1565.
- 12 (a) K. Shen, W. Qian, N. Wang, C. Su and F. Wei, *J. Am. Chem. Soc.*, 2013, **135**, 15322; (b) J. Liu, G. Jiang, Y. Liu, J. Di, Y. Wang, Z. Zhao, Q. Sun, C. Xu, J. Gao, A. Duan, J. Liu, Y. Wei, Y. Zhao and L. Jiang, *Sci. Rep.* 2014, **4**, 7276.
- 13 (a) M. W. Anderson, S. M. Holmes, N. Hanif and C. S. Cundy, *Angew. Chem. Int. Ed.*, 2000, **39**, 2707; (b) A. Dong, Y. Wang, Y. Tang, N. Ren, Y. Zhang, Y. Yue and Z. Cao, *Adv. Mater.*, 2002, **14**, 926; (c) D. Walsh, L. Arcelli, T. Ikoma, J. Tanaka and S. Mann, *Nat. Mater.*, 2003, **2**, 386; (d) V. Valtchev, F. Gao and L. Tosheva, *New J. Chem.*, 2008, **32**, 1331; (e) C. Y. Khripin, D. Pristinski, D. Y. Dunphy, C. J. Brinker and B. Kaehr, *ACS Nano*, 2011, **5**, 1401; (f) T. Nonoyama, T. Kinoshita, M. Higuchi, K. Nagata, M. Tanaka, K. Sato and K. Kato, *J. Am. Chem. Soc.* 2012, **134**, 8841; (g) P. Wang, J. Zhao, R. Xuan, Y. Wang, C. Zou, Z. Zhang, Y. Wan and Y. Xu, *Dalton Trans.*, 2014, **43**, 6762; (h) P. Wang, Z. Geng, J. Gao, R. Xuan, P. Liu, Y. Wang, K. Huang, Y. Wan and Y. Xu, *J. Mater. Chem. A*, 2015, **3**, 1709; (i) H. Huang, Y. Wang, C. Zou, D. Qu, P. Liu, Y. Wan and Y. Xu, *J. Phys. Chem. C*, 2015, **119**, 17552.
- 14 H. Fan, U. Gösele and M. Zacharias, *small*, 2007, **3**, 1660.
- 15 (a) A. Dong, Y. Wang, Y. Tang, N. Ren, Y. Zhang and Z. Gao, *Chem. Mater.*, 2002, **14**, 3217; (b) Y. Wang and F. Caruso, *Adv. Funct. Mater.*, 2004, **14**, 1012; (c) Y. Deng, C. Deng, D. Qi, C. Liu, J. Liu, X. Zhang and D. Zhao, *Adv. Mater.*, 2009, **21**, 1377.
- 16 S. Schwarz, S. Bratskaya, W. Jaeger and B. Paulke, *J. Appl. Polym. Sci.*, 2006, **101**, 3422.
- 17 (a) W. Xu, J. Dong, J. Li, J. Li and F. Wu, *J. Chem. Soc., Chem. Commun.*, 1990, 755; (b) M. Matsukata, M. Ogura, T. Osaki, P. Rao, M. Nomura and E. Kikuchi, *Top. Catal.*, 1999, **9**, 77.
- 18 D. Klemm, B. Philipp, T. Heinze, U. Heinze, W. Wagenknecht, *Comprehensive Cellulose Chemistry, Vol. 1*, Wiley-VCH, Weinheim, 1998, pp. 56-58.
- 19 (a) H. Fan, M. Knez, R. Scholz, K. Nielsch, E. Pippel, D. Hesse, M. Zacharias and U. Gösele, *Nat. Mater.*, 2006, **5**, 627; (b) H. Fan, M. Knez, R. Scholz, D. Hesse, K. Nielsch, M. Zacharias and U. Gösele, *Nano Lett.*, 2007, **7**, 993; (c) W. Wang, M. Dahl and Y. Yin, *Chem. Mater.*, 2013, **25**, 1179.
- 20 Y. Yin, R. M. Rioux, C. K. Erdonmez, S. Hughes, G. A. Somorjai and A. P. Alivisatos, *Science*, 2004, **304**, 711.
- 21 (a) C. Li, G. Xiong, J. Liu, P. Ying, Q. Xin, and Z. Feng, *J. Phys. Chem. B*, 2001, **105**, 2993; (b) Y. Zuo, M. Liu, T. Zhang, L. Hong, X. Guo, C. Song, Y. Chen, P. Zhu, C. Jaye and D. Fischer, *RSC Adv.*, 2015, **5**, 17897.
- 22 R. V. Grieken, J. L. Sotelo, J. M. Menéndez and J. A. Melero, *Microporous Mesoporous Mater.*, 2000, **39**, 135.