

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

3D Graphene/Nylon Rope as Skeleton of Noble Metal Nanocatalysts for Highly Efficient Heterogeneous Continuous-Flow Reaction


Sai Zhang,^a Xuetao Shen,^a Zhiping Zheng,^a Yuanyuan Ma*^a and Yongquan Qu*^{a,b}

^a Center for Applied Chemical Research, Frontier Institute of Science and Technology, Xi'an Jiaotong University, Xi'an, China 710049

^b State key Laboratory for Mechanical Behavior of Materials, Xi'an Jiaotong University, Xi'an, China 710049

E-mail: yongquan@mail.xjtu.edu.cn; yyma@mail.xjtu.edu.cn

An universal approach has been developed to synthesize the 3D noble metal (Au, Ag, Pd and Pt)/graphene/nylon rope catalysts and realize their highly efficient and stable catalytic activity for the heterogeneous continuous-flow reactions. The highly chemical and structural stability of the 3D rope-like catalysts make them compatible to the harsh reaction conditions and shaped reactors.

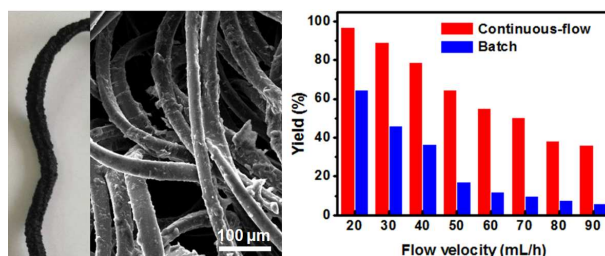

ARTICLE

3D Graphene/Nylon Rope as Skeleton of Noble Metal Nanocatalysts for Highly Efficient Heterogeneous Continuous-Flow Reaction

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/Sai Zhang,^a Xuetao Shen,^a Zhiping Zheng,^a Yuanyuan Ma^{*a} and Yongquan Qu^{*a,b}

Continuous-flow catalytic systems represent a highly efficient approach towards scalable synthesis, with features of saved energy and time, easy operation, and improved safety. Herein, we rationally design a novel 3D noble metal/graphene/nylon rope as highly efficient catalysts for continuous-flow organic reactions. We show that different noble metal (Pd, Pt, Au and Ag) nanocatalysts and graphene can be readily assembled with chemically inert nylon rope by an one-step hydrothermal method. Graphene, acting as the interconnector for noble metal nanoparticles and nylon rope, increases the flexibility and mechanical strength of rope-like catalysts and improves the catalytic activity and stability of the noble metal species. The large voids within the noble metal/graphene/nylon rope catalysts, under optimized reaction conditions, ensure the sufficient chemical transfer for the continuous-flow system. The high catalytic activity and stability of rope catalysts are demonstrated by the Suzuki-Miyaura cross-coupling reaction (SMC) and 4-nitrophenol reduction reaction. Pd/graphene/nylon rope catalysts show a high turnover number of 965 mol h⁻¹ mol_{Pd}⁻¹, a large productivity of 1385 mg h⁻¹ mg_{Pd}⁻¹ at a flow rate of 70 mL/h, and a remarkable stability for continuous-flow SMC reaction. Such a novel minifluidic system integrated with 3D noble metal/graphene/nylon rope catalysts can be extended to many important chemical reactions.

Introduction

Continuous-flow systems are of particular interest for both synthetic and process chemistry including organic catalysis, pharmaceutical synthesis, and nanostructure production.¹⁻⁶ Compared to its counterpart — the conventional batch synthesis, continuous-flow systems have many vital benefits, such as energy efficiency, high time-gain efficiency, easy scale-up, increased reactivity and selectivity, flexible automation, secured reproducibility, improved handling and safety, and enhanced operational reliability.⁷⁻¹¹ As a consequence of these advantages of the continuous-flow system, it has attracted extensive attention in both academia and industry.

Typically, state-of-the-art continuous-flow systems for organic synthesis are established on the basis of homogeneous catalysis, which are catalyzed by molecular complexes in organic media or a mixture of organic solvent and water in the presence of additives.¹²⁻¹⁵ However, such homogeneous continuous-flow systems raise the difficulties in product purification and catalyst recovery. To develop a continuous-flow system that combines immobilized catalysts on solid supports has the potential to address the inconveniences of

homogeneous systems.⁹ Catalysts anchored on the surface of silica,¹⁶ aluminium oxide,^{17,18} and polymer beads^{19,20} packed into the continuous-flow column have been reported to benefit the separation of catalysts from products and reuse of the catalysts. However, the elemental analysis indicates a gradual bleaching of catalytically active species into the reaction solution, which may result in a continuously decreased catalytic efficiency of the system²¹⁻²³. Besides, the swelling of the polymer supports in organic solvent and chemical instability of metal oxides under the harsh conditions further increase complexity to the heterogeneous catalysts in continuous-flow systems. The selected solvents and additives are also limited by the polymer and metal oxides, which may react or be dissolved in the reaction media. Therefore, it is still greatly significant and challenging to seek for a support with high structural stability under harsh reaction conditions, and thus increase the activity of the catalysts and reduce bleaching of the catalytic active component.

Mono or multilayer of chemically exfoliated graphene with many advantages, such as large surface area and porosity, excellent mechanical strength, outstanding chemical stability, and high

electronic conductivity, offers great technical promise of graphene as an ideal support for heterogeneous catalysis.²⁴⁻²⁸ Noble metal graphene composites have been widely explored for chemical reactions, with improved catalytic activity and enhanced durability.²⁹⁻³² Recently, the synthesis and applications of three dimensional (3D) graphene and their composites with metal/metal oxides have attracted considerable interest in the areas of catalysis, energy storage, and environmental remediation³³⁻³⁵. For example, the 3D Pd/graphene presents high activity for the Heck C-C coupling reaction.³⁶ To the best of our knowledge, the investigations on continuous-flow systems integrated with 3D graphene have not been reported, despite the numerous advantages of graphene for catalytic reactions. This could be attributed to the randomly distributed macroscale pores of 3D graphene, which may result in uncontrollable fluid dynamics, limited liquid flow rates, and clogged flow channel. Moreover, the less easily tailored geometric configuration, size, and structural collapse of wet 3D graphene or their composites with slight bending or stretching make them incompatible to the shaped-reactor.

Herein, we report a uniform model for the assembly of a novel 3D macroscale noble metal/graphene/nylon rope as a catalytic fixed-bed incorporated for continuous-flow minifluidic systems. We selected the nylon rope (8.33 mg/cm, specific surface area = 0.015 m²·g⁻¹, $\varphi=1.5$ mm) as the skeleton for the assembled noble metal/graphene due to its excellent chemical inertness, high structural stability and flexibility at harsh conditions, and tens of micron-scaled voids within the rope for efficient liquid flow. Graphene, which acts as the interconnector for the noble metal nanoparticles and nylon rope, increases the flexibility and mechanical strength of the noble metal/graphene/nylon rope and improves the catalytic activity of the noble metal species. The noble metal nanoparticles anchor onto the graphene sheet and could be stabilized in the porous graphene structure. The high catalytic efficiency and remarkable stability of Pd/graphene/nylon ropes (PdGN) are demonstrated by a proof-of-concept reaction of the Suzuki-Miyaura cross-coupling (SMC) between iodobenzene and phenylboronic acid. With the continuous-flow system, a high productivity (1385 mg h⁻¹ mg_{Pd}⁻¹) and a large turnover number (TON, 965 mol h⁻¹ mol_{Pd}⁻¹) are achieved at a high flow rate of 70 mL/h with a short residence time of 1.7 min, which are 5.0 and 4.3 times higher than those for batch synthesis with the same amount of reactants for 1 hour flowing through the continuous-flow system. The successfully assembled Pt/graphene/nylon rope (PtGN), Au/graphene/nylon rope (AuGN), and Ag/graphene/nylon rope (AgGN) proves this is a uniform model for fabrication of noble metal/graphene/nylon rope catalysts (NMGN). Their catalytic activity and remarkable stability are also demonstrated by another model reaction of the chemical reduction of 4-nitrophenol.

Results and Discussion

The synthetic approach of PdGN catalysts are facile and straightforward by a one-step hydrothermal method at 120 °C in a mixed solution containing clean nylon rope, graphene oxides, Na₂PdCl₄ and glucose. As shown in the optical images (Figure 1a and 1b) for nylon rope before hydrothermal treatment and PdGN catalysts, the color evolution from white to black indicates the successful assembly of Pd nanoparticles, graphene, and nylon rope. In contrast, the hydrothermal

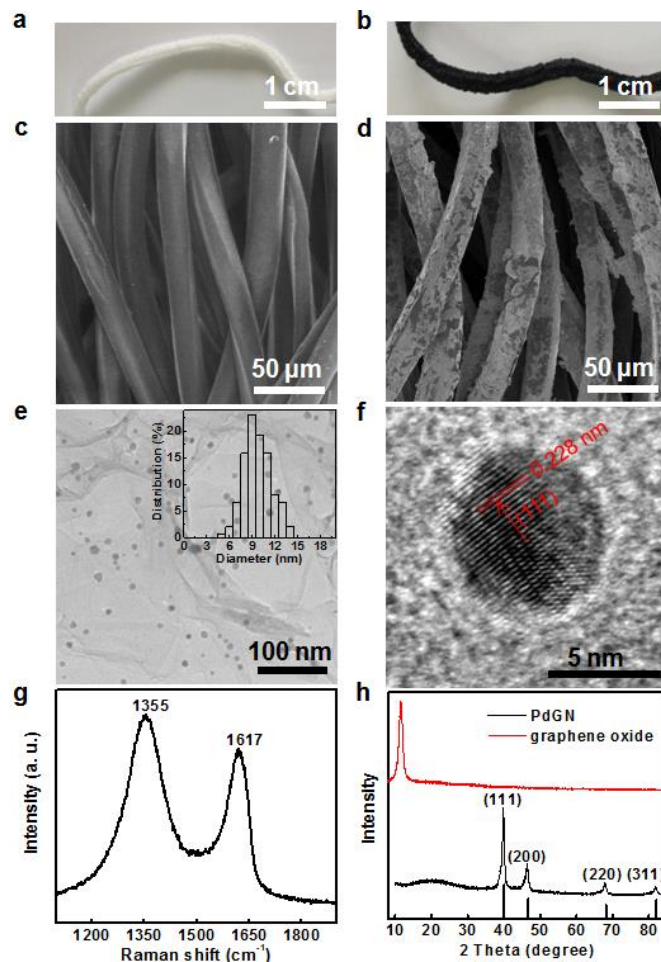


Fig. 1 Structural characterization of the PdGN catalysts. (a) Optical image of clean nylon rope. (b) Optical image of as-synthesized PdGN catalysts. (c) SEM image of clean nylon rope. (d) SEM image of PdGN catalysts. (e) TEM and (f) HRTEM images of Pd nanoparticles anchored on graphene obtained from 30 min ultrasonication of PdGN catalysts in ethanol. Inset is the size distribution of Pd nanoparticles loaded on PdGN catalysts. (g) Raman spectrum of PdGN catalysts. (h) XRD patterns of PdGN catalysts and graphene oxides.

treatments on nylon rope in the absence of Pd precursor and graphene oxide did not induce the color change of rope (Figure S1c, ESI†). Their microstructures are further characterized by scanning electron microscopy (SEM) and transmission electron microscopy (TEM). Compared to the smooth surface of nylon rope (Figure 1c), the corrugated surface of the fibers of PdGN (Figure 1d) indicate the conjugation of graphene with the nylon rope. The TEM image given in Figure 1e exhibits the co-existence of Pd nanocatalysts with a size distribution of 9.74 ± 1.8 nm. Glucose is necessary in formation of PdGN catalysts. It reduces not only the graphene oxide but also the Na₂PdCl₄ salt to form Pd nanoparticles within the PdGN catalysts. The Raman spectrum of the PdGN catalysts (Figure 1g) displays typical Raman peaks of reduced graphene oxides, namely the D-band at 1355 cm⁻¹ and G-band at 1617 cm⁻¹, which confirms the presence of graphene on the nylon rope. A high resolution TEM (HRTEM) study of Pd nanoparticles showed that nanoparticles has a clear crystalline structure (Figure 1f). The crystal domains of nanoparticles have an inter fringe distance of

0.228 nm, which is close to the lattice spacing of the (111) planes of the face-centered cubic Pd crystal (0.223 nm). The XRD patterns of the graphene oxide and PdGN catalysts are shown in Figure 1h. The broad peak centred at 26° for PdGN catalysts further indicates the existence of graphite carbon and confirms the chemical reduction of graphene oxides during the hydrothermal process. The XRD patterns additionally indicate the formation of Pd nanoparticles. The peak centred at 39.91° , 43.6° , 67.9° and 81.8° correspond to the (111), (200), (220), and (311) Bragg reflection, respectively. The presence of rGOs also can be reflected the specific surface area of the catalysts. The measured surface area of $0.057 \text{ m}^2/\text{g}$ for rope-like catalysts was 3.8 times higher than that of nylon rope, suggesting the successful conjugation between nylon rope and graphene. The loading of the reduced graphene oxide in the 3D PdGN catalysts was 6.2 mg/g , which was calculated by the equation shown in the supporting information.

The presence of graphene is also important for the formation of 3D PdGN catalysts. Firstly, it acts as the connector between the noble metal nanoparticles and nylon rope, which increases Pd loading compared with nylon rope. A parallel synthesis to PdGN catalysts was carried out in the absence of graphene oxide, which gave a brown color to the rope (Figure S1d, ESI[†]). Inductively coupled plasma optical emission spectroscopy (ICP-OES) analysis indicates only a small Pd loading of $631 \mu\text{g/g}$, which is 3.1 times lower than that of PdGN catalysts ($1956 \mu\text{g/g}$). Secondly, graphene not only functions as a strong interconnector between the Pd nanoparticles and nylon rope but also enhances the stability of the catalysts. No small broken fragments could be observed upon stretching of the PdGN catalysts (Figure S2 and Video S1, ESI[†]). The Pd nanoparticles anchored and stabilized onto the graphene could depress the bleaching of catalytically active Pd species.³⁷ Thirdly, the presence of graphene can increase the catalytic activity of the noble metal catalyst due to the synergetic composite of the noble metal and graphene, which has been well reported in heterogeneous catalyst system.^{36,38}

The loading of catalytic active Pd nanoparticles can be accurately controlled by varying the length of nylon rope and the initial concentration of Pd precursor. As shown in Figure S3, with 35 mL of Pd^{2+} precursor with a concentration of $280 \mu\text{g/mL}$, the increase of the length of nylon rope from 30 cm to 70 cm led to a decreased Pd loading from $1989 \mu\text{g/g}$ to $1660 \mu\text{g/g}$. Keeping the length of nylon rope of 50 cm and 35 mL of Pd precursor solution, the amount of the loaded Pd linearly increased from $1339 \mu\text{g/g}$ to $3032 \mu\text{g/g}$ with the increase of the initial concentration of Pd^{2+} from $90 \mu\text{g/mL}$ to $470 \mu\text{g/mL}$. In this work, the rope-like catalysts synthesized with 50 cm of nylon ropes in 35 mL of the Pd precursor solution with a concentration of $280 \mu\text{g/mL}$ were used for the SMC reactions.

In continuous-flow synthetic chemistry, high synthetic efficiency is the most important advantages compared with batch processes. Flow velocity and mass/heat transfer are main influence factors for synthetic efficiency. However, they are mutually contradictory for continuous-flow systems. For a specific continuous-flow system, high flow velocity always weakens the mass/heat transfer. Herein, microstructures of PdGN catalysts offer multiple advantages to minimize or solve this contradictory. First of all, the large voids in PdGN catalysts guarantee the high flow rate of the liquid phase. Of importance, the voids in PdGN catalysts become even larger than

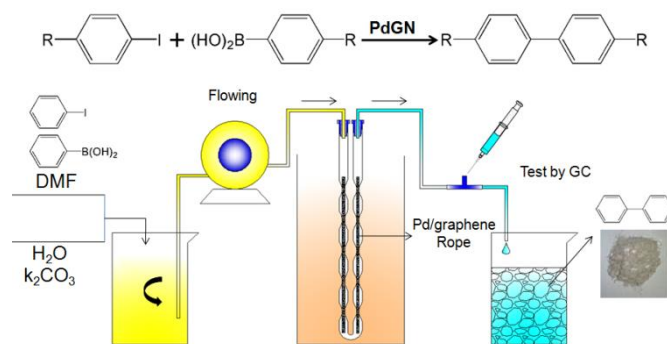


Fig. 2 Schematic representation for the continuous-flow system of Suzuki–Miyaura cross-coupling reactions catalyzed by Pd/graphene/nylon rope. The reaction is performed in a mixture solvent of DMF and water with a volume ratio of 1:1 at 90°C at various flow rates.

Table 1. SMC catalytic activity of catalysts at a flow rate of 20 mL/h

Entry	Catalyst	Loaded Pd (μg)	Conversion (%)	Yield (%)
1	Pd/graphene/nylon rope	489	100.0	97.0
2	Nylon rope	0	0	0
3	Graphene/nylon rope	0	0	0
4	Pd/nylon rope	157.8	19.7	19.0

those of clean nylon rope as shown in Figure 1c and 1d. Hence, more favorable liquid flow within PdGN catalysts is expected. As tested in our system, a flow rate of 300 mL/h did not cause blockage of the reactor. Secondly, the rope-like catalysts can introduce turbulence of the flowing liquids, increasing the possibility of interaction between reactants and Pd nanocatalysts, and assuring more uniformly distributed reactants in the flowing liquid and efficient chemical transfer. Thirdly, high flexibility and mechanical strength of both nylon rope and graphene make PdGN catalysts compatible to any shaped reactors. Moreover, the high chemical and structural stability of both graphene and nylon rope make PdGN catalysts compatible with various solvents and harsh reaction conditions.

The SMC reaction of iodobenzene and phenylboronic acid, as the proof-of-concept demonstration, is used to evaluate the catalytic activity of the PdGN in a continuous-flow system shown in Figure 2. The DMF solution containing iodobenzene, phenylboronic acid, and an aqueous K_2CO_3 solution were mixed completely in a beaker. The mixture was pumped into a homemade U-shaped reactor loaded with PdGN catalysts (Figure S4, ESI[†]). The conversion of the continuous-flow SMC reactions at various conditions is monitored by gas chromatography - mass spectrometry (GC-MS). The inner diameter of the homemade U-shaped reactor is changed regularly. The large inner diameter (4 mm) insures the successful passing of high flow velocity. The small inner diameter (2 mm), similar with the diameter of PdGN rope, improves turbulence of the flowing liquids and the interaction between liquids and Pd nanoparticles and immobilizes the PdGN catalysts in the reactor.

With the initial concentrations of iodobenzene (0.125 M) and phenylboronic acid (0.15 M) in DMF, the conversion of iodobenzene and yield of the biphenyl (confirmed by ^1H NMR spectroscopy, Figure S5, ESI[†]) at different conditions is summarized in Table 1, Table 2 and Figure 3. At a flow velocity of 20 mL/h (Entry 1), the

Table 2. Catalytic activity of PdGN in continuous-flow and batch system** **

Entry	Flow velocity (mL/h)	Residence time (min)	Reactor	Conversion(%)	TON (mol h ⁻¹ mol _{Pd} ⁻¹)	Yield (%)	Productivity (mg h ⁻¹ mg _{Pd} ⁻¹)
5	20	6	Continuous-flow	100.0	542	97.0	764
6	30	4	Continuous-flow	91.9	748	89.1	1052
7	40	3	Continuous-flow	80.9	878	78.7	1239
8	50	2.4	Continuous-flow	69.7	946	64.6	1272
9	60	2	Continuous-flow	58.5	952	54.9	1297
10	70	1.71	Continuous-flow	50.8	965	50.2	1385
11	80	1.50	Continuous-flow	44.2	959	38.5	1211
12	90	1.33	Continuous-flow	40.0	976	36.2	1281
13	20	60	Batch	70.0	379	64.5	508
14	30	60	Batch	47.8	389	46.1	544
15	40	60	Batch	39.9	433	36.6	577
16	50	60	Batch	20.1	273	17.1	336
17	60	60	Batch	16.1	262	12.1	287
18	70	60	Batch	11.9	226	10.0	275
19	80	60	Batch	7.6	167	7.8	245
20	90	60	Batch	6.0	146	5.8	204

* Pd loading is 489 μg for all SMC reactions.

** Equal volume of reactants for continuous-flow synthesis with various flow velocities is used for the corresponded batch experiments.

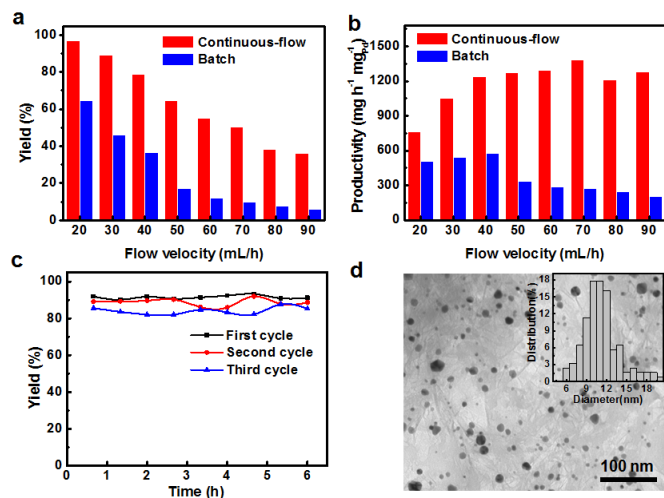


Fig. 3 Catalytic activity of PdGN in the continuous-flow reactor and batch experiments. (a) Plots of biphenyl yields at various flow rates for continuous-flow and batch experiments. (b) Plots of productivities of biphenyl at various flow rates for continuous-flow and batch experiments. (c) Catalytic stability and cyclibility: plots of yields of biphenyl catalyzed by PdGN with a usage time of 6 hours for three cycles. (d) TEM image of Pd nanocatalysts after finishing three cycles of continuous-flow SMC reaction with a duration of 6-hour for each cycle. Inset is the size distribution of Pd nanoparticles.

achieved conversion of iodobenzene reached 100 % with a biphenyl yield of 97.1 % for the PdGN catalysts. The control experiments of nylon rope alone (Entry 2) and graphene/nylon rope (Entry 3) exhibits no catalytic activity towards SMC reaction, indicating the naturally active sites of integrated Pd corresponded to carbon-carbon coupling reactions. Another control experiment of Pd/nylon rope gives a 19.1% conversion and 19.0% yield (Entry 4). The conversion using PdGN catalysts is 5 times higher than Pd/nylon

rope with only 3.1 times Pd loading. The results indicate the presence of graphene can indeed enhance the catalytic activity of Pd catalysts. This can be attributed to the synergetic catalytic effect between the catalytically active component of Pd nanoparticles and functional graphene, in which the rich -OH functional group of graphene donates electron to Pd and accelerates the first step of oxidative addition reaction for SMC reactions.²⁸

To exam the contribution of nylon rope for the catalytic reaction, the Pd/graphene (PdG) catalysts were also prepared in the absence of nylon rope. As-synthesize PdG had a 3D configuration, similar to the previous report.³⁶ For the SMC reaction, the 3D PdG was broken into pieces through sonications. The PdG with equivalent weight to the effective mass of Pd and graphene in PdGN was used. The SMC reactions between iodobenzene and phenylboronic acid catalyzed by PdGN and PdG were evaluated in a glass bottle for 1 h. As shown in Table S1 (ESI[†]), PdG catalysts showed a higher yield (88.9%) of biphenyl compared with PdGN catalysts (79.6%), indicating nylon rope may not contribute to the SMC reactions but function as the 3D skeleton. The relative low yield of product may be attributed to the poor dispersion of the rope-like catalysts compared to the well dispersed PdG catalysts in solution. However, the flow channels were blocked when 3D or broken pieces of PdG catalysts were used for the flow-continuous reaction. Hence, the nylon rope provides a 3D skeleton for the efficient liquid flowing.

Increasing the flow velocities of the reaction solution decreases the conversion of the reactants and the yield of the biphenyl (Entry 5-12), as shown in Table 2 and Figure 3a. For example, the yields of the product were reduced to 89.1%, 54.9% and 36.2% for flow rates of 30, 60 and 90 mL/h, respectively. Such phenomena can be attributed to the shortened duration of contact time between catalysts and reactants and the lower temperature of the reaction solution, as reflected by the decreased residence times with the increased flow velocities. At the lowest flow velocity of 20 mL/h, a residence time

Table 3. Continuous-flow SMC reaction of different reactant^a

Entry	R ₁	R ₂	Product	DMF:H ₂ O ^b	Base	Selectivity (%)	Conversion (%)
21				5:5	K ₂ CO ₃	100	31.4
22				5:5	K ₂ CO ₃	100	61.0 ^c
23				7:5	K ₂ CO ₃	100	100
24				8:5	K ₂ CO ₃	100	33.8
25				5:5	K ₂ CO ₃	100	100
26				5:5	K ₂ CO ₃	100	100
27				10:0	Et ₃ N	100	80.3
28				5:5	K ₂ CO ₃	95.3	92.5
29				5:5	K ₂ CO ₃	100	100
30				5.5:5	K ₂ CO ₃	100	100

^a Unless otherwise noted, the reaction conditions are: R₁ (0.125 M), R₂ (0.15 M), Base (0.375 M) and flow velocity of 20 mL/h, temperature of 90 °C. Pd loading is also 489 μg.

^b The ratio of DMF and H₂O was adjusted to dissolve the reactants completely.

^c The flow velocity is 5 mL/h.

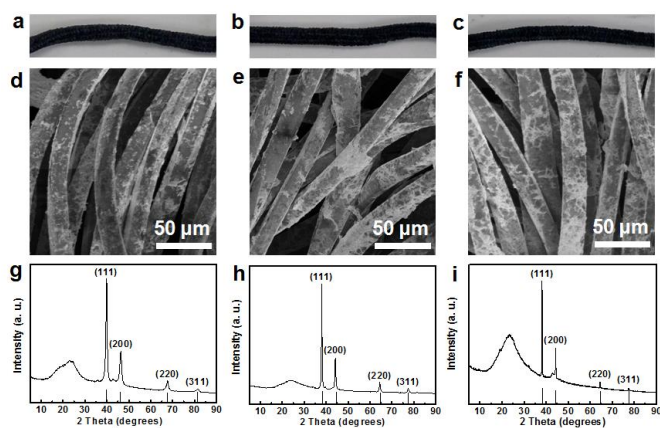


Fig. 4 Structural characterization of noble metal graphene rope catalysts. (a, b and c) Optical images of as-synthesized PtGN, AuGN and AgGN catalysts. (d, e and f) SEM images of PtGN, AuGN, and AgGN catalysts. (g, h and i) XRD patterns of PtGN, AuGN and AgGN catalysts.

of 6 min allows sufficient contact between reactants and Pd nanoparticles and efficient heat transfer between flowing liquid and the surroundings. In contrast, the residence time for a high flow rate of 90 mL/h is only 1.33 min, which may not provide efficient heat transfer to activate the SMC reaction at the expected temperature and also reduce the probability of the collision of reactants with catalytic active sites.

In order to confirm the benefits of PdGN catalysts for a continuous-flow synthesis, the SMC reactions performed through batch reactions (Entry 13-20) were also evaluated. For the batch reaction, the SMC reactions with equal amount of reactants that flew through the continuous-flow reactor within 1 hour were catalyzed by the same PdGN catalysts for 1 hour. As presented in Figure 3a, the catalytic activity for PdGN catalysts in a continuous-flow system, in terms of yield of biphenyl, is much higher than that in the batch synthesis, although the residence times for batch reactions are much longer than those in continuous-flow systems. At the low flow rate of 20 mL/h, the 97.1% yield of biphenyl in continuous-flow reactor is significantly larger than 64.5% in a batch reaction, although the

residence times become longer for the batch synthesis (1 hour). The difference in the catalytic activity of PdGN in the two reaction systems is more apparent when the flow rate is increased. The conversion of iodobenzene for the continuous synthesis at a higher flow rate of 90 mL/h is 40 %, which is 6.67 times higher than that in batch experiments. The calculated turnover number (TON) of PdGN catalysts in the continuous-flow system is 542~976 mol h⁻¹ mol_{Pd}⁻¹, which is 2.3~3.7 times higher than those in Batch (146~433 mol h⁻¹ mol_{Pd}⁻¹). All results clearly demonstrate the high catalytic performance of PdGN catalysts for continuous-flow systems.

To further illustrate the efficiency of PdGN catalysts integrated with continuous-flow systems, the productivities of the continuous-flow systems and batch reactions, calculated by multiplying the yield and the amount of reactants flowing through the catalysts in unit time, are used to characterize the efficiency of the catalytic system. At the flow velocity of 20 mL/h, the calculated productivity of PdGN in the continuous-flow reactor is 764 mg h⁻¹ mg_{Pd}⁻¹. By increasing the flow rates, the productivity clearly shows two distinct regions: initially increased productivity and immediately followed decrease; the maximum productivity of 1385 mg h⁻¹ mg_{Pd}⁻¹ (Entry 10) was obtained at a flow velocity of 70 mL/h. In contrast, the productivity of the corresponding batch synthesis is only 19.86% of the continuous-flow system at a flow velocity of 70 mL/h (Entry 18). As evidenced in Figure 3b, the high productivities of PdGN catalysts integrated into a continuous-flow system unambiguously illustrates the advantages of rationally designed 3D PdGN catalysts for continuous-flow reactions.

To assess the stability of PdGN catalysts, we performed the SMC reaction at a flow rate of 30 mL/h (4 min residence time) up to 6 hours and repeated the experiments three times with the same PdGN catalysts. Figure 3c shows the remarkably stable catalytic activity of PdGN with time of usage, as confirmed by a biphenyl yield of 91.3% after a 6 hours reaction time, which was near to that (91.9 %) at 40 min. The biphenyl yields at the end of the second and third 6-hour cycling were slightly reduced to 88.7% and 85.3%, respectively. The decreased catalytic activity could be explained by the metal bleaching and the morphological evolution of Pd nanocatalysts.^{39,40} The ICP-OES analysis of the reaction solution after the first of cycle

reactions showed a low concentration of 50 ppb, which is much lower than those anchored on silica and polymer substrates previously reported.^{7,41,42} Figure S6 shows the macroscale image of PdGN catalysts after finish three cycles of continuous-flow SMC reaction at a flow rate of 30 mL/h, and there are almost no difference compared with initial PdGN catalysts (Figure 1b). The TEM image of Pd nanoparticles anchored on graphene could clearly show their microscopic changes. Compared with the size of as-synthesized Pd nanoparticles of PdGN (Figure 1e), the larger nanoparticles over 15 nm and the bigger average size of 10.9 ± 2.7 nm (Figure 3d) may response to the slightly reduced activity of PdGN catalysts.^{39,40} Nevertheless, properly designed PdGN catalysts show the remarkable ability to reserve the catalytically active Pd species within the catalysts, compared to previous reports of Pd-loaded silica and polymers.⁴³⁻⁴⁵

With the present catalytic system, the scope of the continuous-flow SMC reactions with various aryl halides and phenylboronics was investigated at 20 mL/h (Table 3). Bromobenzene, another common aryl halide for the SMC reaction, was evaluated in this catalytic system. The conversion was 31.4% at a flow velocity of 20 mL/h (Entry 21), which was much lower than that of iodobenzene. Decreasing the flow velocity to 5 mL/h, the conversion of bromobenzene was improved to 61.0% (Entry 22). This can be ascribed to the lower reactivity of bromobenzene for SMC reaction compared to iodobenzene. The productivity also reached to $120 \text{ mg h}^{-1} \text{ mg}_{\text{Pd}}^{-1}$ at a flow rate of 5 mL/h. Notably, the conversion of iodobenzene with electron donating functional groups (OCH_3 and CH_3 , Entry 25 and 26) and weak electron withdrawing functional group (CHO , Entry 23) reached 100% conversion with 100% selectivity. Because of the strong electron withdrawing effect of $-\text{NO}_2$, the conversion of 4-iodonitrobenzene was 33.75% (Entry 24). Meanwhile, the alternatives of phenylboronics with both electron-donating groups (CH_3 and $t\text{-Bu}$) and electron withdrawing substituents (CHO and phenyl) exhibited high catalytic activity and selectivity for the SMC reactions (Entry 27-30).

The synthetic strategy for PdGN catalysts also can be explored as a general approach towards metal nanocatalysts/graphene/nylon rope catalysts with a 3D configuration. The synthesis of PtGN, AuGN, and AgGN was performed under similar conditions as PdGN, except the NaPdCl_4 was replaced by H_2PtCl_6 , HAuCl_4 and AgNO_3 , respectively. The black color of as-synthesized ropes (Figure 4a-c) indicates the successful conjugations of graphene and nylon ropes. They displayed similar 3D morphological features as PdGN, as presented in the SEM images (Figure 4d-f). Compared to the smooth surface of nylon rope (Figure 2c), the corrugated surface of the fibers further confirms the formation of 3D frameworks of the rope-like catalysts. The XRD patterns (Figure 4 g-i) and TEM images (Figure S7, ESI†) indicate the formation of Pt, Au, and Ag nanoparticles. ICP-OES results additionally exhibited Pt, Au, and Ag loadings of $1766 \mu\text{g/g}$, $1236 \mu\text{g/g}$ and $2465 \mu\text{g/g}$ in the 3D catalysts, respectively. Similar to PdGN, the loading of the noble metal nanocatalysts in the presence of graphene was dramatically larger than that in the absence of graphene, as shown in Table S2 (ESI†).

Chemical reduction of 4-nitrophenol was used to prove the presence of the noble metal in the 3D graphene/nylon rope and evaluate their catalytic activity for the continuous-flow system. This reaction is one of the model reactions for evaluating the catalytic

activity of various noble metal nanoparticles, such as Ag, Au, and Pd, in different substrates.⁴⁶⁻⁴⁸ The reaction was performed using the same system as shown in Figure 2 with initial concentrations of 4-nitrophenol (1 mM) and NaBH_4 (50 mM). As shown in Figure 5a, the 4-nitrophenol could not be reduced by nylon rope and graphene/nylon rope, while all of the noble metal/graphene nylon ropes show excellent catalytic activity for the reduction of 4-nitrophenol. Although the catalytic activities are different, the stability of all these noble metal/graphene/nylon rope catalysts are remarkable. Figure 5b shows the remarkably stable catalytic activity of noble metal/graphene/nylon ropes with a time of 6.5 h. The conversion for all noble metal/graphene/nylon ropes are slightly reduced by less than 5%. The ICP-OES analysis of the reaction solution shows a low concentration of 5.99 ppb (Pd), 10.79 ppb (Pt), 2.30 ppb (Au) and 2.35 ppb (Ag), further confirming that graphene can reduce metal bleaching. Therefore, these noble metal/graphene/nylon ropes have a wide range of potential applications in the organic continuous-flow reaction.

Conclusions

In summary, 3D noble metal/graphene/nylon ropes functioning as heterogeneous catalysts for continuous-flow systems have been successfully synthesized by a one-step hydrothermal method at 120°C . Chemically inert nylon rope provides a 3D framework for macroassembled noble metal/graphene with voids of tens of microns for sufficient chemical transfer at high flow rates of reaction solution. Graphene has multiple functions, including acting as the interconnector between the noble metal species and nylon rope, enhancing the structural stability and mechanical strength of the noble metal/graphene rope, and increasing the catalytic activity and stability of noble metal nanocatalysts. PdGN catalysts show a high catalytic activity, productivity, and stability for continuous-flow SMC reactions compared with traditional batch reactions. The catalytic activity and stability for other noble metal/graphene/nylon rope catalysts is also demonstrated by the reduction of 4-nitrophenol. The current microfluidic continuous-flow systems integrated with 3D NMGN catalysts have the potentials for practical applications and can be extended to many important chemical reactions catalyzed by noble metal.

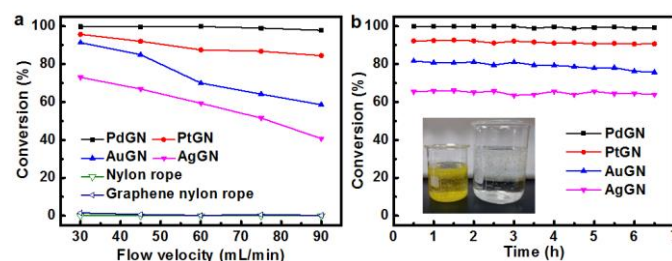


Fig. 5 Catalytic activity and stability of noble metal/graphene/nylon rope catalysts for reduction of 4-nitrophenol in the continuous-flow reactor. (a) Catalytic tests of the reduction rate for the reduction of 4-nitrophenol with different noble metal/graphene/nylon ropes at different flow velocities. (b) Catalytic stability: plots of conversion of 4-nitrophenol catalyzed by different noble metal/graphene/nylon ropes with a usage time of 6.5 hours. Inset shows the color change indicating the reduction of 4-nitrophenol to 4-aminophenol.

Acknowledgements

We acknowledge the financial support from a National Natural Science Foundation of China 21201138. This work was also partially funded by the Ministry of Science and Technology of China through a 973-program under Grant 2012CB619401 and supported by "the Fundamental Research Funds for the Central Universities" (xjj2013102 and xjj2013043). Technical supports for TEM experiments from Frontier Institute of Science and Technology and State Key Laboratory for Mechanical Behavior of Materials, Xi'an Jiaotong University, are also acknowledged.

Notes and references

^a Center of Applied Chemical Research, Frontier Institute of Science and Technology, Xi'an Jiaotong University, Xi'an, China 710049. E-mail: yongquan@mail.xjtu.edu.cn; yyma@mail.xjtu.edu.cn

^b State Key Laboratory for Mechanical Behavior of Materials, Xi'an Jiaotong University, Xi'an, China, 710049.

† Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data. Electronic Supplementary Information (ESI) available: [Experimental details, more characterizations of catalysts; ¹H-NMR spectrum]. See DOI: 10.1039/b000000x/

- Lévesque, F.; Seeberger, P. H. *Angew. Chem. Int. Ed.* 2012, **51**, 1706-1709.
- Webb, D.; Jamison, T. F. *Chem. Sci.* 2010, **1**, 675-680.
- Pastre, J. C.; Browne, D. L.; Ley, S. V. *Chem. Soc. Rev.* 2013, **42**, 8849-8868.
- Marre, S.; Jensen, K. F. *Chem. Soc. Rev.* 2010, **39**, 1183-1202.
- Zhang, L.; Xia, Y. *Adv. Mater.* 2014, **26**, 2600-2606.
- Kim, H.; Nagaki, A.; Yoshida, J.-i. *Nat. Commun.* 2011, **2**, 264.
- Wegner, J.; Ceylan, S.; Kirschning, A. *Chem. Commun.* 2011, **47**, 4583-4593.
- Hartman, R. L.; McMullen, J. P.; Jensen, K. F. *Angew. Chem. Int. Ed.* 2011, **50**, 7502-7519.
- Tsubogo, T.; Ishiwata, T.; Kobayashi, S. *Angew. Chem. Int. Ed.* 2013, **52**, 6590-6604.
- Wiles, C.; Watts, P. *Chem. Commun.* 2011, **47**, 6512-6535.
- Hartman, R. L.; Jensen, K. F. *Lab on a Chip* 2009, **9**, 24952507.
- Ducry, L.; Roberge, D. M. *Angew. Chem.* 2005, **117**, 8186-8189.
- Theberge, A. B.; Whyte, G.; Frenzel, M.; Fidalgo, L. M.; Wootton, R. C.; Huck, W. T. *Chem. Commun.* 2009, 6225-6227.
- Worrell, B.; Malik, J.; Fokin, V. *Science* 2013, **340**, 457-460.
- Shu, W.; Pellegatti, L.; Oberli, M. A.; Buchwald, S. L. *Angew. Chem.* 2011, **123**, 10853-10857.
- Wang, N.; Matsumoto, T.; Ueno, M.; Miyamura, H.; Kobayashi, S. *Angew. Chem.* 2009, **121**, 4838-4840.
- Yin, L.; Liebscher, J. *Chem. Rev.* 2007, **107**, 133-173.
- Gniewek, A.; Ziolkowski, J. J.; Trzeciak, A. M.; Zawadzki, M.; Grabowska, H.; Wrzyszczyk, J. *J. Catal.* 2008, **254**, 121-130.
- Alza, E.; Rodríguez - Escrich, C.; Sayalero, S.; Bastero, A.; Pericàs, M. A. *Chem. Eur. J.* 2009, **15**, 10167-10172.
- Yasukawa, T.; Miyamura, H.; Kobayashi, S. *J. Am. Chem. Soc.* 2012, **134**, 16963-16966.
- Noël, T.; Buchwald, S. L. *Chem. Soc. Rev.* 2011, **40**, 5010-5029.
- Ranganath, K. V.; Schäfer, A. H.; Glorius, F. *ChemCatChem* 2011, **3**, 1889-1891.
- Shore, G.; Morin, S.; Organ, M. G. *Angew. Chem.* 2006, **118**, 2827-2832.
- Georgakilas, V.; Otyepka, M.; Bourlinos, A. B.; Chandra, V.; Kim, N.; Kemp, K. C.; Hobza, P.; Zboril, R.; Kim, K. S. *Chem. Rev.* 2012, **112**, 6156-6214.
- Li, C.; Shi, G. *Nanoscale* 2012, **4**, 5549-5563.
- Xue, T.; Peng, B.; Xue, M.; Zhong, X.; Chiu, C.-Y.; Yang, S.; Qu, Y.; Ruan, L.; Jiang, S.; Dubin, S. *Nat. Commun.* 2014, **5**.
- Xue, T.; Jiang, S.; Qu, Y.; Su, Q.; Cheng, R.; Dubin, S.; Chiu, C. Y.; Kaner, R.; Huang, Y.; Duan, X. *Angew. Chem.* 2012, **124**, 3888-3891.
- G. M. Scheuermann, L. Rumi, P. Steurer, W. Bannwarth and R. Mülhaupt, *J. Am. Chem. Soc.*, 2009, **131**, 8262-8270.
- Huang, X.; Qi, X.; Boey, F.; Zhang, H. *Chem. Soc. Rev.* 2012, **41**, 666-686.
- Nishina, Y.; Miyata, J.; Kawai, R.; Gotoh, K. *RSC Advances* 2012, **2**, 9380-9382.
- Li, Y.; Fan, X.; Qi, J.; Ji, J.; Wang, S.; Zhang, G.; Zhang, F. *Nano Research* 2010, **3**, 429-437.
- Zhang, P.; Gong, Y.; Li, H.; Chen, Z.; Wang, Y. *Nat. Communications* 2013, **4**, 1593.
- Nardecchia, S.; Carriazo, D.; Ferrer, M. L.; Gutiérrez, M. C.; del Monte, F. *Chem. Soc. Rev.* 2013, **42**, 794-830.
- Cong, H.-P.; Ren, X.-C.; Wang, P.; Yu, S.-H. *ACS Nano* 2012, **6**, 2693-2703.
- Wu, Z.-Y.; Li, C.; Liang, H.-W.; Chen, J.-F.; Yu, S.-H. *Angew. Chem. Int. Ed.* 2013, **52**, 2925-2929.
- Tang, Z.; Shen, S.; Zhuang, J.; Wang, X. *Angew. Chem. Int. Ed.* 2010, **49**, 4603-4607.
- Jin, Z.; Nackashi, D.; Lu, W.; Kittrell, C.; Tour, J. M. *Chem. Mater.* 2010, **22**, 5695-5699.
- Kou, R.; Shao, Y.; Wang, D.; Engelhard, M. H.; Kwak, J. H.; Wang, J.; Viswanathan, V. V.; Wang, C.; Lin, Y.; Wang, Y.; Aksay, I. A.; Liu, J. *Electrochem. Commun.* 2009, **11**, 954-957.
- Narayanan, R.; El-Sayed, M. A. *J. Am. Chem. Soc.* 2003, **125**, 8340-8347.
- Li, Y.; Boone, E.; El-Sayed, M. A. *Langmuir* 2002, **18**, 4921-4925.
- Shore, G.; Morin, S.; Organ, M. G. *Angew. Chem.* 2006, **118**, 2827-2832.
- Ceylan, S.; Friese, C.; Lammel, C.; Mazac, K.; Kirschning, A. *Angew. Chem. Int. Ed.* 2008, **47**, 8950-8953.
- Molnar, A. *Chem. Rev.* 2011, **111**, 2251-2320.
- Das, D. D.; Sayari, A. *J. Catal.* 2007, **246**, 60-65.
- Wang, P.; Lu, Q.; Li, J. *Catal. Lett.* 2009, **131**, 444-450.
- Liu, B.; Wang, Q.; Yu, S.; Zhao, T.; Han, J.; Jing, P.; Hu, W.; Liu, L.; Zhang, J.; Sun, L. D.; Yan, C. H. *Nanoscale* 2013, **5**, 9747-9757.
- Baruah, B.; Gabriel, G. J.; Akbashev, M. J.; Boohar, M. E. *Langmuir* 2013, **29**, 4225-4234.
- Gangula, A.; Podila, R.; M, R.; Karanam, L.; Janardhana, C.; Rao, A. M. *Langmuir* 2011, **27**, 15268-15274.