

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

Porous Ge@C materials via Twin polymerization of germanium(II) salicyl alcoholates for Li-ion batteries

P. Kitschke,^a M. Walter,^b T. Ruffer,^c A. Seifert,^d F. Speck,^e T. Seyller,^e S. Spange,^d H. Lang,^c A. A. Auer,^f M. V. Kovalenko^b and M. Mehring^{*a}

Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

The germynes, germanium(II)-2-(oxidomethyl)phenolate (**1**), germanium(II)-4-methyl-2-(oxidomethyl)phenolate (**2**) and germanium(II)-4-bromo-2-(oxidomethyl)phenolate (**3**) were synthesized and their thermally induced twin polymerization to give organic-inorganic hybrid materials was studied. The compounds **1** – **3** form oligomers including dimers, trimers and tetramers as a result of intermolecular coordination of the benzylic oxygen atom to germanium. The structural motifs were studied by single crystal X-ray diffraction analysis and DFT-D calculations. Thermally induced twin polymerization of these germynes gave hybrid materials based on germanium-containing phenolic resins. Carbonization of these resins under reductive conditions resulted in porous materials that are composed of germanium and carbon (Ge@C materials), while oxidation with air provided non-porous germanium dioxide. The porous Ge@C materials were tested as potential anode materials for rechargeable Li-ion batteries. Reversible capacities of 540 mAhg⁻¹ were obtained at a current density of 346 mA g⁻¹ without apparent fading for 100 cycles, which demonstrates that germanium is well accessible in the hybrid material.

Introduction

The chemistry of low valent germanium compounds has been studied intensely within the last four decades, starting with the pioneering work of Curtis, Lappert and Satgé and their coworkers at the 1970s.¹⁻⁵ The early studies mainly focused on the use as ligands in transition metal complexes,^{2, 6-10} the reactivity in organogermanium chemistry^{5, 11-13} and fundamental characterization.¹⁴⁻¹⁶ While research on germynes e.g., as model compounds in addition reactions such as of germanium into N-H and P-Cl bonds, progressed rapidly,¹⁷⁻²⁷ studies focusing on applications e.g., in catalysis²⁸ or as precursors for atomic layer deposition,²⁹ have rarely been reported until now. Quite recently molecular germanium(II) compounds were used to prepare germanium-based anode materials for Li-ion batteries,³⁰⁻³² motivated by the fact that germanium is a highly promising anode material considering its high gravimetric and volumetric theoretical capacities (1384

mAhg⁻¹ / 7367 AhL⁻¹ for Li₁₅Ge₄), high electrical conductivity and lithium-ion diffusivity.³³⁻⁴¹ Nevertheless, bulk germanium shows only poor cycling stability due to the large volume changes of up to 246% upon lithiation and delithiation. Nanostructuring of germanium has been reported as effective method to improve both cycling stability and rate capability,⁴²⁻⁵¹ and following this concept starting from GeI₂³⁰ or diphenyl germylene,^{31, 32} anode materials exhibiting promising capacity retentions were synthesized. Intrigued by this approach, we decided to adopt the novel concept of twin polymerization (TP) to germynes. TP is defined as a concerted formation of two polymers in one synthetic step starting from a single monomer (twin monomer) and provides a simple method to obtain nanostructured hybrid materials that can be converted into highly porous materials.⁵²⁻⁶⁰ Diverse metal salicyl alcoholates (M = Si, Ge and Sn) have been demonstrated to provide nanostructured organic-inorganic hybrid materials by this novel concept.^{52, 61-64} Conversion of such hybrid materials gave e.g., mesoporous metal oxides,^{61, 62} microporous carbon⁶² and mesoporous / microporous nanocomposites such as Sn@C/SiO₂.⁶³ We anticipated that porous materials composed of germanium incorporated in a carbon matrix (Ge@C material) are accessible by applying the concept of twin polymerization to the germanium(II) salicyl alcoholates **1** – **3** (Scheme 1). Ge@C materials are expected to meet requirements such as exhibiting a high capacity and a good cycling stability for anode materials of advanced Li-ion batteries.³⁴ Recently, we reported on the synthesis of germanium(II)-2-(*tert*-butyl)-4-methyl-6-(oxidomethyl)phenolate (**4**), a germanium(II) salicyl alcoholate, which is, however, not suitable for TP.⁶⁵ The *tert*-butyl and methyl substituents at the aromatic moiety of **4** hamper the formation of the phenolic resin resulting in

^a Technische Universität Chemnitz, Fakultät für Naturwissenschaften, Institut für Chemie, Professur Koordinationschemie, 09107 Chemnitz (Germany). Email: michael.mehring@chemie.tu-chemnitz.de


^b Eidgenössische Technische Hochschule Zürich, Department of Chemistry and Applied Biosciences, Laboratory of Inorganic Chemistry, Vladimir-Prelog-Weg 1, 8093 Zürich (Switzerland) and Empa-Swiss Federal Laboratories for Materials Science and Technology, Laboratory for thin films and photovoltaics, Überlandstraße 129, 8600 Dübendorf, (Switzerland).

^c Technische Universität Chemnitz, Fakultät für Naturwissenschaften, Institut für Chemie, Professur Anorganische Chemie, 09107 Chemnitz (Germany)

^d Technische Universität Chemnitz, Fakultät für Naturwissenschaften, Institut für Chemie, Professur Polymerchemie, 09107 Chemnitz (Germany)

^e Technische Universität Chemnitz, Fakultät für Naturwissenschaften, Institut für Physik, Professur Experimentalphysik mit dem Schwerpunkt Technische Physik, 09107 Chemnitz (Germany)

^f Max-Planck-Institut für Chemische Energiekonversion, Stiftsstraße 34-36, 45470 Mülheim an der Ruhr (Germany).

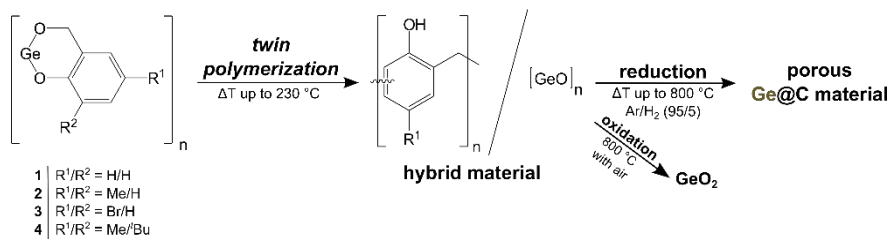

Scheme 1 Illustration of the basic structural motif of the germynes **1** - **4** ($n = 2 - 4$) and the concept for the synthesis of e.g. a porous Ge@C material for rechargeable Li-ion batteries starting from **1** - **3** according to the concept of twin polymerization followed by reduction of the hybrid material.

oligomeric structures rather than polymers upon thermal treatment. However, the new germynes, germanium(II)-2-(oxidomethyl)phenolate (**1**), germanium(II)-4-methyl-2-(oxidomethyl)phenolate (**2**) and germanium(II)-4-bromo-2-(oxidomethyl)phenolate (**3**) are well suited for TP due to the lack of a substituent in the *ortho* position of their phenolate moieties. Moreover, the substituent in the *para* positions of their phenolate moieties possess distinguishable steric and electronic features, which is expected to influence their reactivity towards TP as reported for spirocyclic salicyl alcoholates recently.⁶² Characterization including single crystal X-ray diffraction analysis and DFT-D calculations, and studies on their reactivity in TP using differential scanning calorimetry (DSC) are presented. The as-obtained germanium-containing phenolic resin hybrid materials (**HM-1** - **HM-3**) and the consecutively synthesized GeO₂ and Ge@C materials were characterized by analytical techniques such as solid state NMR spectroscopy (**HM-1** - **HM-3**), X-ray photoelectron spectroscopy (XPS), infrared (IR), Raman and energy-dispersive X-ray (EDX) spectroscopy, powder X-ray diffraction (PXRD), nitrogen-sorption measurements and CHN analysis. Ge@C materials as obtained starting from germylene **1** were tested as anode materials for rechargeable Li-ion batteries and their performance is discussed.


Results

Synthesis and Characterization of germynes

The germynes **1** - **3** were prepared according to the synthesis protocol of **4**⁶⁵ starting from Ge[N(SiMe₃)₂]₂ and the respective salicyl alcohol with yields in the range from 64 % to 73 %. Poor solubility in non-polar solvents was observed for germylene **3**, whereas the compounds **1** and **2** are soluble in all common organic solvents. ¹H NMR and ¹H-¹³C{¹H} HSQC NMR spectroscopic analysis of freshly prepared solutions of the germynes **1** - **3** in d₈-THF at ambient temperature gave broad resonance signals (five signals for **1** and **2** in each case, and four signals for **3**) indicating a dynamic coordination behavior including oligomeric species, presumably dominated by their monomers. Single crystals suitable for X-ray diffraction analysis were obtained from saturated diethyl ether solutions of the germynes **1** and **2**, from a saturated 1,4-dioxane solution of **3** and from the cloudy reaction mixture (7:4 mixture of *n*-pentane and diethyl ether) containing compound **1** after filtration and slow evaporation of the volatile solvents, respectively. In case of germylene **1**, a trimer (crystallization from diethyl ether) and a tetramer (crystallization from the reaction mixture) were

obtained in the solid state, whereas the compounds **2** and **3** form dimers. Noteworthy, a trimer was previously determined for germylene **4** upon crystallization from a saturated diethyl ether solution, whereas in CDCl₃ solution an equilibrium between the trimer and the dimer/tetramer was observed.⁶⁵ Thus, the presence of different oligomers of the compounds **1** - **3** in solution is presumed. DFT-D calculations support this assumption,

which is in accordance with the relative formation energies of their oligomers (Scheme 2). The formation of the tetramers was calculated to be energetically slightly favored in comparison with the corresponding trimer formation, whereas the dimers are energetically less favored. However, the small energy differences between the oligomers, especially between their trimers and tetramers, support the assumption that they are in a chemical equilibrium in solution.

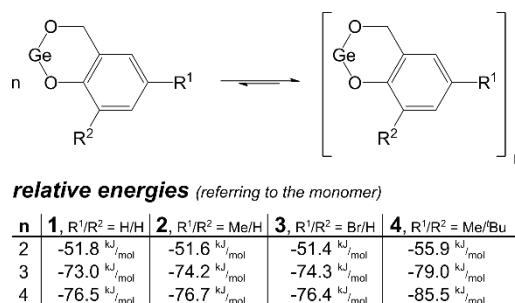

Scheme 2 Illustration of the equilibrium between oligomers of **1** - **4** in solution (top) and relative energies of the respective oligomers (bottom) calculated on the B3LYP-D3/def2-TZVPP level of theory with regard to the respective monomers.

Compound **1** crystallizes in the monoclinic space group $P2_1/n$ and forms trimers (**1**)₃ in the solid state. The molecular structure is given in Figure 1 and selected bond lengths and bond angles are presented in the caption of this figure. Details of the structure determination are summarized in Table 3.

The trimer (**1**)₃ possesses a similar molecular structure as reported for (**4**)₃.⁶⁵ A distorted boat conformation of a six-membered -[Ge-O]₃ ring with three-coordinated germanium atoms, one terminal phenolic oxygen atom and two bridging benzylic oxygen atoms, is observed. The germanium oxygen bond lengths [O_{Aryl}-Ge bonds: 1.8408(19) Å - 1.848(2) Å, O_{Alkyl}-Ge bonds: 1.939(2) Å - 1.988(2) Å] are in the typical ranges reported for Ge-O bonds in compounds with a threefold pyramidal coordination of low valent germanium.⁶⁶⁻⁶⁸ The values reported for the germanium oxygen bonds for (**4**)₃ [O_{Aryl}-Ge bonds: 1.829(2) Å - 1.890(2) Å, O_{Alkyl}-Ge bonds: 1.945(2) Å - 2.044(2) Å] resemble those in (**1**)₃ but are slightly longer (with the exception of Ge3-O5: 1.8447(19) Å for (**1**)₃ and 1.829(3) Å for (**4**)₃) due to sterically more demanding substituents at the aromatic moieties in (**4**)₃.⁶⁵

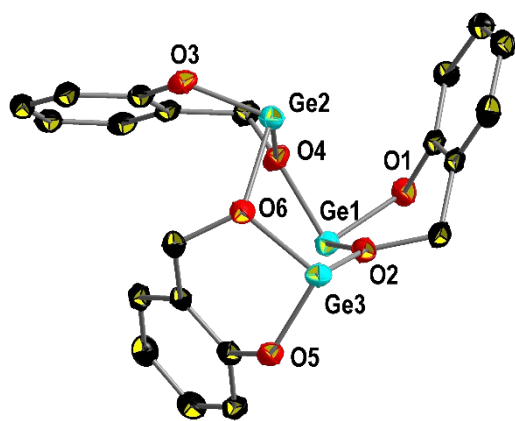


Figure 1 Molecular structure of $(1)_3$ in the solid state. Thermal ellipsoids are drawn with 50% probability. Hydrogen atoms are omitted for clarity. Selected bond lengths [Å] and bond angles [°]: Ge1-O1 1.8408(19), Ge1-O2 1.986(2), Ge1-O4 1.975(2), Ge2-O3 1.848(2), Ge2-O4 1.939(2), Ge2-O6 1.988(2), Ge3-O2 1.988(2), Ge3-O5 1.8447(19), Ge3-O6 1.951(2); Ge1-O4-Ge2 128.28(11), Ge2-O6-Ge3 115.94(10), Ge1-O2-Ge3 132.48(10), O1-Ge1-O2 92.45(9), O1-Ge1-O4 92.50(9), O2-Ge1-O4 86.80(9), O3-Ge2-O4 91.35(9), O3-Ge2-O6 97.57(9), O4-Ge2-O6 88.82(8), O2-Ge3-O5 97.60(8), O2-Ge3-O6 86.64(8), O5-Ge3-O6 92.77(9).

The shorter Ge1-O2 [1.986(2) Å], Ge3-O6 [1.951(2) Å] and Ge2-O4 [1.939(2) Å] bonds in comparison to the Ge1-O4 [1.975(2) Å], Ge3-O2 [1.988(2) Å] and Ge2-O6 [1.988(2) Å] bond lengths, respectively, indicate secondary bonding of O4→Ge1, O6→Ge2 and O2→Ge3 stabilizing the low valent species.

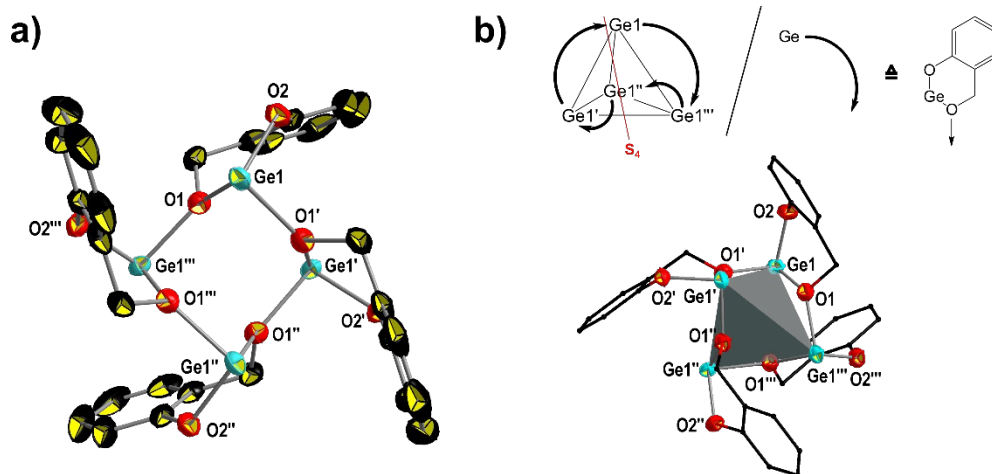


Figure 2 Molecular structure $\alpha-(1)_4$ a) in the solid state and b) with salicylic alcoholate moieties depicted in wireframe style and the tetrahedron spanned by the germanium atoms highlighted in grey. The scheme in b) illustrates the coordination pattern of the bridging benzylic oxygen atoms as indicated by the direction of the arrows. Thermal ellipsoids are drawn with 50% probability. Hydrogen atoms are omitted for clarity. Selected bond lengths [Å] and bond angles [°]: Ge1-O1 1.987(3), Ge1-O2 1.884(3) and Ge1-O1' 2.025(3); Ge1-O1-Ge1' 126.37(16), O1-Ge1-O2 91.36(13), O1-Ge1-O1' 85.29(14) and O2-Ge1-O1' 94.14(12). Symmetry transformations used to generate equivalent atoms: ' = $x-0.5, -y+1.5, -z+0.5$; '' = $-x+2, -y+1, z$; ''' = $-x+1.5, y+0.5, -z+0.5$.

Additionally, the small O-Ge-O bond angles of the salicylic moieties [O1-Ge1-O2 92.45(9)°, O3-Ge2-O4 91.35(9)° and O5-Ge3-O6 92.77(9)°] and the angles \angle O4-O1Ge1O2 89.337(3)°, \angle O2-O5Ge3O6 92.840(2)° and \angle O6-O3Ge2O4 94.408(3)° are in agreement with low valent germanium atoms possessing a stereochemically active lone pair of electrons and donation of electron density from the bridging benzylic oxygen atoms (O4→Ge1, O6→Ge2 and O2→Ge3) into the vacant p-orbitals.

The tetramer $[2 \cdot (1)_4 \cdot n\text{-pentane}]$ crystallizes in the tetragonal space group $I-4$ exhibiting two crystallographically independent tetramers, $\alpha-(1)_4$ and $\beta-(1)_4$, which show similar structural motifs (Figure S1) and thus only $\alpha-(1)_4$ is discussed. The molecular structure of $\alpha-(1)_4$ is given in Figure 2 and selected bond lengths and bond angles are presented in the caption of this figure. Details of the structure determination are summarized in Table 3. Tetramer $\alpha-(1)_4$ consists of four equivalent monomeric building blocks of **1** that can be superimposed as a result of a S_4 axis (Figure 2b). The core units of the tetramer shows an eight-membered $[\text{Ge-O}]_4$ ring in which the germanium atoms span a distorted tetrahedron (Figure 2b). The germanium atoms are three-coordinate by one terminal phenolic oxygen atom and two bridging benzylic oxygen atoms. The Ge1-O1 [1.987(3) Å] bond length is shorter than the Ge1-O1' [2.025(3) Å] bond indicating secondary bonding of O→Ge that stabilizes the low valent germanium atoms. The small deviations in the bond lengths and bond angles between $\alpha-(1)_4$ and $\beta-(1)_4$ may result from crystal packing due to the presence of one molecule n -pentane in the unit cell. Please note, when $2 \cdot (1)_4 \cdot n\text{-pentane}$ is slowly heated, a reconstruction of the framework to give $(1)_3$ and release of the n -pentane were observed by temperature-dependent PXRD and thermogravimetric analysis (TGA), respectively (Figure S2 and S3). In addition, ^1H NMR spectroscopic analysis in CDCl_3 at -60°C gave two sets of signals that are assigned to the trimer

$(1)_3$ and the tetramer $(1)_4$. The observation of only one set of signals for the tetramer of **1** indicates that $\alpha-(1)_4$ and $\beta-(1)_4$ relax in their geometries to result in a single tetrameric structure in solution (Figure S4).

The dimer $(2)_2$ crystallizes in the triclinic space group $P\bar{1}$. The molecular structure of $(2)_2$ is depicted in Figure 3 and selected bond lengths and bond angles are presented in the caption of this figure. Details of the structure determination are summarized in Table 3. A similar

structure to $(2)_2$ was determined for $(3)_2$ (Figure S5), and therefore, only the molecular structure of $(2)_2$ is briefly discussed. The dimer $(2)_2$ exhibits C_i symmetry with a center of inversion located in the plane spanned by the Ge1, O2, Ge1' and O2' atoms. The equivalent benzylic oxygen atoms O2 and O2' bridge the germanium atoms, which exhibit a threefold pyramidal coordination. The germanium oxygen bond lengths and bond angles are in agreement with the values determined for $(1)_3$, $(1)_4$ and $(4)_3$ and thus are not further discussed.⁶⁵


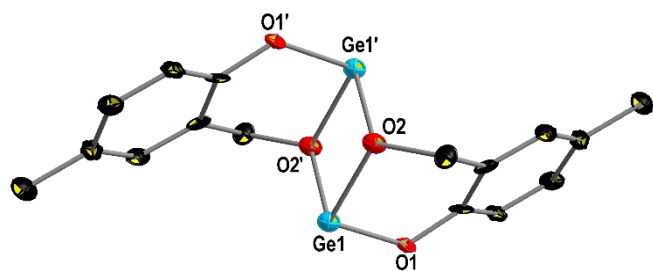


Figure 3 Molecular structure of $(2)_2$ in the solid state. Thermal ellipsoids are drawn with 50% probability. Hydrogen atoms are omitted for clarity. Selected bond lengths [Å] and bond angles [°]: Ge1-O1 1.862(7), Ge1-O2 1.986(6), Ge1-O2' 1.966(7); Ge1-O2-Ge1' 104.6(3), O1-Ge1-O2 91.6(3), O1-Ge1-O2' 94.9(3), O2-Ge1-O2' 75.4(3). Symmetry transformations used to generate equivalent atoms: ' = -x, -y+1, -z+1.

Twin polymerization

Thermally induced twin polymerization of the germylenes **1** - **3** resulted in the formation of germanium-containing phenolic resin hybrid materials. According to the concept of TP the idealized structural motif of the hybrid material is illustrated by Equation (1).

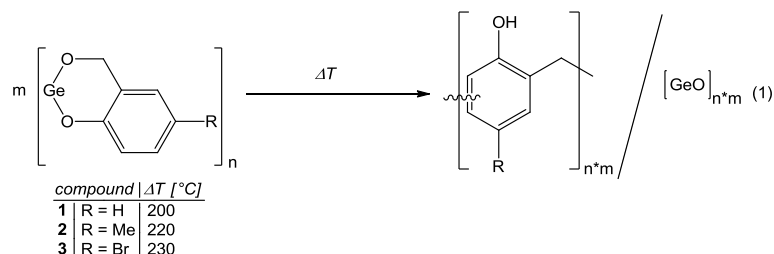

The molecular structures of the compounds **2** and **3**, exhibiting a substituent in *para* position to the phenolic oxygen atom, favor the *ortho/ortho'* connectivity of the bridging methylene groups interconnecting the benzene rings in the phenolic resin as obtained after polymerization. By contrast, precursor **1** allows additional *ortho/para'* connectivity. It is noteworthy that our attempts to obtain polymeric hybrid materials by proton induced twin polymerization as reported for other metal salicyl alcoholates (M = Si, Ge and Sn)^{61, 62, 64} failed. However, thermally induced twin polymerization is feasible as it is outlined in the following section.

Studies on the reactivity

Studies on the reactivity of the compounds **1** - **3** regarding the process of thermally induced TP were performed by differential scanning calorimetry (DSC) measurements up to 300 °C. The thermograms starting from amorphous materials are depicted in Figure 4. The compounds **1** - **3** do not melt and the DSC curves show exothermic processes, which are assigned to thermally induced TP. The onset temperatures are 102 °C (**1**), 163 °C (**2**) and 151 °C (**3**). Two distinguishable minima at 110 °C and 145 °C for **1**, 183 °C and 194 °C for **2**, and 161 °C and 200 °C for **3** indicate that different formation processes take place at specific temperatures during the polymerization processes e.g.,

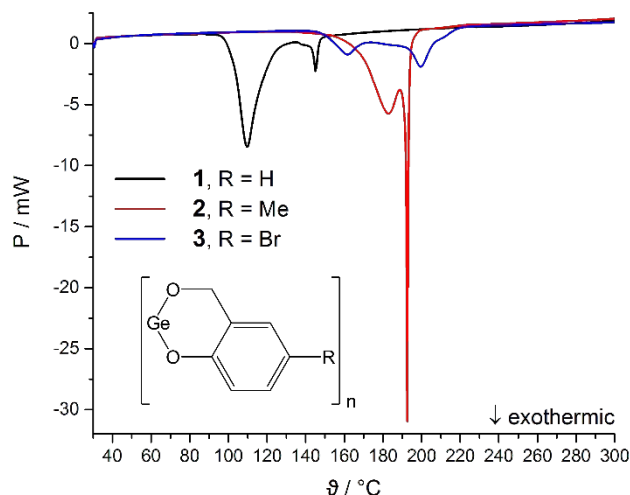


Figure 4 Differential scanning calorimetry of the amorphous materials of the germylenes **1** (black curve), **2** (red curve) and **3** (blue curve); heating rate 10 K min⁻¹, N₂ atmosphere, N₂ volume flow 50 mL min⁻¹.

formation of the phenolic resin and/or condensation to give the final germanium-containing resin. The observation of two minima in all DSC experiments indicate that the polymerization follows similar reaction processes for **1** - **3**, but the compounds show a different reactivity. However, the order of the onset temperatures does not follow the electronic and steric features of the substituents as was expected based on previous reports for spirocyclic silicon salicyl alcoholates.⁶² Thus, we conclude that the nature of the substituents in **1** - **3** plays a minor role for the initiation process here. This assumption is further supported by comparison of the onset temperatures of the polymerization process for amorphous **1** (102 °C) and the crystalline materials $(1)_3$ (142 °C) and $2 \cdot (1)_4 \cdot n$ -pentane (119 °C) (Figure 5).

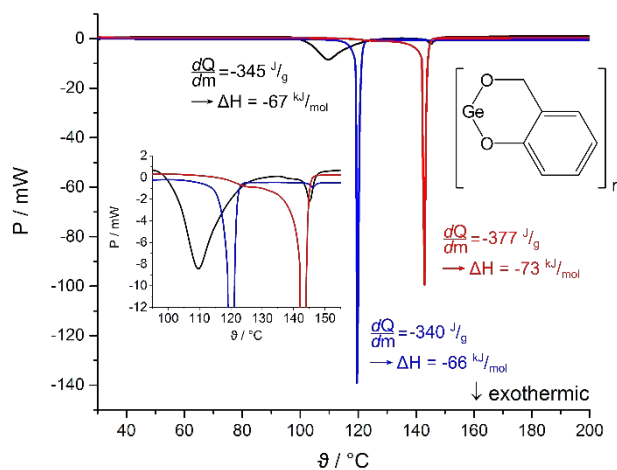


Figure 5 Differential scanning calorimetry of amorphous **1** (black curve), crystals of $(1)_3$ (red curve) and crystals of $2 \cdot (1)_4 \cdot n$ -pentane (blue curve); heating rate 10 K min⁻¹, N₂ atmosphere, N₂ volume flow 50 mL min⁻¹. The inset magnifies the range between 95 °C and 155 °C. The determined dQ/dm values and the as-calculated molar reaction enthalpies (ΔH) that are referred to one monomeric unit of **1** of the exothermic processes are depicted in black for amorphous **1**, red for crystals of $(1)_3$ and blue for crystals of $2 \cdot (1)_4 \cdot n$ -pentane.

The different onset temperatures indicate that the initiation of the polymerization process depends on structural parameters of the germynes e.g., structure of the oligomer and/or crystal packing effects. The crystalline forms of gerylene **1** gave higher onset temperatures and narrower temperature ranges ($\Delta 15\text{ }^\circ\text{C}$) for the exothermic processes than observed for the amorphous material. The exothermic processes gave a dQ/dm value of -345 J/g for amorphous **1**, -377 J/g for crystalline $(\mathbf{1})_3$ and -340 J/g for crystalline $2\cdot(\mathbf{1})_4 \cdot n\text{-pentane}$. Thus, the as-calculated molar reaction enthalpies (ΔH) that are referred to one monomeric unit of **1** ($M = 194.73\text{ g/mol}$) are -67 kJ/mol for amorphous **1**, -73 kJ/mol for crystalline $(\mathbf{1})_3$ and -66 kJ/mol for crystalline $2\cdot(\mathbf{1})_4 \cdot n\text{-pentane}$. As the dQ/dm values and as a consequence the molar reaction enthalpies (ΔH) are comparable for the amorphous and the crystalline materials of **1**, the reaction energies do not rely on the structures of the precursors. It is noteworthy that the DSC curve of $2\cdot(\mathbf{1})_4 \cdot n\text{-pentane}$ exhibits a second minimum at $146\text{ }^\circ\text{C}$ as it is also observed for amorphous **1** ($145\text{ }^\circ\text{C}$). These minima are close to the single minimum detected for the twin polymerization of $(\mathbf{1})_3$ ($143\text{ }^\circ\text{C}$) indicating that at least some formation processes in order to form the hybrid material e.g., formation of the germanium oxide, take place at higher temperatures. We conclude that amorphous materials possess smaller reaction barriers for the initiation process of thermally induced twin polymerization. The initiation of TP for the crystalline materials is aggravated presumably due to crystal packing. However, as the polymerization process is initiated, the thermally induced TP of the germynes is facilitated by a pre-organized arrangement of the precursors considering the narrow temperature ranges of the polymerization process for the crystalline forms of **1**.

Characterization of the hybrid materials obtained by thermally induced twin polymerization

Thermally induced twin polymerization of **1** - **3** was carried out by bulk phase experiments under inert atmosphere. Polymerization temperatures of $200 - 230\text{ }^\circ\text{C}$ were chosen according to the results of the DSC measurements of the germynes **1** - **3**.

Table 1 Polymerization temperatures, product identities and yields of the germanium-containing phenolic resin hybrid materials as obtained by thermally induced TP of **1** - **3**.

Gerylene	R	Polymerization temperature [$^\circ\text{C}$]	Product	Yield ^{a)} [%]
1	H	200	HM-1 , pale yellow monolith	92
2	Me	220	HM-2 , yellow monolith	97
3	Br	230	HM-3 , colorless clumps	98

a) based on the mass of the gerylene.

The as-obtained germanium-containing phenolic resin hybrid materials were characterized by $^{13}\text{C}\{^1\text{H}\}$ cross polarization magic angle spinning (CP-MAS) NMR and IR spectroscopy, PXRD, CHN

analysis, XPS (exemplarily carried out for **HM-1**) and EDX spectroscopy. A summary of the polymerization temperatures, the product identities and the yields of the as-obtained hybrid materials is given in Table 1. Figure 6 depicts the $^{13}\text{C}\{^1\text{H}\}$ CP-MAS NMR spectra of these materials.

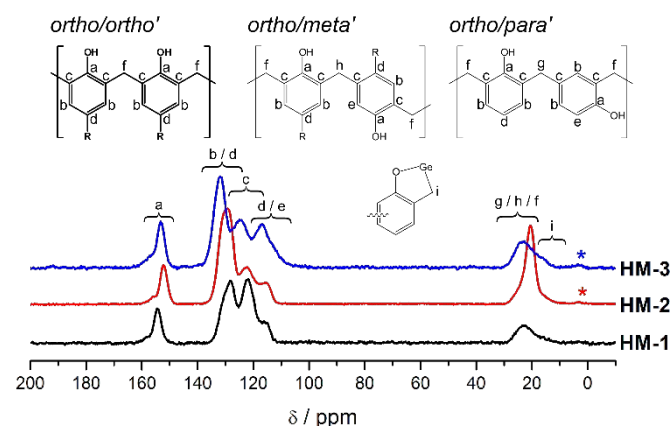


Figure 6 $^{13}\text{C}\{^1\text{H}\}$ CP-MAS NMR spectra of the germanium-containing phenolic resin hybrid materials as obtained by thermally induced twin polymerization of **1** - **3**. The spectra of **HM-1**, **HM-2** and **HM-3** are depicted as black, red and blue lines, respectively. The asterisks * mark spinning side bands. Assignment of the resonance signals is given for the assigned connectivity patterns of the bridging methylene groups (*ortho/para'* only for **HM-1**).

All expected signals for the phenolic resin of the hybrid materials **HM-1** - **HM-3** were observed with typical chemical shifts as reported for hybrid materials obtained by thermally induced TP.^{52, 62} The broad resonance signals with chemical shifts of $\delta = 20 - 30\text{ ppm}$ and the resonance signals between $\delta = 110 - 120\text{ ppm}$ (unsubstituted *ortho* carbons: $\delta = 113 - 117\text{ ppm}$ ⁶⁹) indicate the presence of nonequivalent bridging methylene groups in the phenolic resin for all hybrid materials.⁶⁹⁻⁷¹ Nevertheless, the resonance signals assigned to the bridging methylene groups ($\delta = 20 - 30\text{ ppm}$) exhibit the most intense resonance signals centered at $\delta = 23\text{ ppm}$ indicating that an *ortho/ortho'* connectivity of the bridging methylene groups is prevalent in the phenolic resin even for **HM-1**. These values match with reference data reported for *ortho/ortho'* bridging methylene carbons of phenol-formaldehyde resins ($\delta = 20 - 27\text{ ppm}$).⁷⁰ In addition, a trend for the content of unsymmetrical connectivity patterns of the bridging methylene groups with respect to electronic and steric features of the substituents is not observed, which is in contrast to our studies of the phenolic resin-silica hybrid materials obtained by thermally induced TP of spirocyclic silicon salicyl alcoholates.⁶² The latter and the prevalent *ortho/ortho'* connectivity of the bridging methylene groups indicate that the connectivity motif of the phenolic resin in the hybrid materials is only marginally influenced by the nature of the substituents at the aromatic moieties of the germynes. It is noteworthy that the resonance signals, which are assigned to the bridging methylene groups, exhibit shoulders with chemical shifts centered at $\delta = 16\text{ ppm}$ in all $^{13}\text{C}\{^1\text{H}\}$ CP-MAS NMR spectra. This observation is assigned to the presence of small amounts of Ge-CH_2

connectivity within the hybrid materials (Figure S6). The latter is a result of an oxidative insertion reaction of the germynes as reported previously for compound **4**, which slowly converts into 2,4,6,8-tetra-(3-*tert*-butyl-5-methyl-2-oxidophenyl)methanide-1,3,5,7,2,4,6,8-tetraoxido-germocane (**5**) in solution (Figure S6).⁶⁵ Compound **5** serves as a model compound for XPS analysis that was exemplarily carried out for **HM-1** due to its Ge-CH₂ groups. The

XPS data indicate that the germanium atoms in **HM-1** exhibit a similar chemical environment as it was determined for **5** (Figure S7). However, the XPS data are also consistent with data reported for germanium oxides.⁷²⁻⁸² Thus the XPS data do not allow to differentiate between the presence of Ge-CH₂ connectivity and germanium oxides within **HM-1**. However, in accordance with the ¹³C{¹H} CP-MAS NMR data, we suggest that thermally induced TP of the germynes provides hybrid materials consisting of germanium oxide incorporated in a phenolic resins, which contains small portions of Ge-CH₂ connectivity.

Typical IR absorption bands for $\nu(\text{O-H})$ (3600 - 3200 cm⁻¹), $\nu(\text{C=C})$ (1600 - 1400 cm⁻¹), $\nu(\text{C-O})$ (1250 - 1200 cm⁻¹), aromatic backbone vibrational modes (850 - 700 cm⁻¹) and Ge-O vibrational modes (430 - 650 cm⁻¹) were observed in the FT-IR spectra of all hybrid materials (Figure S8). An additional absorption band maximum at 1096 cm⁻¹ was observed in the IR spectrum of **HM-3**, which is assigned to the C-Br stretching vibrational mode. CHN analyses revealed carbon contents of the hybrid materials that are slightly lower than the values ($\Delta\text{C} < 1.1\%$) calculated for complete conversions of the germynes. The latter is in agreement with the determined minor weight losses (Figure S3) during the polymerization processes. However, the rather small deviations in the determined carbon and hydrogen contents in comparison with their calculated values indicate a high amount of conversion of the germynes into the hybrid materials. This is further supported by EDX analysis and the high yields as obtained for the hybrid materials after the work up procedures.

Synthesis and characterization of porous materials

Conversion of phenolic resin-silica hybrid materials obtained by TP of spirocyclic silicon salicyl alcoholates into microporous carbon and into mesoporous silica was reported by us recently.⁶² Variations of the molecular structure of the precursors e.g., different substituents at the aromatic moieties were shown to affect the properties of the porous materials.⁶² Expecting qualitatively similar results, we carried out the

Table 2 Summary of the product identities of the as-obtained Ge@C and GeO₂ materials, their single point BET surface areas and in case of the Ge@C materials the pore volumes determined by nitrogen adsorption measurements in addition with their germanium content.

Ge@C materials obtained under reductive conditions ^[a]					GeO ₂ materials obtained under oxidative conditions ^[b]		
Starting material	Product	BET surface area ^[c] [m ² /g]	Pore volume ^[d] [cm ³ /g] (micropore content [%])	Germanium content ^[e] [%]	Starting material	Product	BET surface area ^[c] [m ² /g]
HM-1	C-1a	268	0.217 (25.1)	46.5±2.8	HM-1	Ox-1	12
HM-1	C-1b	238	0.165 (34.5)	39.8±2.4	HM-2	Ox-2	9
HM-2	C-2	244	0.236 (14.9)	36.6±2.0	HM-3	Ox-3	20
HM-3	C-3	418	0.273 (46.7)	26.5±1.6			

[a] at 800 °C (600 °C for **C-1b**) for 3 h under Ar/H₂ flux (95/5, 20 l/h), heating rate 10 K/min. [b] at 800 °C for 3 h under air flux (200 l/h), heating rate 10 K/min. [c] $p/p_0 = 0.150 \pm 0.002$. [d] determined by the QSDFT model for slit and cylindrical pores using the adsorption branch of the isotherms. [e] determined by EDX spectroscopy.

conversion reactions of the germanium-containing phenolic resin hybrid materials (**HM-1** - **HM-3**) under reductive and oxidative conditions in order to obtain porous materials consisting of germanium incorporated in a carbon matrix (Ge@C) and porous GeO₂, respectively (Scheme 1). The product identities of the as-obtained Ge@C and GeO₂ materials, their BET surface areas and in case of the Ge@C composites the pore volumes determined by nitrogen adsorption measurements in addition with their germanium content are summarized in Table 2.

The as-prepared Ge@C materials exhibit large BET surface areas with **C-3** (418 m²/g) offering the largest value. The adsorption isotherms of the Ge@C composites are assigned to type I isotherms showing hysteresis loops (Figure S9), which may result from bottleneck pores. Analysis of the adsorption isotherms using QSDFT gave 14.9 % (**C-2**), 25.1 % (**C-1a**), 34.5 % (**C-1b**) and 46.7 % (**C-3**) micropore contents. CHN analyses gave carbon contents of 32.66 % (**C-1a**), 34.41 % (**C-1b**), 31.58 % (**C-2**) and 60.89 % (**C-3**). In addition, EDX spectroscopy revealed germanium contents of (46.5±2.8) % (**C-1a**), (39.8±2.4) % (**C-1b**), (36.6±2.0) % (**C-2**) and (26.5±1.6) % (**C-3**). Bromine was not detected by EDX analysis of **C-3**. The materials **C-1a**, **C-1b** and **C-2** exhibit low carbon but high germanium contents, whereas a low germanium and a high carbon content were determined for **C-3**. The mass losses during the synthesis of **C-1a**, **C-1b** and **C-2** were about 50 %, whereas 68 % was observed for **C-3**. The latter, in addition with the high carbon value, low germanium and lacking bromine content as determined for **C-3**, indicate that larger amounts of germanium and almost all bromine were removed during the synthesis of **C-3** resulting in a material exhibiting a much higher carbon content (C: 60.89 %) as initially present in the starting material **HM-3** (C: 30.10 %) or germylene **3** (C: 30.40 %). Hence, the higher specific surface-to-mass ratio of **C-3** results from larger proportions of carbonized material in addition with the higher micropore content that may result from decomposition processes (Figures S3 and S10) causing the removal of all bromine and some germanium. Crystalline germanium particles with average primary particle sizes of (51±6) nm (**C-1a**), (13±1) nm (**C-1b**), (39±3) nm (**C-2**) and

(38±3) nm (**C-3**) were determined by PXRD analyses (Figure S11). Smaller crystalline particle sizes were obtained at 600 °C [(13±1) nm for **C-1b**] as compared to 800 °C [(51±6) nm for **C-1a**], while the BET surface area does not differ significantly. Raman spectroscopy using a confocal micro Raman system revealed for Ge@C areas that exhibit either high germanium but low carbon or high carbon but low germanium contents (Figure S12). The latter is indicative that phase separation between germanium and carbon on the μm-scale occurred during the synthesis of the Ge@C composites under reductive conditions, which was confirmed by scanning electron microscopy in combination with EDX mapping (SEM/EDX) (Figure S13).

The as-prepared GeO₂ exhibit low BET surface areas, which is indicative for a non-porous material. This is further supported by the adsorption isotherms that were assigned to type II isotherms, which is typical for non-porous and/or macroporous materials (Figure S9). The isotherms show pronounced hysteresis down to $p/p_0 < 0.05$, which may result from hampering adsorption and/or hindered desorption of nitrogen due to interactions between the adsorbate and the adsorbent. PXRD analysis and Raman spectroscopy revealed the formation of hexagonal GeO₂ for all oxidized materials. However, minor portions of tetragonal GeO₂ were also detected for **Ox-1** and **Ox-2** (Figure S11 and S12).

In conclusion, porous Ge@C composites and non-porous GeO₂ were obtained following the synthesis concept of TP (Scheme 1). The properties of the as-obtained Ge@C and GeO₂ materials is only marginally influenced by the molecular structure of the precursors with the exception that bromine within the hybrid material (**HM-3**) results in larger loss of germanium by removal of all bromine during the synthesis of the Ge@C material (**C-3**). This results in higher carbon contents and larger BET surface area for Ge@C composites (**C-3** vs **C-1/C-2**). The finally obtained non-porous GeO₂ materials indicate that the proposed germanium oxide networks within the hybrid materials (Equation 1) is not stable with respect to further conversion processes. However, the formation of the as-obtained microporous Ge@C composites containing germanium nanocrystals indicates that the hybrid materials consisting of phenolic-resin and germanium oxide as dominant germanium species exhibit indeed phase nanodomains.

Electrochemical measurements

In order to provide a proof of principle, the Ge@C materials **C-1a** and **C-1b** were tested as potential anode material for rechargeable Li-ion batteries. Electrodes were prepared by mixing the respective Ge@C sample with carbon black (CB) and

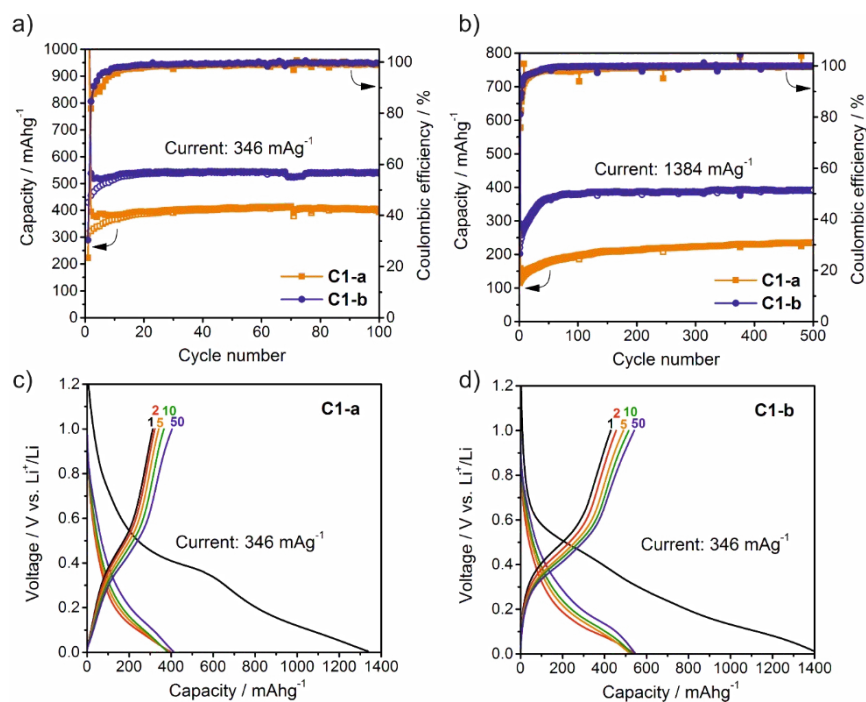


Figure 7 Electrochemical performance of Ge@C materials **C1-a** and **C1-b** as anode material for Li-ion batteries. The approximate size of germanium domains is (51±6) nm for **C1-a** and (13±1) nm for **C1-b**. a) Cycling stability at a current of 346 mA g⁻¹. b) Cycling stability at a current of 1384 mA g⁻¹. c) and d) Galvanostatic charge and discharge curves of composites **C1-a** and **C1-b** at a current of 346 mA g⁻¹. All cells were cycled in the potential range 0.005 – 1.0 V. Capacities and currents are related to the mass of the Ge@C composite corresponding to 80 % of the whole electrodes.

carboxymethyl cellulose (CMC) with the mass ratio of 8:1:1 using a planetary ball-mill. Electrochemical tests were carried out in Li-ion half cells using 1 M LiPF₆ in a mixture (1:1 by weight) of ethylene carbonate (EC) and dimethyl carbonate (DMC) as electrolyte. Fluoroethylene carbonate (FEC) was used as electrolyte additive to improve cycling stability.⁴³ The results of the electrochemical measurements for **C1-a** and **C1-b** are shown in Figure 7. Cells were cycled in the potential range of 0.005 – 1.0 V using a current of 346 mA g⁻¹ or 1384 mA g⁻¹ respectively. For the first discharge cycle high irreversible capacities are obtained due to the formation of the solid electrolyte interface and the reduction of surface oxides according to $\text{GeO}_2 + 4\text{Li}^+ + 4\text{e}^- \rightarrow \text{Ge} + 2\text{Li}_2\text{O}$. However, during subsequent cycling in all cases the coulombic efficiency, the ratio between charge and discharge capacity, increased to ~99 %. For cycling at 346 mA g⁻¹ composite **C1-b** delivers stable capacities of 540 mA h g⁻¹ with no fading for at least 100 cycles. In contrast, composite **C1-a** only provides capacities of approximately 400 mA h g⁻¹. Even at a current of 1384 mA g⁻¹ both samples of porous Ge@C material afforded stable capacities for 500 cycles with **C1-b** showing clearly better rate capability delivering a capacity of ~390 mA h g⁻¹ compared to ~220 mA h g⁻¹ for **C1-a**. It is important to note that in all cases currents and capacities were related to the total mass of the Ge@C composite. Considering that EDX-analysis yields a Ge-content of 46.5±2.8 % for **C-1a** and 39.8±2.4 % for **C-1b** the corresponding Ge-content in the electrodes can be estimated at 37 % and 32 % respectively. Relating currents and capacities only to this fraction of Ge in Ge@C, composite **C1-b** therefore reaches

stable capacities of 1360 mAhg^{-1} for 100 cycles at a rate of $870 \text{ mA}g^{-1}$ and 980 mAhg^{-1} for 500 cycles at a rate of $3480 \text{ mA}g^{-1}$. Despite the fact that direct comparison of electrochemical results has to be done carefully due to typically differences in electrode composition (e.g. Ge-content) or electrochemical cycling (e.g. current, potential range), we note that the performance of the herein presented Ge@C composite **C1-b** is indeed comparable with recent reports on Ge/C materials (Table S1 for detailed comparison).^{37, 48, 50, 83, 84} These good electrochemical properties can be attributed to several factors. Due to nanoscale dimension of crystalline germanium in the Ge@C composites, and appropriate porosity, the massive volume changes occurring during lithiation/delithiation can be effectively accommodated, leading to excellent cycling stability. Further, due to the small size of germanium domains, intimate contact with carbon and porous structure of Ge@C, the ionic and electronic conductivity are enhanced allowing fast charging/discharging. In this regard, the significantly superior rate capability obtained for composite **C1-b** compared to **C1-a** can be attributed to the smaller size of crystalline primary germanium particles [(13±1) nm vs. (51±6) nm, see Table 2] and therefore shorter diffusion distances. The fact that the capacity does not reach the theoretical maximum at ambient temperature of 1384 mAhg^{-1} (assuming formation of $\text{Li}_{15}\text{Ge}_4$), might be attributed to the relatively high currents used and possibly fractions of germanium oxides as indicated by EDX measurements (Table S2), which leads to lower capacities. For comparison, whereas germanium has a theoretical capacity of 1384 mAhg^{-1} the reversible theoretical capacity of GeO_2 is 961 mAhg^{-1} . Figures 7c and 7d show the galvanostatic charge/discharge curves of composite **C1-a** and **C1-b**. In both cases the average delithiation potential is relatively low ($\sim 0.5 \text{ V}$) indicating high suitability of such Ge@C materials for future full cell applications as a high performance alternative to commercial graphite anodes.

Conclusions

The germanium(II) salicyl alcoholates, germanium(II)-2-(oxido-methyl)phenolate (**1**), germanium(II)-4-methyl-2-(oxido-methyl)phenolate (**2**) and germanium(II)-4-bromo-2-(oxido-methyl)phenolate (**3**), have been synthesized by the reaction of $\text{Ge}[\text{N}(\text{SiMe}_3)_2]_2$ and the respective salicyl alcohols. Dimeric, trimeric and tetrameric structures of the germynes were determined in the solid state and equilibria between oligomers of these compounds were observed in solution. Twin polymerization of the compounds **1** - **3** that was thermally induced by heating up to $230 \text{ }^\circ\text{C}$ gave germanium-containing phenolic resin hybrid materials. In contrast to spirocyclic silicon salicyl alcoholates, no influence following the steric and electronic features of their substituents [R = H (**1**), Me (**2**) and Br (**3**)] was observed on the process of thermally induced twin polymerization. Moreover, analyses of the as-obtained hybrid materials and bulk syntheses of Ge@C composites and GeO_2 support this observation. However, a significant dependency on the solid form of the germynes e.g., amorphous vs. crystalline, was observed for the process of thermally induced twin

polymerization. Its initiation is hampered by a densely packed structure in the first place but as the polymerization process is initiated, a pre-organized arrangement of the precursors facilitates the polymerization.

Porous Ge@C composites and non-porous GeO_2 were obtained by either conversion of the as-obtained hybrid materials under reductive or oxidative conditions. Testing the obtained Ge@C composites as anode materials for rechargeable Lithium-ion batteries in order to provide a proof of principle on our concept revealed that excellent cyclability, rate capability and high coulombic efficiency were obtained, especially for the Ge@C composite possessing smaller crystalline germanium primary particle sizes [(13±1) nm]. Despite the fact that the present cost for germanium compounds is possibly too high for implementing germanium-based anodes in commercial Lithium-ion batteries, the herein presented concept of twin polymerization provides a general strategy to prepare high-performance electrode materials by embedding the active material efficiently into a conductive carbon matrix and holds considerable potential to be expanded to further systems in the future.

Experimental Section

All reactions were performed under argon using Schlenk techniques or in a glovebox. Solvents were purified and dried by applying standard techniques. The reactions were carried out with freshly distilled, dried solvents. ^1H , $^{13}\text{C}\{^1\text{H}\}$ and $^1\text{H} \text{ }^{13}\text{C}\{^1\text{H}\}$ HSQC NMR spectra were recorded with a Bruker Avance III 500 spectrometer. Solid-state NMR spectra were measured at 9.4 T with a Bruker Avance 400 spectrometer equipped with double-tuned probes capable of magic angle spinning (MAS). $^{13}\text{C}\{^1\text{H}\}$ CP-MAS NMR spectra were measured at 100.6 MHz in 3.2 mm standard zirconium oxide rotors (BRUKER) spinning at 15 kHz. Cross polarization (CP) with a contact time of 3 ms was used to enhance sensitivity. The recycle delay was 5 s. The spectrum was referenced externally to tetramethylsilane (TMS) as well as to adamantane as secondary standard (38.48 ppm for ^{13}C). All spectra were collected with ^1H decoupling using a two-pulse phase modulation sequence. ATR-FT-IR spectra were recorded with a BioRad FTS-165 spectrometer. FT-IR were recorded with a Nicolet IR 200 spectrometer from Thermo Scientific (Thermo Fisher Scientific Inc., Waltham, MA, USA) in a KBr Matrix. Raman spectra were collected on a LabRam HR800 confocal micro Raman system equipped with a Helium-Neon-laser ($\lambda = 632.8 \text{ nm}$, $P = 3.08 \text{ mW}$) without usage of any filter (DO) at fiftyfold magnification. Energy-dispersive X-ray spectroscopy (EDX) and scanning electron microscopy (SEM) were performed using a NovaNano SEM from FEI with the following parameters: pressure ($\sim 10^{-5} \text{ mbar}$), work distance (5 to 7 mm) and acceleration voltage (18 kV) using a Si Drift Detector XFlash 3001 from Bruker AXS. Melting points were determined with a Melting Point B-540 apparatus from Büchi. CHN analyses were determined using a FlashEA 1112 NC Analyzer from Thermo Fisher Scientific. DSC experiments were determined with a Mettler Toledo DSC 30 using 40 μL aluminum crucibles. The measurements were performed up to $400 \text{ }^\circ\text{C}$ with a heating rate

of 10 K/min in N₂ atmosphere and a volume flow of 50 mL/min. TGA/DSC experiments were determined with a Mettler Toledo TGA/DSC1 1600 system with a MX1 balance. The measurement was performed from 40 to 800 °C with a heating rate of 10 K/min in Ar atmosphere and a volume flow of 60 mL/min. Nitrogen physisorption isotherms were obtained at -196 °C using an Autosorb IQ2 apparatus from Quantachrome. All samples were activated in vacuum at 150 °C for 3 h prior to the measurements. Specific surface areas were calculated applying the BET equation ($p/p_0 = 0.150 \pm 0.002$). The micropore content was estimated according to a QSDFT model (QSDFT: Quenched Solid Density Functional Theory, model for slit and cylindrical pores using the adsorption branch) for carbon samples using the Autosorb 1.56 software from Quantachrome.⁸⁵⁻⁹² The specific micropore and total pore volume were also calculated by the above mentioned DFT models. For X-ray photoelectron spectroscopy (XPS) measurements, the powder samples were pressed on indium foil (99.99 %, from MaTeck GmbH) that was cleaned with standard solvents in an ultrasonic bath. Measurements were performed in ultra-high vacuum (UHV) employing a hemispherical electron analyzer (PHOIBOS 150 from SPECS GmbH) and an Al-K α X-ray source (XR50M from SPECS GmbH) equipped with a monochromator (FOCUS from SPECS GmbH). The pass energy was set to 10 eV for acquisition of the core-level and Auger electron spectra. The estimated error in binding energies is ± 0.2 eV. No charge compensation was applied. Powder X-ray diffraction (PXRD) patterns were collected using a STOE-STADI P diffractometer from STOE with Cu-K α radiation (40 kV, 40 mA) and a Ge(111) monochromator. The crystallite size was estimated using the Scherrer equation: $\tau = K\lambda/\beta\cos\theta$, where τ is the volume weighted crystallite size, K is the Scherrer constant here taken as 1.0, λ is the X-ray wavelength, ϑ is the Bragg angle in ° and β is the full width of the diffraction line at half of the maximum intensity (FWHM, background subtracted). The FWHM is corrected for instrumental broadening using a LaB₆ standard (SRM 660) purchased from NIST (National Institute of Standards and Technology). The value of β was corrected from ($\beta^2_{\text{measured}}$ and $\beta^2_{\text{instrument}}$ are the FWHMs of measured and standard profiles):

$$\beta^2 = \beta^2_{\text{measured}} - \beta^2_{\text{instrument}}$$

Germanium(IV) chloride and 1,1,1,3,3,3-hexamethyldisilazane were purchased from ABCR GmbH & Co KG. 2.5 M *n*-Butyllithium and 5-bromo-2-hydroxybenzaldehyde were purchased from Merck Schuchardt OHG (Hohenbrunn). 2-Hydroxybenzyl alcohol and 4-methylphenol were purchased from Alfa Aesar GmbH & Co KG (Karlsruhe). GeCl₂*1,4 dioxane,¹⁵ LiN(SiMe₃)₂,¹⁵ Ge[N(SiMe₃)₂]₂³ and 2-hydroxy-5-methylbenzaldehyde⁹³ were synthesized according to the literature procedures. 2-Hydroxy-5-methylbenzyl alcohol, 5-bromo-2-hydroxybenzyl alcohol⁹⁴ were synthesized according to modified literature procedures. 2-Hydroxybenzyl alcohol was purified by column chromatography (on silica gel using an ethyl acetate/*n*-hexane mixture (20/80) as eluent) before usage. All details including syntheses and characterizations of the molecular precursors are given in the Supporting Information.

Synthesis of germanium(III)-2-(oxidomethyl)phenolate (1)

A solution of 2-hydroxybenzyl alcohol (0.346 g, 2.78 mmol) in a mixture of diethyl ether (4 mL) and *n*-pentane (4 mL) was added dropwise to a solution of Ge[N(SiMe₃)₂]₂ (1.096 g, 2.78 mmol) in *n*-pentane (10 mL) at ambient temperature. A colorless precipitate occurred within 5 min upon stirring. The mixture was filtered off and washed with *n*-pentane (3 * 3 mL) to give amorphous compound **1** (0.227 g) after evaporating volatile residues under reduced pressure (10⁻² mbar). Slow evaporation of the volatile solvent gave crystalline (**1**)₄ from the filtrate over a period of 2 hours. The colorless crystals were filtered off and all volatile residues were removed by evaporation under reduced pressure (10⁻¹ mbar) to give crystalline **1** [(**1**)₄, 0.174 g]. Yield (both fractions): 0.401 g, 73 %; mp - (decomposition above ~ 101 °C); ¹H NMR (500 MHz, d₈-THF, 25 °C, TMS): $\delta = 4.59$ [s (broad), 2 H, CH₂], 6.66 [m (broad), H, C₆H₄], 6.74 [m (broad), H, C₆H₄], 6.76 [m (broad), H, C₆H₄], 7.12 ppm [m (broad), H, C₆H₄]; ¹³C{¹H} NMR (125 MHz, d₈-THF, 25 °C, TMS): $\delta = 62.1$ (CH₂), 119.4 (C₆H₄), 119.6 (C₆H₄), 120.3 (C₆H₄), 128.3 (C₆H₄), 130.4 (C₆H₄), 158.4 ppm (C₆H₄); ¹H ¹³C{¹H} HSQC NMR (125 MHz, d₈-THF, 25 °C, TMS): $\delta = 4.60/59.1$ (CH₂), 6.64/116.6 (C₆H₄), 6.73/117.2 (C₆H₄), 6.77/125.1 (C₆H₄), 7.10/127.0 ppm (C₆H₄); ATR-FT-IR: 3066 (ν C_{aryl}-H), 3037 (ν C_{aryl}-H), 3015 (ν C_{aryl}-H), 2921 (ν CH₂), 2857 (ν CH₂), 1599 (ν C=C), 1578 (ν C=C), 1478 (δ CH₂), 1453 (δ CH₂), 1254 (ν C-O), 1198 (ν C-O), 756 (ν C₆H₄), 731 (ν C₆H₄), 633 (ν Ge-O), 604 (ν Ge-O), 556 and 525 and 486 and 444 cm⁻¹ (O-Ge-O/Ge-O-Ge); CHN analysis calcd (%) for C₇H₆GeO₂: C, 43.17; H, 3.11; found: C, 43.26; H, 3.55. Single crystals suitable for X-ray diffraction analysis were obtained i) directly from the filtrate of the reaction mixture after filtration of the precipitate to give (**1**)₄, ii) by evaporation of the solvent at ambient temperature of a saturated solution of **1** in diethyl ether and iii) by cooling a saturated solution of (**1**)₄ in diethyl ether to -18 °C to give (**1**)₃, respectively.

Synthesis of germanium(III)-4-methyl-2-(oxidomethyl)phenolate (2)

A solution of 2-hydroxy-5-methylbenzyl alcohol (0.454 g, 3.29 mmol) in a mixture of diethyl ether (6 mL) and *n*-pentane (2 mL) was added dropwise to a solution of Ge[N(SiMe₃)₂]₂ (1.294 g, 3.29 mmol) in *n*-pentane (10 mL) at ambient temperature. A colorless precipitate occurred within 5 min upon stirring. The mixture was filtered off and washed with *n*-pentane (3 * 2 mL) to give amorphous compound **2** (0.168 g) after evaporating volatile residues under reduced pressure (10⁻² mbar). Slow evaporation of the volatile solvent gave crystalline **2** from the filtrate over a period of 2 hours. Filtration and evaporation of all volatile residues under reduced pressure (10⁻¹ mbar) gave **2** (0.288 g) as colorless crystals. Yield (both fractions): 0.456 g, 66 %; mp - (decomposition above ~ 164 °C); ¹H NMR (500 MHz, d₈-THF, 25 °C, TMS): $\delta = 2.20$ [s (broad), 3 H, Me], 4.61 [s (broad), 2 H, CH₂], 6.57 [m (broad), H, C₆H₃], 6.82 [m (broad), H, C₆H₃], 6.97 ppm [m (broad), H, C₆H₃]; ¹³C{¹H} NMR (125 MHz, d₈-THF, 25 °C, TMS): $\delta = 20.8$ (Me), 62.5 (CH₂), 115.9 (C₆H₃), 128.4 (C₆H₃), 128.6 (C₆H₃), 128.7 (C₆H₃), 129.0 (C₆H₃), 154.5 ppm (C₆H₃); ¹H ¹³C{¹H} HSQC NMR (125 MHz, d₈-THF, 25 °C, TMS): $\delta = 2.20/23.1$ (Me), 4.61/64.9 (CH₂), 6.57/118.3 (C₆H₃), 6.82/131.3 (C₆H₃), 6.97/131.2 ppm (C₆H₃); ATR-FT-IR: 3014 (ν C_{aryl}-H), 2909 (ν CH₃/CH₂), 2861 (ν CH₃/CH₂), 1613 (ν

C=C), 1578 (ν C=C), 1484 (δ CH₃/CH₂), 1451 (δ CH₃/CH₂), 1252 (ν C-O), 1214 (ν C-O), 872 (ν C₆H₃), 818 (ν C₆H₃), 644 (ν Ge-O), 556 and 490 and 459 cm⁻¹ (O-Ge-O/Ge-O-Ge); CHN analysis calcd (%) for C₈H₈GeO₂: C, 46.02; H, 3.86; found: C, 45.79; H, 4.00. Single crystals suitable for X-ray diffraction analysis were obtained by slow evaporation of the solvent at ambient temperature of a saturated solution of **2** in diethyl ether to give (**2**)₂.

Synthesis of germanium(II)-4-bromo-2-(oxidomethyl)phenolate (**3**)

A solution of 5-bromo-2-hydroxybenzyl alcohol (0.525 g, 2.58 mmol) in a mixture of diethyl ether (10 mL) and *n*-hexane (5 mL) was added dropwise to a solution of Ge[N(SiMe₃)₂]₂ (1.018 g, 2.59 mmol) in a mixture of diethyl ether (2 mL) and *n*-hexane (10 mL) at ambient temperature. A colorless precipitate occurred within 5 min upon stirring. The mixture was filtered off and washed with *n*-hexane (3 * 3 mL) to give amorphous compound **3** (0.387 g) after evaporating volatile residues under reduced pressure (10⁻² mbar). Yield: 0.457 g, 64 %; mp - (decomposition above ~ 151 °C); ¹H NMR (500 MHz, d₈-THF, 25 °C, TMS): δ = 4.59 (s, 2 H, CH₂), 6.65 (d, H, C₆H₃, ³J_{ortho} = 8.5 Hz), 6.97 (d, H, C₆H₃, ⁴J_{meta} = 1.9 Hz), 7.23 ppm (dd, H, C₆H₃, ³J_{ortho} = 8.5 Hz, ⁴J_{meta} = 1.9 Hz); ¹³C{¹H} NMR (125 MHz, d₈-THF, 25 °C, TMS): δ = 62.0 (CH₂), 111.2 (C₆H₃), 122.1 (C₆H₃), 130.8 (C₆H₃), 131.4 (C₆H₃), 132.8 (C₆H₃), 157.5 ppm (C₆H₃); ¹H ¹³C{¹H} HSQC NMR (125 MHz, d₈-THF, 25 °C, TMS): δ = 4.59/58.9 (CH₂), 6.65/119.0 (C₆H₃), 6.98/127.7 (C₆H₃), 7.24/129.9 ppm (C₆H₃); ATR-FT-IR: 3066 (ν C_{aryl}-H), 2973 (ν C_{aryl}-H), 2913 (ν CH₂), 2867 (ν CH₂), 1590 (ν C=C), 1561 (ν C=C), 1472 (δ CH₂), 1406 (δ CH₂), 1254 (ν C-O), 1225 (ν C-O), 1073 (ν C-Br), 874 (ν C₆H₄), 822 (ν C₆H₄), 656 (ν Ge-O), 544 and 440 cm⁻¹ (O-Ge-O/Ge-O-Ge); CHN analysis calcd (%) for C₇H₅BrGeO₂: C, 30.72; H, 1.84; found: C, 30.40; H, 1.69. Single crystals suitable for X-ray diffraction analysis were obtained by slow evaporation of the solvent at ambient temperature of a saturated solution of **3** in 1,4-dioxane to give (**3**)₂.

General procedure for the synthesis of phenolic resin/germanium oxide hybrid materials by thermally induced twin polymerization in melt - exemplified for compound **1**

Compound **1** (0.507 g, 2.60 mmol) was polymerized at 200 °C under Ar atmosphere and treated at this temperature for 3 h. The obtained solid was washed with dichloromethane (10 * 3 mL) and dried under reduced pressure (10⁻¹ mbar) in order to remove volatile by-products. The product **HM-1** [0.471 g, 92 %, CHN analysis (%) found: C, 42.38; H, 3.38; EDX analysis (%) found: C, 54.1±2.4; O, 18.7±0.9; Ge, 27.2±0.6] was a pale yellow phenolic resin/germanium oxide monolith; Polymerization of: **2** (0.507 g, 2.04 mmol) at 220 °C gave **HM-2** [0.417 g, 97 %, CHN analysis (%) found: C, 47.11; H, 4.44; EDX analysis (%) found: C, 55.9±2.3; O, 17.6±0.8; Ge, 26.5±0.5] as a yellow monolith; **3** (0.876 g, 3.20 mmol) at 230 °C gave **HM-3** [0.861 g, 98 %, CHN analysis (%) found: C, 30.10; H, 1.77; EDX analysis (%) found: C, 33.4±3.1; O, 10.8±1.1; Ge, 27.8±0.9; Br, 28.0±0.9] as colorless clumps.

General procedure for the synthesis of porous Ge@C materials - exemplified for hybrid material **HM-1**

HM-1 (0.136 g) was carbonized under reductive conditions in a stove (deposited in a quartz glass tube) for 3 h with a final temperature of 800 °C (heating ramp of 10 K/min) under Ar/H₂ flux (95/5, 20 l/h) to give **C-1a** [0.065 g, single point BET-surface area determined at p/p₀ = 0.150±0.002: 268 m²/g; CHN analysis (%) found: C, 32.66; H, 0.29; EDX analysis (%) found: C, 44.3±4.1; O, 9.2±1.4; Ge, 46.5±2.8; crystalline Ge particle size determined by applying the Scherer equation based on the (220) reflection of Ge ICDD no. C03-065-0333: 51±6 nm] as metallic shiny black solid; Carbonization of: **HM-1** (0.229 g) at 600 °C gave **C-1b** [0.110 g, single point BET-surface area: 238 m²/g; CHN analysis (%) found: C, 34.41; H, 0.86; EDX analysis (%) found: C, 58.5±7.5; O, 1.7±0.3; Ge, 39.8±2.4; crystalline Ge particle size: 13±1 nm]; **HM-2** (0.123 g) at 800 °C gave **C-2** [0.057 g, single point BET-surface area: 244 m²/g; CHN analysis (%) found: C, 31.58; H, 0.18; EDX analysis (%) found: C, 55.2±6.7; O, 8.2±1.2; Ge, 36.6±2.0; crystalline Ge particle size: 39±3 nm]; **HM-3** (0.371 g) at 800 °C gave **C-3** [0.119 g, single point BET-surface area: 418 m²/g; CHN analysis (%) found: C, 60.89; H, 0.38; EDX analysis (%) found: C, 70.4±8.7; O, 3.1±0.5; Ge, 26.5±1.6; Br, -; crystalline Ge particle size: 13±1 nm].

General procedure for the synthesis of germanium oxide - exemplified for hybrid material **HM-1**

HM-1 (0.218 g) was oxidized in a stove (deposited in a quartz glass tube) for 3 h with a final temperature of 800 °C (heating ramp of 10 K/min) under air flux (200 l/h) to give **Ox-1** [0.115 g, single point BET-surface area determined at p/p₀ = 0.150±0.002: 12 m²/g; CHN analysis (%) found: C, 0.51; EDX analysis (%) found: C, 3.5±0.7; O, 31.0±3.7; Ge, 65.5±3.7; Raman spectroscopy and PXRD confirmed the presence of hexagonal (α-quartz-like structure ICDD no. C00-036-1463) and tetragonal (rutile-like structure ICDD no. C00-035-0729) GeO₂] as gray brittle monolith; Oxidation of: **HM-2** (0.241 g) gave **Ox-2** [0.117 g, single point BET-surface area: 9 m²/g; CHN analysis (%) found: C, 0.22; EDX analysis (%) found: C, 3.1±0.8; O, 28.7±3.9; Ge, 68.2±4.1; Raman spectroscopy and PXRD confirmed the presence of hexagonal and tetragonal GeO₂]; **HM-3** (0.306 g) gave **Ox-3** [0.082 g, single point BET-surface area: 20 m²/g; CHN analysis (%) found: C, 0.60; EDX analysis (%) found: C, 3.3±0.6; O, 31.2±3.4; Ge, 65.5±3.3; Br, -; Raman spectroscopy and PXRD confirmed only the presence of hexagonal GeO₂].

Single crystal X-ray diffraction analyses

Crystallographic data of the compounds (**1**)₃, 2·(**1**)₄ · *n*-pentane, (**2**)₂ and (**3**)₂ · 1,4-dioxane were collected with an Oxford Gemini S diffractometer (CrysAlis RED Version 1.171.32.5 from Oxford Diffraction Ltd.) using Mo-K_α (λ = 0.71073 Å) at 100 K [(**1**)₃] or Cu-K_α radiation (λ = 1.54184 Å) at 110 K [2·(**1**)₄ · *n*-pentane and (**2**)₂] or 100 K [(**3**)₂]. The structures were solved by direct methods using SHELXS-2013 and refined by full matrix least-square procedures on F² using SHELXL-2013.⁹⁵ Absorption corrections were semi-empirical from equivalents. All non-hydrogen atoms were refined anisotropically and a riding model was employed in the refinement of hydrogen atom positions. The crystallographic data for (**1**)₃, 2·(**1**)₄ · *n*-pentane, (**2**)₂ and (**3**)₂ · 1,4-dioxane have been deposited at the Cambridge

Crystallographic Data Centre as supplementary publications CCDC 1438301 [(1)₃], CCDC 1438303 [2·(1)₄ · n-pentane], CCDC 1438302 [(2)₂] and CCDC 1438300 [(3)₂ · 1,4-dioxane], they can be obtained free of charge from the Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif.

Computational Details

The quantum chemical calculations have been carried out at the DFT-D (B3LYP-D3/def2-TZVPP) level of theory using the TURBOMOLE program package.⁹⁶⁻¹⁰³ All structure data given as xyz-files in the Supporting Material were obtained by relaxing all degrees of freedom and confirmed as minima by normal mode analysis.

The resulting aqueous slurries were coated onto Cu foil (9 μm, MTI Corporation) and subsequently dried at 80 °C for 12 hours under vacuum. Electrochemical measurements were conducted in air tight coin-type cells assembled in an Ar-filled glove box (O₂ < 0.1 ppm, H₂O < 0.1 ppm) using elemental lithium as both counter and reference electrode. 1M LiPF₆ in a 1:1 mixture by wt. of ethylene carbonate (EC) and dimethyl carbonate (DMC) (Merck, battery grade) with 3% fluoroethylene carbonate (FEC, Hisunny Chemical Co., battery grade) served as electrolyte. As separator glass fiber (GF/D, Whatman) was used. Galvanostatic cycling tests were carried out at ambient temperature on MPG2 multi-channel workstation (BioLogic).

Table 3 Crystallographic and experimental data of the single crystal X-ray diffraction analyses of (1)₃, 2·(1)₄ · n-pentane, (2)₂ and (3)₂ · 1,4-dioxane.

Compound	(1) ₃	2·(1) ₄ · n-pentane	(2) ₂	(3) ₂ · 1,4-dioxane
Formula	C ₂₁ H ₁₈ Ge ₃ O ₆	C ₆₁ H ₆₀ Ge ₈ O ₁₆	C ₁₆ H ₁₆ Ge ₂ O ₄	C ₁₈ H ₁₈ Br ₂ Ge ₂ O ₆
Molecular mass	584.12 g mol ⁻¹	1629.81 g mol ⁻¹	417.47 g mol ⁻¹	635.32 g mol ⁻¹
Temperature	100 K	110 K	110 K	100 K
Wavelength	1.54184 Å	0.71073 Å	0.71073 Å	0.71073 Å
Crystal system	monoclinic	tetragonal	triclinic	monoclinic
Space group	P2 ₁ /n	I-4	P $\bar{1}$	P2 ₁ /c
Crystal size	0.2 × 0.2 × 0.16 mm	0.20 × 0.20 × 0.18 mm	0.4974 × 0.4881 × 0.0897 mm	0.34 × 0.06 × 0.04 mm
a	11.5755(3) Å	14.4998(3) Å	5.0400(8) Å	9.1184(6) Å
b	16.1191(10) Å	14.4998(3) Å	5.7142(6) Å	5.8156(4) Å
c	11.8463(4) Å	14.6335(6) Å	13.393(2) Å	18.7848(10) Å
α	90°	90°	78.607(11)°	90°
β	110.168(4)°	90°	81.131(14)°	91.848(5)°
γ	90°	90°	89.160(11)°	90°
V	2074.83(16) Å ³	3076.61(18) Å ³	373.54(9) Å ³	995.62(11) Å ³
Z	4	2	1	2
Density calculated	1.870 Mg m ⁻³	1.759 Mg m ⁻³	1.856 Mg m ⁻³	2.119 Mg m ⁻³
μ [mm ⁻¹]	5.455 mm ⁻¹	3.920 mm ⁻¹	4.019 mm ⁻¹	7.066 mm ⁻¹
F (000)	1152	1620	208	616
Theta range for data collection	4.83 to 63.94°	3.421 to 24.977°	3.141 to 24.991°	3.67 to 24.99°
Index ranges	-12 ≤ h ≤ 13 -17 ≤ k ≤ 18 -13 ≤ l ≤ 8	-17 ≤ h ≤ 16 -17 ≤ k ≤ 12 -13 ≤ l ≤ 17	-5 ≤ h ≤ 5 -6 ≤ k ≤ 6 -15 ≤ l ≤ 15	-10 ≤ h ≤ 10 -6 ≤ k ≤ 6 -13 ≤ l ≤ 22
Reflections collected	6394	5657	1656	3242
Independent reflections	3365 [R(int.) = 0.0260]	2651 [R(int.) = 0.0186]	1656 [R(int.) = 0.0612]	1738 [R(int.) = 0.0471]
Data	3365	2651	1656	1738
Goodness-of-fit on F ²	1.031	1.041	1.104	0.916
Final R indices [I > 2σ(I)], ωR2 (F ²) (all data)	R1 = 0.0345, ωR2 = 0.0930	R1 = 0.0219, ωR2 = 0.0463	R1 = 0.0597, ωR2 = 0.1798	R1 = 0.0398, ωR2 = 0.0927
Largest diff. peak and hole	0.632 and -0.531 e.Å ⁻³	0.301 and -0.265 e.Å ⁻³	1.495 and -1.544 e.Å ⁻³	1.108 and -0.649 e.Å ⁻³

Electrode fabrication, cell assembly and electrochemical measurements

Ge@C samples, carbon black (CB, Super C65, TIMCAL), and carboxymethyl cellulose (CMC, Grade: 2200, Daicel Fine Chem Ltd.) were mixed in the ratio 8:1:1 with deionized water using a Fritsch Pulverisette 7 classic planetary mill (1 hour at 500 rpm).

Acknowledgements

We gratefully acknowledge financial support by the DFG Forschergruppe 1497 "Organic-Inorganic Nanocomposites through Twin polymerization" and the Fonds der Chemischen

Industrie for a fellowship (P. K.). We thank N. Rüffer for TGA measurements and M. Weber for recording the Raman spectra.

Keywords

Germynes • twin polymerization • X-ray diffraction analysis • germanium-containing porous materials • organic-inorganic hybrid materials • Li-ion batteries

References

- M. D. Curtis and R. C. Job, *Abstr. Pap. Am. Chem. Soc.*, 1972, 12.
- K. Triplett and M. D. Curtis, *J. Am. Chem. Soc.*, 1975, **97**, 5747-5751.
- D. H. Harris and M. F. Lappert, *J. Chem. Soc., Chem. Commun.*, 1974, 895-896.
- P. Riviere, J. Satgé and A. Castel, *Cr. Acad. Sci. C Chim.*, 1975, **281**, 835-838.
- W. P. Neumann, *Chem. Rev.*, 1991, **91**, 311-334.
- A. Castel, P. Riviere, J. Satge and M. Ahbala, *J. Organomet. Chem.*, 1987, **331**, 11-21.
- A. Castel, P. Riviere, J. Satge, J. J. E. Moreau and R. J. P. Corriu, *Organometallics*, 1983, **2**, 1498-1502.
- P. Jutzi, B. Hampel, M. B. Hursthouse and A. J. Howes, *J. Organomet. Chem.*, 1986, **299**, 19-27.
- S. L. Ellis, P. B. Hitchcock, S. A. Holmes, M. F. Lappert and M. J. Slade, *J. Organomet. Chem.*, 1993, **444**, 95-99.
- J. Baumgartner and C. Marschner, *Rev. Inorg. Chem.*, 2014, **34**, 119-152.
- J. Satgé, M. Massol and P. Riviere, *J. Organomet. Chem.*, 1973, **56**, 1-39.
- L. Lange, B. Meyer and W. W. Dumont, *J. Organomet. Chem.*, 1987, **329**, C17-C20.
- J. Pfeiffer, M. Noltemeyer and A. Meller, *Z. Anorg. Allg. Chem.*, 1989, **572**, 145-150.
- B. Cetinkaya, I. Gumrukcu, M. F. Lappert, J. L. Atwood, R. D. Rogers and M. J. Zaworotko, *J. Am. Chem. Soc.*, 1980, **102**, 2088-2089.
- T. Fjeldberg, A. Haaland, B. E. R. Schilling, M. F. Lappert and A. J. Thorne, *J. Chem. Soc., Dalton Trans.*, 1986, 1551-1556.
- S. R. Stobart, M. R. Churchill, F. J. Hollander and W. J. Youngs, *J. Chem. Soc., Chem. Commun.*, 1979, 911-912.
- N. Zhao, J. Zhang, Y. Yang, G. Chen, H. Zhu and H. W. Roesky, *Organometallics*, 2013, **32**, 762-769.
- Z. D. Brown, J. D. Erickson, J. C. Fettinger and P. P. Power, *Organometallics*, 2013, **32**, 617-622.
- Z. D. Brown and P. P. Power, *Inorg. Chem.*, 2013, **52**, 6248-6259.
- Z. D. Brown, P. Vasko, J. D. Erickson, J. C. Fettinger, H. M. Tuononen and P. P. Power, *J. Am. Chem. Soc.*, 2013, **135**, 6257-6261.
- J. W. Dube, Z. D. Brown, C. A. Caputo, P. P. Power and P. J. Ragogna, *Chem. Commun.*, 2014, **50**, 1944-1946.
- Y. Peng, J.-D. Guo, B. D. Ellis, Z. Zhu, J. C. Fettinger, S. Nagase and P. P. Power, *J. Am. Chem. Soc.*, 2009, **131**, 16272-16282.
- J. K. West and L. Stahl, *Organometallics*, 2012, **31**, 2042-2052.
- A. Jana, V. Huch and D. Scheschkewitz, *Angew. Chem., Int. Ed.*, 2013, **52**, 12179-12182.
- P. S. Billone, K. Beleznyay, C. R. Harrington, L. A. Huck and W. J. Leigh, *J. Am. Chem. Soc.*, 2011, **133**, 10523-10534.
- S. Yao, C. van Wüllen and M. Driess, *Chem. Commun.*, 2008, 5393-5395.
- U. Anandhi and P. R. Sharp, *Inorg. Chim. Acta*, 2006, **359**, 3521-3526.
- K. Revunova and G. I. Nikonov, *Dalton Trans.*, 2015, **44**, 840-866.
- S. B. Kim, P. Sinsersuksakul, A. S. Hock, R. D. Pike and R. G. Gordon, *Chem. Mater.*, 2014, **26**, 3065-3073.
- F.-W. Yuan and H.-Y. Tuan, *Chem. Mater.*, 2014, **26**, 2172-2179.
- T. Kennedy, E. Mullane, H. Geaney, M. Osiak, C. O'Dwyer and K. M. Ryan, *Nano Lett.*, 2014, **14**, 716-723.
- E. Mullane, T. Kennedy, H. Geaney and K. M. Ryan, *ACS Appl. Mater. Interfaces*, 2014, **6**, 18800-18807.
- Y. Liu, S. Zhang and T. Zhu, *ChemElectroChem*, 2014, **1**, 706-713.
- G. H. Yue, X. Q. Zhang, Y. C. Zhao, Q. S. Xie, X. X. Zhang and D. L. Peng, *RSC Adv.*, 2014, **4**, 21450-21455.
- M. Veith, M. Ehses and V. Huch, *New J. Chem.*, 2005, **29**, 154-164.
- S. Jin, N. Li, H. Cui and C. Wang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 19397-19404.
- J. Liu, K. Song, C. Zhu, C.-C. Chen, P. A. van Aken, J. Maier and Y. Yu, *ACS Nano*, 2014, **8**, 7051-7059.
- L. Y. Lim, N. Liu, Y. Cui and M. F. Toney, *Chem. Mater.*, 2014, **26**, 3739-3746.
- N. Nitta and G. Yushin, *Part. Part. Syst. Char.*, 2014, **31**, 317-336.
- H. Jia, R. Klöpsch, X. He, J. P. Badillo, M. Winter and T. Placke, *J. Mater. Chem. A*, 2014, **2**, 17545-17550.
- M. Liu, X. Ma, L. Gan, Z. Xu, D. Zhu and L. Chen, *J. Mater. Chem. A*, 2014, **2**, 17107-17114.
- M.-H. Seo, M. Park, K. T. Lee, K. Kim, J. Kim and J. Cho, *Energ. Environ. Sci.*, 2011, **4**, 425-428.
- K. C. Klavetter, S. M. Wood, Y.-M. Lin, J. L. Snider, N. C. Davy, A. M. Chockla, D. K. Romanovicz, B. A. Korgel, J.-W. Lee, A. Heller and C. B. Mullins, *J. Power Sources*, 2013, **238**, 123-136.
- L. P. Tan, Z. Lu, H. T. Tan, J. Zhu, X. Rui, Q. Yan and H. H. Hng, *J. Power Sources*, 2012, **206**, 253-258.
- A. Jahel, A. Darwiche, C. Matei Ghimbeu, C. Vix-Guterl and L. Monconduit, *J. Power Sources*, 2014, **269**, 755-759.
- G. Cui, L. Gu, L. Zhi, N. Kaskhedikar, P. A. van Aken, K. Müllen and J. Maier, *Adv. Mater.*, 2008, **20**, 3079-3083.
- M.-H. Park, Y. Cho, K. Kim, J. Kim, M. Liu and J. Cho, *Angew. Chem., Int. Ed.*, 2011, **50**, 9647-9650.
- Y. Xiao, M. Cao, L. Ren and C. Hu, *Nanoscale*, 2012, **4**, 7469-7474.
- S. Yoon, C.-M. Park and H.-J. Sohn, *Electrochem. Solid-State Lett.*, 2008, **11**, A42-A45.
- D.-J. Xue, S. Xin, Y. Yan, K.-C. Jiang, Y.-X. Yin, Y.-G. Guo and L.-J. Wan, *J. Am. Chem. Soc.*, 2012, **134**, 2512-2515.
- X. Li, J. Liang, Z. Hou, Y. Zhu, Y. Wang and Y. Qian, *Chem. Commun.*, 2015, **51**, 3882-3885.
- S. Spange, P. Kempe, A. Seifert, A. A. Auer, P. Ecorchard, H. Lang, M. Falke, M. Hietschold, A. Pohlert, W. Hoyer, G. Cox, E. Kockrick and S. Kaskel, *Angew. Chem., Int. Ed.*, 2009, **48**, 8254-8258.

53. S. Grund, P. Kempe, G. Baumann, A. Seifert and S. Spange, *Angew. Chem., Int. Ed.*, 2007, **46**, 628-632.
54. A. A. Auer, A. Richter, A. V. Berezkin, D. V. Guseva and S. Spange, *Macromol. Theory Simul.*, 2012, **21**, 615-628.
55. P. Kempe, T. Löschner, A. A. Auer, A. Seifert, G. Cox and S. Spange, *Chem. Eur. J.*, 2014, **20**, 8040-8053.
56. P. Kempe, T. Löschner, D. Adner and S. Spange, *New J. Chem.*, 2011, **35**, 2735-2739.
57. T. Löschner, A. Mehner, S. Grund, A. Seifert, A. Pohlers, A. Lange, G. Cox, H. J. Hahnle and S. Spange, *Angew. Chem., Int. Ed.*, 2012, **51**, 3258-3261.
58. A. Mehner, A. Pohlers, W. Hoyer, G. Cox and S. Spange, *Macromol. Chem. Phys.*, 2013, **214**, 1000-1010.
59. S. Spange and S. Grund, *Adv. Mater.*, 2009, **21**, 2111-2116.
60. T. Ebert, A. Seifert and S. Spange, *Macromol. Rapid Commun.*, 2015, **36**, 1623-1639.
61. C. Leonhardt, S. Brumm, A. Seifert, G. Cox, A. Lange, T. Ruffer, D. Schaarschmidt, H. Lang, N. Jöhrmann, M. Hietschold, F. Simon and M. Mehring, *ChemPlusChem*, 2013, **78**, 1400-1412.
62. P. Kitschke, A. A. Auer, T. Löschner, A. Seifert, S. Spange, T. Ruffer, H. Lang and M. Mehring, *ChemPlusChem*, 2014, **79**, 1009-1023.
63. C. Leonhardt, S. Brumm, A. Seifert, A. Lange, S. Csihony and M. Mehring, *ChemPlusChem*, 2014, **79**, 1440-1447.
64. P. Kitschke, A. A. Auer, A. Seifert, T. Ruffer, H. Lang and M. Mehring, *Inorg. Chim. Acta*, 2014, **409**, Part B, 472-478.
65. P. Kitschke, T. Ruffer, M. Korb, H. Lang, W. B. Schneider, A. A. Auer and M. Mehring, *Eur. J. Inorg. Chem.*, 2015, **2015**, 5467-5479.
66. C. S. Weinert, A. E. Fenwick, P. E. Fanwick and I. P. Rothwell, *Dalton Trans.*, 2003, 532-539.
67. A. E. Wetherby, Jr., L. R. Göller, A. G. DiPasquale, A. L. Rheingold and C. S. Weinert, *Inorg. Chem.*, 2007, **46**, 7579-7586.
68. T. J. Boyle, L. J. Tribby, L. A. M. Ottley and S. M. Han, *Eur. J. Inorg. Chem.*, 2009, 5550-5560.
69. B. Ottenbours, P. Adriaensens, R. Carleer, D. Vanderzande and J. Gelan, *Polymer*, 1998, **39**, 5293-5300.
70. B. D. Park and B. Riedl, *J. Appl. Polym. Sci.*, 2000, **77**, 1284-1293.
71. R. L. Bryson, G. R. Hatfield, T. A. Early, A. R. Palmer and G. E. Maciel, *Macromolecules*, 1983, **16**, 1669-1672.
72. J. Pola, R. Fajgar, Z. Bastl and L. Diaz, *J. Mater. Chem.*, 1992, **2**, 961-964.
73. P. Y. Timbrell, M. K. Puchert and R. N. Lamb, *Surf. Interface Anal.*, 1994, **21**, 731-736.
74. K. Prabhakaran and T. Ogino, *Surf. Sci.*, 1995, **325**, 263-271.
75. K. Prabhakaran, F. Maeda, Y. Watanabe and T. Ogino, *Appl. Phys. Lett.*, 2000, **76**, 2244-2246.
76. N. A. Tabet, M. A. Salim and A. L. Al-Oteibi, *J. Electron Spectrosc. Relat. Phenom.*, 1999, **101-103**, 233-238.
77. N. Tabet, M. Faiz, N. M. Hamdan and Z. Hussain, *Surf. Sci.*, 2003, **523**, 68-72.
78. S. Rivillon, Y. J. Chabal, F. Amy and A. Kahn, *Appl. Phys. Lett.*, 2005, **87**, 253101.
79. H. Adhikari, P. C. McIntyre, S. Sun, P. Pianetta and C. E. D. Chidsey, *Appl. Phys. Lett.*, 2005, **87**, 263109.
80. M. Matsui, H. Murakami, T. Fujioka, A. Ohta, S. Higashi and S. Miyazaki, *Microelectron. Eng.*, 2011, **88**, 1549-1552.
81. S. K. Sahari, A. Ohta, M. Matsui, K. Mishima, H. Murakami, S. Higashi and S. Miyazaki, *J. Phys.: Conf. Ser.*, 2013, **417**, 012014.
82. C. D. Wagner and A. Joshi, *J. Electron Spectrosc. Relat. Phenom.*, 1988, **47**, 283-313.
83. J.-G. Ren, Q.-H. Wu, H. Tang, G. Hong, W. Zhang and S.-T. Lee, *J. Mater. Chem. A*, 2013, **1**, 1821-1826.
84. W. Li, Z. Yang, J. Cheng, X. Zhong, L. Gu and Y. Yu, *Nanoscale*, 2014, **6**, 4532-4537.
85. C. Lastoskie, K. E. Gubbins and N. Quirke, *Langmuir*, 1993, **9**, 2693-2702.
86. C. Lastoskie, K. E. Gubbins and N. Quirke, *J. Phys. Chem.*, 1993, **97**, 4786-4796.
87. A. Macias-Garcia, M. A. Diaz-Diez, E. M. Cuerda-Correa, M. Olivares-Marin and J. Ganan-Gomez, *Appl. Surf. Sci.*, 2006, **252**, 5972-5975.
88. P. I. Ravikovitch and A. V. Neimark, *Langmuir*, 2006, **22**, 11171-11179.
89. P. I. Ravikovitch, A. Vishnyakov, R. Russo and A. V. Neimark, *Langmuir*, 2000, **16**, 2311-2320.
90. C. J. Rasmussen, A. Vishnyakov, M. Thommes, B. M. Smarsly, F. Kleitz and A. V. Neimark, *Langmuir*, 2010, **26**, 10147-10157.
91. M. Thommes, R. Kohn and M. Fröba, *Appl. Surf. Sci.*, 2002, **196**, 239-249.
92. M. Thommes, R. Kohn and M. Fröba, *J. Phys. Chem. B*, 2000, **104**, 7932-7943.
93. N. U. Hofsløkken and L. Skattebøl, *Acta Chem. Scand.*, 1999, **53**, 258-262.
94. B. Zeynizadeh and T. Behyar, *Z. Naturforsch. B*, 2005, **60**, 453-457.
95. G. M. Sheldrick, *Acta Crystallogr. A*, 2008, **64**, 112-122.
96. A. D. Becke, *J. Chem. Phys.*, 1993, **98**, 5648-5652.
97. C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B*, 1988, **37**, 785-789.
98. R. Ahlrichs, M. Bär, M. Häser, H. Horn and C. Kölmel, *Chem. Phys. Lett.*, 1989, **162**, 165-169.
99. R. Ahlrichs and O. Treutler, *J. Chem. Phys.*, 1995, **102**, 346-354.
100. M. v. Arnim and R. Ahlrichs, *J. Comput. Chem.*, 1998, **19**, 1746-1757.
101. F. Weigend, M. Häser, H. Patzelt and R. Ahlrichs, *Chem. Phys. Lett.*, 1998, **294**, 143-152.
102. F. Weigend and R. Ahlrichs, *Phys. Chem. Chem. Phys.*, 2005, **7**, 3297-3305.
103. S. Grimme, J. Antony, S. Ehrlich and H. Krieg, *J. Chem. Phys.*, 2010, **132**, 154104.

Table of content

Novel germylenes based on salicyl alcoholates were synthesized and their thermally induced twin polymerization to give organic-inorganic hybrid materials was studied. Structural studies including single crystal X-ray diffraction analysis, NMR spectroscopy and DFT-D calculations revealed the formation of oligomers in the solid state and equilibriums in solution. Thermally induced twin polymerization of germylenes gave hybrid materials based on germanium-containing phenolic resins in a single step. Carbonization of these resins under reductive conditions resulted in porous Ge@C materials, which were tested as potential anode materials for rechargeable Li-ion batteries. Reversible capacities of 540 mAhg^{-1} were obtained at a current density of $346 \text{ mA}g^{-1}$ without apparent fading for 100 cycles, which demonstrates that germanium is well accessible in the hybrid material.

