

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Amino Acids as Highly Efficient Modulators for Single Crystals of Zirconium and Hafnium Metal-Organic Frameworks

Ross J. Marshall,^a Claire L. Hobday,^b Colin F. Murphie,^a Sarah L. Griffin,^a Carole A. Morrison,^b Stephen A. Moggach^{b*} and Ross S. Forgan^{a*}

^aWestCHEM School of Chemistry, University of Glasgow, Joseph Black Building, University Avenue, Glasgow, G12 8QQ, UK.

Email: Ross.Forgan@glasgow.ac.uk

Web: <http://www.forganlab.com>

^bEaSTCHEM School of Chemistry, University of Edinburgh, Joseph Black Building, West Mains Road, Edinburgh, EH9 3JJ, UK.

Email: s.moggach@ed.ac.uk

Web: <http://www.moggach.chem.ed.ac.uk>

Abstract

The synthesis of zirconium and hafnium metal-organic frameworks (MOFs) often relies on coordination modulation – the addition of competing monotopic modulators to reaction mixtures – to reproducibly generate highly crystalline material. Typically, large excesses of monocarboxylic acids such as formic, acetic and benzoic acid are applied, but access to diffraction quality single crystals, particularly of UiO-66 topology MOFs, remains troublesome. Herein, we show that amino acids, in particular L-proline, are highly efficient modulators of Zr and Hf MOFs of the UiO-66 series, with as little as four equivalents affording access to large, diffraction quality single crystals that are free of defects. Five crystal structures are reported, including MOFs which previously could not be characterised in this manner, with molecular dynamics simulations utilised to understand dynamic disorder. Additionally, a series of MOFs are characterised in depth, allowing a comparison of the thermal stabilities and porosities for Zr and Hf analogues. We also show that the protocol can be extended to microwave synthesis, and that modulating ability varies dramatically across a series of amino acids. Access to single crystals has facilitated our own in depth study of the mechanical properties of these MOFs, and we expect that our protocols will both enable the discovery of new Zr and Hf MOFs as well as offer new insights into their materials properties.

Introduction

Metal-Organic Frameworks (MOFs) are 3D hybrid materials that have received appreciable amounts of interest in recent years¹ as the almost infinite combination of inorganic metal clusters and organic spacing ligands achievable allows highly specialised materials to be investigated for use in a wide range of applications including selective gas capture and sequestration,² drug delivery³ and catalysis.⁴ Some MOFs have been known to exhibit relatively low chemical and mechanical stabilities, but the use of zirconium, a strong Lewis acid that demonstrates a high affinity for oxygen, results in resilient MOFs as a result of the robust Zr-O bonds that tether the organic and inorganic moieties.⁵

Many zirconium MOFs adopt the well-documented UiO-66 framework topology containing $Zr_6O_4(OH)_4$ secondary building units (SBUs) connected by 12 bridging dicarboxylate ligands, thereby expanding to form cubic framework structures containing large octahedral cages and smaller tetrahedral cages.^{5b} Incorporation of organic ligands that present different coordination environments, including tri- and tetra- topic ligands, into Zr MOFs leads to materials with alternative structures and topologies.⁶ Functionalised ligands presenting greater chemical complexity, or bearing a functional group required for specific post-synthetic modification, have been incorporated in the anticipation of producing highly specialised materials.^{6b, 6d, 6e, 7} Hafnium displays similar chemical properties to zirconium; hafnium MOFs are isostructural with their zirconium analogues, where direct substitution of the Zr_6 SBUs by Hf_6 ones is observed.⁸ There are fewer reports of hafnium MOFs in the literature,^{6i, 9} but they have shown great promise in medicinal applications,¹⁰ as well as in catalysis¹¹ and CO_2 fixation.¹²


Coordination modulation¹³ results in materials with enhanced crystallinity and has recently enabled the isolation of single crystals of zirconium and hafnium MOFs with the UiO-66 topology.^{6b, 6d, 6e, 7c, 7d, 9b, 14} This technique usually requires the addition of large excesses of small foreign materials directly to the MOF synthesis, with small monodentate organic compounds, such as acetic acid and benzoic acid, routinely employed. The precise role of the modulator during synthesis is not known, although it is believed that the crystallisation kinetics are altered, introducing reversibility to the system and ultimately resulting in products with improved crystallinity.¹⁵ Preformation of $Zr_6O_4(OH)_4(RCO_2)_{12}$ building blocks containing the monodentate modulators may also be responsible for the enhanced

crystallinity of the resulting MOFs.^{14b} Under certain conditions, modulation can also promote defect formation, which is prevalent^{9d, 14f, 16} in UiO-66 type MOFs of both Zr and Hf, and these defects can be exploited to confer the MOFs with enhanced gas uptake,¹⁷ proton conduction,¹⁸ mechanical^{5f} or catalytic¹⁹ properties.

Recently the scope of modulators has been broadened and the role of hydrochloric acid in zirconium MOF synthesis has been investigated. HCl modulation was observed to increase the rate of product formation whilst providing access to otherwise inaccessible materials, therefore it has been postulated that HCl could perform numerous roles during synthesis, including conditioning the DMF solvent or assisting in the pre-formation of Zr₆ clusters.^{16b, 20} Despite these advances, reliable isolation of X-ray quality single crystals of UiO-66 topology Zr and Hf MOFs remains troublesome, and so we seek to extend the range of potential modulators for both bulk and single crystal syntheses of Zr and Hf MOF.

Results and Discussion

Herein, we fully investigate for the first time the ability of amino acids to act as modulating agents in the directed synthesis of both zirconium and hafnium MOFs. Amino acids can be viewed as attractive modulating agents as they are readily available small biomolecules and the large diversity of side-chains within these compounds may potentially result in unprecedented modulating properties. We have investigated²¹ a comprehensive range of ligands (**L1-L8**, **Scheme 1**) and report the influence of seven amino acids on the crystallinity of the products obtained, which have the general formula [M₆O₄(OH)₄L₆]_n, where M = Zr⁴⁺ or Hf⁴⁺, and are referred to as **M-L** for simplicity. MOF syntheses were carried out to a general synthetic protocol (see SI, Section S2). One equivalent each of MCl₄ and the chosen ligand were dissolved separately in reagent grade *N,N*-dimethylformamide (DMF), with five equivalents of the amino acid and one equivalent of HCl added to the metal solution. The solutions were combined (the final concentrations of metal and ligand being 45 mM), sonicated and heated for 24 h at 120 °C. The resultant precipitates were thoroughly washed by DMF and methanol, and vacuum dried.²² Powder X-ray diffraction (PXRD) analysis was used to determine the extent of formation and crystallinity of the MOFs in comparison to identical control samples with no amino acid added.

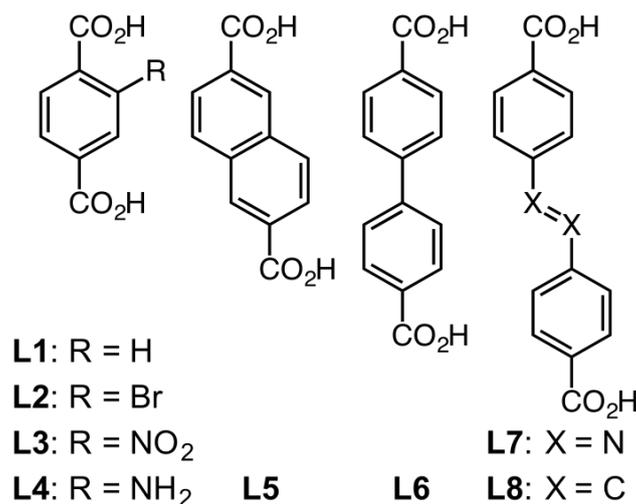

Scheme 1. Chemical structures of the dicarboxylate ligands, **L1-L8**, utilised in this study.

Our examination of this broad experimental parameter space showed dramatic improvements in crystallinity of the Zr MOFs of the longer linkers, **L5-L8**, when certain amino acids were used as modulators; the results for **Zr-L5** (**Figure 1**) are representative of the longer linkers.

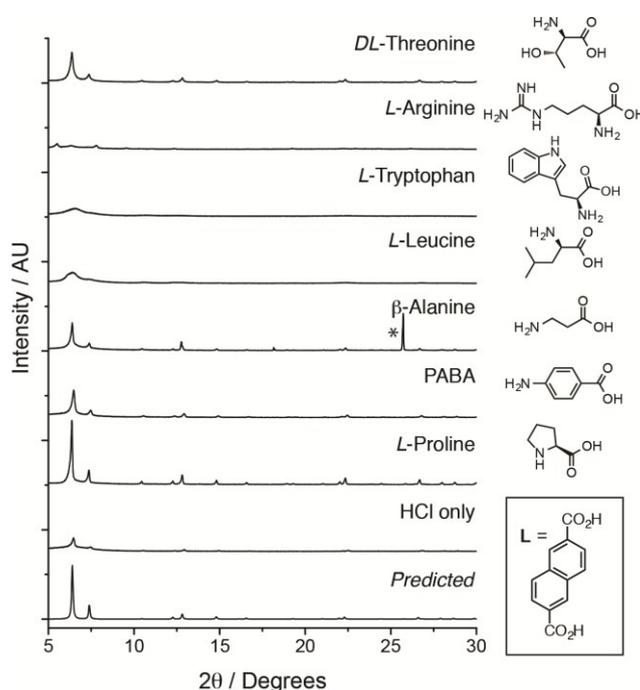


Figure 1. Stacked PXRD patterns of **Zr-L5** synthesised with different amino acid modulators (five equivalents), compared with **Zr-L5** synthesised with one equivalent of HCl only and the pattern predicted from the previously reported crystal structure.^{9b} An unknown crystalline impurity, marked by an asterisk, was occasionally found in β -alanine modulated samples.

The single crystal structure of **Zr-L5** has been reported^{9b} previously, using 47 equivalents of acetic acid as modulator, and comparison of the PXRD patterns of the amino acid modulated syntheses with that predicted from the crystal structure confirm that **Zr-L5** is formed cleanly, and that the smaller, more hydrophobic amino acids, in concert with HCl, significantly enhance the crystallinity of the product in comparison to syntheses using HCl alone.²³ Across the Zr MOFs of **L5-L8**, L-proline stands out as the most effective modulator, with considerable improvements in the crystallinity of the MOFs (**Figure 2a**). SEM images of materials synthesised according to the general synthetic procedure using five equivalents of L-proline (Figures 2b and 2d) show **Zr-L5** and **Zr-L7** to form sheets of polycrystalline material, which has been observed previously²⁴ for **Zr-L7**, with intergrown crystals of around 5-10 μm for **Zr-L5** and up to 50 μm for **Zr-L7**. In contrast, **Zr-L6** and **Zr-L8** tend to form discrete octahedral crystals (Figures 2c and 2e), around 10-20 μm in size for **Zr-L6** (but with occasional larger crystals up to 60 μm) and 5-10 μm size for **Zr-L8**, which also forms some spherical polycrystalline assemblies (see SI, Section S3).

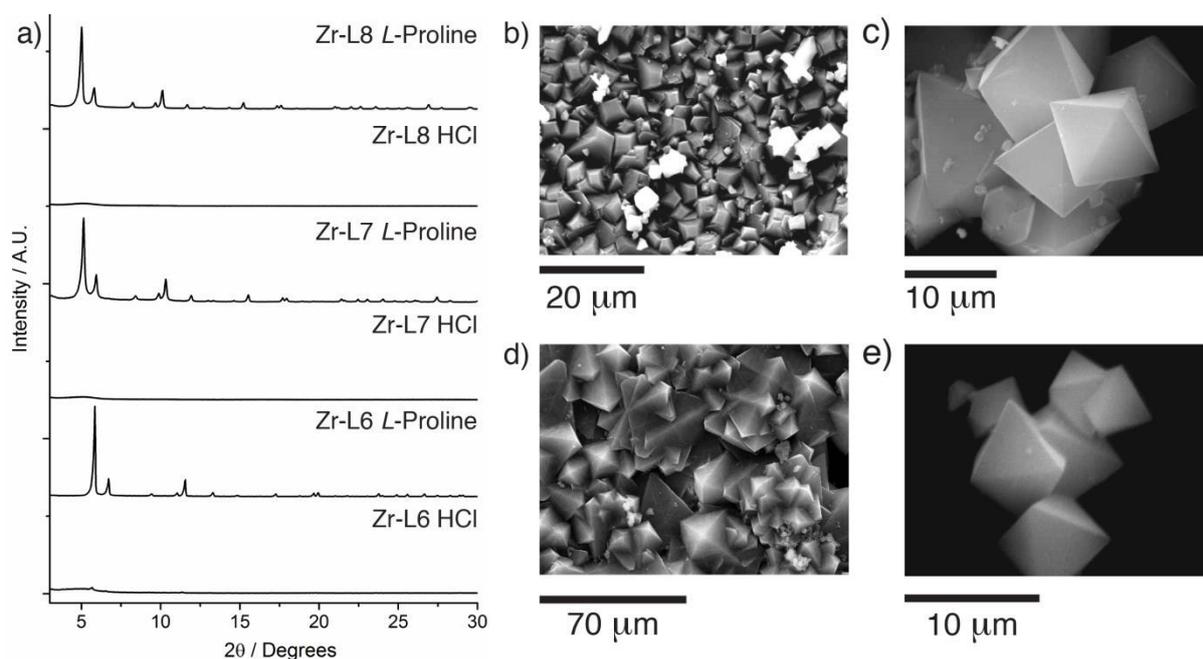


Figure 2. a) PXRD patterns showing the effects of incorporation of 5 equivalents of L-proline and one of HCl into solvothermal syntheses of Zr MOFs of **L6-L8** compared to addition of HCl alone. SEM images of the MOFs formed using this protocol: b) **Zr-L5**, c) **Zr-L6**, d) **Zr-L7**, e) **Zr-L8**.

In contrast, the synthesis of Zr MOFs of **L1-L4**, all terephthalate-based linkers, did not show any appreciable benefits when amino acid modulation was employed in comparison with

samples prepared using HCl alone. The binding of monocarboxylic acids to the zirconium cluster *in situ* has been proposed to decelerate the rate of crystallisation, through establishing exchange equilibrium with the bridging organic ligands,¹⁵ and so we are unable to account for this unusual, seemingly size-selective phenomenon.

The overwhelming performance exhibited by L-proline directed future modulation studies of zirconium MOFs. Considering our synthetic technique combines HCl and L-proline it was vital to investigate the modulation ability of L-proline in the presence/absence of HCl, considering the recent work detailing the advantages of addition of HCl to zirconium MOF syntheses.^{16b, 20} **Zr-L6** (UiO-67) was used to demonstrate the effect of L-proline modulation (See SI, Section S4). PXRD patterns (Figure 3a) showed that while addition of one equivalent of HCl alone to solvothermal syntheses was capable of intermittently producing relatively crystalline material,²³ addition of five equivalents of L-proline consistently produced better quality materials, and a synergistic effect appears to be present when both are incorporated into syntheses. Proline equivalency studies on **Zr-L6** (See SI Section S4) revealed that the addition of between 4 and 10 equivalents of L-proline to syntheses alongside HCl resulted in significantly improved PXRD patterns (Figure 3b). SEM images of the synthesised materials (Figure 3c) showed that when two equivalents of L-proline are added to the synthesis, the **Zr-L6** that forms is ill-defined with a globular morphology, while samples with between four and ten equivalents of L-proline added to syntheses resulted in well-defined octahedral crystals around 10-20 μm in size.

Examination of both PXRD patterns and SEM images suggest that four to five equivalents of L-proline and one equivalent of HCl represent the most efficient modulating conditions. Syntheses can also be carried out under microwave heating,²⁵ with reduced synthesis times (see SI, Section S5). **Zr-L6** prepared in 1 h in a single mode microwave cavity, using five equivalents of L-proline, showed comparable particle size, morphology and porosity to samples prepared by heating for 24 h in the oven.

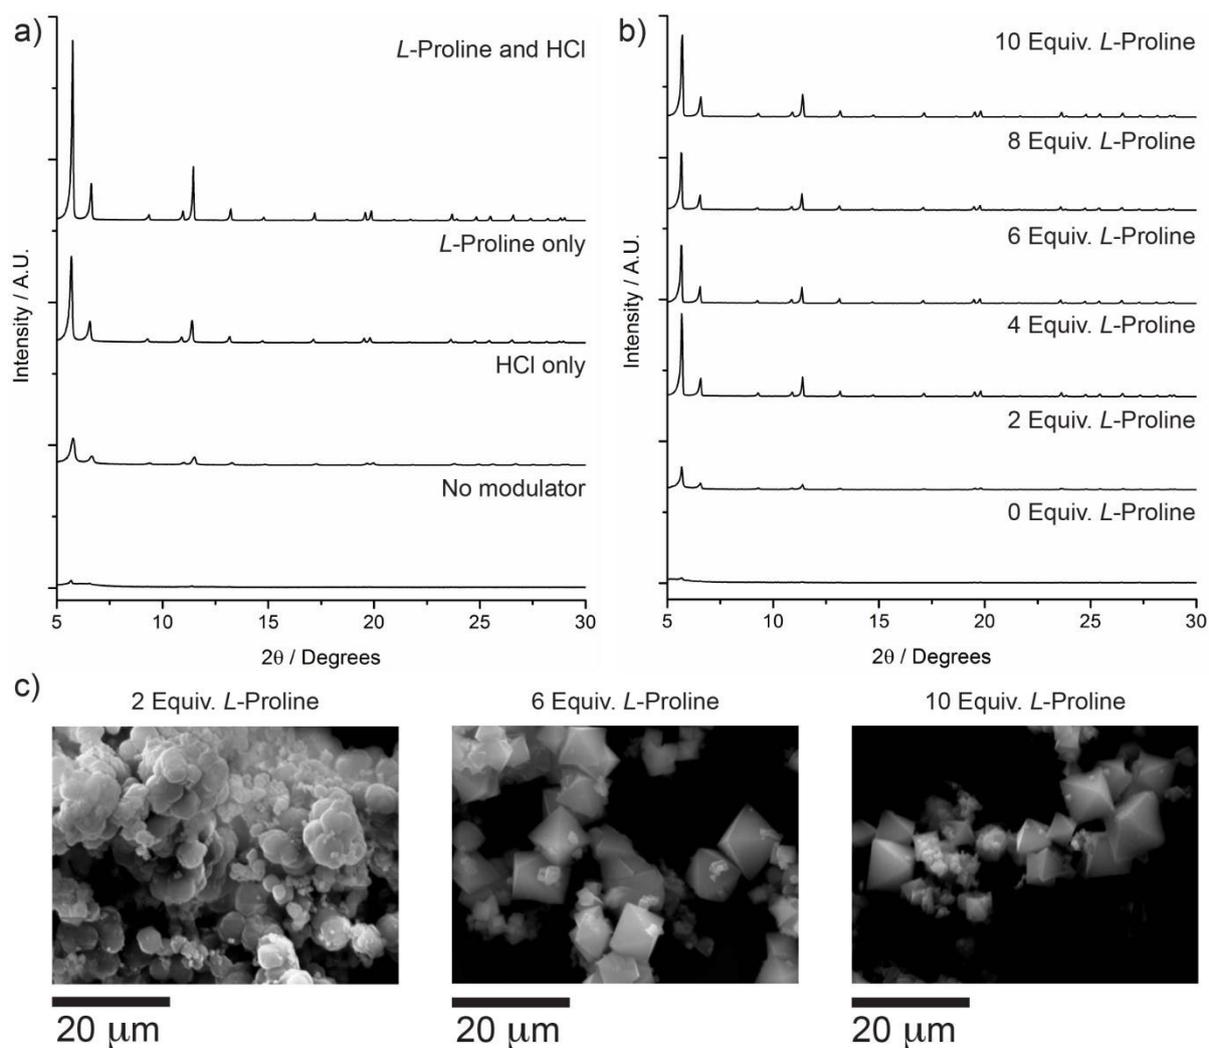


Figure 3. a) PXRD patterns of syntheses of **Zr-L6** with differing modulators, showing that *L*-proline (5 equivalents) is an effective modulator alone but seems to give best results in concert with HCl (one equiv). b) PXRD patterns showing the effect of varying the amount of *L*-proline added to syntheses of **Zr-L6** which also contain HCl, showing little improvement after more than four equivalents are used. c) SEM images show that **Zr-L6** synthesised using two equivalents of *L*-proline produce an ill-defined material, while addition of either six or ten equivalents yields octahedral crystals around 10 μm in size.

Further optimisation of the *L*-proline/HCl modulated conditions allowed the synthesis (see SI, Section S6) of single crystals of many of the MOFs (Figures 4a-4c). High quality single crystals of **Zr-L6**, approximately 60 μm in size, were synthesised solvothermally, at 120 °C in DMF for 24 h, in the presence of 5 equivalents of *L*-proline and one equivalent of HCl, which is minimal when compared to the large excess of modulators commonly required for effective modulation. Until recently, **Zr-L6** had only been isolated as a microcrystalline powder however, during the course of this study single crystals were reported by a number of

different groups. Kaskel *et al.* synthesised the MOF solvothermally, using 117 equivalents of acetic acid modulator,²⁶ Lillerud *et al.* used 30 equivalents of benzoic acid and one equivalent of HCl as modulators in solvothermal syntheses using glassware first pre-treated with basic aqueous solution,²⁷ Kim *et al.* reported a synthesis modulated by 30 equivalents of benzoic acid,²⁸ while Shafir and Gutov reported a similar benzoic acid (30 equivalents) modulated route which included a subsequent “healing” step using additional **L6**. Our own determination of the crystal structure of **Zr-L6** showed it to be very similar to those reported recently (Figure 4d), with no evidence of defects or diffuse scattering observed.²⁹

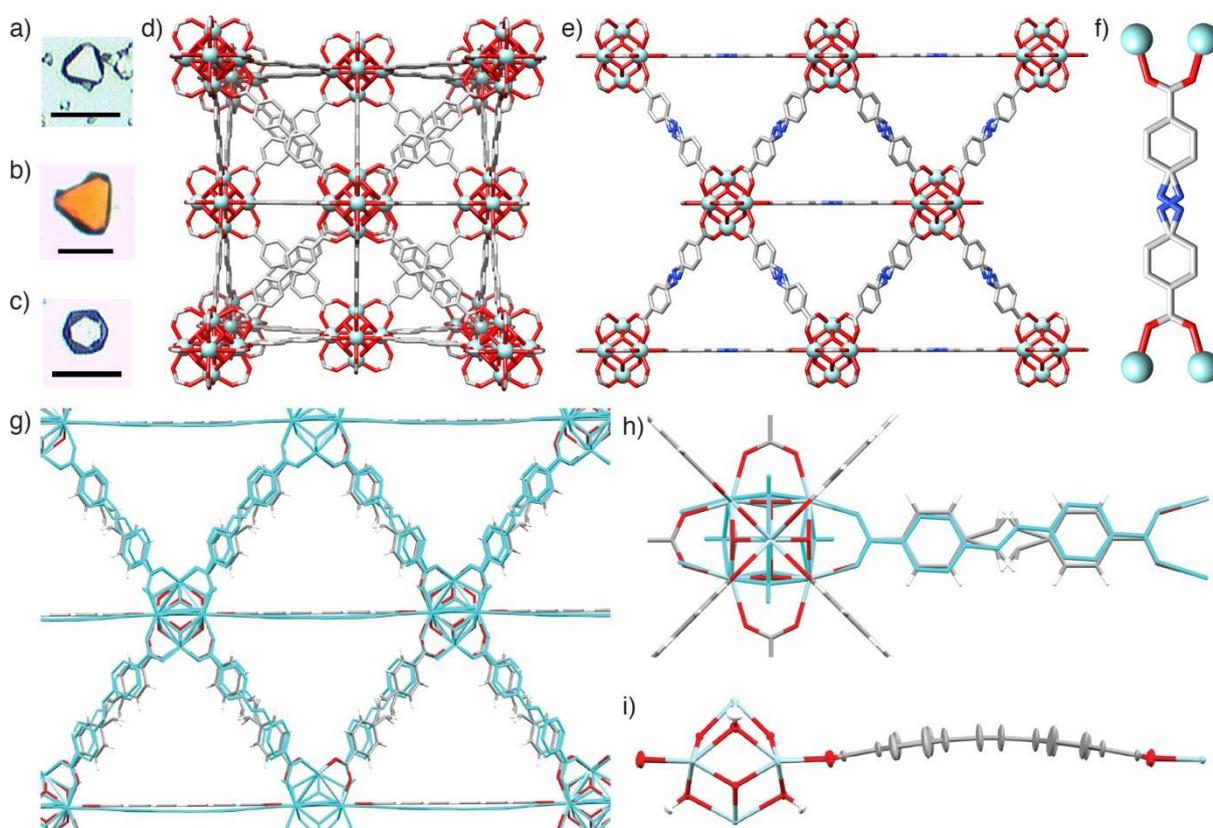


Figure 4. Pictures of single crystals of a) **Zr-L6**, b) **Zr-L7**, and c) **Zr-L8** prepared by L-proline modulation. Scale bars 100 μm . d) Packing structure of **Zr-L6** viewed down crystallographic *a* axis. e) Packing structure of **Zr-L7** from a different angle. f) Disorder in the geometrically frustrated azobenzene ligand in **Zr-L7**. Overlay of closely correlated calculated (teal, MD simulations) and experimental structures of **Zr-L8**, which is isostructural with **Zr-L7**, viewed g) in a packing arrangement, and h) zoomed in onto a single **L8** linker, showing the simulation closely matches the observed disorder. i) Atomic pair-distribution function derived from the MD trajectory showing large thermal motion in the bent **L8** linker.

Similarly, L-proline modulation yielded 50-100 μm single crystals of both **Zr-L7** and **Zr-L8**, which have “bent” linkers. **Zr-L7** was reported previously in 2012 by Behrens *et al.*, with the use of 30 equivalents of benzoic acid as modulator resulting in crystalline sheets rather than discrete single crystals, and weak diffraction combined with disorder meaning no crystal structure could be elucidated.²⁴ A recent catalytic study reported an acetic acid (525 equivalents) modulated synthesis of **Zr-L7** that resulted in micron-sized particles.³⁰ Isolation of discrete octahedral single crystals of **Zr-L7** and **Zr-L8** was possible using four equivalents of L-proline and one equivalent of HCl in a solvothermal synthesis at 100 °C for 48 h in DMF. During repeated syntheses, it was noted that order of addition was key to gaining large single crystals; addition of HCl to a pre-sonicated mixture of the other reagents provided optimal results.

Determination of the crystal structures of the closely related **Zr-L7** and **Zr-L8** MOFs revealed them to be isostructural (Figure 4e). Despite the non-linearity of the “bent” azobenzene and stilbene linkers, **L7** and **L8**, the resultant MOFs crystallise in the cubic *Fm-3m* space group, with the ligands disordered at their interiors and exhibiting geometric frustration (Figure 4f). The longer linkers result in larger unit cells; for **Zr-L7**, $a = 29.3248(8)$ Å³¹ and for **Zr-L8**, the larger value of $a = 29.8884(3)$ Å may be due to the longer length of the C=C bond compared to the N=N bond. Indeed, the separation between the Zr₆ metal clusters, measured from analogous carboxylate oxygen atoms on an individual linker molecule, increases from 13.3104(2) Å in **Zr-L7** to 13.5713(1) Å in **Zr-L8**, illustrating the increase in linker length.

Molecular dynamics (MD) simulations were utilised to understand the nature of the disorder in the MOFs and also to elucidate the slight differences in unit cell values (see SI, Section S7). We have previously used MD simulations to characterise the structural properties of **Zr-L7** in a communication discussing its mechanical properties,²¹ and so analogous calculations were carried out on **Zr-L8**. The simulations confirm that the increase in unit cell length from **Zr-L7** to **Zr-L8** is a consequence of moving from an azobenzene to a stilbene linker, and reveal that the geometrically frustrated ligands, **L7** and **L8**, are accommodated in the structures by bowing out of the mirror plane, sitting above and below the plane with bowing angles as high as 10° (Figure 4g, average value 5(3)°, see SI, Section S7). The average effect

of this dynamic disorder process, wherein the linkers bend and flip between opposite sides of the mirror plane, is the frustrated linear arrangement as observed in the crystal structure.

The time-averaged structures generated by these simulations show a close correlation to the spatially-averaged disorder in the experimental crystal structures (Figure 4h), suggesting that the flexing of the ligand is responsible for the disorder, and atomic pair-distribution functions derived from the MD trajectory show that the ligand is indeed the most dynamic component of the structure (Figure 4i). Finally, key bond distances within the Zr_6 clusters of **Zr-L8** match closely to those of its solid-state structure and those calculated for UiO-66 (**Zr-L1**) by Lamberti *et al.*,^{16d} validating the simulations. The disorder model applied to the structures of **Zr-L7** and **Zr-L8** is very representative of the bulk material; PXRD patterns predicted from the single crystal structures match the experimental patterns from bulk-synthesised samples very closely (see SI, Section S7).

Following effective amino acid modulation of the zirconium MOFs, we investigated the suitability of this technique for the synthesis of their hafnium analogues (See SI, Section S8). We initially sought to investigate the effect of both HCl and L-proline inclusion during the synthesis of **Hf-L6**, analogous to the control experiments performed for **Zr-L6** (Figure 5a). Surprisingly, HCl alone proved to be an ineffective modulator for synthesis of **Hf-L6**, even in the quantities found to modulate the synthesis of **Zr-L6** by Farha *et al.*,^{16b} however L-proline is observed to greatly enhance crystallinity. As with **Zr-L6**, it was observed that a combination of one equivalent of HCl and five equivalents of L-proline in the synthetic mixture leads to the greatest improvement in crystallinity of **Hf-L6**, yielding 10-20 μm octahedral crystals instead of amorphous material (Figures 5b and 5c). Subsequently, syntheses of Hf-MOFs of **L1-L8** were attempted using HfCl_4 as a replacement for ZrCl_4 in the reaction mixture, and modulated by six amino acids.³² As with the zirconium analogues, the greatest enhancement in crystallinity from amino acid modulation is observed for the Hf MOFs of the longer linkers, **L5-L8**, although *para*-aminobenzoic acid seems to slightly improve the PXRD patterns of the Hf MOFs of the terephthalate ligands, **L1-L4**, when it is used as the modulator. For the longer linkers, the incorporation of smaller hydrophobic amino acids into MOF synthesis results in significantly improved crystallinity. L-Proline is again found to be the most effective modulator, although the synthesis of **Hf-L8** seems to benefit most from inclusion of L-tryptophan.

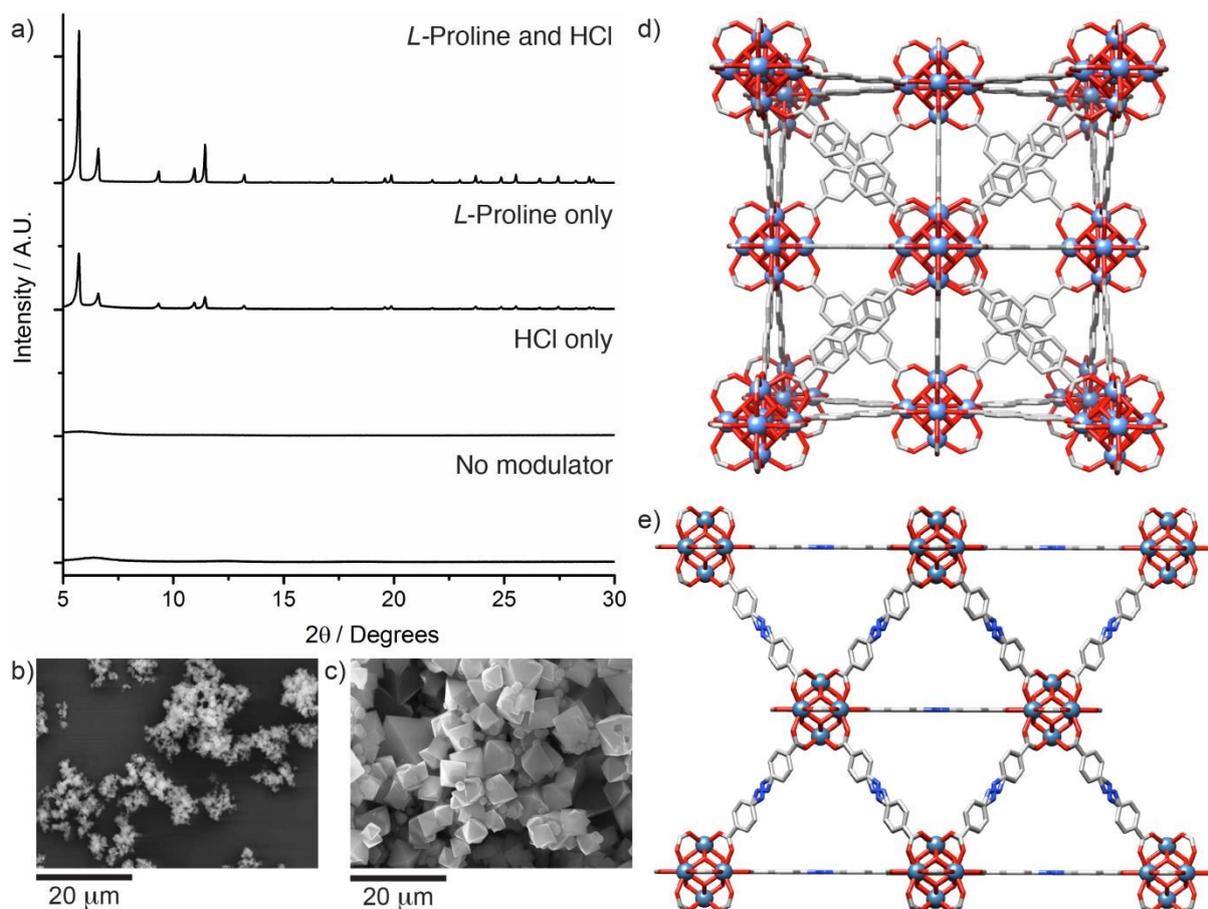


Figure 5. a) Stacked PXRD patterns showing crystallinity of **Hf-L6** is enhanced by L-proline modulation, particularly in concert with HCl, which does not give crystalline material when used alone. SEM images of the products of b) unmodulated synthesis and c) L-proline and HCl modulated synthesis of **Hf-L6**. d) Packing structure derived from the crystal structure of **Hf-L6**. e) Packing structure derived from the crystal structure of **Hf-L7**, with disordered azobenzene linkers. Disorder in phenyl ring orientations not shown.

Single crystals of **Hf-L6** suitable for X-ray diffraction were isolated from solvothermal syntheses in DMF at 120 °C for 24 h with five equivalents of L-proline and one equivalent of HCl as modulators (See SI, Section S9). With small modifications in the synthesis procedure, it was possible to isolate single crystals of **Hf-L7**, using four equivalents of L-proline and one of HCl as modulators in a solvothermal synthesis in DMF at 100 °C for 48 h. Both MOFs are, as expected, isostructural to their zirconium analogues, with a comparison of some pertinent crystallographic details from the five structures (Table 1) illustrating the similarities between the Zr and Hf analogues. We have as yet been unable to isolate single crystals of **Hf-L8**, likely due to the tendency to form spherical microcrystalline architectures when modulated by L-proline in a manner similar to **Zr-L8** (see SI, Section S8).

Table 1. A comparison of some crystallographic parameters for the Zr and Hf MOFs characterised by single crystal X-ray diffraction in this study.

MOF	Unit Cell Edge / Å	Unit Cell Vol / Å ³	M-OOC bond / Å	M ₆ separation / Å ^a
Zr-L6	26.8564(5)	19370.6(11)	2.227(3)	11.209(4)
Hf-L6	26.7451(1)	19130.9(2)	2.214(2)	11.171(4)
Zr-L7	29.3248(8)	25217.7(12)	2.233(6)	12.960(8)
Hf-L7	29.2116(9)	24926.7(20)	2.194(12)	12.959(17)
Zr-L8	29.8884(3)	26699.8(8)	2.199(6)	13.419(8)

^aMeasured as the separation between opposite carboxylate oxygen atoms of one linker molecule

With a range of analogous Zr and Hf MOFs in hand, it was possible to examine their physical properties and similarities. Previous reports of the monocarboxylic acid modulation of **Zr-L6** have described^{6d, 16a, 19, 28} incorporation of acid modulators into the structure, postulated to be at defect or surface inclusion sites, and so ¹H NMR spectra of acid-digested samples of Zr and Hf MOFs of **L5-L8** were examined for evidence of L-proline incorporation (see SI, Section S10). Only **Zr-L5** and **Hf-L5** appeared to contain any appreciable quantities of L-proline or its breakdown products, which may be due to their smaller pore size than the other MOFs, although their incorporation at defects or as surface ligands cannot be ruled out. Thermogravimetric analysis (TGA) of the MOFs confirms that the Hf MOFs retain the thermal stability of their Zr analogues (See SI, Section S11), while an additional mass loss event at 350-450 °C for **Zr-L5** and **Hf-L5** is observed that can be ascribed to removal of incorporated L-proline, with a modulator content of 10% w/w calculated for the two analogous MOFs. Subtle changes in TGA profiles are evident as the ligand is changed for both the Zr and Hf MOFs, indicating that the organic linker has a role to play in the thermal stability of the MOFs.

N₂ adsorption isotherms (see SI, Section S12) carried out at 77 K on the L-proline modulated materials show the high surface areas expected for highly crystalline MOFs (Figure 6). In the case where the Zr MOFs have been reported previously,^{9b, 16b, 24, 30} the BET surface areas closely correlate to those previously measured; 1300 m²g⁻¹ (**Zr-L5**), 2465 m²g⁻¹ (**Zr-L6**), 2830 m²g⁻¹ (**Zr-L7**) and 2950 m²g⁻¹ (**Zr-L8**). The value for **Zr-L5** is slightly lower than reported previously by Kaskel *et al.* (1400 m²g⁻¹)^{9b} which may be a consequence of the

presence of L-proline, as indicated by ^1H NMR spectroscopy and TGA. Pore size distributions calculated using QSDFT show an increase in major pore diameter in concert with the increase in linker length. The Hf analogues show decreased gravimetric surface areas in line with the increased mass of Hf compared to Zr, however, the surface areas of **Hf-L5** ($810\text{ m}^2\text{g}^{-1}$) and **Hf-L8** ($2020\text{ m}^2\text{g}^{-1}$) are slightly lower than expected based on this mass increase. Interestingly, both of these MOFs display spherical microcrystalline aggregates under SEM imaging, whereas all other MOFs formed either discrete single crystals or films, but the effect of morphology on accessible surface area has not been further investigated. The BET surface areas of **Hf-L6** ($1930\text{ m}^2\text{g}^{-1}$) and **Hf-L7** ($2270\text{ m}^2\text{g}^{-1}$) correlate closely to their corresponding Zr analogues.

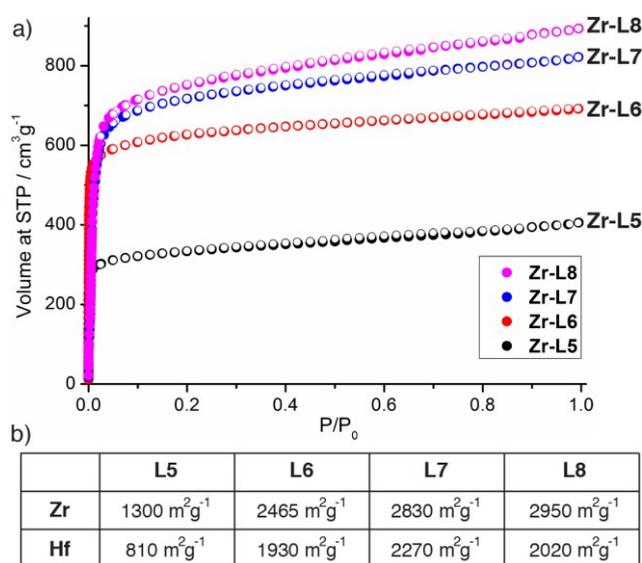


Figure 6. a) N₂ adsorption isotherms (77 K) for **Zr-L5**, **Zr-L6**, **Zr-L7** and **Zr-L8**. b) BET surface areas for all Zr and Hf MOFs, as derived from their N₂ adsorption isotherms.

Conclusions

To conclude, we report that amino acids, in concert with HCl, can effectively modulate the syntheses of zirconium and hafnium MOFs, enhancing crystallinity and ultimately resulting in the isolation of previously inaccessible MOFs, many as single crystals suitable for X-ray diffraction. Whilst a range of amino acids have been investigated, the greatest success has been achieved using L-proline, which is required in as little as four equivalents – a great reduction when compared with the large excess of modulator routinely required for single crystal synthesis (See SI, Section S13) – to offer unprecedented access to defect free single

crystals of a number of UiO-66 topology MOFs of both Zr and Hf.³³ The ability to reliably synthesise Zr and Hf MOFs simply and efficiently has allowed us to compare the properties of the analogous materials, and found that the change in metal has little effect on thermal stability, and N₂ adsorption isotherms show the MOFs have the high surface areas expected from materials of excellent crystallinity. Access to single crystals of Zr MOFs has already facilitated detailed investigations of their mechanical properties by high pressure single crystal X-ray diffraction and nanoindentation,²¹ and also single-crystal to single-crystal post-synthetic modification.^{14e} We expect that adoption of amino acid modulated synthetic protocols, either solvothermally or microwave heated, will result in the improved synthesis of other Zr and Hf MOFs, and we are currently attempting to elucidate the mechanism of modulation while extending the protocol to MOFs linked by other metals.

Acknowledgements

RSF thanks the Royal Society for receipt of a University Research Fellowship and the University of Glasgow for funding. The research was supported at the University of Glasgow by EPSRC (EP/L004461/1). CLH thanks the EPSRC and the University of Edinburgh for a studentship. CAM acknowledges the UK Car-Parrinello consortium (EP/K01465X/1) for access to the high performance computing resource ARCHER, as managed by the Edinburgh Parallel Computing Service. The authors gratefully acknowledge pump-priming funding from the EPSRC Directed Assembly Network (PP 14 05 03). We thank Mr Jim Gallagher at the University of Glasgow for assistance with SEM. The data which underpin this work are available at <http://dx.doi.org/10.5525/gla.research-data.251>. CCDC 1442841–1442841 contain the supplementary crystallographic data for this paper.

References

1. H. Furukawa, K. E. Cordova, M. O'Keeffe and O. M. Yaghi, *Science*, 2013, **341**, 6149.
2. a) D. Britt, D. Tranchemontagne and O. M. Yaghi, *Proc. Natl. Acad. Sci. U.S.A.*, 2008, **105**, 11623-11627; b) S. Ma and H.-C. Zhou, *Chem. Commun.*, 2010, **46**, 44-53; c) L. J. Murray, M. Dinca and J. R. Long, *Chem. Soc. Rev.*, 2009, **38**, 1294-1314; d) K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T.-H. Bae and J. R. Long, *Chem. Rev.*, 2012, **112**, 724-781.
3. a) A. C. McKinlay, R. E. Morris, P. Horcajada, G. Férey, R. Gref, P. Couvreur and C. Serre, *Angew. Chem. Int. Ed.*, 2010, **49**, 6260-6266; b) P. Horcajada, T. Chalati, C. Serre, B. Gillet, C. Sebrie, T. Baati, J. F. Eubank, D. Heurtaux, P. Clayette, C. Kreuz, J.-S. Chang, Y. K. Hwang, V. Marsaud, P.-N. Bories, L. Cynober, S. Gil, G. Férey, P. Couvreur and R. Gref, *Nat. Mater.*, 2010, **9**, 172-178; c) P. Horcajada, C. Serre, G. Maurin, N. A. Ramsahye, F. Balas, M. Vallet-Regí, M. Sebban, F. Taulelle and G. Férey, *J. Am. Chem. Soc.*, 2008, **130**, 6774-6780.
4. a) J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450-1459; b) M. Yoon, R. Srirambalaji and K. Kim, *Chem. Rev.*, 2012, **112**, 1196-1231; c) A. Corma, H. García and F. X. Llabrés i Xamena, *Chem. Rev.*, 2010, **110**, 4606-4655.
5. a) R. J. Marshall, T. Richards, C. Hobday, C. F. Murphie, C. Wilson, S. A. Moggach, T. D. Bennett and R. S. Forgan, *Dalton Trans.*, 2016, DOI: 10.1039/C1035DT03178H; b) J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850-13851; c) J. B. DeCoste, G. W. Peterson, H. Jasuja, T. G. Glover, Y.-G. Huang and K. S. Walton, *J. Mat. Chem. A*, 2013, **1**, 5642-5650; d) M. Kandiah, M. H. Nilsen, S. Usseglio, S. Jakobsen, U. Olsbye, M. Tilset, C. Larabi, E. A. Quadrelli, F. Bonino and K. P. Lillerud, *Chem. Mater.*, 2010, **22**, 6632-6640; e) J. E. Mondloch, M. J. Katz, N. Planas, D. Semrouni, L. Gagliardi, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2014, **50**, 8944-8946; f) B. Van de Voorde, I. Stassen, B. Bueken, F. Vermoortele, D. De Vos, R. Ameloot, J.-C. Tan and T. D. Bennett, *J. Mat. Chem. A*, 2015, **3**, 1737-1742; g) H. Wu, T. Yildirim and W. Zhou, *J. Phys. Chem. Lett.*, 2013, **4**, 925-930; h) L.-M. Yang, E. Ganz, S. Svelle and M. Tilset, *J. Mat. Chem. C*, 2014, **2**, 7111-7125; i) C. Hobday, R. J. Marshall, C. F. Murphie, T. Richards, D. Allan, T. Duren, F.-X.

- Coudert, R. S. Forgan, C. A. Morrison, S. A. Moggach and T. D. Bennett, *Angew. Chem. Int. Ed.*, 2016, DOI: 10.1002/anie.201509352.
6. a) R. Wang, Z. Wang, Y. Xu, F. Dai, L. Zhang and D. Sun, *Inorg. Chem.*, 2014, **53**, 7086-7088; b) H. Furukawa, F. Gándara, Y.-B. Zhang, J. Jiang, W. L. Queen, M. R. Hudson and O. M. Yaghi, *J. Am. Chem. Soc.*, 2014, **136**, 4369-4381; c) V. Guillerme, F. Ragon, M. Dan-Hardi, T. Devic, M. Vishnuvarthan, B. Campo, A. Vimont, G. Clet, Q. Yang, G. Maurin, G. Férey, A. Vittadini, S. Gross and C. Serre, *Angew. Chem. Int. Ed.*, 2012, **51**, 9267-9271; d) A. Schaate, P. Roy, A. Godt, J. Lippke, F. Waltz, M. Wiebcke and P. Behrens, *Chem. Eur. J.*, 2011, **17**, 6643-6651; e) A. Schaate, P. Roy, T. Preuße, S. J. Lohmeier, A. Godt and P. Behrens, *Chem. Eur. J.*, 2011, **17**, 9320-9325; f) W. Morris, B. Voloskiy, S. Demir, F. Gándara, P. L. McGrier, H. Furukawa, D. Cascio, J. F. Stoddart and O. M. Yaghi, *Inorg. Chem.*, 2012, **51**, 6443-6445; g) T. C. Wang, W. Bury, D. A. Gómez-Gualdrón, N. A. Vermeulen, J. E. Mondloch, P. Deria, K. Zhang, P. Z. Moghadam, A. A. Sarjeant, R. Q. Snurr, J. F. Stoddart, J. T. Hupp and O. K. Farha, *J. Am. Chem. Soc.*, 2015, **137**, 3585-3591; h) D. Feng, Z.-Y. Gu, J.-R. Li, H.-L. Jiang, Z. Wei and H.-C. Zhou, *Angew. Chem. Int. Ed.*, 2012, **51**, 10307-10310; i) D. Feng, H.-L. Jiang, Y.-P. Chen, Z.-Y. Gu, Z. Wei and H.-C. Zhou, *Inorg. Chem.*, 2013, **52**, 12661-12667; j) D. Feng, K. Wang, J. Su, T.-F. Liu, J. Park, Z. Wei, M. Bosch, A. Yakovenko, X. Zou and H.-C. Zhou, *Angew. Chem. Int. Ed.*, 2015, **54**, 149-154; k) J. E. Mondloch, W. Bury, D. Fairen-Jimenez, S. Kwon, E. J. DeMarco, M. H. Weston, A. A. Sarjeant, S. T. Nguyen, P. C. Stair, R. Q. Snurr, O. K. Farha and J. T. Hupp, *J. Am. Chem. Soc.*, 2013, **135**, 10294-10297; l) W. Liang, H. Chevreau, F. Ragon, P. D. Southon, V. K. Peterson and D. M. D'Alessandro, *CrystEngComm*, 2014, **16**, 6530-6533.
7. a) P. W. Siu, Z. J. Brown, O. K. Farha, J. T. Hupp and K. A. Scheidt, *Chem. Commun.*, 2013, **49**, 10920-10922; b) S. J. Garibay and S. M. Cohen, *Chem. Commun.*, 2010, **46**, 7700-7702; c) H.-L. Jiang, D. Feng, T.-F. Liu, J.-R. Li and H.-C. Zhou, *J. Am. Chem. Soc.*, 2012, **134**, 14690-14693; d) B. Wang, H. Huang, X.-L. Lv, Y. Xie, M. Li and J.-R. Li, *Inorg. Chem.*, 2014, **53**, 9254-9259; e) K. Manna, T. Zhang and W. Lin, *J. Am. Chem. Soc.*, 2014, **136**, 6566-6569; f) H. Fei and S. M. Cohen, *Chem. Commun.*, 2014, **50**, 4810-4812.
8. S. Jakobsen, D. Gianolio, D. S. Wragg, M. H. Nilsen, H. Emerich, S. Bordiga, C. Lamberti, U. Olsbye, M. Tilset and K. P. Lillerud, *Phys. Rev. B*, 2012, **86**, 125429.

9. a) V. Bon, I. Senkovska, I. A. Baburin and S. Kaskel, *Cryst. Growth. Des.*, 2013, **13**, 1231-1237; b) V. Bon, I. Senkovska, M. S. Weiss and S. Kaskel, *CrystEngComm*, 2013, **15**, 9572-9577; c) V. Bon, V. Senkovskyy, I. Senkovska and S. Kaskel, *Chem. Commun.*, 2012, **48**, 8407-8409; d) M. J. Cliffe, W. Wan, X. Zou, P. A. Chater, A. K. Kleppe, M. G. Tucker, H. Wilhelm, N. P. Funnell, F.-X. Coudert and A. L. Goodwin, *Nat. Commun.*, 2014, **5**, 4176; e) M. Zhang, Y.-P. Chen, M. Bosch, T. Gentle, K. Wang, D. Feng, Z. U. Wang and H.-C. Zhou, *Angew. Chem. Int. Ed.*, 2014, **53**, 815-818; f) P. Xydias, I. Spanopoulos, E. Klontzas, G. E. Froudakis and P. N. Trikalitis, *Inorg. Chem.*, 2014, **53**, 679-681.
10. a) K. Lu, C. He and W. Lin, *J. Am. Chem. Soc.*, 2014, **136**, 16712-16715; b) K. E. deKrafft, W. S. Boyle, L. M. Burk, O. Z. Zhou and W. Lin, *J. Mat. Chem.*, 2012, **22**, 18139-18144.
11. J. Zheng, M. Wu, F. Jiang, W. Su and M. Hong, *Chem. Sci.*, 2015, **6**, 3466-3470.
12. M. H. Beyzavi, R. C. Klet, S. Tussupbayev, J. Borycz, N. A. Vermeulen, C. J. Cramer, J. F. Stoddart, J. T. Hupp and O. K. Farha, *J. Am. Chem. Soc.*, 2014, **136**, 15861-15864.
13. C. V. McGuire and R. S. Forgan, *Chem. Commun.*, 2015, **51**, 5199-5217.
14. a) M. I. Gonzalez, E. D. Bloch, J. A. Mason, S. J. Teat and J. R. Long, *Inorg. Chem.*, 2015, **54**, 2995-3005; b) V. Guillermin, S. Gross, C. Serre, T. Devic, M. Bauer and G. Férey, *Chem. Commun.*, 2010, **46**, 767-769; c) B. Li, B. Gui, G. Hu, D. Yuan and C. Wang, *Inorg. Chem.*, 2015, **54**, 5139-5141; d) L. Li, S. Tang, C. Wang, X. Lv, M. Jiang, H. Wu and X. Zhao, *Chem. Commun.*, 2014, **50**, 2304-2307; e) R. J. Marshall, S. L. Griffin, C. Wilson and R. S. Forgan, *J. Am. Chem. Soc.*, 2015, **137**, 9527-9530; f) C. A. Trickett, K. J. Gagnon, S. Lee, F. Gándara, H.-B. Bürgi and O. M. Yaghi, *Angew. Chem. Int. Ed.*, 2015, **54**, 11162-11167; g) G. Wißmann, A. Schaate, S. Lilienthal, I. Bremer, A. M. Schneider and P. Behrens, *Micropor. Mesopor. Mater.*, 2012, **152**, 64-70.
15. G. Zahn, P. Zerner, J. Lippke, F. L. Kempf, S. Lilienthal, C. A. Schroder, A. M. Schneider and P. Behrens, *CrystEngComm*, 2014, **16**, 9198-9207.
16. a) O. V. Gutov, M. G. Hevia, E. C. Escudero-Adán and A. Shafir, *Inorg. Chem.*, 2015, **54**, 8396-8400; b) M. J. Katz, Z. J. Brown, Y. J. Colon, P. W. Siu, K. A. Scheidt, R. Q. Snurr, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2013, **49**, 9449-9451; c) G. C. Shearer, S. Chavan, J. Ethiraj, J. G. Vitillo, S. Svelle, U. Olsbye, C. Lamberti, S. Bordiga and K. P. Lillerud, *Chem. Mater.*, 2014, **26**, 4068-4071; d) L.

- Valenzano, B. Civalleri, S. Chavan, S. Bordiga, M. H. Nilsen, S. Jakobsen, K. P. Lillerud and C. Lamberti, *Chem. Mater.*, 2011, **23**, 1700-1718.
17. H. Wu, Y. S. Chua, V. Krungleviciute, M. Tyagi, P. Chen, T. Yildirim and W. Zhou, *J. Am. Chem. Soc.*, 2013, **135**, 10525-10532.
18. J. M. Taylor, S. Dekura, R. Ikeda and H. Kitagawa, *Chem. Mater.*, 2015, **27**, 2286-2289.
19. F. Vermoortele, B. Bueken, G. Le Bars, B. Van de Voorde, M. Vandichel, K. Houthoofd, A. Vimont, M. Daturi, M. Waroquier, V. Van Speybroeck, C. Kirschhock and D. E. De Vos, *J. Am. Chem. Soc.*, 2013, **135**, 11465-11468.
20. F. Ragon, P. Horcajada, H. Chevreau, Y. K. Hwang, U. H. Lee, S. R. Miller, T. Devic, J.-S. Chang and C. Serre, *Inorg. Chem.*, 2014, **53**, 2491-2500.
21. The synthesis and crystallographic characterisation of **Zr-L6** and **Zr-L7** were recently reported by us in a preliminary communication concerning their mechanical properties (see ref 5i). The synthesis and crystallographic characterisation of **Zr-L8** were recently reported by us in a communication concerning the effect of post-synthetic modification on mechanical properties (see ref 5a).
22. During the course of our study, it became apparent that **Zr-L8** was unstable in the presence of methanol, which has previously been observed for certain MOFs of the UiO-66 topology (see ref 5c). To avoid sample degradation, acetone replaced methanol in the work up of all MOFs containing **L8** (see Supporting Information).
23. HCl has previously been reported to enhance the synthesis of members of the UiO-66 series when incorporated in large quantities into solvothermal syntheses (see refs 16b and 20). In our hands, syntheses of Zr-MOFs of ligands **L5-L8** with the addition of only one equivalent of HCl did not give reproducible results, particularly in the synthesis of **Zr-L6** (UiO-67) with some products showing good crystallinity and others being completely amorphous. This observation correlates with previous work by Behrens *et al.*, who reported that addition of HCl did not improve their syntheses of UiO-67 (see ref 6d).
24. A. Schaate, S. Dühren, G. Platz, S. Lilienthal, A. M. Schneider and P. Behrens, *Eur. J. Inorg. Chem.*, 2012, **2012**, 790-796.
25. a) Y. Li, Y. Liu, W. Gao, L. Zhang, W. Liu, J. Lu, Z. Wang and Y.-J. Deng, *CrystEngComm*, 2014, **16**, 7037-7042; b) M. Taddei, P. V. Dau, S. M. Cohen, M. Ranocchiari, J. A. van Bokhoven, F. Costantino, S. Sabatini and R. Vivani, *Dalton Trans.*, 2015, **44**, 14019-14026.

26. G. Nickerl, M. Leistner, S. Helten, V. Bon, I. Senkovska and S. Kaskel, *Inorg. Chem. Front.*, 2014, **1**, 325-330.
27. S. Øien, D. Wragg, H. Reinsch, S. Svelle, S. Bordiga, C. Lamberti and K. P. Lillerud, *Cryst. Growth. Des.*, 2014, **14**, 5370-5372.
28. N. Ko, J. Hong, S. Sung, K. E. Cordova, H. J. Park, J. K. Yang and J. Kim, *Dalton Trans.*, 2015, **44**, 2047-2051.
29. **Zr-L6** crystallises in the *Fm-3m* cubic space group, with a unit cell edge $a = 26.8564(5)$ Å for our DMF-solvated sample, a value very similar to the reported parameters for (i) a fully DMF solvated sample, where $a = 26.896(3)$ Å (see ref 26), a second DMF solvated sample, where $a = 26.783(3)$ Å (see ref 28), a third DMF solvated sample, where $a = 26.812(2)$ Å (see ref 16a), (iv) a partially desolvated crystal, where $a = 26.8809(3)$ Å (see ref 27), and (v) a powdered sample, where $a = 26.8499(15)$ Å (see ref 6d).
30. L. T. M. Hoang, L. H. Ngo, H. L. Nguyen, H. T. H. Nguyen, C. K. Nguyen, B. T. Nguyen, Q. T. Ton, H. K. D. Nguyen, K. E. Cordova and T. Truong, *Chem. Commun.*, 2015, **51**, 17132-17135.
31. Our experimental values for **Zr-L7** compare well to previously reported values of $a = 29.4227(4)$ Å and $a = 29.4433(4)$ Å for powder and single crystal examples, respectively (see ref 24) and $a = 29.3994(2)$ Å in the space group *Fm-3* for a powder sample (see ref 30).
32. L-arginine was not used in these evaluations as it showed no modulating effect for the Zr-MOFs and generally produced tar-like materials rather than powder.
33. While some modulators that are usually utilised in large amounts during synthesis of Zr MOFs are available at very low cost (e.g. formic and acetic acid) our highly efficient amino acid modulated syntheses dramatically cut down on waste and do not routinely induce defects in the MOFs.

