

# Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

## Tuning the electrochemical properties of silicon wafer by grafted-from micropatterned polymer brushes

G. Panzarasa,<sup>\*†a</sup> G. Soliveri<sup>bc</sup> and V. Pifferi<sup>bc†</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

[www.rsc.org/](http://www.rsc.org/)

Silicon wafer is the material of choice for microfabrication. However, the development of innovative on-chip electrochemical sensors is hampered by its poor electrochemical properties. In this article we demonstrate how grafted-from, micropatterned polymer brushes dramatically enhance the electrochemical response of silicon electrodes. Our results are relevant not only for a deeper understanding of the structure and behavior of polymer brushes, but also for the combination of the versatility of surface-initiated polymerization and of an innovative patterning technique (remote photocatalytic lithography) which paves the way for the fabrication of integrated devices.

### Introduction

The development of reliable, fast and inexpensive signal-responsive material systems as sensing platforms to monitor target molecules is a flourishing field of investigation<sup>1–3</sup>. The miniaturization and incorporation of such systems onto microchip assemblies is highly desirable for the realization of compact, portable, implantable devices. Silicon wafer would be the substrate of choice for such applications, but even its nm-thick native oxide impairs its electrochemical response<sup>4</sup>. To overcome this problem, a typical strategy involves the grafting of redox-active molecules on the surface of hydride-terminated silicon, but this approach requires specific techniques such as the handling of dangerous hydrofluoric acid for the removal of native oxide.<sup>5,6</sup>

In this paper we report for the first time a potentially powerful approach for the fabrication of integrated lab-on-a-chip and microfluidic devices: we found that the electrochemical response of silicon wafer is dramatically improved when polymer brushes are grafted directly from its surface. Moreover, this behaviour is enhanced if the brushes are micropatterned.

Polymer brushes can be defined as dense arrays of chains tethered on a surface by one end.<sup>7</sup> Thanks to their peculiar physico-chemical properties, they provide extraordinary opportunities for surface functionalization, generating thin films for integration into various devices.<sup>8,9</sup> Being able to

control immobilization and preconcentration of analytes through specific interactions, thanks to the high concentration of functional groups exposed at the brush interface<sup>10</sup>, polymer brushes can be used to significantly enhance the response of different kind of sensors.<sup>11–13</sup>

Understanding the electrochemical properties of polymer thin films is of great importance for a wide range of technologies, from the development of biosensors to the miniaturization of batteries (battery-on-chip)<sup>14</sup> for autonomous microelectronic devices and microsensors. Electrochemistry has already proven to be an useful tool to elucidate the internal structure of polymer brushes<sup>15,16</sup>. The diffusion of probe molecules in and out of the macromolecular environments plays a key role in the response of polymer-based sensor materials or in the design of drug delivery systems. On a molecular level, the effect of the grafting density on the transport through thermoresponsive poly(*N*-isopropylacrylamide) (PNIPAM) brushes grafted on gold substrates was investigated using cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS).<sup>17</sup> EIS has been used to determine the effectiveness of fluorinated poly(2-hydroxyethyl methacrylate) (PHEMA) films as barriers against the transport of redox species.<sup>18,19</sup> Ion exchange inside polyelectrolyte brushes, in which the polymer chains have fixed electrostatic charges, is the subject of extensive study.<sup>20–23</sup> However, a detailed understanding of their electrochemical behaviour has not been obtained yet. In addition, all of these studies have been performed for brushes grafted from highly conductive gold or indium tin oxide (ITO) -coated surfaces: not a single report is available in the literature for polymer brush-modified silicon electrodes.

Here, we would like to fill this gap by studying the electrochemical behaviour of homo- and co- polymer brushes made from 2-hydroxyethyl methacrylate (HEMA) and 2-aminoethyl methacrylate hydrochloride (AMA). Poly(HEMA) is an hydrophilic polymer with current uses in contact lenses,

<sup>a</sup> Dipartimento di Scienze e Innovazione Tecnologica, Università del Piemonte Orientale "Amedeo Avogadro", Viale T. Michel 11, 15100 Alessandria, Italy. E-mail: [guido.panzarasa@uniupo.it](mailto:guido.panzarasa@uniupo.it)

<sup>b</sup> Dipartimento di Chimica, Università degli Studi di Milano, Via Golgi 19, 20133 Milano, Italy.

<sup>c</sup> Consorzio Interuniversitario Nazionale per la Scienza e Tecnologia dei Materiali (INSTM), Via Giusti 9, 50121 Firenze, Italy.

<sup>†</sup> These authors contributed equally.

Electronic Supplementary Information (ESI) available: additional figures and data. See DOI: 10.1039/x0xx00000x

biocompatibilization and drug delivery.<sup>24</sup> On the other hand, poly(AMA) is a cationic polymer which has already found promising application in the biomedical field for the development of antimicrobial surfaces<sup>25</sup> and for the bioconjugation of antigens and proteins, thanks to its primary amine groups allowing post-functionalization reactions.<sup>26</sup>

By means of cyclic voltammetry (CV) and electrochemical impedance spectroscopy (EIS) meaningful correlations were found between the charge transfer resistance, the length and the chemical composition of the brushes, revealing precious information about the structure and dynamics of the brushes themselves.

We then selected the most electrochemically-active brushes to perform micropatterning studies. Patterning is a fundamental tool for the engineering of surfaces and micropatterned polymer brushes can display new useful features compared to bulk analogues<sup>27,28</sup>. As expected, the electrochemical response of the patterned brushes was found to be dramatically different compared to that of non-patterned ones.

The crucial development reported in the present study demonstrates how, by choosing the thickness, composition and microstructurization of polymer brushes, we are able to tune the electrochemical behaviour of silicon wafer, an otherwise poor electrode material, with tremendous importance for the realization of integrated sensing devices.

## Experimental

### Materials and Methods

All the chemicals were reagent grade, purchased from Aldrich and used as received unless otherwise stated. Hydroxyethyl methacrylate (HEMA) was filtered through an inhibitor-remover column and stored at +4 °C until use. 2-Aminoethyl methacrylate hydrochloride (AMA, 90%, contains ~500 ppm phenothiazine as stabilizer) was used as received or purified by washing with inhibitor-free THF (for details refer to the Supporting Information). The ATRP initiator (3-(2-bromoisobutyramido)propyl)triethoxysilane (BIB-APTES) was synthesized and used to functionalize silicon substrates as previously described<sup>26</sup>. Water obtained from a Millipore MilliQ purification system (resistivity  $\geq 18.2 \text{ M}\Omega \text{ cm}^{-1}$ ) was thoroughly used. Silicon (100) wafers, single-polished, n type, phosphorus doped, 3–6 ( $\Omega \text{ cm}$ ), with a native oxide layer  $1.5 \pm 0.2 \text{ nm}$ -thick (ellipsometric) were purchased from Ultrasil Corporation. Thickness of polymer brushes was measured using a Filmetrics F20 reflectometer. Each data was the result of three measurements on different spots of a same sample. Scanning electron microscopy (SEM) was performed, on samples fixed on conducting carbon tape, using a Jeol JSM 7600f Schottky Field Emission Scanning Electron Microscope. A potentiostat/galvanostat Autolab PGSTAT204 (Metrohm, The Netherlands) equipped with a FRA module was employed to perform electrochemical measurements using a standard three electrode-cell with a saturated calomel, a Pt wire and a modified silicon wafer as reference, counter and working electrodes, respectively. Aqueous 0.1 M KCl was thoroughly

used as the supporting electrolyte. Cyclic voltammetry (CV) was performed by scanning the potential between  $-0.1 \text{ V}$  and  $+0.4 \text{ V}$  (SCE) (scan rate  $0.1 \text{ V s}^{-1}$ ). Electrochemical impedance spectroscopy (EIS) was carried out at  $-0.1 \text{ V}$ ,  $+0.1 \text{ V}$  and  $+0.25 \text{ V}$  (SCE) in the presence or in the absence of 3 mM  $\text{K}_4\text{Fe}(\text{CN})_6$  as redox probe. Impedance data were fitted by using ZView 2.0 software.

### Grafting-from of homo- and copolymer brushes by SI-ATRP

Surface-Initiated ATRP was performed on both non-patterned and patterned substrates. To ensure reproducibility each series was polymerized in a same batch.

PHEMA brushes were obtained using the following recipe: 0.0214 g (0.074 mmol) tris(2-pyridylmethyl)amine (TPMA), 0.002 g (0.009 mmol)  $\text{CuBr}_2$  and 0.023 g (0.13 mmol) ascorbic acid were combined in a Schlenck flask under nitrogen and dissolved under stirring in 15.4 mL of a 4:1 v/v methanol-water mixture previously degassed by bubbling nitrogen, then 4.6 mL (0.038 mol) of degassed HEMA were added. Each substrate, contained in a Schlenck flask, was immersed in 5 mL of the resulting mixture under nitrogen and polymerization was allowed to proceed at 30 °C for the desired time. After polymerization the substrates were washed with ethanol, gently sonicated in the same solvent and dried under a nitrogen stream.

PAMA brushes were obtained using the same protocol described for PHEMA brushes, using 6.3 g (0.038 mol) of AMA and 20 mL of the 4:1 v/v methanol-water solution. After polymerization the substrates were washed with water, gently sonicated in the same solvent and dried under a nitrogen stream.

PHEMA-co-PAMA copolymer brushes were obtained using the same basic procedure for PHEMA brushes. For the 80:20 HEMA-AMA monomer ratio, 3.6 mL (0.03 mol) of HEMA, 1.36 g (0.0082 mol) AMA and 17 mL of the methanol-water mixture were combined. For the 50:50 HEMA-AMA monomer ratio, 2.3 mL (0.019 mol) HEMA and 3.41 g (0.0206 mol) AMA were combined with 18 mL of methanol-water. Polymerization proceeded at 30°C for a chosen amount of time, the workup was the same as previously described.

### Micropatterning by remote photocatalytic lithography


Patterning by remote photocatalytic lithography was achieved following our previously reported procedure.<sup>29</sup> Transparent and mechanically robust anatase films with high photoactivity were deposited on glass slides from an acidic  $\text{TiO}_2$  sol using the electrochemically-assisted technique previously reported by us.<sup>30</sup> Before use, the titania-coated glass slides were cleaned by a rapid sonication in water followed by UV irradiation for 1 h. Remote photocatalytic lithography was performed by irradiating with 365 nm near-UV light from a Jelosil HG500 halogen lamp (230 V, 500 W, effective power density from 40 cm:  $57.5 \text{ (mW cm}^{-2}\text{)}$  between 280 and 400 nm) the initiator-functionalized silicon substrates through the titania-coated glass, with the photocatalytic oxide facing the substrate, separated from the surface by a 100  $\mu\text{m}$ -thick Teflon spacer.

Micropatterning was achieved using TEM grids (Gilder Grids, nickel,  $d$  3.05 mm, square mesh) or hollow, circular grid supports ( $d_{\text{ext}}$  3 mm,  $d_{\text{hole}}$  1 mm, by this point onwards referred to as “donuts”) as contact photomasks. To obtain the best pattern resolution, the initiator-functionalized substrates were subjected to remote photocatalytic lithography for 5 h.

## Results and Discussion

### Grafting-from of polymer brushes by SI-ATRP

The grafting-from technique allows the direct growth of polymer chains by starting polymerization from an initiator-functionalized surface. If a controlled radical polymerization such as Atom Transfer Radical Polymerization (ATRP) is used, brushes with increasing thickness can be obtained simply by varying the time of polymerization. The mechanism of ATRP is based on the reversible formation of radicals by the halogen atom abstraction from an alkyl halide (typically a secondary or tertiary bromide) by a copper(I)-ligand complex. This latter breaks the C–Br bond of the initiator and the resulting carbon carbon-centered radical attacks a monomer molecule starting chain growth. At the same time, copper(I) oxidizes to copper(II). Since this process is reversible Cu(II) acts as a deactivator, reducing the overall concentration of active radicals and thus the occurrence of termination events.<sup>31</sup> In the Activators Regenerated by Electron Transfer (ARGET) ATRP, Cu(II) is continuously reduced to active Cu(I) by a reducing agent (Scheme 1) and thus only ppm amounts of copper salt are required, which is beneficial when working with metal-complexing monomers such as AMA. In the present work, polymer brushes were grown at 30°C in a 4:1 v/v methanol–water mixture using a  $\text{CuBr}_2/\text{tris}(2\text{-pyridylmethyl})\text{amine}$  (TPMA) catalyst in the presence of an excess of ascorbic acid as reducing agent.<sup>29</sup> The following molar ratios were employed:  $\text{CuBr}_2/\text{TPMA}/\text{ascorbic acid}/\text{monomer} = 0.036 : 0.3 : 0.5 : 150$ . The solvent mixture was chosen to ensure the complete solubilisation of monomers, also water is known to speed up the polymerization (“water-accelerated ATRP”).<sup>32,33</sup> More importantly, under these conditions we were able to polymerize commercial AMA without the need to remove the added phenothiazine, which is considered a powerful inhibitor for conventional free-radical polymerization (more details are available in the Supporting Information, pp. S3–S5).

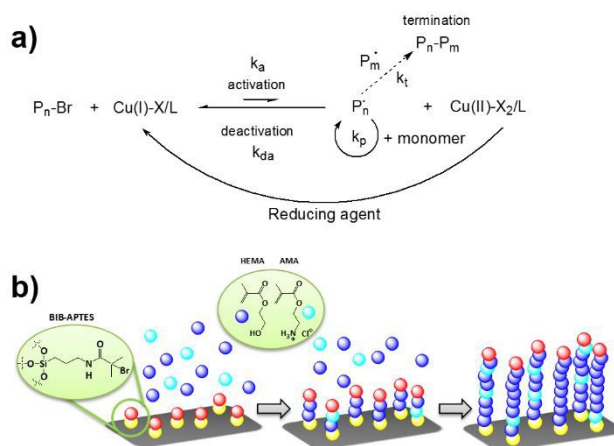

**Scheme 1.** A) Schematic mechanism of ARGET ATRP. B) Depiction of the grafting-from of polymer brushes from an ATRP initiator-functionalized surface.

The kinetics of polymerization (Figure S1) showed a pseudo-linear increase of the brush thickness as a function of the polymerization time suggesting that a good control was attained. The evolution of brush thickness was observed to slow down as a result of the increased fraction of AMA in the polymerization feed: this behaviour could be attributed to the so-called “halogen exchange effect”.<sup>34</sup> If chloride ions are added in a concentration significantly higher than bromide, as for AMA homopolymerization in the present case ( $\text{Cl}/\text{Br}$  molar ratio  $> 4000$ ), the kinetics will be slowed down due to a reduced rate of radical formation, C–Cl being more stable compared to the C–Br bond.


### Micropatterning by remote photocatalytic lithography

Patterning of polymer brushes at the micrometer or sub-micrometer scale can be achieved by a number of techniques. They are divided into several categories according to their main working principle: photolithography, colloidal lithography, soft lithography, direct writing techniques, electron and particle-beam lithography, to name a few.<sup>35</sup> Photolithography is now a mature and versatile approach thanks to the major developments described during the last decades. Among these, photocatalytic lithography has already demonstrated its great potential for surface patterning.<sup>36–38</sup> We previously demonstrated the suitability of remote photocatalytic lithography as a versatile means for the patterning of polymer brushes.<sup>29,39</sup> In the present work, this approach has been preferred compared to classic photolithography both to avoid possible contamination from residual photoresist and to make the procedure easier and faster. According to a generally accepted mechanism, when titanium dioxide is irradiated with UV light, electron-hole pairs are generated and split; the adsorbed water and oxygen were transformed into reactive oxygen species (ROS).<sup>40</sup> Such ROS can migrate in the surrounding atmosphere to another surface

from a considerable distance, of hundreds of microns, where they degrade adsorbed organic molecules.<sup>41</sup>

Here, the target was the initiator-functionalized silicon wafer (Figure 1a). As demonstrated in our previous work, the initiator molecules are completely removed from the exposed surfaces while those protected by the photomask retain their ability to start polymerization.

The resulting pattern was then amplified into polymer brushes by performing SI-ATRP (Figure 1b,c and Figure S4). Two different kinds of photomask (the donut, to obtain a macropatterning and the TEM grid, to obtain a micropatterning) were employed to evaluate the impact of macro- and micro-structuration on the electrochemical performance of brush-decorated electrodes.

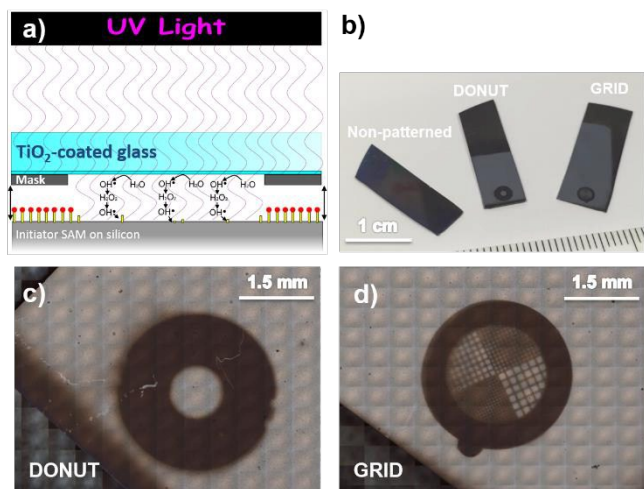


**Figure 1.** a) Scheme of remote photocatalytic lithography. b) Photographs of three representative samples, non-patterned and patterned. c) Optical microscopy images of donut-patterned (DONUT) and grid-patterned (GRID) brushes.

#### Electrochemical study of non-patterned polymer brushes

**Cyclic voltammetry (CV)** Cyclic voltammetry plots for bare silicon showed a pure capacitive behaviour. The absence of peaks even in the presence of a redox probe were indicative of an electrochemically inert surface (for more details see Supporting Information: page S8, Figure S5). The only significant difference for the initiator- and polymer brush-functionalized electrodes was the appearance of a reduction peak at around +0.1 V (Figure S6). This peak was assigned to bromine (or chlorine, for AMA homo- and copolymer brushes) due to its disappearance after selective substitution with azide (more details are available in the Supporting Information, pp. S10-S11 and Figure S7).

**Electrochemical impedance spectroscopy (EIS)** The complex plane plots obtained in the electrolyte solution at + 0.25 V (SCE), in the absence of the redox probe, for bare (SW), initiator-functionalized (BIB-APTES) silicon and for two representative polymer brushes are shown in Figure 2a. All the spectra display the same trend with a semicircle at high frequencies followed

by a straight vertical line at low frequencies, already mentioned in papers dealing with silicon-based electrodes<sup>42</sup>.

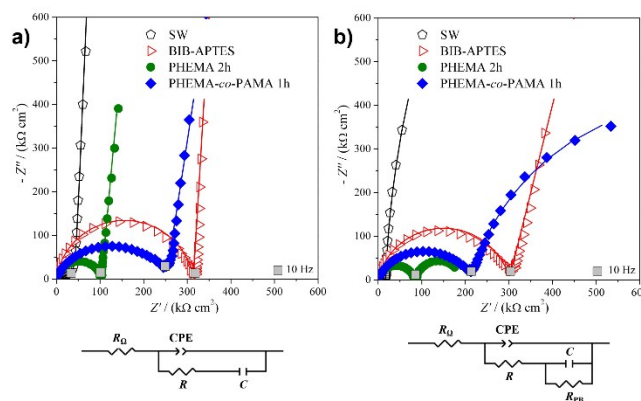

**Figure 2.** Complex plane plots measured for bare (SW) and initiator-functionalized (BIB-APTES) silicon wafer and for two representative brushes, along with the equivalent electrical circuits used for the interpretation of EIS plots, obtained a) in the absence and b) in the presence of redox probe.

The data were fitted using an equivalent circuit (Scheme 1a) already used in the literature for similar samples<sup>23,43,44</sup>. The circuit is made of the electrolyte resistance  $R_{\Omega}$  in series with a constant phase element (CPE) (accounting for the film and silicon native oxide capacitance) and a resistance  $R$  (comprising the resistance of silicon substrate and the polymeric film) in parallel (together represented by the semicircle). In series with the last element, a capacitance ( $C$ ) can be found, representing the double layer and substrate capacitance (described by the vertical straight line). The constant phase element CPE served to model the non-homogeneity of the electrode surface (giving a depressed semicircle). It is defined as (eq. 1):

$$CPE = [(C_{CPE}i\omega)^{\alpha}]^{-1} \quad (1)$$

where the  $\alpha$  parameter indicates the deviation from a purely capacitive behaviour ( $\alpha = 1$ ) to a non-capacitive one ( $\alpha = 0.5$ ) and is thus an indicator of surface homogeneity. Table 1 shows the parameters influenced by the presence of the polymeric films ( $R$ ,  $C_{CPE}$  and  $\alpha$ ) obtained from the spectra fitting since, as expected,  $R_{\Omega}$  and  $C$  maintain similar values for all the samples (the solution and the substrate are always the same).

Sample	$R$ ( $k\Omega\text{ cm}^2$ )	$C_{CPE}$ ( $\mu\text{F cm}^{-2}$ )	$\alpha$
SW	19	0.04	0.63
BIB-APTES	315	0.0006	0.90
PHEMA	103	0.007	0.85
PHEMA-co-PAMA 80:20	255	0.01	0.71

**Table 1.** Electrochemical parameters obtained by fitting the EIS data (without redox probe) for the different samples.

The reported  $R$  values are in accordance with the trend of the semicircle diameters showed in Figure 2a. Bare silicon wafer ("SW") and initiator-functionalized silicon wafer ("BIB-APTES")

showed the lowest and highest values of resistance  $R$ , respectively, suggesting that the initiator layer behaves as strong electrical insulator. The resistance  $R$  for the brushes presents intermediate values thanks to the hydrophilic and polarizable groups, which increased their conductivity. Moreover, PHEMA brushes are more conductive with respect to PHEMA-*co*-PAMA 80:20 ones.

Bare silicon and initiator-functionalized silicon showed the highest and lowest values of  $C_{PE}$ , respectively. When the electrode surface is covered with an insulator layer (e.g. the BIB-APTES layer), the overall capacitance decreases because the capacitance of the insulating layer sums to that of the native oxide. PHEMA brushes, as well as the (PHEMA-*co*-PAMA) brushes, had lower insulating properties thanks to hydrophilic -OH groups and electrically charged primary amine groups.


As previously mentioned, the  $\alpha$  values can give information about surface homogeneity. The low  $\alpha$  values found for bare silicon and the copolymer brushes indicate a lower surface homogeneity, due to the presence of native oxide or of a non-homogeneous polymer. On the other hand, the initiator layer and PHEMA brushes are characterized by really homogeneous surfaces, giving  $\alpha$  values very close to 1.

The EIS data trends for bare and initiator-functionalized silicon wafer were unaffected by the addition of the redox probe potassium ferrocyanide (Figure 3b), confirming the electrochemical inertness of those samples. Contrarily, the polymer brushes impedance at low frequencies showed important changes: the vertical straight line became another semicircle, requiring the introduction of  $R_{PB}$ , the resistance to probe electron transfer, in parallel to  $C$  (Scheme 1b). This indicates that the reaction of the redox probe took place efficiently at brush-modified electrodes<sup>20-23,44,45</sup>. The phenomenon could be due to interactions between the negatively charged probe with polar -OH (PHEMA) and positively charged -NH<sub>3</sub> groups (PHEMA-*co*-PAMA).

**EIS study of swelling** Swelling is an important feature to consider when dealing with polymer-modified electrodes. The conformation of polymer brushes in a solvent is mainly governed by solvation forces and excluded volume effects. If the brush is made of a polyelectrolyte, such as PAMA and PHEMA-PAMA copolymers, electrostatic interactions add up. Water can be considered as a good solvent for all our investigated brushes and their chains would adopt a stretched conformation in pure water due to excluded volume effects of the solvated chain side groups and to the electrostatic repulsion between neighbouring charge-like chains. However, in presence of free electrolytes, the charges of the pendant groups in the polymer chains would be screened according to the relative counterions concentration, minimizing electrostatic repulsion and leading to a more entropically-favorable collapsed conformation.

From an electrochemical point of view, the swelling-collapse behaviour will affect charge-transfer processes, the interface resistance and the capacitance of the brushes. EIS allows to follow this process as a function of time, obtaining information about the mobility and internal structure of polymer chains<sup>44</sup>.


To monitor the swelling process (a representative complex plane plot is shown in Figure 3a), EIS spectra were immediately recorded after immersion in the supporting electrolyte and then after 2 and 4 hours of immersion. The only detectable change was the decrease in diameter of the semicircle, corresponding to a decrease of  $R$ , indicating an increase in polymer permeability with swelling. Figure 3b presents the swelling behaviour for all the analysed brushes, reported as the ratio between the initial  $R(i)$  and the time-dependent  $R(t)$ . The straight line at  $R(i)/R(t) = 1$  corresponds to the value registered immediately after immersion. The data shown suggested that swelling reached completion after the first 2 h. For times longer than 4 h the impedance spectra were superimposable. This time was considered as the optimum time to reach complete swelling and allow equilibration of the brushes with the electrolyte.

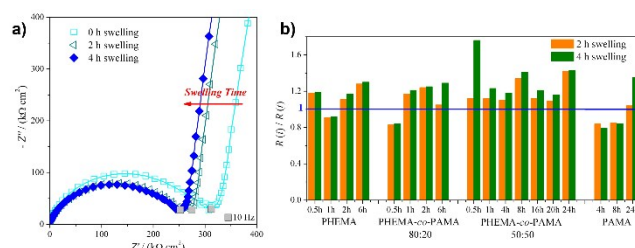

**Figure 3.** A) Complex plane plots showing the swelling of 1  $\mu$ m-thick PHEMA-*co*-PAMA 80:20 brushes. b) Comparison of the swelling behaviour for all the investigated brushes.

**Effect of thickness** The effect of thickness on the electrochemical properties of the brushes could be easily evaluated by considering the changes in  $R$  and  $R_{PB}$  values<sup>21</sup>. To this aim, EIS analyses were carried out in the absence (Figure 4a,b) and in the presence (Figure 5a,b) of the redox probe, respectively. As expected, different brush compositions induced different permeability and response behaviour to the redox probe.

Figure 4a shows the complex plane spectra for the complete series of PHEMA-*co*-PAMA 80:20 brushes as an example: only the diameter of the semicircle increased with increasing thickness, without relevant changes for the other parameters. A higher thickness can be related to higher values of  $R$ , since the electrostatic charge carriers (ions, according to a generally accepted theory<sup>46</sup>) face a longer way to reach the electrode surface. In Figure 4b the  $R$  values are reported for all the series to allow a comparison. PAMA and PHEMA-*co*-PAMA 50:50 brushes had the lowest values: apparently, a high density of charged groups helping the movement of ions inside the brushes was a more determinant factor than thickness. The  $R$  values of the PHEMA-*co*-PAMA 50:50 brushes seemed to be independent to thickness, probably due to a random distribution of the two monomers. PHEMA brushes showed an intermediate behaviour, while the highest values were found for the PHEMA-*co*-PAMA 80:20 ones. In general,  $R$  increased proportionally to the thickness, probably because longer chains impaired diffusion.

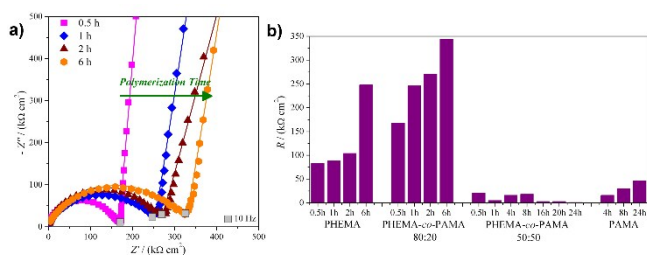


**Figure 4.** Behaviour of  $R$  as a function of thickness: a) complex plane plot for a representative 1 h-polymerized PHEMA-co-PAMA 80:20, b) comparison among the series. These data were obtained without the redox probe.

EIS spectra were then collected in the presence of the redox probe. According to previous swelling studies, the brushes were allowed to completely swell for 4 h, then ferrocyanide (3 mM) was added to the supporting electrolyte and the analysis was carried out after additional 2 h to allow the probe diffusion in the brushes and any other possible interaction to take place. While for PHEMA the interaction with the redox probe is supposed to occur simply by diffusion, PAMA and PHEMA-PAMA copolymer brushes can be considered as polyelectrolytes due to the presence of positively charged primary amine groups, which can facilitate their interaction with the anionic redox probe and consequently the electron transfer. According to Huck *et al.*<sup>46</sup>, one molecule of ferrocyanide would be supposed to coordinate with four amine groups, at last for PAMA brushes. For the 80:20 and 50:50 copolymer brushes, different degrees of coordination would be possible due to the more or less intra- and inter-chain proximity of AMA units (we assume that the copolymers are random).

As previously discussed, in the complex plane plot at low frequencies the vertical straight line becomes a semicircle for all the polymers, indicating that the brushes interact with the probe: a lower resistance  $R_{PB}$  means an easier reaction of the probe at the electrode. All the series were found to interact with the probe, but different  $R_{PB}$  values were obtained depending on the brush composition and thickness. Figure 5a shows the PHEMA-co-PAMA 80:20 series as an example, where the lowest resistances were obtained for intermediate thicknesses, probably as a result of a compromise between the quantity of charged groups that can interact with the probe and the thickness. Figure 5b reports all the obtained  $R_{PB}$  values. The lowest resistance values were displayed by the thickest PHEMA brushes. Probably, probe diffusion was facilitated by the homogeneous distribution of polar but neutral-OH groups while the thicker polymer layer allowed to store a higher concentration of probe, which in turn was forced to react at the electrode giving a low resistance. PAMA brushes exposed at the surface only charged amine groups, promoting strong interactions, which at the same time increased the overall resistance due to local collapse after the

coordination of the probe with amine groups, blocking diffusion of other ferrocyanide molecules. For the PHEMA-co-PAMA 80:20 series higher resistances were obtained in comparison to PHEMA, but the best situation was reached for intermediate polymerization times, probably thanks to a sufficient density of charged groups, while the electron transfer was not complicated by excessive chain length. Similar or even lower values were obtained in comparison with PAMA, even more considering the thicknesses, indicating how the presence of only amine groups was not so favourable to obtain low resistance values. Especially in case of high thicknesses, brushes with a low density of amine groups were more desirable. The PHEMA-co-PAMA 50:50 series displayed the highest  $R_{PB}$  values: it is likely that those brushes suffered from the so-called hydrophobic or ion-pairing collapse, which has been described for similar polyelectrolytes, *e.g.* poly[2-(methacryloyloxy)ethyl]trimethylammonium chloride (PMETAC). Such transition between the extended and collapsed conformational states could be due to a strong interaction between the cationic groups of the brushes with scarcely hydrated, large and highly polarizable ions such as  $\text{ClO}_4^-$  or, in this case,  $[\text{Fe}(\text{CN})_6]^{4-}$ . The hydrophobic collapse typically results in a large water loss for the brush, thus increasing the overall electrical resistance.<sup>23</sup> However, for higher thicknesses the resistance values decrease, probably due to the increase number and availability of interaction sites with the probe.

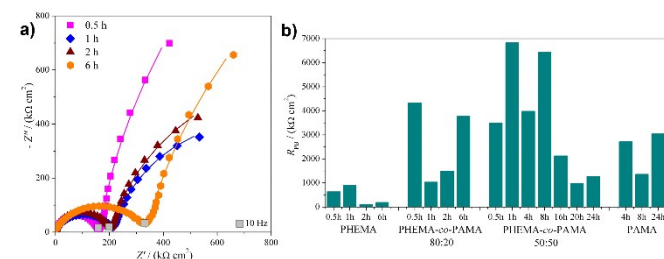


**Figure 5.** Behaviour of the  $R_{PB}$  as a function of thickness: a) complex plane plot for a representative brushes PHEMA-co-PAMA, b) comparison among the series. These data were obtained in presence of the redox probe (3 mM).

### The influence of patterning on the electrochemical properties of polymer brushes

The previously described electrochemical analyses allowed us to select two types of brushes to study the effect of patterning: 1 h-polymerized PHEMA-co-PAMA 80:20 brushes and 2 h-polymerized PHEMA brushes were chosen due to their desirable properties, especially low resistance to probe reaction. For each brush type, three samples were prepared: a non-patterned one, a macropatterned one with a donut shape ("DONUT", Figure 1c) and a micropatterned one with a TEM grid ("GRID", Figure 1d and Figure S4).

The electrochemical response of electrodes modified with patterned polymer brushes was dramatically different

compared to that of non-patterned ones. Significant changes were observed in their EIS plots for both the low and high frequency zones suggesting different (and more efficient) interaction mechanisms with the redox probe.

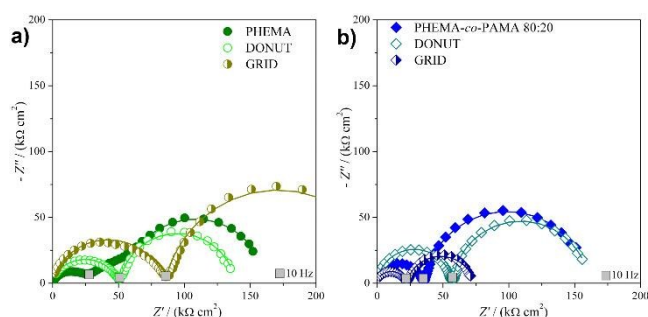

**Figure 6.** Complex plane plots showing the effect of patterning in the presence of redox probe (3 mM).

According to Figure 6a, for PHEMA series there was a clear increase in the first semicircle diameter as a function of patterning, reflecting changes in the film resistance ( $R$ ) of the surface. The trend observed for  $R$  was: PHEMA(non-patterned) < DONUT < GRID, plausible considering the reduced amount of active polymer for the patterned samples (of the order of  $8 \mu\text{g cm}^{-2}$  for non-patterned brushes and  $0.5 \mu\text{g cm}^{-2}$  for patterned brushes) and the correspondingly decreased permeability. On the other hand, the values obtained for the resistance toward the probe reaction  $R_{\text{PB}}$ , reported in Table 2 for both the oxidation (+ 0.1 V) and reduction (+ 0.25 V) potentials of the redox probe, were very similar for the non-patterned and DONUT samples, but were slightly increasing for the GRID sample. Since the resistance values remained of the same order of magnitude, this difference was probably due to an overall increase in disorder as a result of micropatterning.

Sample	PHEMA		PHEMA-co-PAMA 80:20	
	+ 0.1 V	+ 0.25 V	+ 0.1 V	+ 0.25 V
Non-patterned	1413	91	3190	160
DONUT	1289	88	1048	104
GRID	1759	172	623	52

**Table 2.**  $R_{\text{PB}}$  values obtained in case of the non-patterned and patterned samples for homopolymer and copolymer brushes.

The situation observed for the PHEMA-co-PAMA 80:20 brushes is far more different. The trend of the first semicircle diameters is GRID < PHEMA-co-PAMA(non-patterned) < DONUT, which was different for that observed for PHEMA samples. The highest  $R$  value was measured for the DONUT sample, probably due to the reduced overall density of charged groups, which improved ion permeability, compared to the non-patterned sample. Interestingly, the lowest  $R$  value was obtained for the GRID sample, since in this case a high concentration of charged groups was directly exposed to the

electrolyte, enhancing the lateral diffusion. The  $R_{\text{PB}}$  reported in Table 2 assigned the lowest value to the GRID sample, followed by the DONUT. It is noteworthy that these values were consistently lower compared to those obtained for the corresponding non-patterned PHEMA-co-PAMA sample, confirming the relevance of patterning to increase the redox probe uptake ability of the brushes. Moreover, GRID showed also a lower resistance than non-patterned PHEMA, which had the lowest resistance among all the non-patterned samples.

All these results clearly demonstrate the power of patterning and especially of micropatterning to control the values of probe reaction resistance. We hypothesize that its profound effect on the overall electrochemical response of polymer brushes could be the result of a combination of factors. First: micropatterned polymer brushes, compared to the non-patterned ones, display a more open surface towards the surrounding electrolyte (due to a wider perimeter border between the brush-covered and uncovered areas), which would result in more efficient diffusion processes of the redox probe. Second: for the same reason, the presence of microstructures would increase the density of functional groups directly exposed to the electrolyte, promoting their interaction with the probe.

## Conclusions

The need for on-chip electrochemical sensors calls for innovative microfabrication strategies. In this article we demonstrated for the first time that silicon wafer modified with grafted-from polymer brushes holds all the premises for the development of integrated electrochemical microsensors. We employed PHEMA, PAMA and their copolymers as a proof-of-concept. However, it is possible to tune the characteristics of the brushes *e.g.* to make them negatively charged, less or more hydrophilic, to confer antifouling properties (especially for biological applications) simply by choosing the appropriate monomer. More importantly, this means that the system can be designed for specific target molecules. Hydrophilic polymer brushes allowed a typical redox probe, ferrocyanide, to react at an otherwise electrochemically inert surface, suggesting that the grafted chains behaved as “tentacles” to capture the redox probe and holding it in the proximity of the electrode surface. Moreover, such behaviour was found to be dramatically enhanced for micropatterned polymer brushes. This is another unprecedented result which paves the way for miniaturization and on-chip applications, especially considering the remote photolithography approach employed for the micropatterning: mild, dry and highly compatible with conventional microfabrication processes.

## Acknowledgements

The authors want to thank Dr. Gianluigi Marra (Eni Donegani Research Centre for Renewable Energies and Environment, Novara) for kindly providing SEM images. Prof. Silvia Ardizzone and Prof. Luigi Falciola (Università degli Studi di Milano,



## ARTICLE

Journal Name

Department of Chemistry) are especially acknowledged for support and helpful comments for manuscript preparation.

## References

- 1 U. Guth, W. Vonau and J. Zosel, *Meas. Sci. Technol.*, 2009, **20**, 042002.
- 2 G. Soliveri, V. Pifferi, G. Panzarasa, S. Ardizzone, G. Cappelletti, D. Meroni, K. Sparnacci and L. Falciola, *Analyst*, 2015, **140**, 1486–1494.
- 3 V. Pifferi, G. Soliveri, G. Panzarasa, S. Ardizzone, G. Cappelletti, D. Meroni and L. Falciola, *RSC Adv.*, 2015, **5**, 71210–71214.
- 4 S. Xun, X. Song, L. Wang, M. E. Grass, Z. Liu, V. S. Battaglia and G. Liu, *J. Electrochem. Soc.*, 2011, **158**, A1260.
- 5 S. Ciampi, P. K. Eggers, G. Le Saux, M. James, J. B. Harper and J. J. Gooding, *Langmuir*, 2009, **25**, 2530–2539.
- 6 R. D. Röhde, H. D. Agnew, W. S. Yeo, R. C. Bailey and J. R. Heath, *J. Am. Chem. Soc.*, 2006, **128**, 9518–9525.
- 7 R. Barbey, L. Lavanant, D. Paripovic, N. Schüwer, C. Sugnaux, S. Tugulu and H.-A. Klok, *Chem. Rev.*, 2009, **109**, 5437–527.
- 8 S. Minko, *Polym. Rev.*, 2006, **46**, 397–420.
- 9 O. Azzaroni, *J. Polym. Sci. Part A Polym. Chem.*, 2012, **50**, 3225–3258.
- 10 J.-K. Chen, Z.-Y. Chen, H.-C. Lin, P.-D. Hong and F.-C. Chang, *ACS Appl. Mater. Interfaces*, 2009, **1**, 1525–32.
- 11 N. Ayres, *Polym. Chem.*, 2010, **1**, 769–777.
- 12 M. Welch, A. Rastogi and C. Ober, *Soft Matter*, 2011, **7**, 297–302.
- 13 J.-K. Chen, J.-H. Wang, C.-C. Cheng, J.-Y. Chang and F.-C. Chang, *Appl. Phys. Lett.*, 2013, **102**, 151906.
- 14 Y. Wang, M. Hung, C.-H. Lin, H. Lin and J. Lee, *Chem. Commun. (Camb.)*, 2011, **47**, 1249–1251.
- 15 S. Cosnier and A. Karyakin (Eds), *Electropolymerization: Concepts, Materials and Applications*, Wiley 2010.
- 16 W. Knoll and R. C. Advincula (Eds), *Functional Polymer Films*, vol. 1-2, Wiley 2011.
- 17 T. A. García, C. A. Gervasi, M. J. Rodríguez Presa, J. I. Otamendi, S. E. Moya and O. Azzaroni, *J. Phys. Chem. C*, 2012, **116**, 13944–13953.
- 18 M. R. Bantz, E. L. Brantley, R. D. Weinstein, J. Moriarty and G. K. Jennings, *J. Phys. Chem. B*, 2004, **108**, 9787–9794.
- 19 E. L. Brantley, T. C. Holmes and G. K. Jennings, *J. Phys. Chem. B*, 2004, **108**, 16077–16084.
- 20 E.-Y. Choi, O. Azzaroni, N. Cheng, F. Zhou, T. Kelby and W. T. S. Huck, *Langmuir*, 2007, **23**, 10389–10394.
- 21 C. Combellas, F. Kanoufi, S. Sanjuan, C. Slim and Y. Tran, *Langmuir*, 2009, **25**, 5360–5370.
- 22 T. Alonso-García, M. J. Rodríguez-Presa, C. Gervasi, S. Moya and O. Azzaroni, *Anal. Chem.*, 2013, **85**, 6561–6565.
- 23 T. Alonso-García, C. A. Gervasi, M. J. Rodríguez-Presa, E. Gutierrez-Pineda, S. E. Moya and O. Azzaroni, *J. Phys. Chem. C*, 2013, **117**, 26680–26688.
- 24 M. Krishnamoorthy, S. Hakobyan, M. Ramstedt and J. E. Gautrot, *Chem. Rev.*, 2014, **114**, 10976–11026.
- 25 A. E. Madkour, J. M. Dabkowski, K. Nüsslein and G. N. Tew, *Langmuir*, 2009, **25**, 1060–1067.
- 26 Y. Zhang, N. Islam, R. G. Carbonell and O. J. Rojas, *ACS Appl. Mater. Interfaces*, 2013, **5**, 8030–8037.
- 27 M. E. Welch and C. K. Ober, *J. Polym. Sci. Part B Polym. Phys.*, 2013, **51**, 1457–1472.
- 28 T. Chen, I. Amin and R. Jordan, *Chem. Soc. Rev.*, 2012, **41**, 3280–3296.
- 29 G. Panzarasa, G. Soliveri, K. Sparnacci and S. Ardizzone, *Chem. Commun.*, 2015, **51**, 7313–7316.
- 30 G. Maino, D. Meroni, V. Pifferi, L. Falciola, G. Soliveri, G. Cappelletti and S. Ardizzone, *J. Nanoparticle Res.*, 2013, **15**, 2087–2097.
- 31 K. Matyjaszewski, *Macromolecules*, 2012, **45**, 4015–4039.
- 32 W. Huang, J. B. Kim, M. L. Bruening and G. L. Baker, *Macromolecules*, 2002, **35**, 1175–1179.
- 33 M. Fantin, A. a. Isse, A. Gennaro and K. Matyjaszewski, *Macromolecules*, 2015, DOI: 10.1021/acs.macromol.5b01454.
- 34 C. H. Peng, J. Kong, F. Seeliger and K. Matyjaszewski, *Macromolecules*, 2011, **44**, 7546–7557.

- 35 J. K. Chen and C. J. Chang, *Materials (Basel)*, 2014, **7**, 805–875.
- 36 N. Blondiaux, S. Zürcher, M. Liley and N. Spencer, *Langmuir*, 2007, **23**, 5329–5334.
- 37 H. Notsu, W. Kubo, I. Shitanda and T. Tatsuma, *J. Mater. Chem.*, 2005, **15**, 1523–1527.
- 38 K. Komori, J. Nada, M. Nishikawa, H. Notsu, T. Tatsuma and Y. Sakai, *Anal. Chim. Acta*, 2009, **653**, 222–227.
- 39 G. Panzarasa, G. Soliveri, S. Ardizzone and K. Sparnacci, *Mater. Today Proc.*, 2015, **2**, 4183–4189.
- 40 O. Carp, *Prog. Solid State Chem.*, 2004, **32**, 33–177.
- 41 W. Kubo and T. Tatsuma, *J. Am. Chem. Soc.*, 2006, **128**, 16034–16035.
- 42 G. Soliveri, V. Pifferi, R. Annunziata, L. Rimoldi, V. Aina, G. Cerrato, L. Falciola, G. Cappelletti and D. Meroni, *J. Phys. Chem. C*, 2015, **119**, 15390–15400.
- 43 R. N. Vyas and B. Wang, *Int. J. Mol. Sci.*, 2010, **11**, 1956–1972.
- 44 F. Zhou, H. Hu, B. Yu, V. L. Osborne, W. T. S. Huck and W. Liu, *Anal. Chem.*, 2007, **79**, 176–182.
- 45 M. R. Presa and L. Gassa, *Anal. Chem.*, 2009, **81**, 7936–7943.
- 46 E. Spruijt, E. Choi and W. Huck, *Langmuir*, 2008, **24**, 11253–11260.

## Table of Contents

Powering up silicon wafer with micropatterned functional polymer brushes: a new route towards the development of on-chip integrated electrochemical sensors.

