

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

COMMUNICATION

## Improving Electrochemical Performance of $\text{Li}_{1.2}\text{Mn}_{0.52}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ by Surface Nitrogen Doping via the Plasma Treatment

Received 00th January 20xx,  
Accepted 00th January 20xx

Bing Li<sup>a</sup>, Chao Li<sup>b</sup>, Zulai Cao<sup>b</sup>, Jing wang<sup>b</sup>, Jinbao Zhao<sup>\*a,b</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org/

**The nitrogen plasma processing technology is used to introduce nitrogen to the surface of  $\text{Li}_{1.2}\text{Mn}_{0.52}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ . The material shows better rate capability and cycle stability than the pristine  $\text{Li}_{1.2}\text{Mn}_{0.52}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ . Compared to the conventional treatment methods, it is a facile and promising way.**

The development of new energy storage field demands urgently high energy density batteries. For the whole battery system, cathode materials have a great impact on the energy density. The Li-rich oxide layer materials, which could be defined as  $x\text{Li}_2\text{MnO}_3 \cdot (1-x)\text{LiMO}_2$  ( $M = \text{Mn, Co, Ni, etc.}$ ), have been regarded as a promising cathode material to meet the demand for high energy lithium batteries due to their high specific capacity of more than  $250 \text{ mAh g}^{-1}$ .<sup>1-4</sup>

It is generally considered that the  $\text{Li}_2\text{MnO}_3$  component is able to provide additional capacity through the migration of  $\text{Li}^+$  ion<sup>5</sup> and the release of oxygen<sup>6</sup> at above 4.5 V. The active process above 4.5 V may also be considered as the release of  $\text{Li}_2\text{O}$ .<sup>7</sup> This phenomenon could cause a large irreversible capacity loss in the first charge/discharge cycle. The acid treatment has been proved to be an effective way to improve the coulombic efficiency<sup>8</sup>. However, the electrode material would show a poor cycling stability, mostly owing to the  $\text{H}^+/\text{Li}^+$  exchange during the process of acid treatment. Other methods are surface coated with Li-free insertion materials<sup>10</sup>,<sup>11</sup>, and treated with  $(\text{NH}_4)_2\text{SO}_4$  solution<sup>12</sup>, or  $\text{Na}_2\text{S}_2\text{O}_8$  solution<sup>13</sup>. There are also some problems, such as  $\text{H}^+/\text{Li}^+$  exchange, tedious steps, low controllability and a mediocre rate performance. It is noteworthy that the removal of a proper amount of  $\text{Li}^+$  ions from the bulk materials could increase the coulombic efficiency at the first cycle. The surface nitrogen-

doping has been proved to effectively improve the electrochemical performance of Li-rich oxide layer material<sup>14</sup>. Therefore, we thought that the Li-rich oxide layer cathode materials could be improved in electrochemical performance if they were treated with surface nitrogen-doping and simultaneously extracting an appropriate amount of  $\text{Li}^+$ .

In this work, the nitrogen plasma processing technology is used to modify the Li-rich oxide layer material. It has the following advantages: 1) the degree of surface nitrogen-doping can be easily controlled; 2) a trace amount of  $\text{Li}^+$  is removed from the bulk material without  $\text{H}^+/\text{Li}^+$  exchange, implying no damages to the electrode material; 3) the coulombic efficiency at the first charge/discharge cycle, capacity retention and rate performance have been improved; 4) compared with liquid nitrogen treatment<sup>14</sup> or hydrothermal growth in  $\text{NH}_3$  atmosphere<sup>15</sup>, the plasma processing treatment is much more controllable and safe to improve the property of electrode materials.

The Li-rich oxide layer cathode material was prepared through a liquid process reported in our previous report<sup>16</sup>. The material obtained is  $\text{Li}_{1.2}\text{Mn}_{0.52}\text{Co}_{0.13}\text{Ni}_{0.13}\text{O}_2$ , defined as the pristine material. The pristine material was put into a special porous ceramic crucible, the bottom of which was covered with a thin layer of pristine material. The crucible was placed in a vacuum quartz glass tube, which was evacuated to less than 1 Pa. Then, pure  $\text{N}_2$  (99.999%) was introduced into this tube at the flow rate of  $50 \text{ ml min}^{-1}$ . Plasma components were carried out for 2 h. After treatment, the material collected was defined as P1. Plasma was generated by an RF power supply at 1k MHz and 400 W, and the plasma components were located at both ends of the tube.

Scanning electron microscopy (SEM) was carried out on Hitachi 4800 equipment. X-ray diffraction (XRD) patterns were collected through the Rigaku Ultima IV using  $\text{Cu K}\alpha$  radiation source operated at 40 kV and 15 mA. X-ray photoelectron spectroscopy (XPS) was measured using the Quantum 2000 (Physical electronics). X-ray fluorescence (XRF) was performed with a Bruker model S8 TIGER. The inductively coupled plasma-

<sup>a</sup> College of Energy, School of Energy Research, Xiamen University, Xiamen, 361005, P. R. China

<sup>b</sup> State Key Lab of Physical Chemistry of Solid Surfaces, Collaborative Innovation Center of Chemistry for Energy Materials, College of Chemistry and Chemical Engineering, Xiamen University, Xiamen, 361005, P. R. China.  
E-mail: jbzha@xmu.edu.cn

Electronic Supplementary Information (ESI) available: Calculation of the  $\text{Li}^+$  diffusion coefficient]. See DOI: 10.1039/x0xx00000x

atomic emission spectroscopy (ICP-AES) was carried out on the plasma 1000 (NCS Testing Technology, China).

All electrochemical measurements were conducted with the 2016 coin-type cells. The lithium metal sheet (the diameter of 16 mm) was used as the anode of the cells. The active materials mixed with acetylene black and polyvinylidene fluoride in N-methyl-2-pyrrolidone were coated on the Al foil, with the quality ratio of 8:1:1. The electrolyte solution was 1 M LiPF<sub>6</sub> in 1:1:1 (volume ratio) ethylene carbonate, dimethyl carbonate and diethyl carbonate. All the cells were assembled in the Argon-filled glove box (Mbraun, Germany). The average loading of active material was adjusted to 3 mg for each coin cell, and the diameter of cathode sheet is 12 mm.

All cells were galvanostatically charged and discharged between 4.8 V and 2.0 V (vs. Li<sup>+</sup>/Li), using the Land CT2001A (Wuhan, China) battery testing system at room temperature. The rate performance was carried out from 25 mA·g<sup>-1</sup> (0.1 C) to 1250 mA·g<sup>-1</sup> (5 C). All capacities were calculated based on the active material. The electrochemical impedance spectroscopy (EIS) was carried out on an electrochemical workstation (Autolab PGSTA T302N) with frequency range of 0.01 Hz ~ 10 kHz.

The exhaust gas of the plasma treatment device was introduced into the buffer bottle, filled with the indicator solution. The 0.1 % methyl red was used as the indicator. The colour change of indicator was observed, which confirms the generation of nitrogen oxides. Considering the vacuum pre-treatment, the oxygen is more likely from the material Li<sub>1.2</sub>Mn<sub>0.52</sub>Co<sub>0.13</sub>Ni<sub>0.13</sub>O<sub>2</sub> itself. In order to further exclude the environmental interference, a control experiment (without Li<sub>1.2</sub>Mn<sub>0.52</sub>Co<sub>0.13</sub>Ni<sub>0.13</sub>O<sub>2</sub> in the plasma treatment device) was done. The colour of indicator in the control experiment did not change. All the materials were subjected to XRF analysis, and the obtained data are shown in Table 1. After nitrogen plasma treatment, the existence of nitrogen in P1 sample is confirmed, and the mass percentage is about 1.32 %.

Table.1 The XRF analysis of pristine and P1 samples

	Mn/%	Co/%	Ni/%	N/%
pristine	66.75	16.80	16.45	0
P1	66.67	16.75	16.58	1.32

Fig. 1a shows the XRD patterns of pristine and P1 sample. There are no additional diffraction peaks in P1 sample, suggesting that the main structure of pristine material is not damaged during the nitrogen plasma treatment. All the peaks belong to a layer α-NaFeO<sub>2</sub> structure, except a small group of diffraction peaks located between 20° ~25°. The small group of peaks has a relationship with the ordering of Li<sup>+</sup>, Mn<sup>4+</sup> ions in the transition metal layers<sup>17</sup>. The intensity ratio of I<sub>(003)</sub>/I<sub>(104)</sub> means the degree of cation mixing in the Li-layers<sup>18</sup>, and the value of the ratio more than 1.2 is considered to be an acceptable cation mixing<sup>19</sup>. The ratio of all samples is 1.49, denoting no structural rearrangement during nitrogen plasma treatment. The lattice parameters of samples analysed by the XRD data through PDXL2 software are listed

in Table.2, revealing that the nitrogen plasma treatment does not obviously influence the crystal structure of the Li<sub>1.2</sub>Mn<sub>0.52</sub>Co<sub>0.13</sub>Ni<sub>0.13</sub>O<sub>2</sub>, probably owing to the low concentration of nitrogen. The c/a ratio is often regard as a parameter for characterizing hexagonal structure. When the ratio is larger than 4.9, the material can be assumed to possess layered characteristics<sup>20</sup>. It can be seen that both the c/a ratio of pristine and P1 sample are larger than 4.9.

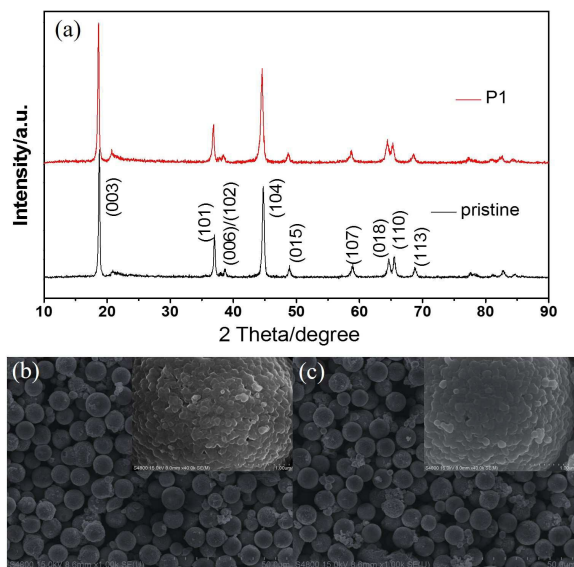


Fig. 1 (a) XRD patterns of the pristine and P1 sample; (b) SEM image of P1; (c) SEM image of the pristine sample.

Table.2 Lattice parameters of pristine and P1 samples

	a=b/Å	c/Å	c/a
Pristine	2.8594	14.2266	4.975
P1	2.8616	14.2601	4.983

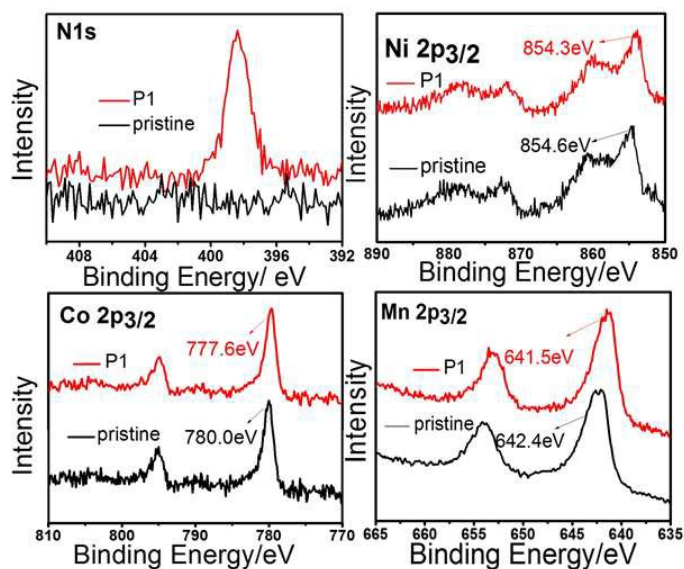


Fig. 2 XPS spectra of pristine sample and P1.

The SEM images (Fig. 1b and c) show that the micro-sized spherical particles are composed of nano-sized particles. After the nitrogen plasma treatment, the spherical particles are not cracked, but the surface becomes slightly rough. This phenomenon may be caused by the oxygen escaping from the crystal lattices.

Fig. 2 shows the XPS spectra of pristine and P1 samples. Firstly, the existence of nitrogen on the surface is affirmed in the P1 material. The position of Mn 2p<sub>3/2</sub> peak in the pristine sample is 642.4 eV, confirming the Mn<sup>4+</sup> oxidation states of the pristine material<sup>21, 22</sup>. However, the Mn 2p<sub>3/2</sub> peak shifts slightly to a lower binding energy in the P1 material. The nitrogen-doping on the surface results in weakening the binding energy of Mn-O bonds<sup>14</sup>. Due to the same reason, the Co 2p<sub>3/2</sub> and Ni 2p<sub>3/2</sub> peaks of the P1 sample shifts to a lower binding energy.

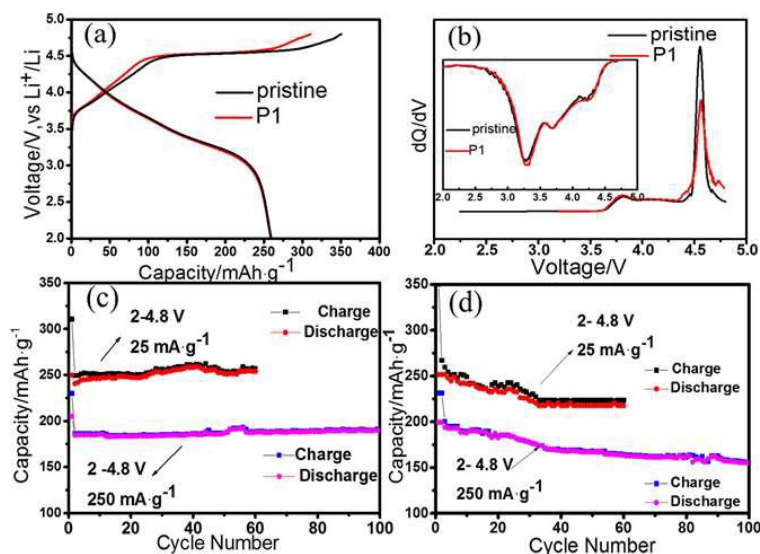


Fig. 3 (a) The first charge/discharge curves of all samples; (b) The dQ/dV curves of pristine and P1 samples for the first cycle; (c) Cycling performance at 25/250 mA·g<sup>-1</sup> of P1; (d) Cycling performance at 25/250 mA·g<sup>-1</sup> of pristine sample.

The first charge/discharge curves of P1 and the pristine sample under 0.1 C rate are shown in Fig. 3a. Both of them could deliver the discharge capacity of 250 mAh·g<sup>-1</sup>. However, the P1 sample has a lower charge capacity than the pristine materials. This may be due to the decrease of oxygen, suppressing the release of Li<sub>2</sub>O, as the previous study<sup>23</sup>. The first part below 4.5 V is corresponding to the oxidation of Ni<sup>2+</sup> and Co<sup>3+</sup>, while the other part above 4.5 V is removal of Li<sub>2</sub>O from Li<sub>2</sub>MnO<sub>3</sub> yielding active MnO<sub>2</sub><sup>24</sup>. The coulombic efficiency of the first charge/discharge circle is 80.5 % for the P1 sample, which is higher than the pristine sample (73.9 %). According to the ICP data, the mole ratio of Li/TM (transitional metal) decreases from 1.50 to 1.48, confirming the loss of lithium. It suggests that an appropriate physical extraction of

lithium from the initial electrode material may reduce the irreversible capacity loss during the first charge/discharge circle, without reducing the discharge capacity<sup>8, 13, 25</sup>. In order to further discuss the influence of nitrogen on the charge process, the dQ/dV curves are discussed (Fig. 3b). The intensity of oxidation peak at around 4.60 V in P1 is lower than the pristine material, which may be associated with the release of oxygen<sup>7</sup>. It is noteworthy that, these two samples have the same discharge dQ/dV curves (Fig. 3b inset), indicating the discharge process is not affected.

The cycling performance of the cells of the pristine material and P1 are compared in Fig. 3c and d. At a rate of 25 mA·g<sup>-1</sup> (0.1 C), the discharge capacity of P1 is 256.7 mAh·g<sup>-1</sup> after 60 cycles, while the pristine delivers only 227.8 mAh·g<sup>-1</sup>. The higher discharge capacity of the P1 electrode may benefit from its more stable surface structure of electrode material after nitrogen plasma treatment. At a higher rate, the discharge capacity of the pristine sample decreases to 169.0 mAh·g<sup>-1</sup> at the 100th cycle, while the P1 sample is 190.9 mAh·g<sup>-1</sup>. Although the improvement is not significant, the data of improved electrochemical performance in this work is as good as others reported<sup>14, 26, 27</sup>. Compared to common method of using liquid nitrogen treatment, the plasma processing method is very convenient.

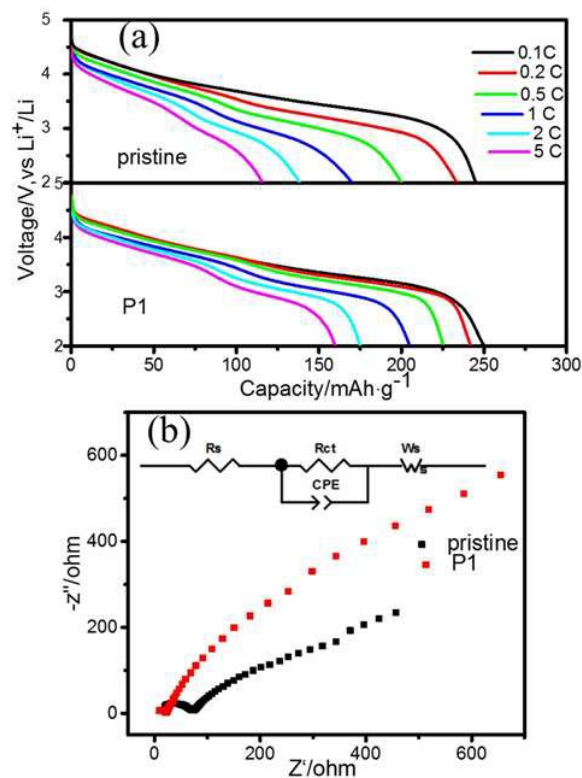


Fig. 4 (a) Rate performances of P1 and the pristine sample; (b) EIS spectra of P1 and the pristine sample.

Fig. 4a shows the rate performance of the cells of the pristine material and P1. The P1 sample can deliver the

discharge capacity of 160.0 mAh·g<sup>-1</sup> at 5 C rate. The improved high-rate capability of the P1 sample is probably due to a fast charge transfer kinetics coming from the surface nitridation. Fig. 4b shows the EIS spectra. According to the equivalent circuit model (Fig. 4b inset), the R<sub>s</sub> means the resistance of the solution (corresponding to a high frequency), while the R<sub>ct</sub> represents the charge transfer associated with the Li<sup>+</sup> pass through the electrode/electrolyte interface<sup>28</sup>. For the P1 sample, the value of R<sub>ct</sub> is 40.10 Ω, which is far less than the pristine sample (89.90 Ω). The improved rate performance could be attributed to the decrease of R<sub>ct</sub>. Meanwhile, the diffusion coefficient of Li<sup>+</sup> in pristine is 5.16×10<sup>-15</sup> cm<sup>2</sup>·s<sup>-1</sup>, while that of the P1 is 1.49×10<sup>-14</sup> cm<sup>2</sup>·s<sup>-1</sup> (Support information). Therefore, it is reasonable to believe that the improvement of the diffusion of Li<sup>+</sup> is mainly due to the introduction of nitrogen to the surface of Li<sub>1.2</sub>Mn<sub>0.52</sub>Co<sub>0.13</sub>Ni<sub>0.13</sub>O<sub>2</sub> material.


The plasma technology was used to improve the electrochemical performance of Li-rich oxide layer cathode material. The material after nitrogen plasma treatment, exhibits an increased coulomb efficiency in the first charge/discharge cycle and an enhanced rate performance. The improved electrochemical performance is attributed to surface nitrogen-doping. Compared to the conventional treatment methods, it is very convenient and could avoid the H<sup>+</sup>/Li<sup>+</sup> exchange, which could damage the structure of materials. Considering usability and safety, it may be a promising way to improve the electrochemical performance of electrode materials for batteries.

### Acknowledgements

The authors gratefully acknowledge the financial support from the Key Project of Science and Technology of Fujian Province (2013H6022), the National Natural Science Foundation of China (21321062) and Fostering Talents of Basic Science (J1310024). The authors also appreciate the positive suggestions of Professor Daiwei Liao.

### Notes and references

1. M. M. Thackeray, C. S. Johnson, J. T. Vaughey, N. Li and S. A. Hackney, *J. Mater. Chem.*, 2005, **15**, 2257-2267.
2. J. Wang, B. Qiu, H. L. Cao, Y. G. Xia and Z. P. Liu, *J. Power Sources*, 2012, **218**, 128-133.
3. F. Amalraj, D. Kovacheva, M. Talianker, L. Zeiri, J. Grinblat, N. Leifer, G. Goobes, B. Markovsky and D. Aurbach, *J. Electrochem. Soc.*, 2010, **157**, A1121-1130.
4. F. Li, S. X. Zhao, Y. C. Wang, K. Z. Wang, B. H. Li and C. W. Nan, *J. Electrochem. Soc.*, 2013, **161**, A102-A108.
5. F. Dogan, B. R. Long, J. R. Croy, K. G. Gallagher, H. Iddir, J. T. Russell, M. Balasubramanian and B. Key, *J Am Chem Soc*, 2015, **137**, 2328-2335.
6. A. R. Armstrong, M. Holzapfe, S. H. Kang, M. M. Thackeray and P. G. Bruce, *J Am Chem Soc*, 2006, **128**, 8694-8698.
7. S. Hy, F. Felix, J. Rick, W. N. Su and B. J. Hwang, *J. Am. Chem. Soc.*, 2013, **136**, 999-1007.
8. Christopher S. Johnson, Naichao Li, Christina Lefief, John T. Vaughey and M. M. Thackeray, *J. Mater. Chem.*, 2008, **20**, 6095-6106.
9. Y. Paik, C. P. Grey, C. S. Johnson, J. S. Kim and M. M. Thackeray, *Chem. Mater.*, 2002, **14**, 5109-5115.
10. F. Wu, N. Li, Y. F. Su, H. Q. Lu, L. J. Zhang, R. An, Z. Wang, L. Y. Bao and S. Chen, *J. Mater. Chem.*, 2012, **22**, 1489-1497.
11. Z. Wang, E. Liu, C. He, C. Shi, J. Li and N. Zhao, *J. Power Sources*, 2013, **236**, 25-32.
12. D. Y. W. Yu, K. Yanagida and H. Nakamura, *J. Electrochem. Soc.*, 2010, **157**, A1177-A1182.
13. J. Zheng, S. N. Deng, Z. C. Shi, H. J. Xu, H. Xu, Y. F. Deng, Z. C. Zhang and G. H. Chen, *J. Power. Sources*, 2013, **221**, 108-113.
14. H. Z. Zhang, Q. Q. Qiao, G. R. Li, S. H. Ye and X. P. Gao, *J. Mater. Chem.*, 2012, **22**, 13104-13110.
15. J. Dai, M. Wang, M. Song, P. C. Li, C. Y. Zhang, A. J. Xie and Y. H. Shen, *Scripta Materialia*, 2016, **112**, 67-70.
16. B. Li, Y. Y. Yu and J. B. Zhao, *Journal of Power Sources*, 2015, **275**, 64-72.
17. M. M. Thackeray, S. H. Kang, C. S. Johnson, J. T. Vaughey, R. Benedek and S. A. Hackney, *Journal of Materials Chemistry* 2007, **17**, 3112-3125.
18. L. Liu, N. Q. Zhang, K. N. Sun and T. Y. Yang, *J. Phys. Chem. Solids.*, 2009, **70**, 727-731.
19. T. Ohzuku, A. Ueda, M. Nagayama, Y. Iwakoshi and H. Komori, *Electrochim. Acta*, 1993, **38**, 1159-1167.
20. S. H. Lee, J. S. Moon, M. S. Lee, T. H. Yu, H. Kim and B. M. Park, *Journal of Power Sources*, 2015, **281**, 77-84.
21. Y. H. Wang, X. F. Bie, K. Nikolowski, H. Ehrenberg, F. Du, M. Hinterstein, C. Z. Wang, G. Chen and Y. G. Wei, *J.Phys.Chem.C*, 2013, **117**, 3279-3286.
22. C. Fu, G. Li, D. Luo, Q. Li, J. Fan and L. Li, *ACS Appl. Mater. Interfaces*, 2014, **6**, 15822-15831.
23. Y. Wu and A. Manthiram, *Electrochemical and Solid-State Letters*, 2007, **10**, A151-A154.
24. S. H. Kang, P. Kemppens, S. Greenbaum, A. J. Kropf, K. Amine and M. M. Thackeray, *J. Mater. Chem.*, 2007, **17**, 2069-2077.
25. X. Y. Liu, T. Huang and A. S. Yu, *Electrochim. Acta*, 2015, **163**, 82-92.
26. G.-Y. Kim, S. B. Yi, Y. J. Park and H. G. Kim, *Mater. Res. Bull.*, 2008, **43**, 3543-3552.
27. Y. Chen, G. Xu, J. Li, Y. Zhang, Z. Chen and F. Kang, *Electrochimica Acta*, 2013, **87**, 686-692.
28. S. J. Shi, J. P. Tu, Y. Y. Tang, X. Y. Liu, X. Y. Zhao, X. L. Wang and C. D. Gu, *Journal of Power Sources*, 2013, **241**, 186-195.

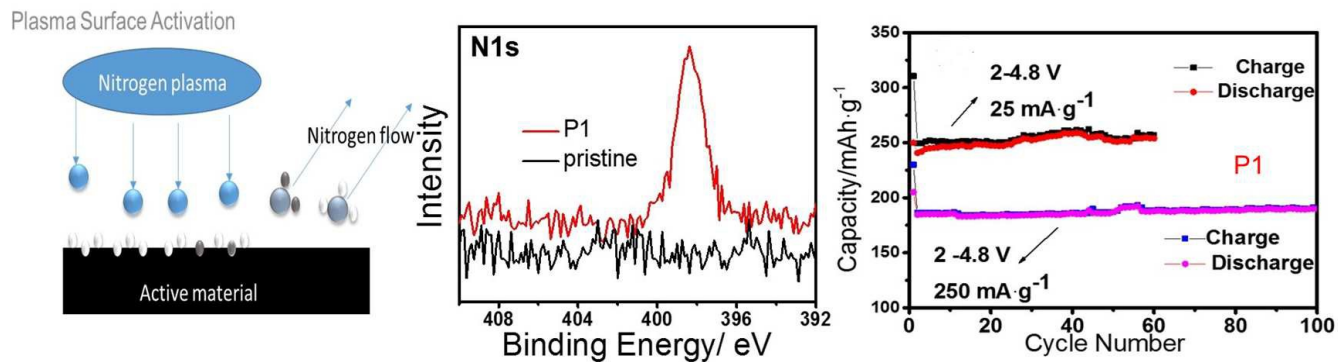

A facile and effective route to introduce the nitrogen on the surface of material with improved electrochemical performance.