

# Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Journal Name

ARTICLE

## A New Approach for Additive-free Room Temperature Sintering of Conductive Patterns Using Polymer-stabilized Sn Nanoparticles

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

www.rsc.org/

Hiroaki Shirai,<sup>a</sup> Mai Thanh Nguyen,<sup>a</sup> Yohei Ishida<sup>a</sup> and Tetsu Yonezawa<sup>\*a</sup>

Tin nanoparticles (Sn NPs) are of considerable interest for conductive printing because of the low melting temperature and low cost. In the present study, polyvinylpyrrolidone (PVP) stabilized metallic Sn NPs were synthesized by a polyol process; and the size of Sn NPs was controlled from 15 to 89 nm by adjusting the amount of PVP. For the first time, we demonstrated that conductive patterns fabricated from the inks of metallic Sn NPs were achieved readily at room temperature under N<sub>2</sub> without reducing gases or additives. The lowest obtained resistivity was  $1.1 \times 10^{-5} \Omega \text{ m}$  which was 100 times higher than that of bulk Sn. The size of Sn NPs, the amount of the stabilizing agent, and the low melting temperature of Sn NPs were found as the main factors controlling the conductivity of the obtained Sn pattern at room temperature sintering. This study offered a new approach for the room temperature fabrication of conductive electronics using printing technique.

### Introduction

Metal nanoparticles (NPs) have been studied in the recent years due to their unique size-dependent physical, chemical, and optical properties.<sup>1-3</sup> One of these size-dependent interesting properties is the melting point depression with a decrease in the size. In particular, the melting point of metal particles dramatically decreases when their size is reduced in the regime of nanoscale size; this has been demonstrated both theoretically and experimentally.<sup>4-7</sup> The surface atoms of a crystal have lower coordination numbers than that of the bulk atoms; thus they bind more loosely to each other compared to the bulk atoms.<sup>6</sup> Therefore a high ratio of the surface area to volume of NPs reduces their melting point significantly.<sup>8</sup> On the basis of this phenomenon, controlling the size of NPs allows for the control of their melting point. As a result, metal NPs are of increasing interest for making inks in order to obtain conductive patterns at a low sintering temperature using printing technique. In contrast to the conventional method called photolithography, conductive printing can produce a large-area pattern at a high speed by a simple process of just printing the ink, evaporating the solvent, and

sintering.<sup>9-15</sup> Conductive printing techniques do not require the deposition and removal of a mask, and the etching and disposal of the useful materials to form the desired pattern as the must steps in photolithography; it is efficient, energy and cost effective, and environmentally friendly. For fabricating conductive patterns at low temperature using the printing technique, the conductive ink made of metallic NPs of good electrical conductivity, chemical stability, and low melting point is highly required.

Until now, NPs of noble metals such as Au<sup>16,17</sup> and Ag<sup>11-13,18,19</sup> have been widely investigated for this purpose because of their high stability and conductivity. However, for a long time the high cost and sintering temperature of noble metal NPs still limit their practical applications. In addition to the high energy consumption, a high sintering temperature causes a thermal stress which induces warpage of the substrate. Recently, sintering Ag NPs at room temperature has been somehow achieved.<sup>20-22</sup> However, in order to promote the aggregation and sintering of Ag NPs to obtain conductive patterns, addition of destabilizing agent, salts, or exposure to HCl vapor is required during these sintering processes. The existence of chlorine or salts in the conductive pattern can oxidize Ag, decrease the stability of the conductive patterns in practical use. Some researchers have considered Cu as an alternative material of noble metals. Although Cu is cheaper than Au and Ag, sintering temperature of Cu<sup>9,10,23,24</sup> NPs is still high and the oxidation of Cu often requires a reductive gas flow during the annealing process. Sometimes, decomposition of organic Cu complex is used for help sintering.<sup>25</sup> Even though some other annealing methods have been suggested to

<sup>a</sup> Division of Materials Science and Engineering, Faculty of Engineering, Hokkaido University, Kita 13, Nishi 8, Kita-ku, Sapporo, Hokkaido, 060-8628, Japan., \* E-mail: tetsu@eng.hokudai.ac.jp; Fax: 011-706-7110

Electronic Supplementary Information (ESI) available: XPS spectrum of Sn NPs; TEM images of Sn NPs synthesized using different amounts of PVP; XRD patterns of as-synthesized Sn NPs and after heated in air; TG curve of only PVP; photographs of a Sn conductive ink and a conductive pattern; SEM image of a conductive pattern; the relation between the PVP amount on surface of Sn NPs and the average diameter of Sn NPs; the calculation of theoretical melting point of Sn NPs; resistivity of Sn patterns prepared from the Sn NPs of different sizes and their mixture; Ratio of number of Sn NPs with diameter less than 24 nm. See DOI: 10.1039/x0xx00000x

substitute the conventional annealing procedure using ultrasonic,<sup>26</sup> laser,<sup>27,28</sup> IR,<sup>29</sup> plasma,<sup>30</sup> and microwave,<sup>31</sup> yet these methods still consume high energy or often yield an incomplete annealing upon one treatment.<sup>32,33</sup>

Then, conductive inks which are low cost and can be sintered at lower temperature without reductive gases or any additives are desired. Researchers have paid considerable attention to Sn NPs as an alternative candidate. Because of the low melting point of the bulk Sn (i.e., 232 °C), the melting temperature of Sn NPs of a size less than few tens of nanometers is expected much lower;<sup>34</sup> this melting point depression of Sn NPs can realize the sintering of Sn NPs even near room temperature without removal of the stabilizing agent. As a result, by using Sn NPs for low temperature sintering, not only the problems associated with materials and energy cost, thermal stress, warpage, and corrosive additives can be solved, but also flexible patterns on paper or plastic substrates can be fabricated using a printing technique.

Zou et al.<sup>35</sup> used a chemical reduction method using NaBH<sub>4</sub> for the synthesis of Sn NPs and successfully synthesized Sn NPs with different average diameters in the range of 30 to 80 nm. However, no clear melting point depression was observed due to the relatively large size and polydispersity of Sn NPs. Jo et al.<sup>36</sup> synthesized fine Sn NPs with sizes range from 11 to 29 nm by a modified polyol process. They found that as the size of Sn NPs decreased, the melting point of Sn NPs got lower. Further their study showed that the melting point of Sn NPs with an average diameter of 11 nm was 177.3 °C. Huang et al.<sup>2</sup> reported the synthesis of Sn NPs with a size of 10.4 nm by mixing a Sn chloride precursor with certain amount of PVP and excess NaBH<sub>4</sub> in a reaction bath. But, the properties of the synthesized Sn NPs were not studied yet.

As described above, the synthesis of Sn NPs with the size of around 10 nm has been reported elsewhere, but there is still a lack of study on the sintering of Sn NPs at near room temperature. Jo et al.<sup>36</sup> reduced the oxide layer on surface of Sn NPs, then removed residual polymer by plasma ashing and sintered Sn inks at 250 °C to obtain the Sn conductive film of 64.27 μΩ cm. Chee et al.<sup>34</sup> synthesized Sn NPs with average size of 8.0 nm, whose melting point was 128 °C. They used these Sn NPs as a binder for commercial Ag inks and got Ag-Sn conductive films after sintering at 170 °C. Sn NPs which have been reported were still required sintering at more than 170 °C. The main reason of the high sintering temperature, despite the fact that the size of NPs of ten to several tens of nanometer, is owing to a thin oxide layer formed on surfaces of Sn NPs in these previous studies. To realize the low sintering temperature and high conductivity of Sn pattern, it is important to prevent the formation of this oxide layer.<sup>34,36,37</sup> Therefore, in the present study, Sn NPs stabilized by PVP were synthesized in reference to the modified polyol process that Jo et al used<sup>36</sup> while all processes regarding the synthesis, purification, and fabrication of Sn NPs and Sn patterns were performed under inert atmosphere (Ar or N<sub>2</sub>). The amount of the input PVP was investigated as a key factor to control both the particle size and surface oxidation of Sn NPs and the conductivity of the resulting Sn pattern. Furthermore,

conductive inks of the as-synthesized Sn NPs were prepared, and then conductive patterns were successfully formed after just drying conductive inks at room temperature without any heating treatment and additives. The factors including the size of NPs, the amount of protecting agent and the low melting point effect of small NPs that influence the resistivity of the obtained Sn pattern will be discussed.

## Experimental

### 2.1 Chemicals

Tin(II) acetate (Wako), polyvinylpyrrolidone (PVP K15, TCI), NaBH<sub>4</sub> (Junsei), and 1,5-pentanediol (Junsei) were used as the precursor, protecting agent, reducing agent, and solvent for the synthesis of Sn NPs, respectively. Molecular sieves 3A 1/16 (Junsei) were used for the dehydration of 1,5-pentanediol. The other chemicals were used as received without further treatment.

### 2.2 Synthesis of Sn NPs

In order to synthesize Sn NPs with various sizes, a certain amount of PVP was dissolved in 50 cm<sup>3</sup> of 1,5-pentanediol in a 200-cm<sup>3</sup> two-neck flask whose inside was cleaned with aqua regia. Then, the mixed solution was vacuumed for 3 hours to remove dissolved oxygen and water. After vacuuming, 0.3552 g of tin(II) acetate was introduced and stirred for 40 minutes under Ar. Then, the mixture was heated to 160 °C. Subsequently, 0.5675 g of NaBH<sub>4</sub> which was dissolved in 10 cm<sup>3</sup> of 1,5-pentanediol was injected into the reaction solution. The reaction solution changed from light yellow to black immediately after the injection of the reducing agent; this implied that the reduction of Sn ions began smoothly. After 15 minutes, the resulting solution was cooled to room temperature. Then, 1-propanol was added to the NPs dispersion and the dispersion was centrifuged for 30 min at 15000 rpm. Centrifuged tube was tightly capped. Addition of 1-propanol to Sn NPs before centrifugation and removal of supernatant after centrifugation were done in nitrogen atmosphere to prevent oxidation. This purification process was repeated 3 times to purify Sn NPs. Different amounts of PVP were used to synthesize Sn NPs as follows, 5.3420, 2.6710, 0.8903, 0.1781, 0.0890, 0.0089, and 0.0018 g; this corresponds to the weight ratios between Sn and PVP (Sn:PVP (w/w)) of 1:30, 1:15, 1:5, 1:1, 1:0.5, 1:0.05, and 1:0.01, respectively. The reaction yield of Sn NPs was higher than 80 % for all syntheses.

### 2.3 Preparation of conductive inks and patterns of Sn NPs

The conductive inks of Sn NPs were prepared by re-dispersing the purified Sn NPs in 1-propanol. The weight concentration of the Sn NPs in all conductive inks was adjusted to 6 wt%. A 20 mm × 20 mm conductive pattern was fabricated by dropping the Sn conductive ink onto a glass substrate and then allowing it naturally drying at room temperature. All procedures were done under nitrogen atmosphere.

## 2.4 Characterizations and measurement

The crystal structure and phases of the obtained NPs were characterized using a Rigaku Miniflex II X-ray diffractometer (XRD, Cu  $K\alpha$  radiation, scanning rate of  $5^\circ \text{min}^{-1}$ ). The morphology of Sn NPs was analyzed using a transmission electron microscope (TEM, JEOL JEM-2000FX, 200 kV). High resolution TEM images were collected using a scanning transmission electron microscope (STEM, FEI Titan3 G2 60-300, 300 kV). Samples for TEM and STEM analysis were prepared by dipping carbon-coated-copper grids in a dispersion of Sn NPs in 1-propanol. The XPS spectrum was measured using an X-ray photoelectron spectroscopic analyser (JPS-9200) in order to confirm that purity of Sn NPs. Sn NPs were deposited on Si wafer for XPS measurements. The amount of PVP remaining on the surface of the obtained Sn NPs was determined using a thermogravimetry analyzer (TGA, Shimadzu DTG-60H). TGA measurement was operated using air at a flow rate of  $100 \text{ cm}^3 \text{ min}^{-1}$  and at a heating rate of  $5^\circ \text{C min}^{-1}$  from room temperature to  $800^\circ \text{C}$ . The sheet resistance of the obtained Sn pattern was measured using a four-point probe equipment (Mitsubishi Chemical Corporation MCP-T610). The sheet resistance of a Sn pattern was calculated from the average of those measured for six different areas of the pattern. A field emission scanning electron microscope (FE-SEM, JEOL JSM-6701F, 15 kV) was used to observe the morphology and take the cross section images of the obtained Sn patterns. The resistivity of a Sn pattern was calculated from the measured sheet resistance and thickness of the pattern.


## Results and Discussion

### 3.1 Crystal structure and morphology of the obtained Sn NPs using various amounts of PVP

Figure 1 shows XRD patterns of Sn NPs synthesized using various amounts of PVP. These XRD patterns exhibited only the peaks of metallic tin without any signals related to tin oxides; this is a good indication that anti-oxidative Sn NPs were successfully synthesized. Furthermore there is no boron signal detected in XPS spectrum of Sn NPs synthesized using lowest PVP amount, i.e. 0.0018 g, (Figure S1). This result indicated that highly pure Sn NPs were obtained.

The morphology of some of the representative Sn NPs synthesized using different amounts of PVP was shown in Figures 2a-2c (also see the TEM images of Sn NPs obtained under other conditions in the Supporting Information, Figure S2). Sn NPs of average diameters of  $15.2 \pm 3.1 \text{ nm}$ ,  $22.3 \pm 5.1 \text{ nm}$ , and  $37.8 \pm 12.5 \text{ nm}$  were obtained using 5.3420, 0.0890, and 0.0089 g of PVP, respectively. The size of the obtained Sn NPs observed by TEM was similar to their crystallite size estimated from the line broadening of the XRD peaks using Scherrer's equation. Therefore, it can be concluded that the synthesized Sn NPs of 15 to 38 nm were single crystalline. In only the case of the largest Sn NPs, TEM size (89 nm) was different from the size calculated from Scherrer's equation (46 nm). This indicates that Sn NPs of more than 46 nm can be

polycrystalline. Figure 2d shows a HRTEM image for the near surface area of a Sn NP (25 nm) synthesized using 0.0890 g of

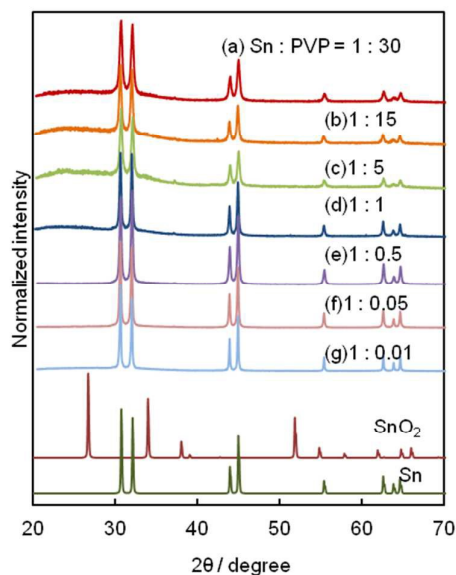

**Figure 1.** XRD patterns of Sn NPs synthesized using different amounts of PVP: (a) 5.3420, (b) 2.6710, (c) 0.8903, (d) 0.1781, (e) 0.0890, (f) 0.0089, and (g) 0.0018 g. The corresponding weight ratios of the input elemental Sn to PVP were indicated inset. The reference patterns of tetragonal  $\text{SnO}_2$  (JCPDS no. 41-1445) and Sn (JCPDS no. 04-0673) are also shown.

PVP. The lattice fringes were observed clearly, and the measured lattice spacing of 0.29 nm corresponds to the (200) planes of  $\beta\text{-Sn}$ .<sup>38</sup> This result suggested that highly pure metallic, single crystalline Sn NPs were synthesized, which also in good agreement with the XRD results where signals related to oxides phases were not observed. The fact that no surface oxide observed in Sn NPs is important, because tin oxides have much lower electrical conductivity and higher melting point, which prevent the sintering of NPs at low temperature with good conductivity. The change in the average diameter of the synthesized Sn NPs in relation to the amount of PVP used is shown in Figure 2e. The size of Sn NPs decreased from 89 to 15 nm with the increase in the amount of PVP used. This was obtained since more PVP presented in the reaction solution prevented the further growth and aggregation of NPs more

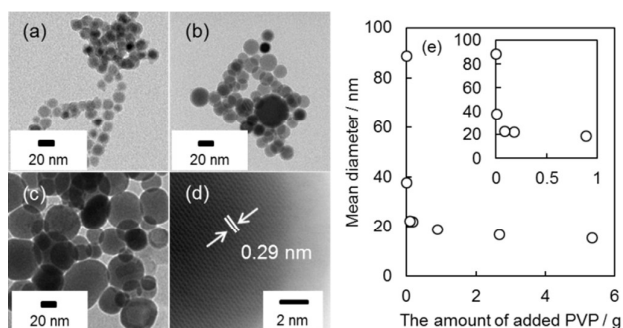


Figure 2. TEM images of Sn NPs synthesized using different amounts of PVP: (a) 5.3420, (b) 0.0890, and (c) 0.0089 g; (d) HRTEM image of a Sn NP (25 nm) obtained using PVP of 0.0890g; (e) average diameter of Sn NPs synthesized with various amounts of PVP from 0.0018 to 5.3420 g. The inset shows the expansion plots of (e) from 0 to 1.0 g of the input PVP.

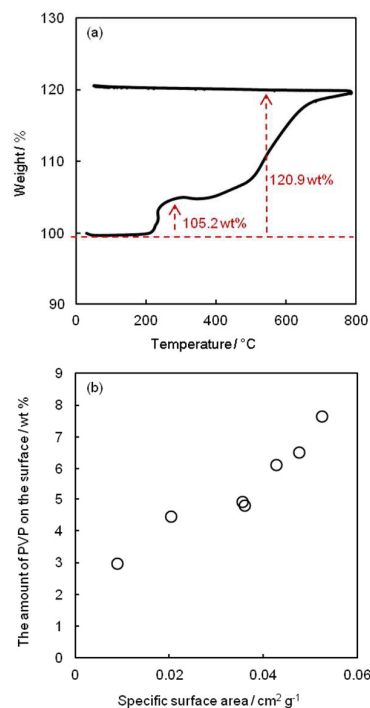


Figure 3. (a) A TGA curve of Sn NPs synthesized using 0.1781 g of PVP, (b) the relation between the specific surface area of Sn NPs and PVP amount on the NP surface.

effectively, leading to the formation of Sn NPs of smaller size. These results suggested that PVP played a role of protecting agent for Sn NPs and varying the PVP amount help control the size of NPs in a wide range.


### 3.2 The amount of PVP on Sn NP surface

In order to study the relation between the amounts of PVP left on NP surface, NP size, and the resistivity of the Sn pattern, it is necessary to estimate these PVP amounts for each size of Sn NPs from the thermogravimetric analysis. Figure 3a shows the TGA result of Sn NPs synthesized using 0.1781 g of PVP. The weight increments were observed at about 220 °C (105.2 wt%)

and 500 °C (120.9 wt%). Weight could be gained from the oxidation of Sn after heating Sn NPs in air. The amorphous oxides were reported on exposure to air at low temperature.<sup>39</sup> The partial oxidation of Sn to crystalline SnO (clearly detected at 400 °C) and complete oxidation to SnO<sub>2</sub> (at 800 °C) during TGA measurement were confirmed as shown in the XRD patterns of the corresponding samples heated to 400 and 800 °C in air (Figure S3). This indicated that the formation of SnO and SnO<sub>2</sub> contributed to the observed weight increases in the TGA result (Figure 3a). Based on the fact that Sn NPs were completely oxidized to SnO<sub>2</sub> after heating to 800 °C and PVP completely decomposed at around 600 °C in the air (Figure S4), the amount of PVP on the surface of Sn NPs was calculated from the weight increment in the TGA analysis. When Sn completely transforms to SnO<sub>2</sub>, it gives a theoretical weight increment of 127.0 wt%. The actual weight increment of 120.9 wt% was obtained from the TGA result (Figure 3a) after SnO<sub>2</sub> completely formed. The difference of the weight increments was attributed to the detachment of PVP remaining on the surface of Sn NPs. By this way, the amount of PVP was estimated for all samples synthesized using different PVP amounts (eq. S1).<sup>24</sup> Figure 3b shows the relation between the specific surface area of Sn NPs, which was calculated from the particle size and the input amount of precursor, and the amount of PVP on the surface of NPs; this implied that the thickness of the PVP layer on the surface of Sn NPs was similar for each sample.

### 3.3 Electrical conductivity of the room temperature sintering Sn films in relation to the PVP amount, NP size and morphology of the films

Sn conductive inks of 6 wt% Sn were successfully prepared by

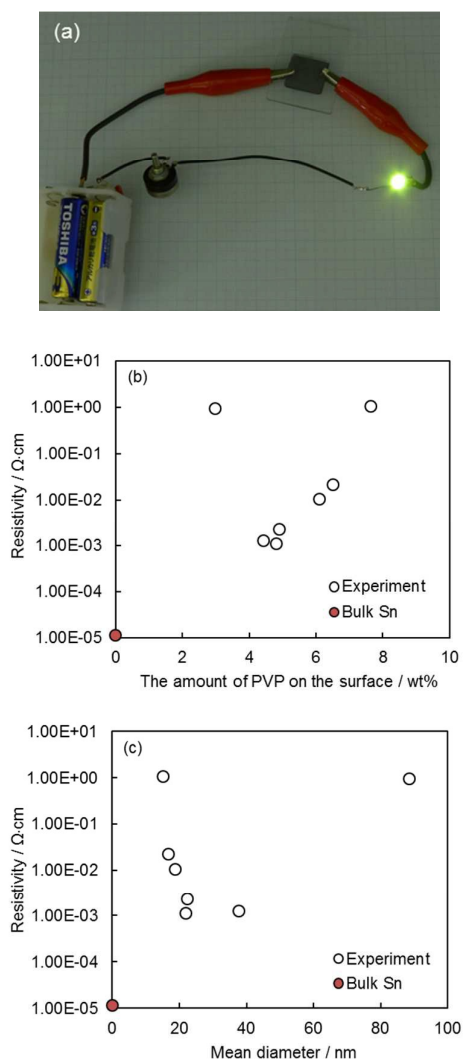


**Figure 4.** (a) An optical photograph of the conductive Sn pattern allowing electrical connection to light-up a LED tip. The resistivity of the Sn conductive patterns as a function of (b) the PVP amount on the surface of Sn NPs and (c) the NP size. A red point is for the resistivity of the bulk Sn.

re-dispersing Sn NPs in 1-propanol (Figure S5a). These Sn conductive inks were dropped on the glass substrates and dried at room temperature, resulted in Sn conductive patterns with surface area of 20 mm × 20 mm (Figure S5b), and thickness of about 100 μm (Figure S6). The conductivity of Sn patterns was achieved at room temperature sintering for all samples. The obtained pattern of the lowest conductivity was demonstrated also enough electron-conductive to turn on a LED tip (Figure 4a).

As PVP used to stabilize NPs is an organic polymer with low conductivity, the presence of the remaining PVP on NPs surface definitely has an important influence on the conductivity of the film made from Sn NPs. The resistivity of the Sn conductive patterns as a function of the amount of PVP on the surface of Sn NPs is shown in Figure 4b. When larger

amount of PVP (7.6 wt%) attached on the surface of Sn NPs, a high resistivity was obtained ( $1.0 \times 10^0 \Omega \text{ cm}$ ). As the amount of PVP on the surface of Sn NPs decreased from 7.6 to 4.4 wt%, the resistivity also decreased to the minimum value of  $1.1 \times 10^{-3} \Omega \text{ cm}$  (4.8 wt% PVP), then kept almost constant around  $1.1 \times 10^{-3}$  (4.4–4.8 wt% PVP). In this regime of PVP amount (7.6–4.4 wt% PVP), a linear relation between the resistivity of the pattern and the remaining PVP amount was observed. It was also found that the resistivity decreased with the increase in the size of Sn NPs (15 to 38 nm, Figure 4c), of which the corresponding PVP amount on the particle surface decreased from 7.6 to 4.4 wt%. Since the amount of PVP remaining on the surface of NPs was reversely proportional to the size of the obtained Sn NPs, NPs of larger size have less PVP on its surface (Figure S7). The larger the NPs, the smaller the total surface area, and the lower the contact resistant and electron scattering. As a result, the greater conductivity is obtained. Therefore, the decrease in the PVP amount and the increase in the NP size both positively contributed to a good conductivity (decrease in the resistivity) of the pattern with the particle size ranging from  $15.2 \pm 3.1$  to  $37.8 \pm 12.5$  nm, and the surface PVP amount decreasing from 7.6 to 4.4 wt%.

When the PVP amount on the surface of NPs decreased from 4.4 to 3.0 wt%, the largest size of Sn NPs (i.e.,  $88.6 \pm 21.3$  nm, 3.0 wt% PVP) were obtained. These particles were also used to make the conductive pattern, but the resistivity sharply increased. This result indicated that in addition to the amount of PVP and the size of NPs, other factors also affected the resistivity of the conductive Sn pattern. Carefully investigating the morphology of the conductive pattern, we found that a significant fusion of Sn NPs occurred in the pattern prepared from Sn NPs of  $37.8 \pm 12.5$  nm (Figure 5a) while that was almost negligible in the pattern prepared from Sn NPs of  $88.6 \pm 21.3$  nm (Figure 5b). In consequence, using Sn NPs of  $37.8 \pm 12.5$  nm likely produced a more compact pattern and better sintering behavior than using Sn NPs of  $88.6 \pm 21.3$  nm. On the contrary, Figure 5b shows almost no necking of the particles. The obtained results could originate from the melting of small Sn NPs observed in Sn NPs of 37.8 nm; these small Sn NPs helped larger NPs join together and filled the space among the NPs in the pattern. The theoretical melting

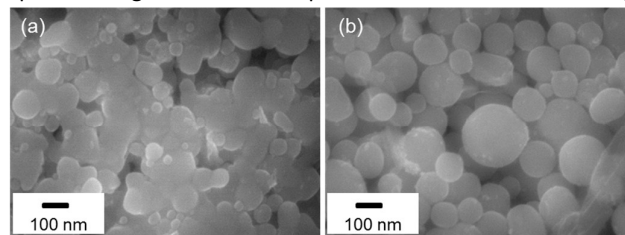


**Figure 5.** SEM images of the surface of Sn patterns made of Sn NPs synthesized using: (a) 0.0089 g PVP (Sn NPs of  $37.8 \pm 12.5$  nm), (b) 0.0018 g PVP (Sn NPs of  $88.6 \pm 21.3$  nm).

point of Sn versus particle size calculated from Gibbs-Thomson equation (eq. S2)<sup>40</sup> was shown in Figure S8. It is noticeable that Sn NPs of 10.5 nm could melt at 26 °C. Hence, these small Sn

NPs can work as joint materials to improve the sintering. The melting of small Sn NPs also worked in other conductive patterns prepared using Sn NPs in size range of 15 to 38 nm, but the effect of the melting of small Sn NPs on decrease of the resistivity of the pattern as the NP size decreased was partly compensated by the high amount of PVP, surface area, and contact resistance owing to small NP sizes. Because of the lack of the small Sn NPs that melt and join other NPs in the pattern at room temperature, even though made from Sn NPs of the largest size ( $88.6 \pm 21.3$  nm) and least amount of PVP, the final Sn pattern still exhibited the highest resistivity. The lowest resistivity obtained for the pattern using Sn NPs of  $22.0 \pm 5.0$  nm was achieved as the optimization of three factors including the NP size, the amount of PVP, and the amount of Sn NPs that can melt.

In order to demonstrate the room temperature binding effect from small Sn NPs, physically mixing Sn NPs of largest size ( $88.6 \pm 21.3$  nm) and smallest size ( $15.2 \pm 3.1$  nm), which both had the highest resistivity, was performed. The pattern fabricated from mixture of Sn NPs (50 wt%) showed a lower resistivity than both patterns made from only smallest or largest Sn NPs alone (Figure 6). In this figure, the average resistivity of the patterns fabricated by only the smallest or the largest Sn NPs was used. It was known from above that the largest Sn NPs could not make neckings each other and smallest NPs contained a large amount of PVP, resulted in high resistivities. The mixture gives a lower resistivity because smallest NPs play a role of glue which makes connections among larger NPs. The resistivity decreased by addition of the smallest Sn NPs to the largest Sn NPs emphasized the room temperature sintering effect of the smallest Sn NPs. In contrast, mixing smallest Sn NPs with Sn NPs of  $37.8 \pm 12.5$  nm (nearly lowest resistivity), no more decrease in resistivity of the mixed-Sn NP pattern compared to that of only Sn NP ( $37.8 \pm 12.5$  nm) pattern was detected (Figure S9). This suggests that the Sn NPs of  $37.8 \pm 12.5$  nm contained enough amount of small NPs to play as binders, addition of the smallest Sn NPs did not reduce the conductivity. As shown in Figure 4, the relation between the PVP amount on Sn NPs and the resistivity of the patterns is linear in the range of the PVP amount on Sn NPs from 4.4 to 7.6 wt%. The ink made from Sn NPs in this range may have enough amount of small Sn NPs which could melt and play as binders. In other word, resistivity in this range

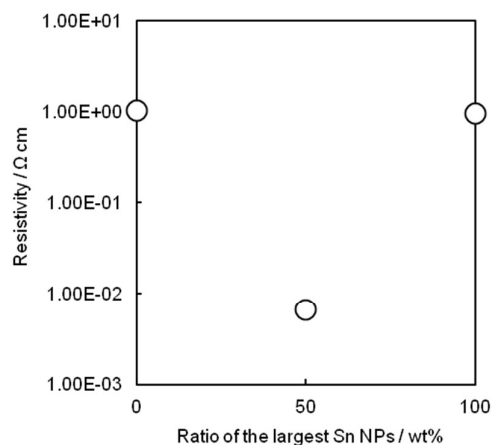

**Figure 6.** Resistivity of Sn patterns prepared from the smallest Sn NPs ( $15.2 \pm 3.1$  nm), the largest Sn NPs ( $88.6 \pm 21.3$  nm), and their mixture at 50 wt%.

depends on only the PVP amount and size of Sn NPs.

We also observed that in the case of Sn NPs with the average diameter of 37.8 nm (2nd largest Sn NPs) where their mixture with the smallest Sn NPs did not result in further decrease of resistivity, the minimum size of Sn NPs observed by TEM and the minimum size of Sn NPs in the sintered film at room temperature observed by SEM was 10 nm and 24 nm, respectively. Moreover, samples in which fusion of Sn NPs were observed contained at least 15 % of Sn NPs of less than 24 nm (Table S1). On the other hand, Sn films without particle fusion did not show Sn NPs in this size range. These results indicated that in practical probably not only Sn NPs with size smaller than 10 nm but also those with size smaller than 24 nm can play a role of glue at room temperature sintering.

The sintering of Sn NPs at room temperature has been revealed for the first time and a low resistivity was achieved without any surface treatment, high temperature sintering, reducing gas or additives. Sn NPs with average diameter less than 10 nm was reported elsewhere,<sup>34</sup> but they could not be used as a glue for room temperature sintering since there were an oxide layer hindering the NPs to join together. Other studies reported the use of Sn NPs for ink-jet printing at room temperature in the ambient atmosphere, but an plasma ashing with oxygen gas to remove the residual polymer and an additional high temperature  $H_2$  reduction step was required followed by high temperature (at more than 160 °C) sintering to obtain conductive Sn patterns.<sup>36</sup> In our study, as metallic Sn NPs was synthesized and purified under inert atmosphere, and inks and conductive patterns were prepared under  $N_2$ , we could demonstrate the room temperature sintering of metallic Sn NPs without addition of corrosive additives and the achieved low resistivity of Sn patterns ( $1.1 \times 10^{-3}$  Ω cm). The obtained resistivity is 100 times higher than that of bulk Sn and 17 times higher than that of Sn films fabricated by Jo et al.,<sup>36</sup> which used sintering at 250 °C for 1h. This may be caused by (i) without using such high temperature sintering, (ii) PVP left on Sn NPs, and may be (iii) very diluted Sn loading in the ink. For further reduction of the resistivity, using a decomposable polymer as a protective agent for Sn NPs or using more benign

additives (short-chain amine compounds) will be considered. These works are a part of our future study.

## Conclusions

PVP-stabilized metallic Sn NPs of various sizes were successfully synthesized in order to obtain low cost conductive inks and to achieve low temperature sintering. The size of Sn NPs was controlled in the range from 15 to 89 nm simply by changing the input amount of PVP. XRD showed no oxide peak. Sn conductive inks were then prepared using the as-synthesized Sn NPs; and Sn conductive patterns with high conductivities were obtained readily at room temperature. The results of the present study illustrated three important factors that influence the resistivity of the conductive patterns: (i) the amount of PVP which attached on the surface of Sn NPs, (ii) the number of contact points among Sn NPs (the size of Sn NPs), and (iii) the existence of Sn NPs which melt at room temperature. Without removing the protective polymer or introducing any additives, the lowest obtained resistivity of Sn pattern was  $1.1 \times 10^{-3} \Omega \text{ cm}$  which was 100 times higher than that of bulk Sn and the highest achieved conductivity for the Sn pattern prepared from Sn NPs at room temperature. The existence of Sn NPs, which can play as binders and allow for room temperature sintering of Sn NPs, was revealed important to obtain low resistivity at room temperature sintering in this study. We believe that the results presented in this study contribute low cost and highly conductive inks for room temperature sintering using printing technique.

## Acknowledgements

This work was partially supported by KAKENHI (A, 24241041 to TY) from JSPS, Japan, and Murata foundation. Some characterizations of tin nanoparticles were performed using the facilities of Nanotechnology platform, MEXT, Japan.

## Notes and references

- C.-P. Liang, Y. Yamauchi, C.-H. Liu and K. C.-W. Wu, *Dalton Trans.*, 2013, **42**, 8704.
- N. Toshima and T. Yonezawa, *New J. Chem.*, 1988, **22**, 1179.
- Y.-C. Yen, B. Creran and V. M. Rottello, *Nanoscale*, 2012, **4**, 1871.
- P.-A. Buffat and J.-P. Borel, *Phys. Rev. A*, 1976, **13**, 2287.
- S. J. Zhao, S. Q. Wang, D. Y. Cheng and H. Q. Ye, *J. Phys. Chem. B*, 2001, **105**, 12857.
- F. G. Shi, *J. Mater. Res.*, 1994, **9**, 1307.
- M. Schmidt, R. Kusche, B. V. Issendorff and H. Haberland, *Nature*, 1998, **393**, 238.
- H. Jiang, K.-S. Moon, F. Hua and C. P. Wong, *Chem. Mater.*, 2007, **19**, 4482.
- M. Matsubara, T. Yonezawa, T. Minoshima, H. Tsukamoto, Y. Yong, Y. Ishida, M. T. Nguyen, H. Tanaka, K. Okamoto and T. Osaka, *RSC Adv.*, 2015, **5**, 102904.
- M. Matsubara, T. Yonezawa and H. Tsukamoto, *Bull. Chem. Soc. Jpn.*, 2015, **88**, 1755.
- J. Yeo, G. Kim, S. Hong, M. S. Kim, D. Kim, J. Lee, H. B. Lee, J. Kwon, Y. D. Suh, H. W. Kang, H. J. Sung, J.-H. Choi, W.-H. Hong, J. M. Ko, S.-H. Lee, S.-H. Choa and S. H. Ko, *J. Power Sources*, 2014, **246**, 562.
- J. Perelaer, M. Klokkenburg, C. E. Hendriks and U. S. Schubert, *Adv. Mater.*, 2009, **21**, 4830.
- Y. M. Shin, H.-J. Kim, S. P. Jang and J.-H. Lee, *J. Electron. Mater.*, 2014, **43**, 3372.
- E. Fisslthaler, S. Sax, U. Scherf, G. Mauthner, E. Moderegger, K. Landfester and E. J. W. List, *Appl. Phys. Lett.*, 2008, **92**, 183305.
- H. Siringhaus, T. Kawase, R. H. Friend, T. Shimoda, M. Inbasekaran, W. Wu and E. P. Woo, *Science*, 2000, **290**, 2123.
- M. B. Cortie, M. J. Coutts, C. Ton-That, A. Dowd, V. J. Keast and A. M. McDonagh, *J. Phys. Chem. C*, 2013, **117**, 11377.
- A. Gupta, S. Mandal, M. Katiyar and Y. N. Mohapatra, *Thin Solid Films*, 2012, **520**, 5664.
- Y. J. Moon, H. Kang, K. Kang, S.-J. Moon and J. Y. Hwang, *J. Electron. Mater.*, 2015, **44**, 1192.
- Q. Huang, W. Shen, Q. Xu, R. Tan and W. Song, *Mater. Chem. Phys.*, 2014, **147**, 550.
- S. Magdassi, M. Grouchko, O. Berezin and A. Kamyshny, *ACS Nano*, 2010, **4**, 1943.
- M. Grouchko, A. Kamyshny, C. F. Mihailescu, D. F. Anghel and S. Magdassi, *ACS Nano*, 2011, **5**, 3354.
- P. F. Moonen, E. Bat, W. P. Voorthuijzen and J. Huskens, *RSC Adv.*, 2013, **3**, 18498.
- Y. Yong, T. Yonezawa, M. Matsubara and H. Tsukamoto, *J. Mater. Chem. C*, 2015, **3**, 5890.
- T. Yonezawa, H. Tsukamoto and M. Matsubara, *RSC Adv.*, 2015, **5**, 61290.
- T. Yonezawa, H. Tsukamoto, Y. Yong, M. T. Nguyen and M. Matsubara, *RSC Adv.*, 2016, **6**, 12048.
- H. Yamauchi, T. Dobashi and S. Sato, *Chem. Lett.*, 2012, **41**, 1154.
- A. Watanabe, *Sci. Technol.*, 2013, **26**, 199.
- G. Qin, A. Watanabe, H. Tsukamoto and T. Yonezawa, *Jpn. J. Appl. Phys.*, 2014, **53**, 096501.
- D. Tobjörk, H. Aarnio, P. Pulkkinen, R. Bollström, A. Määttänen, P. Ihalainen, T. Mäkelä, J. Peltonen, M. Toivakka, H. Tenhu and R. Österbacka, *Thin Solid Films*, 2012, **520**, 2949.
- I. Reinhold, C. E. Hendriks, R. Eckardt, J. M. Kranenburg, J. Perelaer, R. R. Baumann and U. S. Schubert, *J. Mater. Chem.*, 2009, **19**, 3384.
- J. Perelaer, R. Jani, M. Grouchko, A. Kamyshny, S. Magdassi and U. S. Schubert, *Adv. Mater.*, 2012, **24**, 3993.
- Y. H. Yoon, S.-M. Yi, J.-R. Yim, J.-H. Lee, G. Rozgonyi, Y.-C. Joo, *Microelectron. Eng.*, 2010, **87**, 2230.
- T. Kumpulainen, J. Pekkanen, J. Valkama, J. Laakso, R. Tuokko and M. Mäntysalo, *Opt. Laser Technol.*, 2011, **43**, 570.
- S.-S. Chee and J.-H. Lee, *Thin Solid Films*, 2014, **562**, 211.
- C.-D. Zou, Y.-L. Gao, B. Yang and Q.-J. Zhai, *Trans. Nonferrous Met. Soc. China*, 2010, **20**, 248.
- Y. H. Jo, I. Jung, C. S. Choi, I. Kim and H. M. Lee, *Nanotechnology*, 2011, **22**, 225701.
- P.-C. Huang and J.-G. Duh, 2008 Electronic Components and Technology Conference (ECTC), 2008, 431.
- N. H. Chou and R. E. Schaak, *J. Am. Chem. Soc.*, 2007, **129**, 7339.
- K. Kravchik, L. Protesescu, M. I. Bodnarchuk, F. Krumeich, M. Yarema, M. Walter, C. Guntlin and M. V. Kovalenko, *J. Am. Chem. Soc.*, 2013, **135**, 4199.
- T. Yonezawa, S. Arai, H. Takeuchi, T. Kamino and K. Kuroda, *Chem. Phys. Lett.*, 2012, **537**, 65.