

Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Cite this: DOI: 10.1039/xxxxxxxxxx

Local order drives the metallic state in PEDOT:PSS[†]

Philipp Stadler,^{*a} Dominik Farka,^a Halime Coskun,^a Eric D. Glowacki,^a Cigdem Yumusak,^a Lisa M. Uiberlacker,^b Sabine Hild,^b Lucia N. Leonat,^c Markus C. Scharber,^a Petr Klapetek,^d Reghu Menon,^e and N. Serdar Sariciftci^a

Received Date
Accepted Date

DOI: 10.1039/xxxxxxxxxx

www.rsc.org/journalname

Weak localization describes a metallic system, where due to the presence of disorder the electrical transport is governed by inelastic electron relaxation. Thereby the theory defines a threshold of spatial and of energetic disorder, at which a metal-insulator transition takes place. To achieve a metallic state in an inherently disordered system such as a conductive polymer, one has to overcome the threshold of localization. In this work we show that the effective suppression of disorder is possible in solution-processible poly(3,4-ethylenedioxythiophene)-poly(styrene sulfonate). We grow polymer films under optimized conditions allowing self-organization in solution. Interestingly, we find the requisite threshold, at which the system becomes finally metallic. We characterize the transition using a complementary morphology and magneto-electrical transport study and find coherent electron interactions, which emerge as soon as local order exceeds the macromolecular dimensions. These insights can be used for discrete improvement in the electrical performance, in particular for tailoring conductive polymers to alternative metal-like conductors.

1 Introduction

The generation of an intrinsically metallic conductive polymer (CP) is one of the primary goals in developing powerful organic and bio-organic electronics.^{1–8} However, the question, when a CP is regarded as metallic, has caused ambiguous discussions.^{1,2,5,9–11} This relates to the fact, that CPs are highly anisotropic - their solid state structure reflects a mutual interplay of different interactions: A polymer chain is covalently connected along the chain direction, while between the adjacent macromolecules stacking forces are dominant. Finally, conductive polymers have also a strong ionic character, as in the doped form, (delocalized) carriers on the polymer chain are counterbalanced by immobile ions. Furthermore, the polymers themselves are prone to condense dispersively with alternating amorphous and crystalline regions. Taking these views into consideration the formation of a metallic state appears strongly dependent on the local order - with accepting the fact, that some disorder is inher-

ently present. This is an important information, as even classic metals change their electrical transport drastically in presence of disorder. The physics are thereby described by weak localization (WL).¹² WL specifies a system in presence of disorder, when the electrical transport is governed by inelastic scattering processes. This translates to a change in the sign of the temperature coefficient of the conductivity $\frac{d\sigma}{dT}$ to a positive value. At low temperatures, a minimum is reached - Mott's minimum conductivity, σ_{\min} . At this point inelastic and elastic processes are equally present. In practice, the σ_{\min} for CPs is close to $T = 0$ and therefore experimentally difficult to observe. We therefore shift our attention to the mean inelastic electron scattering lengths, which can be measured above σ_{\min} to obtain a direct insight of the local order.^{13–16} With this information it is possible to resolve the ambiguity of the electrical transport in conductive polymers. Shedding light to the inelastic scattering processes allows to resolve the metal-insulator-transitions as described by Mott and Anderson.^{17,18} In this work we harness the great potential of self-organization in solution and set up an experimental study to demonstrate finally the metallic state established by the subsequent local order. This represents the crucial ingredient needed to drive the metallic state - even in systems having at first sight a moderate conductivity at room temperature. The experimental path towards the metal-insulator-transition and the fundamental insight to the electron scattering is presented in detail.

^aInstitute of Physical Chemistry, Johannes Kepler University Linz, Altenbergerstr. 69, 4040 Linz, Austria. Fax: +43 732 2468 1213; Tel: +43 732 2468 8770; E-mail: philipp.stadler@jku.at

^bInstitute of Polymer Science, Johannes Kepler University Linz, Altenbergerstr. 69, 4040 Linz, Austria.

^cThe National Institute for Electrical Engineering, ICPE-CA, Splaiul Unirii 313, 030138 Bucharest, Romania.

^dCentral European Institute of Technology, Koliste 13a, 602 00 Brno, Czech Republic.

^eDepartment of Physics, Indian Institute of Science, Bangalore 560012, India.

[†] Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/b000000x/

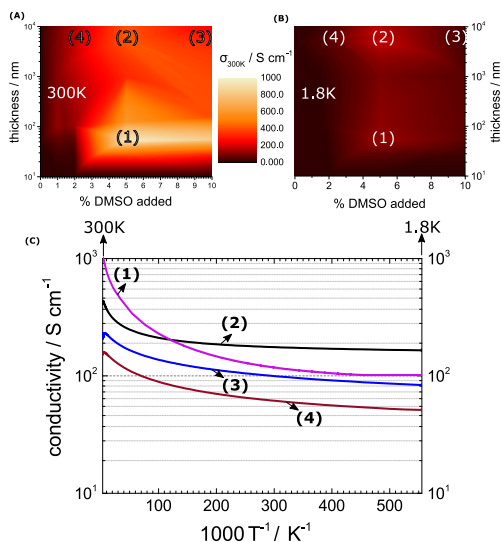


Fig. 1 (A) Room-temperature mapping of PEDOT:PSS conductivities at different DMSO-concentration and thickness. (B) repeats the map at 1.8 K. (C) The temperature profiles of the conductivities are significantly different between bulk and thin-films. The in detail studies systems are highlighted in the map at 55 nm and 5% DMSO (1), 8.4 μm and 5% DMSO (2), 8.4 μm and 10% DMSO (3) and finally 8.4 μm and 2% DMSO (4).

2 Sample growth, measurement techniques and characteristics

We apply a facile route via supramolecular self-organization in solution to intrinsically achieve the metallic state in poly(3,4-ethylenedioxythiophene):polystyrenesulfonate (PEDOT:PSS) with alternating concentrations of dimethylsulphoxide (DMSO) and alternating thickness. The films are prepared from the original commercial dispersion (PH1000, Heraeus) using 4 main recipes with various intermediate blends: No DMSO (ref.), 2% (i.e. 20 μl per ml volume), 5% and 10% DMSO, both spin-coating and drop-casting. The dispersion is vigorously stirred at 60 $^{\circ}\text{C}$ overnight. For the thicker films we used drop-casting with variable volumes of the dispersion (1 ml to 0.1ml) dropped on a glass waver (2.54 \times 2.54 cm^2), which is dried at 60 $^{\circ}\text{C}$ for 2 h. The as-gained films (1 to 10 μm) are elevated from the glass and dried once more in inert atmosphere over CaH_2 at 100 $^{\circ}\text{C}$. For the thin-films the dispersion is spin-cast using various recipes to obtain thin-film systems ranging from 10 nm up to 100 nm. All films are subsequently dried for 3 days in inert atmosphere to remove residual DMSO and water. The free-standing bulk films are cut to a rectangular 1.5 \times 10 mm^2 slices and contacted with gold-patterns in vacuo as shown in the photograph (figure 5D) and mounted to the cryomagnet system, so that the B -field is perpendicular to the film plane (B_z). In similar manner, as cast thin-films on sapphire are contacted directly by as-deposited gold. We denote that due to the change of the processing steps between thicker and thinner films, we find minor thickness-effect on the electrical performance (see figure 1A, 1B). Finally, the voltage drop across the inner leads is measured (at $I_x = 50 \mu\text{A}$) as a function of T and B -field. The metallic film picks are characterized further by repeating scans for conductivity and

magneto-conductivity, respectively. Similarly, for the XRD spectra the films are cut into 1 \times 1 cm^2 squares and analyzed using a Bruker AXS diffractometer with a $\text{CuK}\alpha$ source. For the atomic force microscopy (AFM), the bulk-films are cut with a Leica Ultracut microtome and the polished cross-sections are analyzed using a Asylum Research MFP-3D Stand Alone AFM. The thin-films are analyzed directly on the surface as grown on the sapphire substrate.

3 Results and discussion

The casting process for PEDOT:PSS has been investigated in detail earlier - in particular the co-solvent treatment has lead to substantial improvements in the conductivities.^{4,11,19,20,20–22} An established pair represent PEDOT:PSS and DMSO as co-solvent.^{21,23–25} This is the system of-choice in this work.

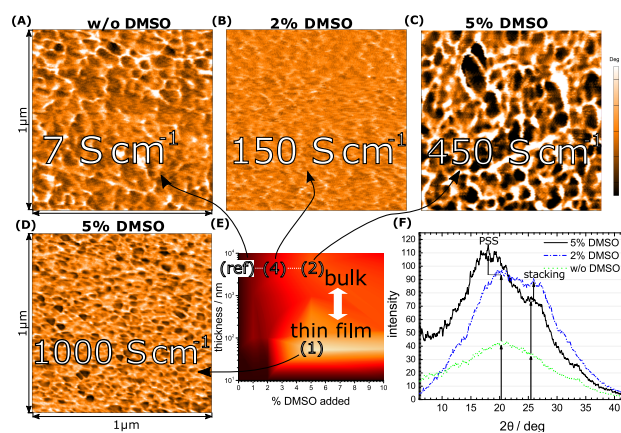


Fig. 2 In the panels (A,B and C) the cross-section morphologies by AFM of no DMSO (ref), (4) and (2) are shown. In (D) the morphology of (1) by AFM is depicted (surface scan). The XRD-spectra in (F) highlight the improved crystallinity in (4) and (2) as compared to (ref) by increasing the DMSO concentration during film-growth.

We start with a number of thin-film PEDOT:PSS recipes yielding 10 nm thickness and successively increase the width to access a more and more bulk phase up to 10 μm . In addition we modify the co-solvent presence between 0 and 10% of the original volume dispersion. Our goal is to attain a detailed insight of the co-solvent concentration and of the final film thickness on the resulting conductivities (figure 1A). We consistently find excellent electrical performances at DMSO-concentrations around 5%. Here we achieve peak conductivities of 1000 S cm^{-1} at a thickness 55 nm as seen in the map in figure 1A denoted further as (1). The effect is less pronounced at lower and higher DMSO concentrations, which is in agreement with previous studies.^{23,24}

When the film thickness expands to a bulk system greater than 1 μm we see a similar rise of the electrical performance on the DMSO-concentration. Nonetheless, the bulk-films achieve maximum 490 S cm^{-1} at 5% DMSO and 8.4 μm respectively (2). So the map in figure 1A exhibits a consistent out-performance of thin-films over bulk films. Other in detail studied systems are 10% DMSO and 8.4 μm (3) and 2% DMSO and 8.4 μm (4).

When we repeat the mapping at 1.8 K we obtain a first insight, where in the map the local order allows the formation of a metal-

lic state (figure 1B). According to Mott's minimum conductivity, regions off the metallic regime exhibit an infinite low conductivity, which is valid for the preponderant dark regions seen in the 1.8 K map. Regimes in proximity of a metal-insulator transition (MIT) appear still conductive - they are found in the same hotspots as at room temperature with an important changeover: At 1.8 K, the bulk systems outperform the thin-films. The reason for this lies in the pronounced temperature-dependence of the thin film conductivities. Meanwhile, the bulk film conductivities exhibit a moderate temperature-profile in agreement with weak localization with a flattening as the temperature approaches 0 (figure 1C).

In combination, the maps show us the optimum region, which lies between 2 and 5% DMSO and 8.4 μm layer thickness (2) and (4). At 5% DMSO and 1.8 K, for example, the bulk-conductivity (2) exceeds the 55 nm thin-film (1) conductivity by a factor of nearly 2. This minor temperature-sensitivity points out that the thickness plays a role in terms of local order - it relates to the different parameters in the processing and to a suppressed substrate-effect in the bulk-systems. To support our findings from the conductivity maps we view the morphologies by AFM and XRD, in particular in the optimum region (figure 2).

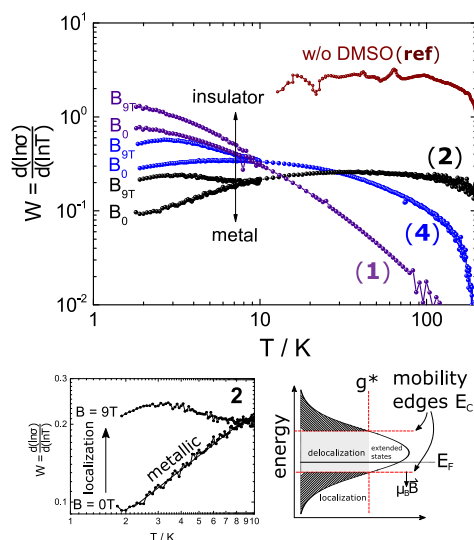


Fig. 3 (A) highlights the exponent of the power-law dependence $\frac{d(\ln\sigma)}{d(\ln T)}$ (W), in particular at low temperatures ($T \leq 10$ K) and high magnetic field ($B = 9$ T). While the first sample (no DMSO) (ref) operates beyond the transition line at $W = 1$, we see a shift towards a metal in (1), (2) and (4) and high B -field localization resulting in a negative magnetoconductivity.

For the bulk films we plot the XRD spectra at no (ref), 2% (4) and 5% DMSO (2). A sharpened profile in terms of crystallinity correlates with the DMSO presence during growth.^{26,27} (figure 2E). In general the rise of the electrical conductivity from figure 1A is reflected in a pronounced signal, which underlines the higher degree of crystallinity. The discrete peak originating from π -stacking of PEDOT emerges at 25 deg. It is overlapped by the broad response of the PSS halo with a maximum at 20 deg. The spectral shaping through DMSO consequently supports our argument of improved crystallization in presence of DMSO valid for both components, PEDOT and PSS, respectively. To clarify,

we present a comparison of PEDOT and regio-regular poly(-3-hexylthiophene) (rr-P3HT) grown at similar conditions in the supporting information. A supplementary view to the morphological changes induced by DMSO is outlined by atomic force microscopy (AFM). As shown in the phase images in figure 2A,B,C and D we find different grain sizes at each representative (conductivity) area (marked as white rectangular frame) from the conductivity map (figure 2E). Figure 2D depicts the thin-film phase image revealing a randomized distribution of structured domains with different grain sizes. This is reminiscent to the bulk-film without DMSO, where polydispersity is detected again. Obviously, little presence of DMSO (2%) and thicker films (4) improve the homogeneity a lot as shown in figure 2B, where the gains of the structure become smaller. To achieve a growing grain size and a homogeneous dispersion the concentration has to be further increased to 5% (2), where we find the point of merit in terms of conductivity, crystallinity and morphology in the bulk-films. We denote that we derive the bulk-film morphology from cross-sectional scans in order to allow a meaningful comparison between bulk and thin-film morphologies.

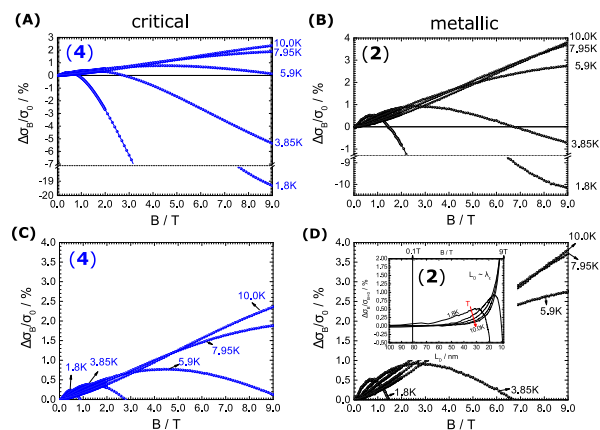


Fig. 4 Both 2% (4) and 5% DMSO-cast (2) PEDOT:PSS systems reflect the interplay between positive and negative magnetoconductivity (MC) at low T . For each T the positive effects dominates first at low B followed by a flip to the negative by increasing B (at 1.8 K, 3.85 K and 5.9 K). At higher T (7.95 and 10.0 K) the MC is only positive. We denote that the negative effect is more pronounced in the critical sample. In (C) and (D) we expand the positive side and show the semicircular development of each MC with B . In the metallic sample (1) we depict its MC as function of the Landau orbit size L_D in addition to show the interference at resonance conditions, when the mean inelastic scattering length λ_e and L_D are of similar dimension (inset).

The morphology response of the different conductivity-stages reveal the importance of long-range order plus the role of dispersivity seen in growing ordered domains of similar size, which explains the improved electrical performance at low- T .

Back in figure 1 we outline the positive temperature coefficient $\frac{d\sigma}{dT}$ with a finite conductivity as T approaches 0 best seen in (4), (1) and (2). This behaviour corresponds to weak localization. To resolve the low- T regime, we use the derivative of the conductivity in logarithmic scale $\frac{d(\ln\sigma)}{d(\ln T)}$ further denoted as W .²⁸

The metallic character is expressed by the slope and magnitude of $W(T)$. As seen in figure 3 the system without DMSO

(ref.) shows a constant W with quantities greater than 1 (insulating regime). In contrast, (4), (1) and (2) deviate - $W(T)$ is not constant. In particular, at low temperature it illustrates, on which side of the MIT the system is situated. In case of bulk 5% DMSO (2), the slope of $W(T)$ becomes positive indicating a metallic state (figure 3B). We denote that in particular the thin-film response from (1) shows a clear non-metallic fingerprint at low- T , which we assign to the role of dispersivity.

The proximity of the metallic state can be tested by applying a high magnetic field perpendicular to the substrate plane ($B_z = 9$ T). The field induces localization and quenches the metallic state as shown in figure 3. A substantial change of $W(T)$ by B is thereby seen below 10 K. There W splits up into a critical-metallic ($B = 0$ T) and non-metallic regime ($B = 9$ T). This is true for both (4) and (2) (only for the bulk systems), where a shallow metallic behaviour is observed at T below 10 K.

So far, we have created a system with sufficient local order. We prove the metallic behaviour in the bulk samples between 1.8 K and 10 K seen by $W(T)$ in figure 3B. In addition we demonstrate that a high magnetic fields can disrupt the local order of a metallic state, in particular at low temperatures.

When we take the view to the lower B -field, interestingly we find a concomitantly stimulating effect on the metallic character in our samples of merit (2 and 4). In contrast to figure 3 low B -fields enhance the conductivity. A detailed view to the magnetoconductivity $\frac{\Delta\sigma_B}{\sigma_0}$ as function of B shows this positive contribution (figure 4.)

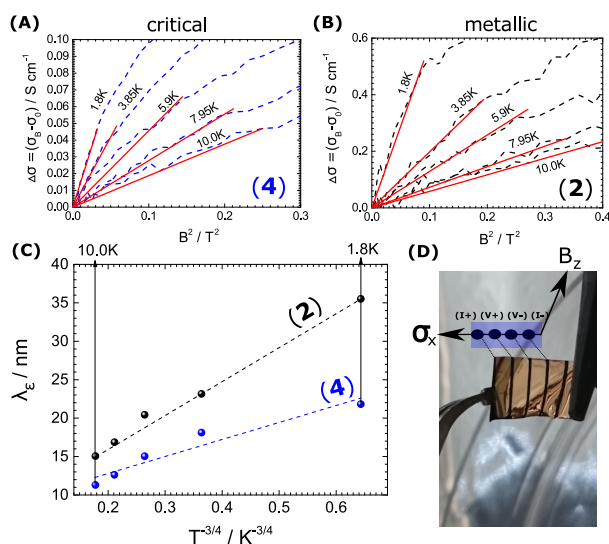


Fig. 5 (A) and (B) depict the linear dependence of the magnetoconductivity $\Delta\sigma_B$ and B^2 at low fields in the samples of merit (2),(4). The slope (linear fit) is proportional to the mean inelastic scattering length λ_ϵ . (C) shows the T -dependence of λ_ϵ . For inelastic scattering an exponent of $-\frac{3}{4}$ is typical. This is only the case in the metallic 5% DMSO sample (2). (D) depicts the sample (free-standing PEDOT:PSS film with 4 Au leads) ready for loading into the cryomagnet.

We observe the conductivity rising up to 4% of the original value. It is followed by a significant decrease to the negative as the field is increased. The negative effect is damped at high temperatures, where the turn to the negative is indicated at high B

and not seen at all at temperatures above 6 K. One explanation for magnetic stimulation relates to an electro-magnetic resonance, earlier found in systems defined by weak localization: In fact, the stimulation reflects an interaction among the electron wave functions, as soon as the inelastic mean free path of electrons λ_ϵ and the Landau orbit size L_D .²⁹⁻³¹ become comparable.

$$L_D \approx \lambda_\epsilon \quad \text{with} \quad L_D = \sqrt{\frac{\hbar}{e \cdot B}} \quad (1)$$

Equation 1 depicts the relation of L_D (or B) and of λ_ϵ (figure 4). At 1.8 K, for example, the $\Delta\sigma_B$ -value increases up to 1 T (2), before it collapses to the negative by increasing B (figure 4C and D). The peak maximum of $\Delta\sigma_B$ corresponds to the amplitude of the local order or λ_ϵ , respectively. It can be consequently read out by plotting L_D instead of B . A similar but right-shifted profile is observed at 3.85 K. At higher temperatures the stimulations does not collapse meaning that λ_ϵ exceeds the maximum field at $B_{\max} = 9$ T or $L_D = 8.1$ nm according to equation 1, as λ_ϵ decreases below the maximum magnetic field as we raise the temperature. Positive magnetoconductivity has been reported solely in combination with metallic samples - it reveals a coherence among electron wave functions and B .^{29,31-38} In our case this is supported by the morphology study (homogeneous domains of similar size, figure 3). Other theories assign the stimulating magneto-effect to the spin-orbit coupling. However, in organic matter these effects can be neglected.¹² We use the coherent electron interactions as direct consequence of long-range order inside the polymer. To quantitatively evaluate the magnetoconductivity, we derive concrete values for λ_ϵ as statistic parameter to visualize the local order. Kawabata has posted a relation between magnetoconductivity and the relaxation time (hence the mean free path λ_ϵ).²⁹ We can derive the magnitude by plotting $+\sigma_B$ versus B^2 according to

$$\Delta\sigma_{MC} = + (4\pi) \cdot \frac{e^2}{h^2} \cdot G_0 \cdot \lambda_\epsilon^3 \cdot (B)^2 \quad (2)$$

using the elemental charge e and the Plank constant h and the conductance quantum $G_0 = \frac{2e^2}{h}$. The corresponding figure 5 shows the temperature-variant slopes and the accompanying linear fits for each temperature. In the best case in (2) the electron coherence quantitatively translates to a scattering length of 35.5 nm at 1.8 K. This value exceeds the macromolecular dimensions and explains the metallic fingerprint of the system. We summarized all relevant parameters in table 1. With the $T^{-\frac{3}{4}} - \lambda_\epsilon$ plot in figure 5C we include the temperature-dependence with the exponent 0.75 typical for inelastic scattering.³⁰ The dimensions of λ_ϵ are exponentially decreasing by increasing temperature - as we go off the metallic regime, we observe a deviation as visible in the critically transition regime in (4).

4 Acknowledgements

This work has been supported by the OEAD (WTZ, IN10/2015) and the Austrian Fund for Advancement of Science (FWF) within the Wittgenstein Prize scheme (Z222-N19 Solare Energiewandlung).

5 Conclusions

We underline here the value of magnetoconductivity to display local order, which is crucial to establish a metallic state in a conductive polymer. The order can be surfaced by the coherent transport and represents a strong argument for achieving a metallic state. We show that it is possible to improve on the electrical performance, when the morphology becomes homogeneous and locally ordered. This is demonstrated by expanding the sample's dimension towards a bulk-phase and by allowing self-organization. Thus our strategy can be a model system for various CP-systems to strengthen their electrical transport properties towards an intrinsically-metallic, alternative conductor.

References

- 1 K. Lee, S. Cho, S. Heum Park, A. J. Heeger, C.-W. Lee and S.-H. Lee, *Nature*, 2006, **441**, 65–68.
- 2 Y. H. Kim, C. Sachse, M. L. Machala, C. May, L. Müller-Meskamp and K. Leo, *Advanced Functional Materials*, 2011, **21**, 1076–1081.
- 3 D. Alemu Mengistie, P.-C. Wang and C.-W. Chu, *Journal of Materials Chemistry A*, 2013, **1**, 9907.
- 4 O. Bubnova, Z. U. Khan, H. Wang, S. Braun, D. R. Evans, M. Fabretto, P. Hojati-Talemi, D. Dagnelund, J.-B. Arlin, Y. H. Geerts, S. Desbief, D. W. Breiby, J. W. Andreasen, R. Lazzaroni, W. M. Chen, I. Zozoulenko, M. Fahlman, P. J. Murphy, M. Berggren and X. Crispin, *Nature Materials*, 2013, **13**, 190–194.
- 5 D. A. Mengistie, P.-C. Wang and C.-W. Chu, *ECS Transactions*, 2013, **58**, 49–56.
- 6 N. Massonnet, A. Carella, A. de Geyer, J. Faure-Vincent and J.-P. Simonato, *Chem. Sci.*, 2015, **6**, 412–417.
- 7 E. Stavrinidou, R. Gabrielsson, E. Gomez, X. Crispin, O. Nilsson, D. T. Simon and M. Berggren, *Science Advances*, 2015, **1**, e1501136–e1501136.
- 8 K. Bourzac, *Nature*, 2015.
- 9 J. Huang, P. Miller, J. de Mello, A. de Mello and D. Bradley, *Synthetic Metals*, 2003, **139**, 569–572.
- 10 Y. Xia, K. Sun and J. Ouyang, *Advanced Materials*, 2012, **24**, 2436–2440.
- 11 B. J. Worfolk, S. C. Andrews, S. Park, J. Reinspach, N. Liu, M. F. Toney, S. C. B. Mannsfeld and Z. Bao, *Proceedings of the National Academy of Sciences*, 2015, **112**, 14138–14143.
- 12 G. Bergmann, *Physics Reports*, 1984, **107**, 1–58.
- 13 S. D. Baranovskii, *physica status solidi (b)*, 2014, **251**, 487–525.
- 14 H. C. F. Martens, J. A. Reedijk, H. B. Brom, D. M. de Leeuw and R. Menon, *Physical Review B*, 2001, **63**, 073203.
- 15 A. Aleshin, R. Kiebooms, R. Menon and A. Heeger, *Synthetic Metals*, 1997, **90**, 61–68.
- 16 R. Menon, C. O. Yoon, D. Moses, A. J. Heeger and Y. Cao, *Physical Review B*, 1993, **48**, 17685–17694.
- 17 P. W. Anderson, *Physical Review*, 1958, **109**, 1492–1505.
- 18 N. F. Mott, *Philosophical Magazine*, 1972, **26**, 1015–1026.
- 19 S. Jönsson, J. Birgeron, X. Crispin, G. Greczynski, W. Osikowicz, A. Denier van der Gon, W. Salaneck and M. Fahlman, *Synthetic Metals*, 2003, **139**, 1–10.
- 20 O. Bubnova, Z. U. Khan, A. Malti, S. Braun, M. Fahlman, M. Berggren and X. Crispin, *Nature Materials*, 2011, **10**, 429–433.
- 21 J. Gasiorowski, R. Menon, K. Hingerl, M. Dachev and N. S. Sariciftci, *Thin Solid Films*, 2013, **536**, 211–215.
- 22 X. Crispin, F. L. E. Jakobsson, A. Crispin, P. C. M. Grim, P. Andersson, A. Volodin, C. V. Haesendonck, M. V. D. Auwerker, W. R. Salaneck and M. Berggren, *Chemistry of Materials*, 2006, **18**, 4354–4360.
- 23 I. Cruz-Cruz, M. Reyes-Reyes, M. Aguilar-Frutis, A. Rodriguez and R. López-Sandoval, *Synthetic Metals*, 2010, **160**, 1501–1506.
- 24 C. Pathak, J. Singh and R. Singh, *Current Applied Physics*, 2015, **15**, 528–534.
- 25 T.-R. Chou, S.-H. Chen, Y.-T. Chiang, Y.-T. Lin and C.-Y. Chao, *J. Mater. Chem. C*, 2015, **3**, 3760–3766.
- 26 Q. Wei, M. Mukaida, Y. Naitoh and T. Ishida, *Advanced Materials*, 2013, **25**, 2831–2836.
- 27 C. M. Palumbiny, F. Liu, T. P. Russell, A. Hexemer, C. Wang and P. Müller-Buschbaum, *Advanced Materials*, 2015, **27**, 3391–3397.
- 28 E. B. Aleksandrov, I. V. Sokolov, A. Gatti, M. Kolobov, L. Lugiato and T. Vartanyan, *Uspekhi Fizicheskikh Nauk*, 2001, **171**, 1263.
- 29 A. Kawabata, *Solid State Communications*, 1980, **34**, 431–432.
- 30 P. A. Lee and T. V. Ramakrishnan, *Reviews of Modern Physics*, 1985, **57**, 287–337.
- 31 A. B. Kaiser, *Reports on Progress in Physics*, 2001, **64**, 1.
- 32 B. Chapman, R. G. Buckley, N. T. Kemp, A. B. Kaiser, D. Beaglehole and H. J. Trodahl, *Physical Review B*, 1999, **60**, 13479–13483.
- 33 F. Pikus and G. Pikus, *Solid State Communications*, 1996, **100**, 95–99.
- 34 T. F. Rosenbaum, R. F. Milligan, G. A. Thomas, P. A. Lee, T. V. Ramakrishnan, R. N. Bhatt, K. DeConde, H. Hess and T. Perry, *Physical Review Letters*, 1981, **47**, 1758–1761.
- 35 R. Menon, K. Väkiparta, Y. Cao and D. Moses, *Physical Review B*, 1994, **49**, 16162–16170.
- 36 Y. Nogami, H. Kaneko, H. Ito, T. Ishiguro, T. Sasaki, N. Toyota, A. Takahashi and J. Tsukamoto, *Physical Review B*, 1991, **43**, 11829–11839.
- 37 H. H. S. Javadi, A. Chakraborty, C. Li, N. Theophilou, D. B. Swanson, A. G. MacDiarmid and A. J. Epstein, *Physical Review B*, 1991, **43**, 2183–2186.
- 38 G. Bergmann, *Physical Review B*, 1983, **28**, 2914–2920.

Table 1 Electrical parameters of the metallic and critically-metallic phase in PEDOT:PSS

label	thickness / nm	% DMSO	$\sigma_{300\text{K}} / \text{S cm}^{-1}$	$\sigma_{1.8\text{K}} / \text{S cm}^{-1}$	ratio $\sigma_{300\text{K}} / \sigma_{1.8\text{K}}$	λ_e / nm (at 1.8 K)
(ref)	8400	0	7.1	N/A	N/A	N/A
(1)	55	5 %	1000	101.5	9.83	N/A
(2)	8300	5 %	490	170	2.54	35.5
(3)	9200	10 %	275	80	3.42	N/A
(4)	8300	2 %	155	50	2.96	21.8

