



CrystEngComm

**Trends in Rare Earth Thiophosphate Syntheses:
 $Rb_3Ln(PS_4)_2$ ($Ln = La, Pr, Ce$), $Rb_{3-x}Na_xLn(PS_4)_2$ ($Ln = Pr, Ce$; $x = 0.50, 0.55$), and $RbEuPS_4$ Obtained by Molten Flux
 Crystal Growth**

Journal:	<i>CrystEngComm</i>
Manuscript ID	CE-ART-05-2021-000703.R1
Article Type:	Paper
Date Submitted by the Author:	30-Jun-2021
Complete List of Authors:	Breton, Logan; University of South Carolina, Chemistry; University of South Carolina Smith, Mark; University of South Carolina, Department of Chemistry and Biochemistry Zur Loye, Hans-Conrad; University of South Carolina, Department of Chemistry and Biochemistry

SCHOLARONE™
 Manuscripts

Trends in Rare Earth Thiophosphate Syntheses: $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ (Ln = La, Pr, Ce), $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ (Ln = Pr, Ce; x = 0.50, 0.55), and RbEuPS_4
Obtained by Molten Flux Crystal Growth

Logan S. Breton, Mark D. Smith, Hans-Conrad zur Loye*

Department of Chemistry and Biochemistry, University of South Carolina, Columbia, South Carolina 29208, United States

*zurLoye@mailbox.sc.edu

Abstract:

Single crystals of new rubidium rare earth thiophosphates with the formulas $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ (Ln = La, Pr, Ce), $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ (Ln = Pr, Ce; x = 0.50, 0.55), and RbEuPS_4 were crystallized out of a molten RbCl flux. The compounds $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ (Ln = La, Pr, Ce) and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ (Ln = Pr, Ce; x = 0.50, 0.55) both crystallize in the monoclinic crystal system adopting the space groups $P2_1$ and $P2_1/c$, respectively, while RbEuPS_4 crystallizes in the orthorhombic crystal system adopting the space group $Pnma$. A survey of all known rubidium rare earth thiophosphates grown using an alkali halide flux revealed trends suggesting that the $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ families of compounds can be actively targeted over a wide range of temperatures by employing RbCl as at least a component of the flux. Fluorescence measurements were performed on all compounds obtained, revealing resolved f-f transitions in $\text{Rb}_3\text{Pr}(\text{PS}_4)_2$ and $\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$ and only single broad emission peaks for $\text{Rb}_3\text{Ce}(\text{PS}_4)_2$ and $\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$, behavior characteristic for cerium(III) compounds.

INTRODUCTION

Molten flux crystal growth is a popular synthetic method that has become a pillar of modern solid state chemistry due to its continued success in the production of X-ray diffraction quality single crystals of a wide variety of structural families, including metal oxides¹⁻³, halides^{4, 5}, and chalcogenides.⁶⁻¹¹ The use of alkali halide fluxes in particular has resulted in many new single crystalline compounds, while also having the added benefit of the desired crystalline products being easily removed from the product mixture using common solvents, such as water or methanol.

Molten flux synthesis has been shown to be an effective approach for the synthesis of thiophosphate compounds and, over the past decades, has resulted in the successful crystal growth of various thiophosphate compositions incorporating many elements, including transition metals¹²⁻¹⁴, rare earth metals¹⁵⁻¹⁸, and the actinides.^{11, 19} The thiophosphates have garnered attention in recent years for their high ionic conductivities^{20, 21} and for their non-linear optical properties.^{22, 23} In addition, numerous studies have focused simply on investigating the rich structural chemistry of thiophosphates, which were found to exhibit great diversity and modularity in composition and structure due to the many thiophosphate motifs that exists and that have been incorporated into new crystal structures, such as the thiopyrophosphate building block $P(V)_2S_7^{4-}$,^{24, 25} the ortho-thiophosphate building block $P(V)S_4^{3-}$,²⁶⁻³² the hexathiometadiphosphate building block $P(V)_2S_6^{4-}$,^{18, 33} and the hexathiohypophosphate building block $P(IV)_2S_6^{2-}$.^{18, 33-37}

Alkali halide fluxes have been demonstrated to be very effective for crystallizing new thiophosphate compounds, such as those prepared in alkali iodide melts by Klepov et al.³⁴, who reported on numerous rare earth containing thiophosphates, such as the two-dimensional $NaLnP_2S_6$ ($Ln = La, Ce, Pr$) thiohypophosphates and $CsLnP_2S_7$ ($Ln = Pr, Nd, Sm, Gd, Tb, Dy, Ho, Er, Yb, Y$) thiopyrophosphates³⁴, as well as the family of one-dimensional thiophosphates, $Cs_2NaLn(PS_4)_2$ ($Ln = La-Nd, Sm, Gd-Ho$).³⁸ Alkali bromide and chloride fluxes also function well for the synthesis of novel thiophosphates, such as the $ALnP_2S_6$ series³⁷ grown out of RbBr and CsBr fluxes, and $K_4Nd_2(PS_4)_2(P_2S_6)$ grown out of a KCl flux.³⁵ Due to the relative sparseness of rubidium containing rare earth thiophosphates, by comparison with those incorporating the other alkali metals, syntheses to create the rubidium analogues of the $Cs_2NaLn(PS_4)_2$ series created by Klepov et al. were carried out by Kutahyali Aslani et al., by employing the same reagents and ratios but replacing the cesium iodide used by Klepov et al. with rubidium bromide. The change

in flux resulted, however, in a new family of thiophosphates with formulas $\text{Rb}_4\text{Ln}_2(\text{P}_2\text{S}_6)(\text{PS}_4)_2$ ($\text{Ln}=\text{La}, \text{Ce}, \text{Pr}, \text{Nd}, \text{Sm}, \text{Gd}$).¹⁷

An overarching goal of solid state chemistry is to achieve the ability to predict structures and to ultimately engineer structures with desired properties. Given the great diversity of thiophosphate structures created in different flux environments, we decided to pursue the synthesis of new thiophosphates by exploring the role of the flux on the formation of thiophosphate products in the hope to better understand the role of the flux as well as to perhaps be able to predict product formation.⁶ To probe the effects of the flux on the resulting product formed, experiments were carried out using the same reagents and molar ratios used by Kutahyali Aslani et al., however, this time employing a RbCl flux in place of the previously used RbBr. Herein we report on the synthesis, crystal structures, and select optical measurements of the new rubidium rare earth thiophosphates $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{La}, \text{Pr}, \text{Ce}$), $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{Pr}, \text{Ce}; x = 0.50, 0.55$), and RbEuPS_4 obtained by employing the RbCl flux. In addition, we discuss our current thoughts concerning the role of the flux in the creation of rubidium rare earth thiophosphates.

EXPERIMENTAL

Reagents

P_2S_5 (99%, Sigma-Aldrich), Na_2S (Alfa Aesar), N,N-dimethylformamide (DMF, Sigma-Aldrich, ACS grade), methanol (MeOH, VWR, ACS grade), and La_2S_3 (STREM Chemicals inc., 99.9%) were all used as received. P_2S_5 and Na_2S were stored and handled in a nitrogen glove bag. Ce_2S_3 , Pr_2S_3 , and EuS were obtained according to the procedure described in the literature.³⁹

Synthesis

The compounds $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{La}, \text{Pr}, \text{Ce}$) and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{Pr}, \text{Ce}; x = 0.50, 0.55$) were all obtained using the same synthetic conditions. In a nitrogen filled glove bag, powders of Ln_2S_3 ($\text{Ln} = \text{La}, \text{Ce}, \text{Pr}$) (0.265 mmol), Na_2S (1.063 mmol), and P_2S_5 (1.062 mmol) were loaded into a fused silica tube in a 1:4:4 molar ratio along with 1 gram of RbCl flux. The fused silica tube was flame sealed under vacuum and placed in a box furnace set to ramp up to 820 °C in 1 hour where it dwelled for 20 hours and was subsequently slow cooled to 620 °C in 30 hours. The furnace was then shut off to allow the reaction mixture to cool to room temperature. The compound RbEuPS_4 was synthesized using an EuS , Na_2S , P_2S_5 molar ratio of 1:2:2 which was

loaded into a fused silica tube that was evacuated, flame sealed, and placed in a box furnace set to the same temperature profile detailed above. To remove the flux and to isolate the single crystals, all products were sonicated in DMF and then subsequently sonicated in MeOH. The crystalline products were filtered and dried in air. The products are moisture sensitive and were therefore stored in a desiccator. Translucent plate crystals of the $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ compounds were obtained via the same product mixtures for each lanthanide sulfide reagent used. RbEuPS_4 was obtained as large yellow/brown plates and was a phase pure product.

Single Crystal x-ray Diffraction

X-ray intensity data from small irregular crystals were collected at 301(2) K for the compounds $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ (Ln = Pr, Ce), $\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$, and RbEuPS_4 , at 291(2) K for $\text{Rb}_3\text{La}(\text{PS}_4)_2$, and at 100(2) K for $\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$ using a Bruker D8 QUEST diffractometer equipped with a PHOTON-II area detector and an Incoatec microfocus source (Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å). The raw area detector data frames were reduced and corrected for absorption effects using the SAINT+ and SADABS programs.^{40,41} Final unit cell parameters were determined by least-squares refinement of large sets of reflections taken from each data set. An initial structural model was obtained with SHELXT.⁴² Subsequent difference Fourier calculations and full-matrix least-squares refinement against F^2 were performed with SHELXL-2018⁴³ using the Olex2 interface.⁴⁴ Detailed explanations on the X-ray structure determination of all compounds reported herein can be found in the Supporting Information. The crystallographic data and results of the diffraction experiments are summarized in Table 1.

Table 1. The crystallographic information for all compounds reported herein.

Chemical formula	Rb ₃ La(PS ₄) ₂	Rb ₃ Pr(PS ₄) ₂	Rb ₃ Ce(PS ₄) ₂	Rb _{2.45(2)} Na _{0.55(2)} Pr(PS ₄) ₂	Rb _{2.50(6)} Na _{0.50(6)} Ce(PS ₄) ₂	RbEuPS ₄
Formula weight	713.74	715.74	714.95	681.32	683.76	396.64
Crystal system	Monoclinic					Orthorhombic
Space group, Z	<i>P</i> 2 ₁	<i>P</i> 2 ₁	<i>P</i> 2 ₁	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> 2 ₁ / <i>c</i>	<i>Pnma</i>
a, Å	9.9053(9)	9.8265(3)	9.8512(6)	9.0570(3)	9.1218(4)	17.3308(4)
b, Å	6.7376(6)	6.7613(2)	6.7530(4)	17.3059(6)	17.4862(8)	6.6787(2)
c, Å	11.4553(10)	11.4228(4)	11.4321(7)	9.4252(3)	9.4704(4)	6.43470(10)
β, deg.	90.005(3)	90.2997(12)	90.241(2)	91.8396(13)	91.7907(17)	90
V, Å ³	764.50(12)	758.92(4)	760.52(8)	1476.54(8)	1509.84(11)	744.80(3)
ρ _{calcd.} , g/cm ³	3.101	3.132	3.122	3.065	3.008	3.537
Radiation (λ, Å)	Mo Kα (0.71073 Å)					
μ, mm ⁻¹	13.545	14.040	13.800	12.644	12.317	16.132
T, K	291(2)	301(2)	301(2)	100(2)	301(2)	301(2)
Crystal dim., mm ³	0.040x0.030x0.020	0.040x0.030x0.020	0.080x0.040x0.020	0.040x0.020x0.020	0.070x0.020x0.010	0.050x0.050x0.010
2θ range, deg.	2.718-30.028	2.073-29.142	2.067-32.597	2.250-30.001	2.234-28.310	3.377- 29.992
Reflections collected	35700	27258	51419	47150	35860	12334
Data/parameters /restraints	4460/132/2	4082/134/1	5434/134/1	4311/143/0	3763/143/0	1170/43/0
<i>R</i> _{int}	0.0387	0.0412	0.0368	0.0462	0.0720	0.0306
Goodness of fit	1.099	1.181	1.157	1.093	1.129	1.171
R ₁ (I > 2σ(I))	0.0493	0.0329	0.0262	0.0297	0.0563	0.0247
wR ₂ (all data)	0.0983	0.0541	0.0515	0.0503	0.1267	0.0647

Powder X-ray Diffraction

Powder X-ray diffraction (PXRD) data for phase purity confirmation was collected using a polycrystalline sample of RbEuPS_4 obtained by grinding single crystals (Figure S1). Data was collected on a Bruker D2 PHASER diffractometer using $\text{Cu K}\alpha$ radiation over a 2θ range $10\text{--}65^\circ$ with a step size of 0.02° .

Energy-Dispersive Spectroscopy (EDS)

EDS was performed on single crystal products using a Tescan Vega-3 SEM equipped with a Thermo EDS attachment. The SEM was operated in low-vacuum mode. Crystals were mounted on an SEM stub with carbon tape and analyzed using a 20 kV accelerating voltage and an 80 s accumulation time. SEM images of the crystals can be found in Figure (S2). The obtained EDS spectra for each crystal can be found in Figures S3-S8. The results of EDS confirm the presence of elements found by single-crystal X-ray diffraction and are summarized in Table S1.

Optical Properties

Photoluminescence data were collected on HORIBA Scientific Standard Microscope Spectroscopy Systems connected with iHR320 Spectrometer and Synchrony detector operating on Labspec 6 software. Spectra were recorded from 400 to 800 nm using 375nm Laser excitation source power 0.5mW with 10xUV objective.

RESULTS AND DISCUSSION

Synthesis

To better understand the role of the flux employed in the molten flux crystal growth of rubidium rare earth thiophosphates, the same starting materials and ratios used by Kutahyali Aslani et al. to synthesize the $\text{Rb}_4\text{Ln}_2(\text{P}_2\text{S}_6)(\text{PS}_4)_2$ series¹⁷ were employed with the only change being the use of a RbCl flux instead of the RbBr flux. This approach resulted in a new series of thiophosphates, specifically, single crystals of the rubidium rare earth thiophosphates $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{La}, \text{Ce}, \text{Pr}$) and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ ($\text{Ln} = \text{Ce}, \text{Pr}; x = 0.50, 0.55$), which were found in the same product mixture. It is important to note that the compound $\text{Rb}_{2.61(1)}\text{Na}_{0.39(1)}\text{La}(\text{PS}_4)_2$ was also obtained in the same product mixture as $\text{Rb}_3\text{La}(\text{PS}_4)_2$, however, a similar compound has already been reported in the literature.¹⁵

As mentioned earlier, one goal of solid state chemistry is to achieve predictive abilities as it pertains to the targeted synthesis of compounds with desired properties. While this goal is far from being accomplished, it is important to document observed patterns and create conversations that may help push this goal further to completion. Our group has had significant success in the growth of alkali rare earth thiophosphates using various alkali halide fluxes and, given the large number of compositions synthesized, this now allows us to look for patterns within this data. Kutahyali Aslani et al. attempted to make the rubidium analogues of the $\text{Cs}_2\text{NaLn}(\text{PS}_4)_2$ series created by Klepov et al.³⁸ utilizing the same starting materials and molar ratios however changing the flux from the CsI used by Klepov et al. to a RbBr flux. With just the change in flux, a new series of compounds, $\text{Rb}_4\text{Ln}_2(\text{P}_2\text{S}_6)(\text{PS}_4)_2$ (Ln = La, Ce, Pr, Nd, Sm, and Gd), was obtained. This success of crystallizing brand new rubidium rare earth thiophosphates with just a change in flux motivated the work reported herein. Using the same starting materials and reagent ratios employed by Kutahyali Aslani et al., however, changing from a RbBr to a RbCl flux, the new compounds $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ (Ln = La, Ce, Pr) and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ (Ln = Ce, Pr; x = 0.50, 0.55) were obtained. Table 2 lists the known rubidium rare earth thiophosphates grown using alkali halide fluxes.

Table 2. A table listing the starting materials used, reagent ratios, flux identities, and reaction temperatures for all known rubidium rare earth thiophosphates grown using alkali halide fluxes.

Compound	Starting Material	Reagent Ratios	Flux Identity	Reaction Temperature	Reference
$\text{Rb}_{2.65}\text{Na}_{0.35}\text{La}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:2:3	RbCl-NaCl	650 for 48 hr	15
$\text{Rb}_{2.42}\text{Na}_{0.58}\text{Nd}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:2:3	RbCl-NaCl	650 for 48 hr	15
$\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:4:4	RbCl	820 for 20 hr	This work
$\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:4:4	RbCl	820 for 20 hr	This work
$\text{Rb}_3\text{Gd}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:2:3	RbCl-NaCl	650 for 48 hr	15
$\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ Ln = La, Ce, Pr	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:4:4	RbCl	820 for 20 hr	This work
$\text{Rb}_2\text{NaNd}(\text{PS}_4)_2$	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:2:3	RbI-NaI	650 for 20 hr	15
$\text{Rb}_4\text{Ln}_2(\text{P}_2\text{S}_6)(\text{PS}_4)_2$ Ln = La, Ce, Pr, Nd, Sm, Gd	$\text{Ln}_2\text{S}_3:\text{Na}_2\text{S}:\text{P}_2\text{S}_5$	1:4:4	RbBr	800 for 12 hr	17
$\text{Rb}_3\text{Pr}_3(\text{PS}_4)_4$	Pr:P:S:RbBr	10:12:42:12	RbBr	950 for 14 days	16
$\text{Rb}_3\text{Er}_3(\text{PS}_4)_4$	Er:P:S:RbBr	4:4:16:3	RbBr	950 for 14 days	16
RbLaP_2S_6	Ln:RbBr:S:P	4:6:18:6	RbBr	800 for 24 hr	37

The data in the table demonstrates that the use of different fluxes led to the crystallization of different thiophosphate compositions. To discuss the role of the flux requires, however, that we address two interconnected variables: the identity of the flux and the reaction temperature used. It is known that different products can crystallize at different temperatures depending on the kinetic and thermodynamic processes at play.⁶ The change in flux from the RbBr used by Kutahyali Aslani et al. to the RbCl used herein also necessitated a change in the reaction temperature used. It is common when using molten fluxes as crystallization media that the reaction temperature is set to 100 °C above the melting point of the flux to ensure the full liquification of the flux and maximizing the likelihood of dissolving all reagents within the flux to achieve the supersaturation necessary for crystal growth upon cooling.¹ The melting point of RbBr is ~700 °C which is the reason that Kutahyali Aslani et al. synthesized their crystals at a reaction temperature of 800 °C. The crystals reported herein, using the RbCl flux with a melting point of ~720 °C, dictated that a reaction temperature of 820 °C be used. The 20 °C difference in reaction temperature, while small, nonetheless introduces temperature as a variable. It is likely that in the case of the $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ families prepared in an RbCl flux, temperature plays only a minor role in determining product formation. This is because other members of the $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ families, Table 2, were synthesized in a RbCl-NaCl eutectic flux (melting point: 486 °C) at a reaction temperature of 600 °C.¹⁵ The fact that $\text{Rb}_3\text{Ln}(\text{PS}_4)_2$ and $\text{Rb}_{3-x}\text{Na}_x\text{Ln}(\text{PS}_4)_2$ crystallizes over a wide temperature range suggests that the identity of the flux predominantly impacts the identity of the product formed. Though the use of a RbBr flux at various temperatures resulted in different products formed, it is interesting that the use of a RbCl flux resulted in the same families of compounds. The observation suggests that these families of compounds can be readily targeted using specifically the RbCl flux as at least one component of the flux. Furthermore, it suggests that it is always worthwhile to explore different alkali halide fluxes after a new composition has been found, as the switch in fluxes may easily lead to additional series of compounds.

The single crystal growth of RbEuPS_4 was performed using a 1:2:2 ratio of EuS, P_2S_5 , and Na_2S in order to keep the ratio of lanthanide to phosphorus pentasulfide and sodium sulfide the same as in the other syntheses reported herein. The resulting product, which utilized 1 gram of RbCl flux, was phase pure yellow/brown plates of RbEuPS_4 . It is important to note that in this structure the lanthanide, europium, is in its 2+ oxidation state where all other compounds reported

herein have the lanthanides in their 3+ oxidation state. This is most likely the reason that a different compound, structure, and composition, was obtained for europium, as its ability of taking on the 2+ oxidation state is unique among the rare earths described herein.

Structure Description:

Rb₃Pr(PS₄)₂, and **Rb₃Ce(PS₄)₂** belong to the Rb₃Ln(PS₄)₂ family of thiophosphates and crystallize in a one-dimensional structure type in the monoclinic space group *P2*₁, Figure 1a-e. The structures consist of two unique PS₄³⁻ tetrahedra and one 8-coordinate LnS₈ highly distorted square antiprism. The LnS₈ polyhedra corner-share with each other creating corrugated infinite chains. Within the chains, the P(1)S₄³⁻ tetrahedra share two edges with adjacent LnS₈ polyhedra and corner share with a third. The P(2)S₄³⁻ thiophosphate tetrahedra then decorate the sides of the LnS₈ polyhedra via face-sharing and point into the channels between the infinite chains. These channels are populated with ordered rubidium cations which hold the infinite chains together resulting in the full structure. In these compounds the Ln—S interatomic distances range from 2.8916(19)—3.253(16) Å, the P—S interatomic distances range from 2.0004(18)—2.089(14) Å, and the Rb—S interatomic distances range from 3.290(17)—3.9974(16) Å.

Rb₃La(PS₄)₂ is isostructural with the other Rb₃Ln(PS₄)₂ compounds reported herein however exhibits rubidium/lanthanum site mixing within the structure, Figure 1f. Of the 4 unique rubidium sites, the Rb1 and Rb2 sites are mixed with lanthanum with La1/Rb1 and La2/Rb2 occupancies of 0.548(4)/0.452(4) and 0.452(4)/0.548(2), respectively, while the Rb3 and Rb4 sites are fully occupied by rubidium. Due to the approximate 50/50 rubidium and lanthanum site mixing, the resulting overall chemical formula is nonetheless the same as those of Rb₃Pr(PS₄)₂ and Rb₃Ce(PS₄). In this compound the Ln—S interatomic distances, impacted by the site mixing, range from 2.976(8)—3.384(6) Å, the P—S interatomic distances range from 1.984(12)—2.108(11) Å, and the Rb—S interatomic distances range from 3.327(8)—3.949(8) Å.

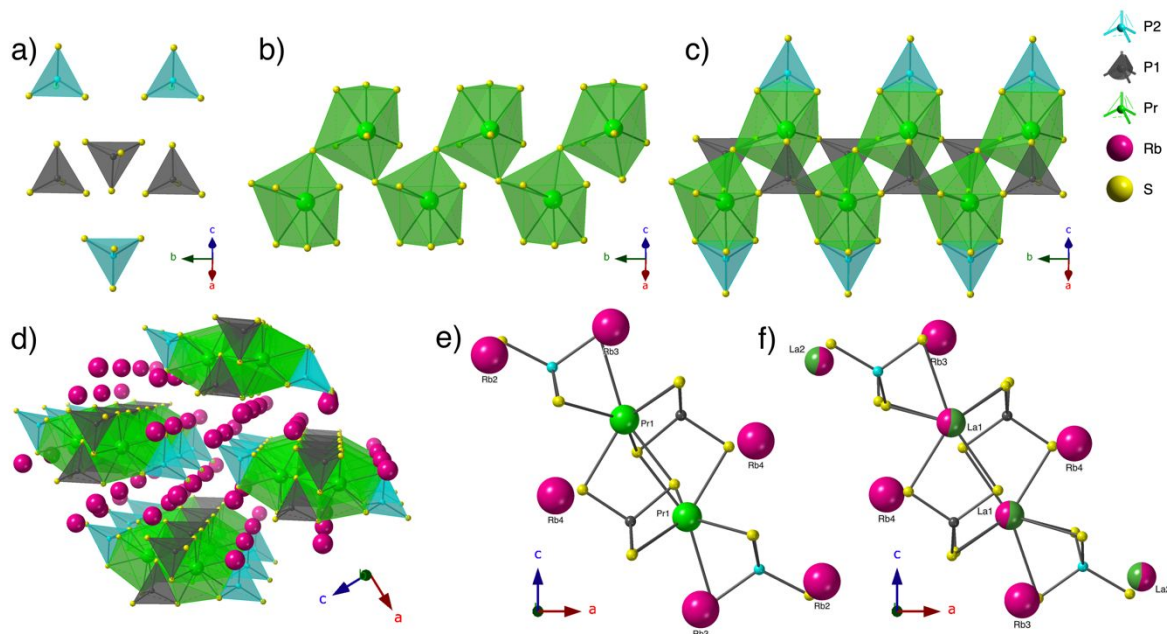


Figure 1. A schematic of the $Rb_3Ln(PS_4)_2$ ($Ln = La, Ce, Pr$) structure showing (a) the two PS_4^{3-} units, (b) the connectivity of the LnS_8 polyhedra, (c) the infinite chains of LnS_8 and PS_4^{3-} polyhedra, and (d) the full crystal structure. Figure 1e and 1f show a ball and stick representation of the infinite chains of the (e) $Rb_3Pr(PS_4)_2$ and (f) $Rb_3La(PS_4)_2$ structures to visualize where the lanthanum/rubidium site mixing (split pink/green spheres) occurs in $Ln = La$ analogue.

$Rb_{2.45(2)}Na_{0.55(2)}Pr(PS_4)_2$ and $Rb_{2.50(6)}Na_{0.50(6)}Ce(PS_4)_2$ belong to the $Rb_{3-x}Na_xLn(PS_4)_2$ family of thiophosphates and crystallize in the monoclinic space group $P2_1/c$, Figure 2. The one-dimensional crystal structure consists of one 9-coordinate LnS_9 polyhedral unit and two unique PS_4^{3-} tetrahedra. The LnS_9 polyhedra alternate between edge- and face-sharing with one another creating infinite LnS_9 chains. Between two face-sharing LnS_9 polyhedra, the $P(1)S_4^{3-}$ tetrahedra face-share with one LnS_9 polyhedra and edge-share with the other. Between two edge-sharing LnS_9 polyhedra, the $P(2)S_4^{3-}$ tetrahedra share one edge with each LnS_9 polyhedra, see Figure 2d. The resulting $[Ln(PS_4)_2]^{3-}$ infinite chains are held together by 3 unique disordered cationic sites. Sites Rb1 (split into Rb1a and Rb1b) and Rb3 (split into Rb3a and Rb3b) contain solely rubidium cations while site Rb2 is a disordered mixed site of both rubidium and sodium cations. In these compounds, the Ln—S interatomic distances range from 2.8731(10)—3.3038(14) Å, the P—S interatomic distances range from 1.996(4)—2.073(3) Å, and the Rb—S interatomic distances, impacted by the site mixing, range from 3.0046(16)—3.958(13) Å.

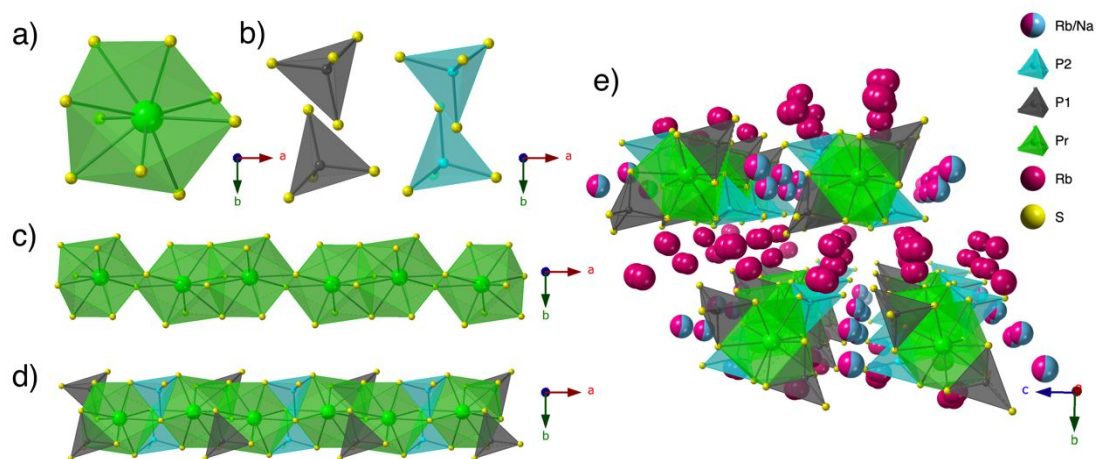


Figure 2. A schematic of the $Rb_{3-x}Na_xLn(PS_4)_2$ ($Ln = Pr, Ce; x = 0.50, 0.55$) structure showing (a) the LnS_9 polyhedral unit, (b) the two PS_4^{3-} units, (c) the connectivity of the rare earth polyhedra, (d) the $[Ln(PS_4)_2]^{3-}$ infinite chains, and (e) the full crystal structure.

RbEuPS₄ is the rubidium analogue of $KEuPS_4$ ³⁶ and crystallizes in the orthorhombic space group *Pnma*, Figure 3. The crystal structure consists of one PS_4^{3-} tetrahedral unit and one 8 coordinate EuS_8 bicapped trigonal prism. The EuS_8 polyhedra edge-share with each other creating a layer of europium polyhedra parallel to the b-c plane. The edge-sharing of the polyhedra leave trigonal prismatic holes in the layers that are filled by the thiophosphate tetrahedra. The successive layers are connected through rubidium cations which are disordered on their respective sites. In this compound the Eu—S interatomic distances range from 2.9679(16)—3.4516(4) Å, the P—S interatomic distances range from 2.021(2)—2.046(2) Å, and the Rb—S interatomic distances range from 3.327(8)—3.809(9) Å.

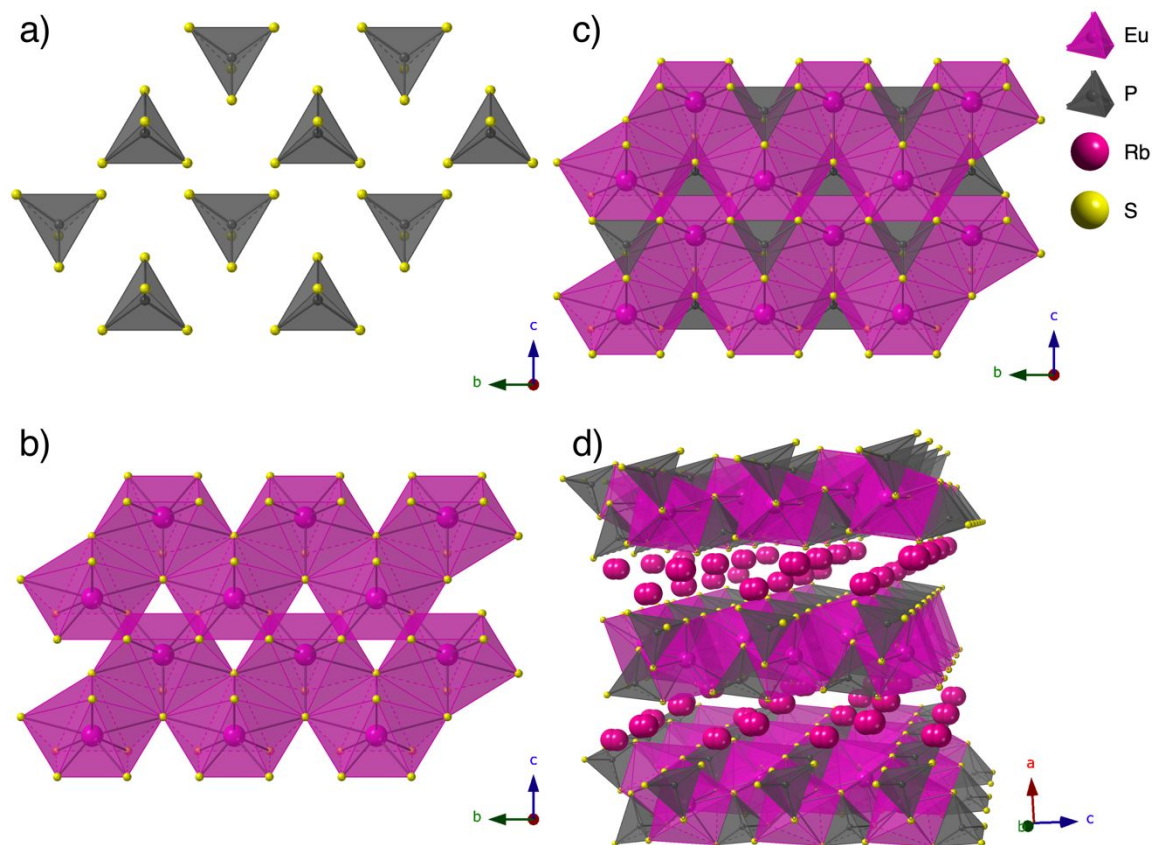


Figure 3. A schematic of the RbEuPS_4 structure showing (a) the PS_4^{3-} unit, (b) the connectivity of the EuS_8 polyhedra, (c) the layers of EuS_8 and PS_4^{3-} polyhedra, and (d) the full crystal structure.

Optical Properties

Fluorescence spectra were obtained at an excitation wavelength of 375 nm on single crystals of $\text{Rb}_3\text{La}(\text{PS}_4)_2$, $\text{Rb}_3\text{Pr}(\text{PS}_4)_2$, $\text{Rb}_3\text{Ce}(\text{PS}_4)_2$, $\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$, $\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$ and RbEuPS_4 . As expected, there was no fluorescence observed for $\text{Rb}_3\text{La}(\text{PS}_4)_2$, as lanthanum compounds have a $4f^0$ electron configuration.⁴⁵ In the case of RbEuPS_4 , where europium is $4f^7$, one might expect fluorescence; however, no fluorescence was observed from the single crystals of RbEuPS_4 . The fluorescence spectra for $\text{Rb}_3\text{Pr}(\text{PS}_4)_2$, $\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$, $\text{Rb}_3\text{Ce}(\text{PS}_4)_2$, and $\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$ are shown in Figure (4). In the $\text{Rb}_3\text{Pr}(\text{PS}_4)_2$ and $\text{Rb}_{2.45(2)}\text{Na}_{0.55(2)}\text{Pr}(\text{PS}_4)_2$ spectra, the expected $^3\text{P}_0 \rightarrow ^3\text{H}_4$, $^3\text{P}_0 \rightarrow ^3\text{H}_5$, $^1\text{D}_2 \rightarrow ^3\text{H}_4$, and $^3\text{P}_0 \rightarrow ^3\text{H}_6$ f-f transitions were observed.⁴⁶ The fluorescence spectra for the $\text{Rb}_3\text{Ce}(\text{PS}_4)_2$ and $\text{Rb}_{2.50(6)}\text{Na}_{0.50(6)}\text{Ce}(\text{PS}_4)_2$, exhibit a single broad

peak covering much of the visible range measured, a phenomenon reported for other cerium compounds in the literature.^{47–49}

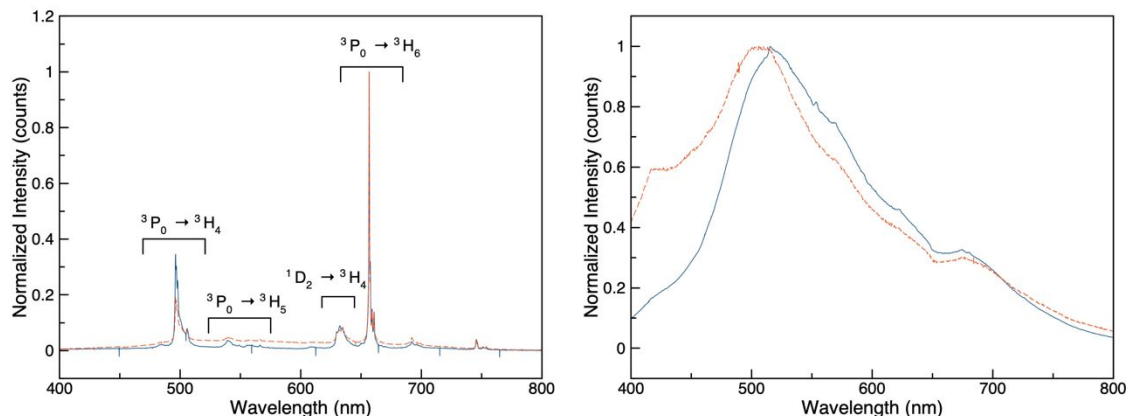


Figure 4. The emission spectrum of $Rb_3Pr(PS_4)_2$ (blue solid line) and $Rb_{2.45(2)}Na_{0.55(2)}Pr(PS_4)_2$ (orange dashed line) on the left, and that of $Rb_3Ce(PS_4)$ (blue solid line) and $Rb_{2.50(6)}Na_{0.50(6)}Ce(PS_4)_2$ (orange dashed line) on the right, taken at an excitation wavelength of 375 nm.

CONCLUSION

Single crystals of new rubidium rare earth thiophosphates with the formulas $Rb_3Ln(PS_4)_2$ ($Ln = La, Pr, Ce$), $Rb_{3-x}Na_xLn(PS_4)_2$ ($Ln = Pr, Ce$; $x = 0.50, 0.55$), and $RbEuPS_4$ were crystallized out of a molten $RbCl$ flux. The role of the flux in the creation of rubidium rare earth thiophosphates was discussed and contrasted with other thiophosphate families crystallized out of similar halide fluxes. Fluorescence measurements were performed on all compounds obtained, revealing resolved f-f transitions in $Rb_3Pr(PS_4)_2$ and $Rb_{2.45(2)}Na_{0.55(2)}Pr(PS_4)_2$ and only single broad emission peaks for $Rb_3Ce(PS_4)$ and $Rb_{2.50(6)}Na_{0.50(6)}Ce(PS_4)_2$, behavior characteristic for cerium(III) compounds.

Supporting information

CCDC 2084750—2084755 contain the supplementary crystallographic information about the compounds reported herein. The data can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/structures. The Supporting Information contains SEM images, EDS spectra and obtained elemental compositions, as well as a PXRD of

the phase pure RbEuPS₄ product, and detailed explanations of the X-ray structure solutions for all compounds reported herein.

Author Contributions

Breton – conceptualization, investigation, sample synthesis, structure determination, writing

Smith – structure determination, writing, reviewing

zur Loye – conceptualization, methodology, writing, reviewing

Conflicts of Interest

The authors declare no conflicts of interest.

Acknowledgment

Research supported by the US Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering under award DE-SC0018739.

REFERENCES

- (1) D. E. Bugaris, and H.-C. zur Loye, *Angew. Chem. Int. Ed. Engl.*, 2012, **51**, 3780-3811
- (2) J. Boltersdorf, N. King, and P. A. Maggard, *CrystEngComm*, 2015, **17**, 2225-2241
- (3) C. Juillerat, V. V. Klepov, G. Morrison, K. A. Pace, and H.-C. zur Loye, *Dalton Trans.*, 2019, **48**, 3162-3181
- (4) K. Habermehl, A.-V. Mudring, and G. Meyer, *Eur. J. Inorg. Chem.*, 2010, **26**, 4075-4078
- (5) V. V. Klepov, C. Juillerat, K. Pace, G. Morrison, and H.-C. zur Loye, *Front. Chem.*, 2020, **8**, #518
- (6) M. G. Kanatzidis, *Inorg. Chem.*, 2017, **56**, 3158-3173
- (7) Y. Wang, J. Wu, Y. Tang, X. Lu, C. Yang, M. Qin, F. Huang, X. Li, and X. Zhang, *ACS Appl. Mater. Interfaces*, 2012, **4**, 4246-4250
- (8) F. Lissner, S. P. Meyer, and T. Schleid, *Z. Naturforsch. B*, 2019, **74**, 99-107
- (9) I. Ijjaali, K. Mitchell, and J. A. Ibers, *J. Solid State Chem.*, 2004, **177**, 760-764
- (10) Y. Yang, and J. A. Ibers, *J. Solid State Chem.*, 2000, **149**, 384-390
- (11) L. S. Breton, V. V. Klepov, and H.-C. zur Loye, *J. Am. Chem. Soc.*, 2020, **142**, 14365-14373
- (12) J. Do, K. Lee, and H. Yun, *J. Solid State Chem.*, 1996, **125**, 30-36
- (13) J.-E. Kwak, and J.-S. Yun, *Bull. Korean Chem. Soc.*, 2008, **29**, 273-275
- (14) Y. Dong, S. Kim, and H. Yun, *Acta Cryst. C*, 2005, **61**, i25-i26
- (15) M. Usman, M. D. Smith, V. Klepov, and H.-C. zur Loye, *Cryst. Growth Des.*, 2019, **19**, 5648-5657
- (16) T. Komm, and T. Schleid, *J. Solid State Chem.*, 2005, **178**, 454-463
- (17) C. Kutahyali Aslani, L. S. Breton, V. Klepov, and H.-C. zur Loye, *Dalton Trans.*, 2021, **50**, 1683-1689
- (18) L. M. Schoop, R. Eger, J. Nuss, F. Pielhofer, and B. V. Lotsch, *Z. Anorg. Allg. Chem.*, 2017, **643**, 1818-1823
- (19) V. V. Klepov, and H.-C. zur Loye, *Inorg. Chem.*, 2018, **57**, 11175-11183

- (20) M. Tachez, J.-P. Malugani, R. Mercier, and G. Robert, *Solid State Ion.*, 1984, **14**, 181-185
- (21) R. Schlem, P. Till, M. Weiss, T. Krauskopf, S. P. Culver, and W. G. Zeier, *Chem. Eur. J.*, 2019, **25**, 4143-4148
- (22) Z. Li, X. Jiang, M. Zhou, Y. Guo, X. Luo, Y. Wu, Z. Lin, and J. Yao, *Inorg. Chem.*, 2018, **57**, 10503-10506
- (23) L. Kang, M. Zhou, J. Yao, Z. Lin, Y. Wu, and C. Chen, *J. Am. Chem. Soc.*, 2015, **137**, 13049-13059
- (24) E.-Y. Goh, E.-J. Kim, and S.-J. Kim, *J. Solid State Chem.*, 2001, **160**, 195-204
- (25) R. F. Hess, P. L. Gordon, C. D. Tait, K. D. Abney, and P. K. Dorhout, *J. Am. Chem. Soc.*, 2002, **124**, 1327-1333
- (26) T. Komm, and T. Schleid, *Z. Anorg. Allg. Chem.*, 2006, **632**, 42-48
- (27) T. Komm, and T. Schleid, *J. Alloy Comp.*, 2006, **418**, 106-110
- (28) C. Muller, S. Jorgens, and A. Mewis, *Z. Anorg. Allg. Chem.*, 2007, **633**, 1633-1638
- (29) V. Manriquez, A. Galdamez, and D. Guzman-Aguila, *Mat. Res. Bull.*, 2008, **43**, 2469-2475
- (30) Y. Klawitter, W. Bensch, and C. Wickleder, *Chem. Mater.*, 2006, **18**, 187-197
- (31) S. Milot, Y. Wu, C. Nather, W. Bensch, and K. O. Klepp, *Z. Anorg. Allg. Chem.*, 2008, **634**, 1575-1580
- (32) T. Komm, S. Strobel, and T. Schleid, *J. Alloy Comp.*, 2008, **451**, 648-653
- (33) A. Kuhn, R. Eger, J. Nuss, and B. V. Lotsch, *Z. Anorg. Allg. Chem.*, 2014, **640**, 689-692
- (34) V. V. Klepov, L. S. Breton, K. A. Pace, V. Kocevski, T. M. Besman, and H.-C. zur Loye, *Inorg. Chem.*, 2019, **58**, 6565-6573
- (35) T. Schleid, I. Hartenbach, and T. Komm, *Z. Anorg. Allg. Chem.*, 2002, **628**, 7-9
- (36) C. R. Evenson, and P. K. Dorhout, *Inorg. Chem.*, 2001, **40**, 2884-2891
- (37) L. M. Schoop, R. Eger, R. K. Kremer, A. Kuhn, J. Nuss, and B. V. Lotsch, *Inorg. Chem.*, 2017, **56**, 1121-1131
- (38) V. V. Klepov, M. D. Smith, and H.-C. zur Loye, *Inorg. Chem.*, 2020, **59**, 1905-1916

- (39) M. Ohta, S. Hirai, H. Kato, V. V. Sokolov, and V. V. Bakovets, *Mater. Trans.*, 2009, **50**, 1885-1889
- (40) L. Krause, R. Herbst-Irmer, G. M. Sheldrick, and D. Stalke, *J. Appl. Crystallogr.*, 2015, **48**, 3-10
- (41) APEX3 Version 2019.1-0 and SAINT+ Version 8.40A., 2019, Bruker Nano, Inc., Madison, WI, United States.
- (42) G. M. Sheldrick, *Acta Crystallogr. A*, 2015, **71**, 3-8
- (43) G. M. Sheldrick, *Acta Crystallogr. A*, 2008, **64**, 112-122
- (44) O. V. Dolomanov, L. J. Bourhis, R. J. Gildea, J. A. K. Howard, and H. Puschmann, *J. Appl. Crystallogr.*, 2009, **42**, 339-341
- (45) P. S. Peijzel, *J. Solid State Chem.*, 2005, **178**, 448-153
- (46) Y.-F. Lin, Y. H. Chang, Y.-S. Chang, B.-S. Tsai, and Y.-C. Li, *J. Electrochem. Soc.*, 2006, **153**, G543-G547
- (47) E. Banks, and R. Ward, *J. Electrochem. Soc.*, 1949, **96**, 297-303
- (48) P. N. Hazin, C. Lakshminarayan, L. S. Brinen, J. L. Knee, J. W. Bruno, W. E. Streib, and K. Folting, *Inorg. Chem.*, 1988, **27**, 1393-1400
- (49) V. V. Klepov, V. Kocevski, T. M. Besmann, and H.-C. zur Loye, *CrystEngComm*, 2021, **23**, 831-840