

REVIEW

View Article Online
View Journal | View IssueCite this: *Inorg. Chem. Front.*, 2020,
7, 4256

Engineering well-defined rare earth oxide-based nanostructures for catalyzing C1 chemical reactions

Kun Yuan and Ya-Wen Zhang *

C1 chemical reactions have attracted extensive attention in recent decades due to their significant roles in energy transfer and utilization and environmental protection. Among the various catalytic materials, rare earth oxide-based nanocatalysts exhibit superior performances in C1 chemical reactions because of their flexible electronic structures and abundant defect states. In this review, we summarize the nanostructural engineering and applications of rare earth oxide-based nanomaterials with well-defined compositions, crystal phases and shapes for efficiently catalyzing C1 chemical reactions. Initially, we introduce the structural features of rare earth oxides. Subsequently, we present common synthetic approaches and nanostructural engineering strategies toward the preparation of rare earth oxide nanomaterials with well-defined structures. Further, we discuss the structure–function correlation of well-defined rare earth oxide-based nanocatalysts in some important C1 chemical reactions including CO oxidation, water-gas shift reaction, CO₂ hydrogenation, methane oxidation and methanol oxidation. Finally, we prospect the challenges and future research trends in this promising field.

Received 24th June 2020,
Accepted 2nd September 2020

DOI: 10.1039/d0qi00750a

rsc.li/frontiers-inorganic

1. Introduction

As a type of important strategic resource, rare earth elements include 15 lanthanide elements (La–Lu) and two other elements, scandium and yttrium. They usually co-exist in minerals and have similar properties, which make their separation challenging.¹ Rare earth elements (except for Sc and Y) have partially unfilled 4f orbitals and abundant electronic energy level structures, thus they have flexible coordination numbers and outstanding catalytic properties for many reactions.^{2,3} Rare earth materials play a significant role in various applications such as agriculture, military, petrochemical industry, metallurgy, glass, and ceramics.^{4,5}

Nanostructured rare earth oxides are the most common rare earth nanomaterials, which are also the most widely studied.⁶ They are cheap and easily obtained, and they have different oxidation states in various conditions. The earliest report of the synthesis of rare earth oxide nanocrystals with a well-defined architecture dates back to the work of Cao's group,⁷ which involved the preparation of square Gd₂O₃ nanoplates *via* a colloidal approach. At almost the same time,

Zhang and Yan's group successively developed various methods for the synthesis of well-defined rare earth oxides with zero-dimensional (0D), one-dimensional (1D), two-dimensional (2D) and three-dimensional (3D) nanostructures.^{8–11} After development for more than 15 years, researchers have developed various synthetic strategies, and successfully prepared many rare earth oxide nanostructures with diverse well-defined morphologies.

Rare earth oxide nanostructures are broadly applied in catalysis, especially heterogeneous catalysis.^{12–15} On the one hand, rare earth oxide nanostructures by themselves are active for some catalytic reactions such as CO oxidation.¹² However, their activity is usually limited due to the weak adsorption of the reagent molecule. On the other hand, rare earth oxide nanostructures can act as supports or promoters to be combined with other metal or metal oxide catalysts.¹⁴ The catalytic properties of composite materials are significantly enhanced due to the synergistic effect between the support materials and loading elements. Further, they are used more widely in catalysis than single rare earth oxide nanostructures.

Among the catalytic reactions, C1 chemical reactions are crucial for addressing both energy and environmental problems faced by mankind in this century due to their important roles in producing essential chemicals (*e.g.* methane and methanol) and controlling pollution (*e.g.* CO and CO₂).^{16–19} Rare earth oxide-based catalysts are a vital class of catalytic nanomaterials for C1 chemical reactions.^{20,21} Thus, the devel-

Beijing National Laboratory for Molecular Sciences, State Key Laboratory of Rare Earth Materials Chemistry and Applications, PKU-HKU Joint Laboratory in Rare Earth Materials and Bioinorganic Chemistry, College of Chemistry and Molecular Engineering, Peking University, Beijing 100871, China. E-mail: ywzhang@pku.edu.cn; Fax: +86-10-62756787; Tel: +86-10-62756787

opment of high-performance rare earth oxide-based catalysts is urgent and significant. Engineering rare earth oxide-based catalysts with well-defined nanostructures is not only beneficial for enhancing their catalytic properties, but also facilitates the study of the relationship between catalytic properties and structure, which can provide guidance for designing catalysts with excellent performances since this is still unclear in many catalytic systems.

Due to the importance of rare earth-based nanomaterials, many groups have reviewed their synthesis and applications in catalysis. For example, Hussein⁶ published a thermal analysis and applied pyrolysis review about the formation, characterization and catalytic activity of rare earth oxides. In addition, Zhan *et al.*³ mainly discussed the catalytic applications of rare earth materials in energy production and utilization, and environmental protection. Guo *et al.*⁵ commented on the research advances of rare earth-based catalysts in heterogeneous transformation reactions of small molecules. Richard *et al.*² focused on the properties and applications of rare earth elements for CO₂ hydrogenation to methanol. Besides, Huang *et al.*¹ reviewed the synthetic routes and electrochemical applications of rare earth-based nanomaterials. Similarly, the review by Gao *et al.*⁴ also discussed and summarized the recent progress on rare earth-based nanocatalysts, but their key point was the incorporation of rare earth elements with transition metals. Although rare earth oxide-based nanostructures were a significant part introduced in the abovementioned reviews, few of them focused on the shape-control of well-defined rare earth nanostructures and their catalytic applications in C1 chemical reactions. Besides, most of the reported

reviews about rare earth oxides mainly focused on the applications of CeO₂ nanomaterials,^{22–30} and rarely discussed other rare earth oxides. Therefore, a review that systematically summarizes the morphological engineering of nanostructured rare earth oxides (not only CeO₂) and highlights their structure–function relationships in some important catalytic reactions is still necessary.

Thus, to meet this demand, in the present review, we focus on the shape-controlled synthesis of well-defined rare earth oxide nanostructures and their catalytic structure–activity correlations. Herein, we introduce the structure features of rare earth oxides and summarize the most common synthetic routes for the preparation of well-defined rare earth oxide nanostructures from the perspective of their morphologies. Moreover, we choose some typical C1 chemical reactions to summarize the relationship between the engineered nanostructures of the rare earth oxide-based nanomaterials and their catalytic properties.

2. Structural features of rare earth oxides

Generally, rare earth oxides can be divided into two categories, trivalent oxides and tetravalent oxides. Most of the stable rare earth oxides are trivalent except for CeO₂, PrO₂ and TbO₂. The trivalent RE₂O₃ usually has three types of structures, which are denoted as A, B, and C (Fig. 1a–c, respectively). The A-type RE₂O₃ is hexagonal, with the *P3m1* space group. The RE³⁺ is seven-coordinated with O, in which six O^{2–} form an octa-



Kun Yuan

Kun Yuan was born in Tianjin, China. He received his BSc Degree in Chemistry from Peking University in 2016. Currently, he is studying for his PhD Degree under the supervision of Prof. Ya-Wen Zhang in the College of Chemistry and Molecular Engineering, Peking University. His current research focuses on the synthesis and investigation of the catalytic properties of ceria-supported noble metal nanocatalysts.



Ya-Wen Zhang

Ya-Wen Zhang is a Full Professor and Principle Investigator at the College of Chemistry and Molecular Engineering of Peking University. The research interests of his group include the rational design, controllable synthesis, ordered assembly, catalytic properties and structure–function relationships of rare earth and noble metal nanostructures. He has published more than 150 papers in peer-reviewed scientific journals and several book chapters, and was a Winner of the National Science Fund for Distinguished Young Scholars in 2010. He obtained his BSc Degree, MSc Degree, and PhD Degree from Peking University in 1988, 1994 and 1997, respectively, and did postdoctoral research in the State Key Laboratory of Rare Earth Materials Chemistry and Applications of Peking University during 1998–2000, and was a visiting scholar in the Department of Chemistry of the University of California at Berkeley and Lawrence Berkeley National Laboratory in 2006–2008.



Fig. 1 Schematic illustration of the crystal structure of rare earth oxides: (a) A-type RE_2O_3 , (b) B-type RE_2O_3 , (c) C-type RE_2O_3 , and (d) fluorite REO_2 .

hedron and the last O^{2-} is located at one of the facets of the octahedron. The B-type RE_2O_3 is monoclinic, with the $C2/m$ space group. Similarly, the RE^{3+} is also seven-coordinated and six O^{2-} form an octahedron, but the last O^{2-} is a little farther from the RE^{3+} . The C-type RE_2O_3 is cubic, with the $Ia\bar{3}$ space group. The RE^{3+} is six-coordinated, and the cell structure of C-type RE_2O_3 is similar to the cubic fluorite structure, in which only two O^{2-} are removed regularly.

REO_2 has a cubic fluorite structure, with the $Fm\bar{3}m$ space group, in which the RE^{4+} is cubic close packing and coordinated with eight O^{2-} , and the O^{2-} is located in a tetrahedral void and coordinated with four RE^{4+} (Fig. 1d). The RE in REO_2 also has a stable valence of +3, and it can transform between +3 and +4 through the generation and elimination of an oxygen vacancy.

As can be seen in the phase diagram in Fig. 2, RE_2O_3 (RE = La–Pr) has an A-type structure, RE_2O_3 (RE = Y, Dy–Lu) has a C-type structure, and the others are C-type at low temperature and become B-type at high temperature.



Fig. 2 Phase diagram of RE_2O_3 .

3. Synthesis of well-defined rare earth oxide nanostructures

Thus far, researchers have developed numerous methods for the synthesis of rare earth oxide nanomaterials with well-defined structures, including 0D nanocubes and nanooctahedra,^{8,31–33} 1D nanorods and nanowires,^{34–37} 2D nanosheets and nanobelts,^{38–41} and 3D dendritic and flower-like structures.^{11,42–44} Optimized strategies such as selective adsorption on specific facets, pH adjustment, templating and self-assembly are widely used in engineering well-defined rare earth oxide nanostructures^{45,46} (Fig. 3). Rare earth oxide nanomaterials with different shapes usually have diverse physical and chemical properties due to their distinguishable surface structures and chemical states. Hence, controlling the shapes of rare earth oxide nanostructures will support the realization of different functions and applications. In this section, we mainly summarize the synthesis of well-defined rare earth nanostructures considering their morphologies, with the introduction of some typical synthetic examples. Furthermore, it should be noted that most of the rare earth oxides in the cases we discuss below are cubic structure according to their phase diagram. Actually, cubic fluorite CeO_2 is the most studied nanomaterial based on the current research status of rare earth oxides.

3.1 0D rare earth oxide nanostructures

0D nanomaterials are defined as nanocrystals with a nanoscale size in three dimensions. They usually contain nanocubes, nanooctahedra, nanotetrahedra, nanopolyhedra, *etc.* In general, nanostructures with different morphologies will have diverse exposed crystal planes. For instance, nanocubes have exposed $\{100\}$ facets, whereas nanooctahedra and nanotetrahedra have exposed $\{111\}$ facets. The key factor for the preparation of rare earth oxide nanocrystals with specific shapes is controlling the relative crystal growth rate of specific facets during either the anisotropic growth mode or isotropic growth mode.^{8,33}

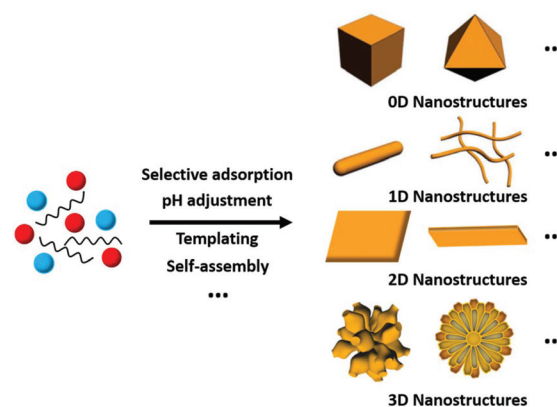


Fig. 3 Schematic illustration of the synthesis of rare earth oxide nanostructures with different morphologies.

Taking the synthesis of rare earth oxide nanocubes as an example, Zhang and Yan's group⁸ prepared CeO₂ nanocubes through pH adjustment using a hydrothermal method. The precipitation reaction occurred between Ce(NO₃)₃ and NaOH, and the secret of gaining CeO₂ nanocubes enclosed with {100} facets was applying a high pH and temperature to achieve a fast dissolution–recrystallization process for the transformation of Ce(OH)₃ into CeO₂ particles. In contrast, a slow dissolution–recrystallization process with a low pH and temperature resulted in the formation of CeO₂ nanopolyhedra with {111} and {100} planes. Besides, the same goal was completed by Dang *et al.*⁴⁷ using a liquid–liquid interface with the assistance of oleic acid (OLA). As shown in Fig. 4a, {111}-dominated CeO₂ nanooctahedra or truncated nanooctahedra were obtained in the water phase initially owing to the lower surface energy of the {111} planes, then the OLA selectively adsorbed on the {100} planes, resulting in the transfer of the CeO₂ nanoparticles from the water phase to the toluene phase. Because of the coating of OLA on the {100} planes, the growth rate of the CeO₂ [100] direction was limited, and finally the CeO₂ nanoparticles turned into nanocubes (Fig. 4b). This was a typical case that using selective adsorption on a specific facet controlled the morphologies of the rare earth oxide nanostructures. Specially, Miao *et al.*⁴⁸ prepared CeO₂ nanocubes through the doping of F. They concluded that the generation of CeO₂ nanocubes was a result of the etching effect by HF in the crystal growth process.

For the preparation of rare earth oxide nanooctahedra, they are easier to be obtained than nanocubes as a consequence of the lower surface energy of the {111} facets than that of the

{100} facets. They can be facily produced by tuning the precipitation step in the hydrothermal method.^{32,33} For example, Feng *et al.*³³ synthesized CeO₂ nanooctahedra with a size of around 100 nm using the weak base Na₃PO₄ in the hydrothermal process. The slow growth rate guaranteed the generation of the more stable morphology of nanooctahedra rather than nanocubes. The authors also demonstrated that replacing Na₃PO₄ with the strong base NaOH would result in the formation of CeO₂ nanospheres and nanocubes. Similarly, CeO₂ nanooctahedra were successfully synthesized by Ren *et al.*⁴⁹ through the hydrothermal route using Ce(NO₃)₃ and a relatively small amount of NaOH. Also, they also showed that a high concentration of NaOH could yield nanocubes. Specially, single crystalline CeO₂ nanooctahedra were obtained through galvanostatic electrodeposition in a conventional three-electrode cell.⁵⁰ It was also the first time that CeO₂ nanooctahedra were prepared *via* the electrochemical route.

In the case of other 0D rare earth oxide nanostructures, nanopolyhedra with no specific shape (called nanoparticles) are common nanomaterials. Their crystal facets usually consist of {100} and {111} planes, and they are easy to obtain because engineering of their morphology is not required. Furthermore, they can be used as reference samples in the study of the plane effect derived from diverse morphologies and are widely used in applications such as catalysis because of their easy accessibility. For their synthesis, Yang *et al.*⁵¹ used the sol–gel method combined with a solvothermal process to obtain CeO₂ nanoparticles with a high surface area. They carried out the solvothermal treatment after they obtained the gel powder, followed by calcination in air to obtain the final product. Additionally, Shiri *et al.*⁵² synthesized Sm₂O₃ nanoparticles using a nitrate bath of Sm(NO₃)₃ *via* pulse electrochemical deposition assisted by ultrasound. Different from the regular precipitation method, precipitation in reverse microemulsions based on different surfactants was applied to prepare CeO₂ nanoparticles by Shlapa *et al.*⁵³ A schematic of the synthetic route is shown in Fig. 5. Compared with the traditional precipitation method, the precipitation reaction in reverse microemulsions is limited by the surfactant molecules, and the size can be easily controlled by tuning the length of the hydrophilic part of the surfactant. The as-prepared CeO₂ nanoparticles had a small and uniform size in the range of 6–10 nm and showed good catalase-like activity.

3.2 1D rare earth oxide nanostructures

Compared with 0D nanostructures, one non-nanoscale dimension is allowed to exist in 1D nanostructures, while the other two dimensions must be on the nanoscale. 1D rare earth oxide nanostructures including nanorods, nanowires and nanotubes are important nanomaterials for catalysis because of their unique exposed crystal planes, abundant defect sites, and good stability, and they can also provide good models for theoretical simulation.^{34,35} In the synthetic strategies for engineering 1D rare earth oxide nanostructures, pH adjustment in the hydrothermal procedure is the most common means because the acid–base balance can influence many key



Fig. 4 (a) Transmission electron microscopy (TEM) images of the evolution from CeO₂ truncated nanooctahedra to nanocube. (b) Schematic illustration of shape evolution of CeO₂ nanocrystals in the organic phase. Adapted with permission from ref. 47 Copyright 2010, American Chemical Society.

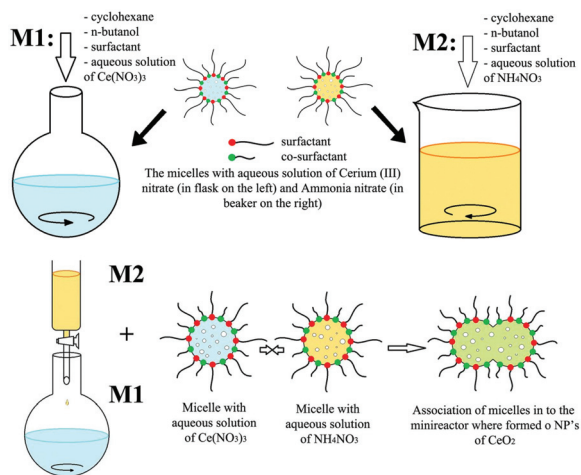


Fig. 5 Schematic illustration of the synthesis of CeO_2 nanoparticles *via* precipitation in reverse microemulsions. Adapted with permission from ref. 53. Copyright 2019, Springer Nature.

factors in shape-control such as the crystal growth rate and stability of intermediates.^{34–37}

Furthermore, it should be noted that the hydrothermal method for the preparation of rare earth oxides can be divided into two types, alkali and acid methods. The alkali hydrothermal route is very common, for example, CeO_2 nanorods with a length in the range of 100–300 nm and width of 13–20 nm were firstly prepared by Zhou *et al.*³⁴ using $\text{Ce}(\text{NO}_3)_3$ and NaOH . The predominantly exposed facets were the unusually active $\{001\}$ and $\{110\}$ planes rather than the $\{111\}$ plane. The authors provided inspiration for designing and controlling the synthesis of nanocrystals with different shapes. Our group³⁵ synthesized CeO_2 nanowires *via* the hydrothermal method at 180 °C using CeCl_3 and NaOH without the addition of any capping agent. In the synthetic process, NaCl was specially used to obtain uniform wire-like nanostructures dominantly enclosed by $\{110\}$ facets. We also prepared Ln-doped (Ln = La–Lu) CeO_2 nanowires using the same method, and the distribution of dopant was very homogeneous. The key was the co-precipitation of Ce^{3+} and Ln^{3+} to form $\text{Ce}(\text{OH})_3 \cdot \text{Ln}(\text{OH})_3$, which transformed into $\text{CeO}_2 \cdot \text{Ln}$ through calcination. The dopant content was about 10%, and the aspect ratio of most of the $\text{CeO}_2 \cdot \text{Ln}$ nanowires were smaller than that of the pure CeO_2 nanowires due to the difference in the ionic radius between Ce and the dopant ion. As another example, Sohn³⁶ successfully synthesized Yb_2O_3 nanowires and nanorods *via* the hydrothermal method at 210 °C using ammonia water as the precipitant, and YbCl_3 and $\text{Yb}(\text{NO}_3)_3$ as the precursor, respectively (Fig. 6). The abovementioned cases indicate that besides the vital role of pH adjustment, the formation of 1D rare earth oxide nanostructures also greatly relies on the transformation of the intermediates. It may be difficult to obtain rare earth oxide nanowires or nanorods directly, but it can be easy to obtain their corresponding hydroxides and transform them into oxides. Acid hydrothermal treatment is less used in

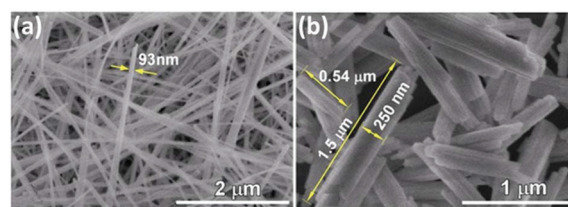


Fig. 6 SEM images of as-synthesized Yb_2O_3 (a) nanowires and (b) nanorods. Adapted with permission from ref. 36. Copyright 2018, Elsevier.

the synthesis of 1D rare earth oxide nanostructures. As an example, Pr_2O_3 nanowires were prepared by Sobahi³⁷ using the hydrothermal method by tuning the pH value of the precursor solution of $\text{Pr}(\text{NO}_3)_3$ to 1.3 and adding glycine as the shaping reagent.

Rare earth oxide nanotubes are another type of important 1D nanomaterials on account of their high surface area and rich defects. Due to the hollow structure of the nanotubes, templating is a very suitable strategy for their preparation. As an example, Eu_2O_3 nanotube arrays (Fig. 7a) could be obtained using the sol-gel method assisted by porous anode alumina templates.⁵⁴ According to the synthetic mechanism shown in Fig. 7b, the alumina templates were impregnated in the mixture of $\text{Eu}(\text{NO}_3)_3$ solution and urea, and the solution filled the pores of the templates. After heating the solution, the pH value increased owing to the hydrolysis of urea, resulting in the formation of $\text{Eu}(\text{OH})_3$ in both the template pores and solution. The sol particles of $\text{Eu}(\text{OH})_3$ were negatively charged, while the templates were positively charged, and therefore the sol particles gathered at the walls of the templates and gradu-

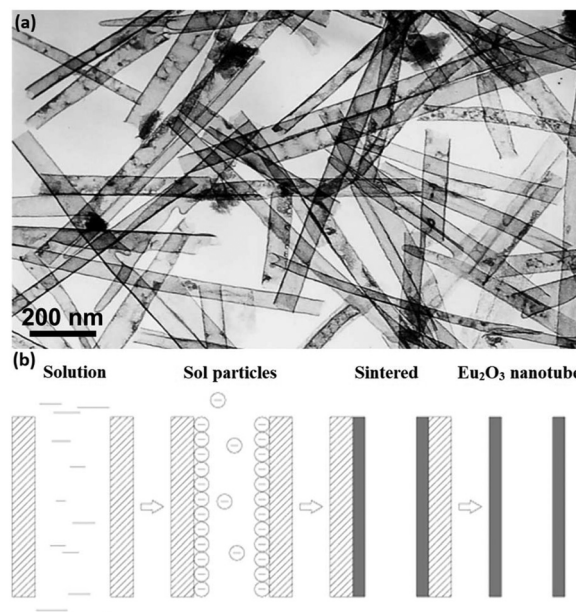


Fig. 7 (a) TEM image of Eu_2O_3 nanotubes. (b) Schematic illustration of the formation mechanism of Eu_2O_3 nanotubes. Adapted with permission from ref. 54. Copyright 2004, American Chemical Society.

ally extended to the center. Finally, the templates were removed from the sol solution and sintered in a furnace, generating Eu_2O_3 nanotubes. As another example, Tb_2O_3 nanotubes were synthesized by Tang *et al.*⁵⁵ through the hydrothermal method using terbium chloride as the precursor and sodium dodecyl benzenesulfonate as the template reagent. $\text{Tb}(\text{OH})_3$ nanotubes were initially obtained *via* the hydrothermal process after adjusting the solution pH to 12 with NaOH. Finally, they calcined the $\text{Tb}(\text{OH})_3$ nanotubes at 800 °C under a reducing atmosphere and obtained Tb_2O_3 nanotubes. Interestingly, Tb_2O_3 nanotubes could also be synthesized through a facile precipitation method using $\text{Tb}(\text{NO}_3)_3$ and ammonia.⁵⁶ The precipitation process involved aging at room temperature for two days, which was necessary for the formation of the tube-like structure under a slow growth rate.

3.3 2D rare earth oxide nanostructures

Similar to the definition of 0D and 1D nanostructures, 2D nanostructures allow the existence of two non-nanoscale dimensions, and thus they usually contain nanosheets, nanoplates, nanobelts, *etc.* 2D rare earth oxide nanocrystals have many advantages for catalytic applications such as huge surface area, a variety of defects, and high atomic utilization owing to their thin structure.^{57–59} However, it is challenging to prepare 2D rare earth oxide nanomaterials due to the complex requirement of anisotropic growth. In general, a relatively slow growth rate of a specific crystal plane is preferred to realize anisotropic morphologies.

Nanoplates are well-known nanomaterials among the 2D rare earth oxide nanostructures, which have been successfully synthesized *via* several methods.^{57,59} The first reported synthetic work on 2D rare earth oxide nanostructures was the Gd_2O_3 square nanoplates prepared by Cao⁷ using a solution-phase decomposition method. Soon afterwards, Zhang and Yan's group^{9,10} prepared a series of cubic rare earth (RE = La–Lu, Y) oxide nanoplates or nanodisks *via* a non-hydrolytic route using various rare earth complexes as precursors with the assistance of oleylamine (OM), oleic acid (OA) and 1-octadecene (ODE). Our group carried out control experiments to determine the specific effects of different experimental parameters. As shown in Fig. 8a, the whole shape evolution can be divided into two parts. Firstly, the rare earth oleates are formed through ion exchange with OA in solution. Secondly, decomposition of the rare earth oleates occurs *via* the catalysis of OM. Due to the selective adsorption of OA on the {100} planes, the RE_2O_3 crystals can realize anisotropic growth to generate 2D structures. Also, they would result in diverse morphologies because of the difference in growth rate, which is affected by the rare earth precursors. As another illustration, La_2O_3 nanoplates were obtained by Wu *et al.*⁶⁰ *via* a combination of precipitation and calcination using $\text{La}(\text{NO}_3)_3$ and formamide. In the precipitation process, $\text{La}(\text{OH})_3$ nanoparticles were formed through nucleation and aggregated (Fig. 8b). Then they grew into 1D $\text{La}(\text{OH})_3$ nanorods because hexagonal $\text{La}(\text{OH})_3$ has an anisotropic crystal structure. During the calci-

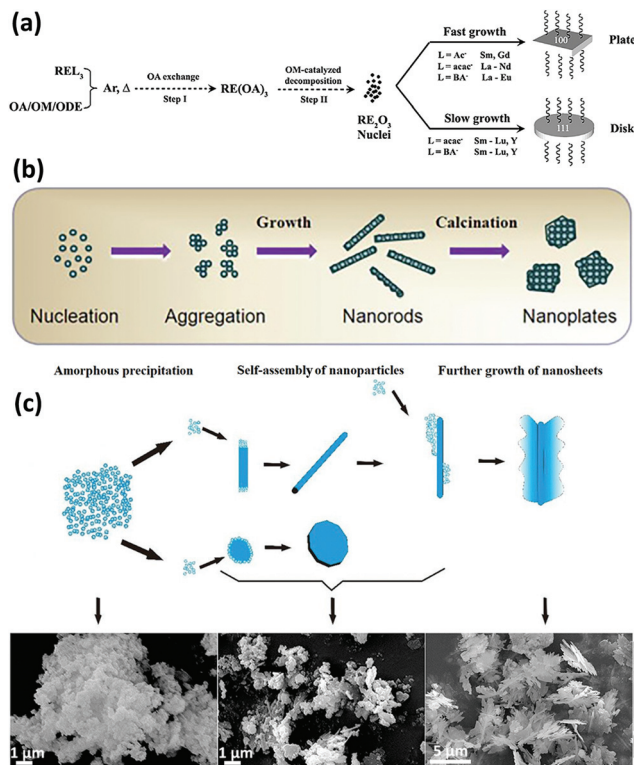


Fig. 8 (a) Schematic of the formation mechanism of RE_2O_3 nanoplates and nanodisks. Adapted with permission from ref. 10. Copyright 2007, American Chemical Society. (b) Schematic illustration of the formation mechanism of La_2O_3 nanoplates. Adapted with permission from ref. 60. Copyright 2013, Elsevier. (c) Schematic formation evolution of leaf-like CeO_2 nanosheets and corresponding scanning electron microscopy (SEM) images of the different stages. Adapted with permission from ref. 61. Copyright 2013, Springer Nature.

nation step, the $-\text{OH}$ groups were removed and the nanocrystals underwent reconstruction to achieve the lowest surface energy. Consequently, the $\text{La}(\text{OH})_3$ nanorods transformed into hexagonal La_2O_3 nanoplates under the driving force of calcination. The high-resolution TEM (HRTEM) results showed the {002} exposed facet, suggesting that preferential growth occurred along the [002] direction.

In the case of engineering of rare earth oxide nanosheets, Hu *et al.*⁶¹ synthesized leaf-like CeO_2 nanosheets mainly enclosed with {111} and {200} facets *via* the hydrothermal method using $\text{Ce}(\text{NO}_3)_3$ as the precursor, NH_4HCO_3 as the precipitant, and ethylenediamine as the complexant. As displayed in Fig. 8c, the product evolution could be divided into three stages. In the first stage, Ce^{3+} reacted with NH_4HCO_3 and generated a large amount of $\text{Ce}(\text{OH})\text{CO}_3$ nanoparticles, which aggregated to form fluffy particles through self-assembly. Afterwards, nanorods and nanosheets emerged due to the dissolution–recrystallization and self-assembly of the fluffy particles. In the last stage, the nanorods continued to grow until the formation of leaf-like nanosheets. In the whole process, ethylenediamine was coordinated with Ce^{3+} and controlled the release of Ce^{3+} , thus further controlling the crystal growth

direction to form nanosheets. Similarly, Dai *et al.*⁶² obtained CeO₂ nanosheets using Ce(NO₃)₃ and NH₄HCO₃, but they did not add ethylenediamine or any other reagents. As an alternative, they selected a low temperature of 30 °C to carry out the precipitation reaction in order to obtain an adequately slow growth rate for the formation of sheet-like nanostructures. As a supplement, the electrochemical method is also good for synthesizing 2D rare earth oxides. For example, Huang *et al.*³⁸ obtained Eu-doped CeO₂ nanosheets through electrodeposition on a Ti substrate and subsequent calcination in N₂. However, the formation mechanism was unclear and needs more exploration.

Rare earth oxide nanobelts is another type of 2D nano-materials that are promising candidates for the fundamental study of physical and chemical properties in many fields.^{63,64} However, they are difficult to synthesize due to the preference to form 1D nanostructures or other nanocrystals with lower anisotropy. Some groups successfully achieved their synthesis through the solvothermal method, which is suitable for crystal shape control.^{63,64} For example, Eu-doped single-crystal Y₂O₃ nanobelts with an average thickness of *ca.* 10 nm and width of 40–100 nm were obtained by Li *et al.*⁶³ using a simple solvothermal method without the addition of any templates. The key factors for controlling the belt-like shape and size were the initial pH of the solution and reaction time of the solvothermal process. As another example, Rao *et al.*⁶⁴ obtained mesoporous CeO₂ nanobelts *via* the hydrothermal method, and subsequent calcination without any template or surfactant. The authors researched the effect of the experimental conditions in the hydrothermal process on morphologies of the CeO₂ precursors, and they found that the temperature, cationic type of alkali and ratio of alkali/Ce contributed to the final shape of the products (Fig. 9a–e). Fig. 9f further illustrates the possible formation mechanism of the mesoporous CeO₂ nanobelts. Briefly, colloidal Ce(OH)₃ nuclei were initially formed, followed by dissolution–recrystallization in a mixture of OH[−] and HCHO. Formates and carbonates were generated in the solution *via* the disproportionation reactions between OH[−] and HCHO, and they could coexist due to the high concentration and small radius of Na⁺, which was vital for the anisotropic growth to form belt-like nanostructures. During the calcination of the nanobelt precursors, they transformed into polycrystalline CeO₂ nanobelts and a mass of pores was generated *via* the decomposition of formates and carbonates, leaving sodium oxide on the surface. After washing with water, the final mesoporous CeO₂ nanobelts with a thickness of 10–30 nm and a width of 50–250 nm (Fig. 9g) were obtained. Since rare earth oxide nanobelts are similar to 1D nanostructures to a certain degree, the electrospinning method is also suitable for the preparation of rare earth oxide nanobelts. As an example, Eu₂O₃ nanobelts with a uniform size were obtained *via* the electrospinning process.⁶⁵

3.4 3D rare earth oxide nanostructures

3D nanostructures can be regarded as composites of 0D, 1D, and 2D nanomaterials. 3D rare earth oxide nanostructures play

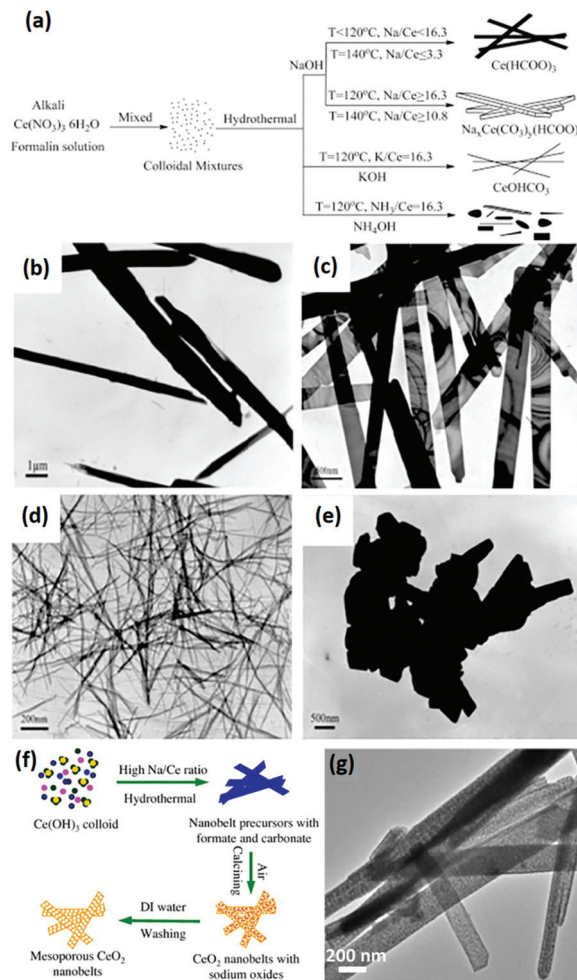


Fig. 9 (a) Schematic illustration of the synthesis of CeO₂ precursors under various conditions. TEM images of CeO₂ precursors prepared under various conditions: (b) 140 °C, NaOH : Ce = 3.3; (c) 140 °C, NaOH : Ce = 10.8; (d) 120 °C, KOH : Ce = 16.3; and (e) 180 °C, NaOH : Ce = 16.3. (f) Schematic illustration of the mechanism for the formation of mesoporous CeO₂ nanobelts. (g) TEM image of mesoporous CeO₂ nanobelts. Adapted with permission from ref. 64. Copyright 2013, Elsevier.

a significant role in catalytic applications mainly because of three advantages.^{11,66–68} First, they usually have good robustness in catalytic processes due to their anti-sintering ability, which is attributed to their large size. Secondly, they possess a large surface area since they consist of small units such as nanoparticles and nanosheets. Thirdly, they are rich in defects and high-index facets due to the oriented attachment of the tiny building blocks. However, unlike 0D, 1D and 2D nanostructures, the 3D rare earth oxide nanostructures hardly have regular morphologies. They have well-known structures such as dendrites and flowers, but most of them are original nanomaterials.^{66–69}

As an instructive work, CeO₂ nanoflowers obtained *via* the rapid thermolysis of (NH₄)₂Ce(NO₃)₆ in a mixture of OA/OM were reported by Zhang and Yan's group.¹¹ The ceria clusters

capped with OA and OM were generated as a result of the hydrolysis of $(\text{NH}_4)_2\text{Ce}(\text{NO}_3)_6$ at a low temperature ($<220\text{ }^\circ\text{C}$). When the temperature increased to above $220\text{ }^\circ\text{C}$, the capping agents on the surface of the ceria particles disappeared quickly through the redox reaction. Consequently, the small particles spontaneously aggregated *via* 3D oriented attachment and generated CeO_2 nanoflowers. Self-assembly is often chosen for the construction of 3D rare earth oxide nanostructures, whose driving force is the hydrophobic effect of the surfactants adsorbed on the nanocrystals. For instance, ultrathin nanodisks of Sm_2O_3 and hierarchical flower-like Gd_2O_3 and Dy_2O_3 (Fig. 10a–c) with abundant high-index $\{400\}$ facets were prepared by Xiao *et al.*⁶⁶ through a benzyl alcohol-based nonaqueous sol-gel route using rare earth acetylacetonates as precursors. The X-ray diffraction (XRD) results showed that all of them were in the cubic phase (Fig. 10d). Also, Fig. 10e shows the possible formation mechanism of these rare earth oxide nanostructures, where nanodisks of the three oxides were obtained in the first stage of the sol-gel process, then Sm_2O_3 stacks were formed through mesocrystal fusion, and flower-like spheres of Gd_2O_3 and Dy_2O_3 were generated *via* self-assembly. The different behaviors in the final stage were

possibly due to their diverse inherent properties such as crystal growth behavior.

With respect to rare earth oxide dendrites, Zhang *et al.*⁶⁷ developed a combination method of hydrothermal treatment and thermal decomposition to prepare CeO_2 dendrites with a three-fold shape. In the hydrothermal procedure, the authors chose $\text{Ce}(\text{NO}_3)_3$ and urea as reactants to react in a water-triethanolamine (TEA) mixed solvent. It is established that TEA can steadily coordinate with Ce^{3+} , which will notably lower the concentration of free Ce^{3+} in solution. Thus, the rate of $\text{Ce}(\text{OH})\text{CO}_3$ formation would be extremely slow, which is beneficial for the crystallization and separation of the nucleation and growth stage. Consequently, the nuclei aggregated with each other and formed three-fold branched units, then these building units connected together through self-assembly and generated the final dendrites. An identical function as TEA could be realized using ammonia water or hydrazine hydrate in the studies by Zhang *et al.*^{43,68} They obtained three-fold and four-fold CeO_2 dendrites by intentionally using ammonia water and hydrazine hydrate, respectively. Both reagents had an important effect on engineering the shape of the CeO_2 dendrites through decreasing the Ce^{3+} concentration and lowering the crystal growth rate, which are crucial for obtaining branched architectures.

Besides 3D dendritic and flower-like rare earth oxides, Qu *et al.*⁶⁹ obtained La_2O_3 hollow spheres with multi shells *via* a one-pot hydrothermal method combined with calcination. They used a mixture of D-glucose and lanthanum nitrate as the precursor solution, and the special evolution mechanism could be ascribed to the template effect of the carbon in the structure. With a continuous increase in the calcination temperature, the carbon contained in the spheres was oxidized to CO_2 , resulting in the formation of a multi-shell structure. Besides, Dong *et al.*⁷⁰ reported the preparation of coral-shaped Dy_2O_3 through an environmentally friendly solvothermal method combined with calcination. They used dysprosium acetylacetonate and carbamide as reagents and methanol as the solvent. The formation of the coral-like Dy_2O_3 was based on the spontaneous accumulation of small particles with a size of about 12 nm. Moreover, 3D porous CeO_2 with various shapes was obtained by Jiang *et al.*⁴⁴ *via* a simple precipitation method using glycine as a soft bio-template. The preparation procedure, which involved stirring at room temperature, drying at $100\text{ }^\circ\text{C}$, and calcination at $500\text{ }^\circ\text{C}$, was very facile, as shown in Fig. 11a. By modulating the reagent ratio of Ce^{3+} , urea and glycine, shuttle-like, bowknot-like, prism-like, and dumbbell-like CeO_2 were obtained (Fig. 11b–g). Furthermore, the authors investigated the formation mechanism of the CeO_2 products, as shown in Fig. 11h. As a bio-template, the glycine provided place for the reaction of Ce^{3+} and urea to produce nanospheres since Ce^{3+} was adsorbed on the surface of glycine. Then the final product was formed through the self-assembly of the nanospheres. The morphologies could be tuned by the reagent ratio because of its influence on the dispersion and hydrolysis rate of Ce^{3+} .

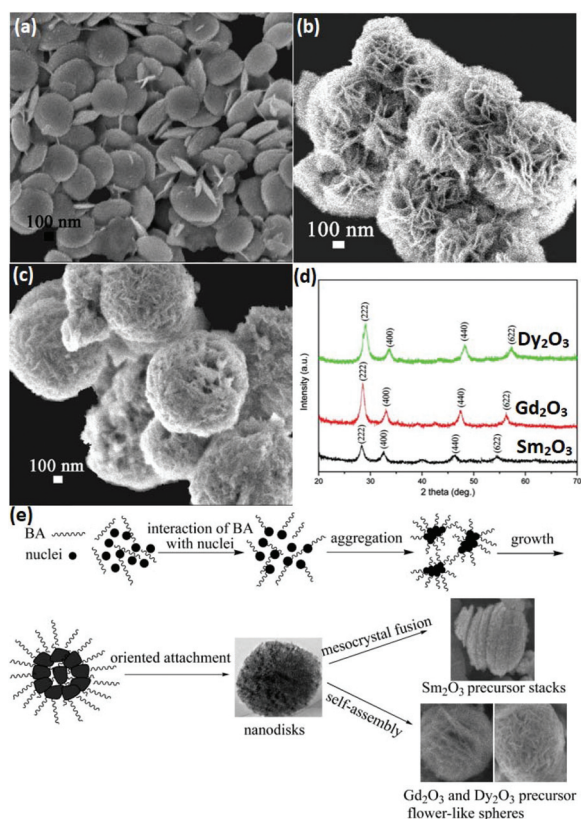


Fig. 10 SEM images of (a) Sm_2O_3 nanodisks; (b) Gd_2O_3 ; and (c) Dy_2O_3 flower-like spheres. (d) XRD patterns and (e) schematic illustration of the possible formation process of Sm_2O_3 nanodisks or Gd_2O_3 and Dy_2O_3 flower-like spheres. Adapted with permission from ref. 66. Copyright 2009, American Chemical Society.



Fig. 11 (a) Procedure for the synthesis of 3D porous CeO_2 . SEM images of CeO_2 prepared with different ratios of reagents (Ce^{3+} : urea : glycine) of (b) 3:0:1; (c) 3:1:1; (d) 3:2:1; (e) 3:40:1; (f) 3:4:2; and (g) 6:2:1. (h) Schematic illustration of the formation of the 3D porous CeO_2 with a bowknot shape. Adapted with permission from ref. 44. Copyright 2018, Royal Society of Chemistry.

4. Catalytic applications of rare earth oxide nanomaterials in C1 chemical reactions

Rare earth oxide nanomaterials are very promising for catalytic applications due to their abundant electronic structures and flexible oxidation states and coordination numbers.^{3–5} Also, researchers have already studied and utilized rare earth oxide-based nanocatalysts in many important reactions such as C1 chemical reactions.^{20,21} C1 chemical reactions are vital because they are closely related with the generation, storage and conversion of energy and environmental protection.^{16–19} Therefore, the development of novel well-defined rare earth oxide nanomaterials with high catalytic performances in C1 chemical reactions has important implications for alleviating the increasing energy and environment crisis. In this section, we employ several typical C1 chemical reactions including the CO oxidation reaction, water gas-shift reaction (WGSR), CO_2 hydrogenation reaction, methane oxidation reaction and methanol oxidation reaction (MOR) to summarize the nanostructural engineering of rare earth oxide nanomaterials in catalytic applications and reveal the corresponding structure–performance relationship, assisted by some representative works.

4.1 CO oxidation reaction

The CO oxidation reaction ($\text{CO} + \text{O}_2 \rightarrow \text{CO}_2$) is often used as a probe reaction to study the structure–activity relationship of catalysts owing to its simple reaction formula and mechanism. Besides, it also has applied value in practical applications such

as automobile tail gas purification, CO sensors, and indoor air purification.^{71,72} For the mechanism of the CO oxidation reaction, the Mars-van Krevelen mechanism is accepted by most researchers, that is, a CO molecule reacts with the lattice oxygen of the oxide and *in situ* generates an oxygen vacancy, and then the oxygen molecule fills the vacancy and finishes the cycle. Consequently, oxygen vacancies play a vital role in the catalytic CO oxidation reaction, which are abundant in many rare earth oxide nanomaterials.

Obviously, rare earth oxide nanomaterials can independently catalyze the CO oxidation reaction without modulation with other non-rare earth metals, and their performance is closely correlated with their morphologies.^{11,34,73} As an example, the CeO_2 nanorods synthesized by Zhou *et al.*³⁴ exhibited a T_{50} (temperature of 50% CO conversion) of 186 °C towards CO oxidation, which is much lower than that of CeO_2 nanoparticles. The enhanced activity was ascribed to the well-defined reactive {001} and {110} planes. Our group⁷³ implemented the dimension-manipulated synthesis of CeO_2 nanostructures and obtained 0D uniform crystals, 2D polycrystalline assembly, and 3D mesoporous framework. The 2D polycrystalline assembly sample showed the highest activity ($T_{50} = 310$ °C) for CO oxidation, while the 3D mesoporous framework had the lowest activity ($T_{50} = 390$ °C), and all three nanocatalysts were much more active than bulk CeO_2 . In addition, Kang *et al.*⁷⁴ prepared hexagonal $\text{Pr}(\text{OH})_3$ and cubic Pr_6O_{11} nanorods and tested their activity for CO oxidation. The $\text{Pr}(\text{OH})_3$ nanorods had a T_{10} (temperature of 10% CO conversion) of 525 °C in the first run and then transformed into Pr_6O_{11} nanorods after the first run. Subsequently, in the second run, the T_{10} was 465 °C due to the transformation from $\text{Pr}(\text{OH})_3$ to Pr_6O_{11} . Although their activity was lower than that of commercial catalysts, they can be applied in catalysis and sensing. As another example, Zhang *et al.*⁷⁵ synthesized 3D ordered porous Pr_6O_{11} and Tb_4O_7 using a hard template method. The Pr_6O_{11} and Tb_4O_7 nanostructures showed a T_{50} of 305 °C and 360 °C, respectively, which were much more active than commercial Pr_6O_{11} (550 °C). The enhanced activity may have originated from their large surface area, abundant oxygen vacancies, and higher low-temperature reducibility.

Doping is a common strategy for enhancing the catalytic activity of rare earth oxide nanomaterials. For instance, the CeO_2 nanowires prepared by our group³⁵ could catalyze the CO oxidation reaction with a T_{50} of 350 °C, which may be ascribed to the facile formation of oxygen vacancies in the CeO_2 {110} facet. We successfully doped lanthanide elements in the CeO_2 nanowires (Fig. 12a) to enhance the activity of CeO_2 , and the most active sample of Nd-doped CeO_2 nanowires showed an order of magnitude higher activity (TOF at 200 °C = $5.4 \times 10^{-4} \text{ s}^{-1}$) than that of the pure CeO_2 nanowires (TOF at 200 °C = $4.1 \times 10^{-5} \text{ s}^{-1}$, Fig. 12b). We also found that the big difference in the activity of the doped catalysts was derived from two aspects. On the one hand, the oxygen vacancy formation energy of the light rare earth-doped samples was much lower than that of the heavy rare earth-doped samples (Fig. 12c), indicating that the former had more oxygen vacancies, which



Fig. 12 (a) EDS mapping images of $\text{CeO}_2:\text{Nd}$. (b) Catalytic activity for the oxidation reaction of lanthanide-doped CeO_2 nanowires versus the radius of the dopants. (c) Oxygen vacancy formation energy of $\text{CeO}_2:\text{Ln}$. (d) Variation of IR intensity at 1454 (unidentate carbonates), 1577 (bidentate carbonates), and 1644 cm^{-1} (bicarbonates) with different dopants. Adapted with permission from ref. 35. Copyright 2013, American Chemical Society.

are beneficial for the catalytic activity. On the other hand, the concentration of the active intermediates of unidentate carbonates was also crucial for governing the activity, and Fig. 12d exhibits that $\text{CeO}_2:\text{Nd}$ had the largest amount of these active species. These two factors together resulted in the volcano-like relationship between the catalytic activity and the ionic radius of the dopant elements. Similarly, Li *et al.*⁷⁶ also demonstrated that doping with La remarkably enhanced the catalytic activity of CeO_2 for the CO oxidation reaction with a T_{50} of 245 °C because the formation of non-stoichiometric $\text{Ce}_{1-x}\text{La}_x\text{O}_{2-\delta}$ increased the formation of oxygen vacancies, and the optimal value of x is 0.5. Besides doping to boost the concentration of oxygen vacancies in rare earth oxides, reduction treatment is also a suitable method for obtaining higher activity for the CO oxidation reaction. As an example, Gao *et al.*¹² enhanced the activity of as-prepared CeO_2 nanorods *via* chemical redox etching with ascorbic acid.

According to the above examples, it can be concluded that single rare earth oxide nanocatalysts have limited activity for the CO oxidation reaction, and thus the introduction of other metals and engineering the local metal-support structure is a valid and common strategy for boosting their activity, in which rare earth oxide nanomaterials can act as a support.^{77–79} For example, our group⁷⁷ systematically investigated the effect of the local coordination structure of Pt/ CeO_2 nanocatalysts on their activity for CO oxidation. We prepared Pt/ CeO_2 catalysts with different Pt–O coordination numbers by tuning the reduction temperature of the samples. A decrease in the activity of the catalysts was observed with an increase in the Pt–O coordination number, and the most active sample had a TOF at 50 °C of $2.0 \times 10^{-2} \text{ s}^{-1}$. The Pt atoms were over-stabilized at the catalyst surface, resulting in the inactivation of

some of the Pt atoms when the Pt–O coordination number kept increasing, and thus the activity of the catalyst decreased. Specifically, it was the local structural effect that determined the catalytic performance. As another example, Huang *et al.*⁷⁸ prepared Pr_6O_{11} nanorods with a diameter of 20–40 nm and length of several microns using a hydrothermal method. They found that the pure Pr_6O_{11} nanorods were not active for CO oxidation until 220 °C. However, when they loaded gold nanoparticles with a size of 8–12 nm on the surface of the Pr_6O_{11} nanorods, the composites could achieve 100% CO conversion at 140 °C, and were also much more active than the Au/ Pr_6O_{11} bulk. Similarly, Zhang *et al.*⁷⁹ synthesized and studied nanostructured Ag/ Pr_6O_{11} for CO oxidation. The authors prepared Pr_6O_{11} nanorods and nanoparticles using different routes, and utilized them as supports to couple with Ag species *via* the conventional impregnation method (Fig. 13a). The XPS results indicated that the Ag/ Pr_6O_{11} nanorods possessed more oxygen vacancies than that of the Pr_6O_{11} nanoparticles (Fig. 13b). Besides, the H_2 -TPR profiles showed a stronger synergistic effect between Ag and Pr_6O_{11} in the Ag/ Pr_6O_{11} nanorods (Fig. 13c), suggesting higher activity for this catalyst. As expected, the Ag/ Pr_6O_{11} nanorods showed a better performance than the Ag/ Pr_6O_{11} nanoparticles for CO oxidation, where the T_{50} of the Ag/ Pr_6O_{11} nanorods was around 125 °C (Fig. 13d and e).

The well-known shape effect of rare earth oxide nanomaterials also has a vital influence on the catalytic activity for

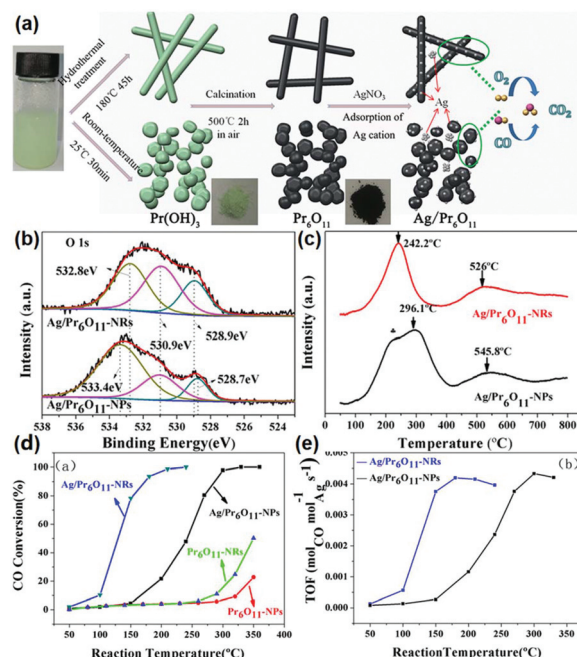


Fig. 13 (a) Schematic illustration of the synthetic routes for Pr_6O_{11} nanostructures. (b) O 1s XPS spectra of Ag/ Pr_6O_{11} catalysts. (c) H_2 -TPR profiles of Ag/ Pr_6O_{11} catalysts. (d) CO conversion of Pr_6O_{11} and Ag/ Pr_6O_{11} samples for CO oxidation. (e) TOF of Pr_6O_{11} and Ag/ Pr_6O_{11} samples for CO oxidation. Adapted with permission from ref. 79. Copyright 2017, American Chemical Society.

CO oxidation when they act as a support.^{80,81} Taking the work of Lykaki *et al.*⁸⁰ as an example, they prepared CeO₂ nanorods (NR), nanopolyhedra (NP), and nanocubes (NC) *via* the hydrothermal method, and explored the shape effect of Cu/CeO₂ on their catalytic properties. The results of the catalytic test showed that the activity (T_{50}) of both the pure CeO₂ and Cu/CeO₂ followed the same order of NR (320/72 °C) > NP (350/83 °C) > NC (385/92 °C). The authors used multiple characterizations to investigate the structure–function correlation, and found that the activity had a direct correlation with the amount of Cu⁺ and oxygen defects. They proposed the reaction mechanism based on the Mars-van Krevelen mechanism, which highlighted the significant roles of oxygen vacancies and Cu⁺ in this benchmark reaction. Furthermore, it is known that the shape effect is equal to the plane effect. Also, NR have mainly exposed {110} and {100} facets, while NP are enclosed with {111} and {100} facets, and NC have exposed {100} facets. Therefore, the CeO₂ {110} planes were beneficial for CO oxidation due to their easy generation of oxygen defects.

In general, the nanostructural engineering of rare earth oxide-based catalysts for the CO oxidation reaction is mainly focused on the tuning of oxygen vacancies, the effect of which mainly embodied in stabilizing the metal loading on the surface of the rare earth oxides and providing sites for the adsorption and activation of O₂. Also, the strategies for modulating oxygen vacancies usually involve reduction treatment, doping, controlling the size and morphology, *etc.* Besides, other factors such as the surface area and metallic oxidation state of the rare earth oxide-based catalysts also have a significant effect on the catalytic performance. Thus, researchers should consider all these factors in the design of catalysts with excellent properties for CO oxidation.

4.2 WGS

The WGS ($\text{CO} + \text{H}_2\text{O} \rightarrow \text{CO}_2 + \text{H}_2$) is mainly used for converting CO to CO₂ and H₂ in syngas, which has important application value in hydrogen production, fuel cells and ammonia synthesis.⁸² Most of the catalysts for the WGS are supported nanomaterials since single materials hardly exhibit activity. Rare earth oxide nanomaterials are widely used as a support for the WGS due to their good stability and abundant oxygen vacancies, which are significant for stabilizing the metal loading and activating H₂O molecules.^{83,84} Also, a good way for improving the catalytic performance is through tuning the morphologies of rare earth oxides since the shape effect is also important for the WGS.

Among the various catalytic systems, noble metals such as Au and Pt supported by well-defined rare earth oxide nanostructures have been extensively applied for the WGS because of their high activity and good stability.^{83–86} For example, Si *et al.*⁸⁷ investigated the catalytic performance of Au/CeO₂ with nanorod, nanocube and nanopolyhedra structures. They found that the WGS performance strongly depended on the exposed facets, and the sample of Au/CeO₂ nanorods showed the highest activity among the three samples. This could be explained by the lowest anion vacancy formation energy on the

{110} planes, which meant more oxygen vacancies boosted the catalytic activity. As another example, Fu *et al.*¹⁵ prepared two types of Au/CeO₂ catalysts, including Au nanoclusters (<2 nm) and Au nanoparticles (3–4 nm), for the WGS (Fig. 14a and b, respectively). Specially, the Au nanoclusters were *in situ* generated in the reaction process from Au single atoms. The Au nanoclusters showed higher activity (rate at 200 °C = $5.0 \times 10^2 \text{ mol g}_{\text{Au}}^{-1} \text{ s}^{-1}$) compared with that of the Au particles (rate at 200 °C = $1.0 \times 10^2 \text{ mol g}_{\text{Au}}^{-1} \text{ s}^{-1}$) because of their more abundant interfacial sites (Fig. 14c). The results of *in situ* Raman spectroscopy demonstrated that the oxygen vacancies were involved in the catalytic reaction, which were the most abundant in the Au_{cluster}/CeO_x sample (Fig. 14d). The authors also performed *in situ* infrared spectroscopy (IR) to investigate the reaction mechanism, and they found that the bridged surface –OH groups were essential for the conversion of the CO adsorbed on the Au^{δ+} species to CO₂, which was verified by the isotopic labelling experiment, where one of the O atoms in CO₂ came from the bridged –OH group (Fig. 14e). Fig. 14f shows the whole cycle of the catalytic process, where H₂O was activated at the oxygen vacancy and generated a bridged –OH group in the first stage, then the bridged –OH group reacted with the CO adsorbed on the Au^{δ+} species to produce CO₂ in the second stage, and finally the CO₂ desorbed and left a new oxygen vacancy. The moderate Au^{δ+} species, bridged –OH group and oxygen vacancies were essential in the WGS.

The use of non-Ce rare earth oxides for supporting noble metals has been less applied in the WGS compared with CeO₂. For instance, novel Au/La₂O₃ and Au/La₂O₂SO₄ catalysts for the low-temperature WGS were synthesized by Lessard *et al.*¹³ through an anion adsorption method. They found that both Au/La₂O₃ and Au/La₂O₂SO₄ had a good WGS activity, and Au/La₂O₂SO₄ showed higher activity compared with that of Au/La₂O₃ which may be because of its higher content of Au³⁺, as confirmed by the X-ray photoelectron spectroscopy (XPS) results. Besides, the authors carried out chemical leaching of the catalysts using NaCN, and the leached samples exhibited no difference in activity, indicating that the support of La₂O₃ and La₂O₂SO₄ could well stabilize the Au species. Besides, Pt supported by a composite oxide of Ce_{0.6}Y_{0.4}O₂ for the WGS was obtained by Lee *et al.*⁸⁶ *via* a sol–gel method. As can be seen in Fig. 15a, the activity of Pt/Ce_{0.6}Y_{0.4}O₂ (TOF at 250 °C = $5.5 \times 10^{-1} \text{ s}^{-1}$) was much higher than that of both Pt/CeO₂ (TOF at 250 °C = $1.6 \times 10^{-1} \text{ s}^{-1}$) and Pt/Y₂O₃ (TOF at 250 °C = $1.3 \times 10^{-1} \text{ s}^{-1}$), and also higher than that of many reported Pt-based WGS catalysts. The H₂-TPR results (Fig. 15b) showed that the introduction of Y to CeO₂ obviously enhanced the reducibility and the oxygen mobility of the support. Furthermore, the CO-TPR profiles indicated that there were much more OH species in the Pt/Ce_{0.6}Y_{0.4}O₂ sample than the other two catalysts (Fig. 15c and d), which are beneficial for the WGS. The authors also performed diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS) to explore the surface reactions on these catalysts (Fig. 15e). The results clearly showed that the CO adsorption on Pt//Ce_{0.6}Y_{0.4}O₂ was weaker than that on Pt/CeO₂ and Pt/Y₂O₃, indicating its more

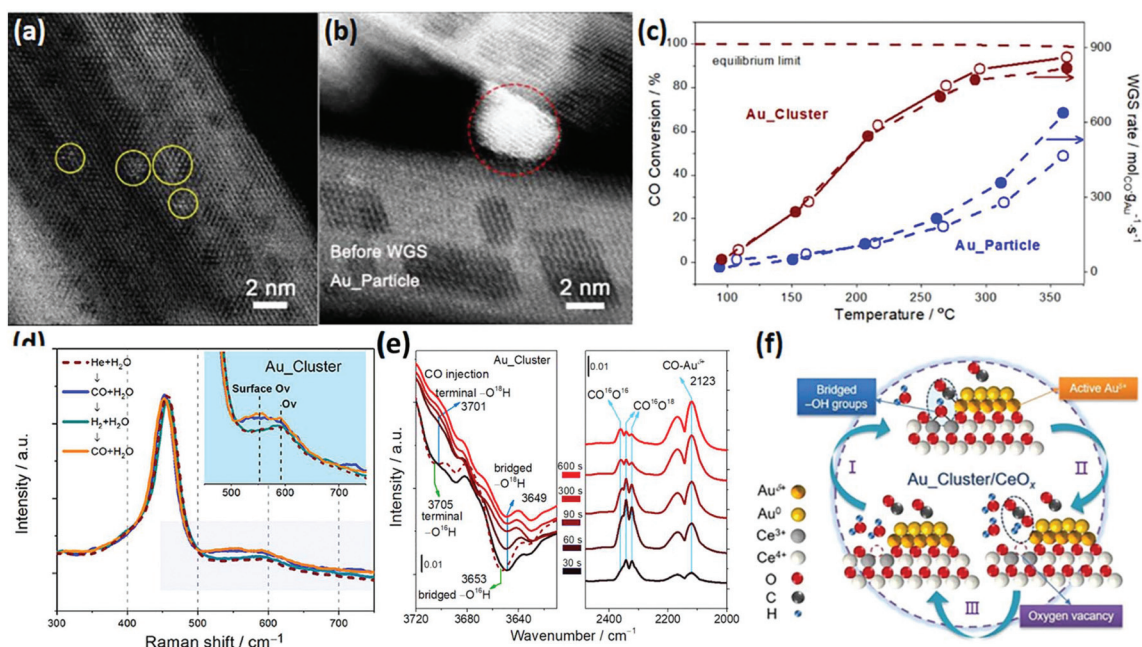


Fig. 14 High-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) images of (a) Au_{cluster}/CeO_x and (b) Au_{particle}/CeO_x catalyst. (c) Catalytic activity for the WGSR by the Au_{cluster}/CeO_x and Au_{particle}/CeO_x catalysts. (d) *In situ* Raman spectra of Au_{cluster}/CeO_x under different atmospheres at 150 °C. (e) *In situ* time-sequencing IR spectra of Au_{cluster}/CeO_x under CO injection with isotope prelabelled using H₂O¹⁸. (f) Schematic illustration of the reaction mechanism of Au_{cluster}/CeO_x catalyst for the WGSR. Adapted with permission from ref. 15. Copyright 2019, American Chemical Society.

efficient activation of CO. In general, the enhanced reducibility of the support and reduced CO adsorption contributed to the higher activity.

Although supported noble catalysts have superior catalytic properties for the WGSR, their high price limits their large-scale application. Accordingly, nowadays, many researchers aim to use a base metal in the nanostructural engineering of catalysts to obtain high performances for the WGSR.^{88–90} For instance, Ren *et al.*⁴⁹ studied the plane effect on the activity of Cu/CeO₂ catalysts for the WGSR. The results showed that the Cu catalysts supported on CeO₂ nanooctahedra with {111} facets were more active than that of supported on nanorods and nanocubes, which could be attributed to the best dispersion of Cu, strongest Cu–CeO₂ interactions and the largest amount of Cu species with a moderate valence. She *et al.*⁸⁸ studied the doping effect of RE₂O₃ (RE = Y, La, Sm, Nd) on the WGSR activity of CuO/CeO₂ catalysts. The evaluation of their catalytic performance showed that the introduction of La₂O₃ and Nd₂O₃ was beneficial for enhancing the activity and stability of CuO/CeO₂, but the doping of Y₂O₃ and Sm₂O₃ exhibited negative effects. The Raman spectra showed that the CuO/CeO₂–La₂O₃ and CuO/CeO₂–Nd₂O₃ samples had more oxygen vacancies than CuO/CeO₂, while that of the Y and Sm-doped samples were less. Besides, the authors measured the Cu dispersion using N₂O and found out that the order of Cu dispersion was consistent with the order of activity. The H₂-TPR results showed three peaks for non-crystalline copper oxide, moderate copper oxide (crystalline) and surface ceria.

Interestingly, the order of the peak area for moderate copper oxide was also consistent with that of activity. In summary, the difference in activity mainly originated from the concentration of oxygen vacancies, Cu dispersion, and moderate Cu valence. Another Cu/CeO₂ catalyst for the WGSR was synthesized by Chen *et al.*⁸⁹ using a co-precipitation method. In order to improve the activity, the authors attempted to calcine the catalyst at 300 °C in air, vacuum and H₂. They found that the catalyst annealed in H₂ had the highest performance due to the highest amount of oxygen vacancies and strongest synergistic interaction between CuO and CeO₂.

Based on the research thus far, it can be concluded that rare earth oxide nanomaterials are rarely used alone for the WGSR on account of their weak adsorption of CO. They are always used as a support and additive to improve the catalytic performance through the construction of well-defined structures and controlling the electronic and geometric structure of the catalysts. The effects of rare earth oxide nanomaterials are mainly reflected in dispersing metal catalysts, providing active sites such as oxygen vacancies and enhancing the metal support interaction and synergistic effect.

4.3 CO₂ hydrogenation reaction

The CO₂ hydrogenation reaction is not a specific reaction since it has several possible products, such as CO, methane and methanol. It is a significant reaction because it not only can weaken the greenhouse effect, but also ease the energy crisis.⁹¹ However, the high chemical stability of the CO₂ molecule and

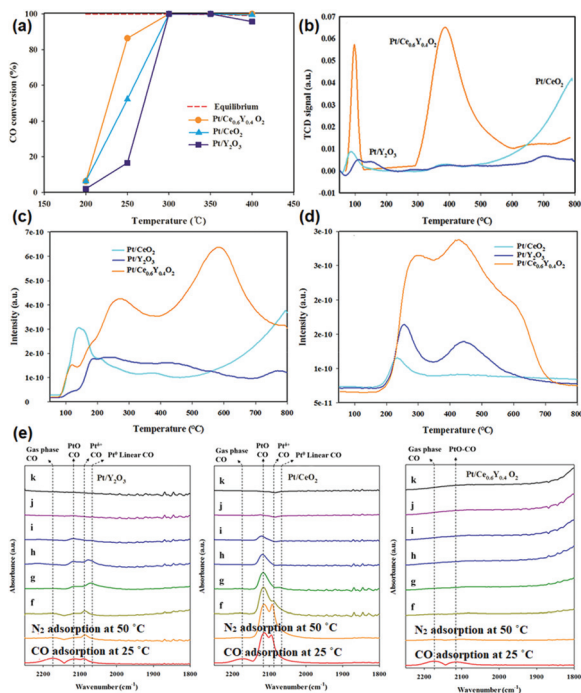


Fig. 15 (a) CO conversion of Pt/Y₂O₃, Pt/CeO₂ and Pt/Ce_{0.6}Y_{0.4}O₂ in the WGS. (b) H₂-TPR profiles of Pt/Y₂O₃, Pt/CeO₂ and Pt/Ce_{0.6}Y_{0.4}O₂. (c) CO-TPR profiles of Pt/Y₂O₃, Pt/CeO₂ and Pt/Ce_{0.6}Y_{0.4}O₂. (d) H₂ profile. (e) DRIFTS spectra of Pt/Y₂O₃, Pt/CeO₂ and Pt/Ce_{0.6}Y_{0.4}O₂: (f) N₂ adsorption at 100 °C; (g) N₂ adsorption at 150 °C; (h) N₂ adsorption at 200 °C; (i) N₂ adsorption at 250 °C; (j) N₂ adsorption at 300 °C; and (k) N₂ adsorption at 350 °C. Adapted with permission from ref. 86. Copyright 2018, American Chemical Society.

the complexity of its products are a big challenge for catalysts for this reaction. The abundant electronic structures and flexible oxidation states of rare earth oxide nanomaterials are beneficial for the CO₂ hydrogenation reaction, which is ascribed to their facile activation of CO₂ and selectivity control.⁹² Nevertheless, pure rare earth oxides are less used for catalyzing this reaction due to their poor activity. Here, we summarize the nanostructural engineering of rare earth oxide nanomaterials utilized in the CO₂ hydrogenation reaction according to the different products.

The CO₂ hydrogenation reaction is also known as the reverse water gas shift (RWGS) reaction (CO₂ + H₂ → CO + H₂O) when the product is CO and H₂O. The morphologies of rare earth oxides have a significant influence on their catalytic performance.^{93,94} As an example, CeO₂ nanocatalysts with different morphologies synthesized by Dai *et al.*⁹³ using various methods showed extremely different activities for the RWGS reaction. CeO₂ with a 3D porous structure was much more active than the loosely aggregated CeO₂ nanoparticles and bulk CeO₂ due to its largest surface area and oxygen vacancy concentration. As another example, Lin *et al.*⁹⁴ prepared Cu/CeO₂ nanorods and Cu/CeO₂ nanospheres and investigated their catalytic performance for the CO₂ hydrogenation reaction. They found that both catalysts mainly produced CO

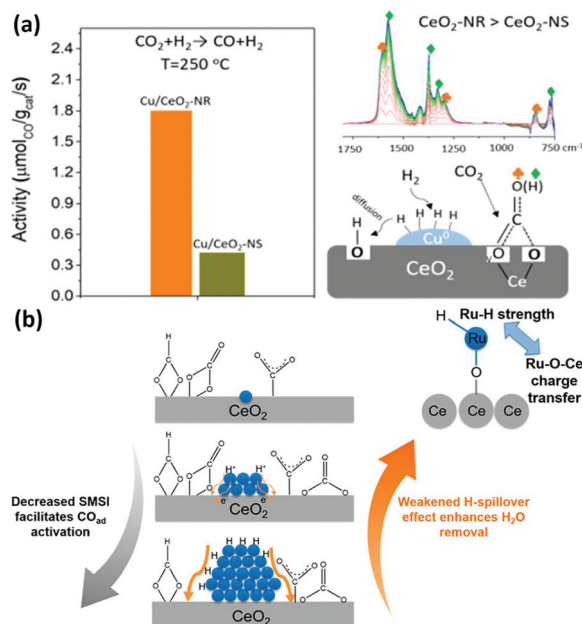


Fig. 16 (a) Activity and schematic illustration of the mechanism of the RWGS reaction for Cu/CeO₂ nanorods and Cu/CeO₂ nanospheres. Adapted with permission from ref. 94. Copyright 2018, American Chemical Society. (b) Schematic illustration of the complete effect between SMSI and H-spillover on Ru/CeO₂ catalysts for the CO₂ methanation reaction. Adapted with permission from ref. 96. Copyright 2018, American Chemical Society.

through the RWGS reaction and the Cu/CeO₂ nanorods exhibited higher activity (rate at 250 °C = 1.8 μmol g_{cat}⁻¹ s⁻¹) (Fig. 16a). The results of multiple *in situ* characterizations showed that the active intermediates of formates and bidentate carbonates were preferentially generated on the CeO₂ {110} facet and CO₂ could also be activated and dissociated more effectively on the CeO₂ {110} facets. Consequently, the Cu/CeO₂ nanorods with more abundant {110} terminations were more active, indicating that researchers can design high-performance CeO₂-based catalysts by engineering their structure. Additionally, Liu *et al.*⁹⁵ synthesized LaNiO₃ perovskite catalysts and tested them for the RWGS reaction in a dielectric barrier discharge plasma reactor. After reduction, the Ni species were extracted from the perovskite structure, and the Ni/La₂O₃ catalysts were thus formed. The highest CO yield among these catalysts was 39.1% at around 100 °C. The activity was closely correlated with the Ni particle size, Ni dispersion and metal-support interactions.

The CO₂ methanation reaction (CO₂ + H₂ → CH₄ + H₂O) is one of the CO₂ hydrogenation reactions and its product is methane. Although this reaction is thermodynamically preferred, the 8-electron reduction process is a big hindrance for obtaining high activity and selectivity. Thus, engineering the morphologies of rare earth oxides to obtain well-defined structures is beneficial to solve this problem. For example, our group⁹⁶ synthesized three types of catalysts containing Ru single atoms, nanoclusters and nanoparticles supported by

CeO₂ nanowires for the CO₂ methanation reaction. We found that the sample of Ru nanoclusters showed the highest activity (TOF at 190 °C = $7.4 \times 10^{-3} \text{ s}^{-1}$), which was also much higher than that of other reported Ru/CeO₂ catalysts. Unexpectedly, the order of activity was not consistent with that of the concentration of oxygen vacancies. According to our investigation, the strong metal support interaction (SMSI) decreased with an increase in the Ru size and benefited the activation of adsorbed CO species, while the H-spillover effect weakened with a decrease in the Ru size and facilitated the removal of H₂O. Accordingly, the competition between the SMSI and H-spillover effect together determined the activity of the Ru/CeO₂ catalysts (Fig. 16b). In the case of other rare earth oxides used in CO₂ methanation, Ilsemann *et al.*⁹⁷ obtained novel Sm₂O₃-Ni xerogel catalysts through the sol-gel method for the CO₂ methanation reaction. The optimal loading of Ni was 39 wt%, which showed the highest activity. Also, the catalysts had a good score in the stability test, and their activity could easily recover by a reduction treatment. Díez-Ramírez *et al.*⁹⁸ studied the effect of different supports (CeO₂, ZrO₂, Gd₂O₃, and ZnO) on the activity of Co catalysts for the CO₂ methanation reaction. The methane yield of Co/CeO₂ was much higher than that of the other catalysts due to the enhanced reducibility related with Co-CeO₂ interactions.

The selective hydrogenation of CO₂ to methanol has attracted increasing attention in recent years because methanol is an important basic chemical in many chemical industries.⁹⁹⁻¹⁰² Chen *et al.*¹⁰³ synthesized rod-like La₂O₂CO₃ through a facile hydrothermal method (Fig. 17a) and used it as a support for Cu catalysts (denoted as Cu/La₂O₂CO₃-R) in the CO₂ hydrogenation to methanol. They also prepared Cu supported by amorphous La₂O₂CO₃ (denoted as Cu/La₂O₂CO₃-A), Cu supported by rod-like CeO₂ (denoted as Cu/CeO₂) and a co-precipitation catalyst of CuLa_xO_y (denoted as CuLa_xO_y-CP) for comparison. The Cu/La₂O₂CO₃-R catalyst had a much better catalytic performance (TOF at 240 °C = $7.0 \times 10^{-3} \text{ s}^{-1}$, selectivity = 92.5%) compared with the control samples and commercial CuZnAl catalyst (TOF at 240 °C = $4.0 \times 10^{-3} \text{ s}^{-1}$, selectivity = 68%) (Fig. 17b). The CO₂ temperature-programmed desorption (TPD) results (Fig. 17c) showed that Cu/La₂O₂CO₃-R had a stronger and larger amount of CO₂ adsorption, indicating that it could activate CO₂ more efficiently. Besides, the order of the Cu^{δ+} ratio was consistent with that of the activity, as can be seen in Fig. 17d, which suggested that Cu^{δ+} species were the active sites. The authors also performed *in situ* DRIFTS to reveal the reaction mechanism, and they found that the HCOO and CH₃O species were the main active intermediates (Fig. 17e), which were stable on the catalyst surface and not easy transformed into CO. In brief, it was the synergistic basic sites of the Cu^{δ+} species tuned by the structure of the metal-support interface that contributed to the high activity. Some groups used rare earth oxide as promoters to adjust the catalyst structure for CO₂ hydrogenation to methanol and obtained positive results.^{104,105} For instance, Ban *et al.*¹⁰⁴ verified that the using of La and Ce as promoters boosted the methanol production of CuZnZr catalyst, especially Ce. However, the

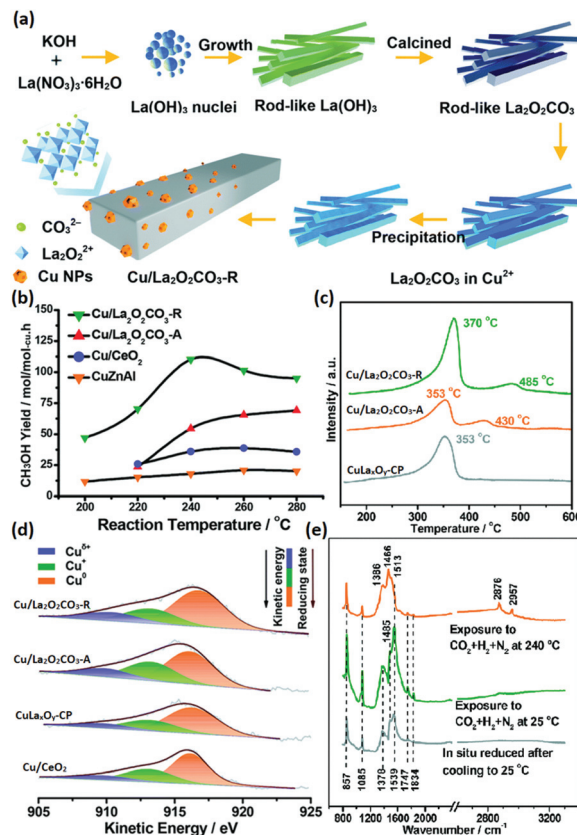


Fig. 17 (a) Schematic illustration of the synthetic route for Cu/La₂O₂CO₃-R. (b) CH₃OH yield of the catalysts for CO₂ hydrogenation to methanol. (c) CO₂-TPD profiles of Cu/La₂O₂CO₃-R, Cu/La₂O₂CO₃-A, and CuLa_xO_y-CP. (d) Cu LMM Auger spectra of Cu/La₂O₂CO₃-R, Cu/La₂O₂CO₃-A, CuLa_xO_y-CP, and Cu/CeO₂. (e) *In situ* DRIFTS spectra of Cu/La₂O₂CO₃-R under different conditions. Adapted with permission from ref. 103. Copyright 2018, Royal Society of Chemistry.

introduction of Pr and Nd as additives decreased the activity. The opposite effect of the different rare earth promoters on activity was mainly due to the enhanced synergistic effect and H₂ adsorption caused by the addition of La and Ce, which were not found in the catalysts with Pr and Nd as additives. Similarly, Kourtelesis *et al.*¹⁰⁵ found that La₂O₃ could promote 30% of the methanol yield for the CuO/ZnO/Al₂O₃ catalyst. La₂O₃ could be facilely introduced by a co-precipitation method, and the enhanced methanol yield could be attributed to enhanced adsorption of CO₂ and active intermediates.

Considering the complexity of the product of the CO₂ hydrogenation reaction, the choice and design of catalysts must be based on selectivity and avoiding side reactions. Thus, reasonably engineering catalysts with well-defined structures is vital. Based on the reported works, using rare earth oxide nanomaterials in the CO₂ hydrogenation reaction as support or promoter can usually enhance the adsorption of CO₂ and metal support interactions, which will result in improved activity and selectivity.

4.4 Methane oxidation reaction

Methane is an important resource due to its applications such as fuel and chemical synthesis. The methane oxidation reaction can be divided into two types, total oxidation and partial oxidation. The total oxidation of methane can be used for energy and heat production or solving the global warming caused by methane.^{106,107} The partial oxidation of methane can produce the syngas for further utilization.^{108–110} Rare earth oxide nanomaterials are widely applied in both reactions^{111–118} as supports or promoters.

In the total oxidation of methane, CeO₂ is often used as a catalyst support on account of its high concentration of oxygen vacancies.^{111,112} Also, the well-defined structures of CeO₂-based catalysts are conducive for catalytic activity. For instance, Co₃O₄ nanoparticles supported by CeO₂ nanorods (Fig. 18a and b) for methane combustion were synthesized by Dou *et al.*¹¹¹ using a deposition precipitation method. The catalyst of Co₃O₄/CeO₂ ($T_{50} = 475$ °C) was found to be much more active than pure Co₃O₄ and CeO₂ due to the synergistic effect between Co₃O₄ and CeO₂, and also the activation energy, which was also much lower in the case of Co₃O₄/CeO₂ (Fig. 18c and d). Pd-based nanomaterials are some of the most effective catalysts for the total oxidation of methane, and using rare earth oxides as a support can be further beneficial due to their unique redox properties. As an example, Ozawa *et al.*¹¹³ tested

the influence of the addition of La₂O₃ and Nd₂O₃ to PdO/Al₂O₃ for the combustion of methane. They found that adding La₂O₃ or Nd₂O₃ alone had an effect of stabilizing Al₂O₃ and enhancing the activity. However, when the authors introduced both La₂O₃ and Nd₂O₃ to PdO/Al₂O₃, they observed reduced activity and an extended lifetime. Besides, this group also investigated the stabilizing effect of La₂O₃, Nd₂O₃, and ZrO₂ on PtPdO/Al₂O₃ for methane combustion.¹¹⁴ Similarly, the introduction of both La₂O₃ and Nd₂O₃ prevented the deactivation of the catalyst, but the addition of ZrO₂ caused deactivation. Also, the addition of all three oxides resulted in the longest lifetime among the catalysts. As another example, Danielis *et al.*¹¹⁵ prepared Pd-embedded CeO₂ catalysts *via* a dry ball-milling method. The Pd–CeO₂ catalysts showed a core–shell structure, in which the shell consisted of Pd and CeO₂. The as-prepared catalyst could activate methane at a much lower temperature ($T_{10} = 291$ °C) compared with that with the conventional Pd/CeO₂ catalyst ($T_{10} = 346$ °C) synthesized by impregnation (Fig. 18e). The superior performance was ascribed to the creation of highly active and stable sites due to the robust contact between Pd and CeO₂.

In the partial oxidation of methane reaction, 1D rare earth oxide nanostructures are often used. For instance, Zhu *et al.*¹¹⁹ prepared a core–shell Ni/nanorod-CeO₂@SiO₂ catalyst using a microemulsion method. The as-prepared catalyst showed better activity and stability than that of Ni/nanorod-CeO₂ and Ni@SiO₂, benefitting from the greater amount of oxygen vacancies and stronger anti-sintering of Ni particles derived from the enhanced metal–support interactions. Even after testing at 750 °C for 140 h, the catalyst maintained a CH₄ conversion of 86% and CO selectivity of 94%. Besides, Ru nanoparticles supported over Ce_{0.5}Zr_{0.5}O₂ nanorods obtained by Das *et al.*¹²⁰ were proven to be more active than Ru/CeO₂ and Ru/ZrO₂. Specifically, the stronger metal–support interactions and higher oxygen storage capacity of the CeO₂–ZrO₂ solid solution contributed to the increased catalytic performance. Innovatively, Singha *et al.*¹¹⁸ reported 3D Pt–CeO₂ nanoporous spheres with a bimodal pore structure for the partial oxidation of methane. The unique bimodal pore structure was confirmed by an N₂-adsorption study, which resulted in a high surface area. The as-prepared Pt–CeO₂ catalysts were highly active and selective for the production of syngas (TOF at 400 °C = 1.3×10^3 s⁻¹, CO selectivity = 50.0%). Briefly, the unique bimodal pore structure resulted in a high surface area and metal–support interactions as well as abundant oxygen vacancies, contributing to the superior catalytic performance for the partial oxidation of methane to produce syngas.

In the case of other rare earth oxides used in the partial oxidation of methane besides CeO₂, Ferreira *et al.*¹¹⁶ tested the catalytic performance of LnNi (Ln = Pr, Gd, Lu) binary oxides. They found that NiO–Gd₂O₃ and NiO–Lu₂O₃ exhibited much higher activity than that of NiO–Pr₂O₃, which was even comparable with that of the commercial 5% Pt/Al₂O₃ catalyst. The authors believed that there was an unusual synergistic effect between the two oxides, resulting in high activity and selecti-

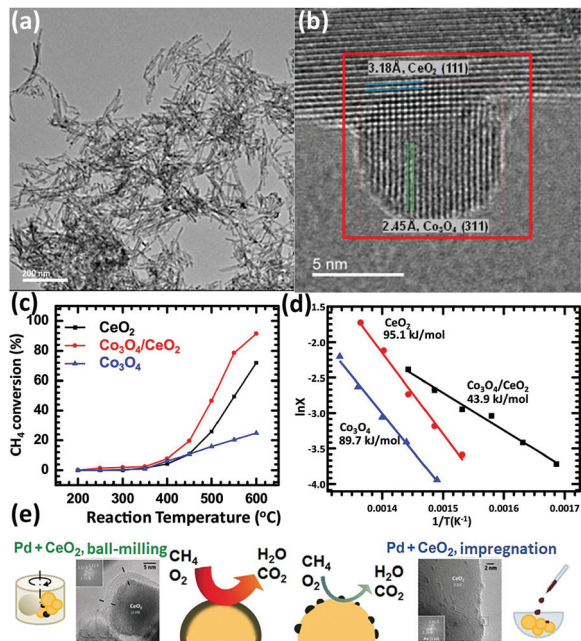


Fig. 18 (a) TEM image of CeO₂ nanorods. (b) HRTEM image of Co₃O₄/CeO₂ nanocomposite. (c) Catalytic activity of CeO₂, Co₃O₄ and Co₃O₄/CeO₂ for methane combustion. (d) Arrhenius plots and corresponding activation energy of CeO₂, Co₃O₄ and Co₃O₄/CeO₂. Adapted with permission from ref. 111. Copyright 2018, Elsevier. (e) Schematic illustration of the preparation method, catalyst morphology and catalytic activity for the methane combustion reaction using Pd/CeO₂ catalysts. Adapted with permission from ref. 115. Copyright 2018, Wiley-VCH.

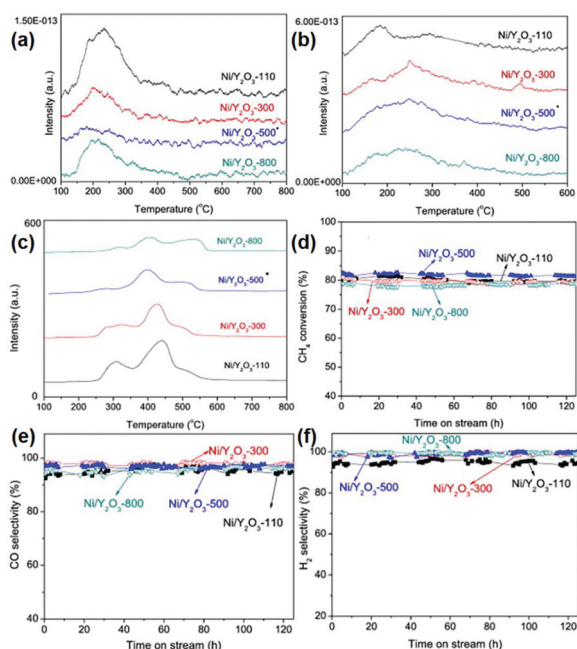


Fig. 19 (a) NH_3 -TPD profiles of the $\text{Ni}/\text{Y}_2\text{O}_3$ samples. (b) CO_2 -TPD profiles of the $\text{Ni}/\text{Y}_2\text{O}_3$ samples. (c) TPR profiles of the $\text{Ni}/\text{Y}_2\text{O}_3$ samples. Catalytic performance of the $\text{Ni}/\text{Y}_2\text{O}_3$ samples in the partial oxidation of methane: (d) CH_4 conversion; (e) CO selectivity; and (f) H_2 selectivity. Adapted with permission from ref. 117. Copyright 2014, Elsevier.

activity for H_2 and CO. Similarly, Liu *et al.*¹¹⁷ developed another Ni-based catalyst, $\text{Ni}/\text{Y}_2\text{O}_3$, for methane oxidation conversion to syngas. They controlled the structural effect by tuning the calcination temperature of the catalysts (Fig. 19a–c), and showed that $\text{Ni}/\text{Y}_2\text{O}_3$ calcined at 500 °C had the highest activity and high anti-carbon deposition ability (Fig. 19d–f). All the $\text{Ni}/\text{Y}_2\text{O}_3$ catalysts showed an extremely low signal in the NH_3 -TPD profiles (Fig. 19a) because Y_2O_3 was a basic oxide. Also, the amount of basic sites and reducible oxygen decreased with an increase in the calcination temperature (Fig. 19b and c). The reason for the highest activity of $\text{Ni}/\text{Y}_2\text{O}_3$ -500 was its appropriate amount of reducible oxygen and moderate interaction between Ni and Y_2O_3 , and both factors were controlled by the calcination temperature. Importantly, Choudhary *et al.*¹²¹ studied the catalytic properties of Pt- and Pd-based alkaline and rare earth oxide catalysts for the partial oxidation of methane. Among the Pt (Pd)/MgO (CaO, La_2O_3 , Pr_6O_{11} , Nd_2O_3 , Sm_2O_3 , Gd_2O_3 , Dy_2O_3 , and Er_2O_3) catalysts, Pt/ Gd_2O_3 and Pd/ Sm_2O_3 showed the best performance with a CO productivity of 9.5 and 7.9 mol g^{-1} h^{-1} , respectively. Besides, both catalysts had high CO selectivity but low H_2 selectivity due to the RWGS reaction. These results also indicated that the rare earth oxides not only acted as supports, but also played an essential role in deciding the activity and selectivity.

In many cases, the total and partial oxidation of methane occurs simultaneously; therefore, it is a challenge to control the product selectivity. Different rare earth oxide nanomaterials may have different preferences towards the two reactions. Thus, researchers can realize diverse goals by choosing

suitable rare earth oxides with designed well-defined structures as a support or promotor.

4.5 MOR

The MOR discussed below refers to the anode reaction of direct methanol fuel cells (DMFCs), which is very important for alleviating the energy crisis since it can directly transform chemical energy to electrical energy.^{122–125} Besides, methanol has a high energy density and is easier to store and transport compared with hydrogen. The catalytic application of rare earth oxide nanomaterials in the MOR is not as extensive as in other C1 chemical reactions such as the CO oxidation and CO_2 hydrogenation reactions because of their weak conductivity. Although it is difficult for rare earth oxide nanomaterials to be used as a single catalyst in MOR, there are many cases that combine rare earth oxide nanomaterials with other well-conducting catalysts for the MOR.^{126–133} This not only can enhance the electronic metal support interactions, but also tune the chemical adsorption of the reactants and intermediates. As an example, Li *et al.*¹²⁶ studied the introduction of Y_2O_3 on the MOR activity of the Pd/C catalyst. A 1.5 times higher specific activity ($\text{SA} = 145 \text{ mA cm}^{-2}$) was observed with the assistance of Y_2O_3 due to the relatively well-dispersed Pd nanoparticles, enhanced electrochemically active surface area and the synergistic interaction between Pd and Y_2O_3 .

In the case that the role of rare earth oxides is a promotor in the MOR, a well-defined structure can also have a positive influence on the catalytic performance. As a good example, Feng *et al.*³³ synthesized three types of well-defined CeO_2 nanostructures containing nanooctahedra, nanospheres and nanocubes as promotors for Pt catalysts. Consequently, the Pt catalyst decorated with CeO_2 nanospheres exhibited the best performance in both activity and stability. The explanation for the enhanced activity could be divided into two parts. One was that the loosened structure of nanospheres was beneficial for the dispersion of Pt particles, thus generating a strong physical interaction between Pt and CeO_2 . The other was the oxygen vacancies, which were the most abundant in the nanospheres. The rich oxygen vacancies led to the transfer of surplus electrons from CeO_2 to Pt, and thereby increased the intrinsic activity of Pt. Besides, Wang *et al.*¹²⁹ investigated the effect of the introduction of La_2O_3 in the Pd/C catalyst for the MOR. As can be seen in Fig. 20a, the Pd nanoparticles (*ca.* 2.6 nm) were uniform and well dispersed. Compared with the Pd/C catalyst, Pd- La_2O_3 /C exhibited a lower onset potential and higher current density (Fig. 20b). The XPS results indicated that the introduction of La_2O_3 resulted in the formation of more metallic Pd species (Fig. 20c and d), resulting in enhanced activity. Furthermore, the authors loaded Pd- La_2O_3 on chitosan-functionalized carbon nanotubes and obtained a better performance than that with Pd- La_2O_3 /C. In addition, a 3D core-shell nanocatalyst of $\text{Au}@\text{CeO}_2@\text{Pt}/\text{C}$ for the MOR was obtained by Dao *et al.*¹³⁰ through a facile hydrothermal route. The as-prepared catalyst showed much higher activity ($\text{MA} = 1360 \text{ mA mg}_{\text{Pt}}^{-1}$) and durability than that of commercial Pt/C ($\text{MA} = 670 \text{ mA mg}_{\text{Pt}}^{-1}$) and $\text{CeO}_2@\text{Pt}/\text{C}$ ($\text{MA} = 920 \text{ mA mg}_{\text{Pt}}^{-1}$) owing



Fig. 20 (a) TEM image of Pd–La₂O₃/C. (b) Cyclic voltammograms of Pd/C and Pd–La₂O₃/C in 1 M KOH + 1 M CH₃OH. XPS spectra of Pd 3d for (c) Pd/C and (d) Pd–La₂O₃/C. Adapted with permission from ref. 129 Copyright 2019, Elsevier. (e) Schematic illustration of the possible mechanism of Au@CeO₂@Pt/C for the MOR. Adapted with permission from ref. 130. Copyright 2019, Royal Society of Chemistry.

to the electronic and synergistic effects among Au, CeO₂ and Pt, which could easily remove the poisoner of CO intermediates (Fig. 20e).

When rare earth oxides are used as a support in the MOR, efforts must be made to improve their conductivity. For example, CeO₂ nanorod-supported Pt catalysts were prepared by Tao *et al.*¹³¹ and used for the MOR. They used plasma etching of the CeO₂ nanorods to modify the surface structure of the CeO₂ support (denoted as CeO₂-P), and used the untreated CeO₂ as a comparison sample (Fig. 21a). The authors found that the abundant oxygen vacancies in Pt/CeO₂-P played a significant role in the enhanced activity (MA = 714 mA mg_{Pt}⁻¹) and stability compared with the sample without plasma etching (MA = 164 mA mg_{Pt}⁻¹) (Fig. 21b and c), which influenced the interactions between Pt and CeO₂ and enriched the electronic density of Pt, resulting in the enhanced conductivity of CeO₂ and MOR activity. As another example, Tang *et al.*¹³³ combined the rare earth oxides of Pr and Ce with carbon black to support Pt species for the MOR. They found that the introduction of Pr₂O₃ and CeO₂ significantly improved the catalytic performance (Fig. 21d and e), and the ratio of Pr/Ce had a crucial effect on the activity. According to their observations, Pt/Pr₁Ce₁O₂-C exhibited the highest activity (SA = 118.3 mA cm⁻²) and best stability among the samples. The

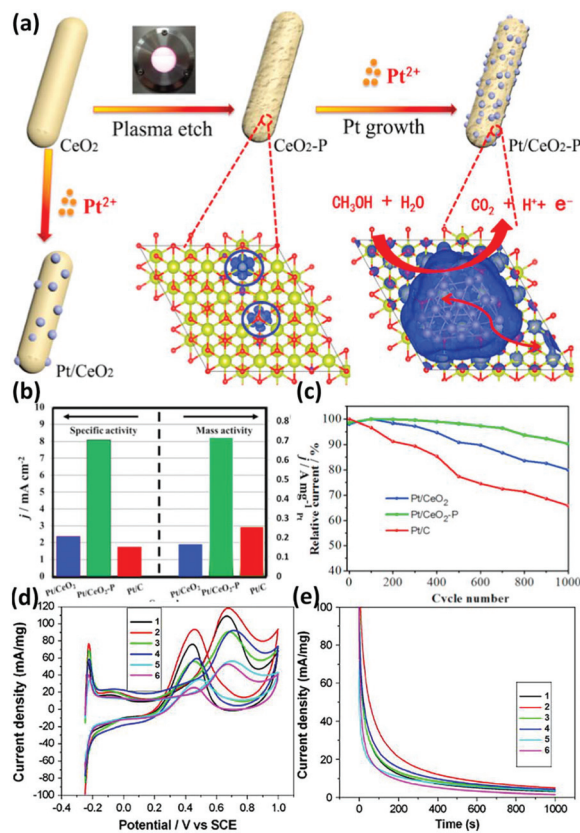


Fig. 21 (a) Schematic illustration of the mechanism of the Pt/CeO₂ catalyst for the MOR. (b) Mass activity and specific activity for the MOR. (c) Stability test for the MOR. Adapted with permission from ref. 131. Copyright 2018, Elsevier. (d) Cyclic voltammograms and (e) chronoamperometry curves at 0.65 V (vs. SCE) for Pt/C and Pt/RE-C catalysts: Sample 1, Pt/Pr₃Ce₁O₂-C; Sample 2, Pt/Pr₁Ce₁O₂-C; Sample 3, Pt/Pr₁Ce₃O₂-C; Sample 4, Pt₃/PrO_x-C; Sample 5, Pt₃/CeO_x-C; and Sample 6, Pt/C. Adapted with permission from ref. 133. Copyright 2008, Elsevier.

abundant surface oxygen-containing species as well as the high oxygen mobility derived from Pr₂O₃ and CeO₂ contributed to the enhanced CO-tolerance and catalytic performance.

In summary, although rare earth oxide nanomaterials have poor conductivity, which limits their activity for the MOR, they are widely used as a promotor or support for the rational engineering of their structures in the MOR since they can enrich the electronic density and improve the CO tolerance through electronic and synergistic effects.

5. Summary and perspective

In this review, we introduced the structural features of the rare earth oxides and summarized the engineering of rare earth oxide nanomaterials with well-defined structures mainly considering their morphology. Then we chose some representative C1 chemical reactions including CO oxidation, water gas-shift reaction, CO₂ hydrogenation reaction, methane oxidation reaction and methanol oxidation reaction to summarize the struc-

Table 1 The synthesis and applications of rare earth oxide-based nanocatalysts for some C1 chemical reactions

Catalyst	Synthetic route	Application	Conditions	Performance	Key factors in catalysis	Ref.
Ln-Doped CeO ₂ nanowires (Ln = La-Lu)	Hydrothermal method	CO oxidation reaction	1% CO-20% O ₂ -He Total speed: 40 mL min ⁻¹	TOF at 200 °C = 5.4 × 10 ⁻⁴ s ⁻¹	Doping effect	35
Pr ₆ O ₁₁	Hard template method	CO oxidation reaction	1% CO-20% O ₂ -N ₂ SV = 10 000 mL g ⁻¹ h ⁻¹	T ₅₀ = 305 °C	Surface area	75
Tb ₄ O ₇	Hard template method	CO oxidation reaction	1% CO-20% O ₂ -N ₂ SV = 10 000 mL g ⁻¹ h ⁻¹	T ₅₀ = 360 °C	Surface area	75
PtO _x nanoclusters/ CeO ₂	Hydrothermal method	CO oxidation reaction	13.3% CO-33.3% O ₂ - 53.3% He Total speed: 15 mL min ⁻¹	TOF at 50 °C = 1.3 × 10 ⁻² s ⁻¹	Oxygen vacancy Suitable Pt-O coordination number	77
Au/Pr ₆ O ₁₁ nanorods	Hydrothermal method	CO oxidation reaction	1% CO-Air Total speed: 33.6 mL min ⁻¹	T ₁₀₀ = 140 °C	Synergistic effect	78
Ag/Pr ₆ O ₁₁ nanorods	Hydrothermal method	CO oxidation reaction	1% CO-20% O ₂ -Ar Total speed: 50 mL min ⁻¹	T ₁₀₀ = 210 °C	Surface area Oxygen vacancy	79
Au/CeO ₂ nanorods	Hydrothermal method	WGS	2% CO-10% H ₂ O-He Total speed: 70 mL min ⁻¹	T ₅₀ ~ 190 °C	Plane effect	87
Au nanoclusters/ CeO ₂	Hydrothermal method	WGS	2% CO-12% H ₂ O-N ₂ Total speed: 30 mL min ⁻¹	Rate at 200 °C ~ 5.0 × 10 ² mol g _{Au} ⁻¹ s ⁻¹	Bridged -OH and Au ^{δ+}	15
Pt/Ce _{0.6} Y _{0.4} O ₂	Sol-gel method	WGS	5% CO-15% H ₂ O-N ₂ WHSV = 30 000 mL g _{cat} ⁻¹ h ⁻¹	TOF at 250 °C = 0.55 s ⁻¹	Reducibility of the support	86
Au/La ₂ O ₃	Hydrolysis method	WGS	10% CO-3% H ₂ O-He	T ₅₀ ~ 375 °C	Oxidation state of Au	13
Au/La ₂ O ₃ SO ₄	Surfactant-assisted technique	WGS	10% CO-3% H ₂ O-He	T ₅₀ ~ 350 °C	Oxidation state of Au	13
CuO/CeO ₂ -La ₂ O ₃	Co-precipitation method	WGS	5% CO-30% H ₂ -6% CO ₂ -50% H ₂ O-N ₂ Total speed: 207.4 mL min ⁻¹	T ₉₀ ~ 225 °C	Oxidation state of Cu and oxygen vacancy	88
Cu/CeO ₂ nanorods	Hydrothermal method	RWGS	10% CO ₂ -50% H ₂ -He Total speed: 20 mL min ⁻¹	Rate at 250 °C = 1.8 μmol g _{cat} ⁻¹ s ⁻¹	CeO ₂ (110) facets	94
Ni/La ₂ O ₃	Sol-gel method	RWGS	50% CO ₂ -50% H ₂ Total speed: 20 mL min ⁻¹	~100 °C; CO ₂ conversion = 51.0%; CO yield = 39.1%	Ni dispersion and SMSI	95
Ru nanoclusters/ CeO ₂	Hydrothermal method	CO ₂ methanation	5% CO ₂ -20% H ₂ -He Total speed: 40 mL min ⁻¹	TOF at 190 °C = 7.4 × 10 ⁻³ s ⁻¹ Selectivity ~100%	SMSI and H-spillover	96
Ni-Sm ₂ O ₃	Sol-gel method	CO ₂ methanation	10% CO ₂ -40% H ₂ -Ar Total speed: 50 mL min ⁻¹	T ₁₀₀ ~ 100 °C Selectivity ~100%	Smaller size and more perimeter sites	97
Co/Gd ₂ O ₃	Impregnation method	CO ₂ methanation	10% CO ₂ -90% H ₂ Total speed: 75 mL min ⁻¹	TOF at 300 °C = 1.3 min ⁻¹ Selectivity ~80%	Reducibility	98
Cu/La ₂ O ₃ CO ₃ nanorods	Deposition-precipitation method	CO ₂ hydrogenation to methanol	24% CO ₂ -72% H ₂ -N ₂ 3.0 MPa	TOF at 240 °C = 7.0 × 10 ⁻³ s ⁻¹	Cu ^{δ+} and enhanced CO ₂ adsorption	103
La ₂ O ₃ doped CuO/ ZnO/ZrO ₂	Co-precipitation method	CO ₂ hydrogenation to methanol	25% CO ₂ -75% H ₂ 3.0 MPa	Selectivity = 92.5% CH ₃ OH productivity at 230 °C = 2.7 mol kg _{cat} ⁻¹ h ⁻¹	Oxygen vacancy	104
La ₂ O ₃ -CuO/ZnO/ Al ₂ O ₃	Co-precipitation method	CO ₂ hydrogenation to methanol	10% CO ₂ -90% H ₂ Total speed: 50 mL min ⁻¹	Selectivity = 49.8% 210 °C; CH ₃ OH yield = 0.9%; selectivity ~40%	Enhanced adsorption of CO ₂	105

Table 1 (Contd.)

Catalyst	Synthetic route	Application	Conditions	Performance	Key factors in catalysis	Ref.
La-Nd-PdO/Al ₂ O ₃	Impregnation method	Methane combustion reaction	1% CH ₄ /Ar	TOF at 850 °C = 4.8 mol g ⁻¹ s ⁻¹	Stabilizing Pd species	113
La-Nd-PdO/ ZrO ₂ -Al ₂ O ₃ Pd-CeO ₂	Impregnation method Ball milling method	Methane combustion reaction Methane combustion reaction	1% CH ₄ /Ar	Rate at 800 °C = 6.9 × 10 ² μmol g ⁻¹ s ⁻¹	Stabilizing Pd species	114
NiO-Gd ₂ O ₃	Controlled oxidation of the intermetallic compounds Precipitation method	Methane combustion reaction Partial oxidation of methane	0.5% CH ₄ -2% O ₂ -He GHSV = 200 000 h ⁻¹ 28% CH ₄ -14% O ₂ -N ₂ GHSV = 8500 mL g ⁻¹ h ⁻¹ 66.7% CH ₄ -33.3% O ₂ Total speed: 165 mL min ⁻¹	T ₅₀ ~ 350 °C T ₅₀ ~ 625 °C	Structural effect Synergistic effect	115
Ni/Y ₂ O ₃	Precipitation method	Partial oxidation of methane	64% CH ₄ -36% O ₂ SV = 5 × 10 ⁵ mL g ⁻¹ h ⁻¹ 64% CH ₄ -36% O ₂ SV = 5 × 10 ⁵ mL g ⁻¹ h ⁻¹ 1 M CH ₃ OH + 0.5 M KOH	CH ₄ conversion at 700 °C ~ 82%; CO and H ₂ selectivity at 700 °C ~ 90%	Basic sites and reducible oxygen	117
Pt/Gd ₂ O ₃	Impregnation method	Partial oxidation of methane	64% CH ₄ -36% O ₂ SV = 5 × 10 ⁵ mL g ⁻¹ h ⁻¹	CO productivity at 700 °C = 9.5 mol g ⁻¹ h ⁻¹	Basic sites	121
Pd/Sm ₂ O ₃	Impregnation method	Partial oxidation of methane	64% CH ₄ -36% O ₂ SV = 5 × 10 ⁵ mL g ⁻¹ h ⁻¹ 1 M CH ₃ OH + 0.5 M KOH	CO productivity at 700 °C = 7.9 mol g ⁻¹ h ⁻¹	Basic sites	121
Pd-Y ₂ O ₃ /C	Microwave-assisted reduction	MOR	1 M CH ₃ OH + 1 M KOH 1 M CH ₃ OH + 0.25 M H ₂ SO ₄ 1 M CH ₃ OH + 0.5 M H ₂ SO ₄	ECSA = 70 m ² g ⁻¹ SA: 145 mA cm ⁻² SA: 1.8 mA cm ⁻²	Enhanced ECSA and synergistic effect	126
Pd-La ₂ O ₃ /C	Reduction reaction	MOR	1 M CH ₃ OH + 1 M KOH	ECSA = 80 m ² g ⁻¹ MA: 1360 mA mg _{Pt} ⁻¹ MA: 714 mA mg _{Pt} ⁻¹	Electronic, bifunctional and synergistic effects	129
Au@CeO ₂ @Pt	Hydrothermal method	MOR	1 M CH ₃ OH + 0.5 M H ₂ SO ₄	MA: 1360 mA mg _{Pt} ⁻¹ MA: 714 mA mg _{Pt} ⁻¹	Oxygen vacancy	130
Pt/CeO ₂	Hydrothermal method etch	MOR	1 M CH ₃ OH + 0.5 M H ₂ SO ₄	SA: 118.3 mA cm ⁻²	Surface oxygen-containing species and oxygen mobility	131
Pt/Pt ₁ Ce ₁ O ₂ -C	Precipitation method	MOR	0.5 M CH ₃ OH + 0.5 M H ₂ SO ₄			133

ture–function correlation of rare earth oxide-based nanomaterials applied in catalytic applications. We also presented the reported works in Table 1, including their preparation methods and catalytic properties. In summary, the role of well-defined rare earth oxide-based catalysts in C1 chemical reactions mainly involves three aspects: (1) providing stable sites for the loading and dispersion of other metal catalysts, (2) providing strong metal support interaction and enhancing the electron density of the metal loading, and (3) providing sites for the adsorption and activation of small molecules such as H₂O, O₂ and CO₂. There is no doubt that rare earth oxide-based catalysts play a significant role in C1 chemical reactions, but there are also many problems that need to be solved.

Firstly, optimized synthesis strategies still need to be developed for the large-scale and low-cost production of rare earth oxide materials with high performances. Based on the current developed synthetic routes, on the one hand, methods such as thermal decomposition and precipitation are low-cost and efficient, but they are not suitable for designing and obtaining nanostructures with a specific morphology, which may result in desirable properties. On the other hand, routes such as the hydrothermal and sol–gel methods are suitable for the preparation of functional nanomaterials, but they cannot guarantee their large production and low cost. Besides, the role of rare earth oxides themselves in the catalytic reaction needs a deeper and clearer understanding. Many reported works have demonstrated that rare earth oxides exhibit catalytic activity for C1 chemical reactions. However, when the rare earth oxides are used as a support to form composite materials with other metal or metal oxides, it is not clear if they only work as support or they also provide active sites. In addition, the defects in rare-earth oxides also play a crucial role in C1 chemical reactions, such as stabilizing the active metal loading, providing sites for the adsorption of reactant molecules such as H₂O and CO₂, and promoting the electron transfer between the support and active metals, especially oxygen defects. However, other defects such as dislocation and grain boundaries in rare earth oxides are rarely discussed in C1 chemical reactions, and thus more research is needed to fill this blank. Furthermore, most of the characterizations of rare earth oxide-based catalysts are restricted to the *ex situ* level. Nevertheless, the surface structure of the catalyst always changes in the reaction process, and there are many intermediate species generated that disappear and cannot be observed by *ex situ* techniques. Consequently, *in situ/operando* characterizations combined with theoretical simulation need to be performed to uncover the real reaction mechanism behind the catalytic reaction. Finally, to date, most of the research on rare earth oxide-based catalysts for C1 chemical reactions has focused on CeO₂, but the catalytic properties of other rare earth oxides need to be explored to obtain more novel catalysts with high performances. Also, the powerful function of computational simulation in explaining and predicting the catalytic properties of rare earth oxides should be noted. There is also a problem that most computational works on rare earth oxides are based on CeO₂ nanomaterials. However, using theoretical computation

to predict properties may result in the development of more non-ceria rare earth oxides nanostructures with high catalytic performances. We believe that all of these problems will be addressed in the future, and rare earth oxide-based nanomaterials will shine brightly at the stage of catalytic applications in C1 chemical reactions.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

We acknowledge financial support from the National Natural Science Foundation of China (no. 21832001 and 21771009), and the National Key Research and Development Program of China (no. 2016YFB0701100).

Notes and references

- H. Huang and J. J. Zhu, The electrochemical applications of rare earth-based nanomaterials, *Analyst*, 2019, **144**, 6789–6811.
- A. R. Richard and M. Fan, Rare earth elements: properties and applications to methanol synthesis catalysis via hydrogenation of carbon oxides, *J. Rare Earths*, 2018, **36**, 1127–1135.
- W. Zhan, Y. Guo, X. Gong, Y. Guo, Y. Wang and G. Lu, Current status and perspectives of rare earth catalytic materials and catalysis, *Chin. J. Catal.*, 2014, **35**, 1238–1250.
- W. Gao, D. Wen, J. C. Ho and Y. Qu, Incorporation of rare earth elements with transition metal-based materials for electrocatalysis: a review for recent progress, *Mater. Today Chem.*, 2019, **12**, 266–281.
- Y. Guo and Y.-W. Zhang, Research advances on rare earth-based heterogeneous catalysts in transformation reactions of small molecules, *J. Rare Earths*, 2017, **035**, 55–68.
- G. A. M. Hussein, Rare earth metal oxides: formation, characterization and catalytic activity thermoanalytical and applied pyrolysis review, *J. Anal. Appl. Pyrolysis*, 1996, **37**, 111–149.
- Y. C. Cao, Synthesis of square gadolinium-oxide nanoplates, *J. Am. Chem. Soc.*, 2004, **126**, 7456–7457.
- H.-X. Mai, L.-D. Sun, Y.-W. Zhang, R. Si, W. Feng, H.-P. Zhang, H.-C. Liu and C.-H. Yan, Shape-selective synthesis and oxygen storage behavior of ceria nanopolyhedra, nanorods, and nanocubes, *J. Phys. Chem. B*, 2005, **109**, 24380–24385.
- R. Si, Y.-W. Zhang, L.-P. You and C.-H. Yan, Rare-earth oxide nanopolyhedra, nanoplates, and nanodisks, *Angew. Chem., Int. Ed.*, 2005, **44**, 3256–3260.
- R. Si, Y.-W. Zhang, H.-P. Zhou, L.-D. Sun and C.-H. Yan, Controlled-synthesis, self-assembly behavior, and surface-dependent optical properties of high-quality rare-earth oxide nanocrystals, *Chem. Mater.*, 2007, **19**, 18–27.
- H.-P. Zhou, Y.-W. Zhang, H.-X. Mai, X. Sun, Q. Liu, W.-G. Song and C.-H. Yan, Spontaneous organization of uniform CeO₂ nanoflowers by 3D oriented attachment in hot surfactant solutions monitored with an in situ electrical conductance technique, *Chem. – Eur. J.*, 2008, **14**, 3380–3390.
- W. Gao, Z. Zhang, J. Li, Y. Ma and Y. Qu, Surface engineering on CeO₂ nanorods by chemical redox etching and their enhanced catalytic activity for CO oxidation, *Nanoscale*, 2015, **7**, 11686–11691.
- J. D. Lessard, I. Valsamakis and M. Flytzani-Stephanopoulos, Novel Au/La₂O₃ and Au/La₂O₂SO₄ catalysts for the water-gas shift reaction prepared via an anion adsorption method, *Chem. Commun.*, 2012, **48**, 4857–4859.
- X. Yang, X. Cheng, J. Ma, Y. Zou, W. Luo and Y. Deng, Large-pore mesoporous CeO₂-ZrO₂ solid solutions with in-pore confined Pt nanoparticles for enhanced CO oxidation, *Small*, 2019, **15**, e1903058.
- X. P. Fu, L. W. Guo, W. W. Wang, C. Ma, C. J. Jia, K. Wu, R. Si, L. D. Sun and C. H. Yan, Direct identification of active surface species for the water-gas shift reaction on a gold-ceria catalyst, *J. Am. Chem. Soc.*, 2019, **141**, 4613–4623.
- C. Mesters, A Selection of Recent Advances in C1 chemistry, *Annu. Rev. Chem. Biomol. Eng.*, 2016, **7**, 223–238.
- P. Li, F. Yu, N. Altaf, M. Zhu, J. Li, B. Dai and Q. Wang, Two-dimensional layered double hydroxides for reactions of methanation and methane reforming in C1 chemistry, *Materials*, 2018, **11**, 221.
- G. Chen, G. I. N. Waterhouse, R. Shi, J. Zhao, Z. Li, L. Z. Wu, C. H. Tung and T. Zhang, From solar energy to fuels: recent advances in light-driven C1 chemistry, *Angew. Chem., Int. Ed.*, 2019, **58**, 17528–17551.
- J. Bao and N. Tsubaki, Design and synthesis of powerful capsule catalysts aimed at applications in C1 chemistry and biomass conversion, *Chem. Rec.*, 2018, **18**, 4–19.
- W. Keim, *Catalysis in C1 Chemistry*, Reidel Publishing Company, 1983.
- W.-G. Cui, G.-Y. Zhang, T.-L. Hu and X.-H. Bu, Metal-organic framework-based heterogeneous catalysts for the conversion of C1 chemistry: CO, CO₂ and CH₄, *Coord. Chem. Rev.*, 2019, **387**, 79–120.
- C. Sun, H. Li and L. Chen, Nanostructured ceria-based materials: synthesis, properties, and applications, *Energy Environ. Sci.*, 2012, **5**, 8475–8505.
- D. Zhang, X. Du, L. Shi and R. Gao, Shape-controlled synthesis and catalytic application of ceria nanomaterials, *Dalton Trans.*, 2012, **41**, 14455–14475.
- N. Ta, J. Liu and W. Shen, Tuning the shape of ceria nanomaterials for catalytic applications, *Chin. J. Catal.*, 2013, **34**, 838–850.
- Z.-A. Qiao, Z. Wu and S. Dai, Shape-controlled ceria-based nanostructures for catalysis applications, *ChemSusChem*, 2013, **6**, 1821–1833.

- 26 W. Huang and Y. Gao, Morphology-dependent surface chemistry and catalysis of CeO₂ nanocrystals, *Catal. Sci. Technol.*, 2014, **4**, 3772–3784.
- 27 K. Wu, L.-D. Sun and C.-H. Yan, Recent progress in well-controlled synthesis of ceria-based nanocatalysts towards enhanced catalytic performance, *Adv. Energy Mater.*, 2016, **6**, 1600501.
- 28 A. Trovarelli and J. Llorca, Ceria catalysts at nanoscale: how do crystal shapes shape catalysis?, *ACS Catal.*, 2017, **7**, 4716–4735.
- 29 Z. Wang and R. Yu, Hollow micro/nanostructured ceria-based materials: synthetic strategies and versatile applications, *Adv. Mater.*, 2019, **31**, 1800592.
- 30 S. Chen, F. Xiong and W. Huang, Surface chemistry and catalysis of oxide model catalysts from single crystals to nanocrystals, *Surf. Sci. Rep.*, 2019, **74**, 100471.
- 31 X. Hao, A. Yoko, C. Chen, K. Inoue, M. Saito, G. Seong, S. Takami, T. Adschiri and Y. Ikuhara, Atomic-scale valence state distribution inside ultrafine CeO₂ nanocubes and its size dependence, *Small*, 2018, **14**, e1802915.
- 32 H. Tan, J. Wang, S. Yu and K. Zhou, Support Morphology-Dependent Catalytic Activity of Pd/CeO₂ for Formaldehyde Oxidation, *Environ. Sci. Technol.*, 2015, **49**, 8675–8682.
- 33 Y.-Y. Feng, H.-S. Hu, G.-H. Song, S. Si, R.-J. Liu, D.-N. Peng and D.-S. Kong, Promotion effects of CeO₂ with different morphologies to Pt catalyst toward methanol electrooxidation reaction, *J. Alloys Compd.*, 2019, **798**, 706–713.
- 34 K. Zhou, X. Wang, X. Sun, Q. Peng and Y. Li, Enhanced catalytic activity of ceria nanorods from well-defined reactive crystal planes, *J. Catal.*, 2005, **229**, 206–212.
- 35 J. Ke, J. W. Xiao, W. Zhu, H. Liu, R. Si, Y. W. Zhang and C. H. Yan, Dopant-induced modification of active site structure and surface bonding mode for high-performance nanocatalysts: CO oxidation on capping-free (110)-oriented CeO₂:Ln (Ln = La-Lu) nanowires, *J. Am. Chem. Soc.*, 2013, **135**, 15191–15200.
- 36 Y. Sohn, Yb₂O₃ nanowires, nanorods and nano-square plates, *Ceram. Int.*, 2018, **44**, 3341–3347.
- 37 T. Sobahi, Photocatalytic degradation of herbicides under visible light using Ni-Pr₂O₃ nanocomposites, *J. Alloys Compd.*, 2017, **695**, 1279–1284.
- 38 Y. Huang, B. Long, M. Tang, Z. Rui, M.-S. Balogun, Y. Tong and H. Ji, Bifunctional catalytic material: an ultra-stable and high-performance surface defect CeO₂ nanosheets for formaldehyde thermal oxidation and photocatalytic oxidation, *Appl. Catal., B*, 2016, **181**, 779–787.
- 39 Y. Zhang, F. Hou and Y. Tan, CeO₂ nanoplates with a hexagonal structure and their catalytic applications in highly selective hydrogenation of substituted nitroaromatics, *Chem. Commun.*, 2012, **48**, 2391–2393.
- 40 Z.-L. Wang, G.-R. Li, Y.-N. Ou, Z.-P. Feng, D.-L. Qu and Y.-X. Tong, Electrochemical deposition of Eu³⁺-doped CeO₂ nanobelts with enhanced optical properties, *J. Phys. Chem. C*, 2011, **115**, 351–356.
- 41 Q. Dai, S. Bai, H. Li, W. Liu, X. Wang and G. Lu, Catalytic total oxidation of 1,2-dichloroethane over highly dispersed vanadia supported on CeO₂ nanobelts, *Appl. Catal., B*, 2015, **168–169**, 141–155.
- 42 M. Mousavi-Kamazani, R. Rahmatolahzadeh and F. Beshkar, Facile solvothermal synthesis of CeO₂-CuO nanocomposite photocatalyst using novel precursors with enhanced photocatalytic performance in dye degradation, *J. Inorg. Organomet. Polym. Mater.*, 2017, **27**, 1342–1350.
- 43 D. Zhang, W. Wu, X. Cao, S. Li, X. Zhang, G. Han, A. Ying, X. Xu and Z. Tong, Fabrication of three-dimensional dendrite-like CeO₂ crystallites via simple template-free solution route, *J. Phys. Chem. Solids*, 2009, **70**, 1348–1352.
- 44 X. Jiang, X. Huang, W. Zeng, J. Huang, Y. Zheng, D. Sun and Q. Li, Facile morphology control of 3D porous CeO₂ for CO oxidation, *RSC Adv.*, 2018, **8**, 21658–21663.
- 45 J. Gu, Y.-W. Zhang and F. Tao, Shape control of bimetallic nanocatalysts through well-designed colloidal chemistry approaches, *Chem. Soc. Rev.*, 2012, **41**, 8050–8065.
- 46 J.-W. Yu, W. Zhu and Y.-W. Zhang, Solution synthesis protocols for shaping mixed valent oxide crystalline particles as robust catalytic materials, *Inorg. Chem. Front.*, 2016, **3**, 9–25.
- 47 F. Dang, K. Kato, H. Imai, S. Wada, H. Haneda and M. Kuwabara, Characteristics of CeO₂ nanocubes and related polyhedra prepared by using a liquid-liquid interface, *Cryst. Growth Des.*, 2010, **10**, 4537–4541.
- 48 H. Miao, G.-F. Huang, J.-H. Liu, B.-X. Zhou, A. Pan, W.-Q. Huang and G.-F. Huang, Origin of enhanced photocatalytic activity of F-doped CeO₂ nanocubes, *Appl. Surf. Sci.*, 2016, **370**, 427–432.
- 49 Z. Ren, F. Peng, J. Li, X. Liang and B. Chen, Morphology-dependent properties of Cu/CeO₂ catalysts for the water-gas shift reaction, *Catalysts*, 2017, **7**, 48.
- 50 X. H. Lu, X. Huang, S. L. Xie, D. Z. Zheng, Z. Q. Liu, C. L. Liang and Y. X. Tong, Facile electrochemical synthesis of single crystalline CeO₂ octahedrons and their optical properties, *Langmuir*, 2010, **26**, 7569–7573.
- 51 J. Yang, L. Lukashuk, H. Li, K. Föttinger, G. Rupprechter and U. Schubert, High surface area ceria for CO oxidation prepared from cerium t-butoxide by combined sol-gel and solvothermal processing, *Catal. Lett.*, 2014, **144**, 403–412.
- 52 H. M. Shiri, A. Ehsani and M. Jalali Khaled, Electrochemical synthesis of Sm₂O₃ nanoparticles: application in conductive polymer composite films for supercapacitors, *J. Colloid Interface Sci.*, 2017, **505**, 940–946.
- 53 Y. Shlapa, V. Sarnatskaya, I. Timashkov, L. Yushko, I. Antal, B. Gerashchenko, I. Nychyporenko, A. Belous, V. Nikolaev and M. Timko, Synthesis of CeO₂ nanoparticles by precipitation in reversal microemulsions and their physical-chemical and biological properties, *Appl. Phys. A*, 2019, **125**, 412.
- 54 G. Wu, L. Zhang, B. Cheng, T. Xie and X. Yuan, Synthesis of Eu₂O₃ nanotube arrays through a facile sol-gel template approach, *J. Am. Chem. Soc.*, 2004, **126**, 5976–5977.

- 55 Q. Tang, J. Shen, W. Zhou, W. Zhang, W. Yu and Y. Qian, Preparation, characterization and optical properties of terbium oxide nanotubes, *J. Mater. Chem.*, 2003, **13**, 3103–3106.
- 56 N. Sabari Arul, J. Vidya, V. Ramya and D. Mangalaraj, Synthesis, characterization and electrochemical sensing of Tb₂O₃ nanotubes, *J. Electron. Mater.*, 2016, **46**, 1072–1078.
- 57 B. Xu, Z. Liu, W. Qiu, Q. Liu, X. Sun, G. Cui, Y. Wu and X. Xiong, La₂O₃ nanoplate: an efficient electrocatalyst for artificial N₂ fixation to NH₃ with excellent selectivity at ambient condition, *Electrochim. Acta*, 2019, **298**, 106–111.
- 58 C. Wang and Y. Wang, Effects of different surfactants on humidity sensing properties of CeO₂ nanobelts thin film prepared by hydrothermal method, *Int. J. Appl. Ceram. Technol.*, 2015, **12**, E142–E148.
- 59 H.-L. Lin, C.-Y. Wu and R.-K. Chiang, Facile synthesis of CeO₂ nanoplates and nanorods by [100] oriented growth, *J. Colloid Interface Sci.*, 2010, **341**, 12–17.
- 60 Y. Wu, Y. Chen and J. Zhou, La(OH)₃ nanorods and La₂O₃ nanoplates: facile synthesis and photoluminescence properties, *Mater. Lett.*, 2013, **95**, 5–8.
- 61 W. Hu, F. He, X. Chen and S. Liu, Hydrothermal synthesis of leaf-like CeO₂ nanosheets and its MnO_x/CeO₂ composites for catalytic combustion of chlorobenzene, *J. Nanopart. Res.*, 2018, **21**, 6.
- 62 Q. Dai, Z. Zhang, J. Yan, J. Wu, G. Johnson, W. Sun, X. Wang, S. Zhang and W. Zhan, Phosphate-functionalized CeO₂ nanosheets for efficient catalytic oxidation of dichloromethane, *Environ. Sci. Technol.*, 2018, **52**, 13430–13437.
- 63 X. Li, Q. Li, Z. Xia, L. Wang, W. Yan, J. Wang and R. I. Boughton, Growth and characterization of single-crystal Y₂O₃:Eu nanobelts prepared with a simple technique, *Cryst. Growth Des.*, 2006, **6**, 2193–2196.
- 64 R. Rao, M. Yang, Q. Ling, Q. Zhang, H. Liu, A. Zhang and W. Chen, Mesoporous CeO₂ nanobelts synthesized by a facile hydrothermal route via controlling cationic type and concentration of alkali, *Microporous Mesoporous Mater.*, 2013, **169**, 81–87.
- 65 J.-M. Li, X.-L. Zeng, Y.-H. Dong and Z.-A. Xu, White-light emission and weak antiferromagnetism from cubic rare-earth oxide Eu₂O₃ electrospun nanostructures, *CrystEngComm*, 2013, **15**, 2372–2377.
- 66 H. Xiao, P. Li, F. Jia and L. Zhang, General nonaqueous sol-gel synthesis of nanostructured Sm₂O₃, Gd₂O₃, Dy₂O₃, and Gd₂O₃:Eu³⁺ phosphor, *J. Phys. Chem. C*, 2009, **113**, 21034–21041.
- 67 D.-E. Zhang, X.-J. Zhang, X.-M. Ni, J.-M. Song and H.-G. Zheng, Fabrication of novel threefold shape CeO₂ dendrites: optical and electrochemical properties, *Chem. Phys. Lett.*, 2006, **430**, 326–329.
- 68 D. Zhang, F. Li, S. Li, X. Zhang, G. Han, A. Ying and Z. Tong, Synthesis of four-fold shape CeO₂ dendrites by a reduction route, *Mater. Chem. Phys.*, 2013, **142**, 496–501.
- 69 S. Qu, Y. Yu, K. Lin, P. Liu, C. Zheng, L. Wang, T. Xu, Z. Wang and H. Wu, Easy hydrothermal synthesis of multi-shelled La₂O₃ hollow spheres for lithium-ion batteries, *J. Mater. Sci.: Mater. Electron.*, 2017, **29**, 1232–1237.
- 70 X. Dong, X. Cheng, X. Zhang, L. Sui, Y. Xu, S. Gao, H. Zhao and L. Huo, A novel coral-shaped Dy₂O₃ gas sensor for high sensitivity NH₃ detection at room temperature, *Sens. Actuators, B*, 2018, **255**, 1308–1315.
- 71 Y. Zhou, Z. Wang and C. Liu, Perspective on CO oxidation over Pd-based catalysts, *Catal. Sci. Technol.*, 2015, **5**, 69–81.
- 72 Y. Cui, L. Xu, M. Chen, C. Lv, X. Lian, C.-E. Wu, B. Yang, Z. Miao, F. Wang and X. Hu, CO oxidation over metal oxide (La₂O₃, Fe₂O₃, PrO₂, Sm₂O₃, and MnO₂) doped CuO-based catalysts supported on mesoporous Ce_{0.8}Zr_{0.2}O₂ with intensified low-temperature activity, *Catalysts*, 2019, **9**, 724.
- 73 H.-P. Zhou, Y.-W. Zhang, R. Si, L.-S. Zhang, W.-G. Song and C.-H. Yan, Dimension-manipulated ceria nanostructures (0D uniform nanocrystals, 2D polycrystalline assembly, and 3D mesoporous framework) from cerium octylate precursor in solution phases and their CO oxidation activities, *J. Phys. Chem. C*, 2008, **112**, 20366–20374.
- 74 J.-G. Kang, B.-K. Min and Y. Sohn, Physicochemical properties of praseodymium hydroxide and oxide nanorods, *J. Alloys Compd.*, 2015, **619**, 165–171.
- 75 Y. Zhang, J. Deng, H. Zhang, Y. Liu and H. Dai, Three-dimensionally ordered macroporous Pr₆O₁₁ and Tb₄O₇ with mesoporous walls: Preparation, characterization, and catalytic activity for CO oxidation, *Catal. Today*, 2015, **245**, 28–36.
- 76 X. Li, C. Ni, X. Lu, S. Zuo, W. Liu and C. Yao, In situ fabrication of Ce_{1-x}La_xO_{2-δ}/palygorskite nanocomposites for efficient catalytic oxidation of CO: effect of La doping, *Catal. Sci. Technol.*, 2016, **6**, 545–554.
- 77 J. Ke, W. Zhu, Y. Jiang, R. Si, Y.-J. Wang, S.-C. Li, C. Jin, H. Liu, W.-G. Song, C.-H. Yan and Y.-W. Zhang, Strong local coordination structure effects on subnanometer PtO_x clusters over CeO₂ nanowires probed by low-temperature CO oxidation, *ACS Catal.*, 2015, **5**, 5164–5173.
- 78 P. X. Huang, F. Wu, B. L. Zhu, G. R. Li, Y. L. Wang, X. P. Gao, H. Y. Zhu, T. Y. Yan, W. P. Huang, S. M. Zhang and D. Y. Song, Praseodymium hydroxide and oxide nanorods and Au/Pr₆O₁₁ nanorod catalysts for CO oxidation, *J. Phys. Chem. B*, 2006, **110**, 1614–1620.
- 79 X. Zhang, S. Cheng, W. Zhang, C. Zhang, N. E. Drewett, X. Wang, D. Wang, S. J. Yoo, J.-G. Kim and W. Zheng, Mechanistic insight into nanoarchitected Ag/Pr₆O₁₁ catalysts for efficient CO oxidation, *Ind. Eng. Chem. Res.*, 2017, **56**, 11042–11048.
- 80 M. Lykaki, E. Pachatouridou, S. A. C. Carabineiro, E. Iliopoulou, C. Andriopoulou, N. Kallithrakas-Kontos, S. Boghosian and M. Konsolakis, Ceria nanoparticles shape effects on the structural defects and surface chemistry: Implications in CO oxidation by Cu/CeO₂ catalysts, *Appl. Catal., B*, 2018, **230**, 18–28.

- 81 W.-W. Wang, W.-Z. Yu, P.-P. Du, H. Xu, Z. Jin, R. Si, C. Ma, S. Shi, C.-J. Jia and C.-H. Yan, Crystal plane effect of ceria on supported copper oxide cluster catalyst for CO oxidation: importance of metal-support interaction, *ACS Catal.*, 2017, **7**, 1313–1329.
- 82 W.-H. Chen and C.-Y. Chen, Water gas shift reaction for hydrogen production and carbon dioxide capture: A review, *Appl. Energy*, 2020, **258**, 114078.
- 83 C. Schilling and C. Hess, Elucidating the role of support oxygen in the water-gas shift reaction over ceria-supported gold catalysts using operando spectroscopy, *ACS Catal.*, 2018, **9**, 1159–1171.
- 84 J. J. Plata, F. Romero-Sarria, J. Amaya Suarez, A. M. Marquez, O. H. Laguna, J. A. Odriozola and J. Fdez Sanz, Improving the activity of gold nanoparticles for the water-gas shift reaction using $\text{TiO}_2\text{-Y}_2\text{O}_3$: an example of catalyst design, *Phys. Chem. Chem. Phys.*, 2018, **20**, 22076–22083.
- 85 L. G. Pinaeva, E. M. Sadovskaya, Y. A. Ivanova, T. G. Kuznetsova, I. P. Prosvirin, V. A. Sadykov, Y. Schuurman, A. C. van Veen and C. Mirodatos, Water gas shift and partial oxidation of CH_4 over $\text{CeO}_2\text{-ZrO}_2\text{-La}_2\text{O}_3$ and $\text{Pt/CeO}_2\text{-ZrO}_2\text{-La}_2\text{O}_3$: performance under transient conditions, *Chem. Eng. J.*, 2014, **257**, 281–291.
- 86 S. M. Lee, G. J. Kim, S. H. Lee, I. H. Hwang, S. C. Hong and S. S. Kim, Catalytic performance of $\text{Ce}_{0.6}\text{Y}_{0.4}\text{O}_2$ -supported platinum catalyst for low-temperature water-gas shift reaction, *ACS Omega*, 2018, **3**, 3156–3163.
- 87 R. Si and M. Flytzani-Stephanopoulos, Shape and crystal-plane effects of nanoscale ceria on the activity of Au-CeO₂ Catalysts for the water-gas shift reaction, *Angew. Chem., Int. Ed.*, 2008, **47**, 2884–2887.
- 88 Y. She, Q. Zheng, L. Li, Y. Zhan, C. Chen, Y. Zheng and X. Lin, Rare earth oxide modified CuO/CeO₂ catalysts for the water-gas shift reaction, *Int. J. Hydrogen Energy*, 2009, **34**, 8929–8936.
- 89 C. Chen, Y. Zhan, J. Zhou, D. Li, Y. Zhang, X. Lin, L. Jiang and Q. Zheng, Cu/CeO₂ catalyst for water-gas shift reaction: effect of CeO₂ pretreatment, *ChemPhysChem*, 2018, **19**, 1448–1455.
- 90 S. Sangsorn, T. Ratana, S. Tungkamani, T. Sornchamni and M. Phongaksorn, Effect of CeO₂ loading of the Ce-Al mixed oxide on ultrahigh temperature water-gas shift performance over Ce-Al mixed oxide supported Ni catalysts, *Fuel*, 2019, **252**, 488–495.
- 91 N. Podrojková, V. Sans, A. Oriňak and R. Oriňaková, Recent developments in the modelling of heterogeneous catalysts for CO₂ conversion to chemicals, *ChemCatChem*, 2020, **12**, 1802–1825.
- 92 M. Boaro, S. Colussi and A. Trovarelli, Ceria-based materials in hydrogenation and reforming reactions for CO₂ valorization, *Front. Chem.*, 2019, **7**, 28.
- 93 B. Dai, S. Cao, H. Xie, G. Zhou and S. Chen, Reduction of CO₂ to CO via reverse water-gas shift reaction over CeO₂ catalyst, *Korean J. Chem. Eng.*, 2018, **35**, 421–427.
- 94 L. Lin, S. Yao, Z. Liu, F. Zhang, N. Li, D. Vovchok, A. Martínez-Arias, R. Castañeda, J. Lin, S. D. Senanayake, D. Su, D. Ma and J. A. Rodriguez, In situ characterization of Cu/CeO₂ nanocatalysts for CO₂ hydrogenation: morphological effects of nanostructured ceria on the catalytic activity, *J. Phys. Chem. C*, 2018, **122**, 12934–12943.
- 95 L. Liu, Z. Zhang, S. Das, S. Xi and S. Kawi, LaNiO₃ as a precursor of Ni/La₂O₃ for reverse water-gas shift in DBD plasma: effect of calcination temperature, *Energy Convers. Manage.*, 2020, **206**, 112475.
- 96 Y. Guo, S. Mei, K. Yuan, D.-J. Wang, H.-C. Liu, C.-H. Yan and Y.-W. Zhang, Low-temperature CO₂ methanation over CeO₂-supported Ru single atoms, nanoclusters, and nanoparticles competitively tuned by strong metal-support interactions and H-spillover effect, *ACS Catal.*, 2018, **8**, 6203–6215.
- 97 J. Ilseemann, A. Sonström, T. M. Gesing, R. Anwender and M. Bäumer, Highly active Sm₂O₃-Ni xerogel catalysts for CO₂ methanation, *ChemCatChem*, 2019, **11**, 1732–1741.
- 98 J. Díez-Ramírez, P. Sánchez, V. Kyriakou, S. Zafeiratos, G. E. Marnellos, M. Konsolakis and F. Dorado, Effect of support nature on the cobalt-catalyzed CO₂ hydrogenation, *J. CO₂ Util.*, 2017, **21**, 562–571.
- 99 Z. Shi, Q. Tan and D. Wu, Enhanced CO₂ hydrogenation to methanol over TiO₂ nanotubes-supported CuO-ZnO-CeO₂ catalyst, *Appl. Catal., A*, 2019, **581**, 58–66.
- 100 B. Ouyang, W. Tan and B. Liu, Morphology effect of nanostructure ceria on the Cu/CeO₂ catalysts for synthesis of methanol from CO₂ hydrogenation, *Catal. Commun.*, 2017, **95**, 36–39.
- 101 Q. Tan, Z. Shi and D. Wu, CO₂ hydrogenation to methanol over a highly active Cu-Ni/CeO₂-nanotube catalyst, *Ind. Eng. Chem. Res.*, 2018, **57**, 10148–10158.
- 102 Q. Tan, Z. Shi and D. Wu, CO₂ hydrogenation over differently morphological CeO₂-supported Cu-Ni catalysts, *Int. J. Energy Res.*, 2019, **43**, 5392–5404.
- 103 K. Chen, X. Duan, H. Fang, X. Liang and Y. Yuan, Selective hydrogenation of CO₂ to methanol catalyzed by Cu supported on rod-like La₂O₂CO₃, *Catal. Sci. Technol.*, 2018, **8**, 1062–1069.
- 104 H. Ban, C. Li, K. Asami and K. Fujimoto, Influence of rare-earth elements (La, Ce, Nd and Pr) on the performance of Cu/Zn/Zr catalyst for CH₃OH synthesis from CO₂, *Catal. Commun.*, 2014, **54**, 50–54.
- 105 M. Kourtelesis, K. Kousi and D. I. Kondarides, CO₂ hydrogenation to methanol over La₂O₃-promoted CuO/ZnO/Al₂O₃ catalysts: a kinetic and mechanistic study, *Catalysts*, 2020, **10**, 183.
- 106 A. Toso, S. Colussi, S. Padigapaty, C. de Leitenburg and A. Trovarelli, High stability and activity of solution combustion synthesized Pd-based catalysts for methane combustion in presence of water, *Appl. Catal., B*, 2018, **230**, 237–245.
- 107 P. Lott, M. Eck, D. E. Doronkin, R. Popescu, M. Casapu, J.-D. Grunwaldt and O. Deutschmann, regeneration of sulfur poisoned Pd-Pt/CeO₂-ZrO₂-Y₂O₃-La₂O₃ and Pd-Pt/

- Al₂O₃ methane oxidation catalysts, *Top. Catal.*, 2018, **62**, 164–171.
- 108 C. Wen, Y. Liu, Y. Guo, Y. Wang and G. Lu, Strategy to eliminate catalyst hot-spots in the partial oxidation of methane: enhancing its activity for direct hydrogen production by reducing the reactivity of lattice oxygen, *Chem. Commun.*, 2010, **46**, 880–882.
- 109 T. H. Nguyen, A. Łamacz, A. Krztoń, B. Liszka and G. Djéga-Mariadassou, Partial oxidation of methane over Ni⁰/La₂O₃ bifunctional catalyst III. Steady state activity of methane total oxidation, dry reforming, steam reforming and partial oxidation. Sequences of elementary steps, *Appl. Catal., B*, 2016, **182**, 385–391.
- 110 Y. J. O. Asencios, F. C. F. Marcos, J. M. Assaf and E. M. Assaf, Oxidative-reforming of methane and partial oxidation of methane reactions over NiO/PrO₂/ZrO₂ catalysts: effect of nickel content, *Braz. J. Chem. Eng.*, 2016, **33**, 627–636.
- 111 J. Dou, Y. Tang, L. Nie, C. M. Andolina, X. Zhang, S. House, Y. Li, J. Yang and F. Tao, Complete oxidation of methane on Co₃O₄/CeO₂ nanocomposite: a synergic effect, *Catal. Today*, 2018, **311**, 48–55.
- 112 A. F. Zedan and A. S. Aljaber, Combustion synthesis of non-precious CuO-CeO₂ nanocrystalline catalysts with enhanced catalytic activity for methane oxidation, *Materials*, 2019, **12**, 878.
- 113 Y. Ozawa, Y. Tochihara, M. Nagai and S. Omi, Effect of addition of Nd₂O₃ and La₂O₃ to PdO/Al₂O₃ in catalytic combustion of methane, *Catal. Commun.*, 2003, **4**, 87–90.
- 114 Y. Ozawa, Y. Tochihara, A. Watanabe, M. Nagai and S. Omi, Stabilizing effect of Nd₂O₃, La₂O₃ and ZrO₂ on Pt-PdO/Al₂O₃ during catalytic combustion of methane, *Appl. Catal., A*, 2004, **258**, 261–267.
- 115 M. Danielis, S. Colussi, C. de Leitenburg, L. Soler, J. Llorca and A. Trovarelli, Outstanding methane oxidation performance of palladium-embedded ceria catalysts prepared by a one-step dry ball-milling method, *Angew. Chem., Int. Ed.*, 2018, **57**, 10212–10216.
- 116 A. C. Ferreira, A. M. Ferraria, A. M. B. do Rego, A. P. Gonçalves, M. R. Correia, T. A. Gasche and J. B. Branco, Partial oxidation of methane over bimetallic nickel-lanthanide oxides, *J. Alloys Compd.*, 2010, **489**, 316–323.
- 117 H. Liu, H. Wu and D. He, Methane conversion to syngas over Ni/Y₂O₃ catalysts—effects of calcination temperatures of Y₂O₃ on physicochemical properties and catalytic performance, *Fuel Process. Technol.*, 2014, **119**, 81–86.
- 118 R. K. Singha, A. Shukla, A. Yadav, T. Sasaki, A. Sandupatla, G. Deo and R. Bal, Pt-CeO₂ nanoporous spheres – an excellent catalyst for partial oxidation of methane: effect of the bimodal pore structure, *Catal. Sci. Technol.*, 2017, **7**, 4720–4735.
- 119 S. Zhu, X. Lian, T. Fan, Z. Chen, Y. Dong, W. Weng, X. Yi and W. Fang, Thermally stable core-shell Ni/nanorod-CeO₂@SiO₂ catalyst for partial oxidation of methane at high temperatures, *Nanoscale*, 2018, **10**, 14031–14038.
- 120 S. Das, R. Gupta, A. Kumar, M. Shah, M. Sengupta, S. Bhandari and A. Bordoloi, Facile synthesis of ruthenium decorated Zr_{0.5}Ce_{0.5}O₂ nanorods for catalytic partial oxidation of methane, *ACS Appl. Nano Mater.*, 2018, **1**, 2953–2961.
- 121 V. R. Choudhary, B. Prabhakar, A. M. Rajput and A. S. Mamman, Oxidative conversion of methane to CO and H₂ over Pt or Pd containing alkaline and rare earth oxide catalysts, *Fuel*, 1998, **77**, 1477–1481.
- 122 A. Moura, J. Fajin, M. Mandado and M. Cordeiro, Ruthenium-platinum catalysts and direct methanol fuel cells (DMFC): a review of theoretical and experimental breakthroughs, *Catalysts*, 2017, **7**, 106.
- 123 E. Antolini, Photo-assisted methanol oxidation on Pt-TiO₂ catalysts for direct methanol fuel cells: A short review, *Appl. Catal., B*, 2018, **237**, 491–503.
- 124 J. S. Spendelow, P. K. Babu and A. Wieckowski, Electrocatalytic oxidation of carbon monoxide and methanol on platinum surfaces decorated with ruthenium, *Curr. Opin. Solid State Mater. Sci.*, 2005, **9**, 37–48.
- 125 A. Ali and P. K. Shen, Recent advances in graphene-based platinum and palladium electrocatalysts for the methanol oxidation reaction, *J. Mater. Chem. A*, 2019, **7**, 22189–22217.
- 126 J. Li, S. Wang, B. Zhang, W. Wang and L. Feng, Highly efficient methanol electrooxidation catalyzed by co-action of PdY₂O₃ in alkaline solution for fuel cells, *Int. J. Hydrogen Energy*, 2017, **42**, 12236–12245.
- 127 Q. Tan, C. Shu, J. Abbott, Q. Zhao, L. Liu, T. Qu, Y. Chen, H. Zhu, Y. Liu and G. Wu, Highly dispersed Pd-CeO₂ nanoparticles supported on N-doped core-shell structured mesoporous carbon for methanol oxidation in alkaline media, *ACS Catal.*, 2019, **9**, 6362–6371.
- 128 H. Wang, Y. Xue, B. Zhu, J. Yang, L. Wang, X. Tan, Z. Wang and Y. Chu, CeO₂ nanowires stretch-embedded in reduced graphite oxide nanocomposite support for Pt nanoparticles as potential electrocatalyst for methanol oxidation reaction, *Int. J. Hydrogen Energy*, 2017, **42**, 20549–20559.
- 129 L. Wang, Y. Wang, A. Li, Y. Yang, J. Wang, H. Zhao, X. Du and T. Qi, Electrocatalysis of carbon black- or chitosan-functionalized activated carbon nanotubes-supported Pd with a small amount of La₂O₃ towards methanol oxidation in alkaline media, *Int. J. Hydrogen Energy*, 2014, **39**, 14730–14738.
- 130 D. V. Dao, T. D. Le, G. Adilbish, I.-H. Lee and Y.-T. Yu, Pt-loaded Au@CeO₂ core-shell nanocatalysts for improving methanol oxidation reaction activity, *J. Mater. Chem. A*, 2019, **7**, 26996–27006.
- 131 L. Tao, Y. Shi, Y.-C. Huang, R. Chen, Y. Zhang, J. Huo, Y. Zou, G. Yu, J. Luo, C.-L. Dong and S. Wang, Interface engineering of Pt and CeO₂ nanorods with unique interaction for methanol oxidation, *Nano Energy*, 2018, **53**, 604–612.

- 132 Q. Zhou, Z. Pan, D. Wu, G. Hu, S. Wu, C. Chen, L. Lin and Y. Lin, Pt-CeO₂/TiN NTs derived from metal organic frameworks as high-performance electrocatalyst for methanol electrooxidation, *Int. J. Hydrogen Energy*, 2019, **44**, 10646–10652.
- 133 Z. Tang and G. Lu, Synthesis and characterization of high performance Pt-(Pr_xCe_yO_z)/C catalysts for methanol electrooxidation, *Appl. Catal., B*, 2008, **79**, 1–7.