



Cite this: *Chem. Commun.*, 2022, 58, 6853

Received 28th February 2022,  
Accepted 17th May 2022

DOI: 10.1039/d2cc01229d

rsc.li/chemcomm

# Tuning the photophysical properties of luminescent lanthanide complexes through regioselective antenna fluorination†

Daniel Kocsi, Andreas Orthaber and K. Eszter Borbas \*

**Carbostyrils monofluorinated in the 3, 5, or 6 positions were synthesised from olefinic precursors via a photochemical isomerisation-cyclisation route, and incorporated into octadentate cyclen triacetate ligands that formed luminescent complexes with Tb(III) and Eu(III). The photophysical properties of the emitters were strongly dependent on the position of the fluorination.**

The luminescence of the trivalent lanthanide (Ln) ions is applied in diverse biological and industrial settings ranging from the monitoring of the components of living cells to the thermometric analysis of materials.<sup>1,2</sup> Ln(III) luminescence is often sensitised by a light-harvesting antenna to avoid the need for direct excitation of the Laporte-forbidden 4f–4f transitions.<sup>3</sup> Optimisation of energy transfer (EnT) to the Ln(III) and elimination of processes that quench the antenna and Ln(III) excited states are essential for bright emitters.


Photoinduced electron transfer (PeT) from the excited antenna to Ln(III) is feasible for several Lns,<sup>4,5</sup> and for Eu(III) emission it can be an effective luminescence quenching process.<sup>6</sup> PeT is suppressed when the antenna is less reducing. Antenna substitution with electron-withdrawing groups (*e.g.* with CF<sub>3</sub>, Fig. 1)<sup>4,5</sup> or protonation<sup>7,8</sup> can increase the Eu(III) luminescence quantum yield, but may have unintended consequences on the antenna excited state energies.<sup>5,9,10</sup> Ln sensitisation commonly takes place *via* the antenna singlet (S<sub>1</sub>) and triplet excited states (T<sub>1</sub>). Even subtle changes to the antenna may alter the S<sub>1</sub> and T<sub>1</sub> energies and EnT. In the previous examples both antenna trifluoromethylation<sup>4,5</sup> and protonation proved detrimental to Tb(III) emission.<sup>8</sup>

Here, we have prepared three monofluorinated 7-aminocarbostyryl regioisomers. Electronegative fluorine was

expected to decrease PeT by making the antenna less reducing, a strategy that complements the use of C–F bonds to replace the more efficiently quenching C–H oscillators.<sup>11</sup> Fluorination has additional potential benefits. Fluorine is a hydrogen isostere conferring metabolic stability, H-bond acceptor ability, and altered lipophilicity on pharmaceuticals.<sup>12</sup> Diagnostic applications of fluorinated probes include multimodal<sup>13</sup> and responsive<sup>14</sup> systems. <sup>19</sup>F-MRI is a promising low-background technique,<sup>15</sup> and <sup>18</sup>F is an attractive PET label.<sup>16,17</sup>

Fluorinated carbostyrils were incorporated into do3a (1,4,7,10-tetraazacyclododecane-1,4,7-triacetate)-based octadentate ligands to enable comparison with previously reported structures.<sup>4,5</sup> The Eu(III), Tb(III), and Gd(III) chelates of the ligands were characterised using <sup>1</sup>H NMR spectroscopy, cyclic voltammetry, and UV-vis absorption and steady-state and time-resolved emission spectroscopies. Our results show fluorination meaningfully impacts the antenna and Ln(III) photophysical properties, and substitution at a remote antenna position could even influence the excited state behaviour of the Ln(III).

Fluorinated antennae were synthesised as shown in Scheme 1 and Schemes S1–S6 (ESI†). The procedures were

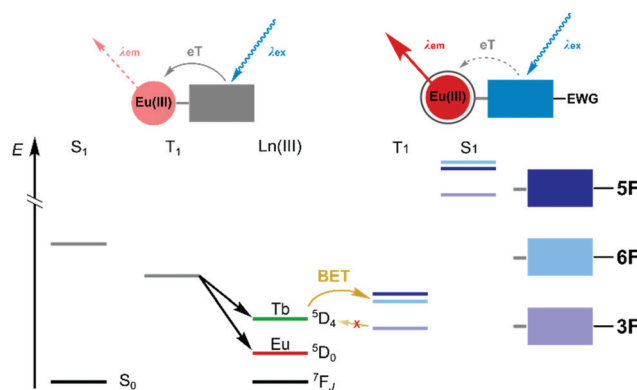


**Fig. 1** Decreased PeT quenching of Eu(III) luminescence through antenna substitution with electron-withdrawing group(s) (EWG), and its effects on the S<sub>1</sub> and T<sub>1</sub> energies.

Department of Chemistry, Ångström Laboratory, Uppsala University, Lägerhyddsvägen 1, 75120, Uppsala, Sweden. E-mail: eszter.borbas@kemi.uu.se

† Electronic supplementary information (ESI) available: Synthesis, characterisation, and NMR spectra of all new compounds, additional crystallographic, photophysical, and electrochemical characterisation. CCDC 2155036–2155038. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d2cc01229d>

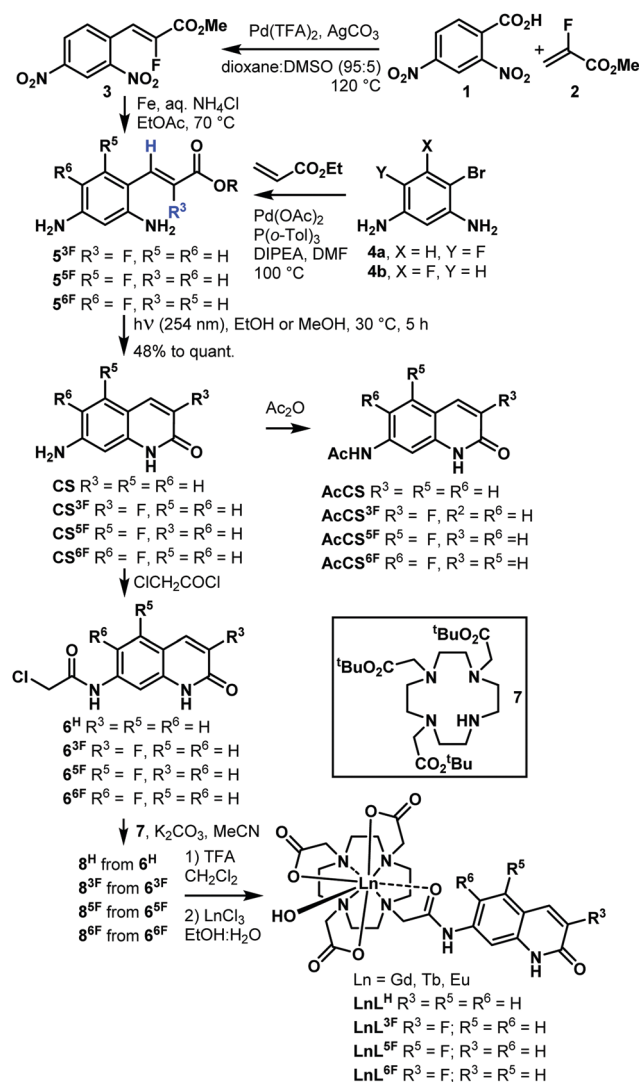

Scheme 1 Preparation of  $\text{CS}^{\text{F}}$ ,  $\text{AcCS}$ ,  $\text{AcCS}^{\text{F}}$ , and  $\text{LnL}^{\text{F}}$ .

robust, scalable (e.g. 466 mg of  $\text{CS}^{\text{6F}}$  was obtained in one experiment), and reproducible. Olefins  $5^{\text{F}}$  were prepared from commercially available starting materials as the *Z* isomers with excellent selectivity due to the steric clash between the ester group and the aromatic ring.<sup>18</sup> The stereochemical assignment was based on the  $^3J_{\text{HF}} = 33\text{--}38$  Hz and  $^3J_{\text{HH}} = 15\text{--}16$  Hz coupling constants. The key photochemical olefin isomerisation-cyclisation was carried out by irradiating a 100 mM solution of **5** in MeOH or EtOH with 254 nm-UV light, giving  $\text{CS}^{\text{3F}}$ ,  $\text{CS}^{\text{5F}}$ , and  $\text{CS}^{\text{6F}}$  in good to excellent yield. Regioisomer identities were confirmed by 1D and 2D NMR spectroscopy and single-crystal X-ray crystallography (Fig. S1–S6 and Tables S1–S3, ESI†). The analogous  $\text{CS}^{\text{4F}}$  could not be accessed *via* similar routes due to the instability of the intermediates (Schemes S3–S5, ESI†).  $\text{CS}/\text{CS}^{\text{F}}$  was acetylated with  $\text{Ac}_2\text{O}$  or chloroacetyl chloride to yield reference compounds  $\text{AcCS}/\text{AcCS}^{\text{F}}$ , or the reactive antennae **6**, respectively. **6** were incorporated into  $\text{LnL}$  ( $\text{Ln} = \text{Gd, Eu, Tb}$ ) using procedures previously developed for similar compounds. Synthetic details, compound characterisations, and the

attempted syntheses of  $\text{CS}^{\text{4F}}$  are given in the ESI†. Analytical data were fully consistent with the assigned structures.

Solution structures of  $\text{EuL}^{\text{F}}$  were studied by paramagnetic  $^1\text{H}$  and  $^{19}\text{F}$  NMR spectroscopy. In  $\text{CD}_3\text{OD}$  at r.t. the  $^1\text{H}$  NMR spectra of  $\text{EuL}^{\text{3F}}$ ,  $\text{EuL}^{\text{5F}}$ ,  $\text{EuL}^{\text{6F}}$ , and  $\text{EuL}^{\text{H}}$ , were similar (Fig. S7–S10, ESI†). The major isomer had square antiprismatic geometry (4 peaks at  $>32$  ppm). Trace amounts of the twisted square antiprismatic isomer were also present (signals at 12–16 ppm).  $^{19}\text{F}$  NMR spectra supported this interpretation, showing a single peak at  $-133.8$ ,  $-118.8$ , and  $-134.1$  ppm for  $\text{EuL}^{\text{3F}}$ ,  $\text{EuL}^{\text{5F}}$ , and  $\text{EuL}^{\text{6F}}$ , respectively (Fig. S11–S13, ESI†). These data are consistent with the ligands imposing similar geometries on the  $\text{Ln}(\text{III})$  ions in solution in the ground state, and is similar to what has been observed for other  $\text{do}3a$ -complexes carrying carbostyryl antennae.<sup>6</sup> This was expected as fluorine is small, and the fluorination sites are quite distant from the  $\text{Ln}(\text{III})$ .

The photophysical properties of  $\text{CS}$  and  $\text{CS}^{\text{F}}$  were recorded in acetonitrile due to their low aqueous solubility. The lowest-energy bands in the absorption spectra were assigned to  $\pi\text{--}\pi^*$  transitions, and were located at 320–360 nm with  $\lambda_{\text{max}} = 335$ , 332, and 339 nm for  $\text{CS}^{\text{3F}}$ ,  $\text{CS}^{\text{5F}}$ , and  $\text{CS}^{\text{6F}}$ , respectively (Fig. S18–S22, ESI†), non-fluorinated  $\text{CS}$  had  $\lambda_{\text{max}} = 337$  nm.  $\text{CS}$ ,  $\text{CS}^{\text{3F}}$ ,  $\text{CS}^{\text{5F}}$ , and  $\text{CS}^{\text{6F}}$  excitation at  $\lambda_{\text{max}}$  resulted in fluorescence emission maxima at  $\lambda_{\text{em}} = 384$ , 400, 387, and 382 nm, respectively (Table 1 and Fig. S23–S27, ESI†).  $\text{CS}^{\text{3F}}$  had the highest fluorescence quantum yield,  $\Phi_{\text{L}} = 56\%$ . Fluorination in the 5-position had minimal effect on  $\Phi_{\text{L}}$  compared to  $\text{CS}$  ( $\Phi_{\text{L}} = 25$  and 27%, respectively), while substitution in the 6-position lowered  $\Phi_{\text{L}}$  to 10%.  $\text{CS}^{\text{F}}$  fluorescence lifetimes ( $\tau_{\text{fl}}$ ) mirrored the observations made for  $\Phi_{\text{L}}$  (Table 1).  $\text{CS}^{\text{3F}}$  had the longest  $\tau_{\text{fl}}$  (2.84 ns), and  $\text{CS}^{\text{6F}}$  the shortest,  $\tau_{\text{fl}} = 0.41$  ns.  $\text{CS}$  and  $\text{CS}^{\text{5F}}$  had very similar  $\tau_{\text{fl}}$ , 1.15 and 1.09 ns, respectively (Table S5 and Fig. S49–S56, ESI†).

$\text{LnL}$  absorption spectra were collected in aqueous solutions (0.01 M PIPES buffer, pH = 6.5). Absorption maxima were blue-shifted relative to the corresponding  $\text{CS}$  with  $\lambda_{\text{max}} = 325$ , 327, 337, and 330 nm for  $\text{LnL}^{\text{3F}}$ ,  $\text{LnL}^{\text{5F}}$ ,  $\text{LnL}^{\text{6F}}$ , and  $\text{LnL}^{\text{H}}$ , respectively (Fig. 2 and Fig. S28–S32, ESI†).

$\text{Gd}(\text{III})$  excited states are too high to accept energy from the antennae, therefore,  $\text{GdL}$  are useful for determining the

Table 1 Photophysical properties of  $\text{CS}$ ,  $\text{CS}^{\text{F}}$ ,<sup>a</sup> and  $\text{GdL}^{\text{F}}$ <sup>b</sup>

|                          | $\lambda_{\text{max}}$ (nm) | $\lambda_{\text{em}}^c$ (nm) | $S_1$ ( $\text{cm}^{-1}$ ) | $T_1^d$ ( $\text{cm}^{-1}$ ) | $\Phi_{\text{L}}^e$ (%) | $\tau_{\text{fl}}$ (ns) |
|--------------------------|-----------------------------|------------------------------|----------------------------|------------------------------|-------------------------|-------------------------|
| $\text{CS}$              | 337                         | 384                          | —                          | —                            | 27                      | 1.15 (5)                |
| $\text{CS}^{\text{3F}}$  | 335                         | 400                          | —                          | —                            | 56                      | 2.84 (6)                |
| $\text{CS}^{\text{5F}}$  | 332                         | 387                          | —                          | —                            | 25                      | 1.09 (2)                |
| $\text{CS}^{\text{6F}}$  | 339                         | 382                          | —                          | —                            | 10                      | 0.41 (6)                |
| $\text{GdL}^{\text{H}}$  | 330                         | 369                          | 28 700                     | 22 500                       | 7.6                     | 0.34 (3)                |
| $\text{GdL}^{\text{3F}}$ | 325                         | 364                          | 29 200                     | 22 100                       | 13                      | 0.60 (5)                |
| $\text{GdL}^{\text{5F}}$ | 327                         | 367                          | 28 900                     | 22 400                       | 6.1                     | 0.44 (8)                |
| $\text{GdL}^{\text{6F}}$ | 337                         | 380                          | 28 100                     | 22 300                       | 5.9                     | 0.36 (4)                |

<sup>a</sup> In acetonitrile at 10  $\mu\text{M}$  concentration. <sup>b</sup> In aqueous PIPES buffer (10 mM), pH 6.5, at 10  $\mu\text{M}$  complex concentrations. <sup>c</sup>  $\lambda_{\text{ex}} = 332$  nm ( $\text{CS}^{\text{3F}}$ ), 331 nm ( $\text{CS}^{\text{5F}}$ ), 338 nm ( $\text{CS}^{\text{6F}}$ ), 335 nm ( $\text{GdL}^{\text{6F}}$ ), 327 nm ( $\text{GdL}^{\text{5F}}$ ), 325 nm ( $\text{GdL}^{\text{3F}}$ ). <sup>d</sup> Calculated from the 0–0 transitions of the  $\text{Gd}$ -complexes recorded at 77 K. <sup>e</sup> Relative to quinine sulfate ( $\Phi = 0.59$ ) in  $\text{H}_2\text{SO}_4$  (0.05 M).<sup>23</sup>



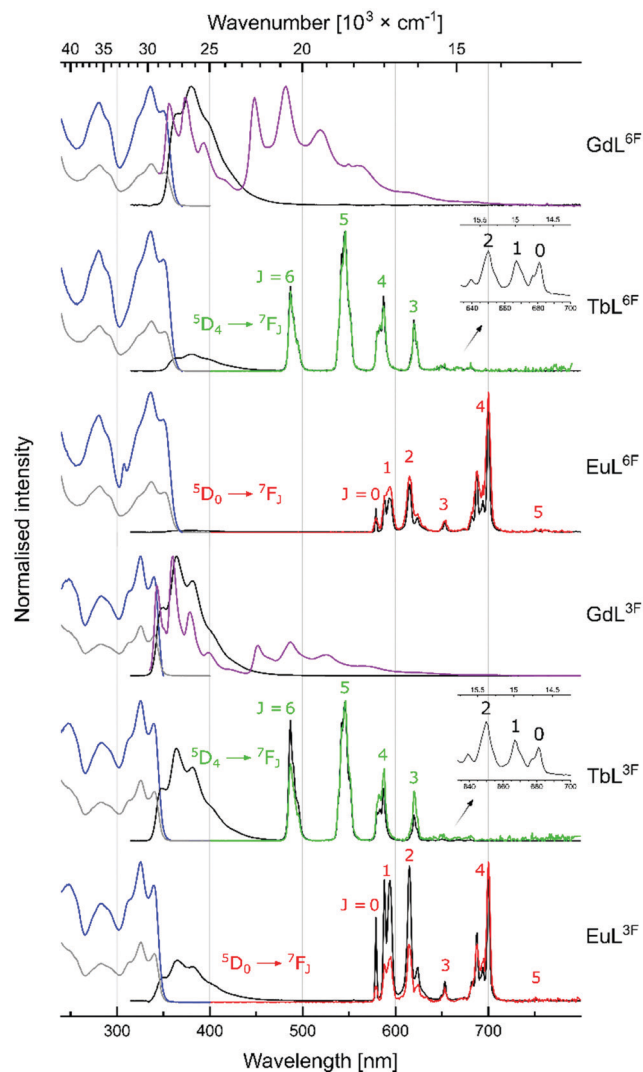


Fig. 2 Normalised absorption (grey, 298 K), excitation [blue,  $\lambda_{\text{em}} = 380$  nm (**GdL<sup>6F</sup>**),  $\lambda_{\text{em}} = 364$  nm (**GdL<sup>3F</sup>**),  $\lambda_{\text{em}} = 546$  nm (Tb),  $\lambda_{\text{em}} = 615$  nm (Eu), 298 K], steady-state emission at 298 K [black,  $\lambda_{\text{ex}} = 335$  nm (**LnL<sup>6F</sup>**),  $\lambda_{\text{ex}} = 325$  nm (**LnL<sup>3F</sup>**), steady-state emission at 77 K [purple,  $\lambda_{\text{ex}} = 335$  nm (**LnL<sup>6F</sup>**),  $\lambda_{\text{ex}} = 325$  nm (**LnL<sup>3F</sup>**)] and time-resolved emission [green (Tb), red (Eu),  $\lambda_{\text{ex}} = 335$  nm (**LnL<sup>6F</sup>**),  $\lambda_{\text{ex}} = 325$  nm (**LnL<sup>3F</sup>**), 298 K] spectra of **LnL<sup>F</sup>**.

antenna photophysical properties in **LnL** without interference from photo- or redox-active **Ln(III)**. Carbostyryl excitation in **GdL** returned antenna fluorescence that was blue-shifted and less intense than that of the corresponding 7-aminocarbostyryl (Fig. S33–S36, ESI†).  $\Phi_L$  was largest for **GdL<sup>3F</sup>** (13%) and smallest for **GdL<sup>6F</sup>** (5.9%), with  $\Phi_L(\text{GdL}^{5F}) = 6.1\%$  and  $\Phi_L(\text{GdL}^H) = 7.6\%$  in between. Steady state emission spectra were recorded at 77 K to determine the antenna  $T_1$  (Fig. S45–S48, ESI†). Notably, fluorination in all three investigated positions lowered the antenna  $T_1$  from 22 500  $\text{cm}^{-1}$  in **GdL<sup>H</sup>**. **GdL<sup>3F</sup>** had the lowest energy  $T_1$  (22 100  $\text{cm}^{-1}$ ), and **GdL<sup>5F</sup>** had the highest, at only 300  $\text{cm}^{-1}$  higher energy. These are small but impactful differences. The  $^5D_4$  emitting level of Tb(III) is located at 20 400  $\text{cm}^{-1}$ , and the antenna  $T_1$  must be at least  $\sim 2000$   $\text{cm}^{-1}$  higher energy to avoid thermal back energy transfer (BET). Thus, **TbL<sup>3F</sup>** and possibly even **TbL<sup>6F</sup>** (but likely not **TbL<sup>5F</sup>**) may be susceptible to BET. Tb(III) complexes that undergo BET are oxygen sensitive, and are useful for  $O_2$ -sensing and cytotoxic singlet oxygen generation.<sup>19,20</sup>  $T_1$  are  $\sim 5000$   $\text{cm}^{-1}$  higher than the emissive  $^5D_0$  level of Eu(III), which is suitable for Eu(III) sensitization.<sup>21</sup>  $T_1$  in **LnL<sup>F</sup>** are closer to the accepting  $^5D_2$  Eu(III) level (21 500  $\text{cm}^{-1}$ ) than in **LnL<sup>H</sup>**, which may result in better energy transfer in the fluorinated complexes.<sup>21,22</sup>

Excitation of **TbL** and **EuL** at  $\lambda_{\text{max}}$  yielded green and red Ln(III) luminescence, respectively (Fig. 2 and Fig. S37–S44, ESI†, Table 2), with residual antenna fluorescence. **TbL** had slightly lower  $\Phi_L$  than the analogous **GdL** likely due to some antenna  $S_1$ -mediated EnT to Tb(III).<sup>6</sup> **EuL** had drastically diminished  $\Phi_L$ , which may be due to a combination of EnT from  $S_1$ , and depopulation of  $S_1$  by PeT. **AcCS<sup>F</sup>** oxidation potentials ( $E_{\text{ox}}$ ) were found by cyclic voltammetry as +1.73, +1.86, and +1.77 V (vs. NHE, for **AcCS<sup>3F</sup>**, **AcCS<sup>5F</sup>**, **AcCS<sup>6F</sup>**, respectively); only 5-fluorination made antenna oxidation more difficult than in **AcCS** ( $E_{\text{ox}} = +1.81$  V). PeT was calculated to be slightly less thermodynamically favoured in **EuL<sup>5F</sup>**, and **EuL<sup>6F</sup>** than in **EuL<sup>H</sup>**, and more favoured in **EuL<sup>3F</sup>** ( $\Delta G(\text{PeT}) = -1.01, -1.14, -0.98$ , and  $-0.97$  eV, for **EuL<sup>H</sup>**, **EuL<sup>3F</sup>**, **EuL<sup>5F</sup>**, and **EuL<sup>6F</sup>**, respectively (see ESI† for details)). Thus, the effects of fluorination on the antenna  $S_1$ ,  $T_1$  and  $E_{\text{ox}}$ , and in turn on  $\Delta G(\text{PeT})$  can be difficult to predict.

Table 2 Photophysical properties of **LnL<sup>F</sup>** (Ln = Eu, Tb),<sup>a</sup> and  $\tau_{\text{rad}}$ ,  $\Phi_{\text{Ln}}$ , and  $\eta_{\text{sens}}$  **EuL<sup>F</sup>**<sup>b</sup>

|                         | $\Phi_L^{cd}$ (%) | $\tau_{\text{fl}}$ (ns)       | $\Phi_{\text{Ln}}^c$ (%) | $\tau_{\text{rad}}$ (ms)              | $\Phi_{\text{Ln}}^d$ (%)              | $\eta_{\text{sens}}$ (%) |
|-------------------------|-------------------|-------------------------------|--------------------------|---------------------------------------|---------------------------------------|--------------------------|
| <b>TbL<sup>H</sup></b>  | 5.1 (67%)         | 0.21(4)                       | 22.5                     | —                                     | —                                     | —                        |
| <b>TbL<sup>3F</sup></b> | 8.1 (63%)         | 0.39(2)                       | 5.6                      | —                                     | —                                     | —                        |
| <b>TbL<sup>5F</sup></b> | 4.6 (75%)         | 0.36(3)                       | 21.7                     | —                                     | —                                     | —                        |
| <b>TbL<sup>6F</sup></b> | 4.6 (78%)         | 0.25(4), 2.40(3) <sup>e</sup> | 16.7                     | —                                     | —                                     | —                        |
| <b>EuL<sup>H</sup></b>  | 0.261 (3.4%)      | —                             | 4.34                     | 5.18 <sup>g</sup> , 4.73 <sup>h</sup> | 11.9 <sup>g</sup> , 13.1 <sup>h</sup> | 36.2 <sup>g</sup>        |
| <b>EuL<sup>3F</sup></b> | 0.680 (5.3%)      | 0.93(6), 0.42(5) <sup>e</sup> | 1.09                     | 9.25 <sup>g</sup> , 5.10 <sup>h</sup> | 6.7 <sup>g</sup> , 12.3 <sup>h</sup>  | 16.1 <sup>g</sup>        |
| <b>EuL<sup>5F</sup></b> | 0.814 (13%)       | 0.47(6), 1.76(5) <sup>e</sup> | 5.05                     | 5.25 <sup>g</sup> , 5.11 <sup>h</sup> | 11.5 <sup>g</sup> , 11.8 <sup>h</sup> | 43.4 <sup>g</sup>        |
| <b>EuL<sup>6F</sup></b> | 0.207 (3.5%)      | 0.20(1), 2.85(5) <sup>e</sup> | 5.10                     | 5.28 <sup>g</sup> , 5.19 <sup>h</sup> | 11.6 <sup>g</sup> , 11.8 <sup>h</sup> | 43.8 <sup>g</sup>        |

<sup>a</sup> [**LnL**] = 10  $\mu\text{M}$  in 10 mM PIPES buffered  $\text{H}_2\text{O}$ , pH 6.5. <sup>b</sup> Determined using the method in ref. 26.  $I_{\text{tot}}/I_{\text{MD}}$ : integral ratio of total Eu-centred corrected emission spectrum (570–800 nm) and  $^5D_0 \rightarrow ^7F_1$  band (582–603 nm),  $A_{\text{MD},0} = 14.65 \text{ s}^{-1}$ ,  $n = 1.333$  (refractive index),<sup>27</sup>  $\tau_{\text{obs}} = \tau_{\text{H}_2\text{O}}$ . <sup>c</sup> Relative to quinine sulfate ( $\Phi = 0.59$ ) in  $\text{H}_2\text{SO}_4$  (0.05 M).<sup>23</sup> <sup>d</sup> In parentheses: compared to **GdL** analogue. <sup>e</sup> Biexponential fit better based on  $\chi^2$ . <sup>f</sup> Too short to measure. <sup>g</sup> Calculated from the steady-state emission spectra. <sup>h</sup> Calculated from the time-resolved emission spectra.

The Ln(III) luminescence lifetimes ( $\tau_{\text{H}_2\text{O}}$ ) were measured by time-resolved emission spectroscopy. The decays were monoexponential.  $\tau_{\text{H}_2\text{O}}$  values varied for Ln = Tb but were almost identical for all **EuL** ( $\sim 0.61$  ms) (Table S4, ESI†). The number of Ln(III)-bound water molecules ( $q$ ) were  $q = 1$  for **EuL**. Deviations for **TbL** from  $q = 1$  could be due to BET, which makes this method inapplicable,<sup>24,25</sup> or the result of the typical error of  $q \pm 0.5$ .

**TbL**<sup>5F</sup> and **TbL**<sup>H</sup> had the highest Tb-centred luminescence quantum yields ( $\Phi_{\text{Ln}} = 21.7\%$  and  $22.5\%$ , respectively, values identical within experimental error). The low  $\Phi_{\text{Ln}}$  of **TbL**<sup>3F</sup> is presumably the result of BET. **EuL**<sup>5F</sup> and **EuL**<sup>6F</sup> had  $\Phi_{\text{Ln}} \sim 5\%$ , which is higher than most Eu(III) complexes with similar structures, i.e. uncharged do3a-based emitters with secondary amide-linked carbostyryl antenna, including **EuL**<sup>H</sup> ( $\Phi_{\text{Ln}} = 4.34\%$ ). **EuL**<sup>3F</sup>, however, had low  $\Phi_{\text{Ln}} = 1.09\%$ . Unlike **TbL**<sup>3F</sup>, **EuL**<sup>3F</sup> does not suffer from BET, therefore, an alternative explanation for the poor performance of this emitter was necessary.

$\Phi_{\text{Ln}}$  is the product of the intrinsic quantum yield of the Ln(III) ( $\phi_{\text{Ln}}^{\text{Ln}}$ ) and the Ln(III) sensitisation efficiency ( $\eta_{\text{sens}}$ , eqn (1)), i.e. the efficiency of Ln(III) excited state population. For Eu(III)  $\phi_{\text{Ln}}^{\text{Ln}}$  can be determined from the corrected emission spectrum.<sup>26</sup>

$$\phi_{\text{Ln}} = \eta_{\text{sens}} \cdot \phi_{\text{Ln}}^{\text{Ln}} = \eta_{\text{sens}} \cdot \frac{\tau_{\text{obs}}}{\tau_{\text{rad}}} \quad (1)$$

In **EuL**<sup>5F</sup> and **EuL**<sup>6F</sup>  $\eta_{\text{sens}}$  is increased compared to **EuL**<sup>H</sup>, presumably due to a combination of the small adjustments in spectral overlap and PeT quenching. **EuL**<sup>3F</sup> had markedly lower  $\eta_{\text{sens}}$  and  $\phi_{\text{Ln}}^{\text{Ln}}$  than the other **EuL** (Table 2). The steady-state and time-resolved **EuL**<sup>3F</sup> emission spectra have different shapes. Eu(III) spectra are sensitive to coordination environment, and these differences indicate the presence of several emissive species.<sup>21</sup> The signal of the slow-decaying component dominating the time-resolved spectrum resembles the **EuL**<sup>5F</sup>/**EuL**<sup>6F</sup>/**EuL**<sup>H</sup> spectra. Contribution from the fast-decaying species modifies the steady-state **EuL**<sup>3F</sup> spectrum. If  $\tau_{\text{obs}}$  is assumed unchanged, the steady-state spectral shape yields a lower overall  $\phi_{\text{Ln}}^{\text{Ln}}$  (Table 2). The spectrum of **TbL**<sup>3F</sup> is similarly time-dependent, but not those of **Eu/TbL**<sup>5F</sup> and **Eu/TbL**<sup>6F</sup>. The reasons for the diminished  $\eta_{\text{sens}}$  of **EuL**<sup>3F</sup> are unclear. PeT is more favoured in **EuL**<sup>3F</sup> than in **EuL**<sup>5F</sup> and **EuL**<sup>6F</sup>, and **EuL**<sup>F</sup> have much lower  $\Phi_{\text{L}}$  than the corresponding **GdL**<sup>F</sup>, which is consistent with PeT quenching. The  $\tau_{\text{fl}}$  of **EuL**<sup>F</sup> and **GdL**<sup>F</sup>, however, cannot be compared directly. The biexponential decay of the **EuL**<sup>F</sup> antenna fluorescence suggested the presence of additional emitters to those seen in **GdL**<sup>F</sup>. Further work is therefore needed to understand the effect of fluorination on EnT and PeT.

In conclusion, monofluorinated 7-aminocarbostyryls, obtained via a photochemical cyclisation, were competent sensitisers of Eu(III) and Tb(III) emission. The position of the fluorine had a dramatic impact on the antenna and Ln(III) photophysical properties, rendering the emission oxygen-sensitive (**TbL**<sup>3F</sup>, **TbL**<sup>4F</sup>), and increasing (**EuL**<sup>5F</sup>, **EuL**<sup>6F</sup>), or decreasing  $\Phi_{\text{Ln}}$  (**TbL**<sup>3F</sup>, **TbL**<sup>6F</sup>, **EuL**<sup>3F</sup>) compared to non-fluorinated **LnL**<sup>H</sup>. 5-Fluorination improved Eu(III) emission without negatively impacting Tb(III) luminescence. Remote fluorination influenced the excited-state behaviour of **LnL**<sup>3F</sup>. Work towards the 4-fluorinated isomer, and ligands containing other EWGs than fluorine is ongoing.

D. K. did all experiments except the crystallographic analysis, which was done by A. O. K. E. B. designed the project, secured funding, and supervised the work. All authors contributed to data analysis and manuscript writing.

This work was funded by Knut och Alice Wallenbergs Stiftelse (Dnr: 2018.0066) and Vetenskapsrådet (2021-04625). We thank Eirini Servetas for help with the synthesis, and Salauat R: Kiraev for the critical reading of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Notes and references

- 1 D. Parker, J. D. Fradgley and K.-L. Wong, *Chem. Soc. Rev.*, 2021, **50**, 8193–8213.
- 2 C. D.-S. Brites, S. Balabhadra and L. D. Carlos, *Adv. Opt. Mater.*, 2019, **7**, 1801239.
- 3 A. de Bettencourt-Dias, in *Luminescence of Lanthanide Ions in Coordination Compounds and Nanomaterials*, John Wiley & Sons Ltd, 2014, ch01, pp. 1–48.
- 4 D. Kovacs and K. E. Borbas, *Coord. Chem. Rev.*, 2018, **364**, 1–9.
- 5 D. Kovacs, X. Lu, L. S. Mészáros, M. Ott, J. Andres and K. E. Borbas, *J. Am. Chem. Soc.*, 2017, **139**, 5756–5767.
- 6 D. Kovacs, E. Mathieu, S. R. Kiraev, J. A.-L. Wells, E. Demeyere, A. Sipos and K. E. Borbas, *J. Am. Chem. Soc.*, 2020, **142**, 13190–13200.
- 7 A. J. Wilkinson, D. Maffeo, A. Beeby, C. E. Foster and J. A.-G. Williams, *Inorg. Chem.*, 2007, **46**, 9438–9449.
- 8 D. Parker, P. K. Senanayake and J. A.-G. Williams, *J. Chem. Soc., Perkin Trans. 2*, 1998, 2129–2139.
- 9 D. Kovacs, S. R. Kiraev, D. Phipps, A. Orthaber and K. E. Borbas, *Inorg. Chem.*, 2020, **59**, 106–117.
- 10 D. Kovacs, D. Phipps, A. Orthaber and K. E. Borbas, *Dalton Trans.*, 2018, **47**, 10702–10714.
- 11 P. B. Glover, A. P. Bassett, P. Nockemann, B. M. Kariuki, R. Van Deun and Z. Pikramenou, *Chem. – Eur. J.*, 2007, **13**, 6308–6320.
- 12 N. A. Meanwell, *J. Med. Chem.*, 2018, **61**, 5822–5880.
- 13 D. Janasik and T. Krawczyk, *Chem. – Eur. J.*, 2022, **28**, e202102556.
- 14 A. M. Kenwright, I. Kuprov, E. De Luca, D. Parker, S. U. Pandya, P. K. Senanayake and D. G. Smith, *Chem. Commun.*, 2008, 2514–2516.
- 15 J. Ruiz-Cabello, B. P. Barnett, P. A. Bottomley and J. W.-M. Bulte, *NMR Biomed.*, 2011, **24**, 114–129.
- 16 X. Deng, J. Rong, L. Wang, N. Vasdev, L. Zhang, L. Josephson and S. H. Liang, *Angew. Chem., Int. Ed.*, 2019, **58**, 2580–2605.
- 17 D. van der Born, A. Pees, A. J. Poot, R. V.-A. Orru, A. D. Windhorst and D. J. Vugts, *Chem. Soc. Rev.*, 2017, **46**, 4709–4773.
- 18 O. Bouazzaoui, K. Rousée, J. K. Mulengi, X. Pannecoucke, J.-P. Bouillon and S. Couve-Bonnaire, *Eur. J. Org. Chem.*, 2018, 3705–3715.
- 19 P. Ung, M. Clerc, H. Huang, K. Qiu, H. Chao, M. Seitz, B. Boyd, B. Graham and G. Gasser, *Inorg. Chem.*, 2017, **56**, 7960–7974.
- 20 G.-L. Law, R. Pal, L. O. Palsson, D. Parker and K.-L. Wong, *Chem. Commun.*, 2009, 7321–7323.
- 21 K. Binnemans, *Coord. Chem. Rev.*, 2015, **295**, 1–45.
- 22 S. Susumu and W. Masanobu, *Bull. Chem. Soc. Jpn.*, 1970, **43**, 1955–1962.
- 23 K. Suzuki, A. Kobayashi, S. Kaneko, K. Takehira, T. Yoshihara, H. Ishida, Y. Shiina, S. Oishi and S. Tobita, *Phys. Chem. Chem. Phys.*, 2009, **11**, 9850–9860.
- 24 A. Beeby, I. M. Clarkson, R. S. Dickens, S. Faulkner, D. Parker, L. Royle, S. A.-S. de, J. A.-G. Williams and M. Woods, *J. Chem. Soc., Perkin Trans. 2*, 1999, 493–504.
- 25 R. M. Supkowski and W. D. Horrocks Jr., *Inorg. Chim. Acta*, 2002, **340**, 44–48.
- 26 M. H.-V. Werts, R. T.-F. Jukes and J. W. Verhoeven, *Phys. Chem. Chem. Phys.*, 2002, **4**, 1542–1548.
- 27 A. H. Harvey, J. S. Gallagher and J. M.-H. L. Sengers, *J. Phys. Chem. Ref. Data*, 1998, **27**, 761–774.

