


 Cite this: *RSC Adv.*, 2022, 12, 26307

Enhanced transformation of CO₂ over microporous Ce-doped Zr metal–organic frameworks†

 Juan Bai,^a Ziwei Song,^{ib} *^a Lijuan Liu,^a Xu Zhu,^a Faming Gao^{ib} *^a and Raghunath V. Chaudhari^{ib} *^b

Metal–organic frameworks (MOF) have been studied extensively for the adsorption and catalytic conversion of CO₂. However, previous studies mainly focused on the adsorption capabilities of partially or totally Ce substituted UiO-66, there are few studies focusing on transformation of the structure and catalytic activity of these materials. In this work, a series of Zr/Ce-based MOFs with UiO-66 architecture catalysts were prepared for the conversion of CO₂ into value-added dimethyl carbonate (DMC). Owing to the different addition order of the two metals, significantly varied shapes and sizes were observed. Accordingly, the catalytic activity is greatly varied by adding a second metal. The different catalytic activities may arise from the different acid–base properties after Ce doping as well as the morphology and shape changes. Besides, the formation of terminal methoxy (t-OCH₃) was found to be the rate limiting step. Finally, the reaction mechanism of CO₂ transformation in the presence of a dehydrating agent was proposed.

 Received 27th April 2022
 Accepted 5th September 2022

DOI: 10.1039/d2ra02680e

rsc.li/rsc-advances


Introduction

As the major greenhouse gas leading to global warming, carbon dioxide (CO₂) has attracted a lot of attention from both academic and industry communities. The development of efficient methods to convert CO₂ into value-added chemicals is the key to realize a carbon-neutral society.^{1,2} CO₂ can be used as an environmental friendly C1 feedstock for its high natural abundance, easy availability and environment benign properties.^{3,4} However, for its inherent inertness, only a few processes using CO₂ have been successfully commercialized.⁵ To overcome the inertness, high-energy starting materials are usually used, such as hydrogen, alkylene oxides, low-carbon, and organometallic rings, *etc.*^{6–9} Choosing low-energy synthetic targets, such as organic carbonates, is also a crucial strategy to convert CO₂. As the simplest organic carbonate, DMC has drawn a lot of attention due to its easy degradation, low toxicity and effective substitution of phosgene, dimethyl sulfate and methyl halide in organic synthesis processes.^{10,11} And the direct synthesis of DMC from CO₂ and CH₃OH has become one of the most attractive processes (as shown in Scheme 1(a)).^{12–14}

The direct catalytic conversion of CO₂ to DMC is simple, clean and with high atom efficiency. But because of the extreme thermodynamic limitation, achieving high DMC yield is still challenging.¹⁵ Besides, the H₂O formed during the reaction

leads to the easily deactivation of the catalysts. To overcome these challenges, various catalytic systems have been developed, such as ionic liquids,^{16,17} alkali carbonates,^{18,19} metal oxides,^{20,21} supported metal oxides,²² heteropoly acids,²³ metal–organic frameworks,^{24,25} *etc.* Among these catalysts, metal–organic frameworks (MOFs) show a promising prospect.

MOFs are porous materials formed by metal ions or metal clusters with organic bridging linkers, showing a diverse range of potential applications, such as used for gas adsorption, catalysis, ionic conduction, *etc.*^{26–28} Previous studies showed

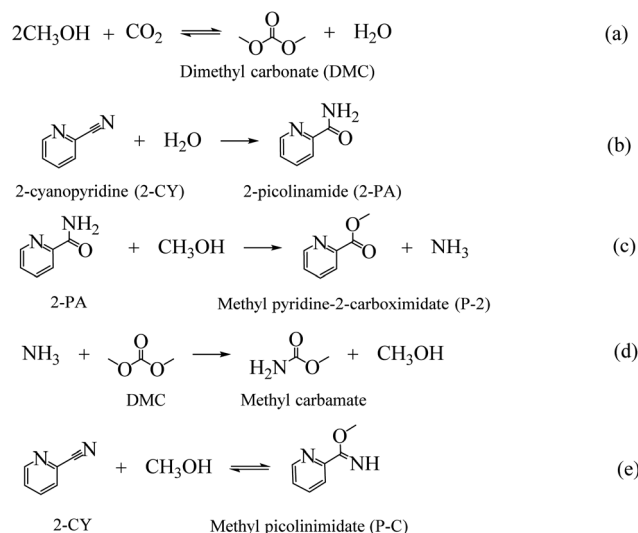

Scheme 1 Reactions involved in the reaction of CO₂ and MeOH with 2-cyanopyridine as dehydrating agent.

^aHebei Key Laboratory of Applied Chemistry, School of Environmental and Chemical Engineering, Yanshan University, Qinhuangdao 066004, China

^bCenter for Environmentally Beneficial Catalysis, Department of Chemical & Petroleum Engineering, University of Kansas, 1530 W15th Street, Lawrence, Kansas 66045, USA

 † Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2ra02680e>


that MOFs offer excellent capacities of CO₂ uptake due to its ultra-high surface areas.²⁹ MOFs can also be used as catalyst for CO₂ conversion.²⁷ The extreme stable UiO-66 was reported to be active for the conversion of CO₂ with 100% selectivity of DMC without dehydrating agent, but with a low DMC yield of around 0.015%.³⁰ Studies demonstrated that the catalytic activity of MOFs could be tuned by introducing/substituting the functional group in an organic linker.^{31,32} Xuan K. and co-workers modified UiO-66 (Zr) with trifluoroacetic acid (TFA), a higher DMC yield (~0.084%) was observed, which could be attributed to the increased number of active sites and the enlargement of porosity originated from TFA modulation.³⁰ In addition, the exchange of the metal ions in UiO-66 by Hf, Ti and Ce could also be used to adjust the catalytic activity of MOFs. Vasudeva and co-workers found that after changing Zr to Hf in the nodes of UiO-66, the TOF of the material for solketal synthesis increased from 153 h⁻¹ to 13 886 h⁻¹, increased by 90 times.³³

Owing to its high oxygen mobility, easy and reversible transition between Ce⁴⁺ and Ce³⁺, introducing Ce into MOF materials has also been implemented.^{34,35} Nouar *et al.* partially substituted Zr in UiO-66 by Ce, leading to easy catalytic decomposition of the methanol, which can be attributed to structural defects and redox activity generated from the introduction of Ce.³⁵ Besides, Stawowy's research found that missing linker molecules in UiO-66(Ce) results in enhanced CO₂ adsorption.³² All these properties obtained through Ce doping can benefit the direct conversion of CO₂. However, to the best of our knowledge, previous studies mainly focused on the adsorption capabilities of partially or totally Ce substituted UiO-66, there are few studies focusing on transformation of the structure and catalytic activity of these materials. In this study, a series of UiO-66 MOFs were prepared and evaluated for the CO₂ conversion to address the transformation of morphologies, structures, texture properties, and catalytic activity that caused by Ce substitution. Furthermore, the cause of the activity difference and the reaction mechanism of CO₂ conversion on MOF were proposed based on experimental and characterization results.

Experimental

Materials

Zirconium chloride (ZrCl₄, 98%), ammonium ceric nitrate ((NH₄)₂Ce(NO₃)₆, 99.9%), terephthalic acid (BDC, 99%), *N,N*-dimethylformamide (DMF, 98%), methanol anhydrous (99.0%), mesitylene (99%) and dimethyl carbonate (DMC, 99%), were purchased from Aladdin Industrial Inc. (Shanghai, China). CO₂ (99.9%) and N₂ (99%) were purchased from Tianjin Vista Technology Co., Ltd. All chemicals were used without further purification.

Catalyst preparation

The Zr-based MOFs were prepared using the following method: 1.16 g ZrCl₄ and 0.84 g terephthalic acid were fully dissolved in 125 ml of DMF, then the mixed solution was vigorously stirred for 30 min. After this, the solution was transferred into a sealed

Teflon-lined autoclave and heated at 120 °C for 24 h. After cooling to room temperature, the white precipitate was collected and washed with DMF and acetone to remove the unreacted ions. Zr-MOFs were finally obtained after drying at 70 °C for 4 h. Ce-MOFs were prepared following the same procedure using (NH₄)₂Ce(NO₃)₆ as precursor.

For Ce doped Zr-MOF and Zr doped Ce-MOF catalysts, the preparation procedure is as follows: 2.79 g (NH₄)₂Ce(NO₃)₆/1.16 g ZrCl₄ was dissolved in 50 ml DMF and stirred for 30 min, denoted as A solution. 1.16 g ZrCl₄/2.79 g (NH₄)₂Ce(NO₃)₆ and 0.84 g BDC were dissolved in 125 ml DMF and stirred for 30 min, denoted as B solution. Then A solution was dropwise added to B solution at room temperature under vigorous stirring. After this, the mixture was vigorously stirred for 30 min at room temperature. Then the same procedure as that of Zr-MOF was applied.

Catalyst characterization

Wide angle XRD patterns of the samples were collected on an X-ray Diffraction Smart Lab using Cu K α radiation ($\lambda = 1.5406 \text{ \AA}$), operated at 40 kV and 30 mA with the scanning range 5–60° at a scanning rate of 5° min⁻¹. Transmission electron microscope (TEM) of the catalyst samples were obtained on a HT770 instrument at an electron acceleration voltage of 120 kV. Scanning electron microscope (SEM) images were captured on a SUPRA 55 field-emission microscope operating at the beam energy of 10.0 kV. The sample powder was stacked on a conducting resin and sprayed with gold for 60 s to gain conductivity.

The textural properties of the synthesized catalyst were determined by N₂-adsorption-desorption isotherms using Autosorb iQ-Chemisorption & Physisorption Gas Sorption Analyzer. The specific surface area was evaluated by the Brunauer-Emmett-Teller (BET) method and pore size distribution of the samples was determined by the Horvath-Kawazoe (HK) method.

XPS spectra were recorded with X-ray photo electron spectrometer Escalab 250Xi apparatus with an Al-K α X-ray source ($h\nu = 1486.6 \text{ eV}$) and a monochromator. The XPS measurement was carried out in the electron binding energy ranges corresponding to carbon 1s, oxygen 1s, zirconium 3d and cerium 3d core excitations. Spectra were deconvoluted by using XPSPEAK 4.0 software. The peak was fitted using Lorentzian-Gaussian function with an asymmetric parameter of 0.

Elemental analysis was performed over an Agilent-7700 inductively coupled plasma mass spectrometry (ICP-MS). 50 mg sample was dissolved and diluted for the analysis.

Fourier transform infrared (FT-IR) spectra for the catalyst samples were recorded in the range of 500–4000 cm⁻¹ on a FT-IR Nicolet iS10 spectrometer. The acidity of the samples was also detected using FT-IR with pyridine as probe molecule. The catalyst samples were immersed in pyridine stream for 24 hours and then dried under vacuum at 60 °C for 8 hours. After cooling to room temperature, the FT-IR spectra of the samples were collected. Diffuse-reflectance UV-Vis absorption spectra were acquired using a UV-2550 spectrometer in the range of 200–



600 nm at room temperature at a scanning wavelength interval of 0.5 nm.

Acid–base properties of the samples were studied by temperature-programmed desorption of ammonia (NH₃-TPD) and temperature-programmed desorption of carbon dioxide (CO₂-TPD) on a BELCAT-B instrument. Prior to adsorption, the sample was pretreated by argon (40 ml min⁻¹) at 150 °C for 1 h. After cooling to room temperature, the argon was switched to NH₃ or CO₂ (40 ml min⁻¹) for 1 h to perform the adsorptive process. The physisorbed NH₃ or CO₂ was then flushed by argon at room temperature for 1 h. The desorption process was conducted in argon (40 ml min⁻¹) from room temperature to 450 °C with a heating rate of 10 °C min⁻¹.

Catalyst activity test

The direct synthesis of DMC from CO₂ and CH₃OH was carried out in a 100 ml stainless-steel autoclave equipped with provisions for temperature control and agitation speed control. A schematic of the experimental setup is shown in Fig. S1.† In a typical experiment, a desired amount of CH₃OH, 2-cyanopyridine (dehydrating agent), mesitylene (internal standard) and catalyst were introduced into the reactor and the mixture was purged with N₂ for three times to remove the air in the sealed reactor. Then a certain amount of CO₂ was charged into the reactor. After reaching the target temperature at a low stirring speed, turning the stirring rate to 900 rpm, signifying the start of the reaction.

All the liquid samples were analyzed using an Agilent gas chromatography (GC-7890A) equipped with a WAX capillary

column and a flame ionization detector (FID). MeOH conversion and the turn over frequency (TOF) as follows:

$$\text{MeOH conversion} = 1 - \frac{\text{final moles of methanol (mmol)}}{\text{initial moles of methanol (mmol)}} \times 100\%$$

$$\text{TOF} = 1$$

$$\frac{\text{moles of DMC methanol (mmol)}}{\text{moles of metal on the surface of catalyst (mmol)} \times \text{time (h)}}$$

Results and discussion

Structure and morphology analysis

The crystalline structures of the as-synthesized MOFs have been characterized by XRD, as shown in Fig. 1(a). Typical diffraction peaks at 7.5°, 8.8° and 25.9° were detected for Zr-MOF, corresponding to the lattice planes of (111), (002) and (224) of UiO-66, indicating the successful synthesis of UiO-66 material.^{30,36,37} With the doping of the second metal Ce [Ce–Zr-MOF blue line in Fig. 1(a)], the intensity peaks of the material increased sharply, suggesting doping of Ce enhances the crystallinity of UiO-66 material. For the Ce-MOF, obvious diffraction peaks located at 7.2°, 8.4°, and 24.9° were also discovered, suggesting the successful formation of Ce-UiO-66.^{32,38} However, when trying to dope Zr in Ce-MOF using the same procedure, similar pattern as

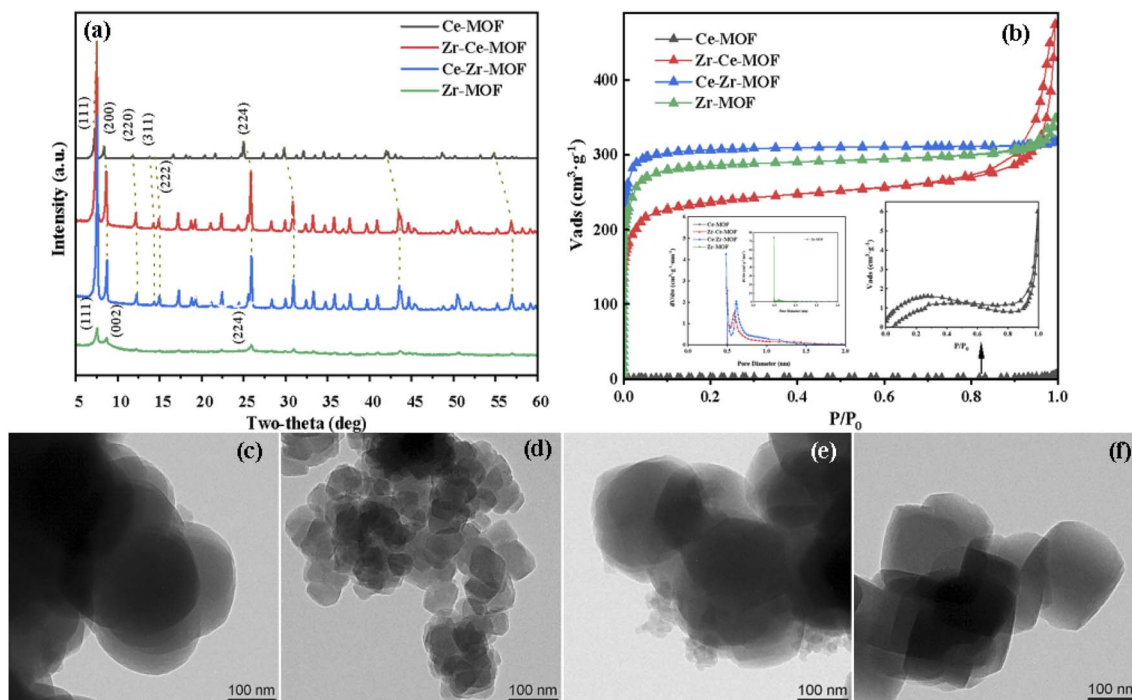


Fig. 1 (a) XRD patterns of Zr/Ce-based MOF materials, (b) N₂-adsorption–desorption isotherm, TEM images of (c) Ce-MOF; (d) Zr–Ce-MOF; (e) Ce–Zr-MOF; (f) Zr-MOF.



that of Ce–Zr–MOF was detected, showing that when Ce and Zr are co-existing during the preparation, Zr is more easily to be incorporated into the UiO-66 frameworks (the metal nodes are mainly Zr, and Ce is existing as dopant).

Interestingly, with doping of Ce in the material, obvious structural distortion (blue shift in the XRD patterns) was detected, as shown in Fig. 1(a). It can be clearly seen that, with the increasing content of Ce in the materials, the distortion is more obvious. For example, the reflection angle of the (111) facet for Zr–MOF is at 7.62° , while for other three materials, the angle has shifted to 7.5° for Zr–Ce–MOF and Ce–Zr–MOF, and to 7.24° for Ce–MOF. Similar shift has also been observed for other planes, corroborating that the second metal has been successfully incorporated into the framework lattice. Specifically, lattice compression may be due to the different radii of Ce^{4+} (0.97 Å) and Zr^{4+} (0.84 Å).^{32,39} Besides, different valence state of Ce (Ce^{3+}) can also lead to deformation of the crystal structure. Furthermore, apparent morphology change has been observed by TEM after incorporation of Ce or Zr into the MOF materials, as shown in Fig. 1(c)–(f). Evolution from tetrahedron to spherical was detected after doping of the second metal. In addition, much smaller particle size for Zr–Ce–MOF than the other three materials was observed. The decreasing particle size indicates that the addition order of the metals plays a significant role in the formation of the solid composite.

N_2 adsorption–desorption analysis was carried out to characterize the textural properties of the samples, as shown in Fig. 1(b). The adsorption isotherms of all these catalysts exhibited type I behavior, suggesting microporous structure for all material.^{31,40,41} However, for the material Zr–Ce–MOF, H3 type of hysteresis loop was detected, indicating possible existence of mesopores in this material.^{40,42} The corresponding textural properties (BET surface area, pore volume) are listed in Table 1. It is noted that Zr–MOF showed the highest surface area ($1159.00 \text{ m}^2 \text{ g}^{-1}$) than the other three materials. However, with the introduction of Ce, the surface area began to decrease, from $1159.00 \text{ m}^2 \text{ g}^{-1}$ to $960.40 \text{ m}^2 \text{ g}^{-1}$ (Ce–Zr–MOF) to $757.91 \text{ m}^2 \text{ g}^{-1}$ (Zr–Ce–MOF). Interestingly, for all the three materials, the pore size is in the same range of 0.5–1.0 nm [as shown in Fig. 1(b)], confirming again that the materials are microporous material.⁴³ Nevertheless, there is no obvious trend for the amount of micropores. For the Ce–MOF, extremely small surface area was detected (as shown in Table 1). Ar atmosphere isothermal

adsorption and desorption analysis was also performed, the results of which are shown in Table S1 (ESI†). Similar small surface area and small pore size were observed, which may result from the non-porous structure of this material, or smaller pore size of this material [smaller than the kinetic diameter of N_2 (0.364 nm), N_2 cannot enter into the pores, only adsorption on the surface occurred] or that the pore structure was collapsed during the N_2 -adsorption–desorption process. Furthermore, no obvious pore structure was observed on the surface from the SEM images (Fig. S4†), indicating super-microporous or non-porous structure of Ce–MOF. Additionally, the Ce–MOF has been prepared for three times, with nearly the same textural properties, which are also included in Table S1.†

Overall, the above results confirmed that both the single metal MOFs and the doped MOFs are successfully synthesized, all of which are crystalline microporous materials with high surface area (above $758 \text{ m}^2 \text{ g}^{-1}$). Besides, when trying to incorporate Zr into the Ce–MOF frameworks, a tetragonal particle shape (more like Zr–MOF) was obtained. Similar phenomenon was observed for the Ce–Zr–MOF preparation, which possessed the shape of the Ce–MOF.

Optimization of CO_2 to DMC conversion

Catalytic evaluation of the MOF materials as well as optimization of the reaction conditions, including temperature, pressure, reaction time and reactant/dehydrating agent ratio was carried out to improve the activity and DMC yield. Firstly, the catalytic activities of the MOF samples were measured by converting CO_2 and methanol in the presence of 2-cyanopyridine (2-CY, dehydrating agent, shown in Scheme 1) at 150°C under 2.6 MPa CO_2 pressure for 6 hours (see Experimental section for details) with DMC as the target product.^{14,44} The catalytic methanol conversion, DMC yield and TOF of the MOF composites are displayed in Fig. 2(a). Interestingly, the conversion and activity were significantly increased when Ce was introduced into the MOF framework (Fig. 2) and then decreased when pure Ce–MOF is used (Fig. 2). In particular, Zr–Ce–MOF exhibits the highest DMC amount of 3.03 mmol and the highest TOF of 0.92 h^{-1} . It could be noted that the DMC amount changes were closely related to Ce content (Table 2), proving that an appropriate amount of Ce can facilitate DMC production pathway. Additionally, pore volume seems to play an important role in the catalytic activity of materials.⁴⁵ Surprisingly, 10.7% methanol was converted and 1.36 mmol DMC was formed without the presence of catalyst. Previous studies have shown that 2-CY not only drastically improved the carbonate yields by breaking the thermodynamic limit, it also could activate the carbonyl bond of CO_2 as a catalyst.¹⁴ However, when the reaction was carried out without dehydrating agent, both the methanol conversion and DMC formation decreased significantly, indicating the critical role of dehydrating agent. In addition, the Zr–Ce–MOF material was also compared with other materials for the CO_2 conversion, as shown in Table S2 in the ESI.† From the table, it is known that a relative high activity and DMC yield can be obtained over Zr–Ce–MOF under a milder reaction conditions compared to other materials. Therefore, Zr–

Table 1 The BET surface area ($\text{m}^2 \text{ g}^{-1}$), and pore volume ($\text{cm}^3 \text{ g}^{-1}$) of the samples

Samples	Surface area ^a ($\text{m}^2 \text{ g}^{-1}$)	Pore volume ^a ($\text{cm}^3 \text{ g}^{-1}$)	Micropore volume ^a ($\text{cm}^3 \text{ g}^{-1}$)
Ce–MOF	4.61	0.013	0.001
Zr–Ce–MOF	757.91	0.73	0.28
Ce–Zr–MOF	960.40	0.49	0.44
Zr–MOF	1159.00	0.54	0.37

^a Determined by N_2 -adsorption–desorption isotherms.



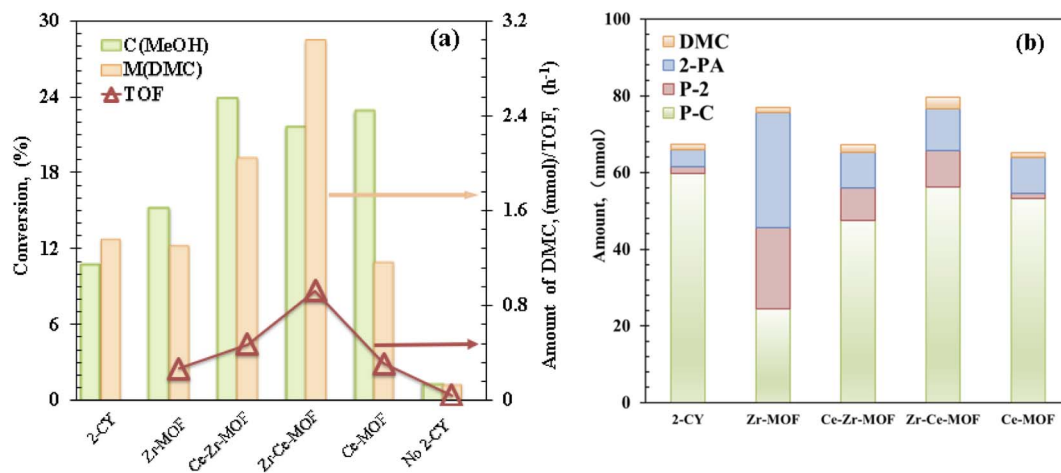


Fig. 2 (a) Catalytic evaluation and (b) product distribution of Zr/Ce-based MOF materials. Reaction conditions: 0.5 mol MeOH, 0.25 mol 2-cyanopyridine, $T = 150\text{ }^{\circ}\text{C}$, $P = 2.6\text{ MPa}$, $t = 6\text{ h}$.

Table 2 Elements distribution from XPS analysis

Samples	Conc. (wt%) of elements ^a				Conc. (wt%) of elements ^b			
	Ce	Zr	C	O	Ce	Zr	Conc. ^a of Ce ³⁺ (wt%)	Conc. ^a of O _v (wt%)
Ce-MOF	34.02	0	41.72	24.26	20.97	0	62.87	18.67
Zr-Ce-MOF	3.83	17.23	51.31	27.63	1.16	23.85	52.37	28.92
Ce-Zr-MOF	1.72	24.44	45.35	28.49	1.23	19.62	19.88	21.89
Zr-MOF	0	26.25	44.16	29.59	0	17.61	—	19.74

^a Concentration of Ce³⁺ and O_v is estimated from XPS data. ^b Determined by ICP-MS.

Ce-MOF is a promising catalyst that could be used for CO₂ transformation.

As shown in Scheme 1, except for the hydration of 2-CY, several other reactions are also involved in the reaction system. The evolution of the formation of the chemicals with different MOF composites are displayed in Fig. 2(b). It is noted that after doping Ce, the activity for the hydration of 2-CY (blue) and reaction of 2-PA with methanol (red) was significantly decreased (total formation of 2-PA and P-2 decreased from 51.11 mmol to 17.83–20.42 mmol). In particular, when Ce-MOF was used, the reaction of 2-PA with methanol (red) diminished to nearly none, only 1.3 mmol of P-2 was formed. However, Zr-MOF has the smallest activity for the reaction of 2-CY with methanol (green), indicating there is competition for the synthesis of the side-products.

Next, the reaction temperature of the Zr-Ce-MOF catalyst was optimized from 140 °C to 170 °C [Fig. 3(a)]. When the temperature was increased, the catalytic activity first increased and then decreased, reaching an optimum DMC value at 160 °C. On the other hand, yields of by-products such as 2-PA and P-2 were also followed the same trend. But yield of P-C decreased with increasing temperature, indicating over-reactions and side reactions take place more easily at lower temperatures. As these by-products is not favorable for DMC synthesis, the optimal reaction temperature is determined to be 160 °C.

The effect of CO₂ pressure was investigated in the range of 1.6 to 4.6 MPa, and the results are shown in Fig. 3(b). DMC formation increased with increasing CO₂ pressure. Moderate amount (1.57 mmol) of DMC was obtained in the presence of 1.6 MPa of CO₂, and higher yield (4.62 mmol) was achieved using 4.6 MPa CO₂. In contrast, the yields of these by-products were increased with increasing CO₂ pressure till 2.6 MPa, then decreased with further increasing CO₂ pressure. As these by-products are produced through reaction with methanol as shown in Scheme 1, and alcohol is known to be activated on acid–base pair sites.^{46–49} Considering that CO₂ can also be strongly adsorbed on the acid–base pair sites, high pressure CO₂ will suppress the formation of these by-products by covering the active sites.^{47,48}

As for the effect of molar ratio of methanol to 2-CY, the DMC formation amount was found to be increased with increasing molar ratio. When the molar ratio of methanol to 2-CY was changed from 1 : 4 to 4 : 1, the DMC formation increased to 4.95 mmol from 0.51 mmol, while the P-C formation first increased then decreased to varying degrees. These results suggested that high MeOH concentration enhances the formation of DMC and inhibits the formation of by-products. Previous studies have also shown that the molar ratio of methanol to 2-CY plays a crucial role in the reaction.¹⁴



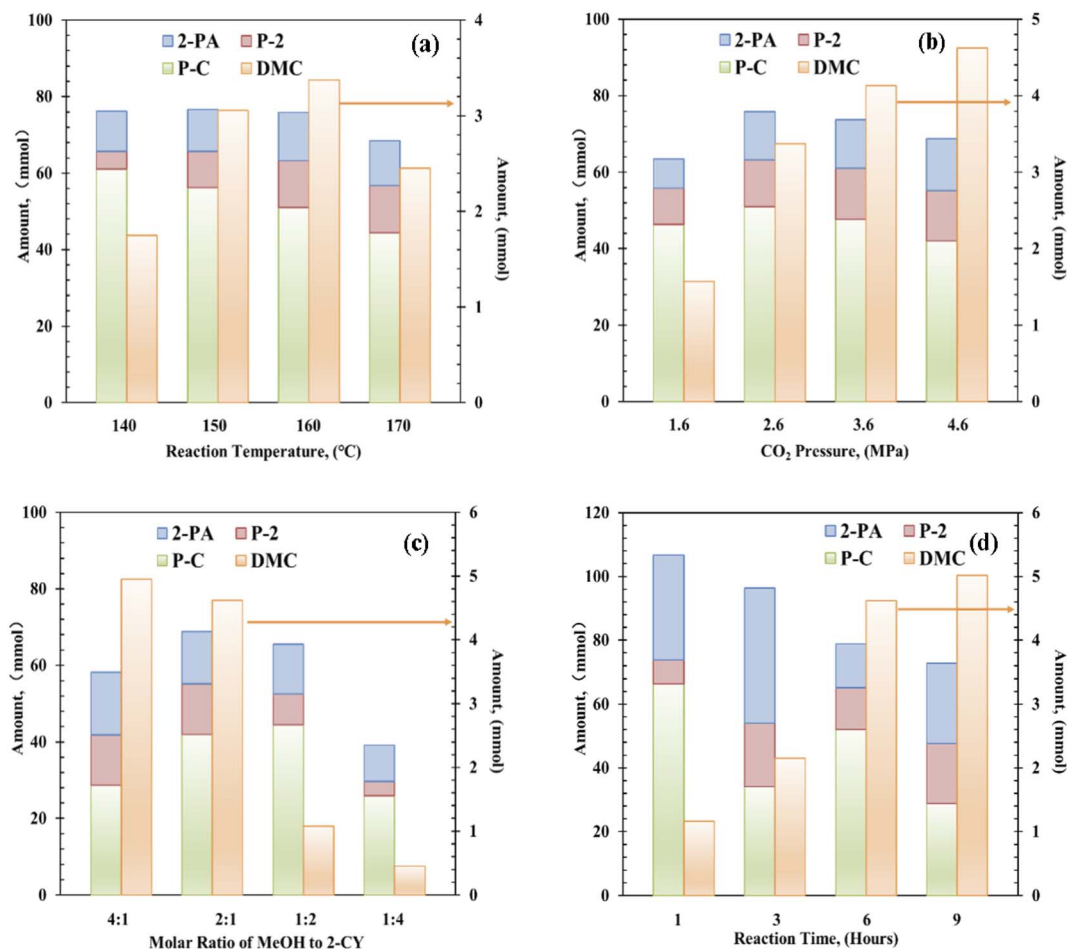


Fig. 3 Effect of (a) reaction temperature, (b) CO₂ pressure, (c) molar ratio of methanol to 2-CY, and (d) reaction time in the reaction of CH₃OH + CO₂ + 2-cyanopyridine system. Reaction conditions: catalyst: 0.1–0.8 g, CH₃OH : 2-cyanopyridine = 4 : 1 to 1 : 4, CO₂: 1.6–4.6 MPa, reaction time: 1–9 h.

Finally, the reaction time effect in DMC synthesis from CO₂ and methanol was studied. Interestingly, in 1 h only 1.16 mmol of DMC was formed, but large amount of P-C was synthesized (~66.30 mmol), indicating faster reaction rate of 2-CY with methanol than CO₂ with methanol. With increasing reaction time, DMC amount increased significantly, when the reaction time reached 9 h, DMC amount reached 5.02 mmol. Meanwhile, the amount of by-products was decreased with increasing reaction time. Especially, the amount of P-C dropped significantly with reaction time, which is attributed to the reversible reaction (e) in Scheme 1. These results show that an obvious competition is existing between the DMC formation and P-C formation.

Catalytic activity discussion

The surface chemical composition and electronic states of the four MOF materials were studied by XPS measurements, the obtained wide scan spectrum is shown in Fig. S2,[†] and the element composition information is summarized in Table 2. The corresponding high-resolution XPS spectra of C 1s, O 1s, Zr 3d and Ce 3d were fitted and demonstrated in Fig. 4(a)–(d),

respectively. Fig. 4(a) shows that C 1s spectrum of all the four MOF materials exhibit three peaks, which are well recognized as being characteristics of C–C (284.8 eV), C–O (286.2 eV) and O–C=O (288.8 eV).^{50,51} Similarly, the O 1s region can be resolved into three peaks for all the catalysts [Fig. 4(b)]. The peak with the lower BE at 530–531.0 eV is associated with the lattice oxygen, while the peak with higher BE at 531.5–531.9 eV can be ascribed to the oxygen in BDC ligand, and the one at 533.1 eV representing the vacancy oxygen.^{52–54} It is worth noting that the position of the lattice oxygen in the samples is located at 531.9 eV for Zr-MOF, which shifts towards lower values (531.7 eV) after incorporating Ce into the framework. This result indicates that the Ce has been successfully incorporated into the Zr-MOF framework, leading to an altered electronic structure of the O atoms in the lattice due to different electron-withdrawing effect of Ce and Zr.

In the high-resolution Zr 3d spectra [Fig. 4(c)], two peaks at around 182.9 eV and 185.3 eV were observed, which represents Zr 3d_{5/2} of the zirconium atoms in Zr₆ clusters and Zr 3d_{3/2} of the zirconium atoms in missing-linker defects, respectively.^{30,50} Besides, with the introduction of Ce, the binding energies of Zr



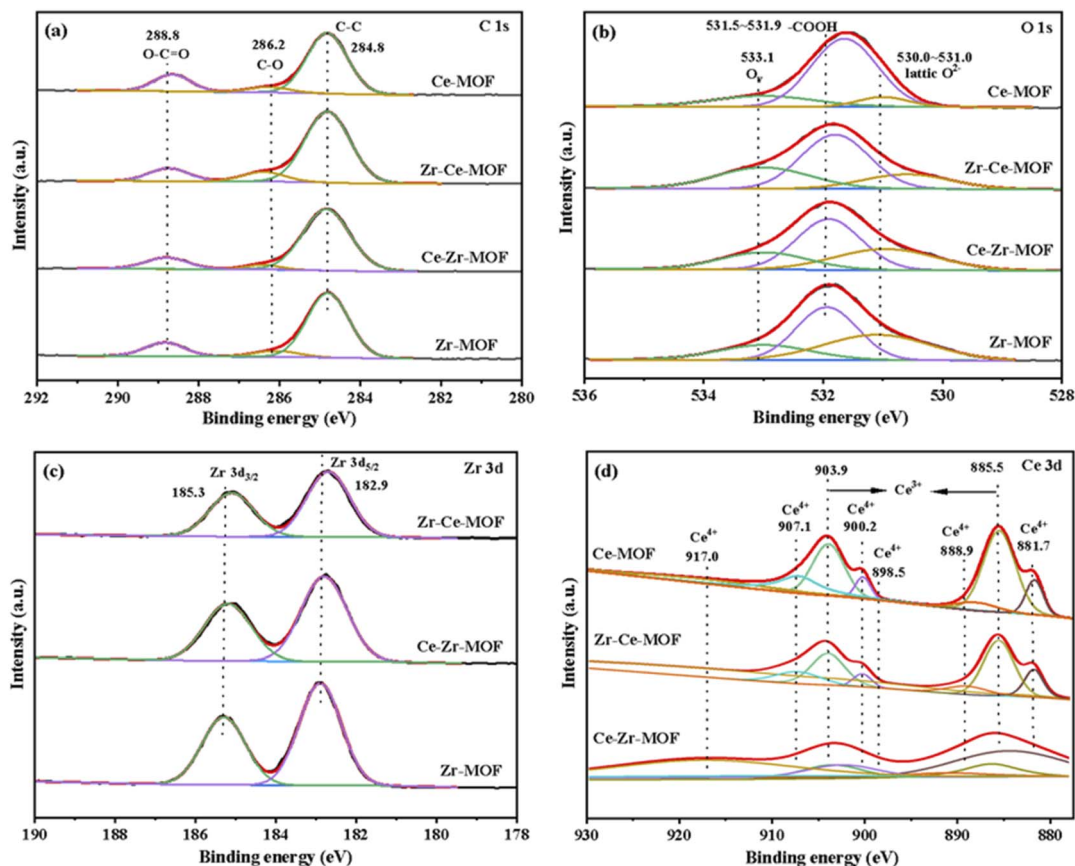


Fig. 4 The XPS spectra of (a) C 1s; (b) O 1s; (c) Zr 3d; (d) Ce 3d.

3d shifted to lower energies [Fig. 4(c)], indicating the successful introduction of Ce into the material, which is consistent with the results from XRD. Furthermore, with the increasing content of Ce in the material (as shown in Table 2), more obvious shift was detected, which could be attributed to the varies electron withdrawing capability of Ce and Zr.

The Ce 3d spectrum could be deconvoluted into four pairs of spin-orbital doublet peaks ($3d_{3/2}$ and $3d_{5/2}$) as shown in Fig. 4(d): 881.7 eV/900.2 eV, 885.5 eV/903.9 eV, 888.9 eV/907.1 eV and 898.5 eV/917.0 eV. The peaks at 881.7 eV/900.2 eV, 888.9 eV/907.1 eV and 898.5 eV/917.0 eV are assigned to Ce(IV) species, while the peaks at 885.5 eV/903.9 eV are attributed to Ce(III) species.^{55,56} These results reveal co-existence of Ce(III) species and Ce(IV) species on the surface of Ce-MOF, Zr-Ce-MOF and Ce-Zr-MOF, which leads to more defects in the material. Defects in UiO-66 is known to enhance Lewis acidic sites, hence, more Lewis acidic sites should be found in Zr-Ce-MOF and Ce-Zr-MOF. To verify this, the pyridine-IR analysis of the samples was investigated, and the result is shown in Fig. 6(c). Zr-Ce-MOF and Ce-Zr-MOF presented much higher peak than pure Zr-MOF and Ce-MOF at 1580 cm^{-1} .

The authentic composition of these four MOF materials was also investigated by ICP-MS, and the metal loading was summarized in Table 2. Notably, the total metal mass fraction increased from 17.61 wt% to 20.85 wt%, wherein Zr content improved from 17.61 wt% to 19.62 wt% when Ce was doped into

the Zr-MOF, indicating that Ce doping is conducive to generation of active sites. On the other hand, if Zr was added later, the bulk Ce decreased from 20.97 wt% to 1.16 wt%, while the content of Zr was as high as 23.85 wt%, suggesting a stronger coordination of Zr metal with the organic linker than Ce. Furthermore, higher surface Ce content on Zr-Ce-MOF than on Ce-Zr-MOF was detected, demonstrating the crucial role Ce played for the CO_2 transformation reaction, which is consistent with previous reports.^{46,74}

The preceding discussed XRD and XPS results gave a strong indication that the incorporation of Ce had been achieved. In order to ascertain if this had any effect on other properties of MOF materials, UV-Vis DRS analyses were conducted, as shown in Fig. 5(a). After incorporation of Ce into the Zr-MOF, the absorption edge of the composite displayed an obvious red-shift, from 341 nm in the UV region to 409 nm and 419 nm in the visible light region, indicating the composite begins to absorb visible light after introduction of Ce, which could be attributed to both the structure effect and the electronic effect.^{57,58} Especially, for the Ce-MOF, the absorption edge was approximately 450 nm [Fig. 5(a)]. In addition, the optical band gaps of the as-prepared materials were calculated using Kubelka-Munk (KM) method, and the results are demonstrated in Fig. 5(b).^{46,59,60} It can be clearly seen that with the increasing content of Ce in the MOF (Zr-MOF, Ce-Zr-MOF, Zr-Ce-MOF and Ce-MOF), the band gaps decrease ($3.53\text{ eV} > 2.88\text{ eV} > 2.87\text{ eV} >$



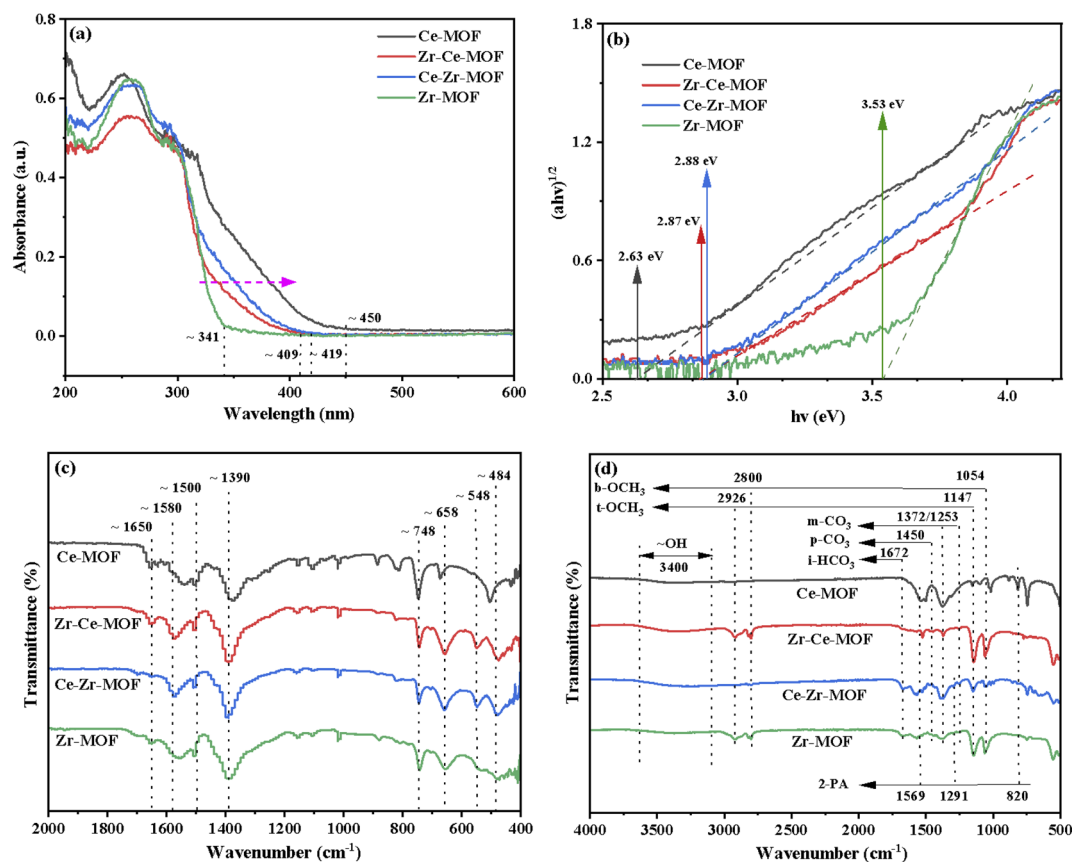


Fig. 5 (a) UV-Vis diffuse absorbance spectra, (b) Tauc plots, (c) FT-IR spectra of fresh Zr/Ce-based MOF materials and (d) FT-IR spectra of used Zr/Ce-based MOF materials.

2.63 eV). Previous reports have shown that band gap changes indicates obvious changes in the amount of defects in the materials, especially the oxygen vacancy change.^{46,61} Thus, the results indicate that the substitution of Ce with Zr species leads to the formation of oxygen vacancy in the material through distorting the lattice structure.

To further investigate the chemical structure of the MOF materials, FT-IR spectra were obtained, as shown in Fig. 5(c). The characteristic peak of the C=O stretching vibration from BDC in the frameworks at 1650 cm^{-1} are detected in all the four materials.³⁹ However, the one for Ce-MOF is wider compared to that of the other three MOFs, indicating that the Ce ions in the material have been successfully coordinated with the C=O of the BDC ligand.⁶² All materials show intense bands at 1580 cm^{-1} and 1390 cm^{-1} , corresponding to the asymmetric and symmetric stretching vibrations of the -COOH from BDC ligand.⁶³ The bands at 1500 cm^{-1} and 748 cm^{-1} could be assigned to the typical vibration of C=C and the bending vibration of C-H on the benzene ring, respectively.^{52,54} For Zr-MOF, Zr-Ce-MOF and Ce-Zr-MOF, characteristic peaks for stretching vibration of Zr-O_{μ₃-O} and Zr-O_{μ₃-OH} bonds of the Zr₆ cluster at 658 cm^{-1} and 484 cm^{-1} were detected, verifying again that Zr-MOF structures can be formed more easily when Ce and Zr co-existing during the preparation procedure.⁶³ An obvious shift for the two peaks was observed for Ce-MOF, suggesting

similar structure of Ce-MOF to that of Zr-MOF. In the low-frequency region, the band near 548 cm^{-1} is ascribed to Zr-O-C or Ce-O-C asymmetric stretching vibration.⁶³

It is widely reported that acid-base properties are crucial to the CO₂ conversion.⁶⁴ As basic sites are required to activate the CO₂ molecule, while acid-base pair sites are often reported to be mandatory for methanol activation (CH₃O⁻ and CH₃⁺ formation). Acidity and basicity properties of the four samples were characterized by NH₃- and CO₂-TPD, as presented in Fig. 6(a) and (b), respectively. NH₃-TPD profiles, as illustrated in Fig. 6(a), presented two broad peaks centered at about 120 °C and 270 °C for all the samples. However, the amount of acid sites (desorption peak area) was significantly affected by the introduction of Ce into Zr-MOF lattice. The amount of acid sites reached maximum for Zr-Ce-MOF. Moreover, strong acid sites with the desorption temperature over 400 °C were observed in Zr-Ce-MOF, demonstrating the influence of dopant Ce on the acidity of Zr-based MOF material.

Meanwhile, the CO₂-TPD profiles are also shown in Fig. 6(b). CO₂ desorption peaks in the regions of 100–350 °C were observed and could be ascribed to the desorption of different carbonate species (linear species, bidentate carbonate and monodentate carbonate). A distinguished sharp desorption peak at 180 °C was observed in the CO₂-TPD of Zr-Ce-MOF, which can be assigned to the removal of bidentate carbonate



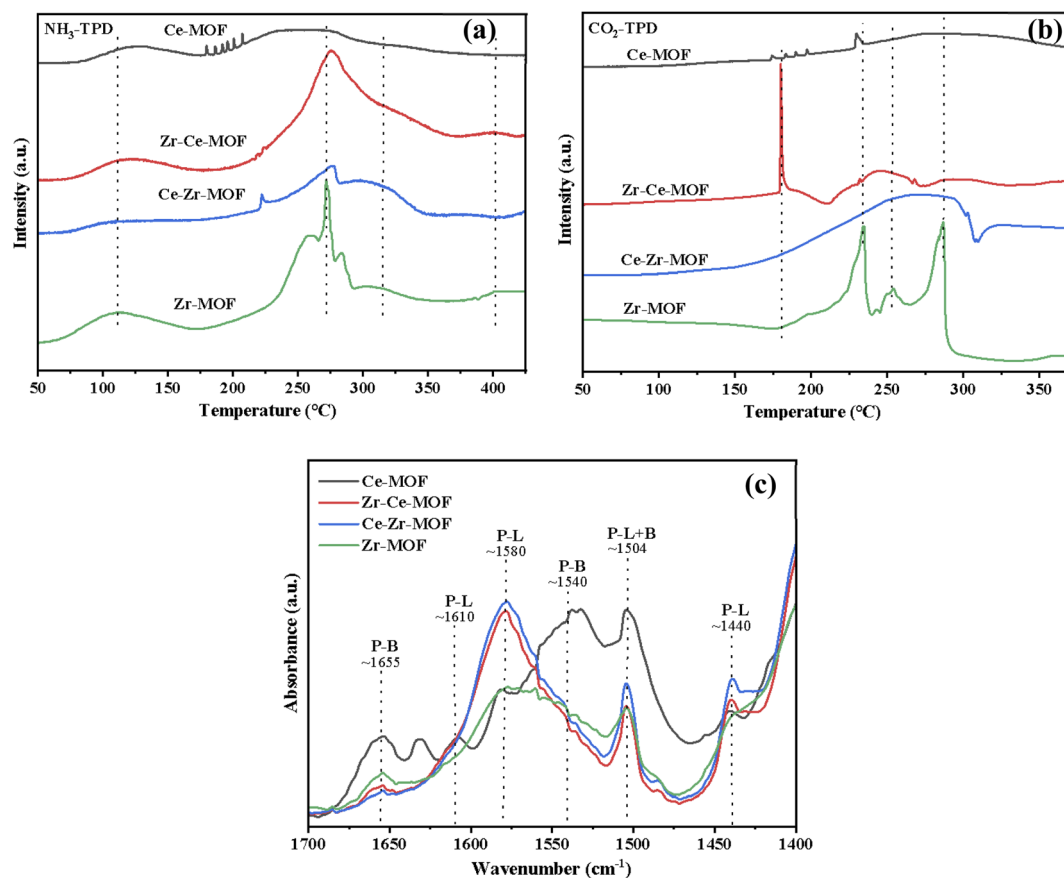


Fig. 6 Temperature programmed desorption (TPD) of (a) NH₃, (b) CO₂ on the prepared MOF materials and (c) pyridine-IR results of MOF materials.

species on the surface.^{46,65} The absence of this particular peak in the other three samples could explain the smaller catalytic activity of the three samples.

In addition, Py-IR experiments are performed to distinguish Lewis acidic sites (LAS) and Brønsted acidic sites (BAS) on Zr-based MOFs. As shown in Fig. 6(c), the bands at 1610, 1580 and 1440 cm⁻¹ are ascribed to LAS with the label P-L, while the bands at 1655 and 1540 cm⁻¹ are assigned to BAS with the label P-B.^{47,66} It is also observed that a combined additional band at 1504 cm⁻¹ is attributed to the vibration of pyridine on both LAS and BAS acid sites with the label P-L+B presents on catalysts.^{66,67} The Py-IR results showed small bands of LAS at 1580 cm⁻¹ on both Zr-MOF and Ce-MOF, but doping of Ce into the Zr-MOF significantly increased the intensity of the band. The LAS was reported to be important in the adsorption of CO₂.^{46,68} Therefore, by doping Ce, varied catalytic activity can be derived for Zr-based MOFs.^{69,70}

Overall, the catalytic activities of the MOF materials were not linearly dependent on the special surface areas, suggesting that other properties of the catalysts should be considered for the better activities of Zr-Ce-MOF. As reported previously, the catalytic activity of catalysts for CO₂ conversion related to the surface area, crystallite size, acid–base properties as well as the surface ratio of Ce⁴⁺/Ce³⁺. However, based on the N₂ adsorption–desorption, XRD and XPS results in the present study,

there is no direct correlation between the crystallite size, surface area and surface proportion of Ce⁴⁺/Ce³⁺ and the activity of the MOF materials.

The acid–base properties of the MOF catalysts were also examined in this study, but the amounts of acidic and basic sites were not in obvious linear relationship with the yield of DMC. The amount of basic sites, which were in favor of CO₂ adsorption and activation, has no direct relationship with the doping of Ce. However, the weak basic site is a key factor for the catalytic activity, which can form bidentate carbonate species on the surface with CO₂. By inspection of Fig. 6(a), it could be seen that the more acid sites catalysts possessed, the better catalytic performance they displayed [Fig. 2(a)]. As shown by Fig. 6(c), the Lewis acid sites responsible for the adsorption and activation of OH group of alcohols is another key factor for the catalytic activity. Therefore, the improved acid–base properties might take major part of the responsibility for the better catalytic performance of Zr-Ce-MOF material.

Possible mechanism analysis of CO₂ conversion

To understand the structure of adsorbed species and the nature of the active sites, FT-IR of the used MOF materials was then conducted, as shown in Fig. 5(d). Fig. 5(d) demonstrates that terminal methoxy (t-OCH₃) and bridged methoxy (b-OCH₃) were



- 10 Y. Chen, Q. Tang, Z. Ye, Y. Li, Y. Yang, H. Pu and G. Li, *New J. Chem.*, 2020, **44**, 12522–12530.
- 11 S. Huang, B. Yan, S. Wang and X. Ma, *Chem. Soc. Rev.*, 2015, **44**, 3079–3116.
- 12 A. H. Tamboli, A. A. Chaugule and H. Kim, *Chem. Eng. J.*, 2017, **323**, 530–544.
- 13 M. Zhang, Y. Xu, B. L. Williams, M. Xiao, S. Wang, D. Han, L. Sun and Y. Meng, *J. Cleaner Prod.*, 2021, **279**, 123344.
- 14 M. Honda, M. Tamura, Y. Nakagawa, K. Nakao, K. Suzuki and K. Tomishige, *J. Catal.*, 2014, **318**, 95–107.
- 15 B. A. V. Santos, V. M. T. M. Silva, J. M. Loureiro and A. E. Rodrigues, *ChemBioEng Rev.*, 2014, **1**, 214–229.
- 16 A. A. Chaugule, H. A. Bandhal, A. H. Tamboli, W. Chung and H. Kim, *Catal. Commun.*, 2016, **75**, 87–91.
- 17 T. Zhao, X. Hu, D. Wu, R. Li, G. Yang and Y. Wu, *ChemSusChem*, 2017, **10**, 2046–2052.
- 18 C. Liu, S. Zhang, B. Cai and Z. Jin, *Chin. J. Catal.*, 2015, **36**, 1136–1141.
- 19 Q. Yang, H. Wang, X. Ding, X. Yang and Y. Wang, *Res. Chem. Intermed.*, 2015, **41**, 4101–4111.
- 20 H. J. Lee, S. Park, I. K. Song and J. C. Jung, *Catal. Lett.*, 2011, **141**, 531–537.
- 21 A. A. Marciniak, O. C. Alves, L. G. Appel and C. J. A. Mota, *J. Catal.*, 2019, **371**, 88–95.
- 22 H. Chen, S. Wang, M. Xiao, D. Han, Y. Lu and Y. Meng, *Chin. J. Chem. Eng.*, 2012, **20**, 906–913.
- 23 C. L. Chiang, K. S. Lin and S. Yu, *Res. Chem. Intermed.*, 2018, **44**, 3797–3811.
- 24 A. Pongsombate, T. Imyen, P. Dittanet, B. Embley and P. Kongkachuichay, *J. Taiwan Inst. Chem. Eng.*, 2017, **80**, 16–24.
- 25 K. Xuan, Y. Pu, F. Li, J. Luo, N. Zhao and F. Xiao, *Chin. J. Catal.*, 2019, **40**, 553–566.
- 26 X. Deng, L. Yang, H. Huang, Y. Yang, S. Feng, M. Zeng, Q. Li and D. Xu, *Small*, 2019, **15**, 1902287.
- 27 H. Wang, Q. Zhu, R. Zou and Q. Xu, *Chem*, 2017, **2**, 52–80.
- 28 H. He, J. A. Perman, G. Zhu and S. Ma, *Small*, 2016, **12**, 6309–6324.
- 29 A. Yurduşen and Y. Yürüm, *Ind. Eng. Chem. Res.*, 2019, **58**, 14058–14072.
- 30 K. Xuan, Y. Pu, F. Li, A. Li, J. Luo, L. Li, F. Wang, N. Zhao and F. Xiao, *J. CO₂ Util.*, 2018, **27**, 272–282.
- 31 S. Biswas and P. Van Der Voort, *Eur. J. Inorg. Chem.*, 2013, **2013**, 2154–2160.
- 32 M. Stawowy, M. Rózewicz, E. Szczepańska, J. Silvestre-Albero, M. Zawadzki, M. Musioł, R. Łuzny, J. Kaczmarczyk, J. Trawczyński and A. Łamacz, *Catalysts*, 2019, **9**, 309.
- 33 V. R. Bakuru, S. R. Churipard, S. P. Maradur and S. B. Kalidindi, *Dalton Trans.*, 2019, **48**, 843–847.
- 34 S. Rojas-Buzo, P. Concepción, J. L. Olloqui-Sariego, M. Moliner and A. Corma, *ACS Appl. Mater. Interfaces*, 2021, **13**, 31021–31030.
- 35 F. Nouar, M. I. Breeze, B. C. Campo, A. Vimont, G. Clet, M. Daturi, T. Devic, R. I. Walton and C. Serre, *Chem. Commun.*, 2015, **51**, 14458–14461.
- 36 J. H. Cavka, S. Jakobsen, U. Olsbye, N. Guillou, C. Lamberti, S. Bordiga and K. P. Lillerud, *J. Am. Chem. Soc.*, 2008, **130**, 13850–13851.
- 37 B. Wang, Q. Yang, C. Guo, Y. Sun, L. Xie and J. Li, *ACS Appl. Mater. Interfaces*, 2017, **9**, 10286–10295.
- 38 M. Lammert, C. Glißmann, H. Reinsch and N. Stock, *Cryst. Growth Des.*, 2017, **17**, 1125–1131.
- 39 M. Lammert, M. T. Wharmby, S. Smolders, B. Bueken, A. Lieb, K. A. Lomachenko, D. D. Vos and N. Stock, *Chem. Commun.*, 2015, **51**, 12578–12581.
- 40 G. C. Shearer, S. Chavan, S. Bordiga, S. Svelle, U. Olsbye and K. P. Lillerud, *Chem. Mater.*, 2016, **28**, 3749–3761.
- 41 R. M. Rego, G. Sriram, K. V. Ajeya, H. Jung, M. D. Kurkuri and M. Kigga, *J. Hazard. Mater.*, 2021, **416**, 125941.
- 42 G. C. Shearer, S. Chavan, J. Ethiraj, J. G. Vitillo, S. Svelle, U. Olsbye, C. Lamberti, S. Bordiga and K. P. Lillerud, *Chem. Mater.*, 2014, **26**, 4068–4071.
- 43 M. Thommes, K. Kaneko, A. V. Neimark, J. P. Olivier, F. Rodriguez-Reinoso, J. Rouquerol and K. S. W. Sing, *Pure Appl. Chem.*, 2015, **87**, 1051–1069.
- 44 H. Ohno, M. Ikhlayel, M. Tamura, K. Nakao, K. Suzuki, K. Morita, Y. Kato, K. Tomishige and Y. Fukushima, *Green Chem.*, 2021, **23**, 457–469.
- 45 D. J. Faria, L. Moreira Dos Santos, F. L. Bernard, I. Selbacch Pinto, M. A. Carmona Da Motta Resende and S. Einloft, *RSC Adv.*, 2020, **10**, 34895–34902.
- 46 B. Liu, C. Li, G. Zhang, X. Yao, S. S. C. Chuang and Z. Li, *ACS Catal.*, 2018, **8**, 10446–10456.
- 47 X. Wang, J. Zhao, Y. Li, S. Huang, J. An, R. Shi, Y. Pei, Z. Li and J. Ren, *Chem. Eng. Sci.*, 2021, **229**, 116018.
- 48 A. A. Pawar, D. Lee, W. Chung and H. Kim, *Chem. Eng. J.*, 2020, **395**, 124970.
- 49 S. Kumar, M. B. Gawande, I. Medřík, M. Petr, O. Tomanec, V. Kupka, R. S. Varma and R. Zbořil, *Green Chem.*, 2020, **22**, 5619–5627.
- 50 Y. Wu, X. Chen, X. Luo, M. Yang, C. Hou and D. Huo, *Anal. Chim. Acta*, 2021, **1183**, 339000.
- 51 J. He, Y. Xu, W. Wang, B. Hu, Z. Wang, X. Yang, Y. Wang and L. Yang, *Chem. Eng. J.*, 2020, **379**, 122431.
- 52 Y. Yang, D. Zhang, W. Ji, F. Bi, L. Song and X. Zhang, *J. Colloid Interface Sci.*, 2022, **606**, 1811–1822.
- 53 D. Phan, V. N. Le, J. Kim and E. Y. Lee, *Fuel Process. Technol.*, 2021, **224**, 107001.
- 54 S. Li, Y. Jin, Z. Hu, Y. Liu, S. Wu, Y. Wang and G. Wang, *J. Radioanal. Nucl. Chem.*, 2021, **330**, 857–869.
- 55 B. Peng, J. Cui, Y. Wang, J. Liu, H. Zheng, L. Jin, X. Zhang, Y. Zhang and Y. Wu, *Nanoscale*, 2018, **10**, 1939–1945.
- 56 Y. Xiong, S. Chen, F. Ye, L. Su, C. Zhang, S. Shen and S. Zhao, *Chem. Commun.*, 2015, **51**, 4635–4638.
- 57 M. M. Khan, S. A. Ansari, M. I. Amal, J. Lee and M. H. Cho, *Nanoscale*, 2013, **5**, 4427.
- 58 M. M. Khan, S. A. Ansari, D. Pradhan, M. O. Ansari, D. H. Han, J. Lee and M. H. Cho, *J. Mater. Chem. A*, 2014, **2**, 637–644.
- 59 Y. Wang, B. Li, C. Zhang, L. Cui, S. Kang, X. Li and L. Zhou, *Appl. Catal., B*, 2013, **130–131**, 277–284.



- 60 N. Wetchakun, S. Chaiwichain, B. Inceesungvorn, K. Pingmuang, S. Phanichphant, A. I. Minett and J. Chen, *ACS Appl. Mater. Interfaces*, 2012, **4**, 3718–3723.
- 61 X. Pan, M. Yang, X. Fu, N. Zhang and Y. Xu, *Nanoscale*, 2013, **5**, 3601.
- 62 X. Dong, Y. Lin, Y. Ma and L. Zhao, *RSC Adv.*, 2019, **9**, 27674–27683.
- 63 Y. L. Wang, S. Zhang, Y. F. Zhao, J. Bedia, J. J. Rodriguez and C. Belver, *J. Environ. Chem. Eng.*, 2021, **9**, 106087.
- 64 K. Tomishige, Y. Gu, T. Chang, M. Tamura and Y. Nakagawa, *Mater. Today Sustain.*, 2020, **9**, 100035.
- 65 C. Xin, M. Hu, K. Wang and X. Wang, *Langmuir*, 2017, **33**, 6667–6676.
- 66 S. Pyen, E. Hong, M. Shin, Y. Suh and C. Shin, *Mol. Catal.*, 2018, **448**, 71–77.
- 67 M. Tamura, K. Shimizu and A. Satsuma, *Appl. Catal., A*, 2012, **433–434**, 135–145.
- 68 Y. Chen, Y. Li, W. Chen, W. W. Xu, Z. Han, A. Waheed, Z. Ye, G. Li and A. Baiker, *Nano Res.*, 2022, **15**, 1366–1374.
- 69 Z. Fu, Y. Zhong, Y. Yu, L. Long, M. Xiao, D. Han, S. Wang and Y. Meng, *ACS Omega*, 2018, **3**, 198–207.
- 70 A. Li, Y. Pu, F. Li, J. Luo, N. Zhao and F. Xiao, *J. CO₂ Util.*, 2017, **19**, 33–39.
- 71 D. Stoian, A. Bansode, F. Medina and A. Urakawa, *Catal. Today*, 2017, **283**, 2–10.
- 72 D. Stoian, F. Medina and A. Urakawa, *ACS Catal.*, 2018, **8**, 3181–3193.
- 73 W. Kuan, W. Yu, F. Tu, C. Chung, Y. Chang, M. M. Lin, T. Yu and L. Chen, *Chem. Eng. J.*, 2022, **430**, 132941.
- 74 A. H. Tamboli, A. A. Chaugule, S. W. Gosavi and H. Kim, *Fuel*, 2018, **216**, 245–254.

