

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *Nanoscale Adv.*, 2021, 3, 2305

# Surface passivation of organometal halide perovskites by atomic layer deposition: an investigation of the mechanism of efficient inverted planar solar cells†

Ran Zhao,<sup>†a</sup> Kai Zhang,<sup>‡b</sup> Jiahao Zhu,<sup>‡a</sup> Shuang Xiao,<sup>‡b</sup> Wei Xiong,<sup>a</sup> Jian Wang,<sup>b</sup> Tanghao Liu,<sup>c</sup> Guichuan Xing,<sup>‡c</sup> Kaiyang Wang,<sup>c</sup> Shihe Yang<sup>‡b</sup> and Xinwei Wang<sup>‡\*a</sup>

Interface passivation plays a pivotal role in achieving high-efficiency organic metal halide perovskite solar cells (PSCs). It has been recently revealed that atomic layer deposition (ALD) of wide-band gap oxides shows great potential to effectively passivate defects at the interface, and ALD is also of great technological promise for industrial upscaling. However, the conflicting observations of ALD passivation are often reported in the literature, even with very similar ALD conditions. To unveil the involved crucial mechanism, this work carefully investigates the evolution of a representative MAPbI<sub>3</sub> perovskite surface during the ALD of Al<sub>2</sub>O<sub>3</sub>, by employing the technique of *in situ* X-ray photoelectron spectroscopy. The ALD at 125 °C was found to cause significant degradation of the perovskite; lowering the deposition temperature can largely minimize the degradation, and 75 °C was found to be the best ALD temperature. Following this conclusion, inverted planar perovskite solar cells were prepared in ambient conditions with ALD Al<sub>2</sub>O<sub>3</sub> interlayers. Indeed, cells with the interlayer deposited at 75 °C exhibited a significantly enhanced power conversion efficiency from 18.8% (champion 19.2%) to 20.0% (champion 20.4%). Photoluminescence measurements further evidence that the ALD layer can effectively passivate defect states at the perovskite surface. Considering the great representativeness and broad applicability of MAPbI<sub>3</sub> and ALD Al<sub>2</sub>O<sub>3</sub>, the mechanism and strategy reported herein should be of significant value for the perovskite interface engineering in general.

Received 30th January 2021  
Accepted 18th February 2021

DOI: 10.1039/d1na00075f

[rsc.li/nanoscale-advances](http://rsc.li/nanoscale-advances)

## Introduction

Organic–inorganic halide perovskite solar cells (PSCs) are highly promising emerging photovoltaic cells, and they have shown rapid improvement in certified power conversion efficiency (PCE) from 3.8% to 25.5% over the past decade.<sup>1,2</sup> While the halide perovskites appear to be resilient to bulk point defects (such as vacancies, interstitials, and antisites), their optoelectronic properties are fairly susceptible to the quality of perovskite (PVK) surfaces and interfaces.<sup>3</sup> Given current synthesis techniques,

perovskite surfaces are rarely stoichiometric and usually defective.<sup>3</sup> Defects at perovskite surfaces could induce significant nonradiative charge recombination and deteriorate the solar cell performance.<sup>3–7</sup> Particularly, in state-of-the-art solar cells, the nonradiative recombination at interfaces between the perovskite and charge transport layers is predominant compared to those in the bulk or at grain boundaries.<sup>4</sup> Therefore, the passivation of interface defects is pivotal to achieve high-efficiency PSCs. To this end, numerous passivation approaches have been reported, for instance, by adding an interlayer of small molecules, polymers, and inorganic compounds or incorporating wide-band gap 2D perovskites.<sup>8–11</sup> Despite their promising improvements on solar cell efficiency, concerns still remain about the upscalability of these approaches.

Recently, atomic layer deposition (ALD) of wide-band gap oxides (e.g. Al<sub>2</sub>O<sub>3</sub>) has emerged as a promising strategy to effectively passivate perovskite surfaces.<sup>12</sup> ALD is a scalable vapor-phase thin-film deposition technique, which relies on sequential alternate self-limiting surface reactions, and it is renowned for producing highly uniform, conformal thin films on non-flat surfaces with atomic-precise film thickness control and

<sup>a</sup>School of Advanced Materials, Shenzhen Graduate School, Peking University, Shenzhen 518055, China. E-mail: wangxw@pku.edu.cn

<sup>b</sup>Guangdong Key Lab of Nano-Micro Material Research, School of Chemical Biology and Biotechnology, Shenzhen Graduate School, Peking University, Shenzhen 518055, China. E-mail: xiaoshuang@pku.edu.cn; chsyang@pku.edu.cn

<sup>c</sup>Institute of Applied Physics and Materials Engineering, University of Macau, Avenida da Universidade, Taipa, Macau, China

† Electronic supplementary information (ESI) available: Additional XPS, SEM results, additional performance of PSCs, and fitting results of TRPL. See DOI: 10.1039/d1na00075f

‡ These authors contributed equally to this work.

remarkable process reproducibility.<sup>13,14</sup> Currently, ALD has been widely used in the Si photovoltaic industry for the production of passivated emitter and rear cells (PERC).<sup>15</sup> Analogously, the passivation of perovskites by ALD is of great technological promise for future industrial upscaling. However, despite a number of positive reports showing promising improvements in the efficiency and stability of PSCs, direct growth of ALD on the top of perovskites has often encountered significant incompatibility issues.<sup>12,16,17</sup> During an ALD process, perovskites are subjected to an often elevated temperature and the exposures of ALD precursors could potentially change the structure, composition, and therefore the optoelectronic properties of perovskites. Notably, these effects are largely dependent on the ALD surface reaction chemistries and the properties of perovskites (such as composition and surface condition).<sup>12,16,17</sup> Hence, understanding the fundamental mechanisms of the interactions between ALD precursors and perovskites becomes the key to reliably employing this ALD technology for PSCs. Toward this goal, a growing number of reports have recently appeared to investigate the related ALD mechanisms, but often conflicting observations were published in the literature.<sup>12</sup> For instance, taking the most studied system of ALD  $\text{Al}_2\text{O}_3$  on methylammonium lead iodide ( $\text{MAPbI}_3$ ) as an example, under quite similar deposition conditions, both increase and decrease in the solar cell efficiency have been reported.<sup>18–26</sup> Notably, a recent study<sup>27</sup> using *in situ* quartz crystal microbalance (QCM) and quadruple mass spectrometry (QMS) showed that the differences in the ALD temperature and precursor partial pressure could result in drastically different outcome interfaces, which were suggested to account for the discrepancies observed across different laboratories. Their conclusion, together with the well-known sensitivity of the perovskite surfaces and subtleties in preparation, highlights two very important issues for this type of studies. First, the mechanism study should be accompanied with the high-reliability and high-performance PSCs; otherwise, the conclusions do not reflect the de facto limiting factors. Second, the mechanism study should be conducted *in situ* or *in vacuo*, in order to avoid possible ambient interference when exposed to air.

To find out the critical mechanism underlying ALD passivation, we herein focused on the PSCs with high benchmarking PCE (18.8% in average) and employed the technique of *in situ* X-ray photoelectron spectroscopy (XPS) to investigate the evolution of the perovskite surface during the ALD process. The representative perovskite of  $\text{MAPbI}_3$  and the ALD material of  $\text{Al}_2\text{O}_3$  were chosen for this study. Following the careful study, we found that quite a few experimental observations were rather different from previous reports, which highlight the importance of carrying out *in situ* investigation on high-efficiency PSCs. Therefore, the results and mechanism reported herein should be of significant value for the interface engineering of high-performance PSCs in general.

## Experimental

### Materials

Fluorine-doped tin oxide (FTO,  $1.5\text{ cm} \times 1.5\text{ cm}$ ) was purchased from OPV TECH LTD. Methylammonium iodide (MAI) was

purchased from Dyesol Ltd. Lead iodide ( $\text{PbI}_2$ , extra dry, 99.999%) and nickel(II) acetylacetonate (95%) were purchased from Alfa Aesar Ltd. *N,N*-Dimethylformamide (DMF, anhydrous, 99.8%), dimethyl sulfoxide (DMSO, anhydrous, 99.8%) and chlorobenzene (CB, extra dry, 99.5%) were purchased from Acros Ltd. 2,2,2-Trifluoroethanol (TFE, 99.5%) was purchased from Energy chemical Ltd. [6,6]-Phenyl-C61-butyric acid methyl ester ( $\text{PC}_{61}\text{BM}$ ) was purchased from NANO-C Tech Ltd. Anisole (anhydrous, 99.7%) was purchased from Aladdin Ltd. Diethanol amine (DEA, 99%) was purchased from Sigma-Aldrich Ltd.

### Device fabrication

**PSC fabrication.** FTO substrates were ultrasonically cleaned with deionized water, ethanol, isopropanol, acetone and ethanol sequentially, and dried in a circulation oven at  $80^\circ\text{C}$ . A NiO film was fabricated according to our previous publication.<sup>8</sup> The sol-gel solution was prepared by dissolving nickel(II) acetylacetonate and DEA in anhydrous ethanol. A NiO layer was fabricated using a home-made ultrasonic spray.

The perovskite precursor solution was prepared according to our previous publications.<sup>28,29</sup> First, 461 mg of  $\text{PbI}_2$  and 159 mg of MAI were dissolved in a mixture of 434  $\mu\text{L}$  DMSO and 124  $\mu\text{L}$  DMF. After stirring on a  $60^\circ\text{C}$  hotplate overnight, the transparent yellowish solution was filtered using a filter head of 0.22  $\mu\text{m}$ . A perovskite film was prepared using the as-prepared solution in a fume hood under the humidity between 20 and 60% RH. Then, 35  $\mu\text{L}$  of the as-prepared precursor solution was drop-casted onto the substrate at room temperature. The spin coating process consisted of four steps, which were 1000 rpm for 45 s, 6000 rpm for 40 s, 0 rpm for 10 s, and 6000 rpm for 10 s sequentially. During the last 5 s of the second step and the whole process of the fourth step, 80  $\mu\text{L}$  anisole was dropped onto the substrate, respectively. After the first dripping, the film was still transparent and it could maintain the state for a long time in ambient air. After the second dripping, the film turned brown in color, and the as-prepared film was converted into a compact perovskite film at room temperature or  $98^\circ\text{C}$  for 7 min in an ambient atmosphere. On top of the perovskite film, atomic layer deposition (ALD) of  $\text{Al}_2\text{O}_3$  was carried out under different conditions.

The  $\text{PC}_{61}\text{BM}$  solution (20  $\text{mg mL}^{-1}$  in CB) was fabricated and stirred at  $60^\circ\text{C}$  for 2 h. First, 35  $\mu\text{L}$  of  $\text{PC}_{61}\text{BM}$  solution was drop-casted onto the substrate and spun at 3000 rpm for 30 s. The interface material PPDIN6 was synthesized according to our previous publication.<sup>11</sup> The PPDIN6 solution (0.5  $\text{mg mL}^{-1}$  in TFE) was fabricated and stirred overnight at room temperature. Then, 40  $\mu\text{L}$  of PPDIN6 solution was drop-casted onto the substrate and spun at 3000 rpm for 30 s. Finally, 150 nm of Ag electrode was evaporated on top.

**ALD of  $\text{Al}_2\text{O}_3$ .** The deposition process was conducted using a home-built tubular ALD reactor, with trimethylaluminum (TMA) and water as the aluminum and oxygen precursors, respectively. Both precursors were kept at room temperature in separate containers. To control the precursor dosage, the precursor vapor was delivered first into a 5 mL gas trap and then into a deposition chamber. Each ALD cycle consisted of one pulse of TMA, 40 s of  $\text{N}_2$  purge, one pulse of water, and 100 s of



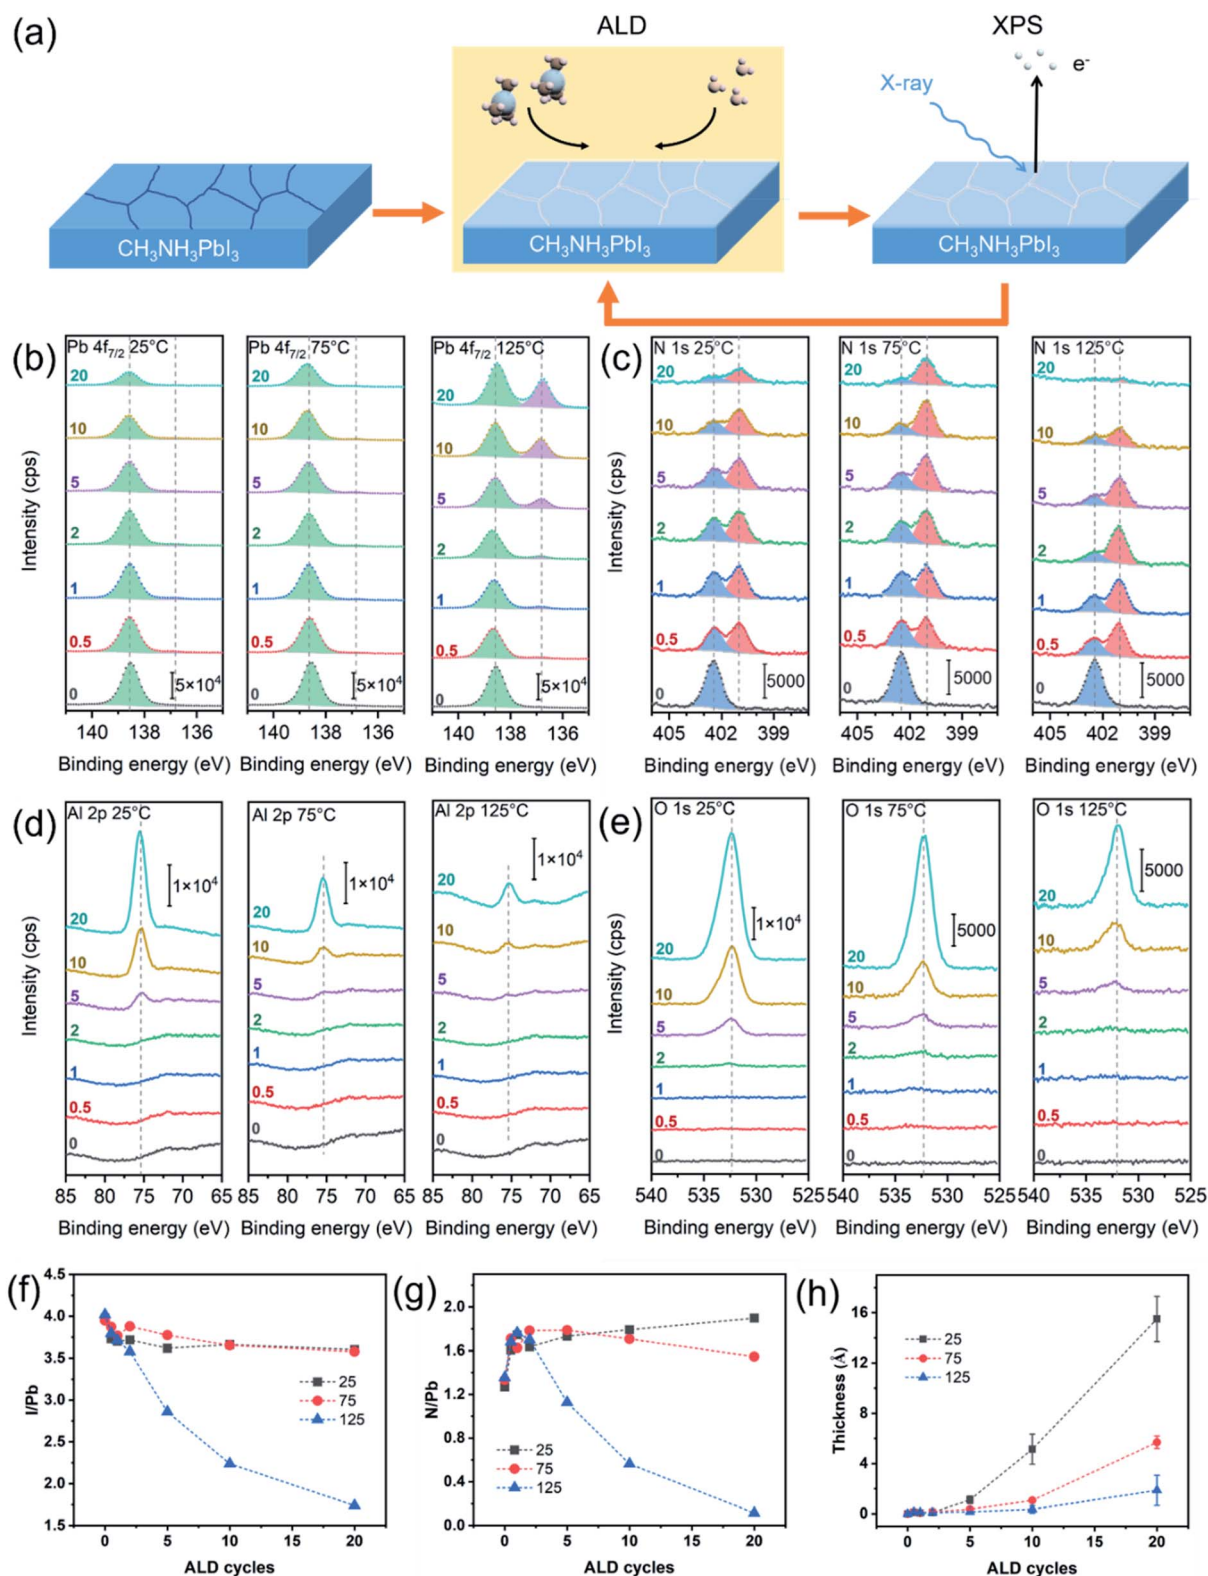


Fig. 1 (a) Schematic of the *in situ* experimental procedure. High-resolution XPS core-level spectra of (b) Pb 4f<sub>7/2</sub>, (c) N 1s, (d) Al 2p, and (e) O 1s taken from 0 cycles (*i.e.*, initial surface) through 20 cycles of ALD of  $\text{Al}_2\text{O}_3$  on MAPbI<sub>3</sub>. The deposition temperatures were 25 °C, 75 °C and 125 °C. Atomic ratios of (f) I/Pb and (g) N/Pb and (h) the equivalent thickness of the deposited  $\text{Al}_2\text{O}_3$  with respect to the number of the ALD cycles.





N<sub>2</sub> purge in sequence. During N<sub>2</sub> purging, the pressure of the deposition chamber was 0.5 Torr.

### Characterization

**In situ X-ray photoelectron spectroscopy.** The *in situ* X-ray photoelectron spectroscopy measurements were performed using a modified Escalab 250Xi (Thermo Scientific) XPS system equipped with an ALD chamber. Details about this system can be found in our previous publications.<sup>30–32</sup> The system contained an ALD chamber for deposition, an intermediate chamber for sample transfer without vacuum break, and an analysis chamber for XPS measurements. The analysis chamber was equipped with a monochromatic Al K $\alpha$  X-ray source (1486 eV). The pass energy was 20 eV for all high-resolution spectra. The binding energy was referenced to Au 4f<sub>7/2</sub> (84.0 eV). For each measurement, the spectrum was taken on a new spot to avoid possible radiation damage from X-ray. Standard sensitive factors provided in Thermo Advantage (v5.945) were used to calculate the atomic ratios, and the peak areal intensities were used for the calculation. The equivalent thickness of Al<sub>2</sub>O<sub>3</sub> was calculated based on the XPS signal attenuation,<sup>33</sup> by  $d = \lambda \sin \theta \ln \left( \frac{I_{\text{Al } 2p}}{\beta I_{\text{I } 3d}} + 1 \right)$ , where  $\lambda$  (=2.3 nm (ref. 34)) is the effective attenuation length of the photoelectrons in the Al<sub>2</sub>O<sub>3</sub> layer,  $\theta$  (=90°) is the photoelectron take off angle,  $I_{\text{Al } 2p}$  and  $I_{\text{I } 3d}$  are the measured intensities of the Al 2p and I 3d signals from the substrate, respectively, and  $\beta$  ( $=I_{\text{Al } 2p}^{\infty}/I_{\text{I } 3d}^{\infty}$ ) is the ratio of the Al 2p and I 3d intensities for thick Al<sub>2</sub>O<sub>3</sub> and perovskite substrates.

**Photoluminescence spectra.** Steady-state PL spectra were recorded using a Horiba Fluorolog-3 spectrophotometer with a 450 W xenon lamp as the continuous light source. Time-resolved PL spectra were recorded using a Picofluo TRPL spectrophotometer (Pico-1000). The wavelengths of the excitation light and detection light were 405 nm and 767 nm, respectively. The obtained TRPL curves were fitted by a bi-exponential decay function,  $y = A_1 e^{-\frac{t}{\tau_1}} + A_2 e^{-\frac{t}{\tau_2}} + y_0$ ,  $\tau_{\text{ave}} = \frac{A_1 \tau_1^2 + A_2 \tau_2^2}{A_1 \tau_1 + A_2 \tau_2}$ , where  $A_1$  and  $A_2$  are the relative amplitudes and  $\tau_1$ ,  $\tau_2$ , and  $\tau_{\text{ave}}$  are the fast, slow, and average decay lifetimes, respectively.

**Other characterizations.** The morphologies of the samples were characterized using a field-emission scanning electron microscope (SEM, JEOL 7100F). The X-ray diffraction (XRD) patterns were recorded using a diffractometer (D8 Discover, Bruker AXS, Germany) with a Cu K $\alpha$  radiation. The current density and voltage ( $J$ - $V$ ) of the devices were measured using a source meter (Keithley, 2400) under 1 Sun illumination (AM 1.5G, 100 mW cm<sup>-2</sup>) with a solar simulator (Newport, Oriel Sol3A). The measurement area was confined by a mask of 0.08 cm<sup>2</sup>. The incident photon-to-current conversion efficiency (IPCE) was measured using a photoelectric detection test system (Zolix Instrument).

## Results and discussion

*In situ* XPS was employed to monitor the evolution of the MAPbI<sub>3</sub> perovskite surface upon the ALD of Al<sub>2</sub>O<sub>3</sub> from

trimethylaluminum (TMA) and H<sub>2</sub>O (Fig. 1a). Three representative ALD temperatures of 25 °C, 75 °C and 125 °C were selected to investigate the temperature effect. As a few recent reports<sup>27,35</sup> suggested that the MAPbI<sub>3</sub> perovskite could be etched by excessively exposing to the TMA and H<sub>2</sub>O vapors, we chose to use relatively small exposures of 0.025 and 0.051 Torr s for the TMA and H<sub>2</sub>O vapors, respectively, in each ALD cycle. These exposures were sufficient to saturate the normal ALD growth of Al<sub>2</sub>O<sub>3</sub> on the flat SiO<sub>x</sub> surface.<sup>36</sup>

Fig. 1b–e shows the acquired *in situ* XPS spectra for the core-level emissions of Pb 4f<sub>7/2</sub>, N 1s, Al 2p, and O 1s. All the XPS spectra were taken for 0 cycle (*i.e.*, initial surface) through 20 cycles of Al<sub>2</sub>O<sub>3</sub> deposited on the perovskite surface. Half-integer and full-integer numbers were used to denote the spectra taken after the TMA and H<sub>2</sub>O half-cycles, respectively. Fig. 1b compares the evolutions of the Pb 4f<sub>7/2</sub> spectra upon the ALD at 25, 75 and 125 °C. All the spectra for the pristine perovskite surfaces (0 cycle) show a similar symmetric peak at a binding energy (BE) of 138.6 eV, which corresponds to Pb<sup>2+</sup>-I in perovskites.<sup>37</sup> However, as the ALD proceeded, the Pb 4f<sub>7/2</sub> spectra behaved differently for the depositions at different temperatures. At a low deposition temperature of 25 °C or 75 °C, the intensity of the Pb<sup>2+</sup>-I peak continually diminished as the deposition proceeded, probably owing to the increasing attenuation of the photoelectrons by the deposited Al<sub>2</sub>O<sub>3</sub> layer on top. Comparatively, the signal diminished faster for 25 °C than 75 °C, suggesting a faster per-cycle growth of Al<sub>2</sub>O<sub>3</sub> at 25 °C. As for the ALD at 125 °C, the Pb 4f<sub>7/2</sub> spectrum continually developed an additional peak at a lower BE of 136.8 eV, and this BE corresponds to metallic lead (Pb<sup>0</sup>),<sup>37</sup> which suggests that the Pb<sup>2+</sup> in perovskite was reduced upon the ALD at 125 °C. Considering that the conduction band minimum of MAPbI<sub>3</sub> has mostly nonbonding Pb *p* character,<sup>38</sup> the reduction of Pb<sup>2+</sup> to Pb<sup>0</sup> can significantly alter the optoelectronic properties of MAPbI<sub>3</sub>. Perhaps because it was only present on the surface and of a small amount compared to the bulk, the metallic lead was not observed by XRD or IR in previous ALD studies,<sup>18,35,39</sup> and thus its adverse effect on the solar cell performance was likely overlooked. In addition, it is worth noting that no Pb-OH species (at 138.2 eV (ref. 20)) was detected on the pristine perovskite surfaces or after the ALD, and this observation is in stark contrast to a previous study on relatively low-PCE (13.6%) MAPbI<sub>3</sub> surface,<sup>20</sup> which therefore signifies a different passivation mechanism for high-PCE MAPbI<sub>3</sub> surfaces.

Fig. 1c compares the evolutions of the N 1s spectra upon the ALD at 25, 75 and 125 °C. All the spectra of the pristine perovskite surfaces show a single peak at 402.4 eV for N in CH<sub>3</sub>NH<sub>3</sub><sup>+</sup>,<sup>37</sup> but after the TMA dose, a pronounced new peak emerged at a lower BE of 401.0 eV. The appearance of this peak is suggestive of the deprotonation of CH<sub>3</sub>NH<sub>3</sub><sup>+</sup> by TMA to afford CH<sub>3</sub>NH<sub>2</sub>,<sup>35,40</sup> which has a lower N 1s BE.<sup>41,42</sup> Although CH<sub>3</sub>NH<sub>2</sub> itself is a gas at room temperature (b.p. -6.8 °C), for the ALD at  $\leq 75$  °C, most of the afforded CH<sub>3</sub>NH<sub>2</sub> seemed to remain in the perovskite or be trapped at the perovskite/Al<sub>2</sub>O<sub>3</sub> interface. In contrast, the ALD at 125 °C resulted in a significant reduction of the overall N 1s signal (*e.g.* 20 cycles), which indicates a significant loss of CH<sub>3</sub>NH<sub>3</sub><sup>+</sup> at 125 °C.



Fig. 1d and e displays the acquired Al 2p and O 1s spectra upon the ALD at 25, 75 and 125 °C. All the Al 2p spectra show a similar trend, where no Al 2p signal was observed for the first 2 cycles, indicating that the growth of ALD Al<sub>2</sub>O<sub>3</sub> on the perovskite was delayed. After 5 ALD cycles, the spectra showed observable Al 2p peaks, and the peak intensities later increased as the ALD proceeded. The peak BE was found to be at 75.5 eV, which agrees with Al<sub>2</sub>O<sub>3</sub> (Al–OH).<sup>21,43</sup> The O 1s spectra showed correlated results that the O signals were barely observable after 2 cycles and became prominent (at 532.7 eV, Al–OH<sup>21,43</sup>) after 5 cycles, and these results corroborate that the ALD Al<sub>2</sub>O<sub>3</sub> growth was delayed on the perovskite. It is worth noting that the O 1s spectra for the initial MAPbI<sub>3</sub> surfaces do not contain any detectable O signals, which is in stark contrast to previous photoelectron spectroscopy studies.<sup>20,21</sup> This discrepancy signifies different ALD growth behaviors, which could therefore lead to different passivation mechanisms for the perovskite solar cells. Nevertheless, the intensities of the Al 2p and O 1s peaks are correlated with the amount of the Al<sub>2</sub>O<sub>3</sub> grown on the perovskite surface, and apparently the growth was slower at a higher temperature. In addition, I 3d<sub>5/2</sub> spectra were also taken. As shown in Fig. S1,† aside from a continual signal intensity decrease with the ALD cycle number, all the I 3d<sub>5/2</sub> spectra show only a single peak at 619.4 eV for Pb<sup>2+</sup>–I,<sup>37</sup> and thus no iodate-like species (at 623.8 eV (ref. 44)) was formed.

Based on the above-mentioned *in situ* XPS results, the change in the perovskite surface composition was traced. Fig. 1f and g plot the atomic ratios of I/Pb and N/Pb extracted from the XPS spectra. Because the mean free path of the photoelectrons is about 2–3 nm,<sup>34</sup> these ratios reflect only the compositional information near the perovskite surface. The I/Pb and N/Pb ratios for the pristine perovskite surfaces (e.g., 0 ALD cycle) were found to be 4.0 and 1.3, respectively. These numbers are greater than those in the stoichiometric MAPbI<sub>3</sub>, which suggests that the initial perovskite surface contained excessive iodine and MAI.<sup>45</sup> Although the I-rich MAI surface termination is more stable than the PbI<sub>2</sub> termination for the MAPbI<sub>3</sub> surface,<sup>46–48</sup> excessive iodine can result in deep electronic traps, thereby deteriorating the solar cell performance.<sup>49</sup> Apparently, as shown in Fig. 1f, the surface reactions of the I-rich MAPbI<sub>3</sub> with the ALD precursors of TMA and H<sub>2</sub>O can reduce the surface I/Pb ratio, by forming volatile CH<sub>3</sub>I, as previously identified *via in situ* QMS.<sup>27</sup> As shown in Fig. 1f, the 10- and 20-cycle ALD at 25 °C or 75 °C reduced the I/Pb ratio to 3.7 and 3.6, respectively. As for the ALD at 125 °C, the I/Pb ratio drastically decreased to 2.2 and 1.7 after 10 and 20 ALD cycles, respectively, which is consistent with the formation of metallic Pb as previously suggested from the BE change. Concurrently, a significant drop of the N/Pb ratio to 0.1 was found for the 20-cycle ALD at 125 °C (Fig. 1g). Such a low N/Pb ratio indicates a significant loss of the CH<sub>3</sub>NH<sub>3</sub><sup>+</sup> ions, which eventually collapsed the perovskite structure to form PbI<sub>2</sub> (as will be shown later). However, we also noticed a pronounced increase in the N/Pb ratio (from 1.3 to 1.7) upon the first TMA dose (0.5 cycle) for all the temperatures. Given the surface-sensitivity of the XPS technique, the increase in the N/Pb ratio suggests that a certain amount of CH<sub>3</sub>NH<sub>2</sub> accumulated near the perovskite surface. CH<sub>3</sub>NH<sub>2</sub> could be

afforded at the perovskite surface and grain boundaries; for the latter, the afforded CH<sub>3</sub>NH<sub>2</sub> diffused outward through the grain boundaries to the top of the perovskite layer. This situation is analogous to a technique called methylamine-induced defect-healing (MIDH), which aims to reduce the perovskite defects by recrystallizing it *via* an intermediate MAPbI<sub>3</sub>·xCH<sub>3</sub>NH<sub>2</sub> liquid.<sup>50,51</sup> Certainly, the *in situ* formed CH<sub>3</sub>NH<sub>2</sub> in our case was only of a small amount and thus not enough to form a full liquid intermediate, but the defects at the surface can be healed by the same scheme. In addition, CH<sub>3</sub>NH<sub>2</sub> can also passivate the surface I vacancies by coordinating to Pb<sup>2+</sup>, forming a Pb–N bond which is much stronger than Pb–OH.<sup>52</sup>

The thickness of the ALD Al<sub>2</sub>O<sub>3</sub> layer can be estimated from the degree of attenuation of the photoelectron signal from the perovskite underneath (see Experimental). Fig. 1h plots the extracted equivalent Al<sub>2</sub>O<sub>3</sub> thickness with respect to the ALD cycle number. For all the deposition temperatures, the initial Al<sub>2</sub>O<sub>3</sub> growth was delayed for at least 2 cycles, and after 5 cycles, the thickness *versus* cycle number exhibited a superlinear relation, which suggests that the per-cycle growth rate accelerated as the deposition proceeded. This behavior is suggestive of an inhibited initial growth mechanism.<sup>53</sup> Inhibited initial growth is usually because of the lack of ALD-reactive moieties on the substrate surface, and it would normally result in the growth of islands on the substrate.<sup>53</sup> Given the small equivalent thickness of ALD-Al<sub>2</sub>O<sub>3</sub> after 10 cycle ALD at 25–125 °C, the afforded Al<sub>2</sub>O<sub>3</sub> islands should be no greater than several nanometers in size and therefore elude direct observation by SEM or AFM. Although detailed chemistry of the ALD Al<sub>2</sub>O<sub>3</sub> growth on MAPbI<sub>3</sub> is still unknown, the ALD Al<sub>2</sub>O<sub>3</sub> growth normally starts from TMA reacting with surface hydroxyls to afford Al–O bonds. Presumably, the same reaction scheme is also plausible if the surface defect sites adsorb H<sub>2</sub>O. Recently, Choudhury *et al.*<sup>35</sup> and Koushik *et al.*<sup>40</sup> proposed another reaction scheme that TMA reacts with MAPbI<sub>3</sub> to afford a PbI<sub>3</sub>–Al(CH<sub>3</sub>)<sub>2</sub> complex; however, our XPS results did not show the presence of Al after the first TMA half-cycle. Therefore, the growth from the surface defect sites is more likely to be the case. Given that the surface defects are often detrimental to the perovskite optoelectronic properties,<sup>3,4</sup> fine-tuning the ALD conditions to well passivate these defects is of crucial importance to achieve high-performance solar cells.

X-ray diffraction (XRD) was employed to investigate the bulk part of the perovskite upon ALD. Fig. 2a compares the obtained XRD patterns for the pristine perovskite and the perovskites with 10-cycle ALD Al<sub>2</sub>O<sub>3</sub> grown at different temperatures. The pattern of the pristine perovskite contains the characteristic MAPbI<sub>3</sub> diffraction peaks of (110) and (200) at 14.2° and 20.1°, respectively,<sup>18,54</sup> and the pattern remained almost the same after the 10-cycle ALD at 25 °C or 75 °C. However, for the ALD at 125 °C, a prominent PbI<sub>2</sub> (001) peak appeared at 12.8°, while the perovskite (110) peak became weaker. These results indicate that a considerable portion of the perovskite was converted to PbI<sub>2</sub> upon the ALD at 125 °C. Notably, thermal annealing at 125 °C itself was not enough to drive this conversion, as the vacuum annealed sample shows an almost unchanged XRD pattern. Therefore, the surface reactions with the ALD



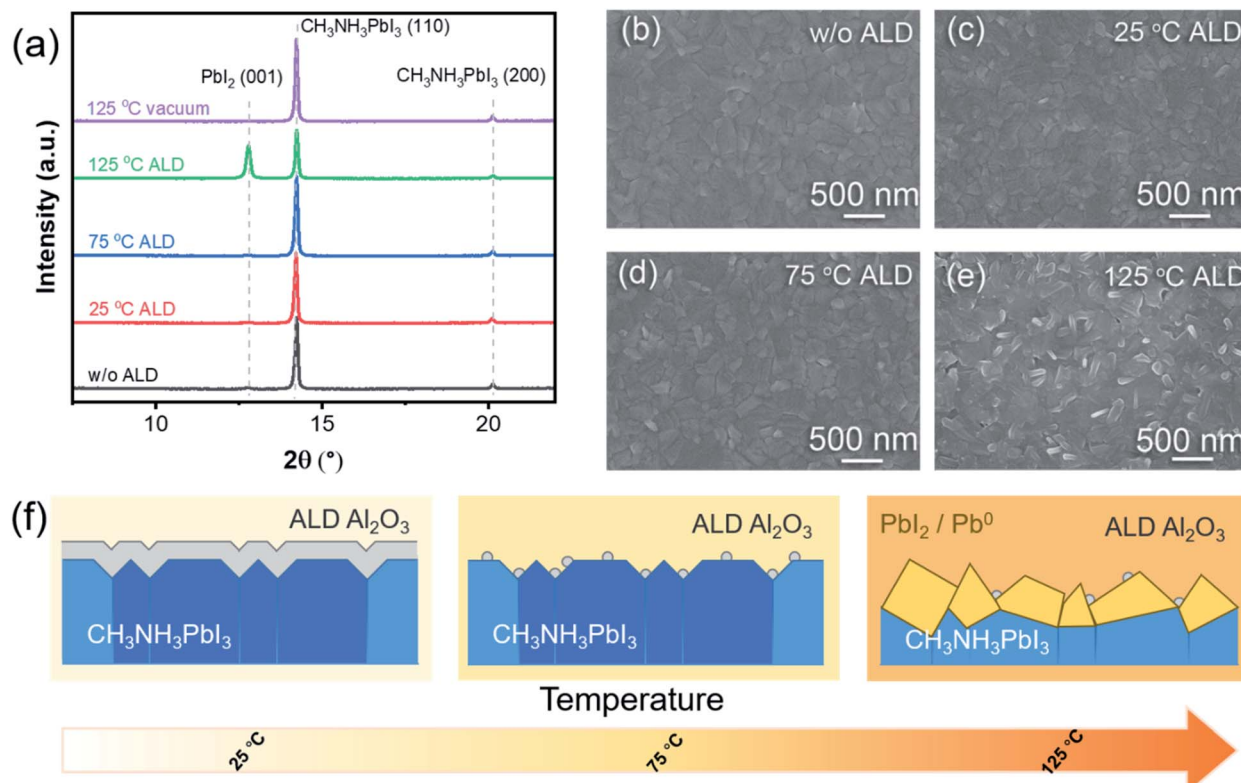


Fig. 2 (a) XRD patterns and (b–e) SEM images taken on a pristine MAPbI<sub>3</sub> film and the films with 10-cycle ALD of Al<sub>2</sub>O<sub>3</sub> on top. The deposition temperatures were 25 °C, 75 °C and 125 °C. For comparison, the XRD pattern for a MAPbI<sub>3</sub> film annealed under vacuum at 125 °C is also shown. (f) Schematic of the evolution of MAPbI<sub>3</sub> upon the ALD of Al<sub>2</sub>O<sub>3</sub> at different temperatures.

precursors must be the promoter to the degradation of the perovskite structure. Scanning electron microscopic (SEM) measurements were performed to examine the morphology of the above perovskite samples. The pristine perovskite layer was found to be fairly smooth and uniform (Fig. 2b), and the surface morphology remained almost unchanged after the ALD at 25 °C or 75 °C (Fig. 2c and d) or by vacuum annealing at 125 °C (Fig. S3†). However, the ALD at 125 °C considerably roughened the surface and created pinholes through the perovskite layer (Fig. 2e). On the basis of the above-mentioned analysis, Fig. 2f schematically summarizes the evolutions of MAPbI<sub>3</sub> upon the ALD of Al<sub>2</sub>O<sub>3</sub> at different temperatures. While the ALD at 125 °C considerably roughened the perovskite surface and formed metallic lead and PbI<sub>2</sub>, the degradation was largely minimized as the ALD temperature was lowered to 25 or 75 °C. Compared to 25 °C, the initial ALD growth at 75 °C was apparently slower, and therefore, the growth could occur more selectively on the surface defects.<sup>55</sup> As such, wide-band gap Al<sub>2</sub>O<sub>3</sub> could be more selective to only passivate the surface defects while not to impede the charge transport across the interface. Therefore, 75 °C was determined to be the best ALD temperature for perovskite passivation. In order to compare the hydrophobicity of the MAPbI<sub>3</sub> surface, we carried out the contact angle measurement. The contact angle increased from 52.79° to 75.81° after 10 cycles of ALD-Al<sub>2</sub>O<sub>3</sub> at 75 °C (Fig. S4†), which


indicates that the MAPbI<sub>3</sub> surface became more hydrophobic after ALD of Al<sub>2</sub>O<sub>3</sub>.

To further demonstrate the ALD passivation effect, we fabricated a series of inverted planar MAPbI<sub>3</sub> solar cells with ALD Al<sub>2</sub>O<sub>3</sub> and measured their photovoltaic performance. The cells had a configuration of FTO/NiO<sub>x</sub>/MAPbI<sub>3</sub>/ALD-Al<sub>2</sub>O<sub>3</sub>/PCBM/PPDIN6/Ag, which is schematically shown in Fig. 3a. The influence of the ALD temperature was first investigated by 10-cycle ALD of Al<sub>2</sub>O<sub>3</sub> directly on MAPbI<sub>3</sub> (Fig. 3b). The benchmarking solar cells (*i.e.* without ALD) exhibited an average power conversion efficiency (PCE) of 18.8% (champion of 19.2%). The ALD at the temperatures of 25 °C and 75 °C were both found to increase the PCE. As shown in Fig. 3b and S2,† the open-circuit voltage ( $V_{oc}$ ) and fill factor were both increased by ALD, probably because of the surface defect passivation by the ALD of Al<sub>2</sub>O<sub>3</sub>. However, the variations in the PSC parameters are considerably larger for 25 °C than for 75 °C, which suggests that the ALD passivation at 25 °C is less stable. However, the ALD at 125 °C was found to drastically deteriorate the efficiency to 14.2%, probably by forming the more insulating PbI<sub>2</sub> at the surface, which hindered the interface charge transfer and therefore reduced the short-circuit current ( $J_{sc}$ ).

Given the optimal ALD temperature of 75 °C, the effect of the total ALD cycle number was also investigated. As shown in Fig. S5,† the cells with 10-cycle ALD of Al<sub>2</sub>O<sub>3</sub> gave out the highest PCE, as compared to the 5- and 20-cycle samples. Notably, the





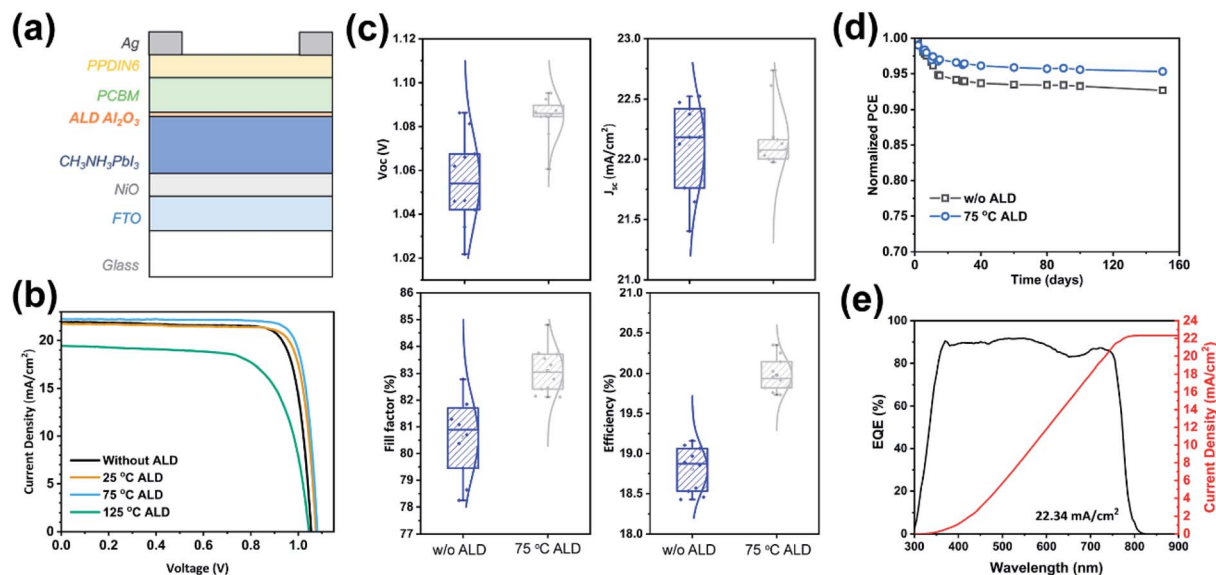

**Fig. 3** (a) Schematic architecture of the ambient-prepared PSCs with an ALD  $\text{Al}_2\text{O}_3$  interlayer: FTO/ $\text{NiO}_x$ /MAPbI<sub>3</sub>/ALD- $\text{Al}_2\text{O}_3$ /PCBM/PPDIN6/Ag. (b) Curves of current density versus voltage ( $J-V$ ) for the PSCs with and without 10 cycles of ALD of  $\text{Al}_2\text{O}_3$  deposited at 25 °C, 75 °C and 125 °C, and the corresponding statistical distributions of performance parameters are shown in Fig. S2† (c) Statistical distributions of  $V_{\text{oc}}$ ,  $J_{\text{sc}}$ , fill factor, and PCE for the PSCs with and without ALD  $\text{Al}_2\text{O}_3$  deposited at 75 °C. (d) Long-term stability of PSCs in a  $\text{N}_2$  atmosphere. (e) Incident photon-to-electron conversion efficiency (IPCE) spectrum and the corresponding integrated current density for the PSCs with 10 cycles of ALD of  $\text{Al}_2\text{O}_3$  at 75 °C ((b): 75 °C ALD).

equivalent thickness of 10-cycle ALD of  $\text{Al}_2\text{O}_3$  was only about 1 Å (Fig. 1h). With this extremely small number, it is highly probable that ALD  $\text{Al}_2\text{O}_3$  grew only selectively on the defect sites of the perovskite surface. This selective growth is desirable for effectively passivating the defects while not impeding the charge transport at the interface. As a result, 10-cycle ALD of  $\text{Al}_2\text{O}_3$  75 °C gave out a much-improved average PCE of 20.0% and a champion PCE of 20.4% (Fig. 3c). Moreover, the hysteresis was small for both of the PSCs with and without 10 cycles of ALD of  $\text{Al}_2\text{O}_3$  at 75 °C (Fig. S6†).

The stability of the fabricated solar cells was also evaluated in a  $\text{N}_2$ -filled glove box. As shown in Fig. 3d, after the initial “burn-in” process,<sup>29,56</sup> the normalized PCE of the solar cells remained fairly stable over the later test period up to 150 days. With the addition of ALD  $\text{Al}_2\text{O}_3$ , the eventual retention of the PCE increased from 92.7% to 95.3%, which suggests a good stability of the ALD-passivated perovskite. The maximum power point tracking result is shown in Fig. S7† in which the PSCs with and without ALD- $\text{Al}_2\text{O}_3$  both have high operational stability. The incident photon-to-electron conversion efficiency (IPCE) spectrum was also measured for the ALD-passivated champion cell. As shown in Fig. 3e, the spectrum shows a rather flat plateau at ~90% over the wavelength range from 380 to 760 nm, and the integrated current density was found to be  $22.34 \text{ mA cm}^{-2}$ , which agrees well with the cell  $J-V$  curve of sample 75 °C ALD in Fig. 3b.

To further understand the charge transport at the perovskite/ $\text{Al}_2\text{O}_3$  interface, we carried out both steady-state photoluminescence spectroscopy (PL) and time-resolved photoluminescence spectroscopy (TRPL) experiments on the perovskite films with PVK/ $\text{Al}_2\text{O}_3$  and without ALD  $\text{Al}_2\text{O}_3$  (PVK).

The observed PL signals (Fig. 4a) reflect the radiative direct recombination of the photo-generated free carriers. With the presence of defects, the photo-generated carriers can be trapped at the defects and recombine non-radiatively *via* a Shockley–Read–Hall (SRH) process, resulting in poor PL efficiency.<sup>57,58</sup> As shown in Fig. 4a, compared to the bare perovskite film, the perovskite with ALD  $\text{Al}_2\text{O}_3$  shows appreciably enhanced PL intensity, which suggests that the defects at the MAPbI<sub>3</sub> surface were well passivated by the ALD of  $\text{Al}_2\text{O}_3$ . At the same time, a small blue-shift from 768 to 766 nm was also observed for the PL peak of the PVK/ $\text{Al}_2\text{O}_3$  sample, and this blue-shift could be well ascribed to the reduction of the defect traps, which recover the band edge transition.<sup>59,60</sup> Reinforcing evidence was also obtained from the TRPL results. Fig. 4b and c show the TRPL spectra of the samples with the laser illumination from the air side (*i.e.* the  $\text{Al}_2\text{O}_3$  side) and the glass side, respectively. Note that the light penetration depth (~100 nm (ref. 61)) is smaller than the perovskite layer thickness, and therefore, the TRPL spectra of different sides can provide information about the location of the defects. As shown in Fig. 4b and c, the TRPL curves were all fitted by a bi-exponential decay function, where a longer lifetime of decay corresponds to fewer defects.<sup>4,62,63</sup> Table S1† displays the detailed fitting results. For the air-side illumination, the average lifetime increases significantly from 20.88 ns to 73.39 ns after the ALD of  $\text{Al}_2\text{O}_3$ , which again suggests that the ALD of  $\text{Al}_2\text{O}_3$  can effectively passivate the defects on the perovskite surface. In comparison, the glass-side TRPL curves give out a smaller increase in the average lifetime from 49.42 ns to 77.52 ns after the ALD. These results suggest that most of the problematic defects are located near the top surface of the

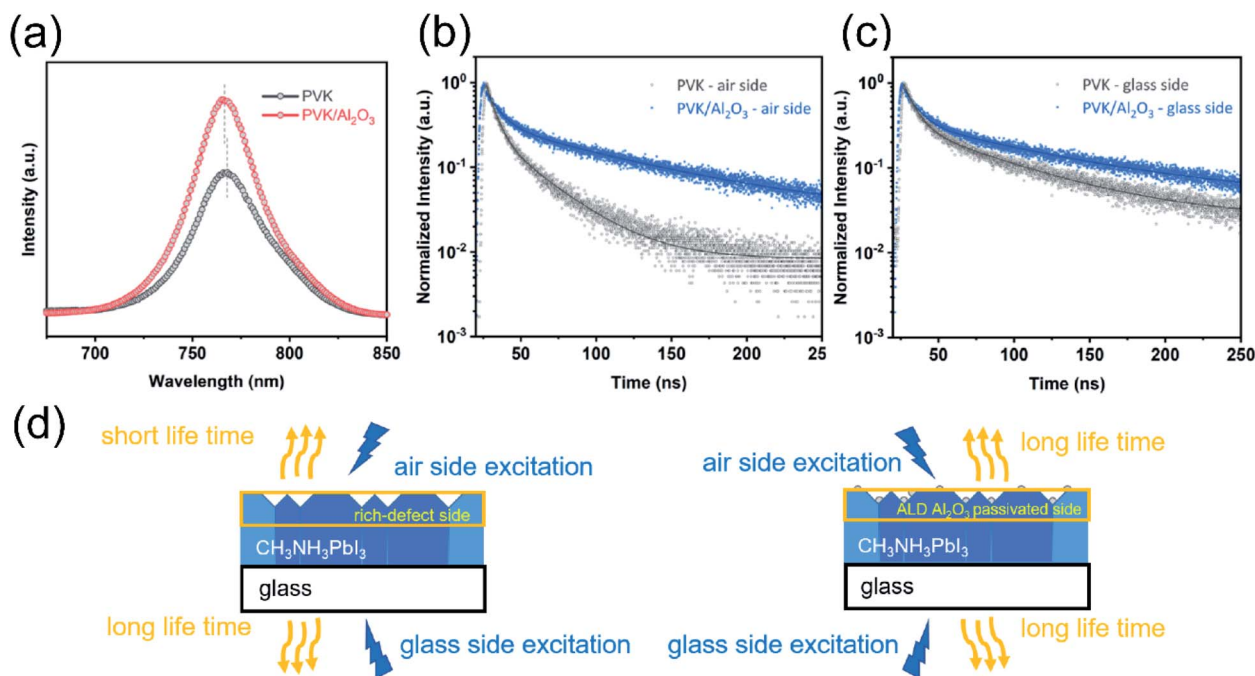


Fig. 4 (a) Steady-state photoluminescence (PL) spectra and (b and c) time-resolved photoluminescence (TRPL) spectra of the perovskite-on-glass samples with and without ALD  $\text{Al}_2\text{O}_3$ . (d) Schematic of the relationship between the carrier life time and laser excitation side.

perovskite and they can be effectively passivated by the ALD of  $\text{Al}_2\text{O}_3$  (Fig. 4d).<sup>64</sup>

## Conclusions

In summary, the atomic layer deposition (ALD) technique offers a generally promising approach to effectively passivate the perovskite surface defects to improve the power conversion efficiency and stability of PSCs. However, owing to the sensitive chemical reactivity of the perovskite surface, discrepant and conflicting observations of the ALD passivation were often reported in the literature. To unveil the involved crucial mechanism, we herein utilized the *in situ* XPS technique to directly investigate the evolution of a representative high-performance  $\text{MAPbI}_3$  perovskite surface during the ALD process of  $\text{Al}_2\text{O}_3$ . For the ALD at 125 °C, we observed pronounced degradation of the perovskite, as there formed metallic lead at the perovskite/ $\text{Al}_2\text{O}_3$  interface and a considerable portion of the bulk perovskite converted to  $\text{PbI}_2$ . As the ALD temperature was lowered to 25 or 75 °C, the degradation was largely minimized, and we observed the formation of  $\text{CH}_3\text{NH}_2$ , which could possibly heal the perovskite surface defects. The initial ALD growth at 75 °C was apparently slower than that at 25 °C, and therefore  $\text{Al}_2\text{O}_3$  grew more selectively on the surface defects, which was desirable to not impede the charge transport across the interface. Therefore, 75 °C was determined to be the best ALD temperature for perovskite passivation. Following this conclusion, inverted planar perovskite solar cells were prepared with the ALD interlayers. Indeed, the cells with the ALD  $\text{Al}_2\text{O}_3$  interlayer deposited at 75 °C exhibited a significantly enhanced PCE from 18.8% (champion 19.2%) to 20.0% (champion 20.4%), along

with improved  $V_{\text{oc}}$  and fill factor. In contrast, the ALD at 125 °C drastically deteriorated the cell PCE, which signifies the crucial importance to restrain the in-ALD-process degradation of the perovskites for the high-performance PSCs. Finally, we carried out steady-state and time-resolved PL to explicitly characterize the perovskite layer, and the results indicated that it was the ALD layer that reduced the defect states at the perovskite surface. The harmony of the PSC performance with the implications from the mechanism investigation well highlights the importance of the *in situ* interface investigation toward rational designing of the perovskite solar cells. Considering the great representativeness and broad applicability of  $\text{MAPbI}_3$  and ALD  $\text{Al}_2\text{O}_3$ , the mechanism and strategy reported herein should be of significant value for the PSC interface engineering in general.

## Author contributions

R. Zhao, K. Zhang, and J. Zhu contributed equally to this work. Prof. S. Yang, S. Xiao and X. Wang supervised this work. R. Zhao, K. Zhang, J. Zhu and S. Xiao designed and conducted the experiments. X. Wang, R. Zhao and J. Zhu took charge of the work of ALD. R. Zhao measured and analysed the *in situ* XPS data, and wrote the manuscript. R. Zhao and J. Zhu optimized the ALD technology and analysed the relevant data. W. Xiong conducted measurement of SEM. S. Yang, S. Xiao and K. Zhang took charge of the work of perovskite solar cells. S. Xiao and K. Zhang conducted device fabrication, characterization and analysis of passivation mechanism, and prepare relevant data. J. Wang analysed defects of perovskite. T. Liu, G. Xing, and K. Wang carried out the measurement and analysis of TRPL. All authors participated in the writing or revise of the manuscript.





## Conflicts of interest

The authors declare no conflict of interest.

## Acknowledgements

This work was financially supported by NSFC (Grant No. 51961165105, 21905006 and 21972006), Shenzhen Fundamental Research Program (Grant No. JCYJ20180302150402760, JCYJ20200109110628172 and JCYJ20190808163201831), Shenzhen Peacock Plan (KQTD2016053015544057), the Nanshan Pilot Plan (LHTD20170001), Guangdong Basic and Applied Basic Research Foundation (2019A1515110434 and 2020B1515120039), The Shenzhen & Hong Kong Joint Research Program (SGLH20180622092406130).

## Notes and references

- 1 A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
- 2 Laboratory, N. R. E., in <https://www.nrel.gov/pv/assets/pdfs/best-research-cell-efficiencies.20190802.pdf>.
- 3 P. Schulz, D. Cahen and A. Kahn, Halide Perovskites: Is It All about the Interfaces?, *Chem. Rev.*, 2019, **119**, 3349–3417.
- 4 C. M. Wolff, P. Caprioglio, M. Stolterfoht and D. Neher, Nonradiative Recombination in Perovskite Solar Cells: The Role of Interfaces, *Adv. Mater.*, 2019, **31**, e1902762.
- 5 A. Fakharuddin, L. Schmidt-Mende, G. Garcia-Belmonte, R. Jose and I. Mora-Sero, Interfaces in Perovskite Solar Cells, *Adv. Energy Mater.*, 2017, **7**, 1700623.
- 6 F. Gao, Y. Zhao, X. Zhang and J. You, Recent Progresses on Defect Passivation toward Efficient Perovskite Solar Cells, *Adv. Energy Mater.*, 2019, 1902650.
- 7 Y. Bai, X. Meng and S. Yang, Interface Engineering for Highly Efficient and Stable Planar p-i-n Perovskite Solar Cells, *Adv. Energy Mater.*, 2018, **8**, 1701883.
- 8 Y. Bai, *et al.*, Dimensional Engineering of a Graded 3D-2D Halide Perovskite Interface Enables Ultrahigh  $V_{oc}$  Enhanced Stability in the p-i-n Photovoltaics, *Adv. Energy Mater.*, 2017, **7**, 1701038.
- 9 E. H. Jung, *et al.*, Efficient, stable and scalable perovskite solar cells using poly(3-hexylthiophene), *Nature*, 2019, **567**, 511.
- 10 Q. Jiang, *et al.*, Surface passivation of perovskite film for efficient solar cells, *Nat. Photonics*, 2019, **13**, 460.
- 11 X. Meng, *et al.*, Molecular design enabled reduction of interface trap density affords highly efficient and stable perovskite solar cells with over 83% fill factor, *Nano Energy*, 2018, **52**, 300–306.
- 12 J. A. Raiford, S. T. Oyakhire and S. F. Bent, Applications of atomic layer deposition and chemical vapor deposition for perovskite solar cells, *Energy Environ. Sci.*, 2020, **13**, 1997–2023.
- 13 S. M. George, Atomic Layer Deposition: An Overview, *Chem. Rev.*, 2009, **110**, 111–131.
- 14 X. Meng, *et al.*, Atomic layer deposition for nanomaterial synthesis and functionalization in energy technology, *Mater. Horiz.*, 2017, **4**, 133–154.
- 15 H. B. Huang, *et al.*, 20.8% industrial PERC solar cell: ALD  $Al_2O_3$  rear surface passivation, efficiency loss mechanisms analysis and roadmap to 24%, *Sol. Energy Mater. Sol. Cells*, 2017, **161**, 14–30.
- 16 K. O. Brinkmann, T. Gahlmann and T. Riedl, Atomic Layer Deposition of Functional Layers in Planar Perovskite Solar Cells, *Sol. RRL*, 2019, **4**, 1900332.
- 17 V. Zardetto, *et al.*, Atomic layer deposition for perovskite solar cells: research status, opportunities and challenges, *Sustainable Energy Fuels*, 2017, **1**, 30–55.
- 18 X. Dong, *et al.*, Improvement of the humidity stability of organic–inorganic perovskite solar cells using ultrathin  $Al_2O_3$  layers prepared by atomic layer deposition, *J. Mater. Chem. A*, 2015, **3**, 5360–5367.
- 19 D. Koushik, *et al.*, High-efficiency humidity-stable planar perovskite solar cells based on atomic layer architecture, *Energy Environ. Sci.*, 2017, **10**, 91–100.
- 20 M. Kot, *et al.*, Room-Temperature Atomic-Layer-Deposited  $Al_2O_3$  Improves the Efficiency of Perovskite Solar Cells over Time, *ChemSusChem*, 2018, **11**, 3640–3648.
- 21 M. Kot, *et al.*, Room-Temperature Atomic Layer Deposition of  $Al_2O_3$ : Impact on Efficiency, Stability and Surface Properties in Perovskite Solar Cells, *ChemSusChem*, 2016, **9**, 3401–3406.
- 22 D. Koushik, *et al.*, Atomic Layer Deposition Enabled Perovskite/PEDOT Solar Cells in a Regular n-i-p Architectural Design, *Adv. Mater. Interfaces*, 2017, **4**, 1700043.
- 23 H. Wei, *et al.*, Enhanced charge collection with ultrathin  $AlOx$  electron blocking layer for hole-transporting material-free perovskite solar cell, *Phys. Chem. Chem. Phys.*, 2015, **17**, 4937–4944.
- 24 Y. H. Lee, *et al.*, Enhanced Charge Collection with Passivation Layers in Perovskite Solar Cells, *Adv. Mater.*, 2016, **28**, 3966.
- 25 H. Si, *et al.*, An innovative design of perovskite solar cells with  $Al_2O_3$  inserting at  $ZnO$ /perovskite interface for improving the performance and stability, *Nano Energy*, 2016, **22**, 223–231.
- 26 J. Zhang, *et al.*,  $Al_2O_3$  Underlayer Prepared by Atomic Layer Deposition for Efficient Perovskite Solar Cells, *ChemSusChem*, 2017, **10**, 3810–3817.
- 27 X. Yu, H. Yan and Q. Peng, Reaction Temperature and Partial Pressure Induced Etching of Methylammonium Lead Iodide Perovskite by Trimethylaluminum, *Langmuir*, 2019, **35**, 6522–6531.
- 28 S. Xiao, *et al.*, An Ultra - low Concentration of Gold Nanoparticles Embedded in the  $NiO$  Hole Transport Layer Boosts the Performance of p-i-n Perovskite Solar Cells, *Sol. RRL*, 2018, 1800278.
- 29 K. Zhang, *et al.*, A prenucleation strategy for ambient fabrication of perovskite solar cells with high device performance uniformity, *Nat. Commun.*, 2020, **11**, 1006.



- 30 R. Zhao, Z. Guo and X. Wang, Surface Chemistry during Atomic-Layer Deposition of Nickel Sulfide from Nickel Amidinate and  $\text{H}_2\text{S}$ , *J. Phys. Chem. C*, 2018, **122**, 21514–21520.
- 31 R. Zhao and X. Wang, Initial Growth and Agglomeration during Atomic Layer Deposition of Nickel Sulfide, *Chem. Mater.*, 2019, **31**, 445–453.
- 32 R. Zhao, S. Xiao, S. Yang and X. Wang, Surface Thermolytic Behavior of Nickel Amidinate and Its Implication on the Atomic Layer Deposition of Nickel Compounds, *Chem. Mater.*, 2019, **31**, 5172–5180.
- 33 R. Zhao, Y. Gao, Z. Guo, Y. Su and X. Wang, Interface Energy Alignment of Atomic-Layer-Deposited  $\text{VO}_x$  on Pentacene: an in Situ Photoelectron Spectroscopy Investigation, *ACS Appl. Mater. Interfaces*, 2017, **9**, 1885–1890.
- 34 S. Tanuma, C. J. Powell and D. R. Penn, Calculation of electron inelastic mean free paths (IMFPs) VII. Reliability of the TPP-2M IMFP predictive equation, *Surf. Interface Anal.*, 2003, **35**, 268–275.
- 35 D. Choudhury, G. Rajaraman and S. K. Sarkar, Self limiting atomic layer deposition of  $\text{Al}_2\text{O}_3$  on perovskite surfaces: a reality?, *Nanoscale*, 2016, **8**, 7459–7465.
- 36 J. Dendooven, D. Deduytsche, J. Musschoot, R. L. Vanmeirhaeghe and C. Detavernier, Modeling the Conformality of Atomic Layer Deposition: The Effect of Sticking Probability, *J. Electrochem. Soc.*, 2009, **156**, P63.
- 37 W. Huang, S. Sadhu and S. Ptasińska, Heat- and Gas-Induced Transformation in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  Perovskites and Its Effect on the Efficiency of Solar Cells, *Chem. Mater.*, 2017, **29**, 8478–8485.
- 38 F. Zheng, H. Takenaka, F. G. Wang, N. Z. Koocher and A. M. Rappe, First-Principles Calculation of the Bulk Photovoltaic Effect in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  and  $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$ , *J. Phys. Chem. Lett.*, 2015, **6**, 31–37.
- 39 A. F. Palmstrom, *et al.*, Interfacial Effects of Tin Oxide Atomic Layer Deposition in Metal Halide Perovskite Photovoltaics, *Adv. Energy Mater.*, 2018, **8**, 1800591.
- 40 D. Koushik, *et al.*, Chemical Analysis of the Interface between Hybrid Organic-Inorganic Perovskite and Atomic Layer Deposited  $\text{Al}_2\text{O}_3$ , *ACS Appl. Mater. Interfaces*, 2019, **11**, 5526–5535.
- 41 M.-C. Jung, *et al.*, Formation of  $\text{CH}_3\text{NH}_2$ -incorporated intermediate state in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  hybrid perovskite thin film formed by sequential vacuum evaporation, *Appl. Phys. Express*, 2019, **12**, 015501.
- 42 A. Calloni, *et al.*, Stability of Organic Cations in Solution-Processed  $\text{CH}_3\text{NH}_3\text{PbI}_3$  Perovskites: Formation of Modified Surface Layers, *J. Phys. Chem. C*, 2015, **119**, 21329–21335.
- 43 M. Tallarida, *et al.*, Substrate Reactivity Effects in the Atomic Layer Deposition of Aluminum Oxide from Trimethylaluminum on Ruthenium, *Chem. Mater.*, 2011, **23**, 3159–3168.
- 44 C. Zeng, *et al.*, Dual redox couples  $\text{Ag}/\text{Ag}^+$  and  $\text{I}^-/(\text{IO}_3)^-$  self-sacrificed transformation for realizing multiplex hierarchical architectures with universally powerful photocatalytic performance, *Appl. Catal., B*, 2017, **200**, 620–632.
- 45 C. Das, M. Wussler, T. Hellmann, T. Mayer and W. Jaegermann, In situ XPS study of the surface chemistry of MAPi solar cells under operating conditions in vacuum, *Phys. Chem. Chem. Phys.*, 2018, **20**, 17180–17187.
- 46 L. She, M. Liu and D. Zhong, Atomic Structures of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  (001) Surfaces, *ACS Nano*, 2016, **10**, 1126–1131.
- 47 J. Haruyama, K. Sodeyama, L. Han and Y. Tateyama, Termination Dependence of Tetragonal  $\text{CH}_3\text{NH}_3\text{PbI}_3$  Surfaces for Perovskite Solar Cells, *J. Phys. Chem. Lett.*, 2014, **5**, 2903–2909.
- 48 C. Quarti, E. Mosconi and F. De Angelis, Interplay of Orientational Order and Electronic Structure in Methylammonium Lead Iodide: Implications for Solar Cell Operation, *Chem. Mater.*, 2014, **26**, 6557–6569.
- 49 A. Buin, *et al.*, Materials processing routes to trap-free halide perovskites, *Nano Lett.*, 2014, **14**, 6281–6286.
- 50 Z. Zhou, *et al.*, Methylamine-Gas-Induced Defect-Healing Behavior of  $\text{CH}_3\text{NH}_3\text{PbI}_3$  Thin Films for Perovskite Solar Cells, *Angew. Chem., Int. Ed.*, 2015, **54**, 9705–9709.
- 51 J.-a. Yang, *et al.*, Methylamine-induced defect-healing and cationic substitution: a new method for low-defect perovskite thin films and solar cells, *J. Mater. Chem. C*, 2019, **7**, 10724–10742.
- 52 M. Long, *et al.*, Textured  $\text{CH}_3\text{NH}_3\text{PbI}_3$  thin film with enhanced stability for high performance perovskite solar cells, *Nano Energy*, 2017, **33**, 485–496.
- 53 R. L. Puurunen and W. Vandervorst, Island growth as a growth mode in atomic layer deposition: A phenomenological model, *J. Appl. Phys.*, 2004, **96**, 7686–7695.
- 54 T. Oku, in *Solar Cells - New Approaches and Reviews*, 2015, ch. 3.
- 55 K. Cao, J. Cai and R. Chen, Inherently Selective Atomic Layer Deposition and Applications, *Chem. Mater.*, 2020, **32**, 2195–2207.
- 56 J. A. Christians, *et al.*, Tailored interfaces of unencapsulated perovskite solar cells for >1000 hour operational stability, *Nat. Energy*, 2018, **3**, 68–74.
- 57 W. Peng, *et al.*, Influence of growth temperature on bulk and surface defects in hybrid lead halide perovskite films, *Nanoscale*, 2016, **8**, 1627–1634.
- 58 V. Sarritzu, *et al.*, Optical determination of Shockley-Read-Hall and interface recombination currents in hybrid perovskites, *Sci. Rep.*, 2017, **7**, 44629.
- 59 Y. Shao, Z. Xiao, C. Bi, Y. Yuan and J. Huang, Origin and elimination of photocurrent hysteresis by fullerene passivation in  $\text{CH}_3\text{NH}_3\text{PbI}_3$  planar heterojunction solar cells, *Nat. Commun.*, 2014, **5**, 5784.
- 60 C. Sun, *et al.*, Amino-Functionalized Conjugated Polymer as an Efficient Electron Transport Layer for High-Performance Planar-Heterojunction Perovskite Solar Cells, *Adv. Energy Mater.*, 2016, **6**, 1501534.
- 61 L. J. Phillips, *et al.*, Dispersion relation data for methylammonium lead triiodide perovskite deposited on a (100) silicon wafer using a two-step vapour-phase reaction process, *Data Brief*, 2015, **5**, 926–928.



- 62 N. K. Noel, *et al.*, Enhanced Photoluminescence and Solar Cell Performance via Lewis Base Passivation of Organic–Inorganic Lead Halide Perovskites, *ACS Nano*, 2014, **8**, 9815–9821.
- 63 N. S. Han, *et al.*, Defect states of ZnO nanoparticles: Discrimination by time-resolved photoluminescence spectroscopy, *J. Appl. Phys.*, 2010, **107**, 084306.
- 64 M. Wang, *et al.*, Repairing Defects of Halide Perovskite Films To Enhance Photovoltaic Performance, *ACS Appl. Mater. Interfaces*, 2018, **10**, 37005–37013.

