

PAPER

[View Article Online](#)
[View Journal](#) | [View Issue](#)


Cite this: *Green Chem.*, 2023, **25**, 10622

Selective chemical disassembly of elastane fibres and polyurethane coatings in textiles†

Martin B. Johansen, ^{‡a} Bjarke S. Donslund, ^{‡b} Martin L. Henriksen, ^c Steffan K. Kristensen ^{*a} and Troels Skrydstrup ^{*d}

The textile industry is ever-growing but only a few recycling options exist for waste fabrics to keep end-of-use clothing articles within the value chain. Generally, these include fibre-to-fibre strategies for pure textiles such as cotton or polyester. However, most textiles comprise blends of fibres which encumbers both mechanical and chemical recycling processes. For example, the polymer elastane is added to increase stretchability in many textiles, whereas polyurethane coatings and membranes partly make up rain clothes, bags and artificial leather items. Here we report the selective disassembly of these two polymers into base chemicals adapting a solvolysis process with *tert*-amyl alcohol. We showcase the successful depolymerisation of elastane recovered from the dissolution of fabric blends, and also the direct disassembly of elastane containing- or PU-coated textiles with polyamide fabrics. This work opens up new opportunities for the recycling of certain blended textiles.

Received 10th August 2023,
Accepted 6th November 2023

DOI: 10.1039/d3gc02994h

rsc.li/greenchem

Introduction

In 2020, the global textile production was estimated to have reached an astonishing 109 million tons. Partially due to a lack of good recycling methods, less than 1% of textiles are recycled in a closed-loop and the majority ends up as waste sent for landfilling or incineration.^{1,2} Clothing production has doubled in the last 15 years, largely due to the success of fast fashion in which low priced textiles are produced at a rate matching the quick turnarounds in fashion.^{2,3} The world demand for textile fibres is therefore projected to increase significantly reaching 140 million tons in 2030.⁴ Polyester, a synthetic fibre, constitutes 52% of the market, whereas the natural fibre cotton covers 24%, leaving the rest to nylon, wool, silk, viscose, elastane *etc.*¹ Chemical and physical recycling initiatives for polyester have already reached commer-

cialisation, while the present recycling of cotton relies on mechanical and physical methods.^{5–8} Regardless, only 1% of the textiles are kept within a closed recycling loop in which end-of-life textile fibres are converted into new textile fibres for similar quality applications (fibre-to-fibre recycling).^{2,9} The EU Commission recently published a new strategy stressing that fibre-to-fibre recycling remains a major challenge and recommends increased communication on sustainability to *e.g.* avoid “downcycling” of food-grade polyethylene terephthalate (PET) bottles into polyester fibres.^{10,11}

Input of single component fibres for recycling offers closed-loop possibilities but mixed fibres impede efficient processes for recycling, and especially, recycling of mixed fibres containing elastane is problematic.^{2,5–11} Elastane (or Spandex – anagram for expands) is a synthetic fibre displaying stretchable properties. It is often used in composite clothing articles in combination with polyester, cotton or nylon, providing high elasticity and durability to the fabric.⁵ DuPont originally branded the product under the name Lycra, especially for women's undergarment products, while U.S. Rubber named its brand Vyrene.^{12,13} Although elastane is regularly added to fabrics in quantities below 3%, this polymer is present in 20% of all potentially recyclable textile waste fractions, a number that is projected to increase to 30% in 2030.^{2,4}

Structurally, elastane is composed of a polyurethane-urea block copolymer prepared from a pre-polymer of 4,4'-methylene diisocyanate (MDI) and a macrodiol, usually poly(tetrahydrofuran) (polyTHF). The polymer is cured with a short diamine chain extender, such as ethylenediamine (Scheme 1a).^{14–17} The polymerisation termination is controlled by the addition of

^aInterdisciplinary Nanoscience Center (iNANO), Aarhus University, Gustav Wieds Vej 14, 8000 Aarhus C, Denmark. E-mail: skk@inano.au.dk

^bCarbon Dioxide Activation Center (CADIAC), Interdisciplinary Nanoscience Center (iNANO) and Department of Chemistry, Aarhus University, Gustav Wieds Vej 14, 8000 Aarhus C, Denmark

^cDepartment of Biological and Chemical Engineering, Aarhus University, Aabogade 40, 8200 Aarhus N, Denmark


^dCarbon Dioxide Activation Center (CADIAC), Novo Nordisk Foundation CO₂ Research Center, Interdisciplinary Nanoscience Center (iNANO) and Department of Chemistry, Aarhus University, Gustav Wieds Vej 14, 8000 Aarhus C, Denmark.

E-mail: ts@chem.au.dk


† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3gc02994h>

‡ These authors contributed equally.

a

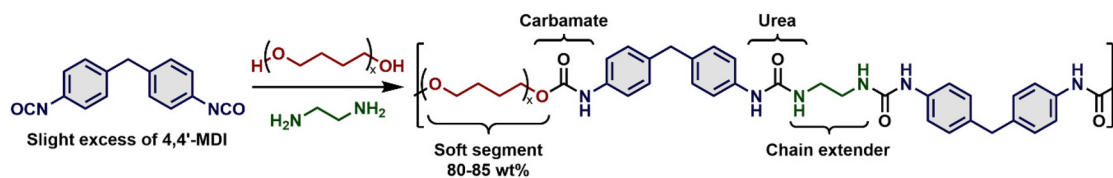

b

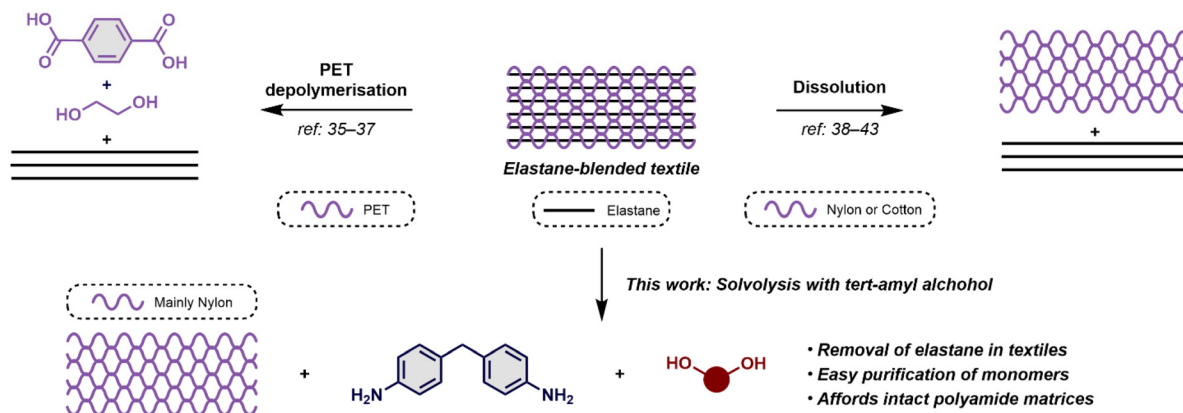

Scheme 1 Synthetic route for elastane and examples of elastane removal from textiles along with this work. (a) Structural composition of elastane based on polyurethane-urea block copolymers. (b) Previous work based on depolymerisation of PET in blended PET-elastane textiles or dissolution methods, and this work based on selective depolymerisation of elastane to base chemicals in blended textiles using *tert*-amyl alcohol as a solvolysis medium.

secondary amines such as diethylamine, which fine-tunes the average molecular weight by the formation of a urea end group.^{16,17} The majority of the polymer (80–85 wt%) is composed of the flexible diol, being referred to as the soft segment. The urea functional groups make up the hard segments and create a pseudo-cross-linked polymer through hydrogen bonding.¹⁶ This makes elastane a flexible solid with molecular similarities to flexible polyurethane (PU) solids.

Potential recycling methods for elastane could be inspired by the current strive towards a circular PU economy.^{18–23} Existing recycling strategies for PU, such as mechanical reuse, have very limited applications for textile waste streams containing elastane, as considerable forces are needed to shred and unravel such elastic materials.^{11,24} On the other hand, chemical recycling by means of disassembly of the textile polymer to monomers could represent a potential solution.^{18,25} To date, only a few chemical recycling methods exist for PU deconstruction, including hydrolysis, aminolysis, acidolysis and glycolysis.^{26–34} However, the scientific literature is scarce when it comes to recycling of textile blends containing elastane, which could be due to issues regarding chemoselectivity or elevated reaction temperature. Nevertheless, a few strategies have been reported. Recently, the selective depolymerisation of a PET-elastane blended textile was revealed to be successful in a $\text{CH}_2\text{Cl}_2/\text{EtOH}$ solvent system in the presence of KOH or in a THF/ethylene glycol (EG) solvent system with excess KOH to afford the EG and terephthalic acid components, leaving the elastane fibres intact (Scheme 1b, left).^{35,36} Thus, the remain-

ing elastane could in theory be melted and extruded into new fibres if sufficient fibre quality can be preserved. Adding to this, Wang and co-workers later provided new insights into the alcoholysis of blended fabrics, showcasing the decomposition of elastane in PET glycolysis and showed how initial dissolution strategies could afford elastane, which could be depolymerised into 4,4'-methylenedianiline (4,4'-MDA), polyTHF and 2-imidazolidone by a glycolysis process.³⁷

Dissolution represents a more established method for separating fibre blends, where certain fibres can be selectively solubilised by judicious choice of solvent.^{38–40} Elastane can accordingly be removed from either nylon or cotton fabrics by applying high-boiling polar amide solvents such as DMF (Scheme 1b, right).^{41–43} This technology represents a useful operation for the removal of elastane from major fibre components, which can subsequently be spun into new yarns and reused in fabrics. However, the removal of the generally undesirable DMF is energy intensive and the quality of the remaining fibre is often compromised as judged by the degree of depolymerisation and highly dependent on the choice of solvent.⁴¹

Our previous endeavours on depolymerisation of PU materials revealed *tert*-amyl alcohol with catalytic amounts of KOH as an efficient solvolysis medium.^{44,45} In those studies, we demonstrated the general value of the depolymerisation process for flexible foam-, rigid foam-, flexible solid- and rigid solid polyurethanes. Herein, we disclose our efforts to disassemble elastane by this process initially starting from virgin elastane,


moving to elastane recovered by dissolution and finally directly from textile blends to assess the possibility of recovering the main textile component and isolating monomers suitable for repolymerization of elastane (Scheme 1b, bottom). As the solvolysis medium is mainly constituted by a weak nucleophile in the form of a tertiary alcohol, it was hypothesised that the chemoselectivity could leave functional groups of *e.g.* nylon and cotton unscathed despite elevated reaction temperatures.

Results and discussion

The study was initiated by performing the solvolysis on 250 mg of pure elastane fibre of an unknown composition using *tert*-amyl alcohol (5 mL) and KOH (1.9 mg) at 225 °C. Resorting to “back-of-the-envelope” calculations, assuming a polyTHF content of 80–85 wt%, the theoretical yield of 4,4'-MDA from 250 mg elastane was estimated to be 28–37 mg (see ESI-4† for full details and calculations). With a reaction time of 2.25 h in *tert*-amyl alcohol and catalytic KOH, a GC yield of 18.9 mg of 4,4'-MDA was achieved, meaning that full depolymerisation was not achieved (Scheme 2a). Extension of the reaction time to 4.5 h resulted in increased formation of 4,4'-MDA and polyTHF with isolated yields of 33.3 mg and 186 mg,

respectively, as an average of two separate reactions, giving an overall mass recovery of 86 wt%. It was noted that the reaction mixture contained small amounts of precipitate possibly originating from the presence of an anti-sticking agent (potentially magnesium stearate) on the elastane filament, which was not investigated further.⁴⁶ Neither the diamine chain extender nor the terminating secondary amine was isolated due to the low boiling point (b.p.) of the suspected ethylenediamine (b. p. 117 °C) and diethylamine (b.p. 56 °C).^{47,48} It is likely that this result represents a full depolymerisation as prolonged reaction times did not increase the yield further.

Next, dissolution of elastane from pieces cut from black nylon tights (73% PA, 27% elastane) obtained at a local shop was performed.^{41–43} From 5.10 g of the tights, 61 wt% of polyamide leftover fabric and 33 wt% of elastane extract were recovered (Scheme 2b). FTIR analysis suggested that the elastane had been effectively removed from the polyamide matrix (see ESI-9† for full details). The elastane extract from the dissolution was subjected to solvolysis using *tert*-amyl alcohol and a catalytic amount of base (Scheme 2c). After purification, the amine and polyTHF were isolated giving a total mass recovery of 84 wt%. Hence, elastane extracted from a polyamide matrix has been successfully depolymerised using solvolysis to afford its base chemicals. This result offers an opportunity for

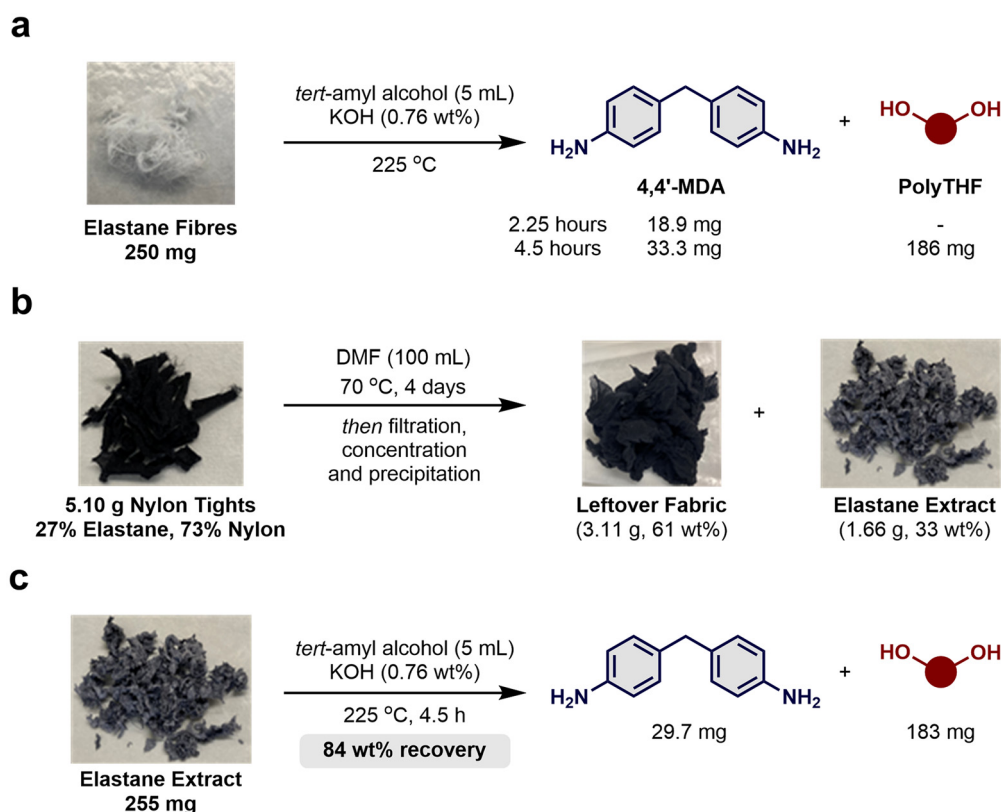

Scheme 2 Solvolysis of elastane fibres and nylon tights. (a) Solvolysis of elastane fibres. Reactions were performed in 45 mL autoclaves fitted with a 30 mL PTFE inlay at 800 rpm under air. GC-FID yield determined using 1,3,5-trimethylbenzene as an internal standard and reported as averages of two parallel reactions. (b) Dissolution of nylon tights to obtain the elastane extract and leftover fabric. (c) Solvolysis of the elastane extract. Reported yields for elastane depolymerisation are isolated yields from column chromatography as an average of two parallel reactions.

recycling elastane obtained from dissolution which is too damaged to be remoulded directly.

To avoid the need for isolation of elastane from a mixed fabric containing both nylon and elastane, the solvolysis methodology was applied directly on black nylon tights (Scheme 3a, top). Here, the solvolysis process afforded 4,4'-MDA, polyTHF and a leftover fabric with an overall 96% mass recovery. The fabric was investigated *via* FTIR and the combined transmission spectra of the nylon tights (black) and leftover fabric (blue) were analysed (Scheme 3a, bottom). The polyamide is characterised by N-H stretch at 3298 cm⁻¹, C-H stretch at 2940 cm⁻¹ and 2855 cm⁻¹, C=O stretch at 1632 cm⁻¹, N-H stretch at 1533 cm⁻¹, C-N stretch at 1274 cm⁻¹ and C-C stretch at 933 cm⁻¹. Furthermore, elastane is characterised by C-H stretch at 2940 cm⁻¹, 2855 cm⁻¹ and 2799 cm⁻¹, C=O stretch at 1730 cm⁻¹ and 1708 cm⁻¹, C-O stretch at 1221 cm⁻¹ and C-O-C stretch at 1104 cm⁻¹. A mixture of nylon and elastane is found in the nylon tights, where only nylon is present in the leftover fabric. Hence, the polyamide remained unaltered, while the elastane fibres in the clothing material were depolymerised, and the elastane building blocks were isolated from the polyamide nylon tights.


The solvolysis process was further tested on two whole pairs of nylon tights (Beige) with a total weight of 33.1 g placed into a 390 mL autoclave (Scheme 4b, top). The stirring bar was omitted as the large fabric size would prevent efficient magnetic stirring. Using 0.19 wt% of KOH in 165 mL of *tert*-amyl alcohol, the leftover fabric was isolated by filtration and dried *in vacuo* providing 75 wt% recovered fabric. Here it is worth mentioning that the fabric closest to the bottom of the reactor had several spots of discolouring from overheating, likely due to the lack of stirring and contact of the fabric with the surface of the autoclave. By acid-base extractions, 4,4'-MDA (873 mg) and polyTHF (6.85 g) were separated summing up to a mass recovery of 23 wt% for the elastane components and a combined 98 wt% recovered material. The FTIR spectra of the nylon tights (Beige) before and after solvolysis were similar to those presented in Scheme 3a (see ESI-7† for full details). Differential scanning calorimetry (DSC) (Scheme 4b, bottom) indicates a crystalline peak for pure elastane at 20 °C. The nylon tights (untreated) show both a crystalline peak for elastane at 20 °C and a broad crystalline phase for the polyamide at 225 °C. Finally, the leftover fabric (treated) has no sign of elastane and the polyamide is capable of forming a crystalline phase at 255 °C. This indicates the successful removal of elastane and the polyamide fibre is intact without signs of degradation or contamination as the crystalline phase is uniform and narrow.

Next, fabrics mainly composed of cotton, viscose and polyester, were tested. The textiles were cut into squares and tested under the solvolysis conditions without any pretreatment. FTIR spectra of the fabrics were recorded before and after the reaction, but it was not possible to firmly conclude on the presence or removal of elastane due to larger overlapping signals (see ESI-10–12† for full details). Starting with organic cotton reported to contain 8 wt% elastane, it was possible to isolate 68.5 mg of polyTHF and discoloured pieces of leftover fabric

(Scheme 4a, top). The diamine 4,4'-MDA was detected in trace amounts by ¹H NMR analysis of the concentrated reaction mixture but the minute quantities were not isolated. For viscose, a cellulosic material containing 9% of elastane, 4,4'-MDA could not be detected, although 84.1 mg of polyTHF were isolated. Here, most of the discoloured leftover solids were physically fragmented into smaller pieces after solvolysis (Scheme 4a, middle). Next, a satin fabric composed of 86 wt% polyester and 14 wt% elastane was deconstructed into 4,4'-MDA, polyTHF and a polyester residue isolated as a powder (Scheme 4a, bottom). Soluble oligomers of polyester complicated the isolation of 4,4'-MDA and polyTHF, suggesting a lack of chemoselectivity as polyester was partially depolymerised during the solvolysis. To test this hypothesis, a sample of virgin polyester fibre was subjected to the solvolysis conditions affording 5.5 mg (2 wt%) of soluble polyester oligomers (see ESI-13† for full details). Thus, polyester degrades or partly solubilises under the standard solvolysis conditions leading to powdered polyester and soluble oligomers. As such, this showcases the lack of chemoselectivity for the solvolysis process when both carbamates and urea in elastane and esters in PET are present. From these findings, we can hypothesise that the high temperature applied in the solvolysis process may be detrimental to the structural integrity of viscose fibres and in particular polyester terephthalate. While the recovered cotton fabric appeared slightly weakened and brittle, the recovered PA66 from the tights qualitatively retained the properties of the clothing fabric.

With the finding that elastane could be removed directly from certain textiles, our attention moved to PU-coated textiles to explore if the solvolysis protocol could also depolymerise these PUs and offer useful remaining matrices. First, a sample of PU leather was tested. The base layer of the PU leather (rough side) was found to be polyester as deduced by FTIR analysis (see ESI-14† for full details). Although the synthetic leather is marketed as “100% PU,” this only applies to the smooth side of the fabric, while the rough side, at least for this sample, is based on polyester. After solvolysis, 4,4'-MDA could be precipitated by the addition of HCl from the crude mixture, and the polyol was thereby co-isolated with polyester oligomers (Scheme 4b, top). FTIR analysis revealed that elastane was not present in the leftover solids, and we speculate that the remaining black powder was a mixture of polyester and carbon black (see ESI-14† for full details).

Next, a pair of work gloves (brand name: HyFlex, PU coated polyamide) were acquired, and the thumb from one glove was subjected to the solvolysis conditions (Scheme 4b, middle). The leftover solid constituted a melted grey lump pointing to PA6 (m.p. = 218 °C). Following remelting to release the trapped solvent, FTIR analysis confirmed the removal of PU, while characteristic amide peaks were preserved (see ESI-15† for full details). The HCl-salt of 4,4'-MDA was isolated by precipitation in an average of 71.7 mg from two experiments. Besides the polyester polyol, the filtrate contained some silicone oil, potentially used as a surfactant during manufacturing. Nonetheless, a combined 91 wt% was recovered. Finally, a white waterproof workwear jacket (brand name: Flexothane Kleen, PU coated

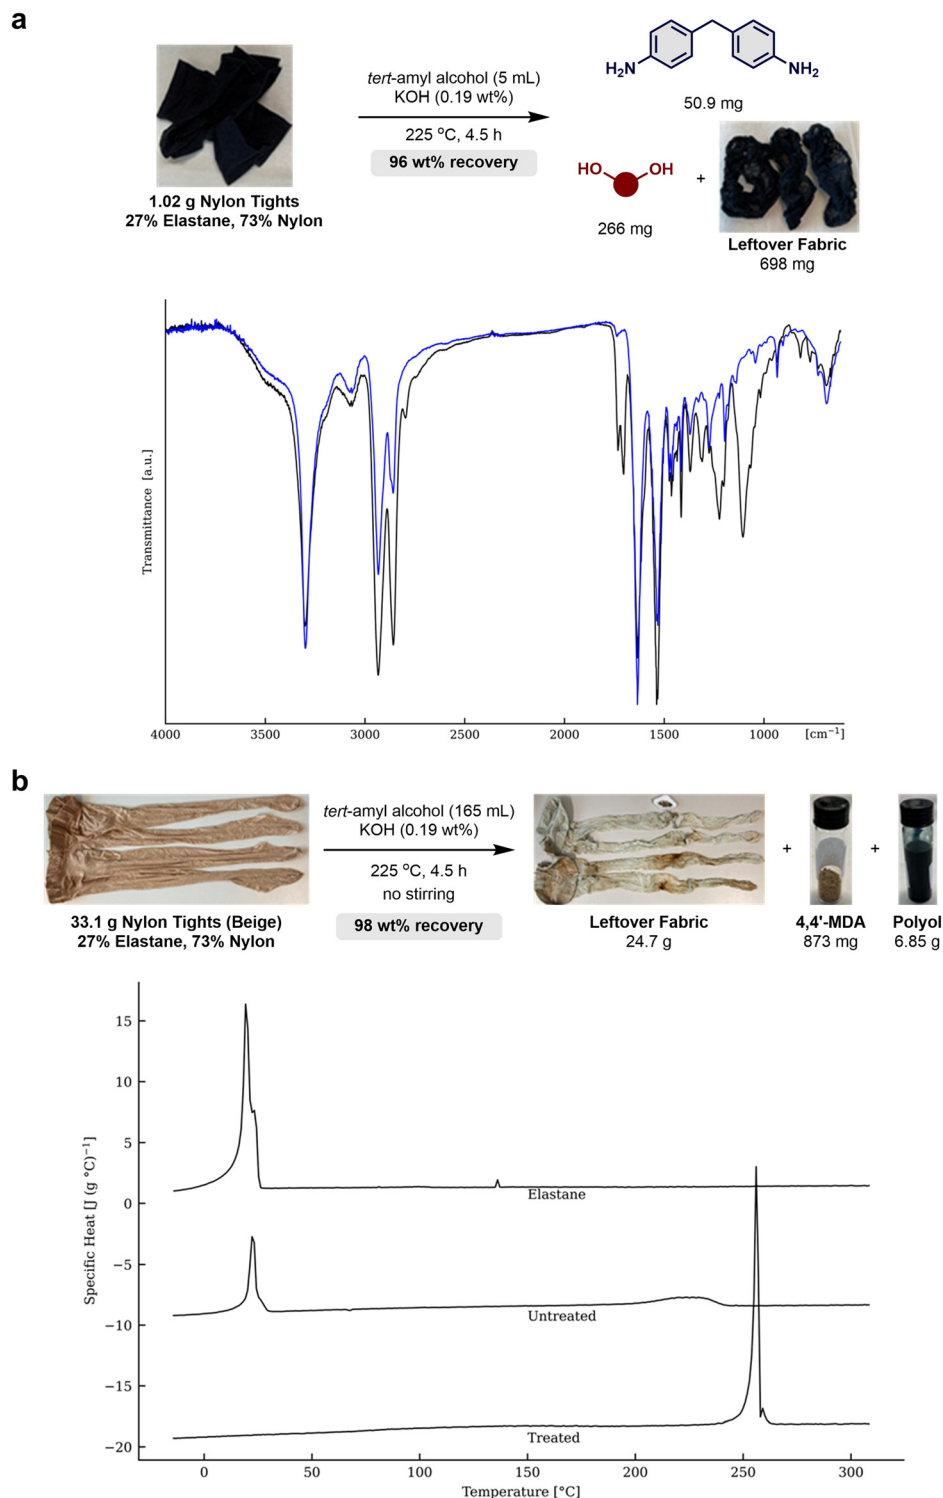


Scheme 3 Solvolysis of nylon-elastane fabrics. (a) Solvolysis of nylon tights along with FTIR of nylon tights (black) and leftover fabric (blue). Reactions were performed in a 45 mL autoclave fitted with a 30 mL PTFE inlay at 800 rpm under air. Reported yields for elastane deconstruction are isolated yields from column chromatography as an average of two parallel reactions. (b) Scale-up solvolysis of nylon tights (Beige) along with differential scanning calorimetry of elastane, the untreated nylon tights and the treated leftover fabric. Reaction was performed in a 390 mL autoclave without stirring under air. Reported yields for elastane deconstruction are isolated yields from column chromatography.


polyamide) was acquired and from the hood, samples were taken and applied to the solvolysis process (Scheme 4b, bottom). Here, the polyamide again appeared to be PA6 as the

leftover solid was isolated as a grey crisp disc, which was isolated from the bottom of the reactor (see ESI-16† for full details). The 4,4'-MDA-salt and polyester polyol were recovered

a

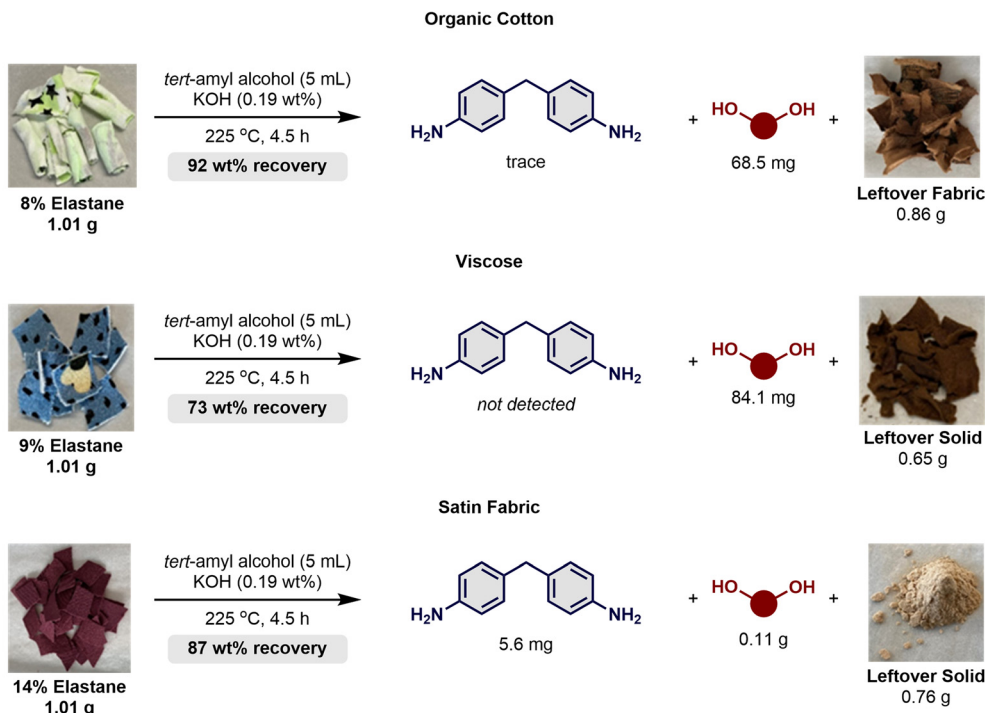

b

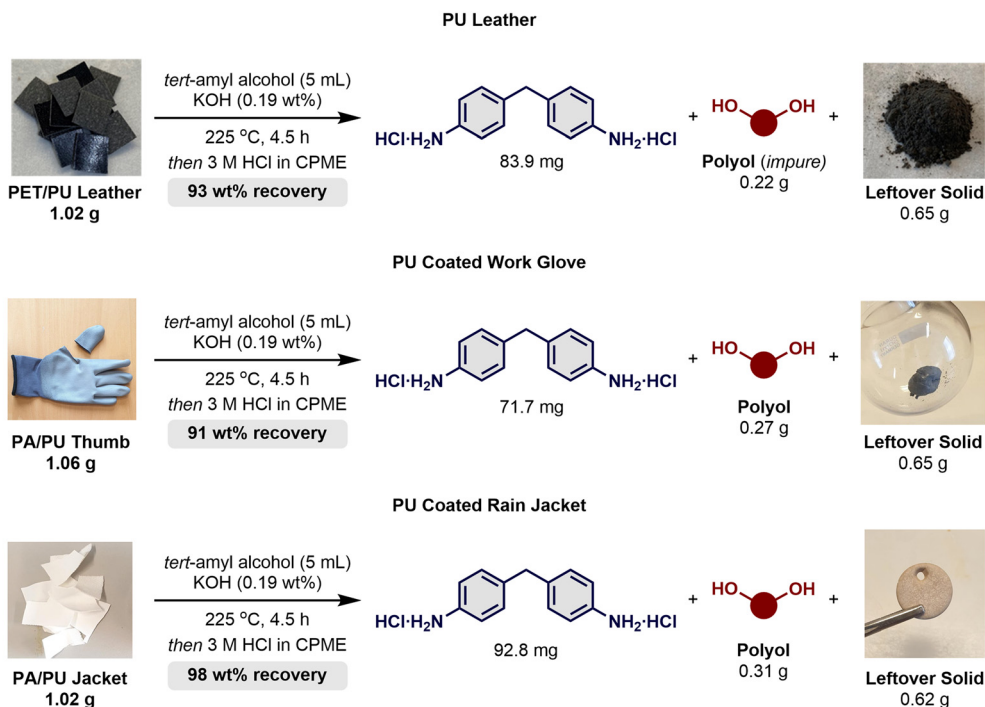

Scheme 4 Solvolysis of elastane from mixed fabrics and PU coated fabrics. (a) Solvolysis of elastane from mixed fabrics. Reactions were performed in 45 mL autoclaves fitted with a 30 mL PTFE inlay at 800 rpm under air. Reported yields from elastane deconstruction are isolated yields from column chromatography as an average of two parallel reactions. (b) Solvolysis of elastane from PU coated fabrics. Reported yields from elastane deconstruction are isolated yields after separation by the addition of HCl (3M, CPME) and given as an average of two parallel reactions.

totalling a combined mass recovery of 98%. These results suggest that the tested method is applicable to PU leathers and PU coated fabrics, although the presence of polyester complicates purification. For nylon-based materials however, sep-

aration was straightforward and depending on the quality, the nylon may be respun to new fibres. To the best of our knowledge, no dissolution technique has been developed for any of these types of materials with the aim of recycling.

Conclusion

In summary, we have reported an approach for the selective depolymerisation of elastane and PU-coating in certain blended fabrics. Solvolysis with *tert*-amyl alcohol directly on the elastane-containing or PU-coated textile proved successful for polyamide textiles, while the chemical technology showed potential for other polymers such as cotton and viscose, but further optimization is needed to increase the selectivity of the disassembly process. Additionally, this solvolysis process represents an efficient option for the two-step process involving dissolution for fibre separation followed by chemical depolymerisation of elastane and can find use in the case where the quality of the elastane isolated from dissolution is low. As such, this work opens up the possibility of applying solvolysis for the removal and depolymerisation of elastane from fabrics for potential repolymerisation and use in new elastane fibres. Both material streams open up for the possibility of fibre-to-fibre recycling which in conjunction with other innovative methods might lower the degree of dependency on fossil fuels as a starting point for new fabric production as waste fractions can re-enter the value streams. Nonetheless, more data are needed to assess if the solvolysis process using *tert*-amyl alcohol and a catalytic amount of KOH is viable on scale, in particular with respect to energy consumption.

Author contributions

M. B. J., B. S. D., S. K. K., and T. S. came up with the original idea. M. B. J., B. S. D., S. K. K., and T. S. conceptualised the strategy. M. B. J., B. S. D. and S. K. K. designed the experiments. M. B. J., B. S. D., and M. L. H. performed the experiments. M. B. J., B. S. D., M. L. H., S. K. K., and T. S. wrote the manuscript.

Data availability

See the ESI[†] for further details.

Conflicts of interest

The authors declare the following competing financial interest (s): Aarhus University is a co-owner of a patent (WO2023194469) covering the *tert*-amyl alcohol process for deconstruction of polyurethane related to the findings described in this manuscript.

Acknowledgements

We deeply appreciate the financial support from the Innovation Fund Denmark (Grant No. 9069-00017B and 0177-00035B), the Carlsberg foundation (Grant No. CF18-1101), the Danish National Research Foundation (Grant No. DNRF118), the Novo

Nordisk Foundation CO₂ Research Center and Aarhus University. Furthermore, we are grateful to the RePURpose consortium for discussions and valuable input. Pernille Mørup and Lise Ladegaard Lind from Beirholm are acknowledged for providing both the elastane and the PET fibres.

References

- 1 A. Scott, *C&EN*, 2022, **100**, 22–28.
- 2 Ellen MacArthur Foundation A New Textile Economy: Redesigning Fashion's Future. <https://ellenmacarthurfoundation.org/a-new-textiles-economy> (Accessed 09.08.2023).
- 3 K. Niinimäki, G. Peters, H. Dahlbo, P. Perry, T. Rissanen and A. Gwilt, *Nat. Rev. Earth Environ.*, 2020, **1**, 189–200.
- 4 C. Jönsson, R. Wei, A. Biundo, J. Landberg, L. S. Bour, F. Pezzotti, A. Toca, L. M. Jacques, U. T. Bornscheuer and P.-O. Syrén, *ChemSusChem*, 2021, **14**, 4028–4040.
- 5 P. Harmsen and H. Bos, *Textiles For Circular Fashion: Part 1: Fibre Resources and Recycling Options*, 2020.
- 6 P. Harmsen, M. Scheffer and H. Bos, *Sustainability*, 2021, **13**, 9714–9731.
- 7 E. Barnard, J. J. R. Arias and W. Thielemans, *Green Chem.*, 2021, **23**, 3765–3789.
- 8 H. Li, H. A. Aguirre-Villegas, R. D. Allen, X. Bai, C. H. Benson, G. T. Beckham, S. L. Bradshaw, J. L. Brown, R. C. Brown, V. S. Cecon, J. B. Curley, G. W. Curtzwiler, S. Dong, S. Gaddameedi, J. E. García, I. Hermans, M. S. Kim, J. Ma, L. O. Mark, M. Mavrikakis, O. O. Olafasakin, T. A. Osswald, K. G. Papanikolaou, H. Radhakrishnan, M. A. Sanchez Castillo, K. L. Sánchez-Rivera, K. N. Tumu, R. C. Van Lehn, K. L. Vorst, M. M. Wright, J. Wu, V. M. Zavala, P. Zhou and G. W. Huber, *Green Chem.*, 2022, **24**, 8899–9002.
- 9 J.-P. Lange, *ACS Sustainable Chem. Eng.*, 2021, **9**, 15722–15738.
- 10 European Commission: EU Strategy for Sustainable and Circular Textiles, 2022, https://environment.ec.europa.eu/document/download/74126c90-5cbf-46d0-ab6b-60878644b395_en?filename=COM_2022_141_1_EN_ACT_part1_v8.pdf (Accessed 09.08.2023).
- 11 European Commission: Study on The Technical, Regulatory, Economic and Environmental Effectiveness of Textile Fibres Recycling, 2021, <https://www.ecologic.eu/sites/default/files/publication/2022/50030-study-textile-recycling-web.pdf> (Accessed 09.08.2023).
- 12 M. Reisch, *Chemical & Engineering News*, 1999, 77(7), 70.
- 13 Fast Growth Looms for Spandex Fibers, *Chemical & Engineering News*, 1962, **40**, 34–37.
- 14 M. F. Sonnenschein and W. Koonce, Polyurethanes, in *Encyclopedia of Polymer Science and Technology*, John Wiley & Sons, Inc., 2011.
- 15 M. F. Sonnenschein, Polyurethane Elastomers: Manufacture, Applications, Markets, and Trends, in *Polyurethanes: Science, Technology, Markets, and Trends*, John Wiley & Sons, Inc., Hoboken, New Jersey, 2014, 294–335.

- 16 K.-H. Wolf, M. Kausch, H. Schröer and M. Schweizer, Fibers, 6. Polyurethane Fibers, in *Ullmann's Encyclopedia of Industrial Chemistry*, Wiley-VCH Verlag GmbH & Co. KGaA, 2011.
- 17 J. E. Boliek and S. A. Denney, Fibers, Elastomeric, in *Encyclopedia of Polymer Science and Technology*, John Wiley & Sons, Inc., 2002.
- 18 A. Kemona and M. Piotrowska, *Polymers*, 2020, **12**, 1752.
- 19 N. V. Gama, A. Ferreira and A. Barros-Timmons, *Materials*, 2018, **11**, 1841.
- 20 D. Simón, A. M. Borreguero, A. de Lucas and J. F. Rodríguez, *Waste Manage.*, 2018, **76**, 147–171.
- 21 J. Datta and P. Koczyńska, *Crit. Rev. Environ. Sci. Technol.*, 2016, **46**, 905–946.
- 22 B. Liu, Z. Westman, K. Richardson, D. Lim, A. L. Stottlemeyer, T. Farmer, P. Gillis, V. Vlcek, P. Christopher and M. M. Abu-Omar, *ACS Sustainable Chem. Eng.*, 2023, **11**, 6114–6128.
- 23 L. P. Fonseca, A. Duval, E. Luna, M. Ximenis, S. D. Meester, L. Avérous and H. Sardon, *Curr. Opin. Green Sustainable Chem.*, 2023, **41**, 100802.
- 24 K. Ragaert, L. Delva and K. Van Geem, *Waste Manage.*, 2017, **69**, 24–58.
- 25 S. C. Kosloski-Oh, Z. A. Wood, Y. Manjarrez, J. P. de los Rios and M. E. Fieser, *Mater. Horiz.*, 2021, **8**, 1084–1129.
- 26 L. R. Mahoney, S. A. Weiner and F. C. Ferris, *Environ. Sci. Technol.*, 1974, **8**, 135–139.
- 27 S. Motokucho, A. Yamaguchi, Y. Nakayama, H. Morikawa and H. Nakatani, *J. Polym. Sci., Part A: Polym. Chem.*, 2017, **55**, 2004–2010.
- 28 N. Gama, B. Godinho, G. Marques, R. Silva, A. Barros-Timmons and A. Ferreira, *Chem. Eng. J.*, 2020, **395**, 125102.
- 29 N. Gama, B. Godinho, G. Marques, R. Silva, A. Barros-Timmons and A. Ferreira, *Polymer*, 2021, **219**, 123561.
- 30 B. Godinho, N. Gama, A. Barros-Timmons and A. Ferreira, *Sustainable Mater. Technol.*, 2021, **29**, e00330.
- 31 M. Grdadolnik, A. Drincic, A. Oreski, O. C. Onder, P. Utrosa, D. Pahovnik and E. Zagar, *ACS Sustainable Chem. Eng.*, 2022, **10**, 1323–1332.
- 32 T. Vanbergen, I. Verlent, J. De Geeter, B. Haeltermann, L. Claes and D. de Vos, *ChemSusChem*, 2020, **13**, 3835–3843.
- 33 P. Zahedifar, L. Pazdur, C. M. L. Vande Velde and P. Billen, *Sustainability*, 2021, **13**, 3583.
- 34 R. Heiran, A. Ghaderian, A. Reghunadhan, F. Sedaghati, S. Thomas and A. H. Haghighi, *J. Polym. Res.*, 2021, **28**, 22.
- 35 S. Zhang, W. Xu, R. Du, W. An, X. Liu, S. Xu and Y.-Z. Wang, *J. Chem. Eng.*, 2023, 144032, DOI: [10.1016/j.ccej.2023.144032](https://doi.org/10.1016/j.ccej.2023.144032).
- 36 S. Zhang, W. Xu, R. Du, X. Zhou, X. Liu, S. Xu and Y.-Z. Wang, *Green Chem.*, 2022, **24**, 3284–3292.
- 37 W.-H. Xu, L. Chen, S. Zhang, R.-C. Du, X. Liu, S. Xu and Y.-Z. Wang, *Green Chem.*, 2023, **25**, 245–255.
- 38 Y.-B. Zhao, X.-D. Lv and H.-G. Ni, *Chemosphere*, 2018, **209**, 707–720.
- 39 A. Mäurer, M. Schlummer and O. Beck, US8138232B2, 2012.
- 40 A. Mäurer and M. Schlummer, EP2513212B1, 2021.
- 41 J. E. G. Van Dam, J. R. I. Knoop and M. J. A. Van den Oever, WO2020130825A1, 2020.
- 42 C. Gong, K. Zhang, C. Yang, J. Chen, S. Zhang and C. Yi, *Text. Res. J.*, 2021, **91**, 18–27.
- 43 Y. Yin, D. Yao, C. Wang and Y. Wang, *Text. Res. J.*, 2014, **84**, 16–27.
- 44 M. B. Johansen, B. S. Donslund, S. K. Kristensen, A. T. Lindhardt and T. Skrydstrup, *ACS Sustainable Chem. Eng.*, 2022, **10**, 11191–11202.
- 45 M. B. Johansen, B. S. Donslund, E. Larsen, M. B. Olsen, J. A. L. Pedersen, M. Boye, J. K. C. Smedsgård, R. Heck, S. K. Kristensen and T. Skrydstrup, *ACS Sustainable Chem. Eng.*, 2023, **11**, 10737–10745.
- 46 R. S. Hanzel and P. J. Sauer, US4296174A, 1981.
- 47 P. Roose, K. Eller, E. Henkes, R. Roszbacher and H. Höke, Amines, Aliphatic, in *Ullmann's Encyclopedia of Industrial Chemistry*, Wiley-VCH Verlag GmbH & Co. KGaA, 2015.
- 48 P. Roose and M. G. Turcotte, Amines, Lower Aliphatic, in *Kirk-Othmer Encyclopedia of Chemical Technology*, John Wiley & Sons, Inc., 2016.