

REVIEW

[View Article Online](#)
[View Journal](#) | [View Issue](#)Cite this: *RSC Adv.*, 2017, 7, 47196Received 29th August 2017
Accepted 27th September 2017

DOI: 10.1039/c7ra09600c

rsc.li/rsc-advances

In-liquid plasma: a novel tool in the fabrication of nanomaterials and in the treatment of wastewaters

S. Horikoshi ^{*ab} and N. Serpone ^c

Attempts to generate plasma in liquids have been successful and various devices have been proposed. Many reports have described the optimal conditions needed to generate plasma, and mechanisms have been inferred, together with the composition of the plasma. Elucidation of a stable method (and mechanism) to generate plasma in liquids has led to various active investigations into applications of this new energy source. This review article describes the generator and the generation mechanism of in-liquid plasma, and pays attention to the evolving technology. The characteristics of submerged plasma are summarized and examples of nanomaterials syntheses and wastewater treatment are given, both of which have attracted significant attention. Extreme reaction fields can be produced conveniently using electrical power even without the use of chemical substances and high-temperature high-pressure vessels. Chemical reactions can be carried out and environmental remediation processes achieved with high efficiency and operability with the use of in-liquid plasma. Suggestions for introducing in-liquid plasma to chemical processes are discussed.

^aDepartment of Materials and Life Sciences, Faculty of Science and Technology, Sophia University, 7-1 Kioicho, Chiyodaku, Tokyo 102-8554, Japan. E-mail: horikosi@sophia.ac.jp

^bMicrowave Science Research Center (MSRC), Sophia University, 7-1 Kioicho, Chiyodaku, Tokyo 102-8554, Japan

^cPhotoGreen Laboratory, Dipartimento di Chimica, Università di Pavia, Via Taramelli 12, Pavia 27100, Italy. E-mail: nick.serpone@unipv.it

1. Introduction

1.1 In-liquid plasma: a novel energy source for chemical reactions

Many chemists think it is strange that as much as or more than 99% of the substances present in the Universe exist as plasma, whereas the typical gas, solid and liquid states of matter tend to be rather rare in that environment. Compared to the vast scale of the Universe, chemists manufacture products in these states



Satoshi Horikoshi (PhD 1999 Meisei University, Tokyo): Associate Professor at Sophia University since 2011 and currently Director of the Japan Society of Electromagnetic Wave Energy Applications (JEMEA); he is on Editorial Advisory Boards of the Journal of Microwave Power and Electromagnetic Energy and three international journals. Research interests involve new functional materials,

nanomaterials synthesis, molecular biology, formation of sustainable energy, and environmental protection using microwave- and/or photo-energy, and co-author of over 180 scientific publications and contributor to and editor/co-editor of 23 books. He is a microwave specialist who often introduces effective methods of using microwave ovens at home on television.



Nick Serpone (PhD, Cornell University, 1968) is a Visiting Professor at the University of Pavia, Italy, a Fellow of the European Academy of Sciences in the Division of Material Sciences, and is currently Head of the Materials Sciences Division of the Academy and Member of the Academy's General Board. His current research interests focus on the photophysics and photochem-

istry of metal-oxide semiconductors, heterogeneous photocatalysis, photochemistry of sunscreens. He has co-authored over 450 articles and co-edited several monographs. His work has been cited over 34 000 times (h-index factor = 93).



Recent years have also witnessed the successful generation of stable plasma in solution (referred to as in-liquid plasma); its application in various fields is currently being investigated. Use of in-liquid plasma has attracted significant attention as being a hot research topic. The state of new substances generated in liquids is expected to be a new tool in solution chemistry fostered by a combination of innovative ideas and the promise of novel materials synthesis. For instance, in-liquid plasma could be applied to fuel (hydrogen) recovery from a methane hydrate layer existing in Japanese waters; the method used is detailed in Fig. 1.² It involves irradiating a methane hydrate layer with in-liquid plasma to achieve dehydrogenation reaction

1.2 Plasma

Michael Faraday (1791–1867), discoverer of electromagnetism in 1821, was the first to provide an explanation for Lichtenberg's observations. His countryman, Sir William Crookes (1832–1919), later discovered the fourth state of matter as radiating matter in discharge tubes,⁴ which he correctly assumed to consist of electrically charged gas molecules in the tubes: *de facto*, plasma was born. He later defined it in his lecture titled "On Radiant Matter" delivered before the British Association for the Advancement of Science, on 22 August 1879 at Sheffield (D. Appleton, The Popular Science Monthly, 1880, Volume 16, pp 157–167). Crookes discovery was followed nearly two decades later (1897) by Sir Joseph John Thomson's (1856–1940) postulation that atoms consist of positively charged electrons that possess a mass.⁵ This was also confirmed by the German chemist Eugen Goldstein, who discovered that the so-called canal rays consisted of positively charged particles with missing electrons (H^+ ions from hydrogen gas). Thus, plasma had been identified as a mixture of electrons and ions. The term plasma was finally defined by the American chemist Irving Langmuir (1881–1957) who in 1923 observed specific oscillations in an ionized gas that he referred to as plasma oscillations generated from an inhomogeneous charge distribution and to the natural tendency of the charge to redistribute uniformly inside the plasma.⁶ The first comprehensive published report on gas discharges was by the German physicist Johannes Stark (Die Elektrizität in Gasen), then Director of the Institute of Physics of the University of Greifswald. Stark was awarded the 1919 Nobel Prize for the discovery of the Doppler Effect in canal rays and for the splitting of the spectral lines in electric fields (the Stark Effect). At the end of 1918, Stark invited Rudolf Seeliger to the University of Greifswald who remained until 1955. Seeliger is one of the pioneers of modern plasma and gas-discharge physics. The fundamental physical properties of plasma were clarified in the first half of the 20th century by Seeliger and others, which led to rapid advances in the engineering applications of plasmas,⁷ as exemplified by the inventions of the mercury discharge lamp (Cooper Hewitt light: 1902), the mercury arc lamp (1905), and the high-pressure mercury lamp (1906) among others.

Coupling theory and technological innovations in plasma applications also advanced noticeably. In the second half of the 20th century, plasmas were used increasingly for a variety of

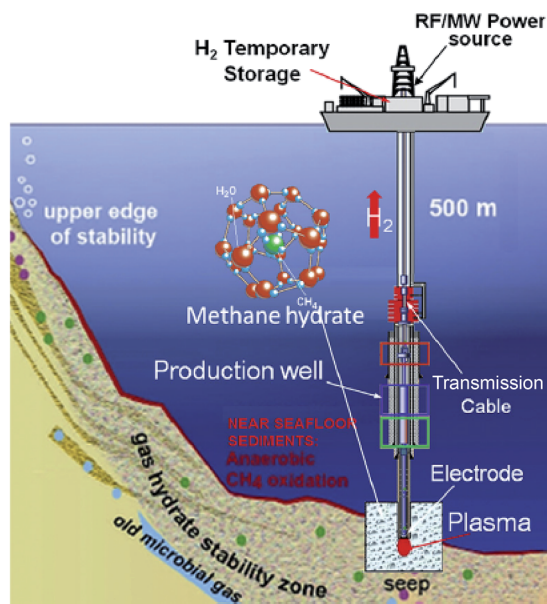


Fig. 1 Process for hydrogen production from hydrate fields in subsea sites using the plasma from the in-liquid method. Reproduced from Rahim and coworkers.² Copyright 2015 by Elsevier.

purposes, such as in neon tubes (vacuum) and in etching processes (hot). Technological progress in the mid-1990s also led plasmas to be generated non-thermally under atmospheric pressure, which opened loads of new possibilities since expensive and complex vacuum systems were no longer needed; processes could now be run continuously without putting stress on materials being treated. As a result, plasma-induced processes could then be applied in, for instance, the medical sector for the gentle sterilization of medical equipment and catheters. In 1996, Laroussi⁸ was one of the first to describe a novel sterilization method that used uniform glow discharge plasma generated at atmospheric pressure. He examined the inactivation of *Pseudomonas fluorescens* bacteria in yeast extract in a polypeptone glucose solution.

Starting with a handful of publications in the mid-1990s, the number of publications that dealt with applications of plasmas increased rapidly at the turn of the 21st century. Indeed, the total number of publications dealing with cold plasma has increased significantly in the past 20 years, attesting to the importance of this emerging technology. As we speak, various engineering application advances are being made. This indispensable technology has developed and currently used extensively in metal welding, in surface treatments, in the processing of materials and electronic components, in the fabrication of nanomaterials, and in wastewater treatment (among others).⁶

Plasma is classified as (i) high-temperature plasma (thermal equilibrium plasma), and (ii) as low-temperature plasma (non-thermal equilibrium plasma). Thermal equilibrium plasma is plasma generated by applying electrical power for a long time under conditions that the gas pressure is 5 kPa or more, and that the electron and gas temperatures are nearly equal. Since the ionization energy of atoms and molecules necessitates several eV or more (tens of thousands of degrees Celsius), some of the electrons and ions become high-energy particles. In general, the materials temperature in thermal equilibrium plasma reaches as much as several thousand degrees Celsius or more; this plasma is casually used as a heat source and light source for welding and lamps. By comparison, the electron temperature is higher than the gas temperature in non-thermal equilibrium plasma. For example, to convert a gas molecule into non-thermal equilibrium plasma, heat transfer to ions and molecules can be restricted by setting gas molecules to a reduced pressure state and by lowering the frequency of collision of electrons with ions or molecules. A characteristic of non-thermal equilibrium plasma is that its gas temperature is low and electrons are in a high-energy state, and as such it is used in the manufacturing of semiconductors and films through chemical reactions. Since non-thermal equilibrium plasma must maintain reduced pressure conditions, facilities such as a vacuum chamber and a vacuum evacuation device are required, even if plasma were generated by a short pulse discharge under atmospheric pressure conditions. This is often referred to as atmospheric pressure non-thermal equilibrium plasma because it has different properties from the plasma in vacuum.

2. In-liquid plasma


2.1 Why plasma can be generated in a liquid (and in a solid)

Since plasma is a state of matter generated by a destabilizing gas, one must ask whether plasma can also form in solids and liquids. Some people are still sceptical about this.

2.1.1 Solid plasma. Regardless of such scepticism, an electron in a metal (solid) contains free electrons that can move around a lattice point; collectively, these are oscillating electrons. When an external electric field is applied to a free electron, it acts as if it were an electron in gas plasma. Although the plasma defined by Langmuir is referred to as gas plasma,⁹ when applied to a solid it can be regarded as a solid plasma even for a solid (metals, semiconductors) that possesses free electrons.¹⁰ The collective oscillation of these free charges (mainly electrons) is known as plasma oscillation; quantizing this oscillation leads to formation of a Plasmon. When metallic nanoparticles are irradiated with specific light, a resonant luminescence appears caused by Plasmon absorption; applications of such nanoparticles in paints, in medical treatment, in measurements, and in microfabrication have been reported.¹¹

2.1.2 In-liquid plasma. For years, some techniques have made use of in-liquid plasma to perform electrical discharge machining, welding, and carburizing (and others) in liquids. Yet, only but a few research studies have taken the trouble to explore and exploit in-liquid plasma, so that its use has been rather limited. The report published by Clements in 1987 (ref. 12) on plasma generation by a high-voltage pulse discharge in water (material changed to a plasma state) was a leading research study of the 1980s. Since then, various studies of the physical elucidation of in-liquid plasma have been carried out from many research quarters, which reported that plasma generated in the liquid phase is a phenomenon greatly different from plasma in the gas phase and suggested the use of in-liquid plasma to wastewater treatment as one of several possible applications. Following these reports, researchers worldwide have optimized in-liquid plasmas with regard to such factors as pressure, temperature, density, viscosity, composition, and conductivity¹³ that have led to an accelerated development of in-liquid plasma generators. In addition to gas-phase plasma used in academia, the bases of plasma in the solid phase and in the liquid phase are now also academically established; systematization of plasma in each state of matter is progressing (Fig. 2). Research into practical applications is also on the increase.

There are two key methods of generating in-liquid plasma. The first key method is an underwater streamer discharge that produces linear plasma in the liquid; the dielectric breakdown of the liquid turns into a type of corona discharge considering the classification of general plasma. During the dielectric breakdown of water, micro-bubbles are formed near the electrode by cavitation produced either by a high electric field or by heating from a conductive current; the plasma is generated in the micro-bubble.¹² To generate an underwater streamer discharge, even in an aqueous solution, an electrical power of 50 to 400 kV and a current of 100 A or more are required. Industrially, it is difficult to achieve and maintain a steady-state



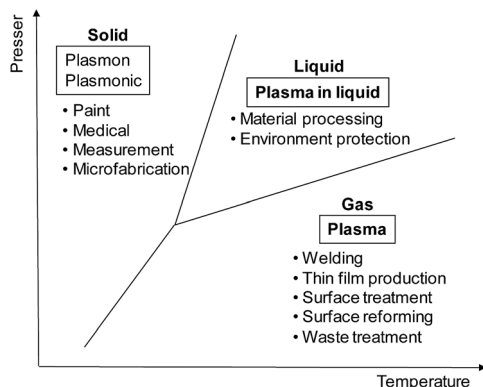


Fig. 2 Relationship between plasma and the three states of matter.

electrical power of this magnitude from the viewpoint of stability and energy saving. Accordingly, many discharges are generated using a pulsed voltage of 1 μs duration or less. An underwater streamer discharge occurs in liquid at a rate of 30 to 100 $\text{mm } \mu\text{s}^{-1}$ while the liquid is being vaporized at the liquid/air interface.^{14,15} The occurrence of an underwater streamer discharge in the liquid phase generates ultraviolet rays, shock waves, and localized heat, together with chemically active species formed by the resulting plasma.¹⁶ The second key method is to generate bubbles by heating, by shock waves, and by gas introduction (or the like) in the liquid to create in-liquid plasma. Since applying electrical power is not always accompanied by a dielectric breakdown of the liquid, in many cases plasma can still be generated with a power of 10 kW or less as a glow discharge, a corona discharge (streamer discharge), and as an arc discharge.

Except for underwater streamer discharge, this review article will restrict its considerations to all in-liquid plasmas as plasma generated in bubbles contained within the liquid.

2.1.3 Chemical composition of plasma generated in a liquid. When plasma is generated in a liquid by ionizing ion-exchanged water, a pale white light is observed (Fig. 3a);¹⁷ the emission spectrum displayed in Fig. 3b is attributed to H_α (at $\lambda = 656 \text{ nm}$) and to H_β (at 486 nm), and to $\cdot\text{OH}$ radicals (at 316 nm). Therefore, the source of plasma is not due to dissolved air in water, but rather to vaporized water that has turned into plasma. Peaks derived from dissolved nitrogen and oxygen gases at $\lambda = 289 \text{ nm}$ (N_β) and $\lambda = 778 \text{ nm}$ (O^*) have also been detected as sharp luminescence.¹⁸

2.2 Methods to generate in-liquid plasma

Fig. 4a shows near surface interactions with plasmas generated outside the liquid.¹⁹ From the cocktail of plasma, such species as radicals, ions, electrons and photons are thought to interact, to differing degrees, with the liquid interface, thereby initiating reactions that cascade well into the liquid phase, possibly *via* biochemical pathways (Fig. 4a). Radicals, ions and photons are often considered, but in attempts to isolate important sources of reactions within liquids, it is also necessary to consider electron interactions directly with the liquid phase (Fig. 4b and

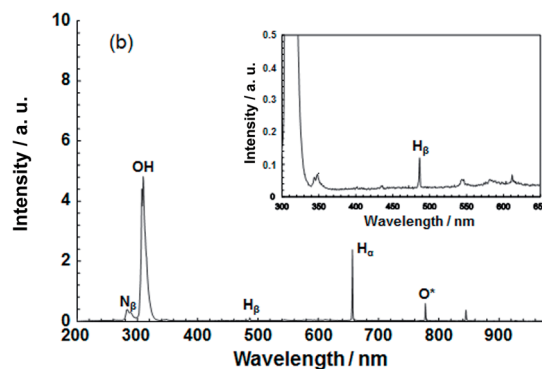
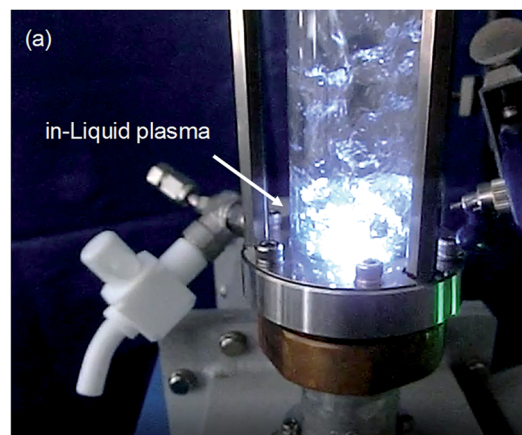


Fig. 3 (a) Photograph illustrating the generation of plasma in liquid using a microwave power supply; (b) spectrum of ultraviolet and visible light emitted by in-liquid plasma generated in ion-exchanged water. Taken from ref. 17. Copyright 2017 by S. Horikoshi.

c); to date, these have received little attention. Accordingly, the focus of this paper will be restricted to phenomena occurring under plasma conditions as illustrated in Fig. 4b and c.

Currently, methods to generate in-liquid plasma can be broadly divided into four categories, and since each possesses


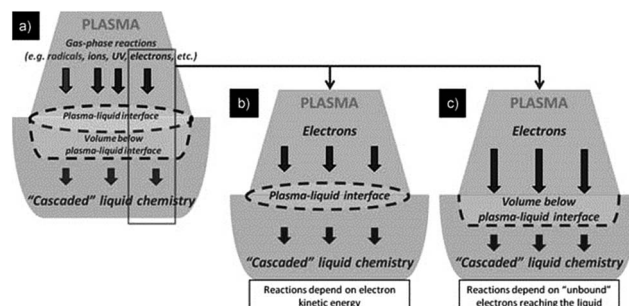


Fig. 4 Schematic diagram of three different types of plasma-in-liquid conditions (PiLC): (a) gas-phase species and plasma-radiation-induced liquid reactions at the plasma-liquid interface; (b and c) electrons from the plasma can initiate non-equilibrium reactions in the liquid phase where both electron energy distribution (b) and electron density play an important and distinct role (c). Reproduced from Mariotti *et al.*¹⁹ Copyright 2012 by WILEY-VCH.



its own characteristics, it is necessary to select the appropriate plasma according to purpose and end-use. Considering electrode configurations and energy sources, generated in-liquid plasma can be subdivided as:

- (1) Plasma A: direct discharge between two electrodes using an AC (plus) power supply.
- (2) Plasma B: contact discharge between an electrode and the surface of the surrounding electrolyte using a DC power supply.
- (3) Plasma C: plasma generated with either radio frequency (RF) or microwave (MW) irradiation.
- (4) Plasma D: plasma generated using the laser ablation technique.

The schematic of generating Plasma A involves a direct discharge between two electrodes that comes in such forms as solution plasma, discharge plasma in liquid, electric spark discharge, arc discharge, capillary discharge, and streamer discharge (Fig. 5a). Two electrodes of similar size and shape are immersed in the liquid at a short distance. Because of the direct discharge, most liquids containing conductive electrolytes in such media as deionized water, ethanol, and liquid nitrogen can be used. Thus, in-liquid plasma is generated between the two electrodes immersed in the electrolyte solution after passing an electric current through the solution. It is important that the liquid used in this method be conductive.

The schematic of Plasma B is displayed in Fig. 5b. In 1963, Hickling and Ingram reported contact glow discharge electrolysis (CGDE),²⁰ whereby a high-temperature plasma sheath formed between an electrode and the surface of the surrounding electrolyte as a result of a high electric field; this was subsequently accompanied by a glow discharge photo-emission. Consider now two electrodes immersed in a conductive electrolyte in which the distance between them is varied from 5 mm to over 100 mm, and the electrode surface area between the anode and cathode is different; one of the electrodes has a smaller surface area than the other. The electrode

with the smaller surface area is covered with a thin film of water vapor within which a discharge occurs. In a submerged plasma two-electrode generator that uses a direct current power supply, passing the electric current through the electrolyte liquid produces foam owing to Joule heating; the in-liquid plasma is generated at the cathode side. In such a system, as the conductivity of the liquid changes, the conditions under which the in-liquid plasma is generated also change, so that it is necessary to keep the conductivity at an appropriate level. In most cases, the cathode consists of a metal plate with a large surface area (*e.g.*, a Pt mesh), while the anode is a metal wire. A stable DC power supply is often used, although pulsed DC has also been used.

Techniques for generating in-liquid plasma by irradiating an antenna electrode with radio frequency or microwaves for Plasma C have been utilized in a variety of fields (Fig. 5c). These techniques are effective in generating in-liquid plasma at a lower electrical power. In the plasma generating apparatus, the dielectric constant and the dielectric loss of the liquid are important factors in the generation process. Unlike other techniques, however, it is not necessary to use an electrolyte solution. Radio frequency or microwave generated in-liquid plasma can be maintained in water over a wide range of water conductivity (from 0.2 to 7000 mS m⁻¹). When plasma is generated in a solution using radio frequency or microwaves, a lower pressure is often applied because energy is absorbed by water as it possesses a dielectric constant and dielectric loss. An advantage here is that plasma can be generated even in pure water, and so various application developments can be expected.

Another method for generating plasma in a liquid uses the laser ablation technique (Plasma D; Fig. 5d). The laser irradiates a solid substrate immersed in the liquid causing a plasma ball to be generated on the surface of the solid. This technology is applied in such research as nanoparticle production²¹ and deep-sea mass spectrometry.²²

The various techniques for generating Plasma A–C proposed according to usage conditions, reaction conditions, and operating equipment (among others) have been classified in some detail by Saito and Akiyama²³ who explained the classification based on the corresponding engineering diagram for the Plasma A–C summarized in Fig. 6,^{23–84} 7,^{85–128} and 8.^{129–154}

2.3 Problems and countermeasures in plasma generation

To generate plasma continuously in a liquid necessitates application of a large electrical power as compared to the case of generating plasma in vacuum or under atmospheric pressure, so that the thermal load on the electrode is large. Consequently, studies on electrodes used in plasma generation have been carried out for many years. In-liquid plasmas have been generated using electrodes made with such materials as tungsten, aluminum, copper, molybdenum, stainless steel (SUS 304), and carbon. Plasma generation with electrodes made of carbon, molybdenum, and SUS 304 lasted no more than 5 min.¹⁵⁵ Moreover, continuous (for 10 min) in-liquid plasma generation with aluminum and copper electrodes caused

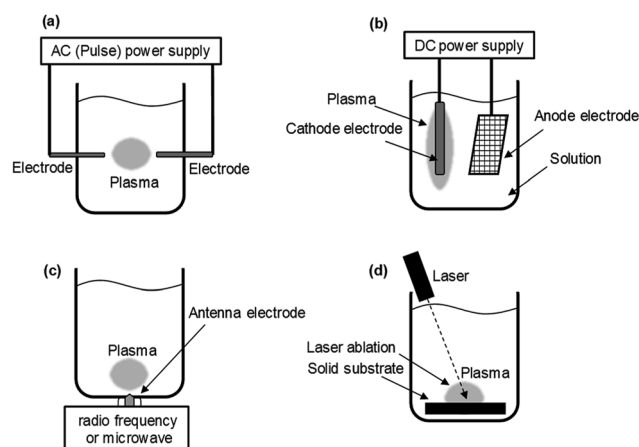


Fig. 5 Images of plasma generation method in a liquid: (a) direct discharge between two electrodes using an AC (plus) power supply; (b) contact discharge between an electrode and the surface of the surrounding electrolyte using a DC power supply; (c) plasma generation with radio frequency (RF) or microwave (MW) irradiation; (d) plasma generation using the laser ablation method.



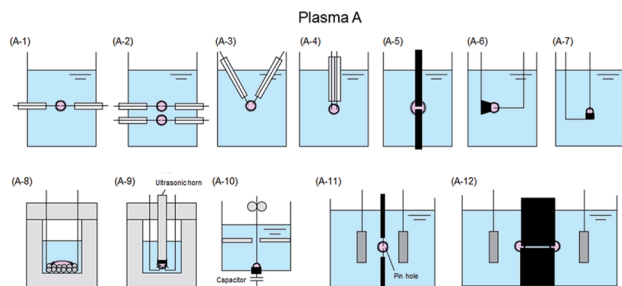


Fig. 6 Typical electrode configuration for Plasma A: (A-1) influence of glow discharge plasma and dielectric barrier discharge;^{24–30} (A-2) dielectric barrier discharge in quartz tube;³¹ (A-3) gliding arc discharge;³² (A-4) gas-liquid interfacial plasma, plasma electrochemistry in ionic liquids, and so forth;^{33–45} (A-5) glow discharge formation over water surface;⁴⁶ (A-6) discharge electrolysis;^{47–64} (A-7) microplasma;^{19,65–75} (A-8) dual plasma electrolysis;⁷⁶ (A-9) plasma in contact with liquids;^{77,78} (A-10) microplasma discharge;⁷⁹ (A-11) glow discharge generated in contact with a flowing liquid cathode;^{80–84} (A-12) AC capillary discharge. Modified with permission from ref. 23. Copyright 2015 by Hindawi.

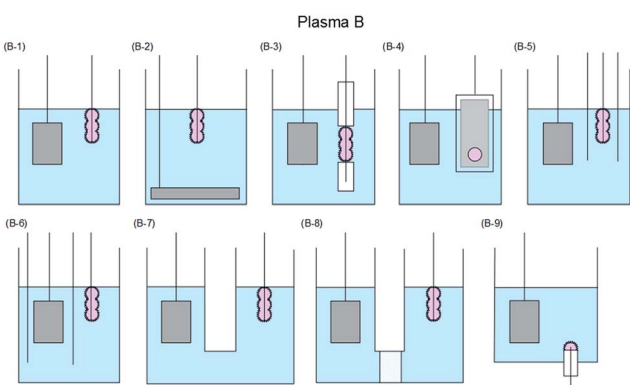


Fig. 7 Typical electrode configuration for Plasma B: (B-1) contact glow discharge;^{85–108} (B-2) electrical discharges;^{109–111} streamer discharge plasma in water;¹¹² (B-3) solution plasma;^{91,93,99,113} electric discharge plasma;¹¹⁴ (B-4) contact glow discharge;^{113,115,116} (B-5) contact glow discharge;¹¹⁷ (B-6) contact glow discharge electrolysis;^{118–120} (B-7) high-voltage cathodic polarization;¹²¹ (B-8) contact glow discharge electrolysis;^{118,122–125} and (B-9) electrical discharge.^{126–128} Modified with permission from ref. 23. Copyright 2015 by Hindawi.

deterioration of the electrode surface. On the other hand, for electrode material with high melting points (*e.g.*, tungsten, mp = 3422 °C), the electrode could, in principle, withstand long-term use (Fig. 9). Nonetheless, deterioration of the electrode surface can still occur depending on the generation conditions of the in-liquid plasma. Therefore, studies on the mechanism of in-liquid plasma heating of the electrodes and improvement measures are ongoing.

Many of the currently reported in-liquid plasmas produce bubbles within which plasma is generated in the liquid. However, if the bubble generating device were to be connected separately, the physical structure of the plasma generating portion would get rather complicated. To resolve this problem, an ultrasonic wave irradiation device is installed in the vicinity

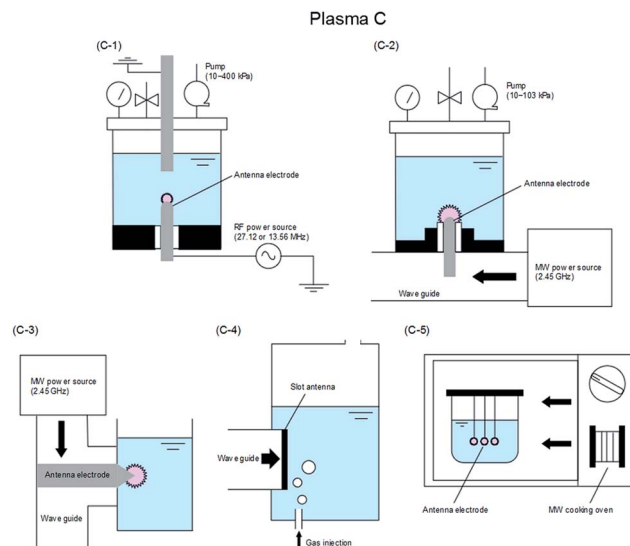


Fig. 8 Typical electrode configuration for Plasma C: (C-1) RF applied in-liquid plasma system under vacuum condition;^{129–140} (C-2) MW applied in-liquid plasma system under vacuum condition;^{134,141–149} (C-3) MW-induced in-liquid plasma system under atmosphere condition;^{150,151} (C-4) slot-excited MW discharge in-liquid plasma system under atmosphere condition;¹⁵² and (C-5) in-liquid plasma generation system with a MW oven.^{153,154} Modified with permission from ref. 23. Copyright 2015 by Hindawi.

of the plasma generating electrode. Even with this method, however, it is not possible to improve the apparatus complexity in the vicinity where plasma is generated. Accordingly, an apparatus has been developed in which the electrode and the ultrasonic homogenizer horn are integrated.

For instance, by sharing the microwave antenna electrode with the ultrasonic homogenizer as an in-liquid plasma apparatus driven by a single microwave power supply, both microwaves and ultrasonic waves can be used to irradiate simultaneously, thereby simplifying the apparatus (Fig. 10).¹⁵⁶ Since the ultrasonic homogenizer can generate fine bubbles in the liquid, they can be produced in the very vicinity where

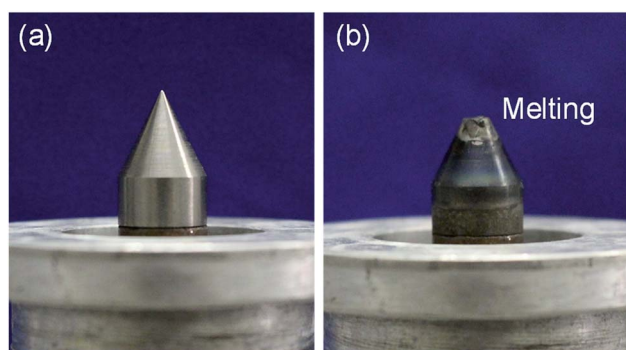


Fig. 9 (a) Photograph of a tungsten pencil-type electrode of an in-liquid plasma generator of the microwave type in an unused state; (b) photograph of a tungsten pencil-type electrode after several minutes of generating in-liquid plasma with continuous microwaves. Taken from ref. 17. Copyright 2017 by S. Horikoshi.



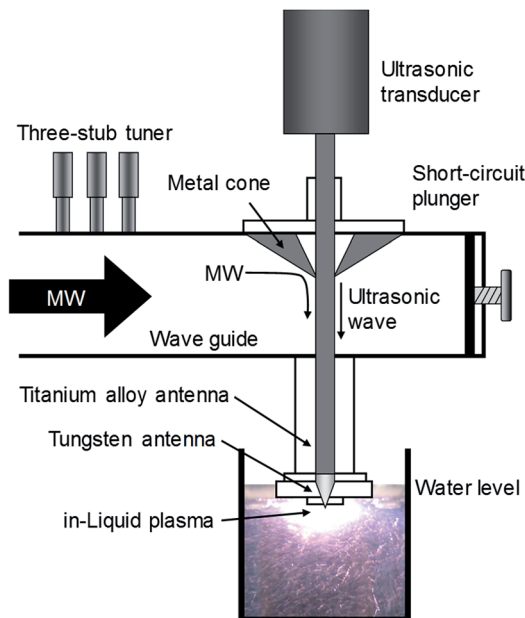


Fig. 10 Schematic diagram of an ultrasonic/microwave simultaneous irradiation type in-liquid plasma generator system. Reproduced from Horikoshi et al.¹⁵⁶ Copyright 2017 by Elsevier.

plasma is generated, causing plasma to be generated efficiently in the bubbles. Using the latter method, even if the incident power of the microwaves were reduced by 45% or more, compared to the existing apparatus without ultrasonic waves, in-liquid plasma could still be generated continuously and deterioration of the electrode could be minimized if not suppressed for long periods of use.

3. In-liquid plasma applications

3.1 Nanomaterials synthesis

3.1.1 Noble metals, alloys and metal-oxide nanoparticles.

Two methods have been reported for nanoparticle synthesis using in-liquid plasma. The first method utilizes dissolution of the electrode described in Section 2.3. In the case of in-liquid plasma, dissolution of the electrode surface proceeds by local heating; utilizing this phenomenon provides a method in which nanoparticles are produced by aggregating the electrode metal while evaporating the electrode surface (evaporation method). The second method (reduction method) involves reduction of a metal salt in aqueous media with the in-liquid plasma to synthesize metal nanoparticles. Nanoparticle synthesis by a gas-phase plasma reduction method has already been achieved; however, substituting this by a liquid-phase plasma increases the number of molecules of raw materials contained in the system by orders of magnitude. Hence, at laboratory level, for example, a yield of more than 10 g h^{-1} can be obtained. In addition, unlike the nanoparticle synthesis process occurring by gas-phase plasma, aggregation of generated particles can be prevented immediately by adding a particle agglutination inhibitor (or the like) into the solution.

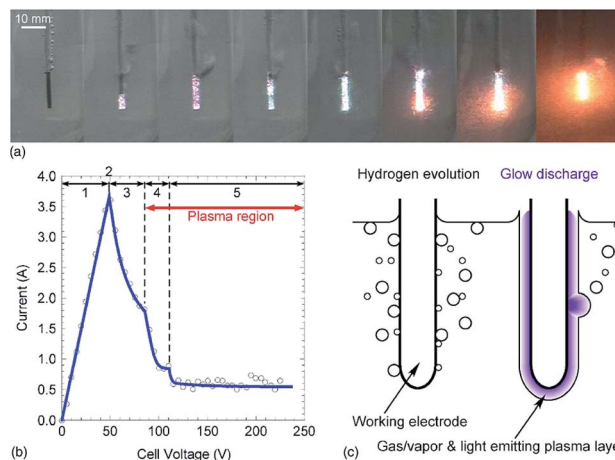


Fig. 11 (a) Photograph of plasma emission during the formation of nanoparticles; (b) relationship between current and voltage; (c) cartoon illustrating the process of nanoparticle generation. Reproduced from Toriyabe et al.⁸⁸ Copyright 2007 by the American Institute of Physics.

Dissolution of the electrode method. Studies have been conducted on the evaporation method to form various metallic nanoparticles by placing cathode electrodes of various metals in a potassium carbonate solution, followed by applying a direct current to this solution to evaporate and dissolve the electrodes. Metallic nanoparticles have been formed in solution during the evaporation of Ni, Ti, Ag, and Au nanowire electrodes with in-liquid plasma (Fig. 11).⁸⁸ The advantage of this method is that various kinds of nanoparticles can easily be formed in a liquid by simply changing the kind of metal used for the wire electrode. Along similar lines, Saito and coworkers⁹⁴ reported the syntheses of a single crystal tin oxide plate (SnO) and a $\text{Sn}_6\text{O}_4(\text{OH})_4$ skeleton using tin wire immersed in an electrolyte solution.

The size and shape of these nanoparticles can be controlled by changing the synthesis conditions (reaction temperature, cooling temperature, dispersant) of generating in-liquid plasma (Fig. 12).⁹⁴ And even if plasma conditions were changed, the morphology and the nature of nanoparticles could still be controlled (Fig. 13).⁹⁹ Metal electrodes can be volatilized using wide-area plasma, partial plasma, and partial plasma under high-temperature conditions. Accordingly, it is possible to produce Ti, Fe, Ni, Cu, Zn, Zr, Nb, Mo, Ag, W, Pt, Au, and SUS 316 nanoparticles using in-liquid plasma as the energy source. In addition, alloy nanoparticles of gold and platinum can be made by the simultaneous evaporation of the two electrode materials with in-liquid plasma (Fig. 14).¹⁵⁷ Another study reported the evaporation of a platinum electrode with in-liquid plasma to produce platinum nanoparticles (particle size, 2 nm) supported on a highly conductive carbon black support dispersed in water.¹⁵⁸ This Pt/C catalyst was produced with very high efficiency and used as a catalyst in fuel cells.

Reduced reaction with plasma method. Zinc oxide nanoparticles (ZnO NPs) have been produced using in-liquid plasma.⁹⁰ In this case, a Zn wire (the cathode) and a mesh



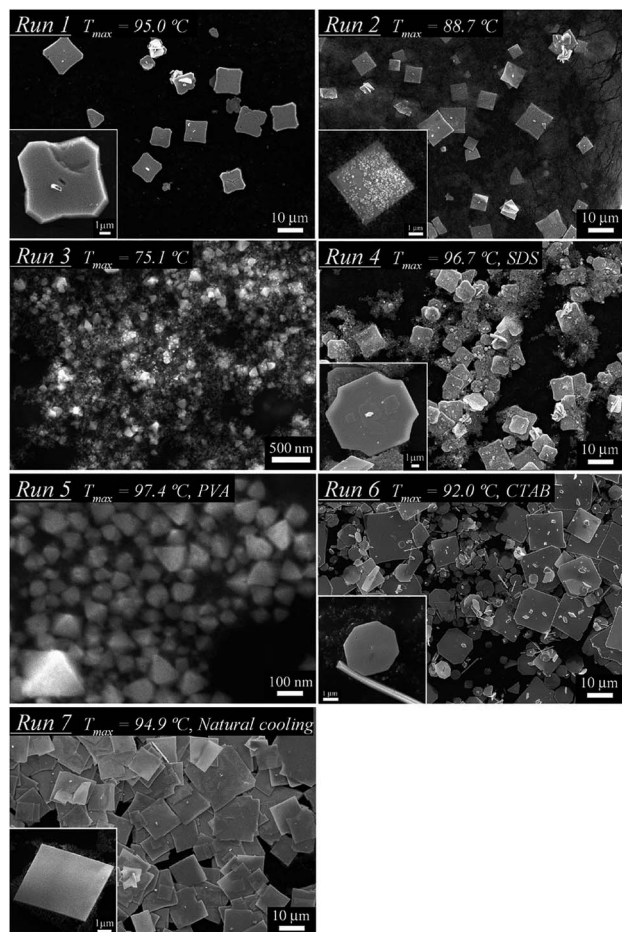


Fig. 12 SEM images of single crystals of a tin oxide SnO plate synthesized by in-liquid plasma under different reaction temperatures, dispersant and cooling conditions. Reproduced from Saito *et al.*⁹⁴ Copyright 2012 by the American Chemical Society.

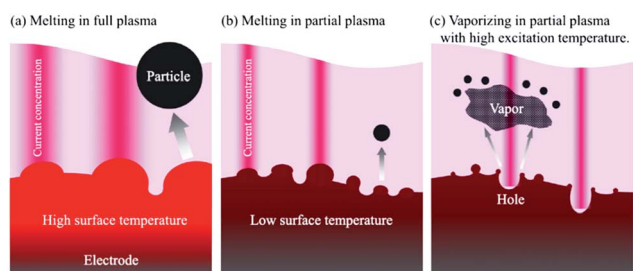


Fig. 13 Images of (a) a wide-area plasma; (b) a partial plasma; and (c) the volatilization of a metal electrode by partial plasma under high temperature conditions. Reproduced from Saito *et al.*⁹⁹ Copyright 2014 by the American Institute of Physics.

made of Pt wire (the anode) were submerged in an aqueous solution of K_2CO_3 . Application of a certain voltage to the solution system generated plasma in the immersed part of the Zn wire. Using medium-power input levels resulted in the formation of flower-like ZnO NPs (Fig. 15a and b),⁹⁰ while applying high-power input levels yielded aggregated ZnO NPs (Fig. 15c);

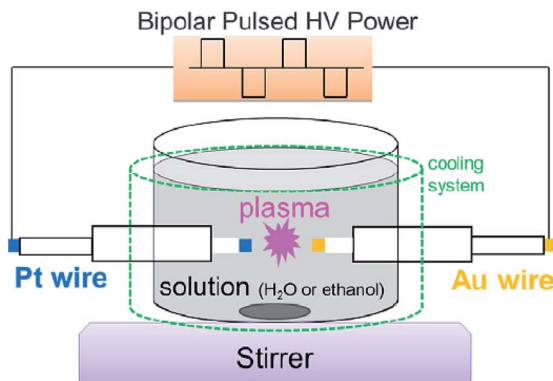


Fig. 14 Image of a synthesis apparatus of a gold/platinum alloy by in-liquid plasma using gold and platinum electrodes. Reproduced from Hua and coworkers.¹⁵⁷ Copyright 2013 by Elsevier.



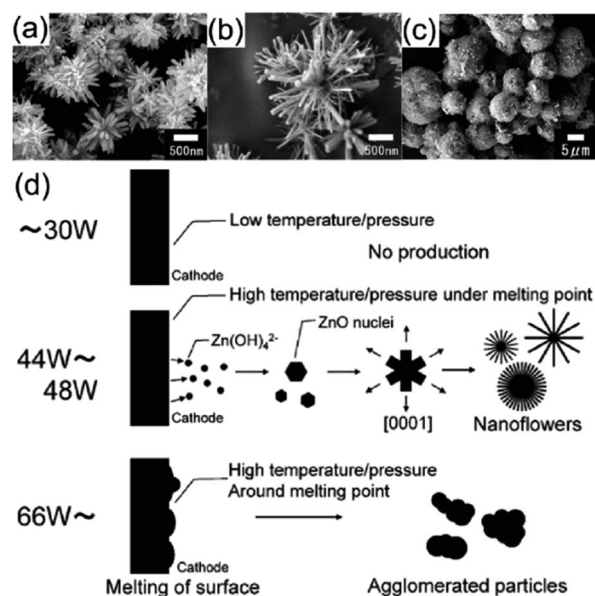


Fig. 15 SEM images of products obtained from in-liquid plasma usage; experimental conditions of K_2CO_3 concentration, and discharge voltage/power are: (a) 1.0 M, 66 V/44 W, (b) 0.5 M, 80 V/48 W, (c) 0.01 M, 200 V/168 W. (d) Schematic processes in the synthesis of ZnO nanoflowers and ZnO aggregates using in-liquid plasma. Modified with permission from ref. 90. Copyright 2011 by Elsevier.

the mechanism of the synthesis is summarized in Fig. 15d. The Zn wire is first oxidized to ZnO on its surface after plasma generation. At low power, the surface temperature of the electrode is below the melting point of zinc and some $Zn(OH)_4^{2-}$ species form around the Zn wire (reaction (1)).



Subsequently, $Zn(OH)_4^{2-}$ migrates to the low-temperature zone and decomposes into ZnO (reaction (2)).



The ZnO nanoparticles grow preferentially along the [0001] direction^{159,160} to form the flower-like ZnO nanoparticles. However, at high power (*i.e.*, at $>300 \text{ W cm}^{-2}$ (ref. 90)), the temperature of the Zn wire reaches its melting point causing rapid evaporation of the Zn wire and the ZnO film resulting in ZnO particle aggregates (Fig. 15c).


Research studies are also being conducted actively on a reduction method to synthesize various nanoparticles. For instance, gold-based bimetallic particles, (*e.g.*, Au-Fe, Au-Ga, Au-In or the like) can be produced using a metal-ion reduction method and a metal nitrate as the precursor from bivalent sp metals, trivalent sp metals, or 3d and 4d metals. A one-step

Table 1 Synthesis of noble metals, alloys and metal-oxide nanoparticles using various in-liquid plasma-related methods (see Fig. 6 for the in-liquid plasma methods)


Nanoparticles produced	Starting materials	In-liquid plasma methods	Ref.
Au	Gold rod or wire	Plasma A	165–169
		Plasma B	88, 99 and 114
		Plasma C	140
	HAuCl ₄	Plasma A	170–179
Ag	NaAuCl ₄	Plasma B	86
		Plasma A	180–183
		Plasma B	88 and 99
	Silver rod or wire	Plasma C	140, 147 and 151
Pt	AgNO ₃	Plasma A	184 and 185
		Plasma A	186
		Plasma A	187
	Ag-zeolite	Plasma A	96
Ni	Platinum wire	Plasma B	151
		Plasma C	86
		Plasma B	96
	H ₂ PtCl ₆	Plasma A	88, 89, 96 and 106
Cu	Nickel wire	Plasma A	188
		Plasma A	189 and 190
		Plasma B	86
	Copper wire	Plasma A	96
Ni	CuCl ₂	Plasma B	88, 89, 96 and 106
		Plasma A	188
		Plasma A	189 and 190
	CuSO ₄	Plasma B	86
Cu	Nickel wire	Plasma A	96
		Plasma B	88, 89, 96 and 106
		Plasma A	188
	Copper wire	Plasma A	189 and 190
Zn	CuCl ₂	Plasma A	86
		Plasma B	144
		Plasma C	98 and 101
	Zinc plate	Plasma B	157
Pt–Au	Tin rod	Plasma A	86
		Plasma B	191
		Plasma A	102
	Pt and Au wires	Plasma B	192
Pt–Au	H ₂ PtCl ₆ , NaAuCl ₄	Plasma A	114
		Plasma B	102
		Plasma B	102
	Ag and Pt rod	Plasma B	102 and 114
Ag–Pt	Alloy wire	Plasma A	193
		Plasma A	194
		Plasma A	195
	Ni(NO ₃) ₂ ·6H ₂ O, Cu(NO ₃) ₂ ·4H ₂ O	Plasma B	196
Ni–Cr	Alloy wire	Plasma A	88, 95 and 197
		Plasma B	109
		Plasma B	198
	Alloy wire	Plasma B	199
Ni–Cu	Alloy wire	Plasma A	200
		Plasma B	201
		Plasma B	202
	Alloy wire	Plasma B	203
Sn–Ag	Cobalt acetate, KBH ₄	Plasma A	204
		Plasma A	205–209
		Plasma A	210
	MoS ₂ powder	Plasma A	211
Sn–Pb	MoS ₂ powder	Plasma A	212 and 213
		Plasma A	
		Plasma A	
	Aluminum rod	Plasma A	
Stainless steel	Aluminum plate	Plasma A	
		Plasma B	
		Plasma B	
	Titanium rod	Plasma A	
Co–B	Ti wire	Plasma A	
		Plasma B	
		Plasma B	
	TiO ₂ nanotube and Pt wires	Plasma B	
MoS ₂	Zn(O ₂ CCH ₃) ₂ ·2H ₂ O	Plasma A	
		Plasma A	
		Plasma A	
	(or anhydrous Zn acetate) and D-glucose	Plasma A	
γ-Al ₂ O ₃	Copper foil	Plasma B	
		Plasma B	
		Plasma B	
	Copper plate	Plasma B	
TiO ₂	Indium and tin plate	Plasma B	
		Plasma B	
		Plasma B	
	Graphite in toluene	Plasma A	
Defective black TiO ₂	Carbon rods	Plasma A	
		Plasma A	
		Plasma A	
	Pt, H ₂ PtCl ₆ , CNT	Plasma A	
Pt nanoparticles supported on TiO ₂ nanotube	Platinum, aluminium, nickel, copper, tungsten, carbon electrodes	Plasma A	
		Plasma A	
		Plasma A	
	Ag NPs, tetraethylorthosilicate (TEOS)	Plasma A	
Cellulose–ZnO composite	Ag NPs, tetraethylorthosilicate (TEOS)	Plasma A	
		Plasma A	
		Plasma A	
	Ag NPs, tetraethylorthosilicate (TEOS)	Plasma A	




Morishita and co-workers¹⁶⁴ investigated the routes of solution-plasma-induced nanocarbon formation from hexane, hexadecane, cyclohexane, and benzene; the synthesis from benzene was the most effective. However, the nanocarbons obtained from linear molecules were more crystalline than those from ring molecules. Linear molecules decomposed into shorter olefins, whereas ring molecules were reconstructed in the plasma. C-H dissociation proceeded in the saturated ring molecules, followed by conversion into unsaturated ring



molecules. However, unsaturated ring molecules were directly polymerized through cation radicals (*e.g.*, benzene radical cation) and were converted into two- and three-ring molecules at the plasma-solution interface. The nanocarbons from linear molecules were synthesized in plasma from small C2 molecules under heat; the products so-obtained were the same as those obtained *via* a pyrolysis synthesis. Conversely, the nanocarbons obtained from ring molecules were directly synthesized through an intermediate (such as benzene radical cations) at the



Ultra-small sized (within 5 nm) and monodispersed silicon quantum dots (Si QDs) are ideal candidates for Si/C nanocomposites to be used as anode materials in lithium ion batteries. However, fabrication of these Si QDs/C nanocomposites remains a gigantic challenge in materials chemistry because of the small size, high chemical activity, and low density of Si QDs with Si-H terminated surfaces. Nonetheless, Wei and coworkers²¹⁸ reported a convenient synthetic method for the preparation of Si QDs/C nanocomposites by a novel liquid-phase plasma-assisted synthetic process, with the Si quantum dots embedded in a carbon matrix (Si-QDs/C) *via* a direct discharge between two electrodes powered by an AC power supply. Fig. 18a shows the setup for the liquid-phase plasma synthetic route.²¹⁸ Briefly, the copper and the tungsten (with a quartz shell) electrodes were placed into an ethanol solution containing Si QDs (photograph (i)). After a 20 min continuous sparking discharge, grey Si QDs/C composites were obtained successfully (photograph (ii)). Photograph (iii) shows the spark during the tungsten electrode discharging process. Fig. 18b displays the TEM image of the Si QDs, revealing a diameter within 5 nm and a single crystalline nature with

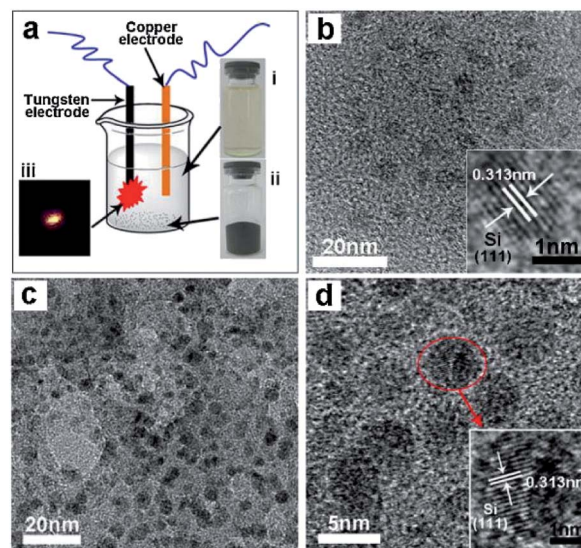

a (111) spacing of about 0.313 nm in the Si crystal (see inset). Fig. 18c depicts the TEM image of the resulting Si QDs/C nanocomposites, and shows that the Si QDs are indeed embedded in large-sized amorphous carbon particles. The HRTEM image of the Si QDs/C nanocomposites is shown in Fig. 18d; the inset image highlights the Si QDs in the nanocomposites maintaining the good crystalline nature and confirms the lattice fringe space of *ca.* 0.313 nm of the (111) plane of the Si crystal. The Si-QDs/C nanocomposites demonstrated high specific capacity, good cycling life and high Coulombic efficiency as anode materials in lithium ion batteries.

In-liquid plasma techniques in wastewater treatments are associated with the formation of a light emitting plasma around an electrode in a high conductivity electrolyte solution at moderate voltages up to 1 kV. In recent years, these techniques have attracted considerable interest as a tool for generating a large quantity of heat and a high yield of solvent-split radicals.²¹⁹ There are several variations of using in-liquid plasma in the treatment of wastewaters: (A) immersing the electrodes in the waters (Fig. 19a), (B) using a water flow (Fig. 19b), and (C) using bubbles (Fig. 19c) that can be roughly divided into three groups.²²⁰ In method (A) – *i.e.*, in an underwater streamer discharge – to the extent that plasma is generated directly in the liquid, it is suitable for treating wastewaters by means of the resulting shock waves and the generated oxidative active species (*e.g.*, $\cdot\text{OH}$ radicals and ozone). Application studies have treated large quantities of water such as: ballast water, river waters, and dams from high concentrations to smaller scales.²²¹ On the other hand, in methods (B) and (C), since the gas is converted to plasma and is introduced into the liquid, the advantage here is that plasma can be generated easily while concurrently getting


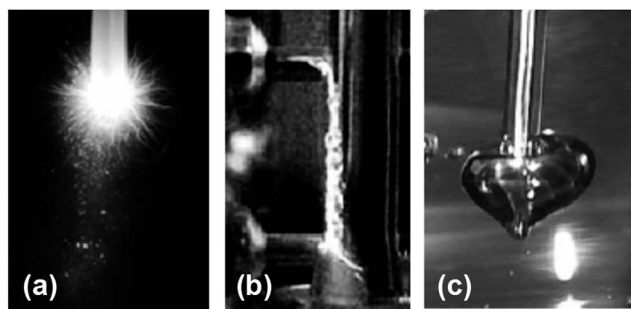


Fig. 19 Method of generating in-liquid plasma for use in water treatment: (a) method of the immersed electrodes in water; (b) method using water flow; (c) method using bubbles. Reproduced from Akiyama *et al.*²²⁰ Copyright 2014 by The Japan Society of Plasma Science and Nuclear Fusion Research.

significant energy saving. These systems generate plasma in bubbles and generate oxidized active species by diffusing them in water as compared with a system in which plasma is directly generated in an aqueous solution. However, compared with method (A), the number of generated $\cdot\text{OH}$ radicals is reduced by about an order of magnitude,¹²⁷ so that the efficiency of the water treatment is lower. For instance, in the concurrent ultrasonic/microwave in-liquid plasma generator described in Fig. 10, the electrode is immersed in the aqueous solution, bubbles are then generated by the ultrasonic waves while plasma is generated in the solution so that the quantity of $\cdot\text{OH}$ radicals generated is decreased. However, because of the cavitation effect of ultrasonic waves, the number of $\cdot\text{OH}$ generated increases such that the total concentration of $\cdot\text{OH}$ radicals produced is also increased.

Various oxidative active species are used in water treatments. Among these, the most powerful oxidative species are the $\cdot\text{OH}$ radicals. Accordingly, studies have been carried out to increase the concentration of $\cdot\text{OH}$ radicals and enhance diffusion efficiency in water in those water treatment processes that involve in-liquid plasma.²²² In addition, generation of $\cdot\text{OH}$ radicals by in-liquid plasma in water and the decomposition of contaminants have also been undertaken.²²³ The mechanism of $\cdot\text{OH}$ radical generation by in-liquid plasma is summarized by eqn (3)–(6). Electrons (e^{-*}) generated by the in-liquid plasma dissociate water and lead to the formation of $\cdot\text{OH}$ radicals (eqn (3)). On the other hand, interaction of these electrons (e^{-*} ; eqn (4)) with dissolved oxygen generates oxygen atoms in their excited $\text{O}(^1\text{D})$ and ground $\text{O}(^3\text{P})$ states, which ultimately generate $\cdot\text{OH}$ radicals from water (eqn (5) and (6)).²²³ Therefore, increasing the concentration of dissolved oxygen leads to an increase in the concentration of $\cdot\text{OH}$ species. However, as the concentration of $\cdot\text{OH}$ radicals increases, their subsequent recombination may be facilitated, so that it is disadvantageous to produce too many such species; note that the recombination process depends on the diffusion conditions of the $\cdot\text{OH}$ radical species.



3.2.1 Degradation of persistent organic pollutants (POPs).

Among the many fluorinated organic compounds, perfluorooctanoic acid (PFOA: $C_7F_{15}COOH$) and perfluorooctanesulfonic acid (PFOS: $C_8F_{17}SO_3H$) possess such excellent chemical and physical characteristics as water repellence, surface-active properties, heat resistance, and chemical resistance. Consequently, they have been used widely as industrial surfactants. However, from the viewpoint of environmental persistence, bioaccumulation and toxicity they are designated as regulated substances by the Stockholm convention (persistent organic pollutants (POPs) convention). Nonetheless, even though PFOS is an alternative albeit difficult surfactant in some industries, its use is exceptionally being permitted; treatment methods to dispose of PFOS have been investigated by Schroder and Maesters²²⁴ who noted that PFOA and PFOS are difficult to decompose with $\cdot OH$ radicals and ozone. Successful methods to decompose these fluorinated substrates have involved: (i) photochemical decomposition using a photocatalyst,²²⁵ (ii) photolysis by 185 nm vacuum UV light,²²⁶ (iii) sulfuric acid radicals ($SO_4^{\cdot -}$),²²⁷ (iv) a mechanochemical method,²²⁸ and (v) ultrasonic cavitation.²²⁹

Horikoshi *et al.*¹⁵⁶ achieved successful decomposition of perfluorooctanoic acid (PFOA) in ion-exchange water using in-liquid plasma. The methodology involved concurrent ultrasonic/microwave irradiation in an in-liquid plasma type generator; results are reported in Fig. 20.

Plasma irradiation of PFOA (0.01 mM) in aqueous media for 90 s led to 59% defluorination accompanying the decomposition of PFOA, a substrate noted above as being difficult to decompose even with $\cdot\text{OH}$ radicals. Nonetheless, PFOA was decomposed synergistically by the cavitation effect generated by


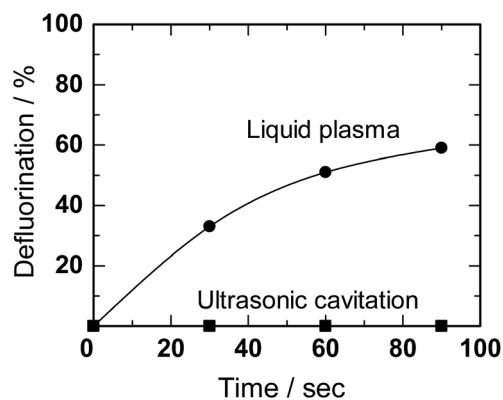


Fig. 20 Defluorination yields (%) from the degradation of aqueous PFOA solutions (0.01 mM) by ultrasonic cavitation alone and by the microwave discharge in-liquid plasma method under simultaneous ultrasonic cavitation (MW power, 220 W; power for cavitation, 90 W). Reproduced from Horikoshi *et al.*¹⁵⁶ Copyright 2017 by Elsevier.

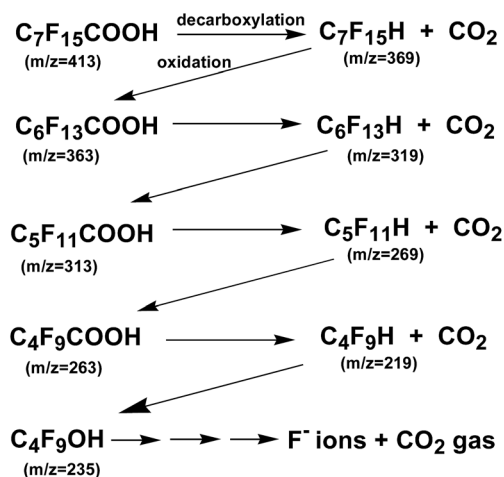

Scheme 1 Sequential loss of CF₂ units from the PFOA perfluorinated acid and decarboxylated intermediates produced during the degradation of PFOA by plasma irradiation for 90 s. Note that loss of CF₂ units after the first decarboxylation step likely occurs by oxidation of the protonated terminal carbon and formation of F[−] ions and CO₂ and so on in the Z-type pathway shown above. From Horikoshi and coworkers.¹⁵⁶ Copyright 2017 by Elsevier.

the homogenizer in addition to the local heat and shock waves generated by the in-liquid plasma. Monitoring the decomposition of PFOA by liquid chromatography/mass spectrometry (LC-MS) revealed a peak for PFOA at $m/z = 413$ that decreased in intensity (thus, decomposition of PFOA) and formation of intermediates whose peak intensities at $m/z = 363$, 313, 263 increased. Assigning these peaks to the various intermediates revealed that the decomposition of PFOA progressed through a gradual release of −CF₂− units (Scheme 1). Complete mineralization of PFOA to CO₂ gas and F[−] ions was achieved.¹⁵⁶

3.2.2 Sterilization of water by in-liquid plasma. Basic research on the sterilization of water with in-liquid plasma is being carried out quite proactively. The effects of in-liquid plasma are expected to be thermal effects in addition to those effects emanating from the generated oxidative active species (·OOH and ·OH radicals). As an example, the effect of culture temperature of *Escherichia coli* on pulsed electric field (PEF) sterilization has been studied by Ohshima and coworkers,²³⁰ who noted that the sterilization efficiency depends on the culture temperature of the *E. coli* bacteria and that the efficiency of PEF sterilization is influenced by the PEF treatment temperature. Moreover, insofar as the bactericidal effect of oxidative active species generated from plasmas in underwater streamer discharge liquids is concerned, sterilization is affected more by the stable hydrogen peroxide produced later in water than by the effect of ·OH species.²³¹

3.2.3 Hybrid in-liquid plasma/photocatalytic degradation system. Several examples exist of wastewater treatments performed with in-liquid plasma in combination with other treatment methods. For instance, synergistic effects occur in wastewater treatments using ultrasonic cavitation of activated carbon^{232–236} in combination with a Fenton catalyst,^{237–243} with TiO₂ photocatalyst particles,^{244–247} and TiO₂ films.^{248,249} In


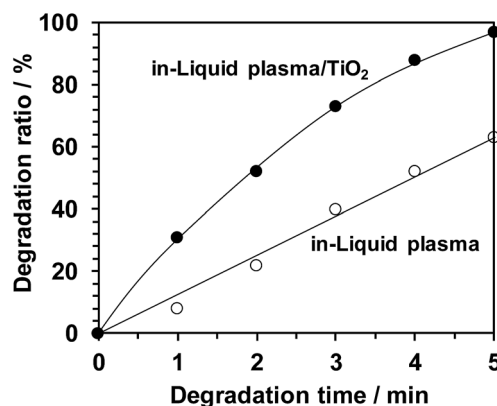



Fig. 21 Decomposition of methylene blue in aqueous solution by in-liquid plasma alone and in combination with photocatalyst TiO₂ particles.¹⁷ Copyright 2017 by S. Horikoshi.

addition, decomposition of dyes (e.g., methylene blue) can be achieved with an in-liquid plasma/photocatalyst system in which the TiO₂ photocatalyst ($\lambda < 387$ nm) was activated by the UV light emitted from the in-liquid plasma; no UV lamp was required.¹⁷ The extent of decomposition of methylene blue was 63% after a 5 min treatment by the in-liquid plasma alone; in the presence of TiO₂ particulates, the decomposition of methylene blue reached 97% (see Fig. 21). The concentration of dissolved oxygen was an important factor for enhancing process efficiency.¹⁷

3.2.4 Scaled-up process. The occurrence of *Microcystis aeruginosa* in nature, a species of freshwater cyanobacteria that can form harmful algal blooms, is cause of some serious concerns: e.g., deterioration of the landscape, emission of a putrid odor, oxygen deficiency in water ecosystems, and not least its toxic properties that greatly affect not only the natural environment but more so the fishing industry. Accordingly, techniques to remove such species by ultrasonic waves and by shock waves (and the like) are being examined. In this regard, Sakugawa and coworkers²⁵⁰ have treated *Microcystis aeruginosa* using in-liquid plasma; on-site demonstration experiments are also underway with a scaled-up apparatus. A demonstration experiment carried out in a vessel (width 3.9 m, height 1.6 m, weight 450 kg) floating in a dam (see Fig. 22) and equipped with a solar cell panel and magnetic pulse compression-type in-liquid plasma generator demonstrated the self-propelled removal of *Microcystis aeruginosa* by the generated in-liquid plasma.²⁵¹ The in-liquid plasma caused the collapse of the gas bubbles inside the *Microcystis aeruginosa* cells triggering the buoyancy of the *Microcystis aeruginosa* to vanish; the treated blue patch sank into the water thus hindering the photosynthesis and suppressing any subsequent growth.

A large-sized apparatus that can process industrial wastewaters at low cost and re-use of the recycled water is being considered by the Mitsubishi Electric Co. Japan.²⁵² Unlike existing equipment, the particular equipment being considered features wastewater treatment that can be carried out with a simple method with no chemicals involved. As such, it is characterized by low cost and no concerns with regard to secondary pollution and use of the





4. Summary remarks

Conflicts of interest

Acknowledgements

for financial support to SH through a Grant-in-aid for Scientific Research (No. C-25420820). Financial support from the Sophia University-wide Collaborative Research Fund to SH is also appreciated. One of us (NS) thanks Professor Angelo Albini of the University of Pavia (Italy) for his continued hospitality during the many winter semesters in his PhotoGreen Laboratory.

Notes and references

- 1 S. Horikoshi, R. F. Schiffrmann, J. Fukushima and N. Serpone, *Microwave Chemical and Materials Processing: A Tutorial*, Springer, Japan, 2017, in press.
- 2 I. Rahim, S. Nomura, S. Mukasa and H. Toyota, Decomposition of methane hydrate for hydrogen production using microwave and radio frequency in-liquid plasma methods, *Appl. Therm. Eng.*, 2015, **90**, 120–126.
- 3 A. Piel, *Plasma Physics: An Introduction to Laboratory, Space, and Fusion Plasmas*, Springer-Verlag, Berlin Heidelberg, 2010.
- 4 W. Crookes, On a fourth state of matter, *Proc. R. Soc. London*, 1879, **30**, 469–472.
- 5 J. J. Thomson, Cathode rays, London Edinburgh Dublin, *Philos. Mag.*, 1897, **44**, 293–316.
- 6 I. Langmuir, Oscillations in ionized gases, *Proc. Natl. Acad. Sci. U. S. A.*, 1928, **14**, 627–637.
- 7 R. Itatani, Progress of plasma physics in 20th century and future, *Appl. Phys. Express*, 2000, **69**, 971–977.
- 8 M. Laroussi, Sterilization of contaminated matter with an atmospheric pressure plasma, *IEEE Trans. Plasma Sci.*, 1996, **24**, 1188–1191.
- 9 R. J. Goldston and P. H. Rutherford, *Introduction to plasma physics*, Taylor & Francis, New York, 1995, ch. 1.
- 10 See: <https://ia902704.us.archive.org/31/items/onradiantmatterl00croorich/onradiantmatterl00croorih.pdf>, accessed August 2017.
- 11 S. Horikoshi and N. Serpone, *Microwaves in Nanoparticle Synthesis – Fundamentals and Applications*, ed. S. Horikoshi and N. Serpone, Wiley-VCH, Weinheim, Germany, 2013, ch. 1.
- 12 J. S. Clements, M. Sato and R. H. Davis, Preliminary investigation of pre-breakdown phenomena and chemical reactions using a pulsed high-voltage discharge in water, *IEEE Trans. Ind. Appl.*, 1987, **IA-23**, 224–235.
- 13 J. C. Devins, S. J. Rzed and R. J. Schwabe, Breakdown and pre-breakdown phenomena in liquids, *J. Appl. Phys.*, 1981, **52**, 4531–4545.
- 14 K. Yasukoka, T. Haehara, J. Katsuki, S. Katsuki, T. Namihira, T. Kaneko and R. Hatakeyama, Generation of underwater discharge plasma and its property, *J. Plasma Fusion Res.*, 2008, **84**, 666–673.
- 15 K. Schoenbach, J. Kolb, S. Xiao, S. Katsuki, Y. Minamitani and R. Joshi, Electrical breakdown of water in microgaps, *Plasma Sources Sci. Technol.*, 2008, **17**, 024010.
- 16 T. Namihira, S. Sakai, T. Yamaguchi, K. Yamamoto, C. Yamada, T. Kiyan, T. Sakugawa and S. Katsuki, Electron temperature and electron density of underwater

- This journal is © The Royal Society of Chemistry 2017

- 49 M. Tokushige, T. Nishikiori and Y. Ito, Plasma-induced cathodic discharge electrolysis to form various metal/alloy nanoparticles, *Russ. J. Electrochem.*, 2010, **46**, 619–626.
- 50 M. Tokushige, H. Tsujimura, T. Nishikiori and Y. Ito, Formation of metallic Si and SiC nanoparticles from SiO₂ particles by plasma-induced cathodic discharge electrolysis in chloride melt, *Electrochim. Acta*, 2013, **100**, 300–303.
- 51 M. Tokushige, T. Yamanaka, A. Matsuura, T. Nishikiori and Y. Ito, Synthesis of magnetic nanoparticles (Fe and FePt) by plasma-induced cathodic discharge electrolysis, *IEEE Trans. Plasma Sci.*, 2009, **37**, 1156–1160.
- 52 M. Tokushige, T. Nishikiori and Y. Ito, Formation of fine Ni nanoparticle by plasma-induced cathodic discharge electrolysis using rotating disk anode, *J. Electrochem. Soc.*, 2010, **157**, E162–E166.
- 53 M. Tokushige, T. Nishikiori and Y. Ito, Synthesis of Ni nanoparticles by plasma-induced cathodic discharge electrolysis, *J. Appl. Electrochem.*, 2009, **39**, 1665–1670.
- 54 M. Tokushige, H. Hongo, T. Nishikiori and Y. Ito, Formation of Sm-Co intermetallic compound nanoparticles based on plasma-induced cathodic discharge electrolysis in chloride melt, *J. Electrochem. Soc.*, 2012, **159**, E5–E10.
- 55 M. Tokushige, T. Nishikiori, M. C. Lafouresse, C. Michiokad, K. Yoshimurad, Y. Fukunakac and Y. Ito, Formation of FePt intermetallic compound nanoparticles by plasma induced cathodic discharge electrolysis, *Electrochim. Acta*, 2010, **55**, 8154–8159.
- 56 P. Bruggeman, E. Ribézl, J. Degroote, J. Vierendeels and C. Leys, Plasma characteristics and electrical breakdown between metal and water electrodes, *J. Optoelectron. Adv. Mater.*, 2008, **10**, 1964–1967.
- 57 W.-T. Yao, S.-H. Yu, Y. Zhou, J. Jiang, Q.-S. Wu, L. Zhang and J. Jiang, Formation of uniform CuO nanorods by spontaneous aggregation: selective synthesis of CuO, Cu₂O, and Cu nanoparticles by a solid-liquid phase arc discharge process, *J. Phys. Chem. B*, 2005, **109**, 14011–14016.
- 58 K. Furuya, Y. Hirowatari, T. Ishioka and A. Harata, Protective agent-free preparation of gold nanoplates and nanorods in aqueous HAuCl₄ solutions using gas-liquid interface discharge, *Chem. Lett.*, 2007, **36**, 1088–1089.
- 59 M. Ito, M. Hayakawa, S. Takashima, E. Asami, T. Aoki, M. Oka, H. Asano, M. Kitahara, S. Nakata and K. Yamaguchi, Preparation of aqueous dispersion of titanium dioxide nanoparticles using plasma on liquid surface, *Jpn. J. Appl. Phys.*, 2012, **51**, 116201.
- 60 T. Hagino, H. Kondo, K. Ishikawa, H. Kano, M. Sekine and M. Hori, Ultrahigh-speed synthesis of nanographene using alcohol in-liquid plasma, *Appl. Phys. Express*, 2012, **5**, 035101.
- 61 M. Matsushima, M. Noda, T. Yoshida, H. Kato, G. Kalita, T. Kizuki, H. Uchida, M. Umeno and K. Wakita, Formation of graphene nano-particle by means of pulsed discharge to ethanol, *J. Appl. Phys.*, 2013, **113**, 114304.
- 62 D. Kozak, E. Shibata, A. Iizuka and T. Nakamura, Growth of carbon dendrites on cathode above liquid ethanol using surface plasma, *Carbon*, 2014, **70**, 87–94.
- 63 M. Tokushige, A. Matsuura, T. Nishikiori and Y. Ito, Formation of Co-Pt intermetallic compound nanoparticles by plasma induced cathodic discharge electrolysis in a chloride melt, *J. Electrochem. Soc.*, 2011, **158**, E21–E26.
- 64 Y. Hayashi, S. Machmudah, N. Takada, H. Kanda, K. Sasaki and M. Goto, Decomposition of methyl orange using pulsed discharge plasma at atmospheric pressure: effect of different electrodes, *Jpn. J. Appl. Phys.*, 2014, **53**, 010212.
- 65 I. G. Koo, M. S. Lee, J. H. Shim, J. H. Ahn and W. M. Lee, Platinum nanoparticles prepared by a plasma-chemical reduction method, *J. Mater. Chem.*, 2005, **15**, 4125–4128.
- 66 C. Richmonds and R. M. Sankaran, Plasma-liquid electrochemistry: rapid synthesis of colloidal metal nanoparticles by microplasma reduction of aqueous cations, *Appl. Phys. Lett.*, 2008, **93**, 131501.
- 67 N. Shirai, M. Nakazawa, S. Ibuka and S. Ishii, Atmospheric DC glow microplasmas using miniature gas flow and electrolyte cathode, *Jpn. J. Appl. Phys.*, 2009, **48**, 036002.
- 68 F.-C. Chang, C. Richmonds and R. M. Sankaran, Microplasma-assisted growth of colloidal Ag nanoparticles for point of-use surface-enhanced Raman scattering applications, *J. Vac. Sci. Technol., A*, 2010, **28**, L5.
- 69 V. Srcek, D. Mariotti and M. Kondo, Microplasma-induced surface engineering of silicon nanocrystals in colloidal dispersion, *Appl. Phys. Lett.*, 2010, **97**, 161502.
- 70 W.-H. Chiang, C. Richmonds and R. M. Sankaran, Continuous-flow, atmospheric-pressure microplasmas: aversatile source for metal nanoparticle synthesis in the gas or liquid phase, *Plasma Sources Sci. Technol.*, 2010, **19**, 034011.
- 71 X. Z. Huang, X. X. Zhong, Y. Lu, Y. Li, A. E. Rider, S. A. Furman and K. Ostrikov, Plasmonic Ag nanoparticles via environment-benign atmospheric microplasma electrochemistry, *Nanotechnology*, 2013, **24**, 095604.
- 72 J. Patel, L. Němcová, P. Maguire, W. G. Graham and D. Mariotti, Synthesis of surfactant-free electrostatically stabilized gold nanoparticles by plasma-induced liquid chemistry, *Nanotechnology*, 2013, **24**, 245604.
- 73 C. Du and M. Xiao, Cu₂O nanoparticles synthesis by microplasma, *Sci. Rep.*, 2014, **4**, 7339–7344.
- 74 R. Wang, S. Zuo, D. Wu, J. Zhang, W. Zhu, K. H. Becker and J. Fang, Microplasma-assisted synthesis of colloidal gold nanoparticles and their use in the detection of cardiac troponin I (cTn-I), *Plasma Processes Polym.*, 2015, **12**, 380–391.
- 75 T. Yan, X. Zhong, A. E. Rider, Y. Lu, S. A. Furman and K. Ostrikov, Microplasma-chemical synthesis and tunable real time plasmonic responses of alloyed Au_xAg_{1-x} nanoparticles, *Chem. Commun.*, 2014, **50**, 3144–3147.
- 76 N. Shirai, S. Uchida and F. Tochikubo, Synthesis of metal nanoparticles by dual plasma electrolysis using atmospheric dc glow discharge in contact with liquid, *Jpn. J. Appl. Phys.*, 2014, **53**, 046202.



- This journal is © The Royal Society of Chemistry 2017

- 106 G. Saito, S. Hosokai, M. Tsubota and T. Akiyama, Ripple formation on a nickel electrode during a glow discharge in a solution, *Appl. Phys. Lett.*, 2012, **100**, 181601.
- 107 M. R. M. B. Julaihi, S. Yatsu, M. Jeem and S. Watanabe, Synthesis of stainless steel nanoballs *via* submerged glow-discharge plasma and its photocatalytic performance in methylene blue decomposition, *J. Exp. Nanosci.*, 2014, **10**, 965–982.
- 108 G. Saito and N. Sakaguchi, Solution plasma synthesis of Si nanoparticles, *Nanotechnology*, 2015, **26**, 235602.
- 109 K. Azumi, A. Kanada, M. Kawaguchi and M. Seo, Formation of microparticles from titanium and silicon electrodes using high voltage discharge in electrolyte solution, *Hyomen Jijutsu*, 2005, **56**, 938–941.
- 110 L. Schaper, W. G. Graham and K. R. Stalder, Vapour layer formation by electrical discharges through electrically conducting liquids—modelling and experiment, *Plasma Sources Sci. Technol.*, 2011, **20**, 034003.
- 111 L. Schaper, K. R. Stalder and W. G. Graham, Plasma production in electrically conducting liquids, *Plasma Sources Sci. Technol.*, 2011, **20**, 034004.
- 112 P. Ruma, N. Lukes, N. Aoki, E. Spetlikova, S. H. R. Hosseini, T. Sakugawa and H. Akiyama, Effects of pulse frequency of input power on the physical and chemical properties of pulsed streamer discharge plasmas in water, *J. Phys. D: Appl. Phys.*, 2013, **46**, 125202.
- 113 G. Saito, Y. Nakasugi and T. Akiyama, Generation of solution plasma over a large electrode surface area, *J. Appl. Phys.*, 2015, **118**, 023303.
- 114 S. Yatsu, H. Takahashi, H. Sasaki, N. Sakaguchi, K. Ohkubo, T. Muramoto and S. Watanabe, Fabrication of nanoparticles by electric discharge plasma in liquid, *Arch. Metall. Mater.*, 2013, **58**, 425–429.
- 115 G. Saito, Y. Nakasugi and T. Akiyama, High-speed camera observation of solution plasma during nanoparticles formation, *Appl. Phys. Lett.*, 2014, **104**, 83104.
- 116 K. Kobayashi, Y. Tomita and M. Sanmyo, Electrochemical generation of hot plasma by pulsed discharge in an electrolyte, *J. Phys. Chem. B*, 2000, **104**, 6318–6326.
- 117 T. Mizuno, T. Akimoto, K. Azumi, T. Ohmori, Y. Aoki and A. Takahashi, Hydrogen evolution by plasma electrolysis in aqueous solution, *Jpn. J. Appl. Phys., Part 1*, 2005, **44**, 396–401.
- 118 A. Hickling and M. D. Ingram, Contact glow-discharge electrolysis, *Trans. Faraday Soc.*, 1964, **60**, 783–793.
- 119 L. Wang, Aqueous organic dye discoloration induced by contact glow discharge electrolysis, *J. Hazard. Mater.*, 2009, **171**, 577–581.
- 120 Y. Liu and X. Jiang, Plasma-induced degradation of chlorobenzene in aqueous solution, *Plasma Chem. Plasma Process.*, 2008, **28**, 15–24.
- 121 K. Azumi, T. Mizuno, T. Akimoto and T. Ohmori, Light emission from Pt during high-voltage cathodic polarization, *J. Electrochem. Soc.*, 1999, **146**, 3374–3377.
- 122 S. K. Sengupta, R. Singh and A. K. Srivastava, A study on the origin of nonfaradaic behavior of anodic contact glow discharge electrolysis: the relationship between power dissipated in glow discharges and nonfaradaic yields, *J. Electrochem. Soc.*, 1998, **145**, 2209–2213.
- 123 J. Gong, J. Wang, W. Xie and W. Cai, Enhanced degradation of aqueous methyl orange by contact glow discharge electrolysis using Fe^{2+} as catalyst, *J. Appl. Electrochem.*, 2008, **38**, 1749–1755.
- 124 J. Gao, Z. Hu, X. Wang, J. Hou, X. Lu and J. Kang, Oxidative degradation of acridine orange induced by plasma with contact glow discharge electrolysis, *Thin Solid Films*, 2001, **390**, 154–158.
- 125 J. Gao, X. Wang, Z. Hu, H. Deng, J. Hou, X. Lu and J. Kang, Plasma degradation of dyes in water with contact glow discharge electrolysis, *Water Res.*, 2003, **37**, 267–272.
- 126 J. Gao, Y. Liu, W. Yang, L. Pu, J. Yu and Q. Lu, Oxidative degradation of phenol in aqueous electrolyte induced by plasma from a direct glow discharge, *Plasma Sources Sci. Technol.*, 2003, **12**, 533–538.
- 127 P. Bruggeman, D. Schram, M. Á. González, R. Rego, M. G. Kong and C. Leys, Characterization of a direct de-excited discharge in water by optical emission spectroscopy, *Plasma Sources Sci. Technol.*, 2009, **18**, 025017.
- 128 K.-Y. Shih and B. R. Locke, Effects of electrode protrusion length, pre-existing bubbles, solution conductivity and temperature, on liquid phase pulsed electrical discharge, *Plasma Processes Polym.*, 2009, **6**, 729–740.
- 129 T. Maehara, K. Nishiyama, S. Onishi, S. Mukasa, H. Toyota, M. Kuramoto, S. Nomura and A. Kawashima, Degradation of methylene blue by radio frequency plasmas in water under ultraviolet irradiation, *J. Hazard. Mater.*, 2010, **174**, 473–476.
- 130 S. Mukasa, T. Maehara, S. Nomura, H. Toyota, A. Kawashima, Y. Hattori, Y. Hashimoto and H. Yamashita, Growth of bubbles containing plasma in water by high-frequency irradiation, *Int. J. Heat Mass Transfer*, 2010, **53**, 3067–3074.
- 131 T. Maehara, S. Honda, C. Inokuchi, M. Kuramoto, S. Mukasa, H. Toyota, S. Nomura and A. Kawashima, Influence of conductivity on the generation of a radio frequency plasma surrounded by bubbles in water, *Plasma Sources Sci. Technol.*, 2011, **20**, 034016.
- 132 T. Maehara, H. Toyota, M. Kuramoto, A. Iwamae, A. Tadokoro, S. Mukasa, H. I. Yamashita, A. Kawashima and S. Nomura, Radio frequency plasma in water, *Jpn. J. Appl. Phys., Part 1*, 2006, **45**, 8864–8868.
- 133 T. Maehara, I. Miyamoto, K. Kurokawa, Y. Hashimoto, A. Iwamae, M. Kuramoto, H. Yamashita, S. Mukasa, H. Toyota, S. Nomura and A. Kawashima, Degradation of methylene blue by RF plasma in water, *Plasma Chem. Plasma Process.*, 2008, **28**, 467–482.
- 134 S. Nomura, H. Toyota, S. Mukasa, Y. Takahashi, T. Maehara, A. Kawashima and H. Yamashita, Discharge characteristics of microwave and high-frequency in-liquid plasma in water, *Appl. Phys. Express*, 2008, **1**, 046002.
- 135 S. Nomura, S. Mukasa, H. Toyota, H. Miyake, H. Yamashita, T. Maehara, A. Kawashima and F. Abe, Characteristics of in liquid plasma in water under higher pressure than



- This journal is © The Royal Society of Chemistry 2017

- 249 A. G. Bubnov, E. Y. Burova, V. I. Grinevich, V. V. Rybkin, J. K. Kim and H. S. Choi, Comparative actions of NiO and TiO₂ catalysts on the destruction of phenol and its derivatives in a dielectric barrier discharge, *Plasma Chem. Plasma Process.*, 2007, **27**, 177–187.
- 250 T. Sakugawa, N. Aoki, H. Akiyama, K. Ishibashi, M. Watanabe, A. Kouda and K. Suematsu, A method of cyanobacteria treatment using underwater pulsed streamer-like discharge, *IEEE Trans. Plasma Sci.*, 2014, **42**, 794–798.
- 251 See e.g., http://www.kumamoto-u.ac.jp/daigakujouhou/kouhou/pressrelease/2013_file/release_130819.pdf, accessed August 2017.
- 252 See e.g., <http://mitsubishielectric.co.jp/corporate/randd/spotlight/a25/index.html>, accessed August 2017.
- 253 T. A. Kareem and A. A. Kaliani, Glow discharge plasma electrolysis for nanoparticles synthesis, *Ionics*, 2012, **18**, 315–327.
- 254 Q. Chen, J. Li and Y. Li, A review of plasma–liquid interactions for nanomaterial synthesis, *J. Phys. D: Appl. Phys.*, 2015, **48**, 424005.
- 255 P. Rumbach and D. B. Go, Perspectives on Plasmas in Contact with Liquids for Chemical Processing and Materials Synthesis, *Top. Catal.*, 2017, **60**, 799–811.

