

Cite this: *Chem. Sci.*, 2019, 10, 2093

All publication charges for this article have been paid for by the Royal Society of Chemistry

## Design of gradient nanopores in phenolics for ultrafast water permeation†

Leiming Guo, ‡ Yazhi Yang, Fang Xu, Qianqian Lan, Mingjie Wei † and Yong Wang †\*

Membrane technology is playing a pivotal role in providing potable water to our thirsty planet. However, the strong demand for highly permeable and durable membranes with affordable costs remains. Such membranes are synthesized herein by designing gradient nanopores in low-cost phenolics. The gradient nanopores are achieved by spontaneous assembly of phenolic nanoparticles with gradually enlarged sizes. These particles nucleate and grow as a result of ZnCl<sub>2</sub>-accelerated thermopolymerization of resol in the progressive downward gelating polymer. Subsequent removal of the gelled polymer and ZnCl<sub>2</sub> exposes the gradient nanopores. The gradient nanopores endow the phenolic structures with unprecedented permselectivity when used in membrane separation, totally rejecting fine particulates down to 5 nm dispersed in water or aggressive solvents while allowing water to permeate up to two orders of magnitude faster than other membranes with similar rejections. Our work opens up an avenue for the rational design and affordable synthesis of ultrafast membranes.

Received 8th July 2018  
Accepted 11th December 2018

DOI: 10.1039/c8sc03012j

rsc.li/chemical-science

### Introduction

Over 1.8 billion people globally use contaminated sources of drinking water.<sup>1</sup> As a result, to produce clean and safe water, purification technologies have been extensively used.<sup>2</sup> As an energy-efficient, easy-to-operate technology with small footprints, membrane separation is ubiquitous nowadays and becoming indispensable in various processes for water purification.<sup>3</sup> Membranes are designed to discriminate ions, organic molecules (*e.g.*, antibodies), viruses, bacteria, or colloids from water by regulating the pore size and shape and pore wall chemistry, *etc.*<sup>4</sup> Ideally, membranes are desired to completely reject contaminants while allowing water to pass at lowest resistance, thus further reducing energy consumption and running costs. To this end, tremendous efforts have been made to design new membranes with enhanced water permeabilities with no or little sacrifice of selectivity.<sup>5–8</sup>

From the Hagen–Poiseuille equation which correlates the structural parameters of porous membranes with permeability ( $P$ ),<sup>9</sup>

$$P = \pi(R^4 \Delta P) / (8\eta L) \quad (1)$$

it can be understood that the thickness ( $L$ ) of the selective layer of the membrane should be minimized to increase the permeability. However, the selective layer also needs to be mechanically robust to withstand the pressure that drives the separation across the membrane. Therefore, asymmetric structures with a thin selective layer on top of a mechanically strong substrate are predominantly applied for membrane separation.<sup>10–13</sup>

Thin-film composite reverse osmosis (RO) membranes are best known for their asymmetric structures.<sup>14</sup> Interfacial polymerization is *in situ* performed on the surface of the polysulfone ultrafiltration (UF) membrane, producing a tight polyamide layer with a thickness of ~100–400 nm on the UF substrate.<sup>15,16</sup> The thus-produced composite membranes are capable of rejecting ions from water. Recently, the bi-layered composite configuration is receiving new attention. A number of nanomaterials including nanoparticles, nanofibers, and two-dimensional materials, for example, graphene oxides,<sup>17</sup> MXene,<sup>8</sup> and C<sub>3</sub>N<sub>4</sub>,<sup>18</sup> have been assembled on the surface of macroporous substrates to form nanoporous layers with a thickness down to a few tens of nanometers. The composite membranes with the selective layers established from low-dimensional building blocks have shown impressively high water permeability while maintaining good selectivity. Unfortunately, the high costs, cumbersome processing, and problematic stability may significantly limit the scalability and real-world applications of these membranes. Therefore, in the ever-straining situation of global water scarcity, the synthesis of

State Key Laboratory of Materials-Oriented Chemical Engineering, Jiangsu National Synergetic Innovation Center for Advanced Materials, College of Chemical Engineering, Nanjing Tech University, Nanjing 210009, Jiangsu, China. E-mail: yongwang@njtech.edu.cn

† Electronic supplementary information (ESI) available: Experimental details and additional characterization (macroscale photographs, SEM images, *etc.*) of phenolic materials prepared under different conditions, and comparison in terms of permeance and BSA and Cyt.c rejections between the phenolic membranes prepared in this work and other membranes. See DOI: 10.1039/c8sc03012j

‡ Present address: Institut für Chemie neuer Materialien, Universität Osnabrück, Barbarastr. 7, 49069 Osnabrück, Germany.



ultra-permeable and robust membranes with tight selectivities from affordable raw materials through simple and efficient processes remains in high demand.

To meet this demand, attention should also be paid to low-cost and easily available materials. Phenolic resins have long been used in many different fields because of their low cost and superior chemical, thermal, and mechanical robustness.<sup>19</sup> Moreover, a number of nanostructured phenolics, including nanospheres, nanofibers, and mesoporous films, have been synthesized by adopting different precursors and controlling the polymerization process.<sup>20–22</sup> These features, all of which are desired for an ideal membrane, inspire us that phenolics are potential candidates for high-performance membranes. Unfortunately, phenolics are insoluble and infusible and therefore they cannot be processed to membranes *via* conventional methods. Alternatively, in precipitation polymerization, phenolic particles are precipitated from solution and form aggregates with certain porosity depending on the polymerization conditions. We expect that if the precipitation of phenolic particles occurs in a suitably controlled way, there might be a chance to have a well-organized assembly of phenolics with tunable porosity favoring fast mass transfer. Moreover, composite structures with a thin layer on top of a macroporous substrate have been widely used to improve the membrane permeance. And these composite structures frequently suffer from complicated preparation processes and poor interfacial adhesion between the two layers.<sup>23</sup> Therefore, the demand to develop other membrane configurations, for example, asymmetric membranes with gradient pores remains.<sup>24</sup> With increasing pore size from the top surface to the bottom, such a structure is expected to exhibit enhanced permeance while maintaining tight rejection.

Based on these considerations, we demonstrate herein the design and synthesis of phenolic-based advanced membranes by establishing a highly gradient nanoporous structure in phenolics. The precipitation polymerization of phenolics is accelerated by  $\text{ZnCl}_2$  and is coupled with the gelation of Pluronic polymer (PEO-*block*-PPO-*block*-PEO block copolymer) with the fast evaporation of the solvent. Under these conditions, phenolic nanoparticles nucleate and grow with gradually increased sizes from the top to the bottom and spontaneously assemble to form membranes with a gradient porous structure. Remarkably, the thus-produced phenolic membranes outperform not only commercial membranes (by a factor of 20–80 in terms of permeance) but also newly developed advanced membranes based on costly 2D materials. Also importantly, the phenolic membranes are selective and robust enough to completely reject fine particulates with a size down to a few nanometers dispersed either in water or in aggressive solvents. The aim of this work is to report an ultrafast membrane for water purification and also to demonstrate the unlimited potentials of low-cost materials in developing ultrafast membranes.

## Results and discussion

### The gradient structure of the phenolic membranes

To prepare the phenolic membranes, an ethanolic solution containing resol (the precursor of phenolics), Pluronic polymer

(P123) and  $\text{ZnCl}_2$  was cast on the surface of a flat substrate and evaporated at 100 °C to produce a thin film supported on the substrate (Fig. S1†). During this heat treatment, resol was thermopolymerized, and the resultant phenolic film containing P123 and  $\text{ZnCl}_2$  exhibited a dense and flat surface (Fig. S2a†). Interestingly, scanning electron microscopy (SEM) revealed that the film was composed of small particles embedded in a dense matrix (Fig. S2b†). We then soaked the phenolic film in  $\text{H}_2\text{SO}_4$  to decompose P123<sup>25</sup> and also to dissolve  $\text{ZnCl}_2$ , producing a free-standing, flexible phenolic membrane. Fig. 1a shows the prepared membrane with a lateral size of 9 cm × 9 cm transferred onto a nonwoven polyester support. Atomic force microscopy (AFM) surface topography revealed that the membrane surface was composed of densely packed nanoparticles (Fig. 1b). In contrast, the bottom of the phenolic membrane exhibited a porous structure composed of interconnected spherical particles with a diameter of *ca.* 67 nm (Fig. 1c). The porous structure spanned the entire 10  $\mu\text{m}$ -thick membrane, demonstrating a pronounced gradient porous structure (Fig. 1d). Spherical particles with gradually increased diameters from the top to the bottom were densely assembled (Fig. 1d and e), forming a continuous skeleton of the membrane. Fig. 1f correlates the size of the phenolic particles with their depths in the membrane (the vertical distance to the top surface). The particle size was increased from  $\sim 13$  nm at a depth of  $\sim 0.1$   $\mu\text{m}$  to  $\sim 26$  nm and  $\sim 36$  nm at a depth of 0.5  $\mu\text{m}$  and 1  $\mu\text{m}$ , respectively, and was further increased to  $\sim 67$  nm at a depth of 10  $\mu\text{m}$ . If the as-synthesized phenolic film was soaked in water instead of  $\text{H}_2\text{SO}_4$ , a similar gradient porous structure

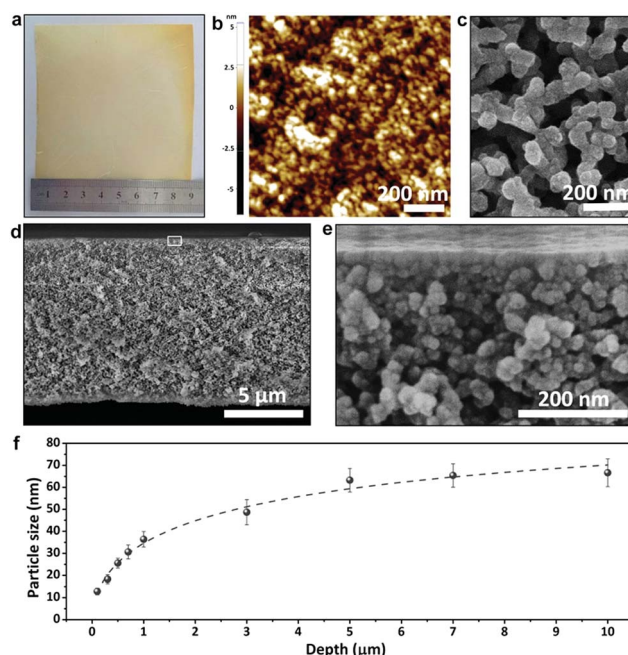


Fig. 1 Phenolic membranes with a gradient nanoporous structure. (a) The photograph of the membrane; (b) the AFM topography image of the top surface; (c) the SEM image of the bottom surface; (d) the SEM image of the cross section and (e) the enlarged image of the boxed area in (d); (f) the size of phenolic particles at different depths across the membrane.



could also be obtained (Fig. S3†). This method is also able to prepare bulk materials of gradient nanoporous phenolics with a thickness  $>100\ \mu\text{m}$  simply by increasing the volume of the casting solution. As shown in Fig. S4,† a phenolic membrane with a thickness of  $\sim 150\ \mu\text{m}$  was synthesized. The thick membrane exhibited a very pronounced gradient porous structure as the phenolic particles in the membranes were progressively enlarged from a few tens of nm near the top surface to  $\sim 500\ \text{nm}$  on the bottom side.

We tried to directly characterize the pore sizes. However, in the gradient structures, the pores are defined as gaps formed by stacking phenolic particles. These pores are interconnected with each other and do not have a measurable profile. Therefore, the sizes of such highly irregular pores cannot be estimated. Instead, the sizes of spherical phenolic particles from the top to the bottom of the membranes can be relatively easily measured, and the gaps between them are highly related to the particle sizes.

### Interplays among the components in the phenolic films

Infrared (IR) spectroscopy was applied to reveal the change in the chemical composition of the phenolic film before and after soaking in  $\text{H}_2\text{SO}_4$  or water. As shown in Fig. 2a, the broad peaks centered around  $3400\ \text{cm}^{-1}$  originate from hydroxyl groups,<sup>26</sup> and the strongest peak of the as-synthesized phenolic film is mainly contributed by water absorbed from the air as a result of

the strong hygroscopicity of  $\text{ZnCl}_2$ .<sup>27</sup> A strong peak emerged at  $1624\ \text{cm}^{-1}$  in the spectrum of the as-synthesized phenolic film, which can be attributed to the interaction between  $\text{ZnCl}_2$  and phenolic group. With the introduction of  $\text{ZnCl}_2$ , the aromatic  $\text{C}=\text{C}$  bond in the phenolic film at  $1605\ \text{cm}^{-1}$  is enhanced due to the facilitated aromatization of the phenolic film by  $\text{ZnCl}_2$  while the deoxygenation effect of  $\text{ZnCl}_2$  weakens the characteristic  $\text{C}=\text{O}$  bond of the phenolic film at  $1648\ \text{cm}^{-1}$ .<sup>28</sup> The overlap of the two neighboring peaks leads to a merged peak at  $1624\ \text{cm}^{-1}$ . After the removal of  $\text{ZnCl}_2$  by water or  $\text{H}_2\text{SO}_4$ , the merged peak is decomposed to the initial two isolated peaks at  $1605\ \text{cm}^{-1}$  and  $1648\ \text{cm}^{-1}$ . The peak of  $\text{C}-\text{O}$  stretching of P123 was reported to be located at  $1100\ \text{cm}^{-1}$ .<sup>29</sup> However, for the as-synthesized phenolic film, this peak is shifted to  $1075\ \text{cm}^{-1}$  as a result of the complexation of  $\text{Zn}^{2+}$  to P123.<sup>30</sup> After complete removal of  $\text{ZnCl}_2$  by water, the peak recovers from  $1075\ \text{cm}^{-1}$  to  $1100\ \text{cm}^{-1}$ . Moreover, a peak at  $1100\ \text{cm}^{-1}$  shows up with a weaker intensity for the water-soaked sample, indicating that P123 was only partially removed by water. In contrast, after soaking in  $\text{H}_2\text{SO}_4$ , the peak disappears, indicating the complete removal of P123.

X-ray photoelectron spectroscopy (XPS) was further used to analyze the phenolic films before and after soaking. Zinc and chlorine elements are distributed on the surface of the as-synthesized phenolic film but absent in the water- and acid-treated films (Fig. 2b), confirming again that both water and  $\text{H}_2\text{SO}_4$  are able to completely remove  $\text{ZnCl}_2$  from the phenolic films. The peak around  $533\ \text{eV}$  originates from  $\text{C}-\text{OH}$  of phenolic and ether groups of P123<sup>31</sup> and exhibits stronger intensity after soaking in water. This is due to the removal of  $\text{ZnCl}_2$ , releasing some coordinated  $-\text{OH}$  groups. The strong peak of this group is also achieved for the  $\text{H}_2\text{SO}_4$ -soaked film (Fig. 2c). However, this peak is weaker compared to that of the water-soaked film. Generally, abundant  $-\text{OH}$  groups are able to be generated in the phenolic film by  $\text{H}_2\text{SO}_4$ , which can improve the surface hydrophilicity of the phenolic films. To demonstrate this, water contact angles were further determined to be  $83^\circ$ ,  $65^\circ$ , and  $41^\circ$  for the as-synthesized phenolic film and the film after soaking in water and  $\text{H}_2\text{SO}_4$ , respectively. It should be noted that the complete decomposition of ether groups of P123 by  $\text{H}_2\text{SO}_4$  leads to a weakened O peak in the spectrum of the acid-treated film although the excessive  $-\text{OH}$  groups can be produced by  $\text{H}_2\text{SO}_4$ . Moreover, the peaks at  $284.8$  and  $286.8\ \text{eV}$  are attributed to the carbon atoms of formaldehyde after cross-linking<sup>32</sup> and ester species ( $^*\text{C}-\text{O}-\text{C}=\text{O}$ ) of the phenolic film<sup>33</sup> in the C 1s spectra, respectively (Fig. 2d). As  $\text{H}_2\text{SO}_4$  is capable of removing the oligomeric phenolic group and further facilitating the crosslinking of phenolics at  $100\ ^\circ\text{C}$ , the  $\text{H}_2\text{SO}_4$ -soaked film exhibits the strongest peak around  $284.8\ \text{eV}$  among all the samples. Meanwhile, the degradation of ester bonds takes place in  $\text{H}_2\text{SO}_4$  at high temperature, resulting in the lowest peak intensity of around  $286.5\ \text{eV}$  for the  $\text{H}_2\text{SO}_4$ -soaked film.

### Mechanism for the development of the gradient structure

We carried out molecular dynamics (MD) simulations to investigate the diffusion and reactions of resol molecules under fast evaporation conditions. We changed the concentrations of



Fig. 2 The chemical composition of the phenolic film before (red curve) and after soaking in water (blue curve) or  $\text{H}_2\text{SO}_4$  (black curve). (a) IR spectra, (b) wide-scan XPS spectra, and the corresponding enlarged spectra of (c) O and (d) C.






solutes (P123 and resol with a fixed molar ratio) to describe the progressive evaporation of ethanol. The concentration of solutes was progressively decreased from the top surface to the bottom with the top surface having a 100% concentration. Fig. 3a shows four snapshots from simulations with the concentration of solutes decreasing from 100% to 40%, which depict the state of the compositions at sections with increasing depths in the evaporating solution. We investigated the diffusivity of resol in solution with various concentrations by simulating the change in its mean square displacements (MSDs) with time. As revealed by Fig. 3b, higher concentrations of solutes lead to smaller slopes of the MSD–time plots, indicating lower diffusivity of resol molecules. In the extreme case with a concentration of 100%, resol totally loses its diffusivity, corresponding to the frozen state in which the polymerization of resol is completely terminated. Fig. 3c exhibits the number of other resol molecules being collided with one certain resol molecule within 10 ns, which is an indicator of the rate of resol thermopolymerization leading to the formation of phenolic particles. In the presence of P123, every resol molecule collides with a smaller number of other resol molecules with increasing concentration of solutes. With lower concentrations, because of the higher diffusivity as discussed above, resol molecules can penetrate through the surrounding P123 chains and collide with more other resol molecules, producing larger phenolic particles. In contrast, higher solute concentrations lead to smaller phenolic particles. That is to say, phenolic particles are progressively enlarged with increasing depths in the film, consistent with our experimental observations. Moreover, simulations of the collision of resol molecules in the absence of P123 show that the numbers of collided resol molecules remain almost constant under different concentrations, clearly indicating the strong suppression of the diffusion of resol into P123. In addition, the numbers of hydrogen bonds between P123 and resol increase with the concentration of solutes (Fig. 3d). This means that with the evaporation of ethanol, the interaction between P123 and resol is enhanced, thus weakening the diffusion of resol and consequently the growth of phenolic

particles. Note that, for simplicity,  $\text{ZnCl}_2$  was not included in the simulation systems, and this simplification does not influence the reliability of the simulated results because  $\text{ZnCl}_2$ , as a small molecule, would not evidently change the relative diffusivity and collision of solute molecules.


Simulations reveal the influence of the solute concentrations on the diffusivity and collision of resol molecules, which helps to elucidate the mechanism for the formation of the gradient structure. At a temperature of 100 °C, thermopolymerization of resol in the solution takes place, producing phenolic polymers with a crosslinking structure.<sup>28</sup> Phenolics are not soluble in ethanol and tend to nucleate in solution as primary particles (Fig. 4a and b). At such a high temperature, ethanol evaporates very fast, and the evaporation starts from the surface of the solution. This leads to the gelation of P123, which also starts from the solution surface and propagates to the interior of the solution. The phenolic particles are, therefore, “frozen” in the gelled surface and no longer grow because unreacted resol molecules are also trapped and cannot diffuse to come into contact with the phenolic nucleates within a reasonable time-frame (which is actually due to the interruption of the supply of resol). However, ethanol in the interior of the solution takes longer time to evaporate and the diffusion of resol there is less suppressed, allowing phenolic nucleates to grow with the continuous supply of resol until being frozen by gelled P123 (Fig. 4c and d). Therefore, phenolic particles with increasing sizes from the top surface to the bottom side are formed in the finally obtained structure, producing a composite film with a superstructure of aggregated phenolic particles embedded in P123 (Fig. S2b†). In the subsequent soaking in  $\text{H}_2\text{SO}_4$ , both P123 and  $\text{ZnCl}_2$  are removed, leaving behind the network composed of interconnected phenolic particles as a nanoporous membrane with gaps among the particles as the pores tapered from the bottom side to the top side (Fig. 4e).

### Separation performance of the phenolic membranes

The produced phenolics feature a gradient nanoporous structure, which is highly desired in membrane separation because it

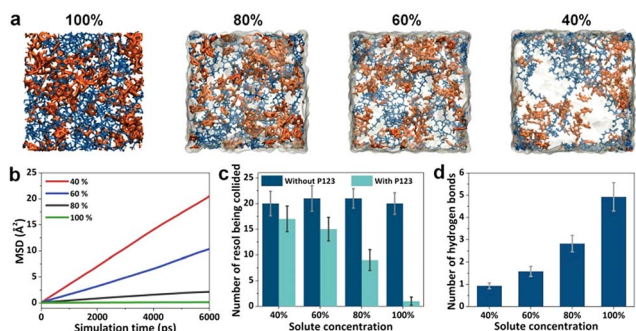

**Fig. 3** Simulations of the diffusivity and collision of resol molecules. (a) Snapshots of simulation systems with the concentration of solutes decreasing from 100% to 40%. Blue, orange, and transparent grey represent P123, resol, and ethanol, respectively; (b) mean square displacement of the resol molecules; (c) the number of other resol molecules that could be collided by a certain resol molecule; (d) the number of hydrogen bonds between resol molecules and P123.

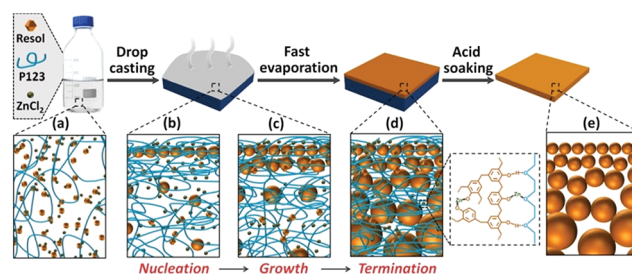

**Fig. 4** Illustration of the formation of the gradient nanoporous phenolics. (a) Casting the ethanolic solution of resol, P123 and  $\text{ZnCl}_2$  onto the substrate; (b and c) heating initiated the thermopolymerization of resol and gelation of P123 with the fast evaporation of ethanol, leading to the nucleation (b) and growth (c) of phenolic nanoparticles; (d) the phenolic particles were frozen in the gelled P123 with the complete evaporation of ethanol and the growth was terminated; (e) the gradient nanoporous structure was produced by removing P123 and  $\text{ZnCl}_2$  with  $\text{H}_2\text{SO}_4$ .



promises fast permeation at little cost of separation selectivity. The phenolic membrane with a thickness of  $\sim 10\ \mu\text{m}$  was robust enough to be used in pressure-driven filtration. The water permeance of the water-soaked membrane was as small as  $1.9\ \text{L bar}^{-1}\ \text{m}^{-2}\ \text{h}^{-1}$ . This should be ascribed to the incomplete removal of P123 from the gaps among the phenolic particles, especially in the top layer. In contrast, the membrane prepared by soaking in  $\text{H}_2\text{SO}_4$  exhibited a permeance of  $\sim 1547\ \text{L bar}^{-1}\ \text{m}^{-2}\ \text{h}^{-1}$ , and its rejections to bovine serum albumin (BSA,  $M_w = 66\ \text{kDa}$ ) and cytochrome C (Cyt.c,  $M_w = 12.4\ \text{kDa}$ ) were measured to be 96% and 95%, respectively (Fig. 5a). As the size of BSA and Cyt.c is  $14\ \text{nm} \times 3.8\ \text{nm} \times 3.8\ \text{nm}$ <sup>34</sup> and  $3.8\ \text{nm} \times 2.5\ \text{nm} \times 2.5\ \text{nm}$ ,<sup>6</sup> respectively, the effective diameter of the pores on the top surface of this phenolic membrane can be estimated to be  $<4\ \text{nm}$ . Furthermore, the molecular weight cut-off (MWCO) of the membrane, which is defined as the equivalent molecular weight of the smallest solute that would exhibit 90% rejection, was determined to be 12.2k Da.

Like other polymeric membranes, there is also a flux decline for the gradient phenolic membranes due to structure compression during filtration. However, as shown in Fig. S5,† a steady permeance can be achieved within 15 min of operation. Moreover, the steady permeance accounts for more than 80% of the initial value. Therefore, the gradient phenolic membranes are relatively stable at the operation pressure investigated here.

We compared the phenolic membranes with gradient porosities prepared in this work with other membranes prepared from different materials ranging from conventional

polymers to newly emerged 2D materials. Strikingly, although the phenolic membranes were prepared from cheap materials through a relatively convenient process, they exhibit  $\sim 20$  to 80 times higher water permeabilities than typical commercial UF membranes with a nominated MWCO of 10 or 20k Da (water permeance  $\sim 20\text{--}70\ \text{L bar}^{-1}\ \text{m}^{-2}\ \text{h}^{-1}$ ).<sup>35</sup> Moreover, compared to newly developed membranes based on costly 2D building blocks, for example, graphene oxide,  $\text{WS}_2$ , and MXene, our phenolic membranes with gradient porosities also show  $\sim 1.5\text{--}6$  times higher permeabilities and similar rejections (Fig. 5b and Table S1†).

Phenolics possess a crosslinked structure with outstanding thermal and chemical stability, implying that the phenolic membranes have great potential to be used under harsh conditions, for example, in aggressive organic solvents. The phenolic membrane was used to filtrate 5 nm gold nanoparticles dispersed in toluene and dimethyl formamide (DMF) (Fig. 5c). The gold particles dispersed either in toluene or in DMF displayed a pink color and exhibited an absorption peak around 539 nm. After filtration, the collected permeates were colorless in both cases and there were no noticeable absorption peaks in the UV-vis spectra (Fig. 5d and e). It should be noted that no damage occurred to the membranes during the course of filtration, and no adsorption of gold particles on the membrane was observed. Therefore, we conclude that the phenolic membranes are robust enough to tolerate both nonpolar and polar organic solvents and are able to reject fine particles as small as 5 nm.

### Tunability of the gradient structures and the separation performances

Fast evaporation of the solvent during the thermopolymerization of resol is essential for the formation of increasingly enlarged phenolic particles. The growth of phenolic nucleates is dependent on the availability of resol molecules which is determined by the gelating state of P123. Moreover, the gelation of P123 is caused by the evaporation of the solvent. If the resol solution was controlled to be slowly evaporated at  $20\ ^\circ\text{C}$  and then subjected to thermopolymerization at  $100\ ^\circ\text{C}$ , in which the gelation of P123 was finished before thermopolymerization, the structure obtained after  $\text{H}_2\text{SO}_4$  soaking was a homogenous film composed of small phenolic particles without a noticeable gradient porous structure (Fig. S6†). In the gelled P123 matrix, resol molecules are trapped and molecular diffusion can only occur within a very local and limited range even at a temperature of  $100\ ^\circ\text{C}$ . As a result, adjacent resol molecules are locally polymerized, forming small phenolic particles which do not grow because of the termination of the supply of resol.

Both  $\text{ZnCl}_2$  and P123 play critical roles in the synthesis of the gradient nanoporous phenolics.  $\text{ZnCl}_2$  stabilizes the two polymers, the phenolic film and P123, to prevent uncontrolled macrophase separation and also accelerates the thermopolymerization process to enable fast nucleation of phenolics before the termination of resol supply by the gelating P123. P123 provides a gelating environment to control the growth of the phenolic nucleates. Syntheses without either  $\text{ZnCl}_2$  or P123

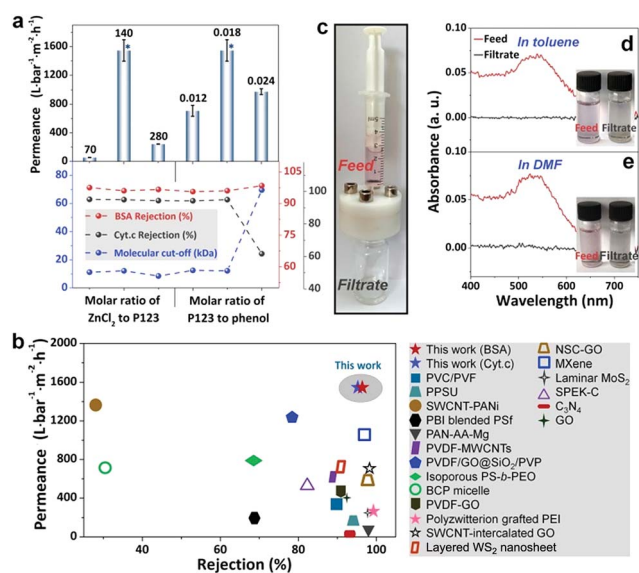


Fig. 5 Separation performance of the phenolic membranes. (a) The permeance, rejections to BSA and Cyt.c and MWCOs of the membranes prepared with different compositions in the resol solution. The performances marked with asterisks are acquired from the same membranes; (b) comparison of the phenolic membrane prepared under the optimized conditions with other membranes in terms of rejection and water permeance; (c) the filtration module for separating 5 nm gold nanoparticles in organic solvents; (d, e) the UV-vis spectra of the feeds and filtrates involved in the separation of 5 nm gold nanoparticles in (d) toluene and (e) DMF.







much ZnCl<sub>2</sub> made the membrane fragile, and both are adverse for reliable membrane separation.

## Conclusions

In summary, gradient nanopores are produced by controlling the thermopolymerization of resol in the mixture of Pluronic polymer (P123) and ZnCl<sub>2</sub>. With the fast evaporation of the solvent, the ZnCl<sub>2</sub>-accelerated thermopolymerization of resol induces the nucleation of phenolics as nanoparticles. They continue to grow until the gelating P123 terminates the supply of resol, thus forming phenolic nanoparticles with increasing sizes from the top to the bottom. These phenolic particles further assemble to form a network with the stabilization effect of P123 and ZnCl<sub>2</sub>. After removal of P123 and ZnCl<sub>2</sub>, phenolics with a gradient nanoporous structure are formed. The thus-produced phenolic structures exhibit unprecedented separation performances when used as membranes. They show ~20–80 times higher water permeance than commercial membranes with similar rejections. Impressively, they also greatly outperform membranes based on expensive 2D materials by a factor of ~1.5–6 in terms of water permeance while their selectivities being comparable. Furthermore, the phenolic membranes are robust enough to operate in aggressive organic solvents. Such a gradient nanoporous structure combined with excellent chemical and thermal stability makes the thus-produced phenolic superstructures an exciting candidate for applications in other areas including batteries, supercapacitors, catalysis, etc.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

Financial support from the National Basic Research Program of China (2015CB655301), the Natural Science Foundation of China (21776126), and the Jiangsu Natural Science Foundation (BK20150944, BK20150063) is acknowledged. We are grateful to the National Supercomputing Center in Wuxi (Sunway Taihu Light) for providing the computational resources. We also thank the Program of Excellent Innovation Teams of Jiangsu Higher Education Institutions and the Project of Priority Academic Program Development of Jiangsu Higher Education Institutions (PAPD) for support.

## Notes and references

- 1 <http://www.un.org/sustainabledevelopment/water-and-sanitation/>.
- 2 J. R. Werber, C. O. Osuji and M. Elimelech, Materials for Next-Generation Desalination and Water Purification Membranes, *Nat. Rev. Mater.*, 2016, **1**, 16018–16034.
- 3 S. Ling, Z. Qin, W. Huang, S. Cao, D. L. Kaplan and M. J. Buehler, Design and Function of Biomimetic Multilayer Water Purification Membranes, *Sci. Adv.*, 2017, **3**, e1601939.
- 4 A. Lee, J. W. Elam and S. B. Darling, Membrane Materials for Water Purification: Design, Development, and Application, *Environ. Sci.: Water Res. Technol.*, 2016, **2**, 17–42.
- 5 K.-V. Peinemann, V. Abetza and P. F. Simon, Asymmetric Superstructure Formed in A Block Copolymer *via* Phase Separation, *Nat. Mater.*, 2007, **6**, 992–996.
- 6 X. Peng, J. Jin, Y. Nakamura, T. Ohno and I. Ichinose, Ultrafast Permeation of Water Through Protein-Based Membranes, *Nat. Nanotechnol.*, 2009, **4**, 353–357.
- 7 S. Kandambeth, B. P. Biswal, H. D. Chaudhari, K. C. Rout, H. S. Kunjattu, S. Mitra, S. Karak, A. Das, R. Mukherjee, U. K. Kharul and R. Banerjee, Selective Molecular Sieving in Self-Standing Porous Covalent-Organic-Framework Membranes, *Adv. Mater.*, 2017, **29**, 1603945–1603953.
- 8 L. Ding, Y. Wei, Y. Wang, H. Chen, J. Caro and H. Wang, A Two-Dimensional Lamellar Membrane: Mxene Nanosheet Stacks, *Angew. Chem., Int. Ed.*, 2017, **56**, 1825–1829.
- 9 J. P. Robinson, E. S. Tarleton, C. R. Millington and A. Nijmeijer, Solvent Flux Through Dense Polymeric Nanofiltration Membranes, *J. Membr. Sci.*, 2004, **230**, 29–37.
- 10 W. A. Phillip, B. O'Neill, M. Rodwogin, M. A. Hillmyer and E. L. Cussler, Self-Assembled Block Copolymer Thin Films as Water Filtration Membranes, *ACS Appl. Mater. Interfaces*, 2010, **2**, 847–853.
- 11 S. E. Querelle, E. A. Jackson, E. L. Cussler and M. A. Hillmyer, Ultrafiltration Membranes with A Thin Poly(styrene)-*b*-Poly(isoprene) Selective Layer, *ACS Appl. Mater. Interfaces*, 2013, **5**, 5044–5050.
- 12 K. Sankhala, J. Koll, M. Radjabian, U. A. Handge and V. Abetz, A Pathway to Fabricate Hollow Fiber Membranes with Isoporous Inner Surface, *Adv. Mater. Interfaces*, 2017, **4**, 1600991–1600994.
- 13 L. Guo and Y. Wang, Nanoslitting of Phase-Separated Block Copolymers by Solvent Swelling for Membranes with Ultrahigh Flux and Sharp Selectivity, *Chem. Commun.*, 2014, **50**, 12022–12025.
- 14 C. Fritzmann, J. Löwenberg, T. Wintgens and T. Melin, State-of-the-Art of Reverse Osmosis Desalination, *Desalination*, 2007, **216**, 1–76.
- 15 A. K. Ghosh and E. M. V. Hoek, Impacts of Support Membrane Structure and Chemistry on Polyamide-Polysulfone Interfacial Composite Membranes, *J. Membr. Sci.*, 2009, **336**, 140–148.
- 16 G.-R. Xu, J.-N. Wang and C.-J. Li, Strategies for Improving the Performance of the Polyamide Thin Film Composite (PA-TFC) Reverse Osmosis (RO) Membranes: Surface Modifications and Nanoparticles Incorporations, *Desalination*, 2013, **328**, 83–100.
- 17 H. Li, Z. Song, X. Zhang, Y. Huang, S. Li, Y. Mao, H. J. Ploehn, Y. Bao and Y. Mao, Ultrathin, Molecular-Sieving Graphene Oxide Membranes for Selective Hydrogen Separation, *Science*, 2013, **342**, 95–98.
- 18 Y. Wang, L. Li, Y. Wei, J. Xue, H. Chen, L. Ding, J. Caro and H. Wang, Water Transport with Ultralow Friction Through Partially Exfoliated G-C<sub>3</sub>N<sub>4</sub> Nanosheet Membranes with



- Self-Supporting Spacers, *Angew. Chem., Int. Ed.*, 2017, **56**, 8974–8980.
- 19 K. Hirano and M. Asami, Phenolic Resins-100 Years of Progress and Their Future, *React. Funct. Polym.*, 2013, **73**, 256–269.
- 20 H. Sun, Q. Wang, H. Geng, B. Li, Y. Li, Q.-H. Wu, J. Fan and Y. Yang, Fabrication of Chiral Mesoporous Carbonaceous Nanofibers and Their Electrochemical Energy Storage, *Electrochim. Acta*, 2016, **213**, 752–760.
- 21 J. Liu, S. Qiao, H. Liu, J. Chen, A. Orpe, D. Zhao and G. Lu, Extension of the Stöber Method to the Preparation of Monodisperse Resorcinol-Formaldehyde Resin Polymer and Carbon Spheres, *Angew. Chem., Int. Ed.*, 2011, **50**, 5947–5951.
- 22 J. Zhang, Z. Qiao, S. Mahurin, X. Jiang, S. Chai, H. Lu, K. Nelson and S. Dai, Hypercrosslinked Phenolic Polymers with Well-Developed Mesoporous Frameworks, *Angew. Chem., Int. Ed.*, 2015, **54**, 4582–4586.
- 23 W. J. Lau, A. F. Ismail, N. Misdan and M. A. Kassim, A Recent Progress in Thin Film Composite Membrane: A Review, *Desalination*, 2012, **287**, 190–199.
- 24 M. Ulbricht, Advanced Functional Polymer Membranes, *Polymer*, 2006, **47**, 2217–2262.
- 25 C.-M. Yang, B. Zibrowius, W. Schmidt and F. Schüth, Consecutive Generation of Mesopores and Micropores in SBA-15, *Chem. Mater.*, 2003, **15**, 3739–3741.
- 26 Y. Meng, D. Gu, F. Zhang, Y. Shi, L. Cheng, D. Feng, Z. Wu, Z. Chen, Y. Wan, A. Stein and D. Zhao, A Family of Highly Ordered Mesoporous Polymer Resin and Carbon Structures from Organic-Organic Self-Assembly, *Chem. Mater.*, 2006, **18**, 4447–4464.
- 27 L. Ji, A. J. Medford and X. Zhang, Electrospun Polyacrylonitrile/Zinc Chloride Composite Nanofibers and Their Response to Hydrogen Sulfide, *Polymer*, 2009, **50**, 605–612.
- 28 Z.-L. Yu, G.-C. Li, N. Fechner, N. Yang, Z.-Y. Ma, X. Wang, M. Antonietti and S.-H. Yu, Polymerization under Hypersaline Conditions: A Robust Route to Phenolic Polymer-Derived Carbon Aerogels, *Angew. Chem., Int. Ed.*, 2016, **55**, 14623–14627.
- 29 X. Zhuang, X. Qian, J. Lv and Y. Wan, An Alternative Method to Remove PEO-PPO-PEO Template in Organic-Inorganic Mesoporous Nanocomposites by Sulfuric Acid Extraction, *Appl. Surf. Sci.*, 2010, **256**, 5343–5348.
- 30 Z. Wang, M. Wang, G. Wu, D. Wu and A. Wu, Colorimetric Detection of Copper and Efficient Removal of Heavy Metal Ions from Water by Diamine-Functionalized SBA-15, *Dalton Trans.*, 2014, **43**, 8461–8468.
- 31 J. Goworek, A. Świątkowski and S. Biniak, Characterization of Modified Active Carbons by Adsorption of Pure Water and Benzene Vapors and Ternary Liquid Mixture Benzene + Diethyl Ketone + N-Heptane, *Langmuir*, 1997, **13**, 1225–1228.
- 32 T. Kimura, A. M. Emre, K. Kato and Y. Hayashi, Phenol Resin Carbonized Films with Anisotropic Shrinkage Driven Ordered Mesoporous Structures, *J. Mater. Chem. A*, 2013, **1**, 15135–15141.
- 33 Y. Nabae, M. Sonoda, C. Yamauchi, Y. Hosaka, A. Isoda and T. Aoki, Highly Durable Pt-Free Fuel Cell Catalysts Prepared by Multi-Step Pyrolysis of Fe Phthalocyanine and Phenolic Resin, *Catal. Sci. Technol.*, 2014, **4**, 1400–1406.
- 34 X. Qiu, H. Yu, M. Karunakaran, N. Pradeep, S. P. Nunes and K.-V. Peinemann, Selective Separation of Similarly Sized Proteins with Tunable Nanoporous Block Copolymer Membranes, *ACS Nano*, 2013, **7**, 768–776.
- 35 Koch ultrafiltration membranes. <http://www.kochmembrane.com/Membrane-Products/Hollow-Fiber/Ultrafiltration.aspx>.
- 36 N. Yan and Y. Wang, Reversible Switch Between the Nanoporous and the Nonporous State of Amphiphilic Block Copolymer Films Regulated by Selective Swelling, *Soft Matter*, 2015, **11**, 6927–6937.
- 37 Y. Meng, D. Gu, F. Zhang, Y. Shi, H. Yang, Z. Li, C. Yu, B. Tu and D. Zhao, Ordered Mesoporous Polymers and Homologous Carbon Frameworks: Amphiphilic Surfactant Templating and Direct Transformation, *Angew. Chem., Int. Ed.*, 2005, **44**, 7053–7059.

