


 Cite this: *RSC Adv.*, 2023, 13, 33129

# The effects of Fe, Mg, and Pt-doping on the improvement of Ni stabilized on Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalysts for methane dry reforming†

 Abbas Jawad <sup>ab</sup>

Herein, the promotional effects of Mg, Fe, and Pt on Ni-based catalysts supported on Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> (Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>) were investigated in the dry reforming of methane (DRM) reaction. The interaction of a suitable amount of MgO and FeO with Ce<sub>2</sub>O<sub>3</sub> stabilized in the catalysts was demonstrated by the temperature-programmed desorption of CO<sub>2</sub> (CO<sub>2</sub>-TPD). Ce<sub>2</sub>O<sub>3</sub> has a high basicity for adsorbing CO<sub>2</sub>, generating a monoclinic Ce<sub>2</sub>O<sub>2</sub>CO<sub>3</sub> species in the DRM reaction. Surface oxygen ions were also produced by adding MgO and FeO, as demonstrated by the temperature-programmed reduction of H<sub>2</sub> (H<sub>2</sub>-TPR). Monoclinic Ce<sub>2</sub>O<sub>2</sub>CO<sub>3</sub> and surface oxygen may both be used to oxidize and remove the carbon that was deposited, maintaining the high activity and stability of the metal Ni and Pt catalysts. The high dispersion and synergistic interactions between the platinum and oxide phases, which are associated with the decrease in reduction temperature and the rise in the number of basic sites, are responsible for the increased activity of Pt with M-Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts. The co-doped Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts with Mg and Fe significantly enhanced the activity (more than 80% methane and 84% CO<sub>2</sub> conversion), the selectivity toward syngas (~90%), and maintained the H<sub>2</sub>/CO ratio at about 0.97 at 700 °C.

 Received 17th July 2023  
 Accepted 26th October 2023

DOI: 10.1039/d3ra04809h

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1. Introduction

The dry reforming of methane (DRM) with CO<sub>2</sub> has attracted attention because of the utilization of two major greenhouse gases (CH<sub>4</sub> and CO<sub>2</sub>) as feedstocks and provides a route for converting them into the low H<sub>2</sub>/CO ratio syngas, which can be directly used as fuel or to produce chemicals and fuels by the methanol synthesis and Fischer-Tropsch (FT) processes.<sup>1-3</sup> DRM is an endothermic reaction and is usually conducted at a very high operation temperature (>800 °C) to ensure high methane conversion and minimize carbon deposition thermodynamically.<sup>4,5</sup>

The majority of the catalysts investigated for DRM are generally made up of group VIII transition metals, such as Ni due to their high activity.<sup>6,7</sup> Promoting nickel-based catalysts with various metals, such as Mg, Fe, Zr, Cr, Ce, V, Mo, Rh, Pt, Pd, and Ru, is the most widely practiced approach for modifying DRM catalysts.<sup>7-10</sup> In particular Pt, Rh, and Ru are highly active

towards DRM, which enhances the stability against coke deposition as compared to the other non-promoted nickel-based catalysts.<sup>11,12</sup> The catalyst performance is dependent on the Ni/metal ratio and the nature of the support.<sup>6,13,14</sup> Both the promoters and support play important roles in metal electron transfer, cluster stabilization, and reducibility.<sup>15</sup> In particular, it has been shown that Ni catalysts are highly reducible in the presence of noble metals, which enables both methane combustion and reforming to occur simultaneously, thereby resulting in higher energy efficiency and improved catalytic activity.<sup>4</sup> Although noble metals are much more resistant to carbon deposition than other metal-based catalysts, they are generally uneconomical. Developing bimetallic catalysts by combining nickel with other metals is an alternative route to obtaining highly coke-resistant Ni-based catalysts for the DRM reaction.<sup>16</sup> Several studies have been dedicated to improving the Ni-based CeO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> performance and stability through the addition of second metal promoters, such as Co, Pd, and Pt. It has been confirmed that adding a trace of transition metals can modify Ni surface properties by promoting the reducibility of Ni and thus increasing the number of active sites to achieve better catalytic performance.<sup>9,17</sup> For example, several bimetallic catalysts such as Ni-Co, Ni-Pd and Ni-Pt with different supports (*e.g.*, SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub>, CeO<sub>2</sub>, MgO, TiO<sub>2</sub>, ZrO<sub>2</sub>, H-ZSM-5) have exhibited much higher activity and carbon resistance than monometallic Ni catalysts.<sup>10,18-20</sup>

<sup>a</sup>Department of Chemical & Biochemical Engineering, Missouri University of Science and Technology, 1101 N. State Street, Rolla, Missouri 65409, USA. E-mail: [ajd5d@mst.edu](mailto:ajd5d@mst.edu); [abbasajd5d@gmail.com](mailto:abbasajd5d@gmail.com)

<sup>b</sup>Midland Refineries Company MRC, AL Daura Refinery Company, Services Energy Board, Baghdad, Iraq

† Electronic supplementary information (ESI) available: Include the stability test is performed for M-Ni-based catalyst at varied temperatures (550, 650, and 700 °C) at feed containing CH<sub>4</sub>/CO<sub>2</sub> = 50/50 for 10 h. See DOI: <https://doi.org/10.1039/d3ra04809h>






2 wt% iron, and 0.005 wt% platinum for Pt/FeNi/CeO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>; 4 wt% nickel, 2 wt% iron, and 0.5 for magnesium for MgFe/Ni/CeO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>; 4 wt% nickel, 2 wt% iron, 0.5 for magnesium, and 0.005 wt% platinum for Pt/MgFe/Ni/CeO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub>.

## 2.2. Instrumental measurements

X-ray diffraction (XRD) patterns of the catalysts were obtained by a diffractometer using a PANalytical instrument operating at 30 kV and 15 mA. The XRD pattern was evaluated at a step size of 0.026° from  $2\theta = 5^\circ$  to  $90^\circ$  and a rate of  $2^\circ \text{ min}^{-1}$ . N<sub>2</sub> physisorption isotherm measurements were carried out in a Micromeritics 3Flex surface characterization analyzer at 77 K. Textural properties such as surface area, total pore volume, micropore volume, and average pore width were determined using Brunauer–Emmett–Teller (BET), Barrett–Joyner–Halenda (BJH), and *t*-plot methods, respectively. Prior to the measurements, samples were degassed at 250 °C for 6 h using a Smart VacPrep. H<sub>2</sub>-TPR measurements were carried out in a U-shaped quartz cell using a 5% vol H<sub>2</sub>/He gas with a flow rate of 50 cm<sup>3</sup> min<sup>-1</sup> at a heating rate of 10 °C min<sup>-1</sup> up to 900 °C by using a Micromeritics 3Flex analyzer. Hydrogen consumption was

followed by on-line mass spectroscopy (BELMass) and quantitative analysis was done by comparison of the reduction signal with the hydrogen consumption of a CuO reference. The temperature-programmed desorption of CO<sub>2</sub> (CO<sub>2</sub>-TPD) was performed on the same Micromeritics 3Flex analyzer. Prior to adsorption measurement, all samples were initially reduced at a temperature of 200 °C in a 5% H<sub>2</sub> in He gas mixture and held at the reduction temperature for 1 h, then cooled down to 50 °C under He. After the temperature was stabilized, the sample was exposed to 10% CO<sub>2</sub> in He for 30 min. To remove physically bound CO<sub>2</sub> from the surface, a flow of He (50 cm<sup>3</sup> min<sup>-1</sup>) for 30 min at 50 °C was used. The desorption of CO<sub>2</sub> was measured from 50 to 600 °C at a constant heating rate of 10 °C min<sup>-1</sup>. To determine the nature of surface acid sites, Fourier-transform infrared spectroscopy (FTIR) of pyridine, using a Bruker Tensor spectrophotometer, was employed to determine the types of acid sites present in the samples. All samples were activated at 450 °C for 4 h to release the moisture before the adsorption of pyridine and cooled down to 60 °C for pyridine adsorption until saturation. All the measured spectra were recalculated to a “normalized” wafer of 10 mg. For the

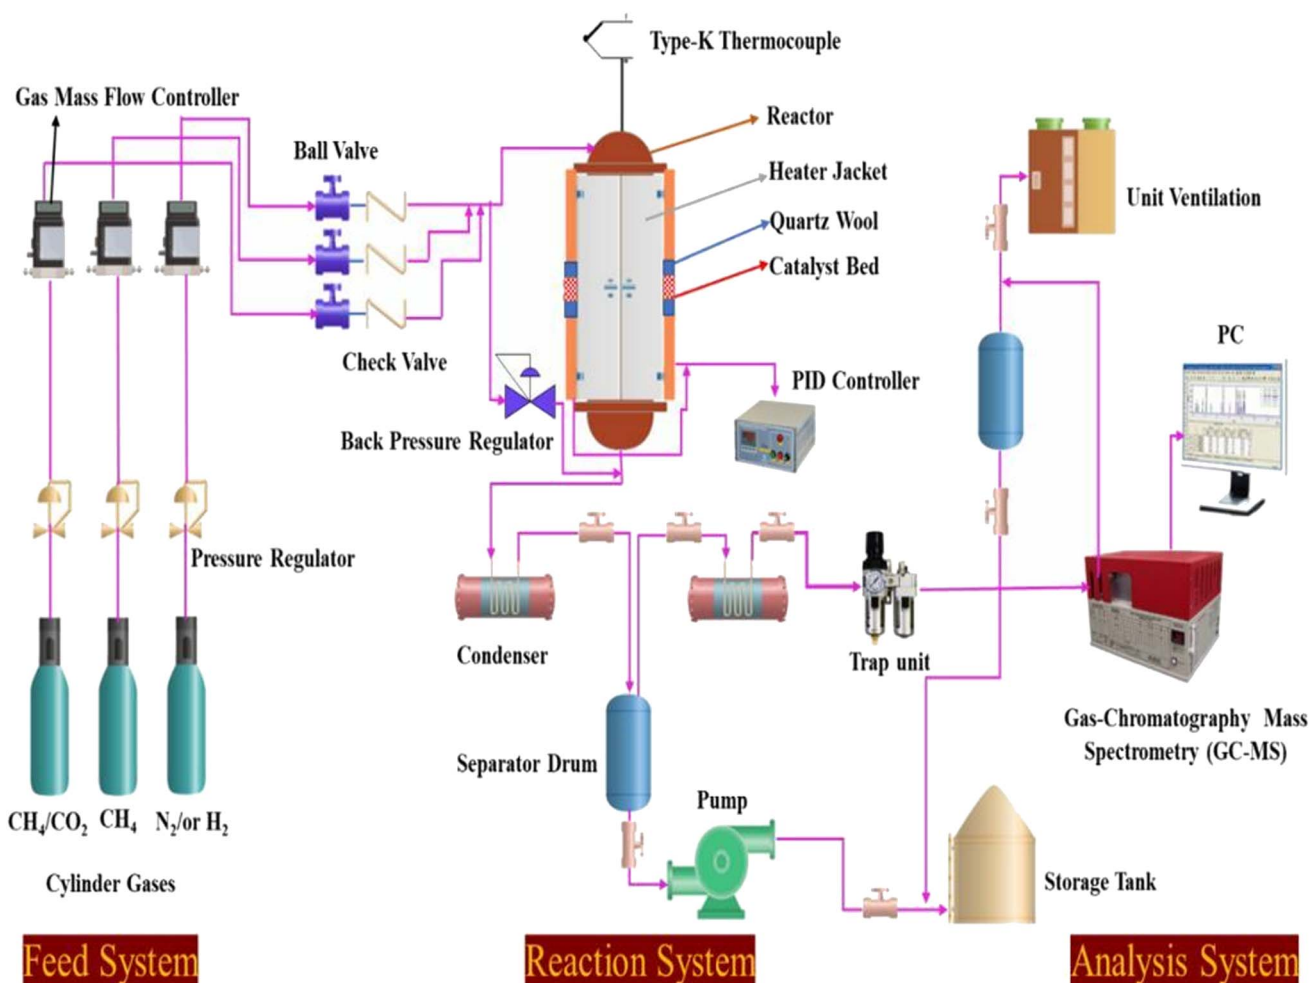

Scheme 1 Schematic diagram of the experimental setup for the dry reforming of methane.



quantitative characterization of acid sites, the bands at 1450 and 1550  $\text{cm}^{-1}$  were considered to correspond to Lewis and Brønsted sites, respectively. Furthermore, inductively coupled plasma mass spectrometry (ICP-MS) analyses were used to obtain the chemical composition of the surfaces and bulk before reaction.

### 2.3. Catalytic tests

Catalyst tests were carried out in a stainless-steel packed-bed reactor with an internal diameter of 10 mm and a length of 300 mm, as depicted in Scheme 1. The feed gas consisted of either pure  $\text{CH}_4$  or 50%  $\text{CH}_4/\text{CO}_2$  and its flow rate was controlled by a digital mass flow controller (MFC, Brooks Instrument) towards the reaction zones. For each run, about 300 mg of the sample (particle size 0.5  $\mu\text{m}$ ) was diluted with sand (particle size 0.5  $\mu\text{m}$ ) at the ratio of 1 : 6 and placed in the center of the reactor with quartz wool at both ends. Prior to the reaction, the catalyst was activated *in situ* at 500  $^\circ\text{C}$  in  $\text{H}_2$  flow for 1 h. Each catalyst was evaluated within a temperature range of 550–700  $^\circ\text{C}$  at a constant weight hourly space velocity (WHSV) of 12 000  $\text{mL g}_{\text{cat}}^{-1} \text{h}^{-1}$ . The reaction temperature was controlled by embedding a type-K thermocouple inside the catalyst center. The reactions were carried out isothermally for 10 h time-on-stream. The reaction products were analyzed online every 30 min with a gas chromatograph (SRI 8610C) equipped with a flame ionized detector (GC-FID) and thermal conductivity detector (TCD) for  $\text{H}_2$ ,  $\text{CO}_2$ ,  $\text{CO}$ ,  $\text{H}_2\text{O}$ , and hydrocarbons. The effluent line of the reactor to the GC injector was kept at 110  $^\circ\text{C}$  to avoid the potential condensation of the hydrocarbons. From Table 1, the Ni, Mg, Fe, and Pt percentages were found to be very close to the theoretical values using ICP elemental analysis, which could be due to the incomplete precipitation of the nickel, magnesium, iron, and platinum metal precursors used during the co-impregnation process.

## 3. Results and discussion

### 3.1. Characterization of the catalyst

The powder X-ray diffraction patterns for the thermally calcined Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  composite catalysts with metal additives are shown in Fig. 1. The diffraction peaks observed at  $2\theta = 28$ ,

33, 48 and 57 $^\circ$  indicate the presence of the cubic crystal structure of the  $\text{CeO}_2$  support.<sup>28</sup> All samples displayed diffraction peaks at  $2\theta = 38, 45, 67^\circ$ , which are attributed to the  $\gamma$ - $\text{Al}_2\text{O}_3$  support. Peaks were barely seen at  $2\theta = 23.5, 35$  and  $60.5^\circ$ , which can be assigned to the NiO (006), NiO (009) and NiO (110) phases, respectively. XRD signatures of MgO,  $\text{Fe}_2\text{O}_3$ , and Pt were not observed in the Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  composite catalysts. This could be due to the presence of a small amount of oxide and also the successful incorporation of these metals into the Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  structure.<sup>29</sup> As listed in Table 1, elemental analysis confirmed the presence of these metals. The average crystalline size of nickel was calculated by using the Debye-Scherrer equation (Table 1). As a function of the metal oxide(s) content, the nickel crystal size decreased from 36 to 26 nm. As a result, the crystallite size also produced oxygen vacancies, in addition to the production of oxygen vacancies mediated by dopants.<sup>30</sup> This phenomenon could be associated with the effects of the metal oxides and nickel that remained on the surface of the sample and inhibited the growth of Ni crystals. This was confirmed by the ICP elemental analysis results shown in Table 1.

The  $\text{H}_2$ -TPR profiles of the reduced Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  composite catalysts showed four well-defined reduction peaks in the range of 550–850  $^\circ\text{C}$  (Fig. 2). These reduction peaks correspond to NiO incorporated within the structure of  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$ .<sup>31</sup> The broad peak at 492–793  $^\circ\text{C}$  is associated with the bulk reduction of  $\text{Ce}^{4+}$  to  $\text{Ce}^{3+}$ .<sup>32</sup> The process of NiO reduction is thought to be a complex solid-gas reaction driven by temperature, reducing gas concentration, and the presence of additives (Mg, Fe, and Pt).<sup>33</sup> This is consistent with the findings of Manukyan *et al.*<sup>34</sup> The decrease began with the initial nucleation of Ni in the temperature range from (265 to 545  $^\circ\text{C}$ ). During this phase, Ni nuclei appeared on the outer surface of NiO particles. This gradual process eventually resulted in the formation of small channels, which began to propagate and initiate the second step of the reduction. A dominant peak was formed between 565 and 900  $^\circ\text{C}$ , indicating the second stage of reduction on the majority of the NiO and metal oxide(s) particles. The

Table 1 XRD and ICP analysis of the Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  composite catalysts

Catalysts	Metal loading <sup>a</sup> (wt%)						$D^b$ (nm)
	Al	Ce	Fe	Ni	Mg	Pt	
$\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	51.2	48.8	—	—	—	—	—
Ni/ $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	48.1	48.0	—	3.9	—	—	36
FeNi/ $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	47.1	46.8	2.1	4.0	—	—	32
Pt/FeNi/ $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	47.5	46.5	2.0	3.9	—	0.005	26
MgFe/Ni/ $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	47.0	46.8	1.9	3.8	0.5	—	33
Pt/MgFe/Ni/ $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$	47.2	46.4	2.1	3.6	0.6	0.005	27

<sup>a</sup> Determined by ICP analysis. <sup>b</sup> Estimated by the Debye-Scherrer equation for Ni (200) of XRD.

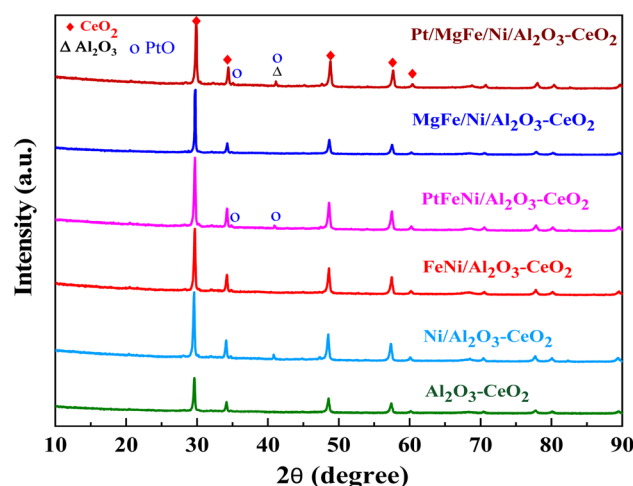


Fig. 1 XRD patterns of Ni-based  $\text{Al}_2\text{O}_3$ - $\text{CeO}_2$  composite catalysts.





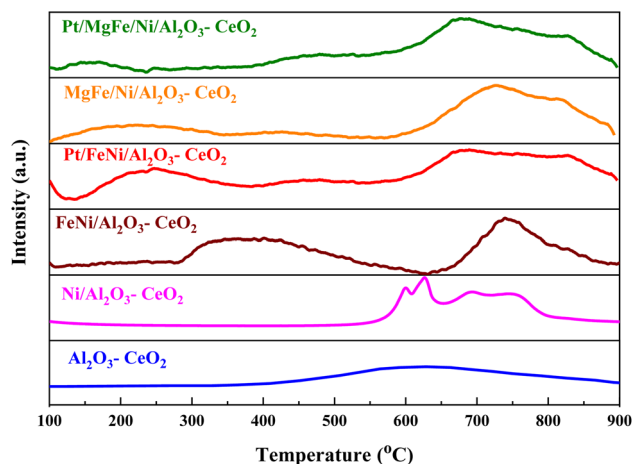


Fig. 2 H<sub>2</sub>-TPR profiles of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts.

small channels evolved into bulk NiO. Further Ni nucleation proceeded on the inner surface of these channels, resulting in the development of Ni nano-layers. The nano-layers then begin branching and interconnecting the network until the NiO phase was totally reduced to Ni.<sup>32,34,35</sup> The addition of Fe and Mg metals into the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst modified the reduction process and caused the decay of the peak connected to unbound NiO, whereas the observation was made for the Fe<sub>2</sub>O<sub>3</sub>-doped systems. It should be noted that the presence of alkaline metal oxide(s) in the catalyst had a substantial impact on the reduction behavior of the NiO catalysts. In addition to the decrease in the temperature for the ceria reduction, promoted by the presence of the Fe<sub>2</sub>O<sub>3</sub>, the supplementary reduction of Fe<sub>2</sub>O<sub>3</sub> was observed as previously reported by Wimmers *et al.*<sup>36</sup> who studied the reduction of Fe<sub>2</sub>O<sub>3</sub> and proposed a reduction in two steps, Fe<sub>2</sub>O<sub>3</sub> → Fe<sub>3</sub>O<sub>4</sub> → Fe, with no formation of FeO. For the same oxide, other authors proposed a three-step reduction process, which considered FeO formation dealing with Fe<sub>2</sub>O<sub>3</sub> → Fe<sub>3</sub>O<sub>4</sub> at about 400 °C, Fe<sub>3</sub>O<sub>4</sub> → FeO at about 600 °C and finally, FeO → Fe at higher temperatures.<sup>37</sup> Irrespective of the number of reduction steps of the Fe<sub>2</sub>O<sub>3</sub>, the separation of its reduction from that of the CeO<sub>2</sub> overlapping reduction zones is hard to achieve. However, the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst without any platinum content was reduced at a much higher temperature than catalysts with platinum. The addition of platinum to Ni particles causes easily reducible NiO particles, thereby decreasing the reduction temperature because of the strong contact between Ni and Pt. Therefore, the Pt/FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and Pt/MgFe/Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts allowed the reduction in the selectivity for carbon and reached values closer to equilibrium at lower reaction temperatures. This implies that the platinum interaction with the support also has a significant effect on increasing the reducibility of the support.<sup>38</sup> Platinum helps reduce the oxide phases through its ability to facilitate dissociative hydrogen adsorption. Hydrogen has been observed to adsorb and dissociate on the surface of the platinum, whereby it spills over to the entire surface of the support.<sup>7,17</sup> On the metallic surface, hydrogen molecules dissociate into hydrogen atoms that diffuse

to the Ni<sup>2+</sup> and can react with NiO, resulting in the uptake of the hydrogen. Nevertheless, the rate of reduction of NiO depends not only on its chemical nature but also on the nucleation process by which metallic nuclei are generated.<sup>14</sup> Compared with FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts, it can be assumed that the highly dispersed and NiO in Pt/FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> could be more easily reduced by hydrogen atoms from the spillover effect due to the unique interactions between Ni, and Pt species and served as metallic nuclei to facilitate the reduction of Fe<sup>2+</sup> and Ni<sup>2+</sup>. The Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> support plays a key role in the active site dispersion, activity and stability. To improve the reducibility, and enhance the oxygen mobility and metal dispersion, γ-Al<sub>2</sub>O<sub>3</sub> material was modified by adding CeO<sub>2</sub> and the formation of the Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> support. Further addition of metal oxide promoters improves the reducibility and chemisorption capacity of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts due to a better dispersion of bi/tri-metallic catalysts on the Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> support. The better interaction between the nickel particles and MO<sub>x</sub>-doped ceria supports could be associated with an anchoring effect inside the mesoporous structure of the support, as revealed by the textural characterization results (Fig. 5 and Table 3). It has been demonstrated that metal nanoparticles confined in mesoporous CeO<sub>2</sub> enhance the metal support interaction and, therefore, the catalytic activity.<sup>39</sup> Specifically, a stronger Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> interaction inhibits the Ni particle agglomeration and coke deposition, which leads to better stability of the catalysts in the DRM reaction.

The number of surface alkaline centers also has an important influence on the DRM process. According to prior research, surface alkaline sites can adsorb and activate CO<sub>2</sub> molecules, resulting in reactive intermediates and surface oxygen species.<sup>40</sup> The adsorbed oxygen species are active in removing the initially produced carbon deposition over time, which is beneficial for the DRM process. As a result, CO<sub>2</sub>-TPD was employed to characterize the surface alkalinity of the catalysts. The CO<sub>2</sub>-TPD results are shown in Fig. 3 and changes in the weak, moderate and strongly basic sites are presented in Table 2. The CO<sub>2</sub>-TPD profile of the samples shows weakly basic sites between 60 and 200 °C, moderately basic sites between 200 and 400 °C, and strong sites between 400 and 800 °C, respectively.<sup>27</sup> The total amount of CO<sub>2</sub> was estimated from the integration of the CO<sub>2</sub>-TPD peak area desorbed, which obviously increased with the addition of metal oxides as compared to Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. Typically, it was reported that the peak below 200 °C was attributed to the desorption of CO<sub>2</sub> on the weakly alkaline sites. Due to its easy desorption, this part of adsorbed CO<sub>2</sub> could have a limited contribution to the reaction. The CO<sub>2</sub> adsorbed on strongly basic sites was desorbed at high temperatures.<sup>27</sup> As a result, the CO<sub>2</sub> desorption peak area improved significantly at higher temperatures, indicating that the amount of adsorbed/desorbed CO<sub>2</sub> was increased at 550 °C, which is in the range of the reaction temperature and favorable for improving the reactivity.

Koo *et al.*<sup>41</sup> reported that besides weak basic sites, moderate basic sites, and strong basic sites are favorable for depressing the coke formation in MgO-promoted Ni catalysts. In our study,



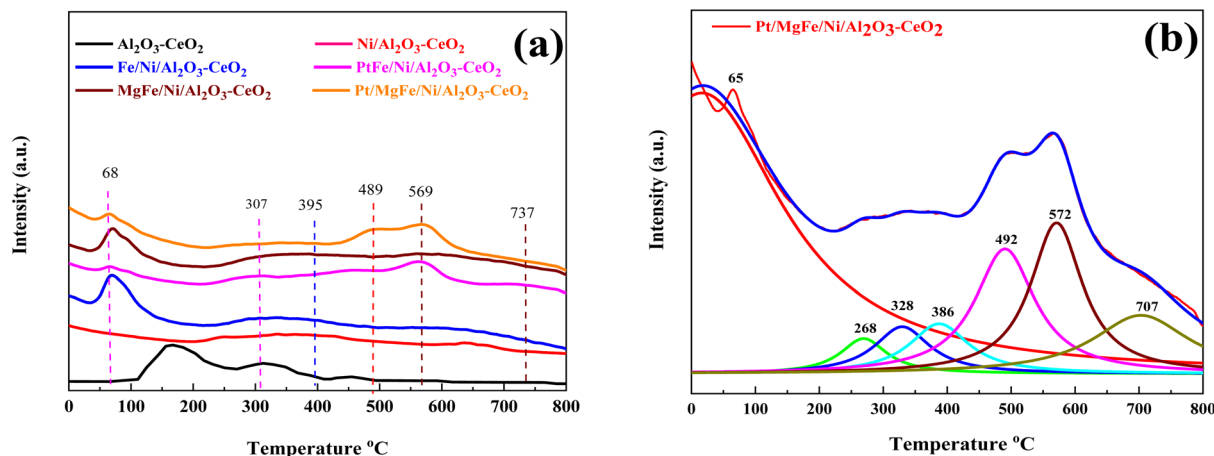


Fig. 3 CO<sub>2</sub>-TPD profiles of (a) Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. (b) The fine structure of the Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts.

Table 2 Summary of CO<sub>2</sub>-TPD of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts

Catalysts	CO <sub>2</sub> desorption <sup>a</sup> (mmol g <sup>-1</sup> )			
	60–200 °C	200–400 °C	400–800 °C	Total
Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.11	0.15	0.09	0.35
Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	—	0.34	0.11	0.45
FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.39	0.08	0.58	1.04
Pt/FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.03	0.26	1.25	1.54
MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.32	0.11	0.71	1.14
Pt/MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.08	0.30	2.15	2.53

<sup>a</sup> The amount and strength of base sites were estimated from CO<sub>2</sub>-TPD profiles.

the catalysts promoted with MO<sub>x</sub> have weak, moderate and strong basic sites, whereas Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts have only weak and moderate basic sites. Therefore, the intensity of TPD peaks became higher, indicating the improved CO<sub>2</sub> adsorption capacity. The higher adsorption of acidic CO<sub>2</sub> over the surfaces of the MO<sub>x</sub>-promoted catalysts confirmed that these catalysts are more basic as compared to Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. It is well-established that the basic catalysts could improve the adsorption of CO<sub>2</sub> during the DRM reaction, which supplies the surface oxygen to suppress the coke deposition. This finding is in agreement with previous studies.<sup>41,42</sup> It can be concluded that the Mg<sup>2+</sup>-containing supports have an increased number of basic sites (greater amount of desorbed CO<sub>2</sub>) with respect to the support. Notably, Mg-containing zirconias showed more basic sites as compared to Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. Similar results over magnesia–zirconia oxides were reported by Moreno *et al.*<sup>43</sup> Moreover, it was observed that Pt/FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts doped with Pt showed high basicity as compared to FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. This is attributed to the increased basicity of the catalysts, which in turn increased the rate of activation of mildly acidic CO<sub>2</sub> and hence assisted in the oxidation of surface carbon and increased the catalyst resistance to deactivation.<sup>7</sup> Compared to

M–Ni tri/bimetallic catalysts, Pt-modified M–Ni tri/bimetallic catalysts greatly increased the contribution of CO<sub>2</sub> deoxidation, and the excellent Pt deposition over M–Ni tri/bimetallic catalysts can be used to explain this, allowing oxygen to diffuse from the metal or support to the Pt<sup>0</sup> in a process known as “reverse oxygen spillover”. This produces PtO and an increase in the concentration of the metal oxide(s) ions, which are the active sites for CO<sub>2</sub> reduction.<sup>44</sup> The PtO was detected by XRD (Fig. 1), which was proven by previous research.<sup>45</sup> Eventually, the catalyst was provided with active oxygen species that suppressed carbon deposition, followed by catalyst deactivation.

Three desorption peaks centered around 395, 489, and 569 °C were also observed for all the catalysts despite the latter two peaks overlapping. The strength of the overlapped peaks was closely related to the addition of the metal oxides. These three peaks might be related to the strongly chemisorbed CO<sub>2</sub>. To meticulously investigate these TPD profiles, the Lorentz mathematical model was used to resolve the overlapped desorption peaks. For example, as shown in Fig. 3b, four distinct desorption peaks centered at 65, 268, 328, 386, 492, 572, and 707 °C were observed over the Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst. This implies that more than one type of basic centers with different intensities existed in the mesoporous framework of the Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalyst. Overall, the categories of the basic centers for Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts were abundant due to their own structural features as well as the promotion of the metal oxides and this is in agreement with previously reported data.<sup>46</sup>

The Brønsted and Lewis sites were found *via* the *ex situ* FTIR spectra of pyridine adsorption using a Bruker Tensor spectrophotometer. The FTIR spectra (Fig. 4 and Table 2) showed the impact of the addition of metal oxides (M = Pt, Mg, and Fe) on the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> surface acid site. One milliliter of dried pyridine was adsorbed on 30 mg of the catalyst for 14 h. The sample was dried at 120 °C for 1 h to release the loosely adsorbed pyridine from the surface of the catalyst. From that dried sample, 10 mg was taken and, to ensure homogeneity, mixed thoroughly with 200 mg of dry KBr. The mixture was then pelletized using hydraulic pressure and the FTIR spectra of the



pellets were then obtained. According to Fig. 4, an absorption band at  $1440\text{ cm}^{-1}$  or  $1434\text{ cm}^{-1}$ , which corresponds to the pyridine coordinated on Lewis acid sites on all of these catalysts, was identified in all catalysts, indicating the interaction between the pyridine and metal oxides.<sup>47</sup> The bands on these catalysts at  $1617\text{ cm}^{-1}$  and  $1596\text{ cm}^{-1}$  were attributed to pyridinium cations generated after pyridine adsorption on Brønsted acid sites and the interactions between the adsorbed pyridine and metal oxides, respectively.<sup>48,49</sup> Fig. 4 and Table 3 demonstrate that the addition of metal oxides resulted in a decrease in the creation of Lewis and Brønsted acid sites, respectively, as compared to the Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst. Conversely, it may be said that M-Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  has greater Lewis basicity than Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$ , which is the preferred material for  $\text{CO}_2$  adsorption.<sup>50</sup> As a result, the activity performance during the DRM is improved, and carbon deposition during formation is reduced.

$\text{N}_2$  physisorption isotherms of the as-prepared samples are shown in Fig. 5 with the corresponding pore size distribution shown as inset figures. All isotherms exhibited a combination of the type IV isotherm with the  $\text{H}_4$  type hysteresis loop, associated with capillary condensation, and indicated the formation of mesoporous structures in all the Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts. The BJH method was used to estimate the

pore size distributions by using the adsorption branch. Metal oxides doped Ni-based  $\text{Al}_2\text{O}_2\text{-CeO}_2$  catalysts displayed a hierarchically bi-modal porous structure with an apex of  $3.8\text{ nm}$  (Fig. 5b) and the other between  $34$  and  $38\text{ nm}$ , both of which fall within the mesoporous range; in contrast, Ni-based  $\text{Al}_2\text{O}_2\text{-CeO}_2$  and  $\text{Al}_2\text{O}_2\text{-CeO}_2$  only presented an apex. It has been established that the presence of the porous architecture in metal oxides-doped Ni-based  $\text{Al}_2\text{O}_2\text{-CeO}_2$  catalysts has a favorable influence on the improvement of catalytic activity because the connected internal voids might potentially function as efficient transport channels.<sup>30,52</sup> Table 4 summarizes the total surface area, micropore surface area, external surface area, mesopore volume pore size and diameter of Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts. For comparison, the  $\text{Al}_2\text{O}_3\text{-CeO}_2$  powder was also measured. The surface areas of  $\text{Al}_2\text{O}_3\text{-CeO}_2$ , Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$  and Pt/MgFe/Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$  were found to be  $92$ ,  $86$ , and  $76\text{ cm}^2\text{ g}^{-1}$ , respectively, suggesting that the addition of metal promoters reduced the total surface area. All the investigated metals influenced the textural properties of the Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst but the extent was varied from metal to metal. This might result from the added metals physically blocking the support pores.<sup>53</sup> The results suggest that the doped metals entered the pores of the  $\text{Al}_2\text{O}_3\text{-CeO}_2$  during the doping process, thereby affecting the mesoporosity and pore volume of the support.

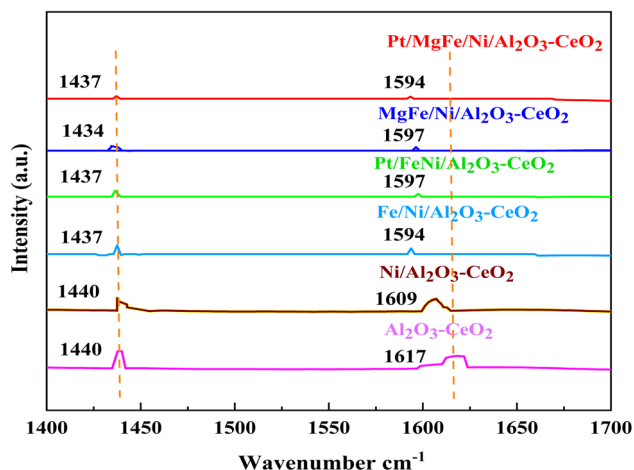


Fig. 4 Pyridine IR spectra of Ni-based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts.

Table 3 Results of FTIR spectra of pyridine adsorption

Catalysts	Pyridine desorption amount ( $\text{mmol}_{\text{py}}\text{ g}_{\text{cat}}^{-1}$ ) <sup>a</sup>		
	1434–1440 $\text{cm}^{-1}$	1596–1617 $\text{cm}^{-1}$	Total
$\text{Al}_2\text{O}_3\text{-CeO}_2$	12.991	38.069	51.060
Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$	11.241	22.215	33.456
FeNi/ $\text{Al}_2\text{O}_3\text{-CeO}_2$	5.831	6.573	12.404
Pt/FeNi/ $\text{Al}_2\text{O}_3\text{-CeO}_2$	2.302	1.209	3.511
MgFe/Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$	2.556	2.417	4.973
Pt/MgFe/Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$	1.826	0.854	2.680

<sup>a</sup> The amounts were calculated by Emeis.<sup>51</sup>

### 3.2. Catalytic performance in DRM

Fig. 6(A)–(C) present catalytic results of the DRM at  $550\text{--}700\text{ }^\circ\text{C}$  in the presence of pure  $\text{CH}_4$  and a  $\text{CH}_4/\text{CO}_2$  mixture ( $50:50$ ). As shown in Fig. S1 (ESI),<sup>†</sup> Tables 5 and 6, the activity and stability of the catalysts, as well as the  $\text{H}_2/\text{CO}$  product ratio were measured at  $550\text{--}700\text{ }^\circ\text{C}$  for  $600\text{ min}$  time-on-stream. For all catalysts, the  $\text{CO}_2$  conversion was higher than that of  $\text{CH}_4$  and the conversions of both  $\text{CO}_2$  and  $\text{CH}_4$  were enhanced with increasing reaction temperature, indicating the occurrence of side reactions such as the reverse water gas shift reaction ( $\text{CO}_2 + \text{H}_2 \rightarrow \text{CO} + \text{H}_2\text{O}$ ).<sup>7,29</sup> In the absence of  $\text{CO}_2$  feeding (pure  $\text{CH}_4$ ), a significant amount of  $\text{CO}$  was formed over different catalysts due to the decomposition of methane ( $\text{CH}_4 \rightarrow \text{C} + \text{H}_2$ ) and a further oxidative regeneration ( $\text{C} + \text{O}_2 \rightarrow \text{CO}_2$ ) process.<sup>54</sup> The  $\text{H}_2/\text{CO}$  ratios were also increased as the reaction temperature increased because the RWGS reaction would gradually be prevented at elevated temperatures.<sup>46</sup> The presence of  $\text{CO}_2$  promoted  $\text{CH}_4$  conversion (Fig. 6, Tables 5 and 6), catalyst stability and  $\text{H}_2/\text{CO}$  ratio as compared to the catalysts in the absence of  $\text{CO}_2$  (Fig. S1<sup>†</sup>) at all reaction temperatures.

The catalytic stability of the catalysts was investigated over  $10\text{ h}$  at varied temperatures ( $550$ ,  $650$ , and  $700\text{ }^\circ\text{C}$ ) and constant mass of catalyst. Fig. S1<sup>†</sup> depicts the  $\text{CH}_4$ , and  $\text{CO}_2$  conversions, as well as the  $\text{H}_2/\text{CO}$  molar ratio as a function of time on-stream (TOS). These results confirmed the better performance of the metal oxide(s)-doped Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst as compared to the Ni/ $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst. The results revealed that all catalysts had good activity and stability during  $10\text{ h}$  on stream (TOS). It may be concluded that the carbon deposition on the surface of the catalyst was minimal, resulting in the stable conversion and



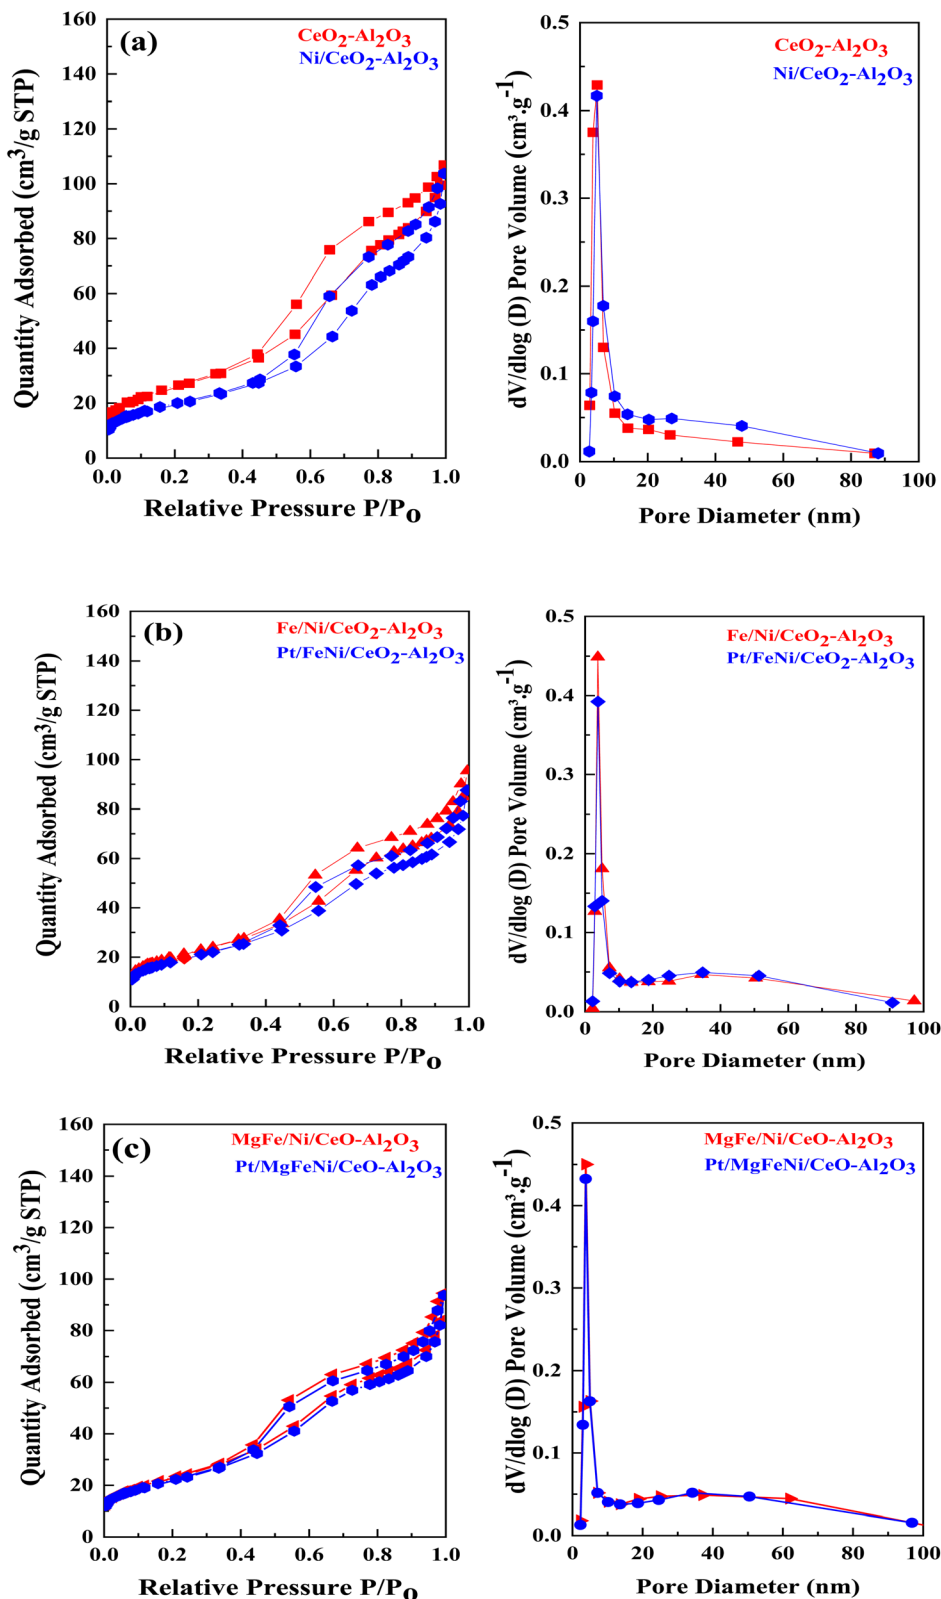


Fig. 5 ((a–c), left side)  $N_2$  physisorption isotherms and ((a–c), right side) BJH pore size distribution of of Ni-based  $Al_2O_3$ - $CeO_2$  composite catalysts.

$H_2/CO$  ratio. The small size of Ni contributes to its excellent stability. Another reason for these catalysts' high activity is the addition of metal oxides as the second active site. This finding is

consistent with previous research.<sup>30,55</sup> The DRM reaction was carried out over the  $Al_2O_3$ - $CeO_2$  support (Fig. 6A–C) as a control experiment to evaluate the potential impact of  $Al_2O_3$ - $CeO_2$ . The





Table 4 Physical properties of the investigated samples obtained from the nitrogen physisorption of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts

Catalysts	$S_{\text{BET}}^a$ (m <sup>2</sup> g <sup>-1</sup> )	$S_{\text{micro}}^b$ (m <sup>2</sup> g <sup>-1</sup> )	$S_{\text{meso}}^c$ (m <sup>2</sup> g <sup>-1</sup> )	$V_{\text{tot}}^d$ (cm <sup>3</sup> g <sup>-1</sup> )	Pore size <sup>e</sup> (nm)
Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	92	3	89	0.04	5.59
Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	86	3	66	0.03	5.56
FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	82	1	80	0.03	5.49
Pt/FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	78	1	76	0.02	5.55
MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	80	1	82	0.03	5.48
Pt/MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	76	2	76	0.02	5.69

<sup>a</sup> Estimated by the Brunauer–Emmett–Teller (BET) at the  $p/p_0$  in the range of 0.05–0.30. <sup>b</sup> Micropore area and micropore volumes were determined using the  $t$ -plot method. <sup>c</sup> Estimated by BJH at the adsorbed amount at the  $p/p_0 = 0.99$  single point. <sup>d</sup> Estimated by a  $t$ -plot. <sup>e</sup> Estimated by BJH desorption average pore diameter.

H<sub>2</sub>/CO ratio was lower than the stoichiometric value for DRM (1 mol mol<sup>-1</sup>) for Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>, however, it was increased by the addition of Ni and other metal promoters. As shown in Fig. 6A–C, Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts exhibited almost two-fold the CH<sub>4</sub> and CO<sub>2</sub> conversions as compared the Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> support in the temperature range investigated. Previous studies have demonstrated that the high metal dispersion led to a large number of active sites and consequently, high activity.<sup>7,29</sup> At all reaction temperatures, the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst performance was further increased significantly and activity follows the trend Pt/MgFe > MgFe > PtFe > FeNi for both CH<sub>4</sub> and CO<sub>2</sub>. The doping of Fe<sub>2</sub>O<sub>3</sub> into the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst resulted in an almost two-fold increase for both the CH<sub>4</sub> and CO<sub>2</sub> conversions (Fig. 6A–C, Tables 5 and 6). Notably, the formation of CO was higher for all Fe-doped catalysts, thereby precluding the accumulated carbon deposition on nearby Ni atoms and enhancing the catalytic activity for non-oxidative methane dehydrogenation and DRM. The redox mechanism is well-defined as the Mars-van Krevelen (MvK), which consists of two reactions: the first reaction is a reduction of the catalyst *via* hydrocarbon (methane), and the second is the re-oxidation reaction of the catalyst.<sup>56</sup> Doping the FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst with 0.005 wt% Pt further improved the catalyst stability and maintained the H<sub>2</sub>/CO ratio, probably by the initial dissociation of methane (CH<sub>4</sub> → CH<sub>3</sub> + H) as shown in Fig. 6A–C, Tables 5 and 6. Previous studies<sup>11,12</sup> also confirmed that the presence of Pt sites can also initiate the reduction of NiO by the rapid dissociation of H<sub>2</sub> and then the migration of atomic H to the NiO surface by the phenomenon of hydrogen spillover, which produces a higher mobility of hydrogen on the support surface, facilitating the access to Ni particles. The Pt/FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst showed more resistance to carbon formation than Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts (Fig. 6A–C, Tables 5 and 6). As noted in Table 5, these findings have been confirmed by calculating the deactivation factor and are consistent with literature reports.<sup>7</sup> A previous study by Pawelec *et al.*<sup>57</sup> demonstrated that adding 0.005%Pt to the Ni catalyst leads to the generation of nanosized NiO particles, which can be readily reduced. Based on their findings, the authors ascribed the enhancement in the performance and coke resistance over the Pt-Ni catalysts to the increase in the nickel metallic dispersion caused by the intimate contact between nickel and platinum. The effect of Mg doping on the catalytic performance of the

FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst was also examined, as illustrated in Fig. 6A–C, Tables 5 and 6. The excellent catalytic activity and long catalytic stability were observed over a MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst. As shown in the FTIR characterization, Mg doping enhanced the Lewis basicity, which is in favor of the chemisorption of CO<sub>2</sub> that would accelerate the reaction, CO<sub>2</sub> + C = 2CO, thus inhibiting the carbon deposition.<sup>50,56,58</sup> The Pt-doped MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst showed the best performance for H<sub>2</sub> selectivity; it performed better than the other five catalysts in the whole process, and reached 0.97 at 650 °C as shown in Fig. 6A–C, Tables 5 and 6, while both Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts showed higher CO selectivity at 550 °C. The Pt/Mg-Fe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> showed the highest CH<sub>4</sub> and CO<sub>2</sub> conversions and H<sub>2</sub>/CO values for all the temperatures, which indicated that the cooperative interaction between metals and the support could suppress the RWGS reaction. Therefore, Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> is considered a promising candidate for the DRM reaction in terms of activity, stability and selectivity. Furthermore, as summarized in Fig. 6A–C, Tables 5 and 6, the highest specific activity was obtained, which was followed by Pt/MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> > MgFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> > PtFe/Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> > FeNi/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>. Surface basicity, oxygen vacancy and redox properties are crucial for enhancing the CO<sub>2</sub> adsorption capacity and carbonate species formation.<sup>59</sup> The addition of metal oxide(s) and rare earth elements (Ce<sub>2</sub>O<sub>3</sub>) effectively enhance the surface basicity and redox properties of the catalysts, which further affect the CO<sub>2</sub> adsorption capacity of the Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst. The characterization analyses and catalytic tests revealed that the introduction of metal oxide(s) into the Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst generated more coordination unsaturated Ni atoms, oxygen vacancies, defects and active sites for the DRM reaction. The existence of Pt can initiate the NiO reduction process by the rapid dissociation of H<sub>2</sub> and migration of atomic H to the NiO surface by the hydrogen spillover phenomenon, which can retrain Ni in the metallic state under DRM conditions. Niu *et al.*<sup>60</sup> demonstrated that the metal with lower electronegativity enhanced CO<sub>2</sub> activation, which had a positive impact on the surface oxygen concentration and promoted the oxidation of the surface carbon species, thus reducing the carbon formation and improving the catalyst stability. The addition of Pt to the catalyst stabilized the size of the Ni particles and prevented Ni from becoming encapsulated in carbon. This phenomenon occurs because of nickel particles being



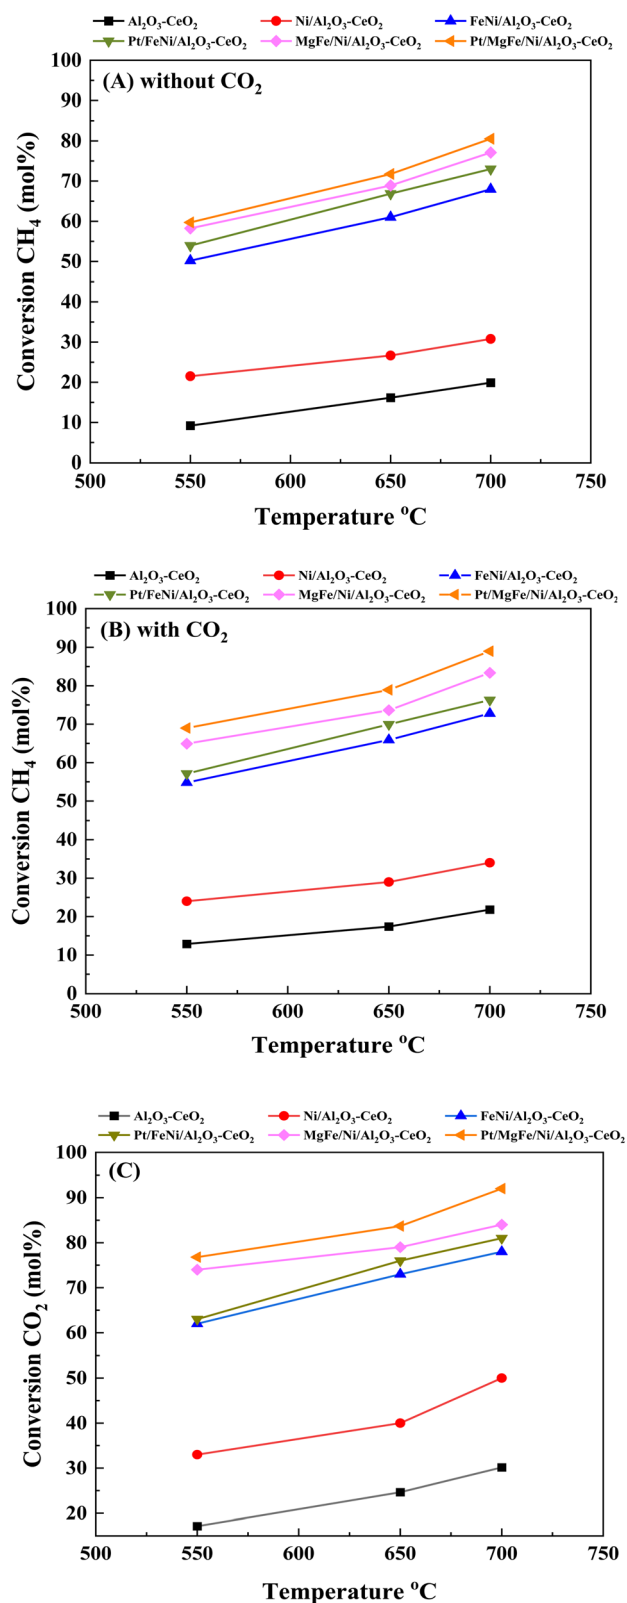


Fig. 6 Activity of catalysts for DRM: (A) CH<sub>4</sub> conversion (without CO<sub>2</sub>); (B) CH<sub>4</sub> conversion (with CO<sub>2</sub>) and (C) CO<sub>2</sub> conversion. Reaction conditions: reaction temperature, 550–700 °C; *P* = 1 bar; feed gas, pure CH<sub>4</sub> (without CO<sub>2</sub>) and CH<sub>4</sub>/CO<sub>2</sub> = 50/50 (with CO<sub>2</sub>), flow rate = 60 mL min<sup>-1</sup>, WHSV = 12 000 mL g<sub>cat</sub><sup>-1</sup> h<sup>-1</sup>.

anchored by several carbon layers that grow in multiple directions. According to García-Diéguez *et al.*,<sup>61</sup> Pt addition to the Ni/Al<sub>2</sub>O<sub>3</sub> catalyst decreases global carbon synthesis, and the C generated in tri-metallic catalysts (Pt/M–Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub>) appears to be less tightly attached to the Ni than in the monometallic and bi-metallic Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalyst. Furthermore, unlike Ni, carbon is gasified on Pt particles rather than dispersed, resulting in the constant activity of Pt sites. According to Niu *et al.*, the electronic structure of active sites is modified in bimetallic catalysts, which affects the adsorption of specific reagents. When compared to monometallic catalysts, it reduces the activation energy of CH<sub>4</sub> dissociation and CO<sub>2</sub> activation. Furthermore, it increases the responsiveness of surface oxygen species, which improves carbon species suppression. The results (Table 7) show that Pt/M–Ni has lower carbon deposition than Ni due to (i) a higher energy barrier for the decomposition of the CH<sub>x</sub><sup>\*</sup> species, which led to C\* (CH<sub>x</sub><sup>\*</sup> = C\* + H\*, step (5), plausible catalytic mechanism) and (ii) lower energy barriers for the oxidation of CH<sub>x</sub><sup>\*</sup> species (CH<sub>x</sub><sup>\*</sup> + O\* = CH<sub>x</sub>O\*, step (17), plausible catalytic mechanism, where CH<sub>x</sub>O\* is an intermediate for CO\*) and C\* species (C\* + O\* = CO\* + \*). As a result, the carbon concentration on the surface of Pt/M–Ni was lowered. Pt/M–Ni also weakens hydrogen dissociation, lowering the RWGS and increasing H<sub>2</sub> generation. To better understand the influence of metal promoters on the activities of the M–Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts for the DRM, the turnover frequencies (TOFs), which reflect the intrinsic activity of the active sites, were calculated based on the Ni crystallites from XRD and the initial CH<sub>4</sub> conversions (*X*<sub>CH<sub>4</sub></sub>) at 550–700 °C, and the results are listed in Table 5. For all catalysts, the TOF was improved by increasing the reaction temperature, and also by secondary and tertiary metal doping, consistent with the variation in CH<sub>4</sub> conversions. These observations are in agreement with the conversion and TPR results, which revealed the best catalytic activity and the highest reducibility for Ni-based catalyst-doped metal oxides. This could be ascribed to the high interaction and dispersion of metal dopants on the catalyst surface in accordance with XRD results (Table 1). The M–Ni tri/bimetallic surface modified with Pt had a lower binding energy for H\* than the monometallic Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalyst. This demonstrates that on Pt-modified M–Ni tri/bimetallic catalysts, the surface oxidation step leading to CO production (potentially CH\* + O\*) became the kinetically significant phase. The electrical modification by generating the Pt-modified M–Ni tri/bimetallic surface can be attributed to the catalyst composition's significant activation energy dependence.<sup>62</sup> The trend of shifting the CO stretching frequency as a result of the charge transfer between Pt and Ni fits well with the tendency of variations in the methane activation energy. Additionally, the methane activation energy tends to be similar to the O\* adsorption energy, but the CO<sub>2</sub> activation energy tends to be similar to the C\* adsorption energy with catalyst composition. This emphasizes the relationship between the heat of C\* or O\* adsorption and the apparent activation energy. The activation energy of CO<sub>2</sub> increases as the C\* adsorption energy increases, while the activation energy of CH<sub>4</sub> increases as the O\* adsorption energy increases. This agrees with earlier literature and emphasizes the relationship between



Table 5 Summary of the catalytic testing of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts

Catalysts	Reaction temp. (°C)	Conversion (mol%)		Selectivity (mol%)		H <sub>2</sub> /CO	DF <sup>a</sup> (%)	TOF <sub>CH<sub>4</sub></sub> (S <sup>-1</sup> )	TOF <sub>CO<sub>2</sub></sub> (S <sup>-1</sup> )
		CH <sub>4</sub>	CO <sub>2</sub>	H <sub>2</sub>	CO				
Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	13	17	48	77	0.58	-132	1.21	1.42
	650	17	25	55	86	0.63	-99	1.49	1.55
	700	22	30	64	88	0.73	-114	1.54	1.77
Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	24	33	48	77	0.62	-120	1.93	2.64
	650	29	40	55	86	0.64	-103	1.98	2.77
	700	34	50	64	88	0.73	-111	2.13	2.92
FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	54	62	60	86	0.70	-70	2.43	2.74
	650	65	73	71	90	0.79	-56	2.64	2.83
	700	71	78	80	91	0.87	-49	2.78	2.97
Pt/FeNi/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	57	63	70	88	0.78	-65	2.76	2.96
	650	69	76	75	90	0.83	-52	2.98	3.28
	700	75	81	84	92	0.92	-46	3.18	3.52
MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	65	74	80	96	0.82	-60	2.94	3.37
	650	74	79	85	94	0.90	-43	3.10	3.58
	700	83	84	91	95	0.96	-40	3.46	3.89
Pt/MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	550	69	76	85	92	0.92	-56	3.33	3.64
	650	79	83	87	96	0.94	-42	3.63	3.96
	700	89	92	93	96	0.97	-36	3.99	4.46

<sup>a</sup> Deactivation Factor (DF) = [(final CH<sub>4</sub> conversion - initial conversion CH<sub>4</sub>)/initial conversion of CH<sub>4</sub>] × 100. Reaction conditions: CH<sub>4</sub>/CO<sub>2</sub> = 50/50, flow rate = 60 mL min<sup>-1</sup>, wt. cat. = 0.3 g, P = 1 bar for 10 h.

Table 6 Catalytic activity from DRM over various catalysts<sup>a</sup>

Catalysts	DRM reaction conditions	CH <sub>4</sub> conv.%	CO <sub>2</sub> conv.%	H <sub>2</sub> /CO	Synthesis method	Ref.
<b>Monometallic system</b>						
4%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 34	≈ 50	≈ 0.73	Impregnation	This work
13%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 180 000 mL g <sup>-1</sup> h <sup>-1</sup>	≈ 44	≈ 58	≈ 0.82	One-pot	65
10%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 80/20)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 40/40, 90 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 40	≈ 50	≈ 0.78	Impregnation	12
<b>Bi-metallic system</b>						
4%Ni-Fe/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 71	≈ 78	≈ 0.87	Impregnation	This work
4%Ni-Mo/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 71	≈ 75	≈ 0.86	Impregnation	66
20%Ni-Ru/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 95/5)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 2/2, 15 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 88	≈ 84	n.a.	Impregnation	67
<b>Tri-metallic system</b>						
PtFe/4%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 75	≈ 81	≈ 0.92	Impregnation	This work
MgFe/4%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 83	≈ 84	≈ 0.96	Impregnation	This work
Pt/MgFe/4%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 89	≈ 92	≈ 0.97	Impregnation	This work
Pt/FeMo/4%Ni/Al <sub>2</sub> O <sub>3</sub> CeO <sub>2</sub> (Al/Ce = 50/50)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 50/50, 12 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 81	≈ 86	≈ 0.91	Impregnation	66
Ni-Co-Ru/MgO-Al <sub>2</sub> O <sub>3</sub> (Mg/Al = 1/4)	760 °C, CH <sub>4</sub> /CO <sub>2</sub> = 1/1, 111 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	≈ 95	≈ 90	n.a.	Impregnation	68
4%NiAuPt/AlMg(Al/Mg = 90/10)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 1/1, 60 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	77.10	85.14	n.a.	Impregnation	69
4%NiAuPt/AlCe(Al/Ce = 90/10)	700 °C, CH <sub>4</sub> /CO <sub>2</sub> = 1/1, 60 000 mL g <sup>-1</sup> h <sup>-1</sup> , 1 bar	79.06	86.94	n.a.	Impregnation	69

<sup>a</sup> n.a. (not available).

the heat of C\* or O\* adsorption and the apparent activation energy. The activation energy of CO<sub>2</sub> increases as the C\* adsorption energy increases, while the activation energy of CH<sub>4</sub>

increases as the O\* adsorption energy increases. This agrees with previous literature.<sup>63</sup> The results show that a minimal addition of Pt could significantly reduce the energy required to



Table 7 Summary of the weight loss of Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> composite catalysts

Catalyst	Weight loss%	
	C <sup>a</sup>	C <sup>b</sup>
Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	4.81	3.38
Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	4.01	2.82
Fe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	2.94	1.97
PtFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	1.6	1.112
MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	1.2	0.79
Pt/MgFe/Ni/Al <sub>2</sub> O <sub>3</sub> -CeO <sub>2</sub>	0.93	0.39

<sup>a</sup> Spent catalyst in the absence of CO<sub>2</sub>. <sup>b</sup> Spent catalyst in the presence of CO<sub>2</sub>.

activate CO<sub>2</sub>. On the surface of catalysts, this will encourage the dissociation of CO<sub>2</sub> into CO and O. The oxidation of surface carbon and CH<sub>x</sub>, which affects the product's H<sub>2</sub>/CO ratio and the rate of coke generation, is another process that is greatly aided by the presence of O\*. Tri/bimetallic Pt-modified Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalyst clusters improve catalytic activity, lower the energy barrier for CO<sub>2</sub> activation, and encourage the creation of surface O\* via CO<sub>2</sub> adsorptive dissociation while lowering the activation energy for CH<sub>4</sub> dissociation. Surface oxygen density may be increased by the tri/bimetallic Pt-modified Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalysts. This is consistent with the findings of CO<sub>2</sub>-TPD (Fig. 3). Enhancing the catalyst's resistance to the generation of coke and extending its useful life during the reaction process is advantageous. According to H<sub>2</sub>-TPR investigations (Fig. 2), the presence of Pt in the Ni particles causes easily reducible NiO particles, thereby decreasing the reduction temperature because of the strong contact between Ni and Pt. As a result, the Ni-Pt matrix (alloy phase) generated with CO<sub>2</sub> dissociation on the metal surface is easier to remove from the surface and subsurface oxygen. Similarly, the Ni-based Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalyst's reducibility increased and the temperature at which the NiO species were reduced dropped after the addition of metal oxides (M = Mg and Fe). This is consistent with the findings of H<sub>2</sub>-TPR (Fig. 2). The estimated TOF numbers are consistent with the literature findings that demonstrated higher methane conversion and syngas yield at higher TOF numbers.<sup>64</sup> In general, the coke generated by methane decomposition (step (6), plausible catalytic mechanism) and the CO disproportionation reaction (step (19), plausible catalytic mechanism) in the methane dry reforming reaction may cover the metal active sites and cause the catalyst to deactivate quickly. A 10 hours long-term durability test at 700 °C was carried out to further evaluate the potential utilization of M-Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts. The small decrease in catalytic activity seen in Fig. S1† and Table 7 could be attributed to a change in catalyst surface during the reaction process. The M-Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts exhibited strong carbon resistance over a 10 hours procedure. Fig. S1† and Table 6 indicate that the M-Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>2</sub> catalysts maintained their CH<sub>4</sub> conversion, CO<sub>2</sub> conversion, and H<sub>2</sub>/CO ratio in the presence of minimal carbon deposition. This is due to the great dispersion of Ni on the support, which prevented Ni active site agglomeration and sintering and the strong metal-support

contact, which kept the Ni nanoparticle size stable during high-temperature reactions. This is a well-established H<sub>2</sub>-TPR profile.

### 3.3. Plausible catalytic mechanism

Metal oxide(s) as promoters are crucial in the development of extremely effective DRM catalysts. All the data show that the additions had a positive effect on the surface basicity, redox characteristics, and dispersion of Ni particles, and knowing these favorable qualities can help to clarify the catalytic mechanism. The activation of CH<sub>4</sub> and CO<sub>2</sub> is commonly regarded as a critical step.<sup>70</sup> As illustrated in Fig. 7, CH<sub>4</sub> is activated over the Ni sites, and CO<sub>2</sub> can be adsorbed and activated on the support surface, and the metal oxide and support interface. As demonstrated in CO<sub>2</sub>-TPD profiles, increasing the basicity of catalysts can increase the rate of CO<sub>2</sub> activation, which has a major impact on catalytic performance (Fig. 3 and Table 2). According to our findings, the addition of metal oxides can effectively increase the surface basicity of the catalysts, thus improving the CO<sub>2</sub> adsorption capacity of metal oxides (M = Pt, Mg, and Fe)-doped Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalysts. This is consistent with the *in situ* DRIFTS analysis via Dengsong *et al.*<sup>71</sup> The adsorbed CO<sub>2</sub> can form two kinds of carbonate species on the catalyst surface: bidentate carbonates and monodentate carbonates. Meanwhile, the active intermediate CH<sub>x</sub> can react with these generated carbonates; bidentate carbonates, in particular, are more suitable for CH<sub>x</sub> conversion. Furthermore, the produced carbonates can efficiently react with the deposited carbon; therefore the presence of the carbonates may assist in the removal of the deposited carbon, resulting in increased catalytic stability. The redox property and its effect on oxygen vacancy are crucial for improving the catalytic performance. Due to the coexistence of redox pairs, the Pt, Mg, Fe, and Ce-modified catalysts showed enhanced redox properties, thereby resulting in abundant oxygen vacancies among the M-Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalysts as shown in the H<sub>2</sub>-TPR profiles (Fig. 2). The abundant oxygen vacancies can provide additional active oxygen and more active sites for CO<sub>2</sub> and CH<sub>4</sub> activation. Active oxygen species played an essential role in reducing carbon deposition. Because surface active oxygen species can react with deposited carbon, this helps to prevent catalyst deactivation during the DRM process. Furthermore, the improved redox characteristics can enable electron transport, which can increase the rate of CH<sub>4</sub>/CO<sub>2</sub> conversion as well as the elimination of deposited carbon. Since metal oxides were incorporated into Ni-based catalysts, the homogeneous dispersion of Ni species had a good effect on the anti-coking behavior, as shown in Table 1. The highly dispersed and small Ni nanoparticles could effectively inhibit the carbon nucleation and the subsequent growth, playing an important role in suppressing the coke formation. However, the hypothesized mechanisms for bi- and tri-metallic Ni-based catalysts are shown below for the DRM. The reaction mechanisms postulated are based on relevant compiled literature data, given as the following steps (1)–(23):








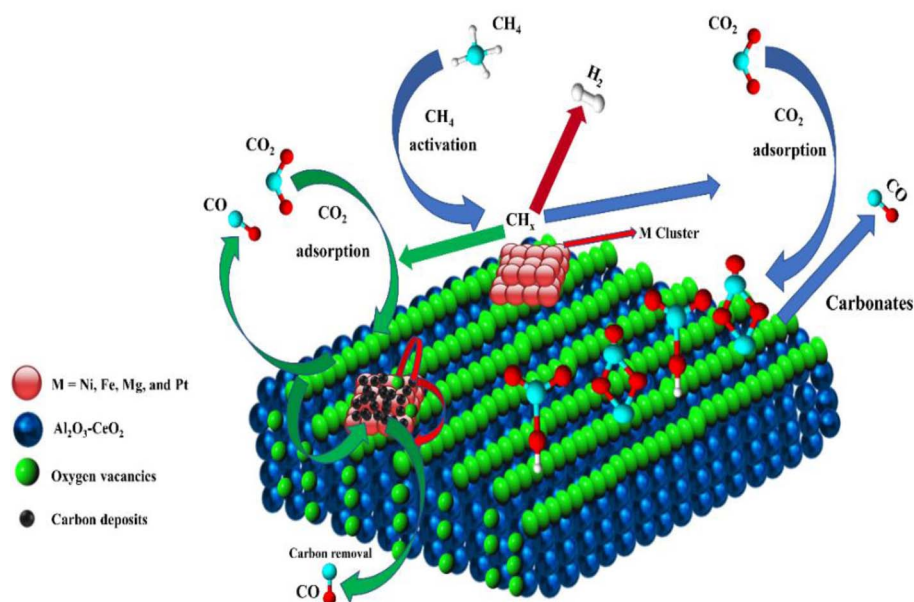

















Fig. 7 Schematic representation of a plausible reaction over the (M = Pt, Mg, and Fe) doped Ni/Al<sub>2</sub>O<sub>3</sub>-CeO<sub>3</sub> catalysts.



Gathering steps (2)–(5) gives step (6):



CO<sub>2</sub> adsorption (metal oxide(s) or metal-support interface) (7)



(\*) and O<sub>LT</sub> represent unoccupied active sites, and lattice oxygen on the metal oxide surface, respectively. According to the above analysis, CH<sub>4</sub> dissociative adsorption occurs on the Ni metal surface (steps (2)–(5)), while CO<sub>2</sub> is adsorbed on the surface of the catalysts in the form of the carbonate species (step (7)). As the carbonate species encounter the methane pyrolysis products, they degrade fast into formate species, which subsequently decompose further into CO (step (9) and step (10)). CO<sub>2</sub> reacts with H<sup>\*</sup> generated by methane dehydrogenation to yield COOH<sup>\*</sup> or HCOO<sup>\*</sup> (step (11)). COOH<sup>\*</sup> is subsequently decomposed into COH<sup>\*</sup> and O<sup>\*</sup> (step (12)) or CO<sup>\*</sup> and OH<sup>\*</sup> (step (13)) before COH<sup>\*</sup> dehydrogenation to produce CO<sup>\*</sup> and H<sup>\*</sup> (step (14)). Adsorbed CH<sub>x</sub> is oxidized *via* OH<sup>\*</sup> groups to create CH<sub>x</sub>OH<sup>\*</sup> (step (15)), which is then dissociated into CO<sup>\*</sup> and H<sup>\*</sup> (step (16)). The lattice oxygen, produced by the dissociation of CO<sub>2</sub>, and the facile movement of oxygen could be



mobilized to the nearby Ni nanoparticles and then react with  $\text{CH}_x^*$  species to give  $\text{CH}_x\text{O}^*$  (step (17)) and then decompose into  $\text{CO}^*$  and  $\text{H}^*$  (step (18)), eliminating carbon deposition and preventing catalyst deactivation. Both  $\text{HCO}^*$  decomposition and  $\text{CH}_x^*$  interaction with  $\text{O}^*$  result in the creation of syngas. Reaction step (19) represents solid carbon,  $\text{C}^*$ , primarily from the  $\text{CH}_4$  molecular dissociation, which may be converted to  $\text{CO}$  *via* reacting with the lattice oxygen coming either from the  $\text{CeAlO}_3$  support or from metal oxide phases ( $\text{M} = \text{Pt}, \text{Mg},$  and  $\text{Fe}$ )-doped  $\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$  catalysts. Reaction step (20) represents the oxidation of the reduced  $\text{CeO}_2\text{-Al}_2\text{O}_3$  sites ( $\text{O}_{\text{LT-1}}$ ) by reaction with  $\text{CO}_2$  molecules, and step (21) represents the reduction *via*  $\text{H}_2^*$ . Finally,  $\text{H}_2^*$  and  $\text{CO}^*$  are desorbed on the catalyst to form  $\text{H}_2(\text{g})$  and  $\text{CO}(\text{g})$  (step (22) and (23)). Fan *et al.*<sup>72</sup> postulated a different reaction mechanism for catalysts with basic supports, such as  $\text{CeO}_2$ , in which  $\text{CO}_2$  activation occurs on the surface of the support rather than the metal active site. In this mechanism,  $\text{CO}_2$  is adsorbed in the vicinity of the metal particles on the catalyst support,  $\text{CO}_2(\text{g}) = \text{CO}_2(\text{support})$ , resulting in the carbonate species,  $\text{CO}_2(\text{support}) + \text{O}^{2-} = \text{CO}_3^{2-}(\text{support})$ . The hydrogen is then used to reduce the carbonate ( $\text{CO}_3^{2-}(\text{support}) + 2\text{H} = \text{HCO}_2^-(\text{support}) + \text{OH}^-$ ) to produce  $\text{CO}$ .<sup>73</sup> According to the theory,  $\text{CO}_2$  is adsorbed on promoters like  $\text{Ce}$  or  $\text{CeO}$  and dissociates into  $\text{CO}$  and  $\text{O}$  (step (5)). Following this, carbon from the decomposition of  $\text{CH}_4$  is deposited on the catalyst's active sites where it reacts with the adsorbed oxygen on the promoter to generate  $\text{CO}$  ( $\text{O}^* + \text{C}^* \rightarrow \text{CO}^*$ ).

## 4. Conclusion

$\text{Pt}, \text{Fe},$  and  $\text{Mg}$  were doped into  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts *via* an impregnation method and evaluated for DRM reaction. All doped  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts presented significantly higher activity and  $\text{H}_2$  selectivity as compared to the  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts. Characterization results showed that compared to unmodified catalysts, the catalysts treated with metal oxide ( $\text{Mg}, \text{Fe},$  and  $\text{Pt}$ ) particles had a significant number of basic sites for enhancing  $\text{CO}_2$  adsorption. The most stable and efficient conversion of  $\text{CO}_2$  and  $\text{CH}_4$  was achieved by the modified catalysts because they displayed the highest  $\text{Ni}$  particle dispersion, which can effectively stop the migration of  $\text{Ni}$  species. Additionally, as shown by the  $\text{H}_2$ -TPR profile, the co-doped catalysts displayed high levels of redox cycling, which enhanced the generated oxygen vacancies and helped eliminate carbon deposition. Although all metal-doped  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalysts showed slightly lower surface areas than the  $\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst and  $\text{Al}_2\text{O}_3\text{-CeO}_2$  support, they presented significantly higher activity and  $\text{H}_2$  selectivity compared to  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalysts. Catalytic activity results revealed the impact of secondary and tertiary metal doping on the  $\text{Ni}$ -based  $\text{Al}_2\text{O}_3\text{-CeO}_2$  catalyst and the highest methane (>85%) and  $\text{CO}_2$  (~90%) conversions and high selectivity towards  $\text{H}_2/\text{CO}$  ratio (0.97) were obtained over the  $\text{Pt}/\text{MgFe}/\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$  composite catalyst. The order of activity of the catalysts, based on the turnover frequencies, was  $\text{Pt}/\text{MgFe}/\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2 > \text{MgFe}/\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$

$> \text{Pt}/\text{FeNi}/\text{Al}_2\text{O}_3\text{-CeO}_2 > \text{FeNi}/\text{Al}_2\text{O}_3\text{-CeO}_2 > \text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$ . The observed better  $\text{Pt}/\text{MgFe}/\text{Ni}/\text{Al}_2\text{O}_3\text{-CeO}_2$  stability could be due to favorable changes in the distribution of surface basic sites, and better  $\text{Ni}$  dispersion.

## Data availability

All data generated or analyzed during this study are included in this published article in the main manuscript and ESI.†

## Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## Acknowledgements

The authors would like to thank the Higher Committee for Educational Development in Iraq (HCED) for its financial support. The authors would also like to acknowledge the Iraqi Ministry of Oil/Midland Refineries Company/AL-Daura Refinery Company for financial their support. The authors thank the Missouri university of Science and Technology for its financial support this work.

## References

- 1 P. Schwach, X. Pan and X. Bao, Direct Conversion of Methane to Value-Added Chemicals over Heterogeneous Catalysts: Challenges and Prospects, *Chem. Rev.*, 2017, **117**, 8497–8520, DOI: [10.1021/acs.chemrev.6b00715](https://doi.org/10.1021/acs.chemrev.6b00715).
- 2 M. A. Atanga, F. Rezaei, A. Jawad, M. Fitch and A. A. Rownaghi, Oxidative Dehydrogenation of Propane to Propylene with Carbon Dioxide, *Appl. Catal., B*, 2018, **220**, 429–445, DOI: [10.1016/j.apcatb.2017.08.052](https://doi.org/10.1016/j.apcatb.2017.08.052).
- 3 R. H. Saihod, Z. M. Shakoor and A. A. Jawad, Prediction of Reaction Kinetic of Al-Doura Heavy Naphtha Reforming Process Using Genetic Algorithm, *Al-Khwarizmi Eng. J.*, 2014, **10**, 47–61.
- 4 W. J. Jang, J. O. Shim, H. M. Kim, S. Y. Yoo and H. S. Roh, A Review on Dry Reforming of Methane in Aspect of Catalytic Properties, *Catal. Today*, 2019, **324**, 15–26, DOI: [10.1016/j.cattod.2018.07.032](https://doi.org/10.1016/j.cattod.2018.07.032).
- 5 N. J. Gunsalus, A. Koppaka, S. H. Park, S. M. Bischof, B. G. Hashiguchi and R. A. Periana, Homogeneous Functionalization of Methane, *Chem. Rev.*, 2017, **117**(13), 8521–8573, DOI: [10.1021/acs.chemrev.6b00739](https://doi.org/10.1021/acs.chemrev.6b00739).
- 6 Q. L. M. Ha, U. Armbruster, C. Kreyenschulte, H. Atia, H. Lund, H. T. Vuong and S. Wohlrab, Stabilization of Low Nickel Content Catalysts with Lanthanum and by Citric Acid Assisted Preparation to Suppress Deactivation in Dry Reforming of Methane, *Catal. Today*, 2019, **334**, 203–214, DOI: [10.1016/j.cattod.2018.11.021](https://doi.org/10.1016/j.cattod.2018.11.021).
- 7 D. Pakhare and J. Spivey, A Review of Dry ( $\text{CO}_2$ ) Reforming of Methane over Noble Metal Catalysts, *Chem. Soc. Rev.*, 2014, **43**, 7813–7837, DOI: [10.1039/C3CS60395D](https://doi.org/10.1039/C3CS60395D).



- 8 S. D. Angeli, F. G. Pilitsis and A. A. Lemonidou, Methane Steam Reforming at Low Temperature: Effect of Light Alkanes' Presence on Coke Formation, *Catal. Today*, 2015, **242**, 119–128, DOI: [10.1016/j.cattod.2014.05.043](https://doi.org/10.1016/j.cattod.2014.05.043).
- 9 J. Al-Darwish, M. Senter, S. Lawson, F. Rezaei and A. A. Rownaghi, Ceria Nanostructured Catalysts for Conversion of Methanol and Carbon Dioxide to Dimethyl Carbonate, *Catal. Today*, 2020, **350**, 120–126, DOI: [10.1016/j.cattod.2019.06.013](https://doi.org/10.1016/j.cattod.2019.06.013).
- 10 M. A. Vasiliades, C. M. Damaskinos, K. K. Kyprianou, M. Kollia and A. M. Efstathiou, The Effect of Pt on the Carbon Pathways in the Dry Reforming of Methane over Ni-Pt/Ce 0.8 Pr 0.2 O 2-δ Catalyst, *Catal. Today*, 2020, **355**, 788–803, DOI: [10.1016/j.cattod.2019.04.022](https://doi.org/10.1016/j.cattod.2019.04.022).
- 11 A. A. Rownaghi and R. L. Huhnke, Producing Hydrogen-Rich Gases by Steam Reforming of Syngas Tar over CaO/MgO/NiO Catalysts, *ACS Sustain. Chem. Eng.*, 2013, **1**, 80–86.
- 12 I. Luisetto, S. Tuti, C. Battocchio, S. Lo Mastro and A. Sodo, Ni/CeO<sub>2</sub>-Al<sub>2</sub>O<sub>3</sub> Catalysts for the Dry Reforming of Methane: The Effect of CeAlO<sub>3</sub> Content and Nickel Crystallite Size on Catalytic Activity and Coke Resistance, *Appl. Catal., A*, 2015, **500**, 12–22, DOI: [10.1016/j.apcata.2015.05.004](https://doi.org/10.1016/j.apcata.2015.05.004).
- 13 Y. H. Taufiq-Yap, S. Sudarno, U. Rashid and Z. Zainal, CeO<sub>2</sub>-SiO<sub>2</sub> Supported Nickel Catalysts for Dry Reforming of Methane toward Syngas Production, *Appl. Catal., A*, 2013, **468**, 359–369, DOI: [10.1016/j.apcata.2013.09.020](https://doi.org/10.1016/j.apcata.2013.09.020).
- 14 C. C. Chong, S. N. Bukhari, Y. W. Cheng, H. D. Setiabudi, A. A. Jalil and C. Phalakornkule, Robust Ni/Dendritic Fibrous SBA-15 (Ni/DFSBA-15) for Methane Dry Reforming: Effect of Ni Loadings, *Appl. Catal., A*, 2019, **584**, 117174, DOI: [10.1016/j.apcata.2019.117174](https://doi.org/10.1016/j.apcata.2019.117174).
- 15 Y. He, A. Jawad, X. Li, M. Atanga, F. Rezaei and A. A. Rownaghi, Direct Aldol and Nitroaldol Condensation in an Aminosilane-Grafted Si/Zr/Ti Composite Hollow Fiber as a Heterogeneous Catalyst and Continuous-Flow Reactor, *J. Catal.*, 2016, **341**, 149–159, DOI: [10.1016/j.jcat.2016.07.001](https://doi.org/10.1016/j.jcat.2016.07.001).
- 16 W. Y. Kim, J. S. Jang, E. C. Ra, K. Y. Kim, E. H. Kim and J. S. Lee, Reduced Perovskite LaNiO<sub>3</sub> Catalysts Modified with Co and Mn for Low Coke Formation in Dry Reforming of Methane, *Appl. Catal., A*, 2019, **575**, 198–203, DOI: [10.1016/j.apcata.2019.02.029](https://doi.org/10.1016/j.apcata.2019.02.029).
- 17 C. Egawa, Methane Dry Reforming Reaction on Ru(0 0 1) Surfaces, *J. Catal.*, 2018, **358**, 35–42, DOI: [10.1016/j.jcat.2017.11.010](https://doi.org/10.1016/j.jcat.2017.11.010).
- 18 T. D. Gould, M. M. Montemore, A. M. Lubers, L. D. Ellis, A. W. Weimer, J. L. Falconer and J. W. Medlin, Applied Catalysis A : General Enhanced Dry Reforming of Methane on Ni and Ni-Pt Catalysts Synthesized by Atomic Layer Deposition, *Appl. Catal., A*, 2015, **492**, 107–116, DOI: [10.1016/j.apcata.2014.11.037](https://doi.org/10.1016/j.apcata.2014.11.037).
- 19 J. Xin, H. Cui, Z. Cheng and Z. Zhou, Bimetallic Ni-Co/SBA-15 Catalysts Prepared by Urea Co-Precipitation for Dry Reforming of Methane, *Appl. Catal., A*, 2018, **554**, 95–104, DOI: [10.1016/j.apcata.2018.01.033](https://doi.org/10.1016/j.apcata.2018.01.033).
- 20 A. A. Jawad and N. J. Saleh, Studying the Effect of Both Gas Oil and Diesel Fuel on Polypropylene-Polycarbonate Reinforcement with Carbon Black, *Eng. Technol. J.*, 2013, **31**, 2039–2054, DOI: [10.30684/etj.31.11A3](https://doi.org/10.30684/etj.31.11A3).
- 21 J. Niu, X. Du, J. Ran and R. Wang, Dry (CO<sub>2</sub>) Reforming of Methane over Pt Catalysts Studied by DFT and Kinetic Modeling, *Appl. Surf. Sci.*, 2016, **376**, 79–90, DOI: [10.1016/j.apsusc.2016.01.212](https://doi.org/10.1016/j.apsusc.2016.01.212).
- 22 N. H. Elsayed, N. R. M. Roberts, B. Joseph and J. N. Kuhn, Low Temperature Dry Reforming of Methane over Pt-Ni-Mg/Ceria-Zirconia Catalysts, *Appl. Catal., B*, 2015, **179**, 213–219, DOI: [10.1016/j.apcatb.2015.05.021](https://doi.org/10.1016/j.apcatb.2015.05.021).
- 23 G. Busca, *Structural, Surface, and Catalytic Properties of Aluminas*, Elsevier Inc., 1st edn, 2014, vol. 57, DOI: [10.1016/B978-0-12-800127-1.00003-5](https://doi.org/10.1016/B978-0-12-800127-1.00003-5).
- 24 A. Jawad and S. Ahmed, Studying the Influence of the Addition of Nano-Titanium Dioxide on the Rheological, Mechanical, Thermal, and Electrical Properties of Polycarbonate/Wood Flour, *J. Thermoplast. Compos. Mater.*, 2023, 1–31, DOI: [10.1177/08927057231162018](https://doi.org/10.1177/08927057231162018).
- 25 A. A. Jawad and N. Salah, Studying the Effect of Addition of Carbon Black on Rheological Properties of Polypropylene and Polycarbonate, *Eng. Technol. J.*, 2013, **31**, 976–990, DOI: [10.30684/etj.31.5A13](https://doi.org/10.30684/etj.31.5A13).
- 26 B. Yan, X. Yang, S. Yao, J. Wan, M. N. Z. Myint, E. Gomez, Z. Xie, S. Kattel, W. Xu and J. G. Chen, Dry Reforming of Ethane and Butane with CO<sub>2</sub> over PtNi/CeO<sub>2</sub> Bimetallic Catalysts, *ACS Catal.*, 2016, **6**(11), 7283–7292, DOI: [10.1021/acscatal.6b02176](https://doi.org/10.1021/acscatal.6b02176).
- 27 Z. Chen, L. Mao, X. Fang, X. Xu, J. Xu and X. Wang, Methane Dry Reforming over Ni/NiO Supported on Ce-, Zr-, and Al-Modified Y<sub>2</sub>O<sub>3</sub> for Hydrogen Production, *Catalysts*, 2023, **13**, 1–18, DOI: [10.3390/catal13020430](https://doi.org/10.3390/catal13020430).
- 28 T. Odedairo, J. Chen and Z. Zhu, Metal-Support Interface of a Novel Ni-CeO<sub>2</sub> Catalyst for Dry Reforming of Methane, *Catal. Commun.*, 2013, **31**, 25–31, DOI: [10.1016/j.catcom.2012.11.008](https://doi.org/10.1016/j.catcom.2012.11.008).
- 29 J. Niu, S. E. Liland, J. Yang, K. R. Rout, J. Ran and D. Chen, Effect of Oxide Additives on the Hydrotalcite Derived Ni Catalysts for CO<sub>2</sub> Reforming of Methane, *Chem. Eng. J.*, 2019, 119763, DOI: [10.1016/j.cej.2018.08.149](https://doi.org/10.1016/j.cej.2018.08.149).
- 30 H. A. Lara-García, D. G. Araiza, M. Méndez-Galván, S. Tehuacanero-Cuapa, A. Gómez-Cortés and G. Díaz, Dry Reforming of Methane over Nickel Supported on Nd-Ceria: Enhancement of the Catalytic Properties and Coke Resistance, *RSC Adv.*, 2020, **10**, 33059–33070, DOI: [10.1039/d0ra05761d](https://doi.org/10.1039/d0ra05761d).
- 31 K. Świrk, M. E. Gálvez, M. Motak, T. Grzybek, M. Rønning and P. Da Costa, Dry Reforming of Methane over Zr- and Y-Modified Ni/Mg/Al Double-Layered Hydroxides, *Catal. Commun.*, 2018, **117**, 26–32, DOI: [10.1016/j.catcom.2018.08.024](https://doi.org/10.1016/j.catcom.2018.08.024).
- 32 E. le Saché, L. Pastor-Pérez, D. Watson, A. Sepúlveda-Escribano and T. R. Reina, Ni Stabilised on Inorganic Complex Structures: Superior Catalysts for Chemical CO<sub>2</sub>recycling via Dry Reforming of Methane, *Appl. Catal., B*, 2018, **236**, 458–465, DOI: [10.1016/j.apcatb.2018.05.051](https://doi.org/10.1016/j.apcatb.2018.05.051).
- 33 M. N. Abu Tahari, F. Salleh, T. S. Tengku Saharuddin, N. Dzakarria, A. Samsuri, M. W. Mohamed Hisham and









