


Cite this: *Mater. Adv.*, 2024,
5, 777

Adsorption of immunomodulatory proteins over silica nanoparticles and the *in vitro* effect

Exequiel David Giorgi,^{ab} Sofía Genovés,^{ab} María Eugenia Díaz,^{ab} Sofía Municoy,^c
Martin Federico Desimone  †*^c and Mauricio César De Marzi†*^{ab}

Silica NPs (SiNPs) used as a platform to deliver molecules have huge potential for biomedical applications. In order to generate new immunomodulatory tools, 2 variants of SiNPs were synthesized and 3 proteins were adsorbed over their surface: bovine serum albumin and the cytokines IL-1 β and TGF- β . Protein adsorption was analyzed according to Langmuir and Freundlich models. The adsorption isotherm of IL-1 β on both SiNP variants had a good fit to the Freundlich model, indicating the formation of a protein multilayer around the NPs. For BSA and TGF- β isotherms, the fit to the Langmuir model was better, evidencing the presence of a protein monolayer on the NPs. SiNPs@TGF- β complexes were tested in THP-1 cells (human monocytes cells). The complexes reduced cellular metabolic activity and did not cause an increase in nitric oxide expression, which is related to the immunosuppressive activity of TGF- β , but was potentiated and prolonged over time compared to the cytokine alone. These nanocomplexes could be important tools for use as nanoinmunomodulators (NIMs) for the therapeutic treatment of inflammatory diseases.

Received 28th September 2023,
Accepted 5th December 2023

DOI: 10.1039/d3ma00776f

rsc.li/materials-advances

Introduction

Metal oxide nanoparticles (NPs) have been used in several industries and consumer products. There is evidence showing that NPs could generate reactive oxygen species (ROS), which endow them with antimicrobial activity but, on the other hand, can induce oxidative stress which could be harmful to the cell membrane and cause DNA damage.^{1–4} Moreover, when proteins interact with the NP surface, the adsorption forces can disrupt non-covalent interactions in the protein structure, so a denaturation process could occur.⁵ In biological systems, a layer of proteins formed on the NP surface is called the protein corona (which includes proteins, lipids, and ions that are immediately adsorbed onto the NP surface),^{6,7} and is an entity that can change over time.^{5,8}

Silica NPs (SiNPs) are among the most widely used NPs for the development of potential delivery tools^{4,9,10} and they can be found in several food and cosmetic products.¹¹ Indeed, SiNPs

have been used in clinical trials and clinical studies. They are mostly employed for oral delivery or bioimaging studies.^{4,12}

Although the biological effects of SiNPs *in vivo* are not fully understood, it is clear that high specific surface areas are associated with increased cytotoxicity in most cases.^{11,13} Orally ingested SiNPs can be tolerated at high doses, but when inhaled they could lead to chronic inflammation.¹⁴ There is evidence of degradation of silica particles into silicic acid in biological media, which can be excreted through the urine.¹⁵ However, it is not possible to establish a general degradation kinetics for different SiNPs because it is a process that not only depends on the particle characteristics, such as surface area, functional groups, pore size, and others, but also on the degradation medium characteristics (*i.e.*, temperature, pH, and concentration).^{15,16} Moreover, SiNPs' biocompatibility depends on their properties such as size and surface properties.^{17–19}

It has been reported that the presence of a protein corona could mitigate the toxicity of these NPs and also change the way they interact with cells, altering their internalization efficiency compared to SiNPs without the protein corona.^{6,20,21}

Bovine serum albumin (BSA) is a common protein model used in NP adsorption studies.^{22,23} Some studies have been carried out on the adsorption of BSA on various surfaces of inorganic and polymeric NPs in biological media and the pH effects on this process.^{24–27} Since oxide NPs are postulated as transporters for therapeutic drugs, immunomodulatory molecules, or antigens, it is necessary to understand the characteristics of protein corona formation under different conditions

^a CONICET-Universidad Nacional de Luján, Instituto de Ecología y Desarrollo Sustentable (INEDES), Grupo de Investigaciones Básicas y Aplicadas en Inmunología y Bioactivos (GIBAIB), Av. Constitución y Ruta 5, Luján, Buenos Aires, Argentina. E-mail: desimone@ffyba.uba.ar

^b Universidad Nacional de Luján, Departamento de Ciencias Básicas, Laboratorio de Inmunología, Av. Constitución y Ruta 5, Luján, Buenos Aires, Argentina

^c Universidad de Buenos Aires, Facultad de Farmacia y Bioquímica, CONICET, Instituto de Química y Metabolismo del Fármaco (IQUIMEFA), Buenos Aires, Argentina

† Both authors contributed equally.



analysis, the samples (*ca.* 0.45 g) were outgassed at 120 °C for 12 h.³⁹

Fourier transform infrared spectroscopy

Fourier transform infrared spectroscopy (FT-IR) analysis was performed on different samples using a Nicolet iS 50 FT-IR spectrophotometer, with a KBr beam splitter. Spectra were obtained with a resolution of 2 cm⁻¹ using a DTGS detector. The samples were measured using the attenuated total reflectance (ATR) technique. For this, 150 μL of the samples were dried under a nitrogen flow and the powder was then placed on the attenuated total reflection accessory of the spectrometer, and the spectra were recorded. FT-IR spectra were conducted to confirm the presence of Si–O–Si bonds (with absorption bands at 1100 cm⁻¹) and silanol groups (Si–OH) (absorption bands at 960 cm⁻¹) in SiNPs, and S–S bonds and amide I, II, and III (characteristic absorption bands for proteins) to corroborate the adsorption of proteins over SiNPs.^{23,37,40}

Protein adsorption studies

Different proteins of immunological interest such as BSA, TGF-β and IL-1β were used for immobilization on NPs. A protein stock solution (2 mg mL⁻¹ in the case of BSA and 0.50 mg mL⁻¹ for the other proteins tested) was prepared in phosphate buffer solution (PBS). Serial dilutions of this protein stock solution were made (until 0.05 mg mL⁻¹) for subsequent use. SiOHNPs and SiNH₂NPs (8 mg mL⁻¹) were dispersed in the same buffer. Equal volumes of protein solution and SiOHNPs or SiNH₂NPs suspension were mixed and incubated at 25 °C in 25 mM PBS pH 7.4 overnight under stirring to favor protein adsorption on the NP surfaces. Finally, the mix was centrifuged and supernatants (SNs) were removed and stored. The pellet (NPs@protein) was washed and centrifuged 3 times with 25 mM PBS pH 7 and stored in 300 μL of the same work buffer for characterization. SNs with non-adsorbed protein were isolated and stored at –20 °C for later protein quantification by Bradford determination. The NPs@protein was resuspended in 1 mL of PBS 1X. Data on the adsorption of different amounts of proteins onto a fixed amount of NPs were collected.

The protein content adsorbed on NPs was calculated as the difference in concentration of the protein in the SN before and after adsorption. Protein concentration was determined using a standard calibration curve of BSA by the Bradford micro-method.^{41,42} These results were corroborated by estimating the protein content using SDS-PAGE and comparing it with BSA samples of known concentrations. The percentage of adsorption efficiency was calculated as shown below:

$$AE\% = \frac{P_{\text{total}} - P_{\text{supernatant}}}{P_{\text{total}}}$$

Also, adsorption capacity was calculated as follows:

$$AC = \frac{\text{mg}_{\text{protein immobilised}}}{\text{mg}_{\text{nanoparticles}}}$$

where P_{total} is the initial amount of protein in the mixture and

$P_{\text{supernatant}}$ is the amount of free protein in the supernatant after immobilization and centrifugation.

From AC and $P_{\text{supernatant}}$ data, adsorption isotherms were composed and their adjustment to Langmuir and Freundlich models was calculated.^{43,44}

Langmuir adsorption model assumes that there are a finite number of interaction points in the surface of NPs where proteins can bind. For that, there is a maximum amount of protein that could be adsorbed, which is represented by the maximum adsorption capacity (MAC) forming a monolayer on the NP surface.^{43,45} The model equation can be represented as follows:

$$q_e = \frac{MACbC_e}{1 + bC_e}$$

C_e : equilibrium concentration (mg L⁻¹); q_e : the amount of the adsorbate in the adsorbent at equilibrium (mg g⁻¹); MAC: maximum amount of the adsorbate in the adsorbent at equilibrium (mg g⁻¹); and b : Langmuir isotherm constant (dm³ mg⁻¹).

From this model the K_m value can be obtained, which represents the equilibrium concentration necessary to reach 50% of MAC.⁴³

The Freundlich adsorption model assumes a heterogeneous surface with high and low affinity regions but with a progressive reduction of adsorption affinity due to lateral repulsion between the adsorbed molecules.⁴⁵ The model is represented by the following equation:

$$q_e = K_f C_e^{1/n}$$

C_e : equilibrium concentration (mg L⁻¹); q_e : the amount of the adsorbate in the adsorbent at equilibrium (mg g⁻¹); K_f : Freundlich isotherm constant (mg g⁻¹) (dm³ mg⁻¹) ^{n} ; and n : adsorption intensity.⁴³

Protein release studies

In vitro release of adsorbed proteins was determined by suspending the protein-loaded NPs in 1 mL of PBS solution at a final NP concentration of 4 mg mL⁻¹. All suspensions were placed in an Eppendorf mixer (100 rpm, 4 °C). The amount of released protein was determined by removing the SN after centrifugation (6800g, 10 min) and replacing it with buffer (1 mL) at specified time points (0.5; 1; 2; 4; 8; 24; 48; 96; 192; 384 and 720 h). Desorbed proteins were measured in the SNs by the Bradford method.

Effect of nanoparticles on cell proliferation

Human monocyte cell line THP-1 (TIB-202™) from American Type Culture Collection (ATCC) were cultivated in complete RPMI 1640 medium (10% fetal bovine serum) at 37 °C and 5% CO₂ atmosphere. For assays, cells were placed in 24-well plates at a final concentration of 1 × 10⁵ cells per mL with 1 mL as the final volume. Cell proliferation in the presence of NPs alone or NPs carrying different proteins was measured for 24–72 h. For this purpose, a concentration of 300 μg mL⁻¹ of NPs or nanocomplexes was employed.

Metabolic activity as an indicator of cellular proliferation was determined with MTT assay as described previously.^{17,37}



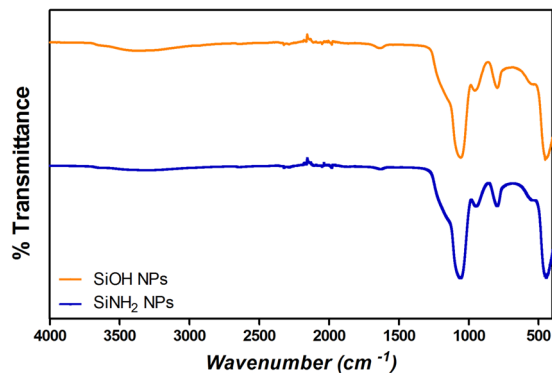


Fig. 2 FTIR analysis of SiOH NPs (orange) and SiNH₂ NPs (blue).

Table 1 Hydrodynamic diameter by DLS and Z potential of NPs

	Hydrodynamic diameter (nm)	Z potential (mV)
SiOH NPs	151 ± 9	-23.7
SiNH ₂ NPs	154 ± 8	+13.3

Table 2 Adsorbed proteins and their characteristics

Protein	Molecular weight	Isoelectric point	Net charge at pH 7.4
BSA	66.46 kDa	4.7	(-)
IL-1β	17.5 kDa	6.1	(-)
TGF-β1	25.62 kDa	8.8	(+)

AC of 50% MAC. The Freundlich model assumes the formation of multiple layers, which can indicate that not all the proteins are in direct interaction with NP surfaces. From this model were obtained the K_f and n values, related to the AC and the adsorption intensity, respectively.⁴³

One of the characteristics of the proteins that is essential for adsorption is the net charge at the medium pH. It is considered that when proteins present an opposite charge to NPs, the adsorption could be favored by electrostatic interactions. It is also important how large the difference is between the isoelectric point of the proteins and the pH of the medium, since

the greater this difference, the more charge the proteins will have and therefore the greater the electrostatic repulsion between them, which makes the process of adsorption on the surfaces of NPs. Choosing a pH medium near pI could boost the adsorption efficiency, because protein-protein repulsions are minimized, allowing high compaction over NPs.^{5,48} Moreover, there is evidence that not only electrostatic interaction is important in protein-NP interaction.⁴⁹ It has also been reported that BSA adsorption is optimal at isoelectric point 4.7 at room temperature.²⁶ According to R^2 values presented in Table 3 and to the adsorption curve shown in Fig. 3, BSA immobilization on SiOH NPs had a better adjustment to the Langmuir model ($R^2 = 0.9802$) than to the Freundlich model ($R^2 = 0.9281$). The MAC calculated from the Langmuir isotherm model was 285.8 mg g⁻¹ SiOH NPs. In the case of BSA adsorption on SiNH₂ NPs a similar adjustment to Langmuir model was obtained ($R^2 = 0.9780$) but for the Freundlich model a higher R^2 value was calculated ($R^2 = 0.9652$). Also, according to the Langmuir model, almost double MAC was obtained (540.2 mg BSA per g SiNH₂ NPs) in comparison with SiOH NPs, which clearly indicates a higher cargo capacity. In both cases, protein release was not detected after several washes. This is a sign of the great stability of the nanocomplexes formed.

When IL-1β was absorbed into NPs, a different pattern was presented as can be seen in Fig. 4. On one hand, the values obtained in the adsorption of IL-1β over SiOH NPs presented a poor adjustment for the Langmuir model ($R^2 = 0.7996$) but a better one for the Freundlich model ($R^2 = 0.9350$). MAC and k_m values were out of range. On the other hand, the K_f and n values of the Freundlich model were very high, showing a high interaction of the protein over the surface. Due to the absence of highly heterogeneous surface, the formation of multilayer could be correlated with protein-protein interactions. When IL-1β adsorption was performed over SiNH₂ NPs, similar R^2 values were obtained for the Langmuir and Freundlich models (0.8265 and 0.9210 respectively). The K_f value was lower than the one presented in SiOH NP adsorption, but the n value was similar. IL-1β pI is 6.1, so it is possible that at pH 7.4 the repulsion between proteins is not too strong to make the adsorption process difficult. Furthermore, IL-1β presents a lower molecular weight (17.5 kDa) than BSA (66.46 kDa), which can explain the differences in the adsorption pattern.

Table 3 Langmuir and Freundlich models' statistics values and percentage protein release

Protein adsorbed	SiOH NPs		SiNH ₂ NPs	
	Langmuir model	Freundlich model	Langmuir model	Freundlich model
BSA	MAC = 285.8 mg g ⁻¹ NPs $K_m = 0.1265$ mg mL ⁻¹ $R^2 = 0.9802$	$K_f = 267.4$ $n = 0.3636$ $R^2 = 0.9281$	MAC = 540.2 mg g ⁻¹ NPs $K_m = 0.4181$ mg mL ⁻¹ $R^2 = 0.9780$	$K_f = 433.0$ $n = 0.6151$ $R^2 = 0.9652$
IL-1β	Protein percentage release = no detected MAC = exceeds the range $K_m =$ exceeds the range $R^2 = 0.7996$	$K_f = 30380$ $n = 1.891$ $R^2 = 0.9350$	Protein percentage release = no detected MAC = exceeds the range $K_m =$ exceeds the range $R^2 = 0.8265$	$K_f = 10790$ $n = 1.870$ $R^2 = 0.9210$
TGF-β1	Protein percentage release = 4.74% MAC = 94.62 mg per cg NPs $K_m = 0.1998$ mg mL ⁻¹ $R^2 = 0.9530$	$K_f = 215.2$ $n = 0.8219$ $R^2 = 0.9548$	Protein percentage release = 6.18% MAC = 37.61 mg g ⁻¹ NPs $K_m = 0.05415$ mg mL ⁻¹ $R^2 = 0.7890$	$K_f = 100.4$ $n = 0.5978$ $R^2 = 0.8208$
	Protein percentage release = 22.53%		Protein percentage release = 40.54%	





Fig. 3 Adsorption isotherms of BSA over SiOH NPs (A) and SiNH₂ NPs (B) with representation of Langmuir and Freundlich curves in orange and green, respectively.

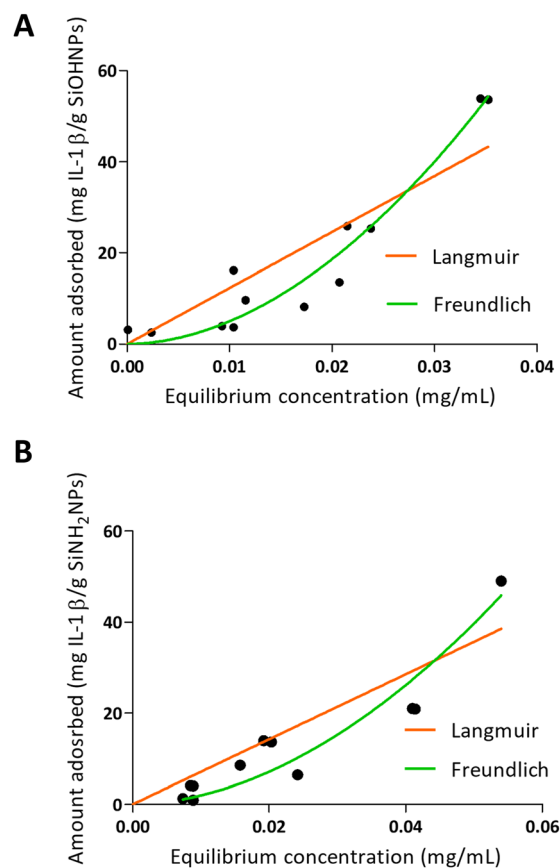


Fig. 4 Adsorption isotherms of IL-1β over SiOH NPs (A) and SiNH₂ NPs (B) with representation of Langmuir and Freundlich curves in orange and green, respectively.

In both NP variants, a low protein release was found over time, that was observed at 30 minutes with no further releases in all other times measured (as far as a month). The protein release percentages for SiOH NPs and SiNH₂ NPs were 4.74% and 6.18% respectively (Table 3). Once again, it seems that the obtained nanocomplexes presented great stability despite the several washes with PBS through time.

In another sense, it was previously reported that the presence of BSA on the surface of NPs alters their charge state and improves their dissolution kinetics. Perhaps this reduces its useful life but improves protein delivery.⁴⁶

When TGF-β adsorption was analyzed over SiOH NPs (Fig. 5), $R^2 = 0.9530$ was obtained for the Langmuir model and $R^2 = 0.9548$ for the Freundlich model. The MAC was 94.62 mg TGF-β per g SiOH NPs. On the other hand, the data obtained for TGF-β adsorption on SiNH₂ NPs presented lower adjustment to the Langmuir and Freundlich models ($R^2 = 0.7890$ and $R^2 = 0.8280$ respectively). MAC was lower, presenting a value of 37.61 mg TGF-β per g SiNH₂ NPs. The protein release percentages for SiOH NPs and SiNH₂ NPs were 22.53% and 40.54% respectively and it was detected in the first hour, with no more detectable released protein after that (Table 3). Taking all this data together it is clear that not only MAC was lower for SiNH₂ NPs, but also a higher percentage of protein was lost in the first

washes with PBS. Despite that, both nanocomplexes seem to present good stability at least for a month at 4 °C.

The differences of adjustment to the models between the adsorption in TGF-β and the adsorption of IL-1β over the two types of NPs can be related to the protein corona formed and the interactions presented. When the data fit better to the Langmuir model, as seen for the adsorption of TGF-β, a protein monolayer is probably formed around the NPs.

Although in some combinations, NPs and proteins did not have opposite charges, successful adsorption was achieved. This was also reported in previous studies. Indeed, Villarruel *et al.* reported the adsorption of recombinant human growth hormone (hGH), which presents an isoelectric point around 5, over silica NPs (synthesized by the Stöber method) in phosphate buffer.⁵⁰ At this point, both NPs and hGH should have presented a net negative charge, but the immobilization was still accomplished.

Effect of nanoparticles on cell proliferation

The effect of bare SiOH NPs and SiNH₂ NPs of similar sizes over the metabolic activity of THP-1 cells at a concentration of 0.6 mg mL⁻¹ (600 μg NPs mL⁻¹) was previously analyzed.¹⁸ It was observed that SiOH NPs generated a decrease in cell metabolic activity while SiNH₂ NPs did not. Given the precedent, the





Fig. 5 Adsorption isotherms of TGF- β over SiOHNPs (A) and SiNH₂NPs (B) with representation of Langmuir and Freundlich curves in orange and green, respectively.

effect of nanocomplexes on cell metabolic activity was analyzed in comparison with the effect generated by bare NPs to identify differences due to the protein coating. SiOHNPs@TGF- β and SiNH₂NPs@TGF- β were tested as model NIMs because TGF- β activity is related to a wide variety of immunological processes and has been reported to be associated with immunosuppression and immunotolerance.^{31,51,52}

The nanocomplexes used in THP-1 culture were produced from a mix of NPs and TGF- β in a proportion of 1 : 20 because at this point the AE% was still near 50%. At higher proportions of TGF- β :NPs, an important decrease of AE% was observed. The treatment with NPs and nanocomplexes was made with a final concentration of 300 μg NPs per mL. At this concentration of nanocomplexes, the concentration of TGF- β adsorbed was around 8 μg mL⁻¹. Initially, the effect of TGF- β was analyzed at that concentration (8 μg mL⁻¹). Fig. 6(A) shows the curves of proliferation considering the value of metabolic activity of unexposed cells, at 24 h as 100%. A decrease in metabolic activity of cells treated with TGF- β at 48 and 72 h can be observed, reaching at the last time a decrease of \sim 25%. In this way, the TGF- β biological activity over human monocytes was corroborated.

When the effect of SiOHNPs and SiOHNPs@TGF- β over THP-1 cells was analyzed (Fig. 6(B)), SiOHNPs@TGF- β showed

a higher effect in the reduction of the metabolic activity. At 24 h, cells treated with SiOHNPs@TGF- β presented an activity \sim 15% below the activity of the ones treated with bare SiOHNPs. At 48 h, the difference was higher, with an activity of 65% for the nanocomplex (taking the 100% as the value of activity of cells treated with SiOHNPs at 24 h). At 72 h, cells treated with SiOHNPs@TGF- β showed even less activity, showing 3-fold lower activity than cells treated with SiOHNPs. The inhibitory effect of TGF- β was enhanced and maintained through the time when it was immobilized over SiOHNPs.

SiOHNPs' effect over metabolic activity at 24 h is similar to what was observed in previous studies by De Marzi *et al.* and Mitarotonda *et al.*, where SiOHNPs generated a decrease in THP-1 cell proliferation.^{17,18} In particular, for NPs around \sim 150 nm, this effect was evident but not as important as in bigger particles (\sim 500 nm).

In Fig. 6(C) the proliferation curves of cells treated with SiNH₂NPs and SiNH₂NPs@TGF- β are presented. While SiNH₂NPs did not affect the growth rate of THP-1 cells, SiNH₂NPs@TGF- β generated a decrease in metabolic activity. In comparison with the metabolic activity of cells treated with SiNH₂NPs at 24 h (100%), SiNH₂NPs@TGF- β presented an activity reduction of \sim 20%, \sim 36%, and \sim 54% at 24, 48, and 72 h respectively. The good biocompatibility presented by SiNH₂NPs was also previously reported by Mitarotonda *et al.*^{18,37}

As the tendency seemed to be similar for both complexes, the metabolic activities of cells treated were compared with control cells' activity. At all the times tested a difference in metabolic cell activity of around 8% between cells treated with SiNH₂NPs@TGF- β and the ones treated with SiOHNPs@TGF- β was found (Fig. 6(D)). As the amount of TGF- β adsorbed over NPs was similar in both cases, the only attributable difference between the complexes was the protein percentage release (\sim 20% for SiOHNPs@TGF- β and \sim 45% SiNH₂NPs@TGF- β), which could explain the slighter increased effect of the SiOHNPs@TGF- β over monocytes.

These results could indicate that NPs-TGF- β complexes maintain their biological activity over time, even more than TGF- β alone, not only because of the slow release that the NPs would perform but also because of the stability that the NPs provide to the protein. Another point of great interest is that nanocomplexes presented a similar tendency over cells despite the Z potential of the original NPs (Table 1) used for immobilization. As can be seen in the comparison with NPs alone, their typical effects of them are completely changed by the presence of TGF- β on the surface of the nanocomplexes. So, the use of NPs previously characterized as adsorption platforms of different proteins of interest can have a big impact on their biological effect and fate.

Nitric oxide expression

It has been described that TGF- β (in conjunction with IL-10) regulates arginase expression on several immune cells, so it also has an important role in the suppression of NO production mediated by arginase.^{53,54} This is why NIMs transporting TGF- β



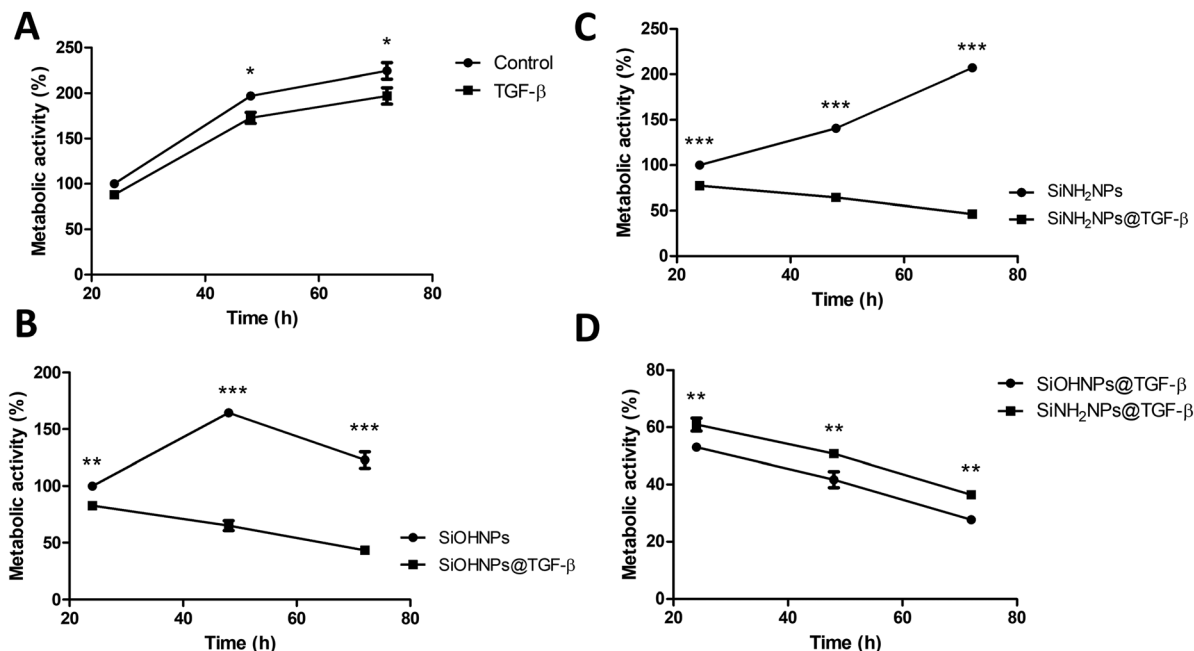


Fig. 6 THP-1 metabolic activity in the presence of NPs and nanocomplexes: (A) proliferation percentage at 24, 48 and 72 h of control cells and cells treated with TGF- β ; (B) proliferation percentage at 24, 48 and 72 h of control SiOHNPs and cells treated with SiOHNPs@TGF- β ; (C) proliferation percentage at 24, 48 and 72 h of control SiNH₂NPs and cells treated with SiNH₂NPs@TGF- β ; (D) proliferation percentage at 24, 48 and 72 h of SiOHNPs@TGF- β and SiNH₂NPs@TGF- β regarding metabolic cell activity of control cells at 24 h. All values relativized considering control metabolic activity at 24 h as 100% of proliferation.

could have a crucial effect on macrophage polarization M1/M2.⁵⁵ Nitrite concentration in monocyte cell cultures was analyzed as an indicator of cell activation.

No significant differences were observed when comparing nitrite concentration in exposed and non-exposed cells to TGF- β at all times (Fig. 7). Only cells treated with SiOHNPs presented high concentrations of nitrites ($\sim 4.5 \mu\text{M}$) at 24 h. A similar tendency in the induction of nitric oxide expression in THP-1 cells by SiOHNPs was reported in a previous study.¹⁸ In the rest of the cases, even when significant differences were found, it did not reach higher values than $2 \mu\text{M}$. Therefore, it is considered that nanocomplexes did not generate cell activation, despite the effect that bare NPs could generate. Furthermore, cell cultures treated with SiOHNPs@TGF- β and SiNH₂NPs@TGF- β did not present significant differences in nitrite concentration between them at any time, which indicates a similar behavior for both nanocomplexes.

The evidence collected shows that the effect of nanocomplexes over monocytes metabolic activity and their expression of NO seems to be correlated with the effect of the TGF- β adsorbed and presented on their surface, determining the interaction between NPs and cells. TGF- β activity could also be altered by conformational changes suffered in the adsorption process.⁵ Nanocomplexes obtained demonstrate that immobilized TGF β not only maintains biological activity but that it is better than soluble TGF β .

These nanocomplexes could be the basis for a new generation of immunomodulators, called NIMs. However, it is still necessary to have a wider comprehension of the effects of these

NIMs over THP-1 cells and to test them in another model that better emulates the natural physiological environment and cell phenotypes such as 3D models and PMBCs.

As far as we know, this is the first time that TGF- β is adsorbed over silica NPs to provide a potential therapeutic tool. Two studies from the last years incorporate different isoforms of TGF- β in a 3D scaffold to achieve a controlled release in the context of cartilage damage. One of them presented a hydrogel with TGF- β 1 and bone marrow-derived mesenchymal stem cells encapsulated with cartilage regeneration properties, demonstrating the high potential of TGF- β as part of complex therapeutic systems for regeneration and different disease treatments.⁵⁶ On the other hand, Shen *et al.* demonstrated that the incorporation of a nanomaterial with TGF- β 3 adsorbed in a 3D scaffold improved the long-term release and therefore its *in vivo* effect.⁵⁷

Herein, the obtained NIMs with an apparent immunosuppressive activity represent true candidates to be tested in a chronic inflammation model and analyze their immunoregulatory capacity. Moreover, these NIMs could be also incorporated into hydrogels and applied to damaged articular cartilage.

Conclusions

In this work, negatively and positively charged SiNPs capable of efficiently adsorbing different proteins on their surface are described. In this sense, all the proteins under study were able to be adsorbed on the surface of both synthesized NPs, but in the case of BSA, SiNH₂NPs showed greater adsorption capacity.



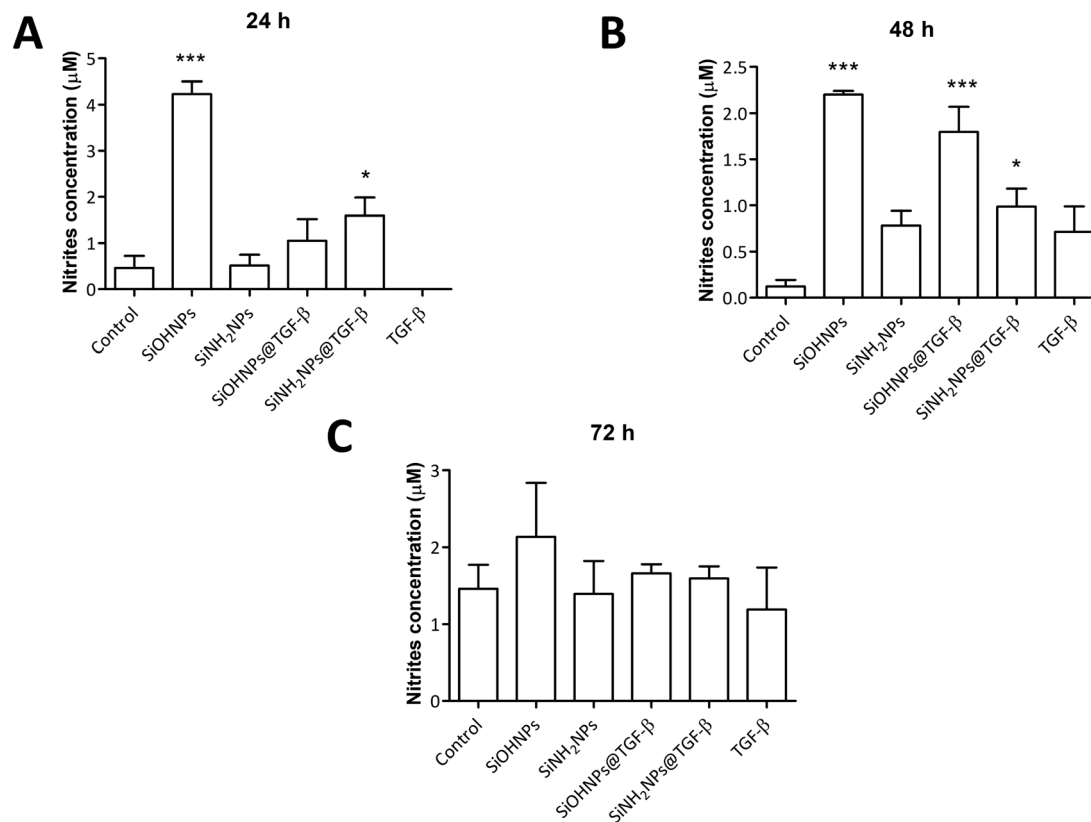


Fig. 7 Nitric oxide expression: (A) nitrite concentration in THP-1 cell cultures with different treatments at 24 h; (B) 48 h; (C) 72 h. All comparisons are with control cells.

The results obtained with IL-1 β suggest the formation of a protein multilayer around the NPs while with TGF- β a higher MAC was obtained for the SiOHNPs. This indicates that the adsorption, as expected, was more favored when the NPs presented an opposite charge to the proteins.

The SiOHNPs@TGF- β and SiNH₂NPs@TGF- β nanocomplexes similarly inhibited monocyte metabolic activity, with SiNH₂NPs@TGF- β having a slightly smaller initial effect. Both nanocomplexes did not induce important increases in NO, indicating the absence of cell activation.

These observations differ from the effect generated by bare NPs, demonstrating that nanocomplexes have novel properties regardless of the original chemical nature of the NP surface.

Therefore, SiNPs are proposed as potential platforms for delivering immunoregulatory molecules to increase their effects on immune cells. Thus, SiNPs present a potential immunomodulatory tool (NIMs) for future use in treating immunological diseases such as hypersensitivity reactions and autoimmune diseases.

Author contributions

Exequiel Giorgi contributed to the synthesis of NPs and nanocomplexes, analysed the effect of nanocomplexes on cell proliferation and activation and performed statistical analysis. He actively participated in the writing of the article. Sofia Genovés contributed with the cell cultures and metabolic activity

determinations as well as statistical analysis. She also actively participated in the writing of the article. María Eugenia Díaz contributed with cell cultures, with the analysis of the effect of nanoparticles on cell proliferation and with statistical analysis. She participated in the writing of the article. Sofia Municoy contributed to the physicochemical characterization of NPs and statistical analysis. She participated in the writing of the article. Martín F. Desimone contributed to the design of experiments and data interpretation. Mauricio C. De Marzi contributed to the conception, design of experiments and acquisition and interpretation of data. Both, Martín F. Desimone and Mauricio C. De Marzi led the writing of the article and grants acquisition. All authors have given approval to the final version of the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

Exequiel Giorgi is grateful for his doctoral fellowship granted by CONICET. This work was supported by the under grant from the Universidad de Buenos Aires PIDAE2022, PIP 0826 and UBACYT 20020190100083BA (to MFD), and from UNLu-RESREC-LUJ 37/22, UNLu- CDDCB-No 326-19 and PICT-2021-GRF-TI-00507 (to MCDM).



Notes and references

- 1 T. Jaswal and J. Gupta, *Mater. Today Proc.*, 2023, **81**, 859–863.
- 2 D. B. Warheit, C. M. Sayes, K. L. Reed and K. A. Swain, *Pharmacol. Ther.*, 2008, **120**, 35–42.
- 3 V. Stone, H. Johnston and M. J. D. Clift, *IEEE Trans Nanobiotechnology*, 2007, **6**, 331–340.
- 4 S. Paul, S. Mukherjee and P. Banerjee, *Mater. Adv.*, 2023, **4**, 2042–2061.
- 5 G. Bashiri, M. S. Padilla, K. L. Swingle, S. J. Shepherd, M. J. Mitchell and K. Wang, *Lab Chip*, 2023, **23**, 1432–1466.
- 6 A. Lesniak, F. Fenaroli, M. P. Monopoli, C. Åberg, K. A. Dawson and A. Salvati, *ACS Nano*, 2012, **6**, 5845–5857.
- 7 I. A. Mudunkotuwa, A. Al Minshid and V. H. Grassian, *Analyst*, 2014, **139**, 870–881.
- 8 M. P. Monopoli, C. Aberg, A. Salvati and K. A. Dawson, *Nat. Nanotechnol.*, 2012, **7**, 779–786.
- 9 H. Zhang, Z. Ji, T. Xia, H. Meng, C. Low-Kam, R. Liu, S. Pokhrel, S. Lin, X. Wang, Y. P. Liao, M. Wang, L. Li, R. Rallo, R. Damoiseaux, D. Telesca, L. Mädler, Y. Cohen, J. I. Zink and A. E. Nel, *ACS Nano*, 2012, **6**, 4349–4368.
- 10 M. J. Mitchell, M. M. Billingsley, R. M. Haley, M. E. Wechsler, N. A. Peppas and R. Langer, *Nat. Rev. Drug Discovery*, 2021, **20**, 101–124.
- 11 A. M. Mebert, C. J. Baglolle, M. F. Desimone and D. Maysinger, *Food Chem. Toxicol.*, 2017, **109**, 753–770.
- 12 T. I. Janjua, Y. Cao, C. Yu and A. Popat, *Nat. Rev. Mater.*, 2021, **6**, 1072–1074.
- 13 G. Oberdörster, E. Oberdörster and J. Oberdörster, *Environ. Health Perspect.*, 2005, **113**, 823–839.
- 14 J. G. Croissant, K. S. Butler, J. I. Zink and C. J. Brinker, *Nat. Rev. Mater.*, 2020, **5**, 886–909.
- 15 J. G. Croissant, Y. Fatieiev, A. Almalik and N. M. Khashab, *Adv. Healthcare Mater.*, 2018, **7**, 1–75.
- 16 A. Ale, M. F. Gutierrez, A. S. Rossi, C. Bacchetta, M. F. Desimone and J. Cazenave, *Environ. Toxicol. Pharmacol.*, 2021, **87**, 103689.
- 17 M. C. De Marzi, M. Saraceno, R. Mitarotonda, M. Todone, M. Fernandez, E. L. Malchiodi and M. F. Desimone, *Ther. Delivery*, 2017, **8**, 1035–1049.
- 18 R. Mitarotonda, M. Saraceno, M. Todone, E. Giorgi, E. L. Malchiodi, M. F. Desimone and M. C. De Marzi, *Ther. Delivery*, 2021, **12**, 443–459.
- 19 V. S. Andrade, A. Ale, S. Municoy, C. Bacchetta, M. F. Desimone, M. F. Gutierrez and J. Cazenave, *Environ. Toxicol. Pharmacol.*, 2023, **102**, 104238.
- 20 J. Saikia, M. Yazdimaghani, S. P. Hadipour Moghaddam and H. Ghandehari, *ACS Appl. Mater. Interfaces*, 2016, **8**, 34820–34832.
- 21 K. Saha, D. F. Moyano and V. M. Rotello, *Mater. Horiz.*, 2014, **1**, 102–105.
- 22 S. Dominguez-Medina, J. Blankenburg, J. Olson, C. F. Landes and S. Link, *ACS Sustainable Chem. Eng.*, 2013, **1**, 833–842.
- 23 B. E. Givens, Z. Xu, J. Fiegel and V. H. Grassian, *J. Colloid Interface Sci.*, 2017, **493**, 334–341.
- 24 N. El Kadi, N. Taulier, J. Y. Le Huérou, M. Gindre, W. Urbach, I. Nwigwe, P. C. Kahn and M. Waks, *Biophys. J.*, 2006, **91**, 3397–3404.
- 25 H. Larsericsdotter, S. Oscarsson and J. Buijs, *J. Colloid Interface Sci.*, 2005, **289**, 26–35.
- 26 M. Winiewska, K. Szewczuk-Karpisz and D. Sternik, *J. Therm. Anal. Calorim.*, 2015, **120**, 1355–1364.
- 27 S. J. McClellan and E. I. Franses, *Colloids Surf., A*, 2005, **260**, 265–275.
- 28 V. H. Nguyen and B. J. Lee, *Int. J. Nanomed.*, 2017, **12**, 3137–3151.
- 29 N. Kaneko, M. Kurata, T. Yamamoto, S. Morikawa and J. Masumoto, *Inflammation Regener.*, 2019, **39**, 1–16.
- 30 R. Bent, L. Moll, S. Grabbe and M. Bros, *Int. J. Mol. Sci.*, 2018, **19**, 2155.
- 31 M. Morikawa, R. Derynck and K. Miyazono, *Cold Spring Harbor Perspect. Biol.*, 2016, **8**, a021873.
- 32 R. Mitarotonda, E. Giorgi, T. Eufrazio-da-Silva, A. Dolatshahi-Pirouz, Y. K. Mishra, A. Khademhosseini, M. F. Desimone, M. De Marzi and G. Orive, *Biomater. Adv.*, 2022, **135**, 212726.
- 33 K. Schuhladen, L. Stich, J. Schmidt, A. Steinkasserer, A. R. Boccaccini and E. Zinser, *Biomater. Sci.*, 2020, **8**, 2143–2155.
- 34 K. Zheng, W. Niu, B. Lei and A. R. Boccaccini, *Acta Biomater.*, 2021, **133**, 168–186.
- 35 I. Lukin, I. Erezuma, M. F. Desimone, Y. S. Zhang, A. Dolatshahi-Pirouz and G. Orive, *Biomater. Adv.*, 2023, **154**, 213637.
- 36 W. Stöber, A. Fink and E. Bohn, *J. Colloid Interface Sci.*, 1968, **26**, 62–69.
- 37 F. G. Baudou, L. Fusco, E. Giorgi, E. Diaz, S. Municoy, M. F. Desimone, L. Leiva and M. C. De Marzi, *Colloids Surf., B*, 2020, **193**, 111128.
- 38 C. A. Schneider, W. S. Rasband and K. W. Eliceiri, *Nat. Methods*, 2012, **9**, 671–675.
- 39 B. Ledesma, E. Sabio, C. M. González-García, S. Román, M. E. Fernandez, P. Bonelli and A. L. Cukierman, *Processes*, 2023, **11**, 1–22.
- 40 A. Beganskienė, V. Sirutkaitis, A. Kareiva, M. Kurtinaitienė and R. Juškėnas, *Mater. Sci.*, 2004, **10**, 287–290.
- 41 M. M. Bradford, *Anal. Biochem.*, 1976, **72**, 248–254.
- 42 T. Zor and Z. Selinger, *Anal. Biochem.*, 1996, **236**, 302–308.
- 43 K. Y. Foo and B. H. Hameed, *Chem. Eng. J.*, 2010, **156**, 2–10.
- 44 I. Langmuir, *J. Am. Chem. Soc.*, 1918, **60**, 1361–1403.
- 45 M. Naderi, *Prog. Filtr. Sep.*, 2015, 585–608.
- 46 M. S. Ali, M. J. Uttinger, S. Romeis, J. Schmidt and W. Peukert, *Colloids Surf., B*, 2022, **214**, 112466.
- 47 Ł. Zych, A. M. Osyczka, A. Łącz, A. Różycka, W. Niemiec, A. Rapacz-Kmita, E. Dzierzkowska and E. Stodolak-Zych, *Materials*, 2021, **14**, 1–17.
- 48 B. E. Givens, N. D. Diklich, J. Fiegel and V. H. Grassian, *Biointerphases*, 2017, **12**, 02D404.
- 49 S. Tenzer, D. Docter, S. Rosfa, A. Wlodarski, A. Rezik, S. K. Knauer, C. Bantz, T. Nawroth, C. Bier, J. Sirirattanapan, W. Mann, L. Treuel, R. Zellner, M. Maskos and R. H. Stauber, *Am. Chem. Soc. NANO*, 2011, **5**, 7155–7167.
- 50 L. A. Villarruel, B. Brie, S. Municoy, D. Becú-Villalobos, M. F. Desimone and P. N. Catalano, *Int. J. Pharm.*, 2023, **634**, 122662.



- 51 K. Fujio, T. Komai, M. Inoue, K. Morita, T. Okamura and K. Yamamoto, *Autoimmun. Rev.*, 2016, **15**, 917–922.
- 52 M. O. Li, Y. Y. Wan, S. Sanjabi, A. K. Robertson and R. A. Flavell, *Annu. Rev. Immunol.*, 2006, **24**, 99–146.
- 53 M. Kupani, S. Sharma, R. K. Pandey, R. Kumar, S. Sundar and S. Mehrotra, *Front. Cell. Infect. Microbiol.*, 2021, **10**, 1–9.
- 54 Y. Vodovotz and C. Bogdan, *Prog. Growth Factor Res.*, 1994, **5**, 341–351.
- 55 C. D. Mills, K. Kincaid, J. M. Alt, M. J. Heilman and A. M. Hill, *J. Immunol.*, 2000, **164**, 6166–6173.
- 56 D. Zheng, T. Chen, L. Han, S. Lv, J. Yin, K. Yang, Y. Wang and N. Xu, *Int. Wound J.*, 2022, **19**, 1023–1038.
- 57 H. Shen, H. Lin, A. X. Sun, S. Song, B. Wang, Y. Yang, J. Dai and R. S. Tuan, *Acta Biomater.*, 2020, **105**, 44–55.

