

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Effect of ordering of PtCu₃ nanoparticle structure on the activity and stability for the oxygen reduction reaction

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Nejc Hodnik,^{a,b*}, Chinnaya Jeyabharathi,^{a,c} Josef C. Meier,^a Alexander Kostka,^a Kanala L. N. Phani,^c Aleksander Rečnik,^d Marjan Bele,^b Stanko Hočevár,^b Miran Gaberšček^{a*} and Karl J. J. Mayrhofer^{a*},

In this study the performance enhancement effect of structural ordering for the oxygen reduction reaction (ORR) is systematically studied. Two samples of PtCu₃ nanoparticles embedded on a graphitic carbon support are carefully prepared with identical initial composition, particle dispersion and size distribution, yet with different degrees of structural ordering. Thus we can eliminate all coinciding effects and unambiguously relate the improved activity for the ORR and more importantly the enhanced stability to the ordered nanostructure. Interestingly, the electrochemically induced, morphological changes are common to both ordered and disordered samples. The observed effect could have a groundbreaking impact on the future directions in the rational design of active and stable platinum alloyed ORR catalysts.

Introduction

The oxygen reduction reaction (ORR) is the essential process in low- to medium-temperature polymer electrolyte membrane fuel cells. In contrast to its anodic counterpart, i.e., the hydrogen oxidation reaction, the electrocatalysis of this cathodic reaction suffers from large overpotentials and thus limits the overall performance of the cell. Researchers across the globe are therefore investing large efforts to develop both, active and durable industrial electrocatalysts beyond the so far state-of-the-art material Pt/C, besides trying to reduce or even eliminate the noble metal content.^{1,2} However, non-noble metal or metal-free catalysts still have low mass activity and poor stability under the harsh operating conditions in fuel cells. Pt based alloy electrodes have shown promising mass activities of 2-5 times higher than pure Pt, while at the same time reducing the noble metal content.² This enhancement is due to lower adsorption energies of blocking hydroxyl species (OH_{ad}), yielding higher number of active sites available for the ORR at comparable overpotentials.³⁻¹⁰ This holds even after removal of the transition metal from the catalyst surface and formation of a Pt rich shell, as the several times higher activity¹¹ is retained

due to the electronic (ligand effect) and geometric (strain effect) influence of the alloying element inside the core.^{7, 12, 13} Upon selective leaching of the non-noble transition metal, either naturally under operating conditions or intentionally as a pretreatment, several special structures have been obtained, such as for instance Pt-skeleton shell/alloy-core¹⁴, Pt-skin shell/alloy core¹⁵, strained Pt shell/alloy-core⁷, strained Pt shell/multi-core¹⁶ and “Swiss cheese” type porous particles.¹⁷ Thereby, the obtained structure depends on several parameters, such as the synthesis conditions, the initial composition^{5, 13} and the size of the alloyed material^{8, 13, 18-20}, as well as on the type of dealloying protocol used, e.g. chemical or electrochemical^{6, 9}. An important parameter that seems to have significant impact on the final properties of electrochemically treated Pt-alloys is the effect of structural ordering, as shown for the ORR activity in PtCu,^{9, 17, 21} PtFe^{22, 23} and PtCo²⁴⁻²⁶ systems. The stability of the so-called intermetallic Pt-alloys, in contrast to disordered structures or solid solutions, is however poorly understood. One reason is that the impact of structural ordering is difficult to differentiate from other effects, such as varying composition and particle size distribution³¹ resulting from different

synthesis and pretreatment conditions, especially during annealing.²⁴⁻²⁶ In this study we eliminate all these coinciding effects and unambiguously demonstrate an improved activity and even more important an enhanced stability of a partially ordered catalyst, exemplified by a PtCu₃.

Experimental

PtCu₃ alloy nanoparticles supported on commercially available graphite support (Vulcan XC72R) were synthesized by a modified sol-gel method, and alloying of Pt with Cu was achieved by thermal annealing (above 700 °C) as described in the patent literature.^{19, 27} The catalyst composite contains 23.8 wt.% Cu and 25.5 wt.% Pt. The partially ordered analogue consisting of a combination of ordered (Pm $\bar{3}$ m) and disordered (Fm $\bar{3}$ m) structure was obtained by setting the temperature below the order-disorder transition temperature (~550 °C) so that the system attained thermodynamic equilibrium. By contrast, a completely disordered analogue PtCu₃ (s.s.; Fm $\bar{3}$ m structure) was obtained from the partially ordered material by heating to 700 °C, above the disorder-order transition temperature, and quenching in liquid nitrogen.

Results and discussion

Exemplary HR-TEM study of a single PtCu₃ particle with XRD spectra are shown in Figure 1 a); a more detailed structural analysis of both analogues is given in the Supporting info S1. The partially ordered material consists of a rather thick, ordered (Pm $\bar{3}$ m) shell (Fig. 1 c) around a predominantly disordered (Fm $\bar{3}$ m) core (Fig. 1 d). Despite the fact that no complete ordering of the entire nanoparticle is achieved, the material can still be considered as an “ordered material” for catalysis, where surface properties are decisive. In contrast, the structure of the quenched sample is found completely “disordered” with only pure Fm $\bar{3}$ m reflections within the nanoparticles. Except for these crucial differences in the surface structure, both catalysts are embedded in the same type of carbon support and exhibit identical particle size distributions as well as composition.

To study the electrochemical stability of ordered and disordered nanoparticles, both samples were subjected to identical treatments, as shown in Figure 2. Initial dealloying consisted of either 500 potential cycles from 0.05 to 1.2 V_{RHE} (0.2 V s⁻¹) or application of a constant potential at 1.2 V_{RHE} for 2 hours (the time equivalent to 500 cycles), both followed by a subsequent degradation protocol of 7000 cycles (see schematic of experiments in Fig. 2a). Thereby the surface area was continuously monitored over time, and after each individual treatment also the ORR activity was measured. The microstructural changes during different electrochemical treatments were investigated by identical location transmission microscopy (IL-TEM), and the impact of the degradation

protocol on this type of catalyst has been reported.⁸ Here, those results are further analyzed for a comparison between the behavior of the ordered and disordered analogues. Interestingly, despite the structural differences of the two samples, the morphological investigation before, during and after the electrochemical treatments reveal the same main patterns and trends for degradation in both samples (Fig. 2 b). So, for example, the quite wide, identical particle size distribution between 5 and 50 nm (see Supporting info S2.1) for both samples does not change essentially during the electrochemical treatment. Although, the catalyst particles of sizes ~ 10 - 20 nm changed their shape to faceted structures during initial 500 potential cycles (for more images and IL-tomography see Supp. Info S2.2 and S2.4 – or link to a movie), whereas only porosity was observed after holding a potential at 1.2 V_{RHE}, in the larger particles a gradual development of porosity with degradation time is observed in both samples.

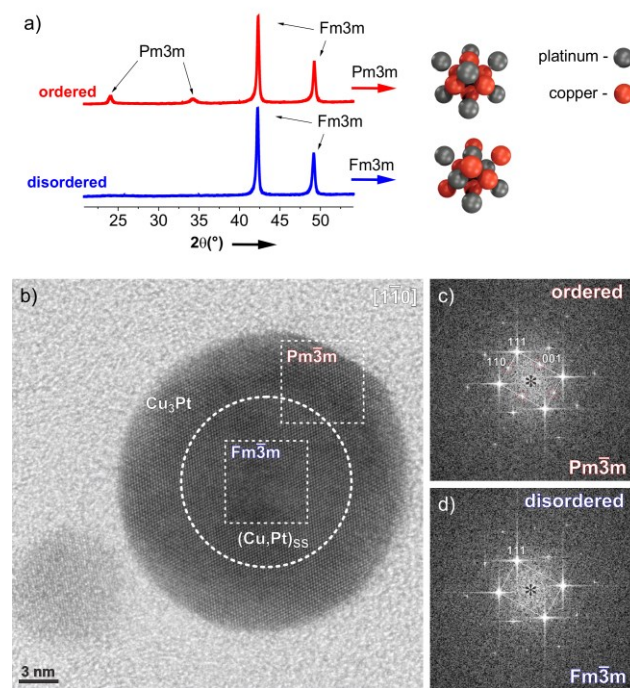


Figure 1. a) XRD patterns of ordered and disordered carbon supported PtCu₃ samples together with a representative Pm $\bar{3}$ m and Fm $\bar{3}$ m atomic arrangements, illustrated on the right. Structural analysis of partially ordered PtCu₃ nanoparticles. b) HRTEM image of a single PtCu₃ nanoparticle crystal oriented along the crystallographic [11-0] axis showing an apparent core-shell disordered-ordered structure. Averaged FFT power spectra for the (c) shell region with additional symmetry-specific Pm $\bar{3}$ m reflections (indicated with 110 and 001); and the (d) core Fm $\bar{3}$ m region without the super-structure reflections.

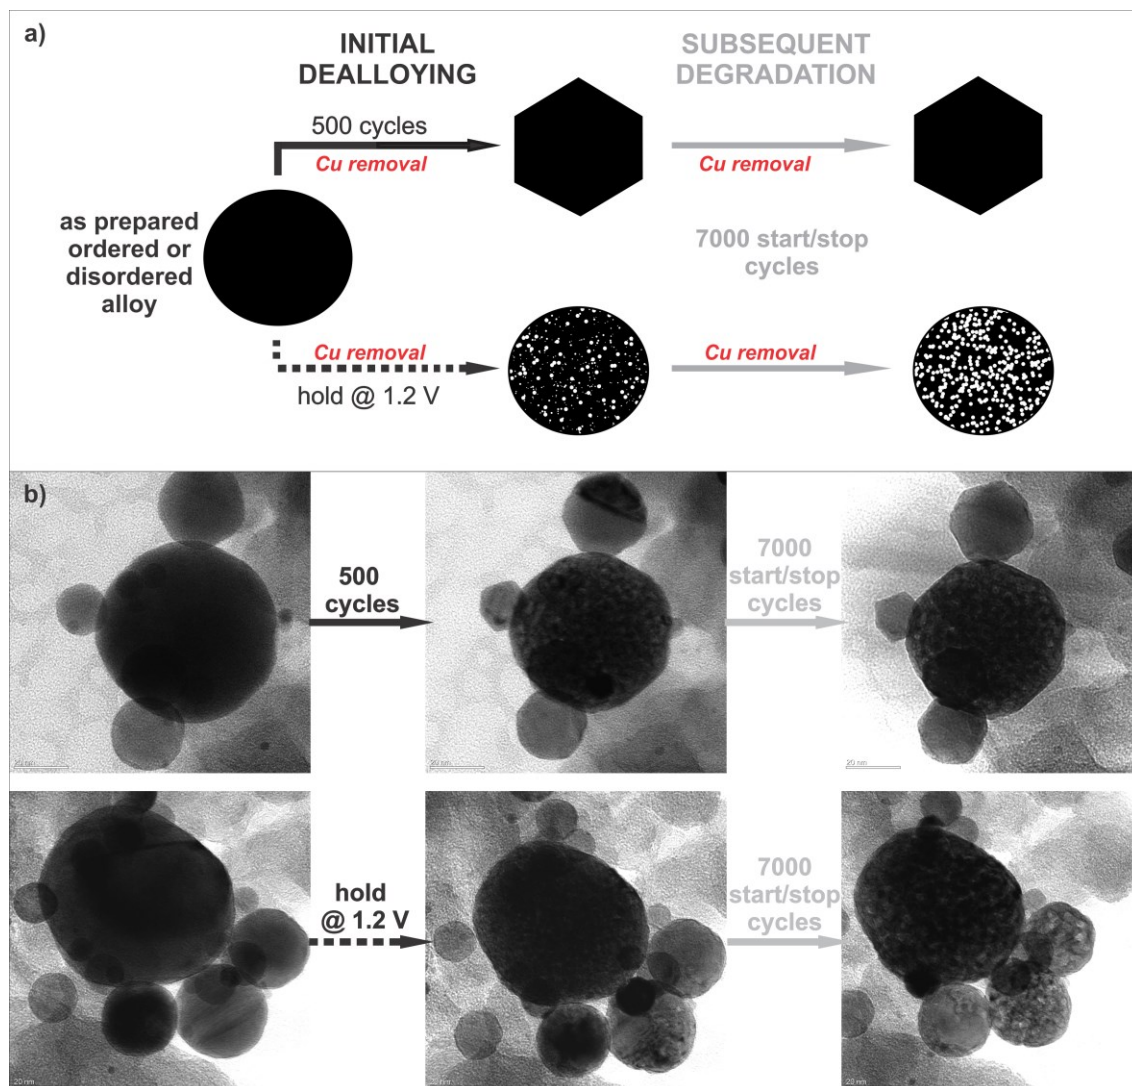


Figure 2: Electrochemical stability of the PtCu_3 nanocrystals. a) Schematic presentation of two types of electrochemical treatment protocols. Initial dealloying stage leads to a surface structure with reproducible activities, whereas the prolonged subsequent degradation gives a true insight into the stability of the catalyst. b) IL-TEM micrographs of disordered catalysts before, after initial dealloying and subsequent degradation. The upper sequence corresponds to dealloying with 500 potential cycles ($1.2 \text{ V}_{\text{RHE}}$ upper limit), the lower one to dealloying with hold at $1.2 \text{ V}_{\text{RHE}}$ for 2 hours.

Finally, in the light of the so-called proximity effect described in the recent paper of Nesselberger et al.²⁸, also no significant differences in the average distance between the particles were observed. Namely, the temperature treatment of both samples differs only in the last post-treatment stage, where the nanoparticles have already achieved their final state on the carbon matrix (see S2.3). If there is any effect of proximity it is identical for both catalysts.

Despite the obvious congruency in the evolution of the microstructure, certain remarkable differences in the development of the electrochemical behaviour of the ordered and disordered samples appear in the cyclic voltammograms (Fig. 3). The copper dissolution from the alloy, as represented by two peaks, denoted Cu_{Bulk} and Cu_{UPD} in Figs. 3a and b, appear at about 0.4 V and span up to 0.9 V . The Cu_{Bulk}

dissolution, which reflects the dissolution of copper that is coordinated mainly to other copper atoms in the alloy, is more or less common to both samples. However, the position and shape of the Cu_{UPD} peak/shoulder that represents dissolution of various Pt-coordinated Cu atoms (denoted also underpotential deposition - UPD) is quite different.^{29, 30} The peak potential is shifted by approximately 250 mV more positive for the ordered material, due to the increased statistical probability of copper atoms being coordinated to platinum. Moreover, in the H_{UPD} and the initial Pt oxidation region of the disordered catalyst (marked as 1 and 2 in Fig. 3d, respectively), additional “Cu oxidation” peaks seem to emerge. Considering that the surface prior to the 40th cycle is free from Cu oxidation and the H_{UPD} has already started to evolve, this might be explained by additional Cu from beneath the surface becoming exposed and

finally dissolved. Another explanation could be the formation of some new metastable surface Pt facet which then after 100 starts to gradually disappear (see sup. info. Fig. 3). In contrast, the transition from a Cu-rich to a Cu-depleted phase is smooth in the ordered catalyst, i.e. after the removal of all surface Cu a well-defined cyclic voltammogram for Pt continuously emerges indicating a quicker formation of a protective Pt shell. Notably, regardless of these differences, after about 500 cycles the CVs of both materials attain a pure Pt signature with typical H_{UPD}

and Pt-oxidation features and identical surface area. It is interesting that a similar, pure Pt-like CV is also obtained after dealloying by potential hold for 2 hours at 1.2 V_{RHE} (figure 3e and f). However, after cycling three H-oxidation/reduction peaks can be observed, while after potential hold these peaks overlap and are less defined. This can be explained by the formation of shaped nanoparticles in the cycling treatment, whereas in the potential hold experiment the initial shape is more or less preserved (see Fig. 2).⁸

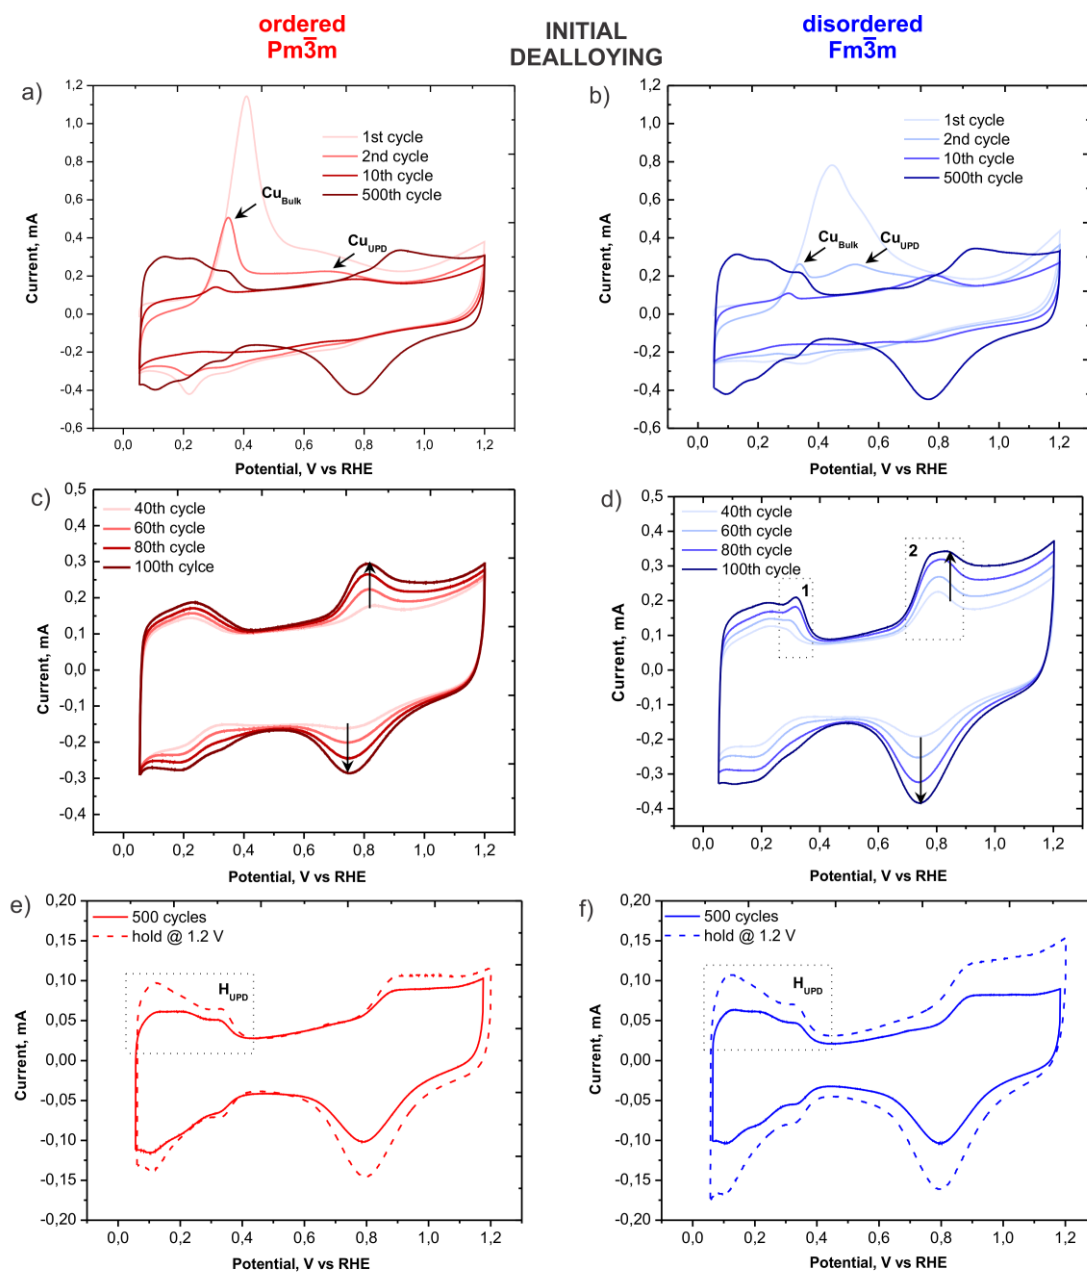


Figure 3. Selected cyclic voltammograms of the continuously recorded scans during dealloying with 500 cycles of the ordered Pm $\bar{3}$ m (a, c; red) and the disordered Fm $\bar{3}$ m (b, d; blue) catalyst, recorded at a scan rate of 0.2 Vs⁻¹. Comparison of the baseline scans of the ordered (e) and the disordered (f) catalyst after dealloying by cycling (solid line) and potential hold @ 1.2 V for 2 hours (dashed line), recorded at a scan rate 0.05 Vs⁻¹ in 0.1 M HClO₄.

The activity of both catalysts towards ORR has been determined by voltammetry after each electrochemical treatment using a rotating disk electrode (RDE, see Supporting info S3 for more detail). The specific activity (SA) of the ordered catalyst is significantly and consistently higher than the SA of its disordered analogue at all states (see the bar chart in Fig. 4a). For example, after the initial 500 potential cycles the activity of the ordered catalyst is $2.5 \text{ mA cm}^{-2}_{\text{Pt}}$, whereas the disordered exhibits activity of $1.78 \text{ mA cm}^{-2}_{\text{Pt}}$. An even greater difference, i.e. $2.4 \text{ mA cm}^{-2}_{\text{Pt}}$ vs $1.5 \text{ mA cm}^{-2}_{\text{Pt}}$, can be observed after the potential hold treatment (2 h at 1.2 V), the full comparison of activity at all conditions studied is provided in the Supporting info Tables S3.1 and S3.2.

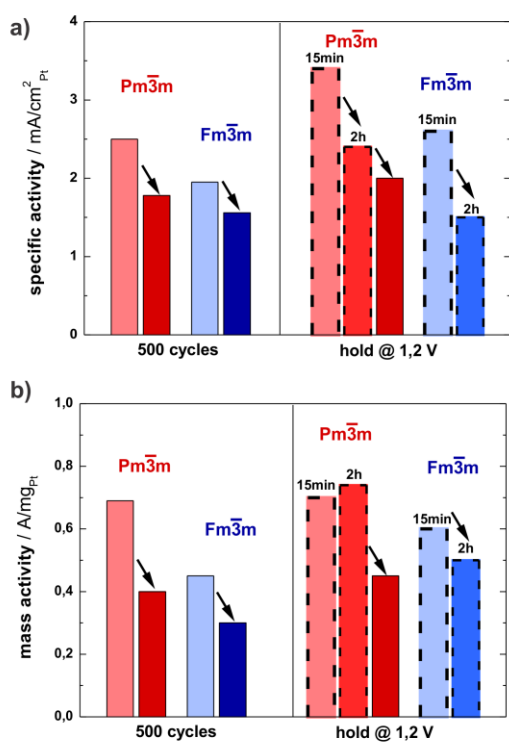


Figure 4. Comparison of a) specific and b) mass activities @ $0.9 V_{\text{RHE}}$ of the ordered (red) and the disordered (blue) catalysts after dealloying (500 cycles and potential hold @ 1.2 V for 15 min and 2 hours, respectively) and subsequent degradation (dark red and dark blue color). No subsequent degradation after holding the potential at $1.2 V_{\text{RHE}}$ was done for the disordered catalyst.

Moreover, the mass activity (MA) of the ordered phase is also significantly higher than for the disordered one, but follows the same declining trend as the absolute surface area over time (Fig. 4b). Only the mass activity of the ordered catalyst after 2 hours hold is somewhat higher than after 15 min, which is due to the increase in ECSA by the porosity formation.

The significantly higher specific activity of the ordered phase could have several origins. Firstly, after a typical electrochemical treatment the ordered phase is able to retain more copper than the disordered one. This hypothesis, which stems from the cyclic voltammograms, is confirmed by post-mortem ICP-MS analysis of the electrolyte after various electrochemical treatments: the amount of Cu leached out of the alloy is always higher in the case of the disordered catalyst. Therefore all data on the disordered sample with comparable treatment are shifted to higher values of removed copper as seen in Fig. 5. Specifically, after the initially 500 potential cycles 56 % of copper is removed from the ordered catalyst, whereas as much as 73 % of Cu is removed from the disordered one. Similarly, after a potential hold treatment (2 h at 1.2 V) the ordered catalyst loses about 80 % of the initial copper, while the loss in the disordered phase is close to 90 %. For more details see table S4 in Supporting info, where all the ICP-MS experimental data are summarized. It should be noted that the platinum content in the electrolyte is always below 0.1%. The difference in the electrochemical stability of Cu in the two alloys studied can be correlated with the unequal surface structure, since the number of Cu-Cu and Pt-Cu bonds per unit cell of the pristine ordered and disordered catalysts varies. In the ordered phase there are statistically 24 Cu-Cu bonds and 24 Pt-Cu bonds, while in the disordered structure there are 27 Cu-Cu, 18 Pt-Cu, and 3 Pt-Pt bonds per unit cell on average. As the Cu dissolution potential from a copper substrate is much lower than from platinum ($0.34 \text{ V} < 0.7 \text{ V}$)^{18,29}, the higher number of stronger Pt-Cu bonds in the ordered phase results in a less Cu leaching. In turn, more residual Cu in the ordered alloy nanoparticles leads to an activity increase due to an enhanced ligand and/or strain effect. The effect of “copper retention” on alloy activity is reflected by an activity increase due to a horizontal shift along the x-axis denoted as “ligand/strain effect”.

Obviously, as can be seen in Fig. 5, the larger quantity of residual copper is not the only source of the activity enhancement. A remarkable increase in the activity remains when comparing the ordered and disordered alloys with the hypothetically same amount of residual copper, as indicated by the vertical shift denoted as “ordering effect” in Fig. 5. A similar effect of structural ordering on activity has been observed recently in selected other alloys PtCu^{9, 17, 21}, PtFe^{22, 23}, or PtCo.²⁴⁻²⁶ The underlying mechanism is however still unclear. One possibility is that structural ordering changes the lateral strain in the Pt-skin overlayer and hence changes the binding energies of adsorbates.⁷ Another possibility is that dealloying from the ordered structure results in a skin rather than skeleton type morphology and affects the structural sensitive ORR.^{14, 15, 31} Regardless of the exact mechanism, the present experimental results demonstrate clearly the positive effect of structural ordering on the activity of selected alloy throughout a prolonged testing in different electrochemical regimes, and independent of other material parameters influenced by synthesis and pretreatment conditions.

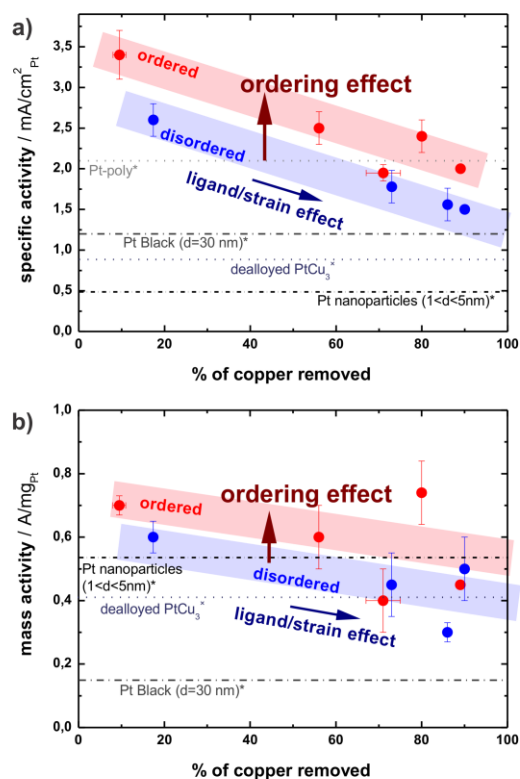


Figure 5: a) Specific activity and b) mass activity in relation to the copper content of the electrolyte upon different electrochemical treatments (dealloying and subsequent degradation). Activities of Pt-poly, Pt-black, dealloyed PtCu₃ and Pt nanoparticles are taken from references (*)³² and (×)¹⁸.

Conclusions

Based on a comparison of carefully prepared samples we have shown the significant, systematic effect of structural ordering on activity and stability of PtCu₃ nanoparticles. Two catalysts exhibit identical initial bulk composition, particle dispersion and size distribution, with the only difference being the degree of structural order induced by different thermal annealing. Expectedly, the activity of both alloys decreases with the increasing time of exposure to harsh electrochemical treatment conditions. However, regardless of the degradation/dealloying treatment, the partially ordered structure (Pm3m) contains significantly (20-30%) higher specific activity compared to the fully disordered sample. At least two effects lead to the improved performance of the ordered catalyst: 1) a better retention of copper inside the ordered structure after a given treatment and 2) an intrinsic structural effect on the alloy activity. The latter could be due to modified lateral strain in the Pt skin⁷ overlayer and/or due to the different morphology of the de-alloyed material.¹⁴

Acknowledgements

The work was financed in part through the Slovenian Centre of Excellence Low Carbon Technologies (CO NOT). We would also like to thank Andrea Mingers, Milena Zorko and Barbara Jozinović for their assistance and professional graphic designer Jaka Birsa for his help with TOC.

Notes and references

^a Max-Planck-Institut für Eisenforschung GmbH, Max-Planck Str. 1, 40237 Düsseldorf Germany.

^b National Institute of Chemistry, Hajdrihova 19, 1000 Ljubljana, Slovenia.

^c CSIR-Central Electrochemical Research Institute, Karaikudi 630 006, Tamil Nadu, India.

^d [†]Department for Nanostructured Materials, Jožef Stefan Institute, Ljubljana, 1000, Slovenia.

† Electronic Supplementary Information (ESI) available: Description of structural, electrochemical, ICP-MS and IL-TEM characterization methods and experimental conditions. Dealloying cyclic voltammograms (500 cycles), ORR polarisation curves and SEM pictures of ordered and disordered catalysts. IL-TEM, IL-tomography movie and TEM images of ordered catalysts. 3 tables with ORR activities (mass and specific) and ECSA measured after all electrochemical treatments together with copper content data. See DOI: 10.1039/b000000x/

1. A. Rabis, P. Rodriguez and T. J. Schmidt, *ACS Catalysis*, 2012, 2, 864-890.
2. M. K. Debe, *Nature*, 2012, 486, 43-51.
3. S. Mukerjee, S. Srinivasan, M. P. Soriaga and J. McBreen, *Journal of The Electrochemical Society*, 1995, 142, 1409-1422.
4. V. R. Stamenkovic, B. Fowler, B. S. Mun, G. Wang, P. N. Ross, C. A. Lucas and N. M. Markovic, *Science*, 2007, 315, 493-497.
5. L. Gan, M. Heggen, S. Rudi and P. Strasser, *Nano Letters*, 2012, 12, 5423-5430.
6. L. Gan, M. Heggen, R. O'Malley, B. Theobald and P. Strasser, *Nano Letters*, 2013, 13, 1131-1138.
7. P. Strasser, S. Koh, T. Anniyev, J. Greeley, K. More, C. Yu, Z. Liu, S. Kaya, D. Nordlund, H. Ogasawara, M. F. Toney and A. Nilsson, *Nature chemistry*, 2010, 2, 454-460.
8. C. Jeyabharathi, N. Hodnik, C. Baldizzone, J. C. Meier, M. Heggen, K. L. N. Phani, M. Bele, M. Zorko, S. Hocevar and K. J. J. Mayrhofer, *ChemCatChem*, 2013, 5, 2627-2635.
9. D. Wang, Y. Yu, H. L. Xin, R. Hovden, P. Ercius, J. A. Mundy, H. Chen, J. H. Richard, D. A. Muller, F. J. DiSalvo and H. D. Abruña, *Nano Letters*, 2012, 12, 5230-5238.
10. N. Hodnik, M. Bele and S. Hocevar, *Electrochemistry Communications*, 2012, 23, 125-128.
11. R. Srivastava, P. Mani, N. Hahn and P. Strasser, *Angewandte Chemie International Edition*, 2007, 46, 8988-8991.
12. J. Greeley, I. E. Stephens, A. S. Bondarenko, T. P. Johansson, H. A. Hansen, T. F. Jaramillo, J. Rossmeisl, I. Chorkendorff and J. K. Nørskov, *Nature chemistry*, 2009, 1, 552-556.
13. J. Snyder, I. McCue, K. Livi and J. Erlebacher, *Journal of the American Chemical Society*, 2012, 134, 8633-8645.
14. V. R. Stamenkovic, B. S. Mun, M. Arenz, K. J. J. Mayrhofer, C. A. Lucas, G. Wang, P. N. Ross and N. M. Markovic, *Nat Mater*, 2007, 6, 241-247.
15. C. Wang, M. Chi, D. Li, D. Strmcnik, D. van der Vliet, G. Wang, V. Komanicky, K. C. Chang, A. P. Paulikas, D. Tripkovic, J. Pearson, K. L. More, N. M. Markovic and V. R. Stamenkovic, *Journal of the American Chemical Society*, 2011, 133, 14396-14403.
16. M. Heggen, M. Oezaslan, L. Houben and P. Strasser, *The Journal of Physical Chemistry C*, 2012, 116, 19073-19083.

17. I. Dutta, M. K. Carpenter, M. P. Balogh, J. M. Ziegelbauer, T. E. Moylan, M. H. Atwan and N. P. Irish, *The Journal of Physical Chemistry C*, 2010, 114, 16309-16320.
18. M. Oezaslan, M. Heggen and P. Strasser, *Journal of the American Chemical Society*, 2011, 134, 514-524.
19. N. Hodnik, M. Zorko, M. Bele, S. Hočevar and M. Gaberšček, *The Journal of Physical Chemistry C*, 2012, 116, 21326-21333.
20. I. McCue, J. Snyder, X. Li, Q. Chen, K. Sieradzki and J. Erlebacher, *Physical Review Letters*, 2012, 108, 225503.
21. N. Hodnik, M. Bele, A. Rečnik, N. Z. Logar, M. Gaberšček and S. Hočevar, *Energy Procedia*, 2012, 29, 208-215.
22. H. Chen, D. Wang, Y. Yu, K. A. Newton, D. A. Muller, H. Abruña and F. J. DiSalvo, *Journal of the American Chemical Society*, 2012, 134, 18453-18459.
23. J. Kim, Y. Lee and S. Sun, *Journal of the American Chemical Society*, 2010, 132, 4996-4997.
24. D. Wang, H. L. Xin, R. Hovden, H. Wang, Y. Yu, D. A. Muller, F. J. DiSalvo and H. D. Abruña, *Nat Mater*, 2013, 12, 81-87.
25. M. Watanabe, K. Tsurumi, T. Mizukami, T. Nakamura and P. Stonehart, *Journal of The Electrochemical Society*, 1994, 141, 2659-2668.
26. S. Koh, M. F. Toney and P. Strasser, *Electrochimica Acta*, 2007, 52, 2765-2774.
27. M. Bele, M. Gaberšček, G. Kapun, N. Hodnik and S. Hočevar, *Electrocatalytic Composite(s), Associated Composition(s) and Associated Process(es): Patentna Prijava : US Appln*, United States Patent and Trademark Office, 2011.
28. M. Nesselberger, M. Roefzaad, R. Fayçal Hamou, P. Ulrich Biedermann, F. F. Schweinberger, S. Kunz, K. Schloegl, G. K. H. Wiberg, S. Ashton, U. Heiz, K. J. J. Mayrhofer and M. Arenz, *Nat Mater*, 2013, advance online publication.
29. P. Strasser, S. Koh and J. Greeley, *Physical Chemistry Chemical Physics*, 2008, 10, 3670-3683.
30. D. M. Kolb, M. Przasnyski and H. Gerischer, *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry*, 1974, 54, 25-38.
31. D. F. van der Vliet, C. Wang, D. Tripkovic, D. Strmcnik, X. F. Zhang, M. K. Debe, R. T. Atanasoski, N. M. Markovic and V. R. Stamenkovic, *Nature materials*, 2012, 11, 1051-1058.
32. M. Nesselberger, S. Ashton, J. C. Meier, I. Katsounaros, K. J. J. Mayrhofer and M. Arenz, *Journal of the American Chemical Society*, 2011, 133, 17428-17433.