

Cite this: *Chem. Sci.*, 2020, **11**, 5339

All publication charges for this article have been paid for by the Royal Society of Chemistry

## Observation of binding of carbon dioxide to nitro-decorated metal–organic frameworks†‡

Thien D. Duong,<sup>a</sup> Sergey A. Sapchenko,<sup>abc</sup> Ivan da Silva,<sup>d</sup> Harry G. W. Godfrey,<sup>a</sup> Yongqiang Cheng,<sup>e</sup> Luke L. Daemen,<sup>e</sup> Pascal Manuel,<sup>d</sup> Mark D. Frogley,<sup>f</sup> Gianfelice Cinque,<sup>f</sup> Anibal J. Ramirez-Cuesta,<sup>de</sup> Sihai Yang<sup>de</sup>\*<sup>a</sup> and Martin Schröder<sup>de</sup>\*<sup>a</sup>

Metal–organic frameworks (MOFs) functionalised with amine, amide and hydroxyl groups show great promise for CO<sub>2</sub> binding due to their ability to form hydrogen bonds to CO<sub>2</sub>. Herein we report the adsorption and selectivity of CO<sub>2</sub> in four iso-reticular MOFs adopting the NbO topology. Functionalisation of the parent MOF, MFM-102, with –NO<sub>2</sub>, –NH<sub>2</sub> and alkyl groups leads to an enhancement of CO<sub>2</sub> adsorption of up to 36% for the NO<sub>2</sub>-decorated MOF and with raised selectivity. MFM-102-NO<sub>2</sub> shows the highest adsorption capacity for CO<sub>2</sub> (184 cm<sup>3</sup> g<sup>−1</sup> at 273 K and 1.0 bar) within this series, comparable to the best-behaving iso-reticular MOFs. At 298 K and 1.0 bar, MFM-102-NO<sub>2</sub> shows a CO<sub>2</sub>/CH<sub>4</sub> selectivity of 5.0. *In situ* inelastic neutron scattering and synchrotron FT-IR micro-spectroscopy were employed to elucidate the host–guest interaction dynamics within CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub>. Neutron powder diffraction enabled the direct observation of the preferred binding domains in MFM-102-NO<sub>2</sub>, and, to the best of our knowledge, we report the first example of CO<sub>2</sub> binding to a –NO<sub>2</sub> group in a porous MOF. Synergistic effects between the –NO<sub>2</sub> group and the open metal sites lead to optimal binding of CO<sub>2</sub> molecules within MFM-102-NO<sub>2</sub> via hydrogen bonding to C–H groups.

Received 25th August 2019  
Accepted 26th February 2020

DOI: 10.1039/c9sc04294f

rsc.li/chemical-science

## Introduction

Emissions of carbon dioxide (CO<sub>2</sub>) are causing significant environmental impacts.<sup>1</sup> However, CO<sub>2</sub> is also an inexpensive, non-toxic and a potentially abundant renewable C<sub>1</sub> source, and, therefore, the development of cost-effective and efficient methods for carbon capture and storage (CCS) is a major target. State-of-the-art CCS is often based upon scrubbing systems that rely heavily upon the use of toxic and corrosive amines, and

require high operational cost. In contrast, reversible physisorption of CO<sub>2</sub> within porous materials is a promising approach with the potential of low running-cost and high efficiency. A wide spectrum of materials, such as zeolites, activated carbons, ionic liquids and silica-based materials have been investigated for CO<sub>2</sub> adsorption.<sup>2–5</sup>

Metal–organic framework (MOF) materials show potential for gas adsorption and storage owing to their high porosity and designed pore size and structure reflecting their versatility via incorporation of active binding sites by decoration of the pores with functional groups and/or by incorporation of open metal sites.<sup>6,7</sup> MOFs decorated with –NH<sub>2</sub>,<sup>8</sup> –OH,<sup>9</sup> –CONH–,<sup>10</sup> piperazine,<sup>11</sup> and pyridyl groups<sup>12</sup> have been explored extensively for CO<sub>2</sub> adsorption. The nitro group (–NO<sub>2</sub>) is one of the most powerful electron-withdrawing groups, which can polarise –CH groups on phenyl rings. We argued that potentially this might lead to enhanced interactions between –CH groups and adsorbed CO<sub>2</sub> molecules, and moreover, the –NO<sub>2</sub> group might itself serve as a binding site for CO<sub>2</sub> molecules via dipole/quadrupole interactions.<sup>13,14</sup> However, to date, experimental evidence of CO<sub>2</sub> binding to NO<sub>2</sub>-decorated MOFs has not been reported. Herein, we report the adsorption and selectivity of CO<sub>2</sub> in four iso-reticular NbO-type MOFs with different organic functional groups, namely –NO<sub>2</sub>, –NH<sub>2</sub> and alkyl groups. The introduction of these functional groups inevitably reduces the pore volume of the parent MOF, but leads to notable enhancement in CO<sub>2</sub>

<sup>a</sup>School of Chemistry, University of Manchester, Manchester, M13 9PL, UK. E-mail: Sihai.Yang@manchester.ac.uk; M.Schroder@manchester.ac.uk

<sup>b</sup>Nikolaev Institute of Inorganic Chemistry, Siberian Branch of the Russian Academy of Sciences, 3, Acad. Lavrentieva Ave., Novosibirsk, 630090, Russia

<sup>c</sup>Faculty of Natural Sciences, Novosibirsk State University, 2, Pirogova St., Novosibirsk, 630090, Russia

<sup>d</sup>ISIS Facility, STFC Rutherford Appleton Laboratory, Chilton, Oxfordshire, OX11 0QX, UK

<sup>e</sup>Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA

<sup>f</sup>Diamond Light Source, Harwell Science and Innovation Campus, Oxfordshire, UK

† Electronic supplementary information (ESI) available: Synthetic procedures, characterization and additional analysis of crystal structures. Single crystal data of CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub> is deposited at Cambridge Crystallographic Data Centre (CCDC) 1860478. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c9sc04294f

‡ The crystal data for MFM-102-NO<sub>2</sub>, MFM-102-NH<sub>2</sub>, and bare MFM-102-NO<sub>2</sub>, CCDC 1857304, 1857305 and 1857873, respectively, were previously reported in ref. 16.

adsorption. In particular, the NO<sub>2</sub>-functionalised MOF MFM-102-NO<sub>2</sub> shows a 36% increase in CO<sub>2</sub> uptake compared to the parent MFM-102, confirming a positive effect on CO<sub>2</sub> binding. A combination of static and dynamic experiments using *in situ* neutron powder diffraction (NPD), inelastic neutron scattering (INS) and synchrotron-based IR micro-spectroscopy have been applied to study the binding domains of adsorbed CO<sub>2</sub> and the host-guest binding dynamics in MFM-102-NO<sub>2</sub> as a function of CO<sub>2</sub> loading to reveal fundamental insights into the mechanisms for enhanced CO<sub>2</sub> adsorption.<sup>15</sup>

## Experimental

### Material and instrumentation

Chemicals and reagents were purchased from Fisher Scientific, Sigma Aldrich or Fluorochem and used as received without further purification. The detailed synthesis of MFM-102 has been reported previously.<sup>16</sup> <sup>1</sup>H NMR and <sup>13</sup>C NMR spectra were measured on a Bruker AV400 or AV500 spectrometer. High-resolution electrospray mass spectra were measured on a Bruker MicroTOF spectrometer with samples dissolved in MeOH, and scanning was conducted in both positive and negative modes. Infrared (IR) spectra were recorded in the 400–4000 cm<sup>−1</sup> range in ATR sampling mode with a Thermo Scientific iD5 diamond ATR on a Nicolet iS5 FT-IR spectrometer, and elemental analysis was carried out on a CE-440 elemental analyser (EAI Company). TGA measurements were performed using a PerkinElmer TGA 7 Gravimetric Analyser under a flow of N<sub>2</sub> (20 ml min<sup>−1</sup>) at a heating rate of 5 °C min<sup>−1</sup>. Powder X-ray diffraction (PXRD) patterns were obtained on a PANalytical X'Pert Pro MPD diffractometer in Bragg-Brentano geometry with Cu-K<sub>α1</sub> radiation ( $\lambda = 1.5406 \text{ \AA}$ ) at 40 kV and 30 mA over  $2\theta$  range 3–40°. Samples were evenly dispersed on zero-background silicon plates with a cavity depth of 0.3 mm.

### Neutron powder diffraction (NPD) of gas-loaded MFM-102-NO<sub>2</sub>

NPD data were collected at WISH beamline at ISIS Muon and Neutron facility. Acetone exchanged MFM-102-NO<sub>2</sub> was loaded into vanadium cans of 11 mm diameter, and the sample was activated by heating at 393 K and at  $1 \times 10^{-7}$  mbar for 2 days. Data for the bare framework were collected after placing the sample can into a liquid He cryostat and cooling to 7 K. CO<sub>2</sub> gas was dosed into the system after warming to 290 K. The gases were dosed volumetrically from a calibrated volume, and to ensure gases were fully adsorbed into the sample without condensation elsewhere the system was cooled to 7 K slowly over 3 h. Structure solutions of gas-loaded MFM-102-NO<sub>2</sub> were solved by sequential difference Fourier analyses followed by Rietveld refinements (see ESI† Section 4).

### Inelastic neutron scattering (INS) of CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub> and MFM-102-NH<sub>2</sub>

INS data were collected on the TOSCA beamline at ISIS Muon and Neutron facility and on the VISION spectrometer at Spallation Neutron Source, Oak Ridge National Laboratory (USA).

MFM-102-NO<sub>2</sub> and MFM-102-NH<sub>2</sub> were loaded into a vanadium can of 11 mm diameter and outgassed at  $10^{-7}$  mbar at 393 K for 2 days. After placing the sample into a He cooled cryostat, INS data of the bare framework were collected at 7 K. CO<sub>2</sub> was dosed volumetrically from a calibrated volume at room temperature and gradually cooled to 7 K to allow the gas to fully adsorb into MFM-102-NO<sub>2</sub> and MFM-102-NH<sub>2</sub>. INS data of CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub> and CO<sub>2</sub>-loaded MFM-102-NH<sub>2</sub> were collected at 7 K. Experimentally obtained INS data were compared with modelled data obtained *via* density functional theory (DFT) calculations (see ESI† for further details).

### Synchrotron FTIR micro-spectroscopy of CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub>

Single crystals of MFM-102-NO<sub>2</sub> were loaded onto a ZnSe slide and placed into a Linkam FTIR600 variable temperature gas-tight cell fitted with ZnSe windows. The MOF sample was activated *in situ* under a flow of N<sub>2</sub> whilst heating the Linkam stage to 413 K for 6 h. Partial pressures of zeolite dried gases N<sub>2</sub> and CO<sub>2</sub> were controlled by varying the volumetric flow of the two gases *via* separate mass flow controllers. FTIR spectra were collected at B22 MIRIAM beamline at Diamond Light Source using a highly bright synchrotron IR source connected to a Bruker Hyperion 3000 IR microscope with a 15× objective and MCT detector (liq. N<sub>2</sub> cooled). Spectra (256 scans) were measured at room temperature with a 20 × 20 μm beam, in the spectral range of 4000–650 cm<sup>−1</sup> (4 cm<sup>−1</sup> resolution).

## Results and discussion

### Synthesis, structure and porosity

MFM-102, MFM-102-NH<sub>2</sub>, MFM-102-NO<sub>2</sub> and MFM-111 were synthesised according to our previously reported methods,<sup>16–18</sup> and the phase purity of all bulk materials was confirmed by powder X-ray diffraction (see ESI† Section 1). All four MOFs are iso-structural and crystallise in the trigonal space group *R3m*. The framework is built from Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub> paddlewheel units in which two Cu<sup>II</sup> cations are bridged by four carboxylate groups surrounded the [Cu⋯Cu] axis and two terminal H<sub>2</sub>O molecules at axial positions to form a [Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub>(OH<sub>2</sub>)<sub>2</sub>] node. These Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub> units are bridged by the diisophthalate ligands to afford a 3D extended NbO-type network. Within each framework, there are two different types of metal-ligand cages (denoted as A and B) in a 1 : 1 ratio (Fig. 1). Cage A consists of six Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub> paddlewheels and six linkers to give a spherical shape of 15 Å diameter. Cage B is constructed of twelve Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub> paddlewheels residing at the vertices and six ligands on the faces to form an ellipsoid shaped cavity of 32 Å along the *c* axis and 18 Å across *ab* plane. Due to the alternative packing of cages A and B, the alkyl, nitro, and amino groups are directly grafted into the pore walls, providing an excellent platform to study their role in guest binding. The Brunauer-Emmett-Teller (BET) surface area and pore volume of MFM-102, MFM-111, MFM-102-NH<sub>2</sub>, MFM-102-NO<sub>2</sub> were determined to be 3412, 2930, 2928, 2893 m<sup>2</sup> g<sup>−1</sup> and 1.29, 1.19, 1.12, 1.14 cm<sup>3</sup> g<sup>−1</sup>, respectively, from N<sub>2</sub> isotherms at 77 K. As



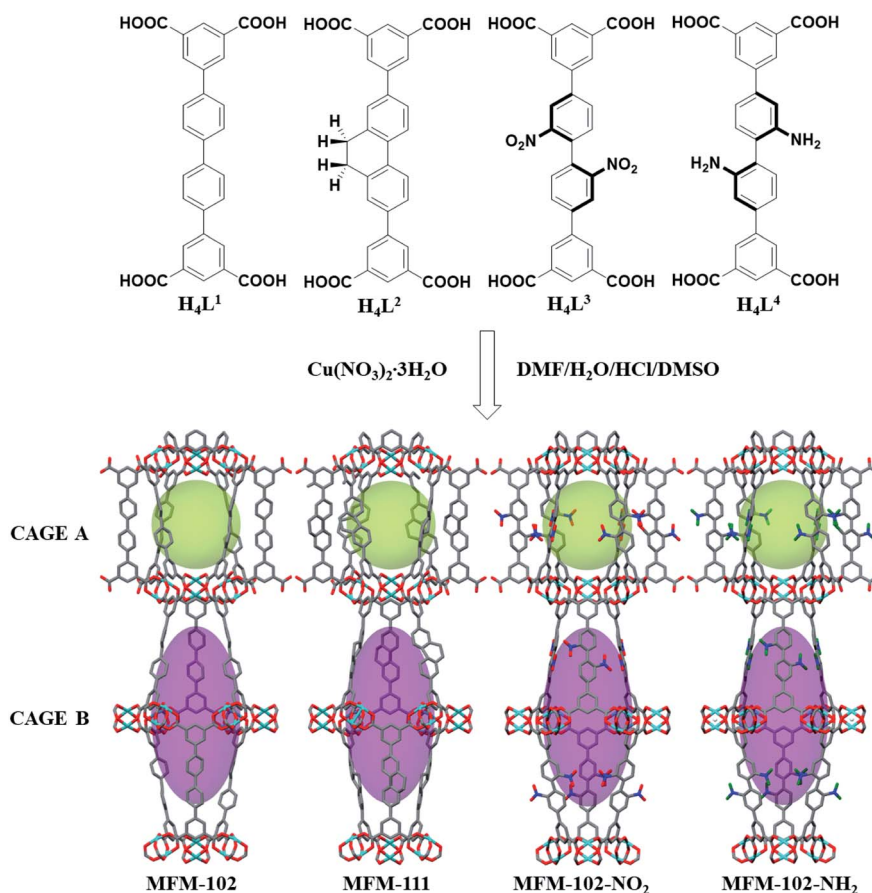


Fig. 1 Views of organic ligands used to construct the MFM-102 series of MOFs and the X-ray crystal structures of MFM-102, MFM-111, MFM-102-NO<sub>2</sub> and MFM-102-NH<sub>2</sub>. The functional groups are highlighted in ball-stick mode. (C, dark grey; O, red; N, blue; Cu, turquoise; all coordinated H<sub>2</sub>O and hydrogen atoms are omitted for clarity, except for the hydrogen atoms on the –NH<sub>2</sub> group, green).

expected, the porosity of decorated complexes reduces compared to the parent MOF, and so introduction of alkyl, –NH<sub>2</sub> and –NO<sub>2</sub> groups into MFM-102 leads to reduction in BET surface areas of 14%, 14% and 15%, respectively.

### Gas adsorption properties

Adsorption isotherms of CO<sub>2</sub> and CH<sub>4</sub> were recorded at 273 and 298 K up to 1 bar. All isotherms are completely reversible, and show fast adsorption–desorption kinetics with equilibrium achieved typically within 3–5 min. Uptake of CO<sub>2</sub> at 273 K and 1.0 bar were recorded as 184, 178, 165, 135 cm<sup>3</sup> g<sup>−1</sup> for MFM-102-NO<sub>2</sub>, MFM-102-NH<sub>2</sub>, MFM-111 and MFM-102, respectively (Fig. 2a). Interestingly, despite the reduction in porosity, the introduction of alkyl, –NH<sub>2</sub> and –NO<sub>2</sub> groups into MFM-102 leads to enhancement on the CO<sub>2</sub> uptake of resultant MOFs by 22%, 32% and 36%, respectively. Notably, the CO<sub>2</sub> uptake of MFM-102-NO<sub>2</sub> is comparable to the best-performing isoreticular MOF (NJU-Bai-14, 187 cm<sup>3</sup> g<sup>−1</sup>) under the same conditions.<sup>19</sup> Similar enhancement of CO<sub>2</sub> adsorption was also observed at 298 K for the decorated MOFs (Fig. 2b), and these uptakes are comparable to other leading NbO-type MOFs (Table 1). In sharp contrast, these MOFs show similarly low uptakes of CH<sub>4</sub> at 273 and 298 K and 1.0 bar (ranging from 30 cm<sup>3</sup> g<sup>−1</sup> to 20 cm<sup>3</sup> g<sup>−1</sup>). This result indicates the potential of MFM-102-NO<sub>2</sub>

as a promising material for selective adsorption of CO<sub>2</sub>. The adsorption selectivities for equimolar mixtures of CO<sub>2</sub>/CH<sub>4</sub> within these MOFs have been calculated using ideal adsorbed solution theory (IAST) using the experimental single-component isotherm data (Fig. S4 and S5<sup>†</sup>). At 298 K and 1 bar, the CO<sub>2</sub>/CH<sub>4</sub> (50 : 50) selectivity is 5.0, which is comparable to those reported for other Cu-based MOFs with similar porosity, such as NJU-Bai12 (5.0),<sup>20</sup> ZJNU-81(5.5),<sup>21</sup> ZJNU-82 (5.4),<sup>21</sup> ZJNU-83 (4.9),<sup>21</sup> ZJU-15 (4.4) (ref. 22) and ZJNU-57 (5.5),<sup>23</sup> but which do not show NbO topologies.

The isosteric heats of adsorption ( $Q_{st}$ ) of CO<sub>2</sub> were calculated using virial method based on isotherm data at 273 and 298 K (Fig. 2c). The values for  $Q_{st}$  at low surface coverage range from 24.0 to 24.6 kJ mol<sup>−1</sup>, comparable to other MOFs of NbO topology with a high density of open Cu(II) sites (Table 1). With increasing CO<sub>2</sub> loading, the values of  $Q_{st}$  steadily reduce in all four cases. Interestingly, the  $Q_{st}$  values of MFM-102 drop more rapidly than functionalised materials with increasing loading, indicating the presence of additional binding sites in the decorated MOFs.

### In situ neutron powder diffraction (NPD) of CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub>

In situ NPD was employed to determine the binding domains for adsorbed CO<sub>2</sub> molecules within desolvated MFM-102-NO<sub>2</sub> at

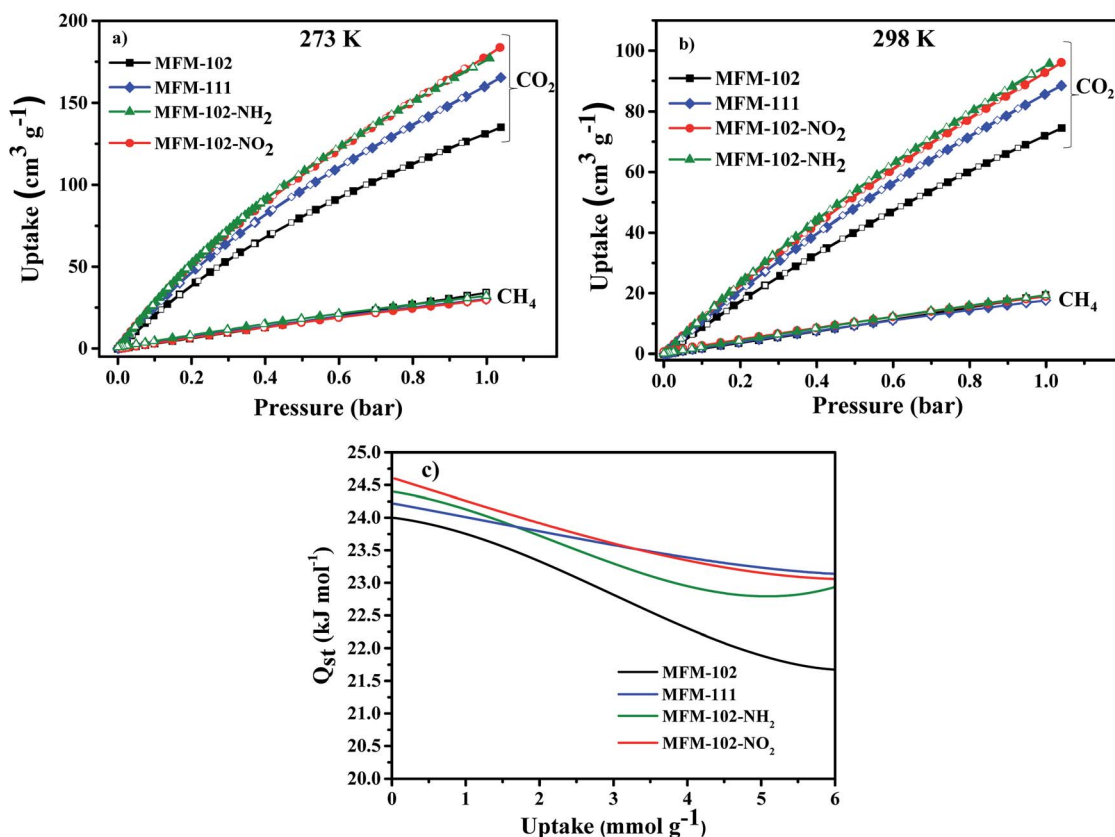


Fig. 2 Adsorption isotherms for desolvated MFM-102, MFM-111, MFM-102-NO<sub>2</sub> and MFM-102-NH<sub>2</sub> (a) 273 K, (b) 298 K. Solid and open symbols represent adsorption and desorption, respectively. (c) Heat of adsorption as a function of CO<sub>2</sub> uptake derived by the virial method.

a loading of 2.0 CO<sub>2</sub>/Cu. NPD data for the desolvated complex confirm the complete removal of guest solvents, including coordinated H<sub>2</sub>O molecules on the Cu sites, and no significant structural distortion is observed compared to the parent solvated material. A loading of 2.0 CO<sub>2</sub>/Cu was used to assess the strongest binding sites within the material without involving notable adsorbate-adsorbate interactions. Fourier difference map analysis of the NPD patterns afforded the location of guest CO<sub>2</sub> molecules, which after further development by Rietveld refinement, allowed

unambiguous determination of gas positions, orientations and crystallographic occupancies within each sample.

MFM-102-NO<sub>2</sub> displays six binding sites for CO<sub>2</sub> (denoted as I to VI with decreasing occupancies, Fig. 3 and 4). Significantly, site I (occupancy = 0.50) was found not to be at the open Cu(II) sites but is confined to the window between Cages A and B. At site I, CO<sub>2</sub><sup>I</sup> forms supramolecular interactions to aromatic -CH group from two adjacent NO<sub>2</sub>-substituted phenyl rings [O<sub>CO2</sub>...HC- = 2.13(5), 2.42(8) Å]. It is noteworthy that -NO<sub>2</sub> is a strong electron-withdrawing groups which leads to

Table 1 Comparison of CO<sub>2</sub> uptakes in selected Cu-MOFs of NbO topology

| MOFs                    | CO <sub>2</sub> uptake, 273 K (cm <sup>3</sup> g <sup>-1</sup> ) | CO <sub>2</sub> uptake, 298 K (cm <sup>3</sup> g <sup>-1</sup> ) | V <sub>p</sub> , pore volume (cm <sup>3</sup> g <sup>-1</sup> ) | BET area (m <sup>2</sup> g <sup>-1</sup> ) | Q <sub>st</sub> (kJ mol <sup>-1</sup> ) | Ref.      |
|-------------------------|------------------------------------------------------------------|------------------------------------------------------------------|-----------------------------------------------------------------|--------------------------------------------|-----------------------------------------|-----------|
| ZJNU-44                 | 175                                                              | 116                                                              | 0.894                                                           | 2314                                       | —                                       | 24        |
| ZJNU-43                 | 180                                                              | 103                                                              | 0.894                                                           | 2243                                       | —                                       | 24        |
| ZJNU-45                 | 163                                                              | 107                                                              | 0.877                                                           | 2232                                       | —                                       | 24        |
| ZJNU-40                 | —                                                                | 86                                                               | 0.997                                                           | 2072                                       | 24.0                                    | 25        |
| ZJNU-41                 | —                                                                | 97                                                               | 0.837                                                           | 2530                                       | 23.5                                    | 26        |
| ZJU-8                   | 175                                                              | 98                                                               | 1.022                                                           | 2501                                       | 21.9                                    | 27        |
| NJU-Bai-14              | 187                                                              | 100                                                              | 0.942                                                           | 2384                                       | 24.5                                    | 19        |
| MFM-101                 | 164                                                              | 86                                                               | 1.080                                                           | 2805                                       | —                                       | 25        |
| MFM-102                 | 135                                                              | 74                                                               | 1.297                                                           | 3412                                       | 24.0                                    | This work |
| MFM-102-NO <sub>2</sub> | 184                                                              | 96                                                               | 1.118                                                           | 2893                                       | 24.6                                    | This work |
| MFM-102-NH <sub>2</sub> | 180                                                              | 97                                                               | 1.140                                                           | 2928                                       | 24.4                                    | This work |
| MFM-111                 | 165                                                              | 88                                                               | 1.190                                                           | 2930                                       | 24.2                                    | This work |
| MFM-130                 | 109                                                              | 59                                                               | 1.000                                                           | 2173                                       | 26.0                                    | 28        |



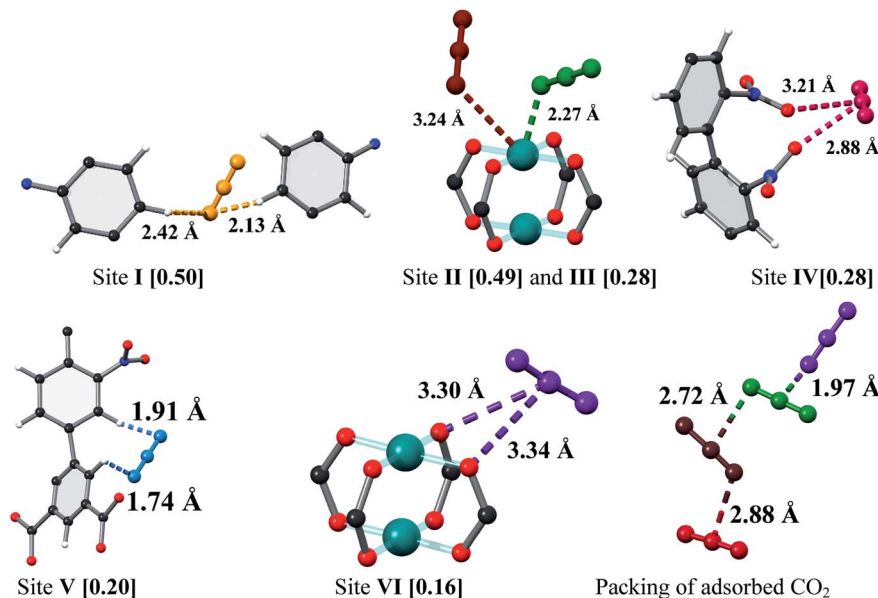


Fig. 3 View of the binding sites for adsorbed CO<sub>2</sub> molecules in MFM-102-NO<sub>2</sub> and the relative positions of these positions in the framework cages [C, dark grey; O, red; N, blue; Cu, turquoise and CO<sub>2</sub> molecules at site I (yellow), site II (green), site III (brown), site IV (ruby), site V (blue) and site VI (purple)].

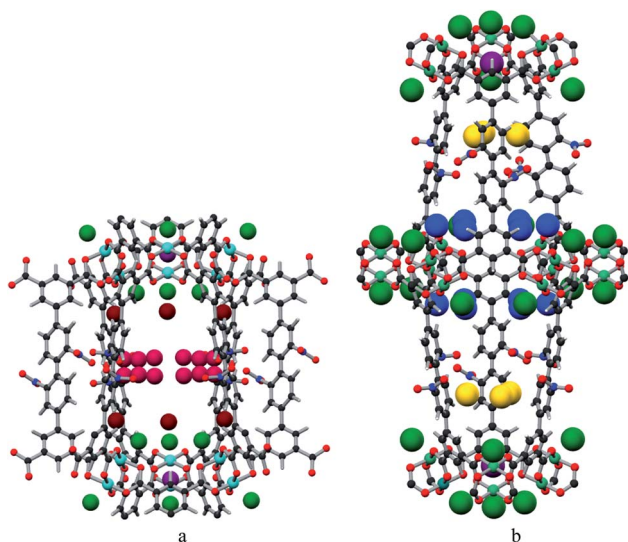


Fig. 4 The positions of the CO<sub>2</sub> in the framework cage A (a) and B (b) of MFM-102-NO<sub>2</sub>. CO<sub>2</sub> molecules are at site I (yellow), site II (green), site III (brown), site IV (ruby), site V (blue) and site VI (purple).

polarisation of adjacent –CH moieties. These –CH groups therefore show enhanced acidity and thus act as effective hydrogen bond donors to CO<sub>2</sub> molecules. Site II and III (occupancy = 0.49 and 0.28, respectively) reside at the open Cu(II) centre [ $\text{O}_{\text{CO}_2} \cdots \text{Cu} = 2.27(7) \text{ \AA}$  and  $3.24(7) \text{ \AA}$  for site II and III, respectively]. Site IV (occupancy = 0.28) is stabilised by the dipole/quadrupole interaction between  $\text{O}(\delta^-)$  of the –NO<sub>2</sub> group from 2 neighbouring phenyl rings and the  $\text{C}(\delta^+)$  centre of CO<sub>2</sub> with distances of  $3.20(6)$  and  $2.87(9) \text{ \AA}$ . Site V (occupancy = 0.20) was found close to the isophthalate phenyl ring

[ $\text{O}_{\text{CO}_2} \cdots \text{HC} = 1.72(9) \text{ \AA}$ ] and the NO<sub>2</sub>-decorated phenyl ring [ $\text{O}_{\text{CO}_2} \cdots \text{HC} = 1.91(4) \text{ \AA}$ ] stabilised by interactions with aromatic hydrogen atoms. At site VI (occupancy = 0.167), the C atom of CO<sub>2</sub> is close to the two oxygen atoms from carboxylate groups of the  $[\text{Cu}_2(\text{O}_2\text{CR})_4]$  paddlewheel with distances of  $3.30(1)$ – $3.34(5) \text{ \AA}$ . Overall, the effects of –NO<sub>2</sub> groups on CO<sub>2</sub> binding are two-fold: (i) polarising neighbouring phenyl C–H bonds *via* the conjugate effect of the aromatic ring bound to electron-withdrawing –NO<sub>2</sub> groups (site I), and (ii) creating additional adsorption sites *via* direct dipole/quadrupole interaction of –NO<sub>2</sub> with CO<sub>2</sub> (site IV).

#### *In situ* synchrotron FT-IR micro-spectroscopy of MFM-102-NO<sub>2</sub>

To investigate further the nature of host–guest interactions, *in situ* synchrotron FT-IR micro-spectroscopy was conducted on a single crystal of activated MFM-102-NO<sub>2</sub>. FTIR spectra were collected as a function of CO<sub>2</sub>-loading by increasing the partial pressure of CO<sub>2</sub> in N<sub>2</sub> from 0 to 1.0 bar (ppCO<sub>2</sub>) (Fig. 5a). Gaseous CO<sub>2</sub> has three fundamental vibrational modes: the symmetric C=O stretching mode  $\nu_1$  ( $1388 \text{ cm}^{-1}$ ), a doubly-degenerate bending mode  $\nu_2$  ( $667 \text{ cm}^{-1}$ ) and an asymmetric stretching vibration  $\nu_3$  ( $2349 \text{ cm}^{-1}$ ) (Table S1†).<sup>29</sup> The  $\nu_1 + \nu_3$  ( $3714 \text{ cm}^{-1}$ ) and  $2\nu_2 + \nu_3$  ( $3612 \text{ cm}^{-1}$ ) combination bands of CO<sub>2</sub> (Fig. 5a) were used to monitor CO<sub>2</sub> sorption as the fundamental anti-symmetric stretch at  $\sim 2348 \text{ cm}^{-1}$  saturates at ppCO<sub>2</sub> above 0.2 bar. On adsorption, a combination of electrostatic and dispersion forces between CO<sub>2</sub> and the pore surface weakens the C=O bonds in CO<sub>2</sub>, leading to the observed redshift of IR bands of adsorbed CO<sub>2</sub> to lower frequencies ( $3700$  and  $3600 \text{ cm}^{-1}$ , respectively) compared to those observed in gas phase (Table S1†). If CO<sub>2</sub> strongly coordinates to an open metal



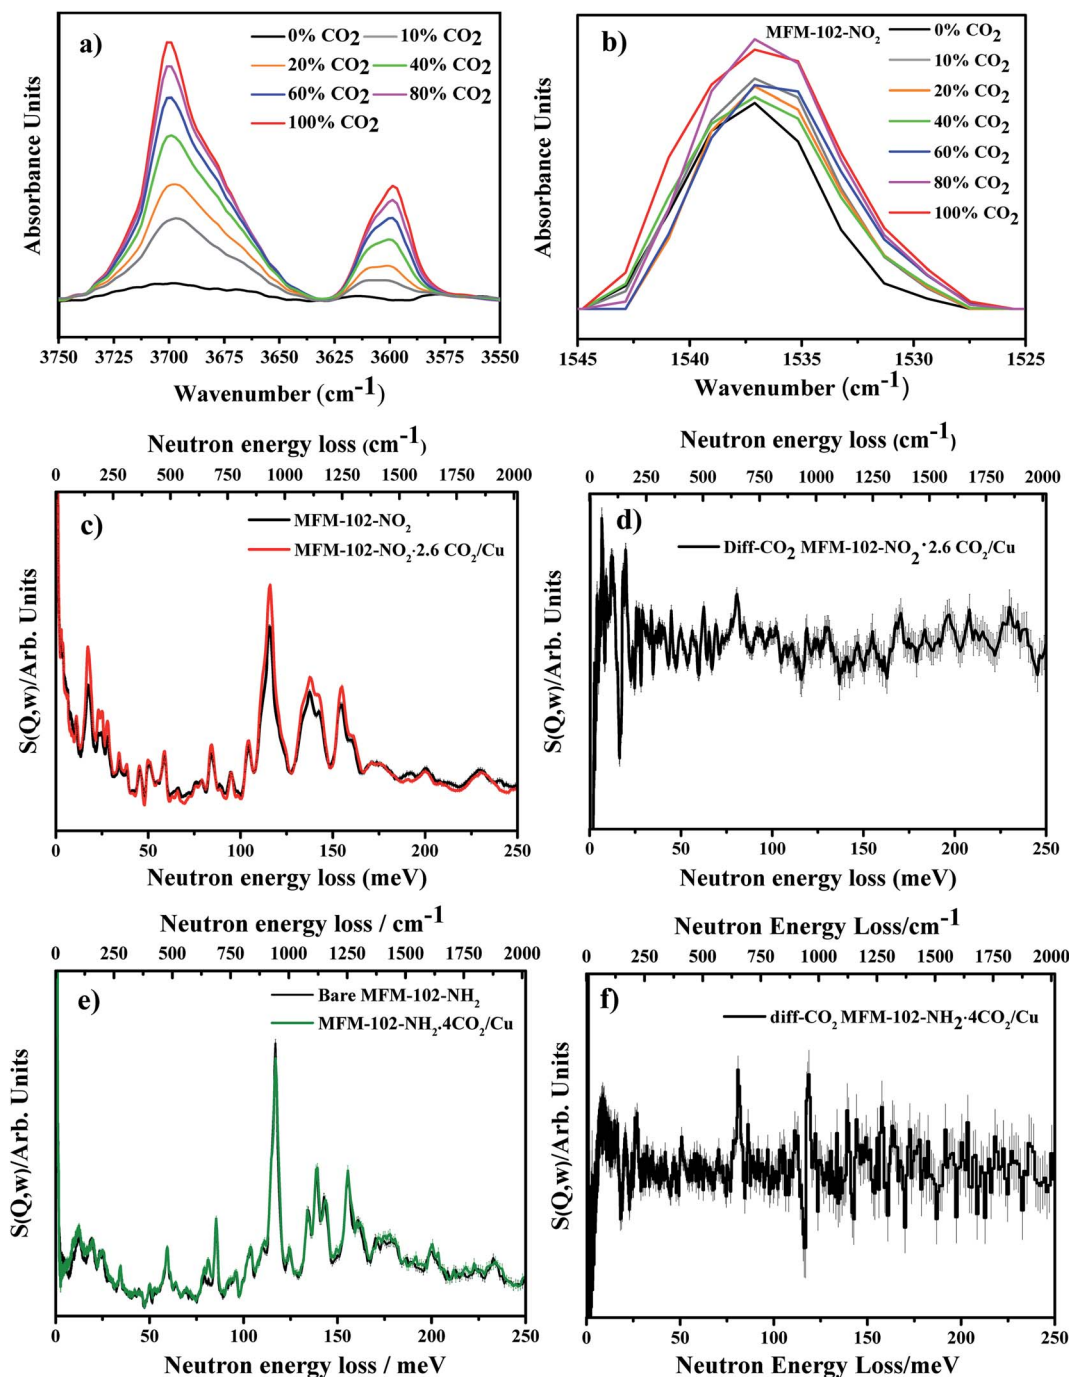


Fig. 5 (a) IR spectra showing the adsorption of CO<sub>2</sub> into MFM-102-NO<sub>2</sub> and demonstrating the growth in  $\nu_1 + \nu_3$  and  $2\nu_2 + \nu_3$  combination bands for CO<sub>2</sub> near 3700  $\text{cm}^{-1}$  and 3600  $\text{cm}^{-1}$ . (b) Changes in intensity and broadening of the N=O asymmetric stretching vibration with CO<sub>2</sub> loading. (c) INS spectra for activated MFM-102-NO<sub>2</sub> and MFM-102-NO<sub>2</sub> with CO<sub>2</sub> loading. (d) Difference INS plot, derived by subtracting INS spectra for CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub> and bare MFM-102-NO<sub>2</sub> spectra. (e) and (f) are the same as (c) and (d), respectively, but replacing MFM-102-NO<sub>2</sub> with MFM-102-NH<sub>2</sub>.

site, the molecular symmetry is lowered and the degeneracy of the  $\nu_2$  bending mode is removed, splitting the band into two peaks.<sup>30</sup> Three IR spectra of the activated, 10% CO<sub>2</sub>- and 100% CO<sub>2</sub>-loaded MFM-102-NO<sub>2</sub> reveal the changes in the peak at 660  $\text{cm}^{-1}$ . This peak shows a significant increase in intensity at 10% CO<sub>2</sub> loading, and broadens and splits into two peaks at

657  $\text{cm}^{-1}$  and 663  $\text{cm}^{-1}$  at 100% CO<sub>2</sub> loading (Fig. S7a†). The IR band of the host framework reveals some interesting features. There is a continuous red shift of the band at 1670  $\text{cm}^{-1}$  (the C=O stretching mode of -COO groups<sup>31</sup>) with increasing CO<sub>2</sub> loading, consistent with the interactions between CO<sub>2</sub> molecules and [Cu<sub>2</sub>(O<sub>2</sub>CR)<sub>4</sub>] paddlewheel units (site VI, Fig. S7b†). An



apparent change in the peak shape and intensity at  $1537\text{ cm}^{-1}$  (N–O asymmetric stretching mode in the  $-\text{NO}_2$  group<sup>32</sup>) suggests dipole/quadrupole interaction between the  $-\text{NO}_2$  groups and adsorbed  $\text{CO}_2$  molecules (Fig. 5b). In the low energy regions, the peak at  $1025\text{ cm}^{-1}$  (corresponding to C–H out-of-plane wagging<sup>33</sup>) gradually decreases in intensity with increasing  $\text{CO}_2$  loading, while the peak at  $1005\text{ cm}^{-1}$  grows and shifts to lower energy (Fig. S7c†). These changes in FTIR spectra are in excellent agreement with the presence of multiple interactions between the framework and  $\text{CO}_2$  molecules as observed by the NPD experiment.

### Inelastic neutron scattering (INS) studies of $\text{CO}_2$ -loaded MFM-102- $\text{NO}_2$ and MFM-102- $\text{NH}_2$

To gain further insight into the host–guest dynamics of  $\text{CO}_2$ -loaded MFM-102- $\text{NO}_2$ , *in situ* INS has been investigated. The calculated INS spectrum of bare MOF was found to be in good agreement with the experimental INS data (Fig. S8†) leading to assignment of all the vibrational modes. In the INS spectrum of  $\text{CO}_2$ -loaded MFM-102- $\text{NO}_2$ , all the INS peaks shift slightly to higher energy, attributed to a stiffening effect of the host–guest lattice on  $\text{CO}_2$  adsorption (Fig. 4c). There are changes in the peak intensity at 164 and 193 meV, corresponding to the symmetrical and asymmetrical stretching of  $-\text{NO}_2$  groups. The various distortion motions of the phenyl rings (83 meV), out-of-plane C–H bending on the isophthalate rings (116 meV) and in-plane C–H bending on phenyl rings (136 meV) increase in intensity. These results confirm the important role of  $-\text{NO}_2$  and  $-\text{CH}$  groups on the adsorption of  $\text{CO}_2$ . Similarly, the difference INS spectra of  $\text{CO}_2$ -adsorbed MFM-102- $\text{NH}_2$  also show changes in intensity of the peaks at 80, 117, 119 meV, originating from various in-plane deformational vibrations of the phenyl rings and the wagging motion of aromatic C–H groups. These changes are attributed to the reduction of the motion of aromatic C–H groups with the introduction of  $\text{CO}_2$  into the framework.

## Conclusions

We report a comprehensive investigation of the adsorption and binding of  $\text{CO}_2$  in four iso-reticular MOFs with varying functional groups. Introduction of  $-\text{NO}_2$  group to the parent MOF, MFM-102, leads a 15% reduction on the BET surface area but a 36% enhancement on the  $\text{CO}_2$  adsorption capacity at 273 K and 1.0 bar. NPD analysis of  $\text{CO}_2$ -loaded MFM-102- $\text{NO}_2$  reveals cooperative binding of  $\text{CO}_2$  to  $-\text{CH}$  hydrogen bond donors that is enhanced by the electron withdrawing effects of the  $-\text{NO}_2$  groups that decorate pore walls. In addition, direct interaction of  $\text{CO}_2$  with the open metal sites and the  $-\text{NO}_2$  groups is observed, thus enhancing further interaction of the MOF with  $\text{CO}_2$ . The *in situ* spectroscopic studies using INS and FTIR spectroscopy establish that adsorbed  $\text{CO}_2$  molecules interact strongly with the  $-\text{NO}_2$  and  $-\text{CH}$  groups of MFM-102- $\text{NO}_2$ , with apparent shifts and changes of intensity of N=O and C–H vibrational bands on  $\text{CO}_2$  loading. This work provides a fundamental understanding of the effect of the  $-\text{NO}_2$  group on  $\text{CO}_2$

adsorption, and the information gained here provides further insights into the development of materials showing improved gas binding *via* specific interaction with ligand sites within the MOF structure.

## Conflicts of Interest

The authors declare no competing interests.

## Acknowledgements

We thank EPSRC (EP/I011870), the Royal Society and University of Manchester for funding. This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement no 742401, NANOCHM). We thank ISIS/STFC, Diamond Light Source and Oak Ridge National Laboratory for access to Beamlines WISH, B22 and VISION, respectively. Neutron scattering experiments were performed at ORNL's Spallation Neutron Source, supported by the Scientific User Facilities Division, Office of Basic Energy Sciences, US DOE, under Contract No. DE-AC0500OR22725 with UT Battelle, LLC. The computing resources were made available through the VirtuES and the ICE-MAN projects, funded by Laboratory Directed Research and Development program and Compute and Data Environment for Science (CADES) at ORNL.

## Notes and references

- 1 D. W. Keith, *Science*, 2009, **325**, 1654–1655.
- 2 E. David and J. Kopac, *J. Anal. Appl. Pyrolysis*, 2014, **110**, 322–332.
- 3 T. D. Pham, R. Xiong, S. I. Sandler and R. F. Lobo, *Microporous Mesoporous Mater.*, 2014, **185**, 157–166.
- 4 M. Yang, Y. Song, L. Jiang, X. Wang, W. Liu, Y. Zhao, Y. Liu and S. Wang, *J. Ind. Eng. Chem.*, 2014, **20**, 322–330.
- 5 M. Ramdin, T. W. de Loos and T. J. H. Vlucht, *Ind. Eng. Chem. Res.*, 2012, **51**, 8149–8177.
- 6 S. Kazemi and V. Safarifar, *Polyhedron*, 2018, **154**, 236–251.
- 7 Y. Liao, L. Zhang, M. H. Weston, W. Morris, J. T. Hupp and O. K. Farha, *Chem. Commun.*, 2017, **53**, 9376–9379.
- 8 A. Greenaway, B. Gonzalez-Santiago, P. M. Donaldson, M. D. Frogley, G. Cinque, J. Sotelo, S. Moggach, E. Shiko, S. Brandani, R. F. Howe and P. A. Wright, *Angew. Chem., Int. Ed.*, 2014, **53**, 13483–13487.
- 9 X. Duan, H. Wang, Z. Ji, Y. Cui, Y. Yang and G. Qian, *J. Solid State Chem.*, 2016, **241**, 152–156.
- 10 O. Benson, I. da Silva, S. P. Argent, R. Cabot, M. Savage, H. G. W. Godfrey, Y. Yan, S. F. Parker, P. Manuel, M. J. Lennox, T. Mitra, T. L. Easun, W. Lewis, A. J. Blake, E. Besley, S. Yang and M. Schröder, *J. Am. Chem. Soc.*, 2016, **138**, 14828–14831.
- 11 Q. Mu, H. Wang, L. Li, C. Wang, Y. Wang and X. Zhao, *Chem.-Asian J.*, 2015, **10**, 1864–1869.
- 12 Q.-Q. Dang, Y.-F. Zhan, L.-N. Duan and X.-M. Zhang, *Dalton Trans.*, 2015, **44**, 20027–20031.



- 13 R. Banerjee, H. Furukawa, D. Britt, C. Knobler, M. O'Keeffe and O. M. Yaghi, *J. Am. Chem. Soc.*, 2009, **131**, 3875–3877.
- 14 S. Biswas, T. Ahnfeldt and N. Stock, *Inorg. Chem.*, 2011, **50**, 9518–9526.
- 15 T. L. Easun, F. Moreau, Y. Yan, S. Yang and M. Schröder, *Chem. Soc. Rev.*, 2017, **46**, 239–274.
- 16 T. D. Duong, S. A. Sapchenko, I. da Silva, H. G. W. Godfrey, Y. Cheng, L. L. Daemen, P. Manuel, A. J. Ramirez-Cuesta, S. Yang and M. Schröder, *J. Am. Chem. Soc.*, 2018, **140**, 16006–16009.
- 17 X. Lin, I. Telepeni, A. J. Blake, A. Dailly, C. M. Brown, J. M. Simmons, M. Zoppi, G. S. Walker, K. M. Thomas, T. J. Mays, P. Hubberstey, N. R. Champness and M. Schröder, *J. Am. Chem. Soc.*, 2009, **131**, 2159–2171.
- 18 S. Yang, X. Lin, A. Dailly, A. J. Blake, P. Hubberstey, N. R. Champness and M. Schröder, *Chem. - Eur. J.*, 2009, **15**, 4829–4835.
- 19 M. Zhang, Q. Wang, Z. Lu, H. Liu, W. Liu and J. Bai, *CrystEngComm*, 2014, **16**, 6287–6290.
- 20 B. Zheng, R. Yun, J. Bai, Z. Lu, L. Du and Y. Li, *Inorg. Chem.*, 2013, **52**, 2823–2829.
- 21 M. He, Y. Wang, X. Gao, S. Li and Y. He, *Dalton Trans.*, 2018, **47**, 8983–8991.
- 22 X. Duan, Y. Zhou, R. Lv, B. Yu, H. Chen, Z. Ji, Y. Cui, Y. Yang and G. Qian, *J. Solid State Chem.*, 2018, **260**, 31–33.
- 23 Y. Wang, M. He, Z. Tian, H. Zhong, L. Zhu, Y. Zhang, X. Zhang, D.-L. Chen and Y. He, *Dalton Trans.*, 2018, **47**, 2444–2452.
- 24 C. Song, J. Hu, Y. Ling, Y. Feng, R. Krishna, D.-L. Chen and Y. He, *J. Mater. Chem. A*, 2015, **3**, 19417–19426.
- 25 C. Song, Y. He, B. Li, Y. Ling, H. Wang, Y. Feng, R. Krishna and B. Chen, *Chem. Commun.*, 2014, **50**, 12105–12108.
- 26 C. Song, Y. Ling, L. Jin, M. Zhang, D.-L. Chen and Y. He, *Dalton Trans.*, 2016, **45**, 190–197.
- 27 J. Cai, H. Wang, H. Wang, X. Duan, Z. Wang, Y. Cui, Y. Yang, B. Chen and G. Qian, *RSC Adv.*, 2015, **5**, 77417–77422.
- 28 Y. Yan, M. Juriček, F.-X. Coudert, N. A. Vermeulen, S. Grunder, A. Dailly, W. Lewis, A. J. Blake, J. F. Stoddart and M. Schröder, *J. Am. Chem. Soc.*, 2016, **138**, 3371–3381.
- 29 S. Andonova, E. Ivanova, J. Yang and K. Hadjiivanov, *J. Phys. Chem. C*, 2017, **121**, 18665–18673.
- 30 J. G. Vitillo, M. Savonnet, G. Ricchiardi and S. Bordiga, *ChemSusChem*, 2011, **4**, 1281–1290.
- 31 N. R. Dhumal, M. P. Singh, J. A. Anderson, J. Kiefer and H. J. Kim, *J. Phys. Chem. C*, 2016, **120**, 3295–3304.
- 32 F. X. W. Robert, M. Silverstein, D. J. Kiemle and D. L. Bryce, *Spectrometric Identification of Organic Compounds*, 8th edn, 2014.
- 33 F. P. Ureña, M. F. Gómez, J. J. L. González and E. M. n. Torres, *Spectrochim. Acta, Part A*, 2003, **59**, 2815–2839.

