

Dalton Transactions

An international journal of inorganic chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. C. Corner, G. K. Gransbury and D. P. Mills, *Dalton Trans.*, 2024, DOI: 10.1039/D4DT02713B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Influence of weakly coordinating anions binding to the hexa-*tert*-butyl dysprosocenium
cation

View Article Online

DOI: 10.1039/D4DT02713B

Sophie C. Corner,^a Gemma K. Gransbury,^{a} and David P. Mills^{a*}*

^aDepartment of Chemistry, The University of Manchester, Oxford Road, Manchester,
M13 9PL, U.K.

*Email: david.mills@manchester.ac.uk, gemmagransbury@gmail.com.



AbstractView Article Online
DOI: 10.1039/D4DT02713B

Complexes containing isolated dysprosocenium cations, $[\text{Dy}(\text{Cp}^{\text{R}})_2][\text{WCA}]$ (Cp^{R} = substituted cyclopentadienyl, WCA = weakly coordinating anion), have recently emerged as leading examples of high-temperature single-molecule magnets (SMMs) due to a combination of the axial orientation and rigidity of the Cp^{R} rings. However, our understanding of the effects of transverse fields on the magnetic properties of $[\text{Dy}(\text{Cp}^{\text{R}})_2]^+$ cations is underdeveloped. Here we investigate the impact of equatorially-bound WCAs *via* the synthesis of the Dy(III) *bis*- Cp^{R} complexes $[\text{Dy}(\text{Cp}^{\text{ttt}})_2\{\text{AlCl}[\text{OC}(\text{CF}_3)_3]_3-\kappa\text{-Cl}\}]$ (**1**) and $[\text{Dy}(\text{Cp}^{\text{ttt}})_2\{\text{AlCl}(\text{C}_2\text{H}_5)[\text{OC}(\text{C}_6\text{F}_5)_3]_2-\kappa\text{-Cl}\}]$ (**2**), and their characterisation by single crystal XRD, elemental analysis, ATR-IR and NMR spectroscopy, and *ab initio* calculations. Despite the similarity of the Dy coordination spheres in **1** and **2** we find that their effective energy barriers to reversal of magnetisation are vastly different ($U_{\text{eff}} = 886(17) \text{ cm}^{-1}$ and $559(18) \text{ cm}^{-1}$, respectively) and they both show waist-restricted magnetic hysteresis at 2 K. Together, these data provide fresh insights into the sensitivity of the magnetic properties of $[\text{Dy}(\text{Cp}^{\text{R}})_2]^+$ cations to relatively weak equatorial interactions.



Introduction

Single-molecule magnets (SMMs) show effective energy barriers to the relaxation of magnetisation (U_{eff}) and can exhibit open magnetic hysteresis up to a certain temperature (T_{H});¹ lanthanide (Ln) complexes have provided the most promising SMM candidates to date.^{2,3} Dy(III) and Tb(III) SMMs with axial crystal fields have been targeted most often as these geometries provide the largest U_{eff} through stabilisation of the ground $\pm m_J$ states and concomitant destabilisation of the least magnetic $\pm m_J$ states for these ions.⁴⁻⁶ Ideal Dy(III) and Tb(III) complexes with perfectly linear geometries would exhibit suppressed Raman and quantum tunnelling of magnetisation (QTM) under-barrier relaxation mechanisms due to high $\pm m_J$ state purities,⁴⁻⁶ but such complexes are difficult to achieve as predominantly ionic Ln bonding regimes favour additional metal-ligand interactions.⁷

In 2017 the first isolated dysprosocenium complex, $[\text{Dy}(\text{Cp}^{\text{ttt}})_2][\text{B}(\text{C}_6\text{F}_5)_4]$ ($\text{Cp}^{\text{ttt}} = \text{C}_5\text{H}_2^{\text{tBu}}\text{Bu}_{3-1,2,4}$), was reported to exhibit a large U_{eff} value of 1223(15) cm^{-1} and T_{H} of 60 K due to a combination of its axial geometry and the rigid aromatic Cp^{ttt} rings suppressing Raman and QTM processes.⁸ It is noteworthy that the precursor to this complex, $[\text{Dy}(\text{Cp}^{\text{ttt}})_2(\text{Cl})]$ is not an SMM in zero field and has $T_{\text{H}} < 2$ K,⁹⁻¹¹ highlighting the substantial impact of equatorially-bound ligands on the magnetic properties of complexes containing $\{\text{Dy}(\text{Cp}^{\text{R}})_2\}$ ($\text{Cp}^{\text{R}} =$ substituted cyclopentadienyl) cores, as previously shown systematically for halides in $[\text{Dy}(\text{Cp}^*)_2(\text{X})(\text{THF})]$ ($\text{Cp}^* = \text{C}_5\text{Me}_5$, $\text{X} = \text{Cl}, \text{Br}, \text{I}$).¹² In the interim many other high-temperature SMMs have been synthesised that contain $\{\text{Dy}(\text{Cp}^{\text{R}})_2\}$ ($\text{Cp}^{\text{R}} =$ substituted cyclopentadienyl) motifs,¹³⁻¹⁵ or heteroatom-containing analogues,¹⁶⁻¹⁹ and the expansion of this chemistry to dinuclear complexes has since provided the current best-performing Dy Cp^{R} -based SMM to date, $[\{\text{Dy}(\text{C}_5^{\text{iPr}}\text{Pr}_5)\}_2(\mu\text{-I})_3]$, ($U_{\text{eff}} = 1631(25) \text{ cm}^{-1}$; $T_{\text{H}} = 80$ K).²⁰

Recently, we reported that a Dy(III) contact ion-pair complex containing a weakly coordinating anion (WCA), $[\text{Dy}(\text{Cp}^{\text{ttt}})(\text{Cp}^*)\{\text{Al}[\text{OC}(\text{CF}_3)_3]_4\}]$, maintains a high $U_{\text{eff}} =$



1265(15) cm^{-1} , but its T_{H} value (36 K) is significantly diminished compared to the corresponding separated ion-pair complex $[\text{Dy}(\text{Cp}^{\text{ttt}})(\text{Cp}^*)][\text{Al}[\text{OC}(\text{CF}_3)_3]_4]$ ($U_{\text{eff}} = 1221(25) \text{ cm}^{-1}$, $T_{\text{H}} = 52 \text{ K}$), despite the geometrical similarity of their $\{\text{Dy}(\text{Cp}^{\text{ttt}})(\text{Cp}^*)\}$ cores.¹⁵ Conversely, the related halobenzene-bound complexes $[\text{Dy}(\text{Cp}^{\text{ttt}})(\text{Cp}^*)(\text{XPh})][\text{Al}[\text{OC}(\text{CF}_3)_3]_4]$ ($\text{X} = \text{F}, \text{Cl}, \text{Br}$) exhibit lower U_{eff} (range: 1100(9)–1182(9) cm^{-1}) and T_{H} (range: 22–24 K) values,²¹ challenging assumptions that an anion always introduces a greater transverse field than a weakly-bound neutral ligand.^{12,22–42} We sought to investigate the effect of other WCAs binding to $\{\text{Dy}(\text{Cp}^{\text{ttt}})_2\}$ to further establish the sensitivity of SMM parameters to weak equatorial interactions.

Here we disclose the synthesis of $[\text{Dy}(\text{Cp}^{\text{ttt}})_2\{\text{AlCl}[\text{OC}(\text{CF}_3)_3]_{3-\kappa-\text{Cl}}\}]$ (**1**) and $[\text{Dy}(\text{Cp}^{\text{ttt}})_2\{\text{AlCl}(\text{C}_2\text{H}_5)[\text{OC}(\text{C}_6\text{F}_5)_3]_{2-\kappa-\text{Cl}}\}]$ (**2**), and their characterisation by ATR-IR and NMR spectroscopy, elemental analysis, SQUID magnetometry and complete active space self-consistent field spin-orbit (CASSCF-SO) calculations. We find that coordination of the WCA to the Dy(III) ion in these complexes increases $\text{Dy}\cdots\text{Cp}^{\text{ttt}}$ distances and reduces $\text{Cp}^{\text{ttt}}_{\text{centroid}}\cdots\text{Dy}\cdots\text{Cp}^{\text{ttt}}_{\text{centroid}}$ angles vs. parent $[\text{Dy}(\text{Cp}^{\text{ttt}})_2][\text{B}(\text{C}_6\text{F}_5)_4]$ ⁸ to significantly reduce the strength of the axial ligand field. The purities of the $\pm m_J$ state manifold are reduced to different extents in **1** and **2** but in both cases U_{eff} and T_{H} are hugely diminished *c.f.* $[\text{Dy}(\text{Cp}^{\text{ttt}})_2][\text{B}(\text{C}_6\text{F}_5)_4]$ ⁸ with the differences in U_{eff} highlighting the extreme sensitivity of the electronic structures of Dy(III) ions to the variable strength of WCA binding.

Results and discussion

Synthesis

The reaction of $[\text{Dy}(\text{Cp}^{\text{ttt}})_2(\text{Cl})]$ ^{8,10,11} with one equivalent of $\text{PhF-Al}\{\text{OC}(\text{CF}_3)_3\}_3$ ⁴³ in fluorobenzene gave bright yellow crystals of **1** in 58% yield after recrystallisation from pentane (Scheme 1). The addition of a further equivalent of $\text{PhF-Al}\{\text{OC}(\text{CF}_3)_3\}_3$ did not lead to the



expected abstraction of chloride to form $[\text{Dy}(\text{Cp}^{\text{ttt}})_2][\{\text{Al}[\text{OC}(\text{CF}_3)_3\}_2(\mu\text{-Cl})]$,⁴⁴ *via in situ* generation of a bulkier WCA. Similarly, the reaction of $[\text{Dy}(\text{Cp}^{\text{ttt}})_2(\text{Cl})]$ with $[\text{Al}(\text{C}_2\text{H}_5)\{\text{OC}(\text{C}_6\text{F}_5)_3\}_2]$ in fluorobenzene gave yellow crystals of **2** in 60% yield after recrystallisation (Scheme 1). This superacid was chosen as $[\text{Dy}(\text{Cp}^{\text{ttt}})_2(\text{Cl})]$ did not react with $[\text{Al}\{\text{OC}(\text{C}_6\text{F}_5)_3\}_3]$ ⁴⁵ in fluorobenzene at room temperature. The stoichiometric reaction of **2** with $\text{HO}(\text{C}_6\text{F}_5)_3$ in hexane gave $[\text{Dy}(\text{Cp}^{\text{ttt}})_2(\text{Cl})]$ and $[\text{Al}\{\text{OC}(\text{C}_6\text{F}_5)_3\}_3]$, as a stronger thermodynamic driving force is required for chloride abstraction from the highly Lewis acidic Dy(III) centre.^{8,10,11}

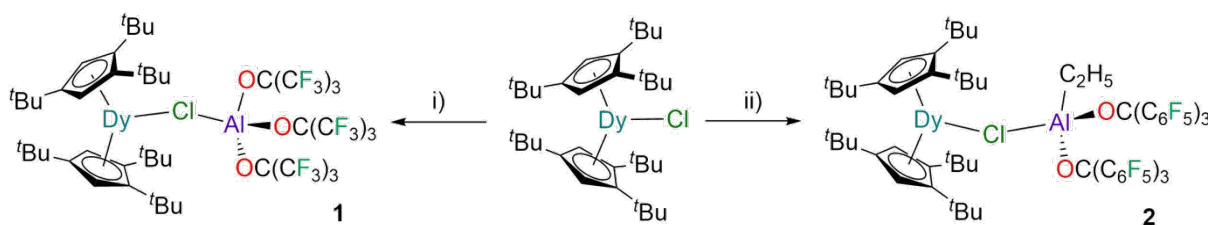


Figure 1. Synthesis of **1** and **2**. Conditions: i) $\text{PhF-Al}\{\text{OC}(\text{CF}_3)_3\}_3$ in fluorobenzene at room temperature; ii) $[\text{Al}(\text{C}_2\text{H}_5)\{\text{OC}(\text{C}_6\text{F}_5)_3\}_2]$ in fluorobenzene at room temperature.

Bulk characterisation

Elemental analysis results obtained for **1** and **2** typically gave lower carbon and hydrogen values than expected, which we attribute to carbide formation⁴⁶ and the uncertainty that can be introduced in these experiments from high fluorine contents.⁴⁷ The ATR-IR spectra of **1** and **2** show diagnostic resonances for C–H, C–F and C–O stretches (see Supporting Information Figures S1 and S2). The paramagnetism of **1** and **2** preclude the assignment of their ^1H , $^{13}\text{C}\{^1\text{H}\}$ and ^{19}F NMR spectra (Figures S3 and S5); the magnetic susceptibility values obtained by the Evans method⁴⁸ in fluorobenzene solutions (with a $\text{C}_6\text{H}_5\text{F}/\text{C}_6\text{D}_6$ insert; Figures S4 and S6) are close to the expected value for a Dy(III) ion (**1**: $10.63 \mu_{\text{B}}$, $14.1 \text{ cm}^3 \text{ K mol}^{-1}$, **2**: $10.20 \mu_{\text{B}}$, $13.0 \text{ cm}^3 \text{ K mol}^{-1}$; expected: $10.65 \mu_{\text{B}}$, $14.2 \text{ cm}^3 \text{ K mol}^{-1}$).⁴⁹



Single crystal X-ray Crystallography

The solid-state structures of **1** and **2** were determined by single crystal XRD (structures depicted in Figure 2, selected bond distances and angles compiled in Table 1; for crystallographic parameters see Supporting Information Table S1). These complexes show similar bulk features, with *pseudo*-trigonal arrangements of the two Cp^{ttt} centroids and Cl. Both complexes exhibit significant disorder at 100 K; for **1** this is observed in the {Cl-Al[OC(CF₃)₃]₃} moiety and parameters considered are the mean values for the disordered components, whilst for **2** there is disorder of the Cp^{ttt} groups about the Dy(III) centre in the plane perpendicular to the Dy–Cl axis and only the component with the highest occupancy is considered. The Cp^{ttt}_{centroid}⋯Dy⋯Cp^{ttt}_{centroid} angles of **1** [145.71(2)°] and **2** [145.57(2)°] are more bent than in both [Dy(Cp^{ttt})₂][B(C₆F₅)₄] [152.56(7)°] and [Dy(Cp^{ttt})₂(Cl)] [146.67(7)°];^{8,10,11} this is in accord with the large steric effects imposed by the WCAs. The proximity of the WCAs in **1** and **2** also induces an eclipsed arrangement of the Cp^{ttt} groups (Figures S10 and S11); by contrast [Dy(Cp^{ttt})₂(Cl)] and [Dy(Cp^{ttt})₂][B(C₆F₅)₄] both adopt a staggered arrangement.^{8,10,11} The Dy–Cl–Al angle of **1** [152.1(5)°] is lower than that of **2** [165.30(7)°], due to the three {OC(CF₃)₃} substituents in the former compared to one ethyl and two {OC(C₆F₅)₃} groups in the latter showing different steric effects.

The mean Dy⋯Cp^{ttt} distances of **1** [2.3549(10) Å] and **2** [2.3658(4) Å] are longer than in [Dy(Cp^{ttt})₂][B(C₆F₅)₄] [2.316(3) Å] but shorter than for [Dy(Cp^{ttt})₂(Cl)] [2.413(3) Å].^{8,10,11} This can be attributed to the Dy–Cl bond distance in [Dy(Cp^{ttt})₂(Cl)] [2.5480(12) Å] being shorter than for the WCAs in **1** [2.801(9) Å] and **2** [2.7301(12) Å]. Following correction for relative covalent radii (F: 0.64 Å; Cl: 0.99 Å),⁵⁰ the Dy–Cl bond lengths in **1** [1.811(9) Å] and **2** [1.7401(12) Å] are shorter than the Dy–F bond in [Dy(Cp^{ttt})(Cp*){Al[OC(CF₃)₃]_{4-κ-F}}] [2.812(4) Å before and 2.172(4) Å after correction];¹⁵ this indicates that the WCAs in **1** and **2**



bind strongly. The longer Dy–Cl distance in **1** compared to **2** can be ascribed to a combination of steric and electronic effects, where the combination of small ethyl and bulky {OC(C₆F₅)₃} groups of **2** lower the Lewis acidity and coordinative saturation of the Al centre; this is also reflected in the increased Al–Cl bond distance from **1** [2.220(10) Å] to **2** [2.316(2) Å].

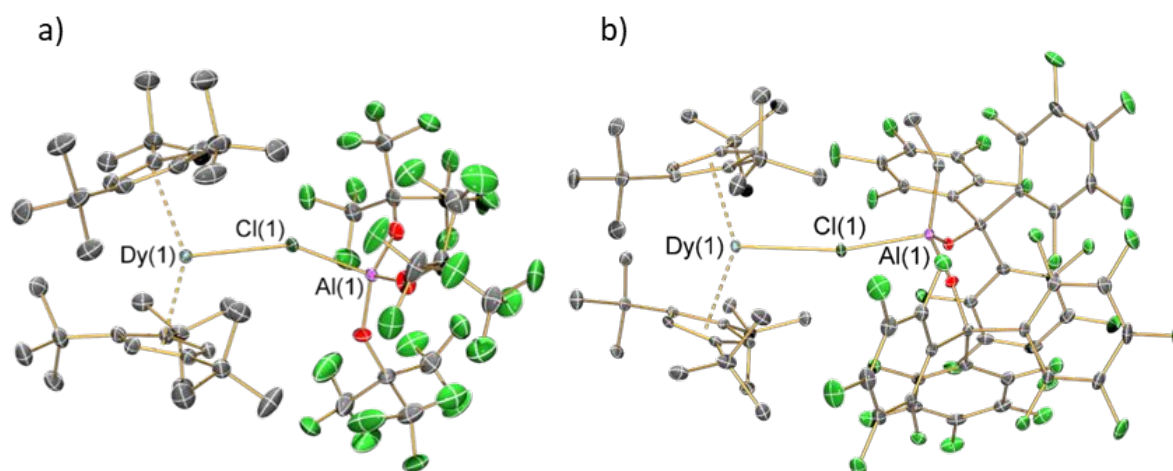


Figure 2. Single crystal XRD structures of a) **1** and b) **2** (Dy: cyan, C: grey, Al: purple, F: green, O: red). Displacement ellipsoids set at 30% probability levels; hydrogen atoms and the lattice fluorobenzene molecules have been omitted for clarity.

Table 1. Selected bond lengths and angles of **1** and **2**.

Parameter	1	2
Dy(1)⋯Cp ^{ttt} _{centroid}	2.3580(6) Å	2.3783(2) Å
Dy(1)⋯Cp ^{ttt} _{centroid}	2.3517(8) Å	2.3532(3) Å
Dy–Cl(1)	2.801(9) Å	2.7301(12) Å
Closest Dy(1)⋯C	2.979(10) Å	3.002(6) Å
Closest Dy(1)⋯H	2.562 Å	2.765 Å
Al(1)–Cl(1)	2.220(10) Å	2.316(2) Å
Cp ^{ttt} _{centroid} ⋯Dy(1) ⋯Cp ^{ttt} _{centroid}	145.71(2)°	145.57(2)°
Cp ^{ttt} _{centroid} ⋯Dy(1)–Cl(1)	100.61(9)°	107.87(3)°
Cp ^{ttt} _{centroid} ⋯Dy(1)–Cl(1)	112.49(9)°	106.46(3)°



Dy(1)–Cl(1)–Al(1)

152.1(5)°

165.30(7)°

View Article Online
DOI: 10.1039/D4DT02713B

Magnetism and CASSCF-SO Calculations

The static and dynamic magnetic properties of **1** and **2** were investigated by SQUID magnetometry (Figure 3, Supporting Information Figures S12–S23 and Tables S2 and S3). The molar magnetic susceptibilities ($\chi_M T$) at 300 K [**1**: 13.2 cm³ K mol⁻¹; **2**: 12.1 cm³ K mol⁻¹] are lower than the expected Dy(III) free-ion value (⁶H_{15/2}, $\chi T = 14.2$ cm³ K mol⁻¹)⁵¹ and the Evans method values, which we attribute to small mass or sample shape correction errors (measurement of sample dimensions and assumption of a cylindrical sample). The susceptibilities decrease slowly with temperature to *ca.* 22 K for **1** and 26 K for **2**, at which point there is a sharp decrease that can be attributed to slow thermalisation of the sample. Saturation of the spin states *via* the application of a 7 T field at 2 K results in a magnetisation of 4.92 $N\mu_B$ for **1** and 4.46 $N\mu_B$ for **2**; the latter is markedly lower than the expected value of *ca.* 5 $N\mu_B$, which is also attributed to the mass or shape correction error.⁵² Magnetisation *vs.* field measurements are the first indication of slow magnetisation dynamics with a step at low fields.⁵³ Butterfly-shaped hysteresis is observed for both complexes (Figure 3), with **1** retaining a larger magnetisation between 1 T and the onset of QTM, suggesting slower in-field dynamics for **1** in this range. The hysteresis curves remain marginally open around zero field at 2 and 4 K (with sweep rate of 22 Oe s⁻¹ in this region) but without a significant coercive field or remanent magnetisation (Figure 3). The coordination of the WCA in **1** and **2** significantly increases the magnetic relaxation rate compared to that of the separated ion-pair complex [Dy(Cp^{III})₂][B(C₆F₅)₄] ($T_H = 60$ K). However, the hysteresis loops of **1** and **2** are more open at 2 K than for [Dy(Cp^{III})₂(Cl)] which is closed at zero field and only slightly open in fields < 1 T,^{10,11} showing the positive effect of the delocalisation of the negative charge in the WCAs compared to chloride. By contrast, the T_H of the contact-ion pair complex [Dy(Cp^{III})(Cp*){Al[OC(CF₃)₃]₄}] (36 K) is only slightly lower than that of the separated ion-



pair complex $[\text{Dy}(\text{Cp}^{\text{ttt}})(\text{Cp}^*)][\text{Al}[\text{OC}(\text{CF}_3)_3]_4]$ (52 K),¹⁵ showing that the binding of the WCAs in **1** and **2** is relatively strong in comparison to this literature example; the WCA binding in **1** and **2** has also had a greater effect on the T_{H} values of a dysprosocenium cation than previously seen for weakly-bound haloarenes.^{21,54}

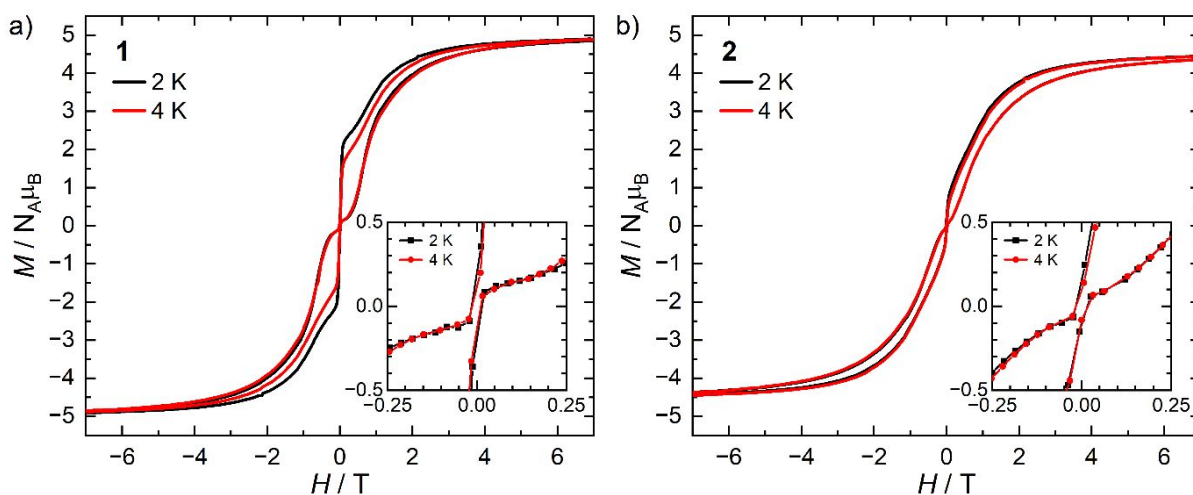


Figure 3. M vs. H hysteresis loops of a) **1** and b) **2** suspended in eicosane at 2 and 4 K, inset shows zero field region. The sweep rates are 22 Oe s^{-1} for $|H| < 1$ T, 54 Oe s^{-1} for $1 < |H| < 2$ T, and 91 Oe s^{-1} for $2 < |H| < 7$ T.

For zero-field AC susceptibility data, peaks are observed between 2–73 K for **1** and 12–59 K for **2**; these data fitted well to the generalised Debye model in CC-FIT2^{55,56} and the relaxation profile was extracted (Figure 3). At low temperatures the relaxation rates of complex **2** lie between the AC and DC timescales and are too fast to be accurately characterised by DC magnetisation decay measurements. Predominantly Orbach relaxation mechanisms are observed at high temperatures until the Raman process begin to dominate at around 50 K for **1** and 40 K for **2**. For **1**, a plateau in the data < 20 K is indicative of QTM starting to dominate, for **2** QTM is not observed within the observable range. The relaxation profiles were fit to a combination of Orbach ($10^{-A} e^{\frac{U_{\text{eff}}}{T}}$), Raman ($10^R T^n$) and QTM (10^{-Q}) processes (**1** only);^{55,56}



the resultant parameters are compiled in Table 2. The differences in the magnetic properties of **1** [$U_{\text{eff}} = 886(17) \text{ cm}^{-1}$] and **2** [$U_{\text{eff}} = 559(18) \text{ cm}^{-1}$] are ascribed to the variations in their crystal fields, with longer Dy–Cl and shorter Dy \cdots Cp^{ttt}_{centroid} distances in **1** contributing to the larger U_{eff} . By contrast, [Dy(Cp^{ttt})₂(Cl)] relaxes via a Raman process rather than an over-barrier Orbach process, and this slow relaxation could only be observed in an applied DC field,⁹ thus slower QTM in **1** and **2** can be attributed to elongation of the Dy–Cl bonds. The large difference in U_{eff} between **1**, **2** and [Dy(Cp^{ttt})₂][B(C₆F₅)₄] (1223 cm⁻¹);⁸ is in contrast to [Dy(Cp^{ttt})(Cp*)][Al{OC(CF₃)₃}₄] and [Dy(Cp^{ttt})(Cp*){Al[OC(CF₃)₃]_{4-κ-F}}], which exhibit similar U_{eff} values upon the coordination of the WCA [1221(25) and 1265(15) cm⁻¹, respectively].¹⁵ It was previously reported that low Raman exponents are characteristic of heavy 4f-metalloceonium cations and that this property is disrupted by Cl⁻ coordination;⁹ we find that this is a gradual transition as the value of n trends with the strength of the Dy–Cl interaction: [Dy(Cp^{ttt})₂][B(C₆F₅)₄] \approx **1** < **2** < [Dy(Cp^{ttt})₂(Cl)] [$n = 2.151, 2.3(2), 3.13(9)$ and $5.3 \text{ s}^{-1} \text{ K}^{-n}$, respectively].^{8,9} The differing Raman rates in **1** and **2** are attributed to both crystal field effects and the different low-energy vibrations of the two WCAs;⁵⁷ the coordination of a WCA and subsequent introduction of low-energy vibrations was observed to increase Raman rates in [Dy(Cp^{ttt})(Cp*){Al[OC(CF₃)₃]_{4-κ-F}}].¹⁵

View Article Online
DOI: 10.1039/D4DT02713B



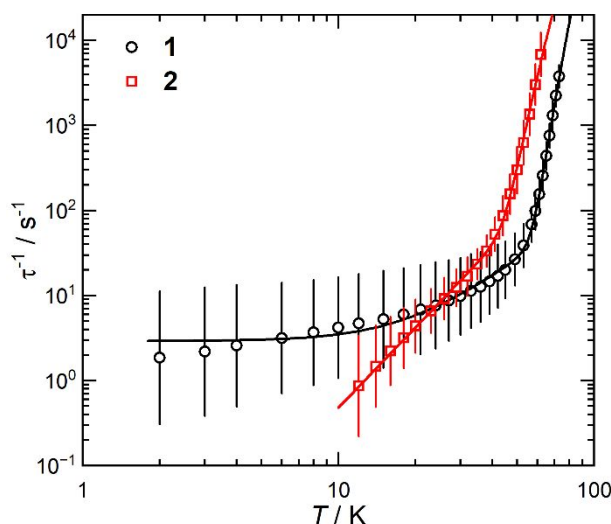


Figure 4. Temperature-dependent magnetic relaxation rates of **1** and **2**. Relaxation rates are derived from AC susceptibility data. Error bars represent one standard deviation in the logarithmic distribution of relaxation rates. Lines of best fit are given by Equation S2.

CASSCF-SO calculations were performed on models of **1** and **2** using the metrical parameters obtained from single crystal XRD in OpenMolcas⁵⁸ (see Figure 5 and Supplementary Information Tables S4 and S5). The calculated U_{eff} values [**1**: 778 cm^{-1} ; **2**: 584 cm^{-1}], derived from when the g_x and g_y contributions surpass 0.1, are comparable to measured values proceeding *via* the 3rd excited $\pm m_J$ state for **1** and the 2nd excited state for **2**; a better match of the calculated and experimental U_{eff} values of **1** is for Orbach relaxation to proceed *via* the 4th excited state (892 cm^{-1}). The CASSCF calculations do not explain the faster QTM in **1** than **2**: ground states for **1** and **2** are dominated by 98% and 97% $m_J = \pm 15/2$ respectively, with transverse g -values of up to $1-2 \times 10^{-4}$.



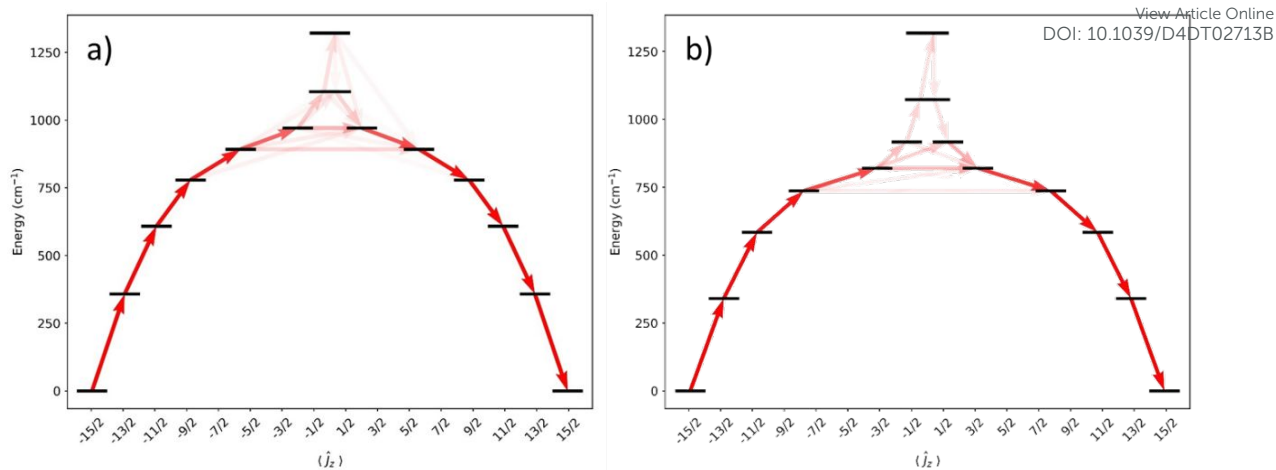


Figure 5. Energy barrier to magnetic relaxation for models of **1** and **2**. Electronic states from CASSCF-SO calculations, labelled with their dominant m_J composition in the $J = 15/2$ basis. Arrows represent the Orbach relaxation pathway, where the opacity of the arrows is proportional to the transition probability approximated with the average matrix elements of magnetic moment connecting the states, $\gamma_{ij} = (1/3)[|\langle i|\mu_x|j\rangle|^2 + |\langle i|\mu_y|j\rangle|^2 + |\langle i|\mu_z|j\rangle|^2]$, normalised from each departing state and commencing from $|-15/2\rangle$.

Table 2. Selected magnetic properties of **1** and **2**.

	1	2
U_{eff}	886(17) cm^{-1}	559(18) cm^{-1}
τ_0	$10^{-11.1(2)}$ s	$10^{-9.4(2)}$ s
C	$10^{-2.5(3)}$ $\text{s}^{-1} \text{K}^{-n}$	$10^{-3.45(14)}$ $\text{s}^{-1} \text{K}^{-n}$
n	2.3(2)	3.13(9)
τ_{QTM}	$10^{-0.46(4)}$ s	-

Conclusions

Two dysprosium metallocene complexes have been reported that have equatorially bound WCAs. During the synthetic investigations we found that the *in situ* formation of larger WCAs was not viable by the routes investigated. By a combination of single crystal XRD, magnetic measurements and *ab initio* calculations we find that the WCAs in the two novel



complexes herein bind relatively strongly compared to literature examples of WCA- and haloarene-bound dysprosium metallocene complexes but are more weakly coordinating than chloride. The transverse fields introduced using the WCAs herein almost quench magnetic hysteresis entirely, and greatly reduce the effective magnetic barriers to magnetic relaxation, but significant differences are seen between the two complexes. Together, these data provide fresh insights into the sensitivity of dysprosocenium cations to weak equatorial ligand fields.

Experimental

Materials and methods

All manipulations were performed in an inert atmosphere (argon) with rigorous exclusion of oxygen and water using Schlenk line and glovebox techniques. Fluorobenzene was dried by stirring with CaH₂ overnight and was stored over 4 Å molecular sieves. Pentane was dried over a column charged with alumina and stored over potassium mirrors. Anhydrous benzene was purchased and was stored over 4 Å molecular sieves. All solvents were degassed before use. For NMR spectroscopy C₆D₆ was dried by refluxing over K, and was vacuum transferred and degassed by three freeze-pump-thaw cycles before use. The reagent AlEt₃ (1 M in heptane) was purchased from Sigma-Aldrich and used as received. The reagents [Dy(Cp^{ttt})₂(Cl)],^{8,10,11} HOC(C₆F₅)₃,⁵⁹ PhF–Al{OC(CF₃)₃}₃,⁴³ [Al{OC(C₆F₅)₃}₃]⁴⁵ were synthesised according to literature procedures. The reagent [Al{OC(C₆F₅)₃}₂(C₂H₅)] was synthesised *via* an adapted literature procedure.⁴⁵ ¹H (400 and 500 MHz), ¹³C {¹H} (126 MHz) and ¹⁹F (376 MHz) NMR spectra were obtained on a Bruker Avance III 400 or 500 MHz spectrometer at 298 K and were referenced to the solvent used, or to external TMS (¹H, ¹³C), or C₇H₅F₃/CDCl₃ (¹⁹F). ATR-IR spectra were recorded on a Bruker Alpha spectrometer with Platinum-ATR module. Elemental analysis was carried out by Mr Martin Jennings and Mrs



Anne Davies at the Microanalytical service, Department of Chemistry, the University of Manchester. View Article Online
DOI: 10.1039/D4DT02713B

Synthetic procedures

[Dy(Cp^{ttt})₂{AlCl[OC(CF₃)₃]₃-κ-Cl}] (1). [Dy(Cp^{ttt})₂(Cl)] (0.332 g, 0.5 mmol) and PhF–Al{OC(CF₃)₃}₃ (0.442 g, 0.5 mmol) were cooled to 0 °C. Fluorobenzene (10 mL) was added and the reaction mixture was stirred at 0 °C for 4 hr. The solvent was removed *in vacuo*, and pentane (40 mL) was added to extract the product. The solvent was removed under vacuum until crystals started to form. The solution was stored at –30 °C and bright yellow crystals formed overnight. The solvent was decanted and residual volatiles were removed under vacuum to afford **1** (0.407 g, 0.3 mmol, 58%). Anal. Calcd (%) for C₄₆H₅₈AlClDyF₂₇O₃: C, 39.55; H, 4.13. Found: C, 38.27; H, 4.33. μ_{eff} product = 10.63 μ_{B} (Evans method, C₆D₆, 298 K). The paramagnetism of **1** precluded the assignment of ¹H, ¹³C{¹H} and ¹⁹F NMR spectra. FTIR (ATR, microcrystalline): $\tilde{\nu}$ = 2966 (s, C–H stretch), 2908 (w, C–H stretch), 2875 (w, C–H stretch), 1483 (w), 1463 (w), 1398 (w), 1361 (m), 1301 (s), 1260 (s, C–F stretch), 1235 (s), 1217 (s), 1178 (s), 1093 (br. s), 1019 (s), 972 (s), 859 (m), 828 (s), 799 (s), 728 (s), 686 (m), 563 (m), 538 (s), 444 (s).

[Dy(Cp^{ttt})₂{AlCl(C₂H₅)[OC(C₆F₅)₃]₂-κ-Cl}] (2). Fluorobenzene (10 mL) was added to [Dy(Cp^{ttt})₂(Cl)] (0.330 g, 0.5 mmol) and [Al{OC(C₆F₅)₃}₂(C₂H₅)] (0.807 g, 0.5 mmol) at room temperature. The yellow reaction mixture was stirred overnight, concentrated under vacuum to *ca.* 2 mL, and yellow crystals formed at room temperature overnight. The solvent was decanted, and residual volatiles removed under vacuum to afford **2** (0.593 g, 0.3 mmol, 60%). Anal. Calcd (%) for C₈₆H₇₃AlClDyF₃₂O₂: C, 52.40; H, 3.73. Found: C, 49.84; H, 3.30. μ_{eff} product = 10.20 μ_{B} (Evans method, C₆D₆, 298 K). The paramagnetism of **2** precluded the assignment of ¹H, ¹³C{¹H} and ¹⁹F NMR spectra. FTIR (ATR, microcrystalline): $\tilde{\nu}$ = 2963 (m,



C–H stretch), 2910 (w, C–H stretch), 2869 (w, C–H stretch), 1650 (s), 1594 (w), 1525 (s), 1490 (s), 1402 (m), 1363 (w), 1303 (s), 1264 (w), 1239 (m), 1215 (s), 1153 (s), 1130 (s), 1112 (s), 1023 (s), 995 (s), 993 (s), 980 (s), 960 (s), 873 (m), 828 (m), 795 (s), 787 (s), 754 (s), 699 (s), 684 (s), 649 (w), 631 (s), 619 (s), 569 (m), 499 (m), 442 (m), 427 (w).

$[\text{Al}(\text{C}_2\text{H}_5)\{\text{OC}(\text{C}_6\text{F}_5)_3\}_2]$. Toluene (100 mL) was added HOC(C₆F₅)₃ (5.300 g, 10 mmol), the solution was added to triethylaluminium (5 mL, 5 mmol, 1.0 M in heptane) in toluene (50 mL) at –78 °C. The solution was stirred at for 1 h, then warmed to room temperature and stirred for 1h. The reaction mixture was then stirred at 90 °C for 1 h; gas evolution was observed and the reaction was stopped once this ceased. The colourless solution was concentrated to *ca.* 70 mL under vacuum and stored at –35 °C overnight to yield a white precipitate. The solution was decanted, the product washed with pentane (2 x 30 mL) and volatiles removed *in vacuo* to obtain the product (3.453 g, 3.1 mmol, 62%). Anal. Calcd (%) for C₄₀H₅AlF₃₀O₂: C, 43.11; H, 0.45. Found: C, 43.30; H, 0.39. A septet in the ¹H NMR spectrum at 3.51 ppm (*J* = 2.0 Hz) corresponds to an impurity that we were not able to assign; correlation spectroscopy was inconclusive when we attempted to resolve its identity. However, elemental analysis results obtained were in good agreement with expected values for $[\text{Al}(\text{C}_2\text{H}_5)(\text{OC}(\text{C}_6\text{F}_5)_3)_2]$, so this material was used without further purification. ¹H NMR (400.13 MHz, C₆D₆, 298 K): δ = 3.64 (q, 2H, ³*J*_{HH} = 7.0 Hz, CH₂CH₃), 0.84 (t, 3H, ³*J*_{HH} = 7.0 Hz, CH₂CH₃). ¹³C {¹H} NMR (125.79 MHz, C₆D₆, 298 K): δ = 146.1–136.5 (m, C₆F₅), 73.6 (CH₂CH₃), 14.4 (CH₂CH₃). ¹⁹F NMR (376.46 MHz, C₆D₆, 298 K): δ = 140.8 (d, ³*J*_{FF} = 20.0 Hz, C₆F₅-*o*), 151.2 (t, ³*J*_{FF} = 20.0 Hz, C₆F₅-*p*), 161.0 (t, ³*J*_{FF} = 20.0 Hz, C₆F₅-*m*).

X-ray Crystallography

Crystals of **1** were examined using a Rigaku XtalLAB AFC11 diffractometer with a Hybrid Photon Counting area detector and mirror-monochromated Cu Kα (λ = 1.54178 Å) or



Mo K α radiation ($\lambda = 0.71073 \text{ \AA}$). Crystals of **2** were examined using an Oxford Diffraction Supernova diffractometer, furnished with a CCD area detector and a mirror-monochromated Mo K α radiation ($\lambda = 0.71073 \text{ \AA}$). Intensities were integrated from data recorded on 1° frames by ω or ϕ rotation. Cell parameters were refined from the observed positions of all strong reflections in each data set. A Gaussian grid face-indexed absorption correction with a beam profile was applied to all structures.⁶⁰ The structures were solved by direct and heavy atom methods using SHELXS or dual-space methods using SHELXT;⁶¹ the datasets were refined by full-matrix least-squares on all unique F^2 values,⁶¹ with anisotropic displacement parameters for all non-hydrogen atoms, and with constrained riding hydrogen geometries; $U_{\text{iso}}(\text{H})$ was set at 1.2 (1.5 for methyl groups) times U_{eq} of the parent atom. The largest features in final difference syntheses were close to heavy atoms and were of no chemical significance. CrysAlisPro⁶⁰ was used for control and integration, and SHELXL^{61,62} was employed through OLEX2⁶³ for structure solution and refinement. ORTEP-3⁶⁴ and POV-Ray⁶⁵ were employed for molecular graphics.

Magnetic Measurements

Magnetic measurements were made using a Quantum Design MPMS3 superconducting quantum interference device (SQUID) magnetometer. All samples were prepared in the same manner. All samples were crushed with a mortar and pestle under an inert atmosphere, and then loaded into a borosilicate glass NMR tube along with eicosane, which was then evacuated and flame-sealed to a length of *ca.* 5 cm. The eicosane was melted by heating the tube gently with a low-power heat gun in order to immobilise the crystallites. The NMR tube was then mounted in the centre of a drinking straw using friction by wrapping it with Kapton tape, and the straw was then fixed to the end of the sample rod. For **1** 25.6 mg of sample was prepared with 15.4 mg of eicosane, for **2** 21.0 mg sample with 12.9 mg eicosane. The measurements were corrected



for the diamagnetism of the straw, borosilicate tube and eicosane using calibrated blanks and for the intrinsic diamagnetism of the sample estimated as the molecular weight (g mol^{-1}) multiplied by $-0.5 \times 10^{-6} \text{ cm}^3 \text{ K mol}^{-1}$. The moment was also corrected for the shape of the sample (divided by 1.022 for **1** and 1.029 for **2**), calculated with the Quantum Design Geometry Simulator assuming a perfectly cylindrical sample shape with height 3.79 mm and diameter 4.06 mm (**1**) or height 3.31 mm and diameter 4.05 mm (**2**).

All DC magnetic measurements were performed in DC scan mode with a scan length of 40 mm and a scan time of 6 s. The equilibrium magnetic susceptibility was measured under 0.1 T field, on cooling in temperature settle mode. For **1** the sweep rates were 5 K min^{-1} from 300–100 K, 2 K min^{-1} from 100–10 K and 1 K min^{-1} from 10–1.8 K, with addition waits of 2, 4, 10 and 18 minutes at 3.0, 2.5, 2.1 and 1.8 K, respectively. For **2** the sweep rates were 5 K min^{-1} from 300–100 K, 2 K min^{-1} from 100–50 K and 1 K min^{-1} from 50–1.8 K. Equilibrium magnetisation *vs.* field measurements held the temperature and field stable for 10 mins (2 K) or 5 mins (4 K) before each measurement. Hysteresis measurements were performed in continuous sweep mode between $\pm 7 \text{ T}$ on a sample that had been magnetised at 7 T. The sweep rates were 22 Oe s^{-1} for $|\text{H}| < 1 \text{ T}$, 54 Oe s^{-1} for $1 < |\text{H}| < 2 \text{ T}$, and 91 Oe s^{-1} for $2 < |\text{H}| < 7 \text{ T}$.

Alternating frequency (AC) susceptibility measurements were recorded for 8 frequencies per decade between 0.1–1000 Hz with a 2 Oe oscillating field. Averages were performed for 2 s or for 10 cycles, whichever was longer. Slow thermalisation was observed below 40 K for **1** (much slower at 21 K and below) and below 20 K for **2**, so after changing temperature the ac susceptibility was monitored as a function of time to ensure complete thermalisation before recording the frequency dependence of the ac susceptibility.

AC data were fit to the Generalised Debye model (Equation S1) in CC-FIT2 to extract relaxation rates and distributions.^{55,56}



$$\chi(\omega) = \chi_S + (\chi_T - \chi_S) \frac{1}{1 + (i\omega\tau_{Debye})^{1-\alpha}}$$

View Article Online
DOI: 10.1039/D4DT02713B

Equation S1

where τ_{Debye}^{-1} is the relaxation rate, ω is the angular frequency of the AC field and χ_T and χ_S are the isothermal and adiabatic susceptibilities, respectively. There is good agreement between the model and the data (Figures S17–S19, S20–S22). The resultant parameters are shown in Tables S2–S3.

The temperature-dependence of the rates of **1** and **2** in zero-field was fit to:

$$\log_{10}[\tau^{-1}] = \log_{10} \left[10^{-A} e^{-\left(\frac{U_{eff}}{k_B T}\right)} + 10^R T^n + 10^{-Q} \right]$$

Equation S2

where 10^{-A} s^{-1} (τ_0^{-1}) is the Orbach prefactor, U_{eff} is the effective energy barrier for the Orbach process, $10^R \text{ s}^{-1} \text{ K}^{-n}$ (C) and n are phenomenological parameters that describe the Raman process, and 10^{-Q} s^{-1} (τ_{QTM}^{-1}) is the quantum tunnelling of magnetisation (QTM) rate; for **2** the QTM rate is omitted as rate were determined only for 12 K and above and no plateau was observed in this region.

CASSCF-SO Calculations

OpenMolcas⁵⁸ was used to perform CASSCF-SO calculations on **1** and **2** to determine the electronic structure. The molecular geometries from the single crystal XRD structures were used with no optimisation. Electron integrals were performed in the SEWARD module using basis sets from ANO-RCC library^{66–69} with VTZP quality for the Dy atom, VDZP quality for the cyclopentadienyl C atoms and the fluorobenzene F atoms, and VDZ quality for all remaining atoms, employing the second-order DKH Hamiltonian for scalar relativistic effects. Resolution of identity Cholesky decomposition (RICD) of the two-electron integrals with atomic compact Cholesky decomposition (acCD) auxiliary basis sets was employed to reduce



computational demand.⁷⁰ The molecular orbitals (MOs) were optimised in state-averaged CASSCF (SA-CASSCF) calculations in the RASSCF module, where the active space was defined by the nine electrons in the seven 4f orbitals of Dy(III). A SA-CASSCF calculation was performed for the lowest 18 sextets, where these states were then mixed by spin orbit coupling in the RASSI module. SINGLE_ANISO was used to decompose the resulting spin-orbit wave functions into the CF Hamiltonian formalism.⁷¹

View Article Online
DOI: 10.1039/D4DT02713B

Author contributions

S.C.C. and D.P.M. provided the original concept. S.C.C. synthesised and characterised the complexes. S.C.C. collected and finalised the SCXRD data. S.C.C. performed *ab initio* calculations. G.K.G. collected the magnetic data. G.K.G. and S.C.C. interpreted the magnetic data. G.K.G. supervised the magnetism and calculations components. D.P.M. supervised the synthetic component and directed the research. S.C.C., G.K.G. and D.P.M. wrote the manuscript.

Conflicts of interest

There are no conflicts to declare.

Data availability

Supplementary information is available in the online version of the paper. Correspondence and requests for materials should be directed to G.K.G. and D.P.M. Crystallographic data for the structures reported in this Article have been deposited at the Cambridge Crystallographic Data Centre, under deposition numbers CCDC 2386076 (1), 2386077 (2). Copies of the data can be obtained free of charge from the CCDC via www.ccdc.cam.ac.uk/getstructures. Raw research data files supporting this publication are available from Figshare at



<https://doi.org/10.6084/m9.figshare.27091723>. Apart from the data sets mentioned, all other data supporting the findings of this study are available within the Article and Supplementary information.

Acknowledgements

We thank the University of Manchester for access to the Computational Shared Facility and the European Research Council (CoG-816268) and the UK EPSRC (EP/P001386/1 and EP/S033181/1) for funding. We acknowledge the EPSRC UK National Electron Paramagnetic Resonance Service for access to the SQUID magnetometer.

References

- 1 D. Gatteschi, R. Sessoli and J. Villain, *Molecular Nanomagnets*, Oxford University Press, Oxford, 2006.
- 2 *Lanthanides and Actinides in Molecular Magnetism*, Eds. R. A. Layfield and M. Murugesu, Wiley, Hoboken, 2015.
- 3 M. J. Giansiracusa, G. K. Gransbury, N. F. Chilton and D. P. Mills, in *Encyclopedia of Inorganic and Bioinorganic Chemistry*, Ed. R. A. Scott, John Wiley & Sons Ltd, Chichester, 2021, DOI:10.1002/9781119951438.eibc2784.
- 4 J. D. Rinehart and J. R. Long, *Chem. Sci.*, 2011, **2**, 2078–2085.
- 5 L. Ungur and L. F. Chibotaru, *Phys. Chem. Chem. Phys.*, 2011, **13**, 20086–20090.
- 6 N. F. Chilton, C. A. P. Goodwin, D. P. Mills and R. E. P. Winpenny, *Chem. Commun.*, 2015, **51**, 101–103.
- 7 F. Ortu and D. P. Mills, in *Handbook on the Physics and Chemistry of Rare Earths*, Eds. J.-C. G. Bünzli and V. K. Pecharsky, Elsevier B.V., Amsterdam, 1st edn., 2019, vol. 55, pp. 1–87.



- 8 C. A. P. Goodwin, F. Ortu, D. Reta, N. F. Chilton and D. P. Mills, *Nature*, 2017, **548**, 439–442. View Article Online
DOI: 10.1039/D7DT02713B
- 9 C. A. P. Goodwin, D. Reta, F. Ortu, N. F. Chilton and D. P. Mills, *J. Am. Chem. Soc.*, 2017, **139**, 18714–18724.
- 10 F.-S. Guo, B. M. Day, Y.-C. Chen, M.-L. Tong, A. Mansikkamäki and R. A. Layfield, *Angew. Chem. Int. Ed.*, 2017, **56**, 11445–11449.
- 11 F.-S. Guo, B. M. Day, Y.-C. Chen, M.-L. Tong, A. Mansikkamäki and R. A. Layfield, *Angew. Chem. Int. Ed.*, 2020, **59**, 18844.
- 12 Y.-S. Meng, Y.-Q. Zhang, Z.-M. Wang, B.-W. Wang and S. Gao, *Chem. Eur. J.*, 2016, **22**, 12724–12731.
- 13 K. R. McClain, C. A. Gould, K. Chakarawet, S. J. Teat, T. J. Groshens, J. R. Long and B. G. Harvey, *Chem. Sci.*, 2018, **9**, 8492–8503.
- 14 F.-S. Guo, B. M. Day, Y.-C. Chen, M.-L. Tong, A. Mansikkamäki and R. A. Layfield, *Science*, 2018, **362**, 1400–1403.
- 15 G. K. Gransbury, S. C. Corner, J. G. C. Kragsskow, P. Evans, H. M. Yeung, W. J. A. Blackmore, G. F. S. Whitehead, I. J. Vitorica-Yrezabal, M. S. Oakley, N. F. Chilton and D. P. Mills, *J. Am. Chem. Soc.*, 2023, **145**, 22814–22825.
- 16 P. Evans, D. Reta, G. F. S. Whitehead, N. F. Chilton and D. P. Mills, *J. Am. Chem. Soc.*, 2019, **141**, 19935–19940.
- 17 F.-S. Guo, M. He, G.-Z. Huang, S. R. Giblin, D. Billington, F. W. Heinemann, M.-L. Tong, A. Mansikkamäki and R. A. Layfield, *Inorg. Chem.*, 2022, **61**, 6017–6025.
- 18 J. C. Vanjak, B. O. Wilkins, V. Vieru, N. S. Bhuvanesh, J. H. Reibenspies, C. D. Martin, L. F. Chibotaru and M. Nippe, *J. Am. Chem. Soc.*, 2022, **144**, 17743–17747.
- 19 A. H. Vincent, Y. L. Whyatt, N. F. Chilton and J. R. Long, *J. Am. Chem. Soc.*, 2023, **145**, 1572–1579.



- 20 C. A. Gould, K. R. McClain, D. Reta, J. G. C. Kragoskow, D. A. Marchiori, E. Lachman, E. S. Choi, J. G. Analytis, R. D. Britt, N. F. Chilton, B. G. Harvey and J. R. Long, *Science*, 2022, **375**, 198–202.
- 21 S. C. Corner, G. K. Gransbury, I. J. Vitorica-Yrezabal, G. F. S. Whitehead, N. F. Chilton and D. P. Mills, *Inorg. Chem.*, 2024, **63**, 9552–9561.
- 22 S. Demir, J. M. Zadrozny, M. Nippe and J. R. Long, *J. Am. Chem. Soc.*, 2012, **134**, 18546–18549.
- 23 S. Demir, M. Nippe, M. I. Gonzalez and J. R. Long, *Chem. Sci.*, 2014, **5**, 4701–4711.
- 24 S. Demir, J. M. Zadrozny and J. R. Long, *Chem. Eur. J.*, 2014, **20**, 9524–9529.
- 25 T. Pugh, N. F. Chilton and R. A. Layfield, *Angew. Chem. Int. Ed.*, 2016, **55**, 11082–11085.
- 26 F.-S. Guo and R. A. Layfield, *Chem. Commun.*, 2017, **53**, 3130–3133.
- 27 S. Demir, M. D. Boshart, J. F. Corbey, D. H. Woen, M. I. Gonzalez, J. W. Ziller, K. R. Meihaus, J. R. Long and W. J. Evans, *Inorg. Chem.*, 2017, **56**, 15049–15056.
- 28 C. A. Gould, L. E. Darago, M. I. Gonzalez, S. Demir and J. R. Long, *Angew. Chem. Int. Ed.*, 2017, **56**, 10103–10107.
- 29 B. M. Day, F.-S. Guo and R. A. Layfield, *Acc. Chem. Res.*, 2018, **51**, 1880–1889.
- 30 S.-M. Chen, J. Xiong, Y.-Q. Zhang, F. Ma, H.-L. Sun, B.-W. Wang and S. Gao, *Chem. Commun.*, 2019, **55**, 8250–8253.
- 31 P. Evans, D. Reta, C. A. P. Goodwin, F. Ortu, N. F. Chilton and D. P. Mills, *Chem. Commun.*, 2020, **56**, 5677–5680.
- 32 D. Errulat, B. Gabidullin, A. Mansikkamäki and M. Murugesu, *Chem. Commun.*, 2020, **56**, 5937–5940.
- 33 R. Collins, M. J. Heras Ojea, A. Mansikkamäki, J. Tang and R. A. Layfield, *Inorg. Chem.*, 2020, **59**, 642–647.



- 34 C. Chen, Z.-B. Hu, H. Ruan, Y. Zhao, Y.-Q. Zhang, G. Tan, Y. Song and X. Wang, *Organometallics*, 2020, **39**, 4143–4148. View Article Online
DOI: 10.1039/D0DT02713B
- 35 C. A. Gould, E. Mu, V. Vieru, L. E. Darago, K. Chakarawet, M. I. Gonzalez, S. Demir and J. R. Long, *J. Am. Chem. Soc.*, 2020, **142**, 21197–21209.
- 36 C. Chen, Z. Hu, J. Li, H. Ruan, Y. Zhao, G. Tan, Y. Song and X. Wang, *Inorg. Chem.*, 2020, **59**, 2111–2115.
- 37 N. Mavragani, D. Errulat, D. A. Gálico, A. A. Kitos, A. Mansikkamäki and M. Murugesu, *Angew. Chem. Int. Ed.*, 2021, **60**, 24206–24213.
- 38 L. E. Darago, M. D. Boshart, B. D. Nguyen, E. Perlt, J. W. Ziller, W. W. Lukens, F. Furche, W. J. Evans and J. R. Long, *J. Am. Chem. Soc.*, 2021, **143**, 8465–8475.
- 39 E. Castellanos, F. Benner and S. Demir, *Inorg. Chem. Front.*, 2022, **9**, 1325–1336.
- 40 N. Mavragani, A. A. Kitos, A. Mansikkamäki and M. Murugesu, *Inorg. Chem. Front.*, 2023, **10**, 259–266.
- 41 S. Demir, M. I. Gonzalez, L. E. Darago, W. J. Evans and J. R. Long, *Nat. Commun.*, 2017, **8**, 2144.
- 42 E. R. Pugliese, F. Benner, E. Castellanos, F. Delano and S. Demir, *Inorg. Chem.*, 2022, **61**, 2444–2454.
- 43 L. O. Müller, D. Himmel, J. Stauffer, G. Steinfeld, J. Slattery, G. Santiso-Quiñones, V. Brecht and I. Krossing, *Angew. Chem. Int. Ed.*, 2008, **47**, 7659–7663.
- 44 A. Martens, P. Weis, M. C. Krummer, M. Kreuzer, A. Meierhöfer, S. C. Meier, J. Bohnenberger, H. Scherer, I. Riddlestone and I. Krossing, *Chem. Sci.*, 2018, **9**, 7058–7068.
- 45 J. F. Kögel, A. Y. Timoshkin, A. Schröder, E. Lork and J. Beckmann, *Chem. Sci.*, 2018, **9**, 8178–8183.
- 46 F. P. Gabbaï, P. J. Chirik, D. E. Fogg, K. Meyer, D. J. Mindiola, L. L. Schafer and S.-L.



- You, *Organometallics*, 2016, **35**, 3255–3256.
- 47 V. P. Fadeeva, V. D. Tikhova and O. N. Nikulicheva, *J. Anal. Chem.*, 2008, **63**, 1094–1106.
- 48 S. K. Sur, *J. Magn. Reson.*, 1989, **82**, 169–173.
- 49 *The Lanthanides and Actinides*, Eds. S. T. Liddle, D. P. Mills and L. S. Natrajan, World Scientific Publishing Europe Ltd, Singapore, 2022.
- 50 P. Pykkö, *J. Phys. Chem. A*, 2015, **119**, 2326–2337.
- 51 O. Kahn, *Molecular Magnetism*, VCH-Verlag: Weinheim, 1993.
- 52 J.-L. Liu, Y.-C. Chen and M.-L. Tong, *Chem. Soc. Rev.*, 2018, **47**, 2431–2453.
- 53 G. K. Gransbury, B. L. L. Réant, A. J. Wooles, J. Emerson-King, N. F. Chilton, S. T. Liddle and D. P. Mills, *Chem. Sci.*, 2023, **14**, 621–634.
- 54 S. C. Corner, G. K. Gransbury, I. J. Vitorica-Yrezabal, G. F. S. Whitehead, N. F. Chilton and D. P. Mills, *Inorg. Chem.*, 2024, **63**, 9562–9571.
- 55 D. Reta and N. F. Chilton, *Phys. Chem. Chem. Phys.*, 2019, **21**, 23567–23575.
- 56 W. J. A. Blackmore, G. K. Gransbury, P. Evans, J. G. C. Kragoskow, D. P. Mills and N. F. Chilton, *Phys. Chem. Chem. Phys.*, 2023, **25**, 16735–16744.
- 57 A. Chiesa, F. Cugini, R. Hussain, E. Macaluso, G. Allodi, E. Garlatti, M. Giansiracusa, C. A. P. Goodwin, F. Ortu, D. Reta, J. M. Skelton, T. Guidi, P. Santini, M. Solzi, R. De Renzi, D. P. Mills, N. F. Chilton and S. Carretta, *Phys. Rev. B*, 2020, **101**, 174402.
- 58 I. Fdez. Galván, M. Vacher, A. Alavi, C. Angeli, F. Aquilante, J. Autschbach, J. J. Bao, S. I. Bokarev, N. A. Bogdanov, R. K. Carlson, L. F. Chibotaru, J. Creutzberg, N. Dattani, M. G. Delcey, S. S. Dong, A. Dreuw, L. Freitag, L. M. Frutos, L. Gagliardi, F. Gendron, A. Giussani, L. González, G. Grell, M. Guo, C. E. Hoyer, M. Johansson, S. Keller, S. Knecht, G. Kovačević, E. Källman, G. Li Manni, M. Lundberg, Y. Ma, S. Mai, J. P. Malhado, P. Å. Malmqvist, P. Marquetand, S. A. Mewes, J. Norell, M. Olivucci, M.

View Article Online
DOI: 10.1039/D4DT02713B



- Oppel, Q. M. Phung, K. Pierloot, F. Plasser, M. Reiher, A. M. Sand, I. Schapiro, P. Sharma, C. J. Stein, L. K. Sørensen, D. G. Truhlar, M. Ugandi, L. Ungur, A. Valentini, S. Vancoillie, V. Veryazov, O. Weser, T. A. Wesolowski, P. O. Widmark, S. Wouters, A. Zech, J. P. Zobel and R. Lindh, *J. Chem. Theory Comput.*, 2019, **15**, 5925–5964.
- 59 J. F. Kögel, E. Lork, M. Løkov, E. Parman, I. Leito, A. Y. Timoshkin and J. Beckmann, *Eur. J. Inorg. Chem.*, 2019, **2019**, 3612–3618.
- 60 *CrysAlis Pro*, Agilent Technologies, Yarnton, England, 2010.
- 61 G. M. Sheldrick, *Acta Crystallogr. Sect. A Found. Crystallogr.*, 2008, **64**, 112–122.
- 62 G. M. Sheldrick, *Acta Crystallogr. Sect. C Struct. Chem.*, 2015, **71**, 3–8.
- 63 O. V. Dolomanov, L. J. Bourhis, R. J. Gildea, J. A. K. Howard and H. Puschmann, *J. Appl. Crystallogr.*, 2009, **42**, 339–341.
- 64 L. J. Farrugia, *J. Appl. Crystallogr.*, 2012, **45**, 849–854.
- 65 *POV-Ray*, Persistence of Vision Raytracer Pty. Ltd., Williamstown, Australia, 2004.
- 66 B. O. Roos, V. Veryazov and P.-O. Widmark, *Theor. Chem. Acc.*, 2004, **111**, 345–351.
- 67 B. O. Roos, R. Lindh, P. Å. Malmqvist, V. Veryazov and P. O. Widmark, *J. Phys. Chem. A*, 2004, **108**, 2851–2858.
- 68 B. O. Roos, R. Lindh, P.-Å. Malmqvist, V. Veryazov and P.-O. Widmark, *J. Phys. Chem. A*, 2005, **109**, 6575–6579.
- 69 B. O. Roos, R. Lindh, P.-Å. Malmqvist, V. Veryazov, P.-O. Widmark and A. C. Borin, *J. Phys. Chem. A*, 2008, **112**, 11431–11435.
- 70 F. Aquilante, R. Lindh and T. B. Pedersen, *J. Chem. Phys.*, 2007, **127**, 114107(1–7).
- 71 L. F. Chibotaru and L. Ungur, *J. Chem. Phys.*, 2012, **137**, 064112.



Data availability

View Article Online
DOI: 10.1039/D4DT02713B

Supplementary information is available in the online version of the paper. Correspondence and requests for materials should be directed to G.K.G. and D.P.M. Crystallographic data for the structures reported in this Article have been deposited at the Cambridge Crystallographic Data Centre, under deposition numbers CCDC 2386076 (1), 2386077 (2). Copies of the data can be obtained free of charge from the CCDC via www.ccdc.cam.ac.uk/getstructures. Raw research data files supporting this publication are available from Figshare at <https://doi.org/10.6084/m9.figshare.27091723>. Apart from the data sets mentioned, all other data supporting the findings of this study are available within the Article and Supplementary information.

