

Nanoscale

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: K. Mutoh, S. Kawakita, T. Yahagi and T. Nakashima, *Nanoscale*, 2024, DOI: 10.1039/D4NR03810J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

“Sergeants-and-soldiers” principle in the synthesis of intrinsically chiral Au₁₃ clustersKatsuya Mutoh,^a Sonomi Kawakita,^a Teppei Yahagi^a and Takuya Nakashima^{*a}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Surface ligand modification on atomically precise metal clusters is one of the important strategies not only to stabilize monodisperse clusters but also to derive unique optical and electronic properties. The chiral coordination of surface ligands on clusters controls the global chirality in clusters giving rise to unambiguous optical activity including circular dichroism (CD) and circularly polarized luminescence (CPL). Stereoselective synthesis of intrinsically chiral clusters has been achieved by the use of chiral ligands stabilizing one-handed cluster selectively. Herein, we investigate the effect of chiral ligand coordination on the deracemization of intrinsically chiral Au₁₃ superatom cluster. The mixture of achiral bis(diphenylphosphino)ethane (DPPE) and chiral (*R,R*)-1,2-bis[(2-methoxyphenyl)phenylphosphino]ethane (*R*-DIPAMP) led to the formation of the mixture of [Au₁₃(*R*-DIPAMP)_{*x*}(DPPE)_{5-*x*}Cl₂]³⁺ clusters with varied *x*-values (*x* = 0–5). Reverse phase HPLC successfully fractionalized the mixture into solutions composed of single component Au₁₃ cluster depending on the *x*-values. The separated Au₁₃ clusters afforded the similar optical activity to that of [Au₁₃(*R*-DIPAMP)₅Cl₂]³⁺ in the CD study regardless of *x*-values (*x* = 1–4). The DFT calculation supports that the coordination of single DIPAMP ligand is enough to bias the twisting direction in the Au₁₃ superatom with dictating the torsional orientation of other four DPPE ligands. The emergence of “sergeants-and-soldiers principle”, wherein the small number of chiral ligands determine the chiral orientation of other achiral ligands, is thus demonstrated in the synthesis of intrinsically chiral Au₁₃ clusters.

Introduction

Chiral amplification phenomena have received significant attention in several research areas in chemical sciences, not only for the development of asymmetric catalysts and nonlinear optical materials,^{1–6} but also for seeking the origin of homochirality evolution in nature.^{7–10} Effective communications among chiral/achiral building units in helical polymers and supramolecular assemblies have been investigated in detail to clarify the specific stereochemical interaction for the chiral amplification.^{11,12} “Sergeants-and-soldiers principle” is one of the representative chiral amplification expressions.^{13,14} An intrinsically chiral system, such as a helical polymer, built by achiral monomers usually consists of the racemic mixture of left- and right-hand ones. The introduction of a small amount of chiral monomers with a similar structure to achiral one effectively deracemizes the system by selectively stabilizing one-handed helical polymer. The achiral monomer units obey the orientation given by the chiral ones aligning in a one-hand direction together in a helical polymer. Chirality could thus be significantly amplified by a slight chiral input as a result of strong cooperative interactions among monomers and entire polymer, producing chiral polymers with a large helical sense excess.

Ligand-protected metal clusters have been extensively investigated in recent years owing to their unique electronic property derived from unambiguous atomically precise structure revealed by single crystal X-ray diffraction (SCXRD) study.^{15–20} Chiral metal clusters have constituted an important class of chiral nanomaterials due to their fascinating chiroptical property.^{21–25} Some clusters possess intrinsic chirality in their asymmetric structures and their deracemization has been achieved by employing chiral ligands,²⁶ chiral HPLC separation²⁷ and spontaneous resolution.^{28,29} Recent works have focused on the dynamic control of chirality in intrinsically chiral metal clusters through ligand engineering.^{30–32}

The icosahedral Au₁₃ structure is one of the commonly observed superatomic fundamental unit in which 12 gold atoms occupy the vertices of icosahedron and one remaining gold is situated in the center. While the stable icosahedral Au₁₃ superatom alone is achiral and highly symmetric, the intrinsic chirality, or chiral distortion can be induced mostly by the coordination of bidentate ligands such as bis(diphenylphosphino)ethane (DPPE, Fig. 1).^{33,34} The detailed investigation in the crystal structure of [Au₁₃(DPPE)₅Cl₂]³⁺ cluster demonstrated the distortion between the two gold pentagons (blue and red in Fig. 1 bottom) arranging five bridging DPPE ligands in a helical propeller pattern, indicating the existence of intrinsic chirality in the Au₁₃ superatom.^{34,35} The deracemization of Au₁₃-based cluster has been demonstrated by the enantioselective synthesis with chiral ligands,^{36–40} spontaneous resolution⁴¹ and enantioseparation with a chiral column.⁴² It is of interest to note that the heteroatom doping^{41,43}

^a Department of Chemistry, Graduate School of Science, Osaka Metropolitan University, 3-3-138 Sugimoto, Sumiyoshi, Osaka 558-8585, Japan.

Supplementary Information available: Experimental details and supplemental simulation and spectral data. See DOI: 10.1039/x0xx00000x



in the center of Au₁₃ with Ir³⁺ successfully leads to the spontaneous resolution of [IrAu₁₂(DPPE)₅Cl₂]⁺ cluster suppressing the rapid racemization upon crystallization. Given the inherent energy barrier for the racemization of [Au₁₃(DPPE)₅Cl₂]³⁺ cluster is not so small, a slight chiral input may enhance the activation energy biasing the formation of Au₁₃ cluster with a unidirectional twist. In this study, we investigate the effect of the coordination of chiral ligand on the chirality induction in the Au₁₃ superatom cluster. We prepared the Au₁₃ clusters by using a mixed ligand system of achiral DPPE and chiral (*R,R*)-1,2-bis[(2-methoxyphenyl)phenylphosphino]ethane (*R*-DIPAMP)³⁶ with changing the DPPE/*R*-DIPAMP (A/C) ratio (Fig. 1). The as-prepared samples displayed optical activity depending on the A/C ratio, while they were composed of mixture of Au₁₃ clusters with different ligand compositions ([Au₁₃(*R*-DIPAMP)_{*x*}(DPPE)_{5-*x*}Cl₂]³⁺, *x* = 0–5). The as-prepared samples were therefore separated by means of reverse phase HPLC depending on the *x*-value. Circular dichroism (CD) measurement for the fractionalized eluents clearly suggested the non-additive effect of chiral ligand on the chirality induction, demonstrating the “sergeants-and-soldiers principle” in the synthesis of metal clusters for the first time. The entire twist in the Au₁₃ superatom is dictated by single DIPAMP ligand in [Au₁₃(*R*-DIPAMP)₁(DPPE)₄Cl₂]³⁺ cluster. The twist in Au₁₃ propagates to the helical torsion and arrangement of other four DPPE ligands.

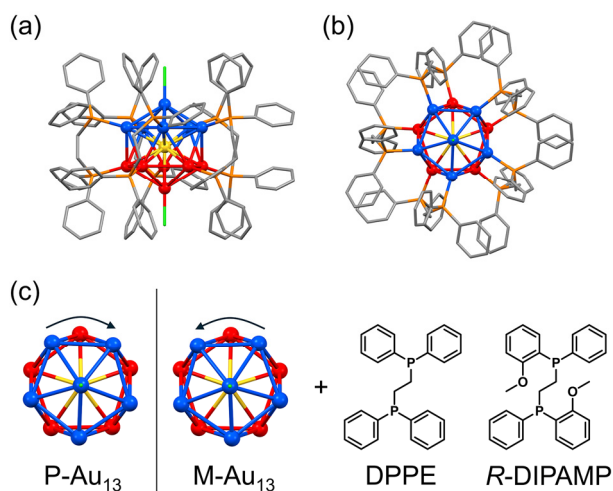


Fig. 1 Structural models of (a,b) [Au₁₃(DPPE)₅Cl₂]³⁺ cluster, and (c) the top views of right- and left-handed helically distorted Au₁₃ core and chemical structures of achiral (DPPE) and chiral (*R*-DIPAMP) ligands discussed in this study.

Results and discussion

The DFT calculations for Au₁₃ clusters protected by DPPE and *R*-DIPAMP ligands ([Au₁₃(*R*-DIPAMP)_{*x*}(DPPE)_{5-*x*}Cl₂]³⁺, called **R0–R5**: *x* = 0–5, respectively) were first carried out to predict the geometries with left- and right-hand twists and their stabilities. Fig. 2 shows the energy diagrams of the *P*- and *M*-[Au₁₃(*R*-DIPAMP)_{*x*}(DPPE)_{5-*x*}Cl₂]³⁺ clusters for the right- and left-hand twisted structures (Fig. 1), respectively. The chiral arrangement of the ligands results in the chiroptical properties originating

from the helical right- and left-hand structures (global chirality) of Au₁₃ clusters.^{34,36} It should be noted the calculation based on [Au₁₃(PMe₂Ph)₁₀Cl₂]³⁺ structure resulted in an achiral Au₁₃ superatom core ($\theta_2/\theta_1 = 1$, Fig. 2).³⁴ The chiral distortion is therefore introduced by the bridging nature of DPPE coordination with a certain P–P distance. When the Au₁₃ superatom core is protected by DPPE ligand, the energy difference between *P*- and *M*-Au₁₃ clusters is zero because they are enantiomers to each other (Fig. 2). The enantioseparation of them with a chiral column was reported to be unsuccessful probably due to the rapid racemization.³⁵ In contrast, the protection by *R*-DIPAMP ligands gives diastereomeric isomers with different energies between *P*- and *M*-clusters. The DFT calculations for **R0–R5** reveal that *M*-type conformation is destabilized by increasing the number of chiral ligands. While **R2** and **R3** should have two structural isomers in terms of ligand sequence for each, those isomers were estimated to have negligible energy difference (~0.2 kJ/mol, Fig. S1). The ratio of averaged torsion angle (θ_2/θ_1) between the two Au-pentagons (Fig. 2a) slightly increases in the order of **R1–R5** (Table 1), whereas the differences are negligible (< 2%) compared to the differences in the energy. The optimized structures for *P*- and *M*-conformations of **R5** (Fig. 2b) show the distinctive different arrangement of methoxy groups in *R*-DIPAMPs on the exterior shell. The methoxy groups are present in the latitudinal direction of the clusters in *P*-Au₁₃, whereas, in *M*-Au₁₃, they are located in the equatorial plane of the clusters, leading to a more crowded stereostructure. This conformational difference in *R*-DIPAMP can be considered as the primary origin of the pronounced energy differences between *P*-Au₁₃ and *M*-Au₁₃.

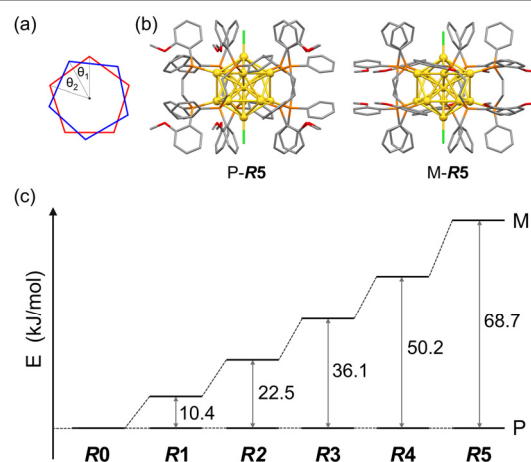


Fig. 2 (a) The torsion angles between the two equatorial Au₅ pentagons in Fig. 1c. (b) The optimized structures of *P*- and *M*-[Au₁₃(*R*-DIPAMP)₅Cl₂]³⁺ clusters by the DFT calculation. (c) The energy differences between the *P*- and *M*-Au₁₃ clusters for **R0–R5**.

Table 1. The equilibrium constants for the twist inversion between *P*- and *M*-**R1–R5** ($K = [M]/[P-R1-R5]$) and the averaged torsion angles in *P*-**R1–R5**, estimated by the DFT calculations.

| | R1 | R2 | R3 | R4 | R5 |
|---------------------|-----------------------|-----------------------|-----------------------|-----------------------|------------------------|
| <i>K</i> | 1.48×10^{-2} | 1.15×10^{-4} | 4.69×10^{-7} | 1.56×10^{-9} | 9.12×10^{-13} |
| θ_2/θ_1 | 1.200 | 1.207 | 1.212 | 1.217 | 1.220 |



The DFT-optimized structures for P -Au₁₃ and M -Au₁₃ also disclosed the characteristic conformational differences in the diphosphine ligands. The diphosphine ligands coordinate on the surface by tilting to the right (P -**R1**) or left (M -**R1**) with respect to the central axis of icosahedron (Cl–Cl axis), determining the global chirality of Au₁₃ clusters. Fig. 3 shows the Newman projections along the ethylene C–C axis for DPPE and R -DIPAMP ligands in **R1**. The entire ethylene unit adopts an eclipsed conformation, rather than a staggered one. The dihedral angles between the two H–C bonds (φ , Fig. 3) are calculated to be ca. +4° (clockwise) for DPPE and R -DIPAMP in the stable P -**R1**, indicating DPPE and R -DIPAMP coordinate to the Au₁₃ core with similar geometries regardless of the presence of methoxy groups in P -**R1**. In contrast, the difference in the conformation of ethylene unit was observed in M -**R1**. While the ethylene units of DPPE in M -**R1** have a mirror-image form of those in P -**R1** (anticlockwise, $\varphi \sim -4^\circ$), that of R -DIPAMP keeps the clockwise direction ($\varphi \sim +5.6^\circ$). Similar tendency of the coordination of R -DIPAMP is also confirmed in the optimized structure of P - and M -**R5**. This result suggests the R -DIPAMP ligand prefers clockwise conformation (in terms of φ) against the global chirality of M -Au₁₃. Thus, single R -DIPAMP ligand plays the role of “sergeant” transferring its chiral coordination structure to other four DPPE on the surface of Au₁₃ in P -**R1** while its role is invalid in M -**R1**.

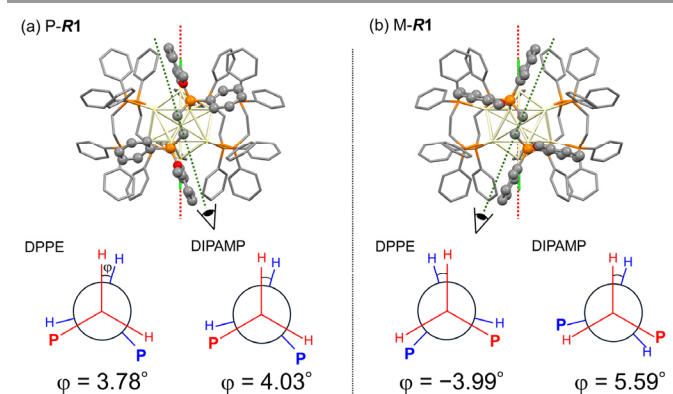


Fig. 3 The optimized structures and Newman projections along the ethylene C–C axis for DPPE and R -DIPAMP ligands of (a) P -**R1** and (b) M -**R1**. R -DIPAMP ligands are highlighted with a ball and stick model. The dihedral angle for DPPE ligand was calculated as an averaged value of four DPPE ligands.

Given that the P - and M -Au₁₃ isomers are assumed to be in equilibrium, the equilibrium constants (K) for **R1**–**R5** at 298 K can be estimated approximating the calculated energy differences as ΔG (Table 1). The population ratio of unstable M -**R1** at 298 K was calculated to be 1.46% and those for the other **R2**–**R5** were approximately zero. While the activation barrier of twist inversion could not be calculated easily, the estimated energy difference suggests that the formation of P -Au₁₃ cluster can be significantly biased by the introduction of just one R -DIPAMP ligand.

The synthesis of a series of **R0**–**R5** clusters was performed through a previously reported method with changing the ratio of the gold complexes, Au₂(DPPE)Cl₂/Au₂(R -DIPAMP)Cl₂, being Achiral/Chiral (A/C) ratios = 5/0, 4/1, 3/2, 2/3, 1/4 and 0/5, in

the reduction step with NaBH₄.^{33,36} The reduction of the mixed solution of gold complexes, followed by the acid (TFA) etching yielded the mixture of Au₁₃ clusters at room temperature. The as-prepared samples were treated by a reverse phase column chromatography (Wakosil 100C18, Wako-Fuji Film) using methanol solution containing 0.5vol% trifluoroacetic acid (TFA) and 0.5vol% diethylamine (DEA) as an eluent to remove larger agglomerates. The treated samples afforded almost identical absorption spectra indicating the successful formation of Au₁₃ clusters regardless of A/C ratio (Fig. S2). Meanwhile, they exhibited optical activity dependent on the A/C ratio for the preparation condition. The A/C = 5/0 and 0/5 samples exclusively contain **R0** and **R5** with no and the largest optical activity, respectively, while other ratios should give the mixtures of **R0**–**R5**. To compare the optical activity, CD spectra were translated to g -spectra ($g = \Delta\epsilon/\epsilon$) with the equation of $g = \text{CD}[\text{mdeg}]/(32980 \cdot \text{Abs})$ (Fig. 4a). The plot of anisotropy value (g -value) at 550 nm clearly demonstrated the dependence of optical activity on the A/C ratio for the preparative condition. The non-linear relationship between the g -value and C/(A+C) ratio suggested the emergence of chiral amplification or the non-additive effect of chiral ligand on the entire optical activity of Au₁₃ clusters. However, the unseparated samples contain **R0**–**R5** clusters with a certain distribution. The ESI-MS spectrum for the A/C = 1/4 sample indeed demonstrated that the solution contains all possible compositions (Fig. 5). Furthermore, the result of DFT calculation motivated us to isolate **R0**–**R5** species to investigate the effect of single chiral ligand coordination on the optical activity of Au₁₃ cluster.

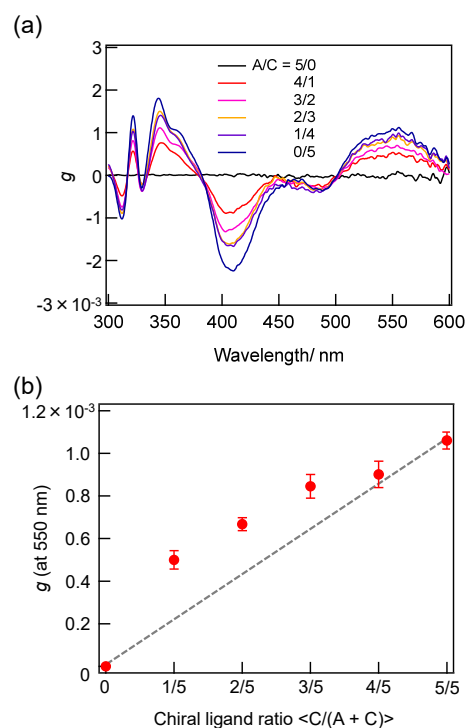


Fig. 4 (a) g -Spectra of the sample prepared with A/C = 5/0–0/5 ratios and the plot of g -value at 550 nm as a function of C/(A+C) ratio in the synthetic condition.



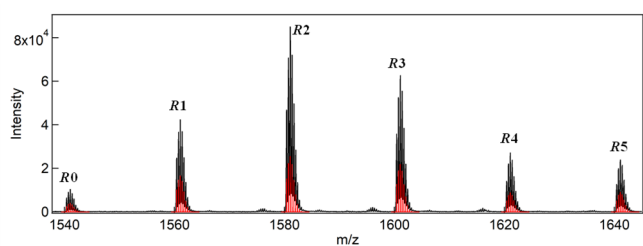


Fig. 5 ESI-MS spectrum of the sample prepared with A/C = 1/4 ratio together with simulated isotope peak patterns (red bars) for **R0–R5**.

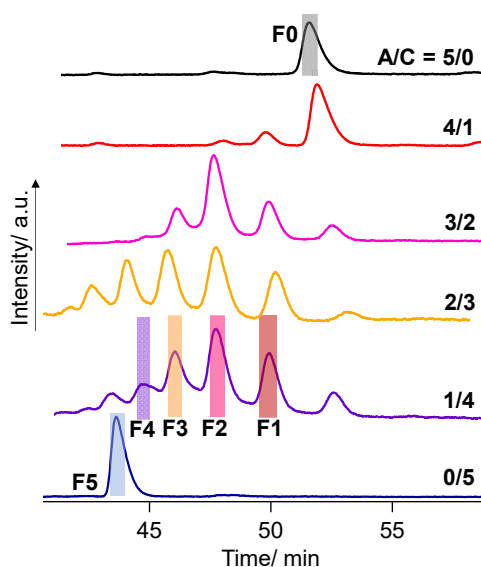


Fig. 6 HPLC chromatograms for the mixture solutions of $[\text{Au}_{13}(\text{R-DIPAMP})_x(\text{DPPE})_{5-x}\text{Cl}_2]^{3+}$ clusters synthesized with different A/C ratios.

Negishi and coworkers demonstrated the precise HPLC separation of nonionic $\text{PdAu}_{24}(\text{SR})_{18-n}(\text{SR}')_n$ clusters by gradient elution using a reverse phase column.^{44,45} On the other hand, a tricationic $[\text{Au}_{13}(\text{bisNHC})_5\text{Cl}_2]^{3+}$ (NHC: *N*-heterocyclic carbene) cluster was subjected to a chiral column using methanol as an eluent with TFA/DEA additives.⁴² In the present study, a preparative reverse phase column (InertSustain C30, GL Science) was employed and a gradient elution condition was considered. Finally, the successful separation was achieved by using the mixture of methanol containing TFA (0.2 vol%) and DEA (0.2 vol%) and water (see the ESI for details). Fig. 6 shows the result of the HPLC separation. The A/C = 5/0 sample gave a single peak at 52–53 min collected as **F0** (fraction 0, Fig. 6), which was confirmed as **R0** cluster with ESI-MS (Fig. S3). Meanwhile, the A/C = 0/5 sample afforded a peak at the shorter retention time assigned to **R5**, which was collected as **F5**. The retention times in the HPLC charts for A/C = 4/1–1/4 samples were adjusted by using **R0** peaks as a standard. The A/C = 1/4 sample, of which ESI-MS data demonstrated the presence of all species **R0–R5** (Fig. 5), displayed 4 more peaks in-between the peaks assigned to **R0** and **R5**, indicating the separation of all the species. To confirm the separation of **R1–R4**, the eluate was fractionalized into **F1–F4** depending on the peak positions (Fig. 6). The ESI-MS measurement demonstrated **F1–F4** exclusively contain **R1–R4**, respectively (Fig. S3). While two isomers with

different ligand sequences for **R2** and **R3** could not be discriminated, successful separation was achieved in terms of ligand compositions.

The peak intensity ratio in the ESI-MS spectrum for the A/C = 1/4 sample (Fig. 5) well accorded with that in the elution profile (Fig. 6) corresponding to the abundance ratio of **R0–R5**. However, this distribution was far different from theoretical one assuming the random incorporation of ligand based on the given A/C ratio (Fig. S4). The A/C = 1/4 ratio should give **R4** and **R5** as the major and second major products with 45 and 30% probabilities and there is a negligible chance for the **R0** formation. The experimental result suggests the less reactivity of DIPAMP ligand for the coordination on Au_{13} cluster than DPPE. The A/C = 4/1 condition highlights the less reactivity of DIPAMP by the formation of **R0** as the major product with faint formation of **R1** and **R2** (Fig. 6). The two-step reaction mechanism for the efficient synthesis of Au_{13} clusters has been discussed by Shichibu and Konishi.³³ The first reduction process of $\text{Au}_2(\text{diphosphine})\text{Cl}_2$ gives a mixture of polydispersed gold clusters with various compositions. These polydispersed clusters converged to $[\text{Au}_{13}(\text{diphosphine})_5\text{Cl}_2]^{3+}$ upon the addition of HCl aq. Most of kinetically formed metastable clusters were subjected to the etching being consumed as precursors forming the most stable one. While both the enantiomers of $[\text{Au}_{13}(\text{DPPE})_5\text{Cl}_2]^{3+}$ have the identical stability, the *M*- Au_{13} clusters containing *R*-DIPAMP ligands should have the less stability than *P*-ones (Fig. 2), being subject to the etching. Furthermore, achiral DPPE is considered to preferentially participate in the coordination on the preformed *M*- Au_{13} superatom over *R*-DIPAMP with adopting the torsional conformation appropriate to the left-hand twisted cluster (Fig. 3). The formation of **R0** thus preferentially proceeds in the condition of small chiral ligand content.

When the content of chiral ligand changed from A/C = 4/1 to 3/2, the major product drastically changed from **R0** to **R2**. While the incorporation of *R*-DIPAMP in the Au_{13} cluster formation seems less probable than DPPE, the yield of **R2** is higher than **R1**. The coordination of the first *R*-DIPAMP ligand might facilitate the introduction of the second *R*-DIPAMP in a similar manner to the emergence of allosteric effect in the chiral guest incorporation by prochiral double decker porphyrins.^{46,47} More specifically, if an Au_{13} superatom with *P*-type twist induced by the single *R*-DIPAMP coordination had a vacant coordination site, *R*-DIPAMP with a geometry preorganized (Fig. 3) for the coordination on the *P*-type cluster could be more feasible than DPPE to fill that site. However, the inherent less reactivity with sterically less flexible nature compared to DPPE may result in the less formation probabilities of **R3**, **R4** and **R5** for the conditions of A/C = 3/2, 2/3 and 1/4. Another possibility includes the selective consumption of chiral DIPAMP ligand for the formation of cluster species other than Au_{13} , resulting in the decrease of practical chiral ligand ratio to form Au_{13} clusters.

The absorption and CD measurements were carried out for the fractions of **F1–F5**. As described above, the ESI-MS measurement for **F1–F5** demonstrated the successful isolation of Au_{13} clusters into a single composition of **R1–R5**, respectively. At the very least, no trace of **R0** was contained in those fractions



because of its well-separated peak position in the HPLC charts (Fig. 6). All **F1–F5** fractions containing **R1–R5**, respectively, exhibited almost identical absorption and CD profiles (Figs. S5,6). Furthermore, the *g*-spectra of **R1–R4** showed similar profiles with that of **R5** with very similar *g*-values at 550 nm (Fig. 7). The contamination of **R0** in the solutions should result in the lower optical activity of the unseparated samples than that of **R5** (Fig. 4). The result thus confirmed that the single coordination of *R*-DIPAMP ligand is enough to induce the unidirectional helical twist in the Au₁₃ superatom as predicted by the DFT study. Meanwhile, other four achiral DPPE ligands adopt the helical torsional conformation following the one-hand twist in the Au₁₃ superatom (Fig. 3).

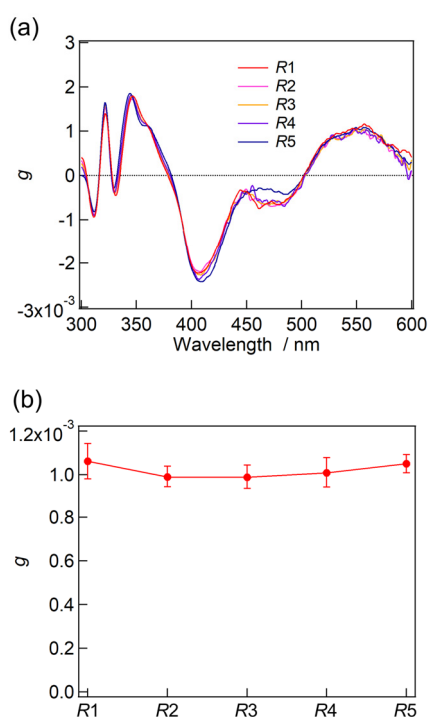


Fig. 7 (a) *g*-Spectra of **R1–R5** separated by the HPLC. (b) The plot of *g*-value at 550 nm for **R1–R5**.

Bürgi and coworkers have extensively utilized the HPLC technique to monitor the ligand exchange reaction of the intrinsically chiral Au₃₈(SR)₂₄ clusters and to isolate the ligand-exchanged products.^{30,48–51} The intrinsically chiral Au₃₈ enantiomer demonstrated the diastereoselective ligand exchange with chiral ligands, suppression of racemization by the introduction of a chiral ligand and modulation of optical activity by the ligand exchange. In the present study, the HPLC separation of chiral-achiral mixed-ligand-protected clusters disclosed the clear composition-chiroptical property relationship with a one-to-one correspondence.

The CD spectra of **R1–R5** were well reproduced by the DFT calculations (Fig. S7). While the compositions in the ligand shell are different, **R1–R5** gave very similar CD spectra which also supports the first Cotton effect originates from the internal chirality in the helical superatom core (Au₁₃). The average torsion angles calculated from the optimized structures of **R1–R5** slightly increased by increasing the number of *R*-DIPAMP as

discussed above (Table 1). Although the nearly similar torsion angles of **R1–R5** may have minimal effect on the intensity of the CD signal, these experimental results support the argument that the chiroptical properties arise from the differences in the angle between the two Au-pentagons.³⁴

Conclusion

The effect of a chiral ligand on the chirality induction in [Au₁₃(diphosphine)₅Cl₂]³⁺ clusters have been investigated. The DFT calculation indicated the coordination of single chiral ligand DIPAMP could greatly stabilize the one-handed twist structure in an icosahedral Au₁₃ superatom core with 98.5% occupancy over the opposite-twist regardless of the presence of other four achiral DPPE ligands. While the synthesis in a mixed ligand system of DPPE and *R*-DIPAMP led to the formation of the mixture of [Au₁₃(*R*-DIPAMP)_{*x*}(DPPE)_{5-*x*}Cl₂]³⁺ clusters, they have been successfully separated into individual composition in terms of *x*-values (*x* = 0–5) by reverse-phase HPLC. The fractionalized HPLC eluents including **R1–R5**, free from [Au₁₃(DPPE)₅Cl₂]³⁺ (**R0**), afforded the identical optical activity clearly supporting the result of DFT calculation. Thus the non-additive effect of chiral ligand on the chirality induction in the Au₁₃ cluster has been demonstrated in theoretical and experimental manners. In other words, the chirality of DIPAMP ligand could be successfully communicated into a chiral conformation of DPPE.⁵² The HPLC separation technique^{53,54} should provide the opportunity of clear role division between different ligands for mixed-ligand clusters, further expanding the usage of ligands as toolboxes in functional cluster.⁵⁵

Author contributions

K. M.: investigation, funding acquisition, visualization, writing–original draft, writing–review & editing. S. K.: investigation, T. Y.: investigation, T. N.: conceptualization, investigation, funding acquisition, resources, supervision, writing–review & editing.

Conflicts of interest

There are no conflicts to declare.

Data availability

The data supporting this article have been included as part of the ESI.†

Acknowledgements

This work was financially supported by JST CREST (Grant Number: JPMJCR20B2), JSPS KAKENHI grant numbers JP22H05134 (TN) for Transformative Research (A) “Revolution of Chiral Materials Science using Helical Light”, JP23H01938 (TN) and JP24K01458 (KM) for Scientific Research (B), and by Tokyo Ohka Foundation for The Promotion of Science and Technology for K. M. A part of this work was conducted in



Institute for Molecular Science, supported by “Advanced Research Infrastructure for Materials and Nanotechnology in Japan (ARIM)” of the Ministry of Education, Culture, Sports, Science and Technology (MEXT). Proposal Number JPMXP1224MS0001.

References

- R. Noyori and M. Kitamura, *Angew. Chem., Int. Ed.*, 1991, **30**, 49–69.
- H. B. Kagan, *Synlett*, 2001, **2001**, 888–899.
- T. Satyanarayana, S. Abraham and H. B. Kagan, *Angew. Chem., Int. Ed.*, 2009, **48**, 456–494.
- S. Sioncke, T. Verbiest and A. Persoons, *Mater. Sci Eng. R Rep.*, 2003, **42**, 115–155.
- X. Yan, Q. Wang, X. Chen and Y.-B. Jiang, *Adv. Mater.*, 2020, **32**, 1905667.
- M. Rok, A. Miniewicz, M. Zdończyk, B. Zarychta, J. W. Mikurenda, S. Bartkiewicz, M. Wiśniewska-Belej, J. Cybińska and A. Piecha-Bisiorek, *J. Phys. Chem. Lett.*, 2024, **15**, 5276–5287.
- J. S. Siegel, *Chirality*, 1998, **10**, 24–27.
- D. G. Blackmond and M. Klussmann, *Chem. Commun.*, 2007, 3990–3996.
- K. K. Konstantinov and A. F. Konstantinova, *Orig. Life Evol. Biosph.*, 2018, **48**, 93–122.
- N. Suzuki and Y. Itabashi, *Symmetry*, 2019, **11**, 966.
- A. R. A. Palmans and E. W. Meijer, *Angew. Chem., Int. Ed.*, 2007, **46**, 8948–8968.
- E. Yashima, N. Ousaka, D. Taura, K. Shimomura, T. Ikai and K. Maeda, *Chem. Rev.*, 2016, **116**, 13752–13990.
- M. M. Green and P. Ridy, *J. Am. Chem. Soc.*, 1989, **111**, 6452–6454.
- A. R. A. Palmans, J. A. J. M. Vekemans E. E. Havinga and E. W. Meijer, *Angew. Chem. Int. Ed.*, 1997, **36**, 2648–2651.
- R. Jin, C. Zeng, M. Zhou and Y. Chen, *Chem. Rev.*, 2016, **116**, 10346–10413.
- Y. Du, H. Sheng, D. Astruc and M. Zhu, *Chem. Rev.*, 2020, **120**, 526–622.
- S. Takano and T. Tsukuda, *J. Am. Chem. Soc.*, 2021, **143**, 1683–1698.
- Y. Saito, C. Murata, M. Sugiuchi, Y. Shichibu and K. Konishi, *Coord. Chem. Rev.*, 2022, **470**, 214713.
- W. Du, S. Jin, L. Xiong, M. Chen, J. Zhang, X. Zou, Y. Pei, S. Wang and M. Zhu, *J. Am. Chem. Soc.*, 2017, **139**, 1618–1624.
- S. Chen, S. Wang, J. Zhong, Y. Song, J. Zhang, H. Sheng, Y. Pei and M. Zhu, *Angew. Chem. Int. Ed.*, 2015, **54**, 3145–3149.
- Y. Li, T. Higaki, X. Du and R. Jin, *Adv. Mater.*, 2020, **32**, e1905488.
- Y. Zhu, J. Guo, X. Qiu, S. Zhao and Z. Tang, *Acc. Mater. Res.*, 2020, **2**, 21–35.
- Y. Shichibu and K. Konishi, *ChemNanoMat* 2022, **8**, e202200194.
- J.-H. Huang, X.-Y. Dong, Y.-J. Wang and S.-Q. Zang, *Coord. Chem. Rev.*, 2022, **470**, 214729.
- K. K. Ramankutty, *Nanoscale*, 2024, **16**, 11914–11927.
- J. Kumar, T. Kawai, T. Nakashima, *Chem. Commun.*, 2017, **53**, 1269–1272.
- I. Dolamic, S. Knoppe, A. Dass and T. Bürgi, *Nat. Commun.*, 2012, **3**, 798.
- J. H. Huang, Z. Y. Wang, S.-Q. Zang and T. C. W. Mak, *ACS Cent. Sci.*, 2020, **6**, 1971–1976.
- S. Chen, W. Du, C. Qin, D. Liu, L. Tang, Y. Liu, S. Wang and M. Zhu, *Angew. Chem. Int. Ed.*, 2020, **59**, 7542–7547.
- Y. Wang, B. Nieto-Ortega and T. Bürgi, *Nat. Commun.*, 2020, **11**, 4562.
- H. Yoshida, M. Kuzuhara, R. Tanibe, T. Kawai and T. Nakashima, *J. Phys. Chem. C*, 2021, **125**, 27009–27015.
- T. Nakashima, R. Tanibe, H. Yoshida, M. Ehara, M. Kuzuhara and T. Nakashima, *Angew. Chem. Int. Ed.*, 2022, **61**, e202208273.
- Y. Shichibu and K. Konishi, *Small*, 2010 **6**, 1216–1220.
- Y. Shichibu, Y. Ogawa, M. Sugiuchi and K. Konishi, *Nanoscale Adv.*, 2021, **3**, 1005–1011.
- J. Zhang, Y. Zhou, K. Zheng, H. Abroshan, D. R. Kauffman, J. Sun and G. Li, *Nano Res.*, 2018, **11**, 5787–5798.
- Y. Yang, Q. Zhang, Z.-J. Guan, Z.-A. Nan, J.-Q. Wang, T. Jia and W.-W. Zhan, *Inorg. Chem.*, 2019, **58**, 3670–3675.
- P. Luo, X.-J. Zhai, S. Bai, Y.-B. Si, X.-Y. Dong, Y.-F. Han, S.-Q. Zang, *Angew. Chem. Int. Ed.*, 2023, **62**, e202219017.
- H. Hirai, T. Nakashima, S. Takano, Y. Shichibu, K. Konishi, T. Kawai and T. Tsukuda, *J. Mater. Chem.*, 2023, **11**, 3095–3100.
- Y. Sato, M. Mitani and H. Yao, *J. Phys. Chem. C*, 2020, **124**, 25547–25556.
- E. L. Albright, S. Malola, S. I. Jacob, H. Yi, S. Takano, K. Mimura, T. Tsukuda, H. Häkkinen, M. Nambo and C. M. Crudden, *Chem. Mater.*, 2024, **36**, 1279–1289.
- H. Hirai, S. Takano, T. Nakamura and T. Tsukuda, *Inorg. Chem.*, 2020, **59**, 17889–17895.
- H. Yi, K. M. Osten, T. I. Levchenko, A. J. Veinot, Y. Aramaki, T. Ooi, M. Nambo and C. M. Crudden, *Chem. Sci.*, 2021, **12**, 10436–10440.
- H. Hirai, S. Takano, T. Nakashima, T. Iwasa, T. Taketsugu and T. Tsukuda, *Angew. Chem. Int. Ed.*, 2022, **61**, e202207290.
- Y. Niihori, M. Matsuzaki, T. Pradeep and Y. Negishi, *J. Am. Chem. Soc.*, 2013, **135**, 4946–4949.
- Y. Niihori, M. Matsuzaki, C. Uchida and Y. Negishi, *Nanoscale*, 2014, **6**, 7889–7896.
- S. Shinkai, M. Ikeda, A. Sugasaki and M. Takeuchi, *Acc. Chem. Res.*, 2001, **34**, 494–503.
- T. Ikeda, K. Sada, S. Shinkai and M. Takeuchi, *Supramol. Chem.*, 2011, **23**, 59–64.
- S. Knoppe, R. Azoulay, A. Dass and T. Bürgi, *J. Am. Chem. Soc.*, 2012, **134**, 20302–20305.
- S. Knoppe, S. Michalet and T. Bürgi, *J. Phys. Chem. C*, 2013, **117**, 15354–15361.
- A. Baghdasaryan, K. Martin, L. M. L. Daku, M. M. Talamo, N. Avarvari and T. Bürgi, *Nanoscale*, 2020, **12**, 18160–18170.
- Y. Wang, Ee. Makkonen, X. Chen and T. Bürgi, *Chem. Sci.*, 2021, **12**, 9413–9419.
- I. Dolamic, B. Varnholt and T. Bürgi, *Nat. Commun.*, 2015, **6**, 7117.
- Y. Niihori, C. Uchida, W. Kurashige and Y. Negishi, *Phys. Chem. Chem. Phys.*, 2016, **18**, 4251–4265.
- Niihori, D. Shima, K. Yoshida, K. Hamada, L. V. Nair, S. Hossain, W. Kurashige and Y. Negishi, *Nanoscale*, 2018, **10**, 1641–1649.
- K. Konishi, M. Iwasaki, M. Sugiuchi and Y. Shichibu, *J. Phys. Chem. Lett.*, 2016, **7**, 4267–4274.



Data availability statements

View Article Online
DOI: 10.1039/D4NR03810J

The data supporting this article have been included as part of the ESI.

