

Reaction Chemistry & Engineering

Linking fundamental chemistry and engineering to create scalable, efficient processes

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: H. Wang and R. N. Shiju, *React. Chem. Eng.*, 2024, DOI: 10.1039/D4RE00384E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

REVIEW

A mini review on aromatization of n-alkanes

Hongqi Wang^a, and N. Raveendran Shiju^{*a}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The catalytic aromatization of n-alkanes is an important process in the chemical industry, especially for the production of value-added aromatics from the abundant and unreactive small alkanes. This mini review summarizes the recent progress on the development of catalysts for the aromatization of n-alkanes and the mechanistic studies. The effects of various catalysts (e.g. shape selective zeolites and noble metals) and reactant compositions on the aromatization performance are discussed to shed light on the rational design of novel heterogeneous catalysts.

1. Introduction

The catalytic aromatization of n-alkanes is an important process to upgrade the low-cost feedstock into value-added aromatic chemicals such as benzene, toluene and xylene (BTX) and to improve the octane number of gasoline.¹⁻³ The abundant alkanes could be acquired from the traditional fossil fuels (e.g. crude oil and natural gas especially the shale gas), as well as from recycled sources (e.g. chemical degradation of plastics wastes). The catalytic aromatization is one of the most promising methods to valorize these alkanes.⁴ The produced aromatic compounds especially BTX are crucial building blocks in chemical industry and currently BTX is mainly produced from the naphtha reforming.⁵ Another advantage of alkane aromatization, especially for utilizing methane and ethane, is the easier transportation of the liquid-form aromatic compounds than the feedstock gases.

The alkane aromatization is generally composed of complicated multi-step reactions in parallel or series over a catalyst, including cracking, dehydrogenation, isomerization, oligomerization and cyclization reactions.⁶ Various parameters, including reactant composition, catalyst and operating parameters (e.g. temperature and pressure), will affect the reaction routes and thus the product distribution and yield. Among these factors, the reactant and catalyst are of paramount importance and would be discussed in this review. Among the reactants, the aromatization of CH₄ and C₂H₆ is still in the laboratory developmental stage. However, for the C₃₊ alkanes, some aromatization processes are commercial, such as Cyclar (UOP and BP) and M2-reforming (Mobil). The Zeolite Socony Mobil-5 (ZSM-5) zeolite and its various modifications

(e.g. gallium modified) are effectively utilized in these processes due to their shape selectivity and the ability to inhibit coke formation.⁷ However, almost all the aromatization processes are limited by the low yield because of side reactions and catalyst deactivation due to coke formation.⁸ Various new catalysts are developed to overcome these bottleneck problems by improving the activity, selectivity and long-term stability.

While there are some reviews focusing on certain alkanes (e.g. naphtha³) or catalysts (e.g. ZSM-5⁹), a generalized mechanism is necessary to understand the interaction between alkane and catalyst. This review summarizes the recent advances of the catalyst development and discusses the effects of the reactant composition during the catalytic aromatization of linear alkanes, aiming to provide readers a comprehensive insight into the generalized mechanism of alkane aromatization (especially the importance of unsaturated intermediate pool) and to give a perspective about future direction. Firstly, the zeolite catalysts together with its modifications, noble metals and other types of catalysts are summarized. Then the effects of reactants including single alkane, co-aromatization and process coupling with oxidation are also discussed.

2. Catalysts

2.1 Zeolites

2.1.1 Unmodified zeolite

Zeolites are the most commonly utilized catalysts for the alkane aromatization due to the shape selectivity and ability to reduce coke formation. The H-ZSM-5 zeolite is the most widely used framework type for alkane aromatization. Besides the framework structure, the type of acidity and strength determined by heteroatoms species (e.g. Al or Ga) and the ratio of heteroatom to Si also affect the catalytic performance for alkane aromatization. In addition, the smaller crystal size of H-

^a Catalysis Engineering Group, Van 't Hoff Institute for Molecular Sciences, University of Amsterdam, 1090 GD Amsterdam, The Netherlands.

† h.wang4@uva.nl; n.r.shiju@uva.nl



REVIEW

ZSM-5 catalysts leads to enhanced cracking activity to form olefins because the larger external surface allows more pore

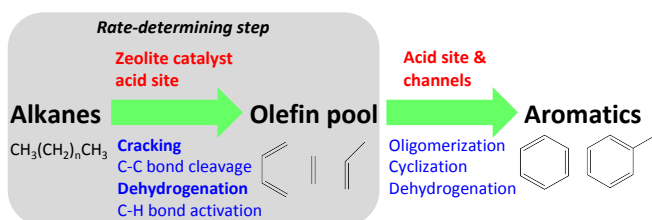


Fig. 1. Generalized steps for the catalytic aromatization of alkanes on zeolite catalysts.

entrances.¹⁰ The cracking reaction is favored on Brønsted acid sites compared to dehydrogenation during the conversion of alkanes when using the unmodified (monofunctional) zeolite catalysts.¹¹ The initial activation of alkanes is generally the rate determining step, which could convert the unreactive alkanes into adsorbed olefin species. The cracking and dehydrogenation mechanisms correspond to the C-C bond cleavage and C-H bond activation, respectively. These cracking products, especially the unsaturated olefin species on the acid sites, might be the intermediates for the subsequent aromatics formation.¹² The internal channels or pores of the zeolites could help the conversion of the activated intermediates to aromatics through oligomerization, cyclization and dehydrogenation (Fig. 1).

2.1.2 Metal modified zeolites

To improve the selectivity of aromatics, many metal elements such as Ga, Zn, Pt, Mo, Mg and Cu are utilized to modify the zeolite to produce bifunctional catalysts.^{9, 13-18} Generally, the Brønsted acid sites of the unmodified zeolites (Section 2.1.1) would contribute to the cracking reaction, whereas the introduction of metal elements could lead to the formation of Lewis acid sites which would enhance the dehydrogenation reaction. In another word, the Brønsted acid sites would favor the C-C bond breakage while Lewis acid sites would promote C-H bond cleavage during the activation of the reactant alkane. As shown in Fig. 2, the cracking rate is higher than dehydrogenation rate on Brønsted acid sites (Ga/Al = 0) whereas the dehydration rate is higher than cracking rate on Lewis acid sites (Ga/Al > 0).¹⁹ The introduction of metal elements into the zeolite can create Lewis acid sites which can promote the dehydrogenation. For example, the dehydrogenation rate of n-butane over Ga/H-MFI is 180 times higher than that over H-MFI under the same condition.²⁰ Both Lewis and Brønsted acid sites are involved in the aromatization process, especially for the ethylene oligomerization.²¹ It is also reported that alkane dehydrogenation can also occur over the Lewis-Brønsted acid site pairs via a bifunctional mechanism derived from the synergy between the Lewis and Brønsted acid sites.¹⁹ Therefore, the Brønsted and Lewis acidity of the zeolite catalyst could be tuned to optimize the catalytic performance. The pyridine Fourier transform infrared spectroscopy (FT-IR) is usually utilized to quantify the Brønsted and Lewis acid sites.²²

The nature and dispersion of the metal modifier have an impact on the activity, which could be tuned by preparation and

pretreatment methods. For example, it is reported that Zn²⁺ on H-BEA zeolite prepared by reaction with zinc vapor has higher activity than ZnO/H-BEA synthesized by hydrolysis of zinc-

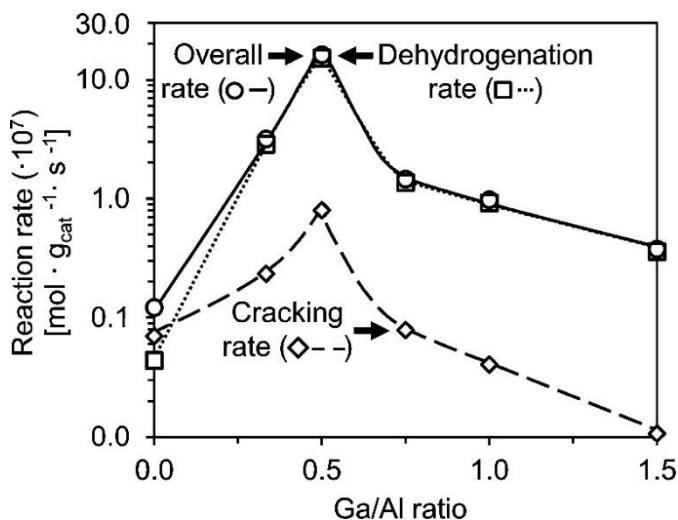


Fig. 2. Cracking and dehydrogenation rates at different Ga/Al ratios (This figure is reproduced from ¹⁹ with permission).

organic species during the propane aromatization.²³ However, in another study, the opposite conclusion was reached indicating the subnanomeric ZnO clusters on H-ZSM-5 might have higher selectivity than Zn²⁺ ions.²⁴ This contradictory result might be caused by a support effect. For example, the Zn/SiO₂@ZSM-5 core-shell catalyst synthesized by the hydrothermal coating method would lead to higher alkane conversion and aromatics selectivity than the conventional Zn/ZSM-5 during the co-aromatization of methane and propane.²⁵ Moreover, the H₂-chemisorbed Zn species could significantly improve the aromatic selectivity to 30% by hydrogen treatment compared to 11% of the H-ZSM-5 during pentane aromatization.²⁶ Additionally, it is found that the Zn/ZSM-5 microsphere catalyst with hierarchical structure exhibited improved stability compared to the conventional microporous Zn/ZSM-5 because of the presence of intergranular mesopores which could enhance the molecular transport and resistance to coke formation.²⁷

Furthermore, Zn and Pt are commonly used as the promoters for alkane reforming to achieve high BTX yield due to the incorporation of Zn into the framework of ZSM-5 and the enhanced metal dispersion by Pt.^{1, 5, 28} It is reported that Zn, as a promoter, can increase the aromatic selectivity.²⁹ Similarly, Pt could enhance the catalytic conversion of ethane because of the strengthened reducibility of Ga species on ZSM-5³⁰ and the synergistic interaction³¹. One disadvantage of Zn/ZSM is the agglomeration and loss of Zn after a certain time on stream even though it could be re-dispersed evenly after regeneration.^{29, 32} Zn/ZSM-5 should be modified with higher thermal stability and activity, such as introducing other metal elements.

Similarly, the Lewis acid sites of Ga modified zeolite promoted the aromatization and Ga introduced by direct (or *in-situ*) synthesis seems to have better performance.^{31, 33} GaH₂⁺



Reaction Chemistry & Engineering

species was highly active for the hexane dehydroaromatization over Ga modified H-ZSM-5 and could be acquired by pretreatment using hydrogen.³⁴ The Ga species incorporated in the framework favored the BTX formation than the extra framework ones because of the insignificant shielding of acid sites for the framework ones.³⁵ As for the effects of dispersion, the highly dispersed Ga on the hierarchical zeolite nanosheets also contributed to the activation of the n-pentane.³⁶ However, the mesopores of the desilicated hierarchical Ga/H-ZSM-5 via alkaline treatment decreased the activity and selectivity for propane aromatization apparently because the mesopores lowered the residence time of olefins and inhibited the dehydrogenation which is the rate-determining step.³⁷ The investigation of structure-activity relationship by correlating the catalyst structure and performance could give some insights into the reaction pathway, which also emphasizes the importance of olefin pool shown in Fig.1.³⁸ In addition, operando characterization is required to analyse the active sites even though the coke formation could make the analysis difficult.³⁹

Mo-modified zeolite can be used to aromatize small alkanes (e.g. C1-C3).¹⁸ Induction period is consistently present when using Mo/ZSM-5.⁴⁰ This is because the Mo carbide as the active species will be formed by carburization at the beginning.⁴¹ Mg as a promoter can enhance the catalytic activity and stability of Mo/ZSM-5.⁴²

High Cu loading decreases the acidic strength of zeolite catalyst, which can maintain the alkane conversion and selectivity to aromatics.¹³ It is reported that mononuclear Cu is the dominant species at low Cu loading (0.1 wt%) while multinuclear Cu with Cu-O-Cu bridge is the main species at higher Cu loading (1.4 wt%).⁴³

2.1.3 Non-metal modification

Phosphorous (P) is a typical non-metal modifier for alkane aromatization catalysts. The introduction of P can form

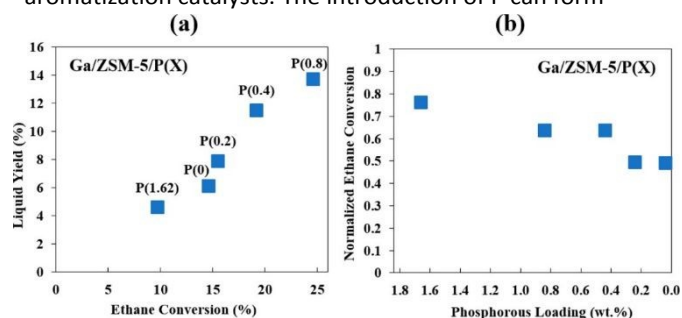


Fig.3. Effects of phosphorus (wt %) on the yield of liquid aromatics (a) and ethane conversion (b) (This figure is reproduced from⁴⁴ with permission).

aluminum phosphate with both framework and extra-framework Al and thus can decrease the concentration and strength of Brønsted acid sites over the parent H-ZSM-5.⁴⁵ Besides reducing the strength of acid sites, the P modification could also tune the pore structure of zeolite, which would help decrease the H₂ formation barriers and promote the formation of aromatics.⁴⁴ For example, P could enhance the yield of liquid aromatics and stability in ethane conversion as shown in Fig.3.

Additionally, the P modification improved the hydrothermal stability of Ga-ZSM-5 by lowering the binding energy between H₂O and the Brønsted acid sites as well as decreased the coke formation by reducing the amount of strong acid sites where cracking is favored.⁴⁴

Similar to the phosphorous, boron, being near to Al and Si in the periodic table, could also reduce the deactivation rate in the Zn-B/ZSM-5 catalyst during the hexane aromatization even though it decreased the catalyst activity initially.⁴⁶ The boron was incorporated into the framework and reduced the acidity of the Brønsted acid sites, which could further limit the conversion of coke precursors on these sites.

2.2 Noble metals

The noble metal catalysts such as platinum and palladium⁴⁷ are generally featured with high activity and are extensively applied in the scales of single atom, cluster and nanoparticles loaded on various supports such as carbon, zeolite and alumina. Table 1 shows various catalyst combinations and their performance. The single site platinum catalyst on CeO₂ support exhibited high selectivity for dehydrocyclization and aromatization reactions compared to Pt cluster and nanoparticle catalysts during hexane reforming even though its thermal stability degraded after 450 °C.⁴⁸ Besides the noble metal sizes, the location of the metal atoms on the support could also affect the catalyst performance and therefore the product distribution. For example, the Pt nanoparticles inside the zeolite channels led to higher selectivity to aromatics than those on the external surface because the Pt sites inside the pores would favor the cyclization.⁴⁹ However, the Pt particles inside the channels might relocate to the outside during the reaction and thus lead to deactivation.⁵⁰ Besides the relocation of Pt particles, the higher cost of noble metals than Ga and Zn should also be taken into consideration. The development of single atom noble metal catalysts may help to decrease the cost due to the maximum utilisation of noble metals.⁴⁸

The catalytic performance of noble metal catalysts is also support-dependent. The hierarchical support structure (e.g. micro-/mesoporous Pt/KL) can enhance the aromatization by a combined effect of the high activity of the Pt in micropores and the inhibited side reactions due to the mesoporous catalyst.⁵¹ For example, the mesopores in Pt/desilicated ZSM-5 contributed to the higher ethane conversion by 60% and BTX selectivity by 75% compared to the Pt/conventional ZSM-5.⁵² Some macroporous oxides (e.g. Ta₂O₅) support can improve the desired selectivity (up to 97% towards isomerization) by allowing charge transfer at the metal-oxide interface and high electron density of Pt.⁵³

Furthermore, metal promoters such as Zn^{54, 55} and Fe⁵⁶ could be introduced to improve the dispersion of noble metal atoms on the support. The formed bimetallic catalyst enhanced the alkane conversion and BTX selectivity by accelerating the initial dehydrogenation to form olefins and the subsequent dehydrocyclization to produce aromatics. Another study showed that the introduction of Zn to Pt over H-ZSM-5 could reduce coke yield from 8.3 to 1.7 µg/g cat-h and thus alleviate catalyst deactivation.⁵⁷ Moreover, for bimetallic catalysts, the



REVIEW

interaction between both metals (e.g. Pt–Zn nanoparticles) and the support (e.g. uniform compact cylindrical ZSM-5) also improved the selectivity over 90% towards aromatics compared to the selectivity less than 40% from the Pt-Zn over the conventional ZSM-5.⁵⁸

2.3 Other catalysts

Besides the widely-utilized zeolites and noble metals, other catalysts were also used to aromatize the alkanes. GaN as a nitride semiconductor could catalyze the aromatization of light alkanes to benzene with high selectivity.^{59, 60} However, the small surface area (e.g. 8 m²/g) of GaN required high temperature (> 650 °C) to initiate benzene formation because the activity is limited by the number of active sites which are dependent on the surface area.³ Activated carbon doped with phosphorus is also reported to aromatize n-hexane into benzene with the -P(O)(OH) functional group as the active sites.^{61, 62} The active sites of the P@AC catalyst are weak/medium-strength acidic centers in nature, which could selectively activate the C-H bond instead of the C-C bond.

2.4 Catalyst Deactivation

During the catalytic aromatization n-alkanes, coke formation is almost inevitable and is the major reason for the catalyst deactivation because the formed coke will block the active sites and zeolite channels.^{63, 64} However, measures could be taken to suppress the coke formation, such as developing bimetallic catalysts. Incorporation of Co into Mo/ZSM-5 could enhance the resistance to deactivation by reducing the coke formation during the aromatization of methane.⁶⁵ Similarly, introducing of Pt into Ga/ZSM-5 could facilitate the hydrogenolysis of coke precursors.⁶⁶ Besides modifying the catalyst, conducting aromatization under a reduction environment (e.g. with H₂ in the feed) could also suppress coke formation.^{21, 67}

3. Reactants

The aromatization of methane⁶⁴, ethane⁷, and propane⁶⁸ has been separately reviewed in the literature. The purpose of discussion here is to provide a big picture about the influence of the alkane structure and a generalized reaction mechanism of alkane aromatization.

3.1 Single alkane

CH₄ is abundant in natural gas and is produced as a by-product in many chemical processes. The strong C-H bond in CH₄ would make it the most unreactive hydrocarbon species. The most widely investigated catalyst for CH₄ aromatization is the Mo/H-ZSM-5.⁶⁴ As shown in Fig.1, the aromatization of CH₄ over Mo/H-ZSM-5 at 700 °C involves the formation of a hydrocarbon pool. An induction period was also observed due to the accumulation of adsorbed hydrocarbon on the Mo sites.⁶⁹ It is believed that the molybdenum carbide species are only responsible for the activation of CH₄ molecules and the Mo-carbide/H-ZSM-5 is more active and stable than the Mo-oxide/H-ZSM-5 during CH₄ aromatization.^{70, 71} This could explain the presence of an induction period when the Mo-oxide is converted into Mo-carbide. The formation of carbides is facilitated by the reduction and carburization

Table 1. Noble metal catalysts for the aromatization of alkanes

Noble metal	Support	Reactant	Condition	Conversion/Selectivity	Key findings	Ref.
Pd	C	n-octane	500 °C, WHSV = 2 h ⁻¹ , hydrogen to hydrocarbon molar ratio=2	conversion = 54.4 wt%; aromatics selectivity = 58 wt%	Pd/C has higher selectivity to xylenes.	47
Pt	CeO ₂	n-hexane	500 °C	conversion = 5%; aromatization selectivity = 40%	The single-site catalyst Pt/CeO ₂ shows higher selectivity to dehydrocyclization and aromatization than CeO ₂ -supported Pt clusters and nanoparticles.	48
Pt	KL zeolite	n-heptane	420 °C, hydrogen/n-heptane molar ratio = 6, WHSV = 0.68 h ⁻¹	conversion = 88 mol%; aromatics selectivity = 84.3 mol%	The location of Pt nanoparticles in KL zeolites could be controlled by changing the exposure time of Pt precursor.	49
Pt	KL zeolite	n-heptane	500 °C, 1 atm, WHSV = 1 h ⁻¹ , H ₂ /n-heptane = 6 mol/mol, Pt loading = 0.6 wt%	conversion = 63.89 wt%; aromatics selectivity = 58.84 wt%	High dispersion of Pt in KL zeolite could improve the stability.	50
Pt	desilicated ZSM-5	ethane	550 °C, 2 barg, GHSV = 0.3 h ⁻¹	conversion = 25%; selectivity = 42%	Pt nanoparticles in desilicated ZSM-5 are near the acid sites, which could increase the activity and selectivity to BTX.	52



pretreatment and thus improved the catalytic properties.⁷² As shown in Fig. 4, the catalysts with pre-carburization demonstrated higher benzene yield and slower deactivation rate. Various Mo-carbide species such as MoC³⁹, Mo₂C⁷³, Mo₂C₆⁷⁴ and MoC_xO_y⁷⁵, each with distinct structural and catalytic properties, may be the active sites to catalyze the aromatization. There is still debate about the evolution of the species during the reaction and their effects on the catalytic performance. For instance, it is reported that the isolated Mo-oxide evolves into Mo-carbide nanoparticles during reaction.⁷⁶ It is also proved that even though MoC_xO_y could activate CH₄, MoC_x is essential for the formation of aromatics.⁷⁵ To resolve the debate, advanced operando techniques are required to determine the reaction pathways. In addition, the doping of metal elements such as Co and Pd to Mo/ZSM-5 catalyst enhanced the stability and improved the resistance to deactivation.^{65, 73} It is also reported that the physical mixing of NiO with Mo/H-ZSM-5 enhanced the aromatic yield and catalytic stability because NiO could increase the dispersion of molybdenum carbide and metal Ni can decrease the coke formation by converting the coke precursors to carbon nanotube.⁴¹ Besides zeolite, sulfated zirconia supported Mo with various promoters could also promote the aromatization with little coke formation.⁷⁷

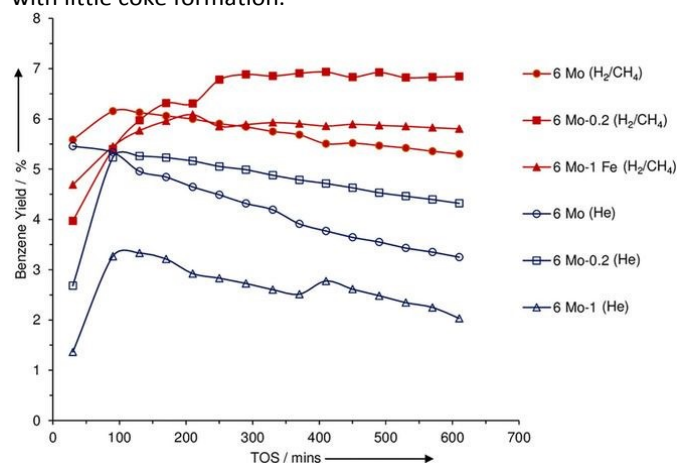


Fig. 4. Benzene yield for catalysts 6Mo/ZSM-5, 6Mo-0.2Fe/ZSM-5, and 6Mo-1Fe/ZSM-5 under He treatment (open symbols) and pre-carburization (closed symbols) (This figure is reproduced from ⁷² with permission).

Similar to the unreactive methane, the ethane aromatization has not been commercialized until now as well. Besides Mo/ZSM-5 and its modification (e.g. Fe or Zn as the promoter)²⁹, other active metals such as Pt⁷⁸, Zn²¹, Ga⁴⁰, Re⁷⁹, GaPt^{30, 66} and NiGa⁸⁰ could be supported on ZSM-5 to catalyze the ethane aromatization reaction. After ethane activation (i.e. dehydrogenation), oligomerization would also take place to form new C-C bonds over both Brønsted and Lewis acid sites.⁸¹ The newly formed unsaturated intermediate pool of a certain size (e.g. C₆ – C₈) would further undergo cyclization and dehydrogenation to produce aromatics.

The aromatization of C₃₊ alkanes, especially the C₃ – C₆ species and their mixture, has been commercialized using Ga or Zn modified H-ZSM-5 catalyst or supported noble metals, such

as Cyclar and M2-reforming processes. Typically, the yield of aromatic compounds could reach up to 58 – 60 wt% when C₃ and C₄ are utilized as the feedstock.⁷ Lower temperature is generally required for the aromatization of C₃₊ alkanes compared to methane or ethane.⁸²

The aromatization of C₆₊ alkanes is also called “reforming” in the industry. The main aim of reforming is to convert alkanes and cycloalkanes into aromatics with platinum catalysts such as Pt/γ-Al₂O₃ and Pt/KL zeolite.⁸³⁻⁸⁶ Besides the supported noble metal catalysts, other metals such as Mo⁶³, Cu¹³, and Ga³⁴ could also be utilized to achieve the aromatization. Even though it is thought that the straight carbon chain of C₆ – C₈ alkanes could be converted into aromatics without cracking or oligomerization reactions⁵⁸, BTX will be present in the products when a single alkane acts as the reactant⁸⁷, which could prove the existence of unsaturated intermediate pool.

The reports of the aromatization of C₉₊ alkanes are fewer than the lighter alkanes. The cracking reaction of C₉₊ alkanes would be more desired compared to the light alkanes¹², because it would be easier for the C₂ – C₈ species in the unsaturated intermediate pool to form the aromatics. After cracking, the species in the unsaturated intermediate pool would undergo similar aromatization route.⁸⁸

3.2 Co-aromatization

Co-aromatization is generally conducted for CH₄ with other alkanes such as propane^{89, 90} and pentane⁹¹ because it is supposed that the presence of a co-reactant could reduce the thermodynamic limitation. Conversely, CH₄ could also function as a co-reactant to promote BTX production during the aromatization of light alkanes over Zn-Ga/H-ZSM-5⁹² or the aromatization of complex naphtha over Zn-Pt/H-ZSM-5²⁸. As shown in Fig. 5, the presence of methane could increase the liquid and BTX yield compared to N₂. The H_x and CH_x intermediates formed from CH₄ are anticipated to involve in the formation of light aromatics and suppress the formation of heavy aromatics compared to N₂.⁶⁷ The incorporation of fragments from CH₄ in the products during the co-aromatization with propane was supported by the detection of ¹³C of CH₄ in the aromatic rings of the products.^{93, 94} The catalyst properties might affect the CH₄ reaction pathway, such as the acidity influenced by the Al sites⁹⁵ and the location of Zn species over the Zn/H-ZSM-5 zeolite⁹⁶. The aromatization of naphtha as a paraffin mixture could also be considered as a co-aromatization of similar alkanes.⁹⁷

3.3 Coupling with oxidation process

Besides the direct aromatization discussed above, the oxidative dehydrogenation could be coupled with the aromatization. CO₂ has been used already to produce valuable olefins or synthesis gas from alkanes via the CO₂-oxidative dehydrogenation (CO₂ - ODH) or dry reforming.⁹⁸⁻¹⁰⁰ Chen et al. proposed a tandem CO₂ oxidative dehydrogenation-aromatization reaction, which could promote the dehydrogenation and enhance the subsequent aromatization by consuming H₂.⁴⁴ Fig.6 demonstrates that CO₂-oxidative dehydrogenation and aromatization could achieve a higher equilibrium ethane conversion than direct dehydrogenation and aromatization. It is proposed that CO₂



REVIEW

Reaction Chemistry & Engineering

consumes the coke via the reverse Boudouard reaction ($\text{CO}_2 + \text{C} \rightarrow 2\text{CO}$), thus enhancing stability.¹⁰¹ Moreover, the reverse water gas shift reaction (RWGS) is promoted by CO_2 , consuming H_2 and thereby enhancing the dehydrogenation activity.

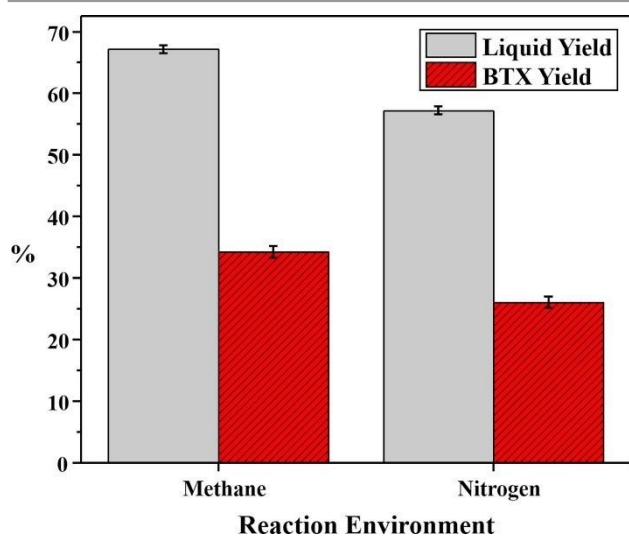


Fig. 5. Effects of environments on liquid and BTX yields during the reforming of naphtha utilizing Pt-Zn/ZSM-5 catalyst (This figure is reproduced from ²⁸ with permission).

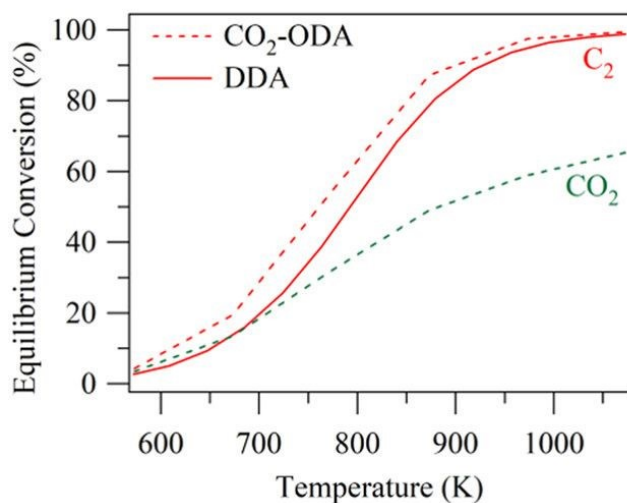


Fig. 6. Effects of temperature on the equilibrium ethane conversion (DDA: direct dehydrogenation and aromatization; CO_2 -ODA: CO_2 -oxidative dehydrogenation and aromatization) (This figure is reproduced from ⁴⁴ with permission).

Besides the direct coupling of chemical reactions, the methane aromatization process can also be integrated with the chemical looping for selective H_2 oxidation and H_2O removal so that a high combined aromatic yield could be acquired for the whole integrated process.¹⁰²

4. Challenges and outlook

During the catalytic aromatization, low activity/selectivity especially for methane conversion and catalyst deactivation are

the main challenges.²⁹ As discussed in Section 3.1, methane is very difficult to activate, which requires high temperatures. On the other hand, elevated temperatures could cause side reactions to lower the selectivity and increased coke formation accelerating the deactivation. Promising catalysts are reported in the literature, however, improvements are still needed in activity and stability. Moreover, the scale-up should be carefully considered, as most of the studies are on lab-scale. Alternate reactor configurations also need to be studied, considering the heat effects associated with the reaction.

Future efforts should be focusing on using small alkanes such as methane from abundant natural gas⁷ and carbonous waste such as biomass and plastic waste. New catalysts and process technologies need to be developed to address the challenges, as mentioned above.²³

Conclusions

This paper reviews the recent advances about the development of catalysts and the mechanism investigations of alkane aromatization. The most important step in the alkane aromatization is the activation of alkanes to form the unsaturated intermediate pool with the help of a catalyst. The C-H bond activation is essential for the formation of unsaturated intermediate pool from the alkanes, whereas the C-C bond breakage would occur via the cracking. For the zeolite catalyst, the Brønsted acid sites favor the C-C bond breakage while Lewis acid sites promote C-H bond cleavage during the activation of the reactant alkane. Oligomerization might also occur depending on the exact carbon number of the alkane feedstock, such as methane and ethane, which are more difficult to activate compared to higher alkanes. Besides zeolites and their modified materials, noble metals and other catalysts such as GaN could also be utilized to aromatize alkanes. Based on the summary of the past works, we believe that there is still a large scope for future research in different aspects of this reaction. There is potential in either improving the existing catalysts or designing new catalysts which could enhance the formation of unsaturated intermediate pool. The use of predictive modeling or rapidly developing machine learning approach may help to identify novel potential compositions that were not tested so far in this reaction.¹⁰³ Materials such as niobia, which are tunable in their Lewis/Brønsted acidity could also be examined as part of such compositions.¹⁰⁴⁻¹⁰⁶ It would also be interesting to try non-conventional synthesis methods such as hydrothermal methods and microwave-assisted methods to accelerate the catalyst synthesis or to control the compositions more accurately.¹⁰⁷ Doping with suitable components will also help to modulate the activity and stability of the new catalyst compositions.¹⁰⁸ The use of tandem reactions, as described above, could be another option to overcome the issues in the direct aromatization such as the coke deposition and consequent deactivation. It would also help in having a deeper insight into the mechanism through in-situ spectroscopy and computational calculations. Simultaneously, the studies in the reaction engineering will help



to address the probable challenges in the potential scale-up possibilities of the aromatization of alkanes.

Author contributions

Hongqi Wang: Conceptualization, Investigation, Data curation, Visualization, Writing – original draft, Writing – review & editing. N. Raveendran Shiju: Supervision, Writing – review & editing.

Conflicts of interest

There are no conflicts to declare.

References

- Q.-m. Zhou, S. Wang, Z.-f. Qin, M. Dong, J.-g. Wang and W.-b. Fan, *Journal of Fuel Chemistry and Technology*, 2023, **51**, 1529-1539.
- K. Li, M. Yan, H. Wang, L. Cai, P. Wang and H. Chen, *Fuel Processing Technology*, 2023, **252**, 107982.
- M. N. Akhtar, A. M. Aitani, A. C. Ummer and H. S. Alasiri, *Energy & Fuels*, 2023, **37**, 2586-2607.
- F. Yu, S. Liu and B. Liu, *Molecules*, 2024, **29**, 1288.
- D. Xu, L. Wei, M. Yan, F. Yi, G. Zhao, A. Jia, D. Zhu, S. Wang and Y. Li, *Applied Catalysis A: General*, 2023, **663**, 119308.
- G. He and D. Mei, *Journal of Catalysis*, 2024, **436**, 115623.
- Y. Xiang, H. Wang, J. Cheng and J. Matsubu, *Catalysis Science & Technology*, 2018, **8**, 1500-1516.
- V. I. Bogdan, A. E. Koklin, I. I. Mishanin, T. V. Bogdan, N. V. Mashchenko and L. M. Kustov, *Mendeleev Communications*, 2021, **31**, 230-232.
- D. Liu, L. Cao, G. Zhang, L. Zhao, J. Gao and C. Xu, *Fuel Processing Technology*, 2021, **216**, 106770.
- A. A. Rownaghi, F. Rezaei and J. Hedlund, *Chemical Engineering Journal*, 2012, **191**, 528-533.
- T. F. Narbeshuber, H. Vinek and J. A. Lercher, *Journal of Catalysis*, 1995, **157**, 388-395.
- S. Pradhan, R. Lloyd, J. K. Bartley, D. Bethell, S. Golunski, R. L. Jenkins and G. J. Hutchings, *Chemical Science*, 2012, **3**, 2958-2964.
- O. Tursunov, L. Kustov and Z. Tilyabaev, *Journal of Petroleum Science and Engineering*, 2019, **180**, 773-778.
- C. M. Lok, J. Van Doorn and G. Aranda Almansa, *Renewable and Sustainable Energy Reviews*, 2019, **113**, 109248.
- F. Goodarzi, R. P. Thumbayil, K. Enemark-Rasmussen, J. Mielby, T. T. M. Nguyen, P. Beato, F. Joensen and S. Kegnæs, *ChemCatChem*, 2020, **12**, 1519-1526.
- B. Xu, M. Tan, X. Wu, H. Geng, F. Song, Q. Ma, C. Luan, G. Yang and Y. Tan, *Fuel*, 2021, **283**, 118889.
- Z. Hou, X. Mi, X. Li and H. Liu, *Industrial & Engineering Chemistry Research*, 2021, **60**, 12100-12108.
- Y. Hyun Lim, H. Won Ryu, K. Nam, Y. Hwang, J. Roh and D. Heui Kim, *Fuel*, 2023, **342**, 127906.
- M. W. Schreiber, C. P. Plaisance, M. Baumgärtl, K. Reuter, A. Jentys, R. Bermejo-Deval and J. A. Lercher, *Journal of the American Chemical Society*, 2018, **140**, 4849-4859.
- N. M. Phadke, E. Mansoor, M. Head-Gordon and A. T. Bell, *ACS Catalysis*, 2021, **11**, 2062-2075.
- T. Liang, S. Fadaeeraeyeni, J. Shan, T. Li, H. Wang, J. Cheng, H. Toghiani and Y. Xiang, *Industrial & Engineering Chemistry Research*, 2019, **58**, 17699-17708.
- A. K. Panda, A. Alotaibi, I. V. Kozhevnikov and N. R. Shiju, *Waste and Biomass Valorization*, 2020, **11**, 6337-6345.
- S. S. Arzumanov, A. A. Gabrienko, A. V. Toktarev, Z. N. Lashchinskaya, D. Freude, J. Haase and A. G. Stepanov, *The Journal of Physical Chemistry C*, 2019, **123**, 30473-30485.
- L. Lin, J. Liu, X. Zhang, J. Wang, C. Liu, G. Xiong and H. Guo, *Industrial & Engineering Chemistry Research*, 2020, **59**, 16146-16160.
- G. Xu and X. Zhu, *Applied Catalysis B: Environmental*, 2021, **293**, 120241.
- S. Tamiyakul, T. Sooknoi, L. L. Lobban and S. Jongpatiwut, *Applied Catalysis A: General*, 2016, **525**, 190-196.
- J. Wang, C. Liu, P. Zhu, H. Liu, X. Zhang, Y. Zhang, J. Liu, L. Zhang and W. Zhang, *New Journal of Chemistry*, 2021, **45**, 18659-18668.
- J. Jarvis, A. Wong, P. He, Q. Li and H. Song, *Fuel*, 2018, **223**, 211-221.
- B. Robinson, X. Bai, A. Samanta, V. Abdelsayed, D. Shekhawat and J. Hu, *Energy & Fuels*, 2018, **32**, 7810-7819.
- A. Caiola, B. Robinson, X. Bai, D. Shekhawat and J. Hu, *Industrial & Engineering Chemistry Research*, 2021, **60**, 11421-11431.
- Y. Wang, A. Caiola, B. Robinson, Q. Li and J. Hu, *Energy & Fuels*, 2020, **34**, 3100-3109.
- R. Geng, Y. Liu, Y. Guo, P. Wang, M. Dong, S. Wang, J. Wang, Z. Qin and W. Fan, *ACS Catalysis*, 2022, **12**, 14735-14747.
- Y. Zhou, H. Thirumalai, S. K. Smith, K. H. Whitmire, J. Liu, A. I. Frenkel, L. C. Grabow and J. D. Rimer, *Angewandte Chemie International Edition*, 2020, **59**, 19592-19601.
- A. Thivasasith, T. Maihom, S. Pengpanich, J. Limtrakul and C. Wattanakit, *Physical Chemistry Chemical Physics*, 2019, **21**, 5359-5367.
- B. J. Lee, J. H. Lee, D. H. Kim, Y. G. Hur and K.-Y. Lee, *Microporous and Mesoporous Materials*, 2021, **323**, 111243.
- W. Wannapakdee, D. Suttipat, P. Dugkhuntod, T. Yuthalekha, A. Thivasasith, P. Kidkhunthod, S. Nokbin, S. Pengpanich, J. Limtrakul and C. Wattanakit, *Fuel*, 2019, **236**, 1243-1253.
- M. Raad, S. Hamieh, J. Toufaily, T. Hamieh and L. Pinard, *Journal of Catalysis*, 2018, **366**, 223-236.
- Y. Wu, Y. Lv, R. Wang, L. Bao, Z. Zhang, D. Shi, A. Zhang, Y. Zhang, Q. Liu, Q. Wu, D. Shi, K. Chen, G. Jiang and H. Li, *Langmuir*, 2024, **40**, 11998-12008.
- I. Vollmer, I. Yarulina, F. Kapteijn and J. Gascon, *ChemCatChem*, 2019, **11**, 39-52.
- E. A. Uslamin, H. Saito, Y. Sekine, E. J. M. Hensen and N. Kosinov, *Catalysis Today*, 2021, **369**, 184-192.
- K. Nam, H. W. Ryu, M. Y. Gim and D. H. Kim, *Applied Catalysis B: Environmental*, 2021, **296**, 120377.
- H. W. Ryu, Y. H. Lim, W. Jung, K. Nam, Y. Hwang, J. E. Roh and D. H. Kim, *Chemical Engineering Journal*, 2023, **467**, 143404.
- A. A. Kolganov, A. A. Gabrienko, S. A. Yashnik, E. A. Pidko and A. G. Stepanov, *The Journal of Physical Chemistry C*, 2020, **124**, 6242-6252.
- E. Gomez, X. Nie, J. H. Lee, Z. Xie and J. G. Chen, *Journal of the American Chemical Society*, 2019, **141**, 17771-17782.



REVIEW

Reaction Chemistry & Engineering

45. W. Lin, Y. Song, L. Han, X. Yang, J. Liu and B. Peng, *Fuel*, 2021, **299**, 120890.
46. P. T. Huyen, V. D. Trinh, M. Teresa Portilla and C. Martínez, *Catalysis Today*, 2021, **366**, 97-102.
47. M. Yin, R. H. Natelson, A. A. Campos, P. Kolar and W. L. Roberts, *Fuel*, 2013, **103**, 408-413.
48. S. Zhang, L. Chen, Z. Qi, L. Zhuo, J.-L. Chen, C.-W. Pao, J. Su and G. A. Somorjai, *Journal of the American Chemical Society*, 2020, **142**, 16533-16537.
49. D. Xu, S. Wang, B. Wu, C. Huo, Y. Qin, B. Zhang, J. Yin, L. Huang, X. Wen, Y. Yang and Y. Li, *Journal of Catalysis*, 2018, **365**, 163-173.
50. K. Li, Q. Chang, J. Yin, C. Zhao, L. Huang, Z. Tao, Y. Yun, C. Zhang, H. Xiang, Y. Yang and Y. Li, *Journal of Catalysis*, 2018, **361**, 193-203.
51. K. Lee and M. Choi, *Journal of Catalysis*, 2016, **340**, 66-75.
52. F. Goodarzi, D. B. Christensen, F. Joensen, S. Kegnæs and J. Mielby, *Applied Catalysis A: General*, 2020, **592**, 117383.
53. K. An, S. Alayoglu, N. Musselwhite, K. Na and G. A. Somorjai, *Journal of the American Chemical Society*, 2014, **136**, 6830-6833.
54. P. He, Y. Chen, J. Jarvis, S. Meng, L. Liu, X.-D. Wen and H. Song, *ACS Applied Materials & Interfaces*, 2020, **12**, 28273-28287.
55. G. Liu, J. Liu, N. He, S. Sheng, G. Wang and H. Guo, *Journal of Energy Chemistry*, 2019, **34**, 96-103.
56. D. Xu, S. Wang, B. Wu, B. Zhang, Y. Qin, C. Huo, L. Huang, X. Wen, Y. Yang and Y. Li, *ACS Applied Materials & Interfaces*, 2019, **11**, 29858-29867.
57. J. Jarvis, P. He, A. Wang and H. Song, *Fuel*, 2019, **236**, 1301-1310.
58. J. S. Jarvis, J. H. Harrhy, P. He, A. Wang, L. Liu and H. Song, *Chemical Communications*, 2019, **55**, 3355-3358.
59. L. Li, X. Mu, W. Liu, X. Kong, S. Fan, Z. Mi and C.-J. Li, *Angewandte Chemie International Edition*, 2014, **53**, 14106-14109.
60. K. Dutta, L. Li, P. Gupta, D. P. Gutierrez and J. Kopyscinski, *Catalysis Communications*, 2018, **106**, 16-19.
61. Y. Li, H. Zhao, S. Chen, S. Bao, F. Xing and B. Jiang, *Catalysis Communications*, 2021, **156**, 106318.
62. Y. Li, S. Bao, H. Zhao, B. Feng, S. Chen, T. Gu, B. Yang and B. Jiang, *Chemical Communications*, 2021, **57**, 4166-4169.
63. R. Barthos and F. Solymosi, *Journal of Catalysis*, 2005, **235**, 60-68.
64. J. J. Spivey and G. Hutchings, *Chemical Society Reviews*, 2014, **43**, 792-803.
65. V. Fila, M. Bernauer, B. Bernauer and Z. Sobalik, *Catalysis Today*, 2015, **256**, 269-275.
66. A. Samanta, X. Bai, B. Robinson, H. Chen and J. Hu, *Industrial & Engineering Chemistry Research*, 2017, **56**, 11006-11012.
67. Q. Li, P. He, J. Jarvis, A. Bhattacharya, X. Mao, A. Wang, G. M. Bernard, V. K. Michaelis, H. Zeng, L. Liu and H. Song, *Applied Catalysis B: Environmental*, 2018, **236**, 13-24.
68. A. Bhan and W. Nicholas Delgass, *Catalysis Reviews*, 2008, **50**, 19-151.
69. I. Vollmer, E. Abou-Hamad, J. Gascon and F. Kapteijn, *ChemCatChem*, 2020, **12**, 544-549.
70. M. Rahman, A. Sridhar and S. J. Khatib, *Applied Catalysis A: General*, 2018, **558**, 67-80.
71. V. Ramasubramanian, H. Ramsurn and G. L. Price, *Journal of Energy Chemistry*, 2019, **34**, 20-32.
72. A. Sridhar, M. Rahman and S. J. Khatib, *ChemCatChem*, 2018, **10**, 2571-2583. DOI: 10.1039/D4RE00384E
73. N. Pasupulety, A. A. Al-Zahrani, M. A. Daous, H. Driss and L. A. Petrov, *Journal of Materials Research and Technology*, 2021, **14**, 363-373.
74. T. S. Khan, S. Balyan, S. Mishra, K. K. Pant and M. A. Haider, *The Journal of Physical Chemistry C*, 2018, **122**, 11754-11764.
75. I. Lezcano-González, R. Oord, M. Rovezzi, P. Glatzel, S. W. Botchway, B. M. Weckhuysen and A. M. Beale, *Angewandte Chemie International Edition*, 2016, **55**, 5215-5219.
76. J. Gao, Y. Zheng, J.-M. Jehng, Y. Tang, I. E. Wachs and S. G. Podkolzin, *Science*, 2015, **348**, 686-690.
77. M. A. Abedin, S. Kanitkar, S. Bhattar and J. J. Spivey, *Catalysis Today*, 2021, **365**, 71-79.
78. H. Liu, H. Wang, A.-H. Xing and J.-H. Cheng, *The Journal of Physical Chemistry C*, 2019, **123**, 15637-15647.
79. L. Ma and X. Zou, *Applied Catalysis B: Environmental*, 2019, **243**, 703-710.
80. S. Fadaeeraeyeni, J. Shan, E. Sarnello, H. Xu, H. Wang, J. Cheng, T. Li, H. Toghiani and Y. Xiang, *Applied Catalysis A: General*, 2020, **601**, 117629.
81. A. Mehdad and R. F. Lobo, *Catalysis Science & Technology*, 2017, **7**, 3562-3572.
82. D. Zeng, G. Zhu and C. Xia, *Fuel Processing Technology*, 2022, **226**, 107087.
83. E. A. Belopukhov, D. I. Kir'yanov, M. D. Smolikov, V. A. Shkurenok, A. S. Belyi, A. V. Lavrenov, A. V. Kleimenov and D. O. Kondrashev, *Catalysis Today*, 2021, **378**, 113-118.
84. V. Y. Tregubenko, K. V. Veretelnikov, N. V. Vinichenko, T. I. Gulyaeva, I. V. Muromtsev and A. S. Belyi, *Catalysis Today*, 2019, **329**, 102-107.
85. D. Xu, B. Wu, P. Ren, S. Wang, C. Huo, B. Zhang, W. Guo, L. Huang, X. Wen, Y. Qin, Y. Yang and Y. Li, *Catalysis Science & Technology*, 2017, **7**, 1342-1350.
86. W. D. Shafer, G. Jacobs, U. M. Graham, V. R. R. Pendyala, M. Martinelli, G. A. Thomas, T. Jermwongratanachai, A. MacLennan, Y. Hu and B. H. Davis, *Catalysis Letters*, 2018, **148**, 97-107.
87. T. E. Tshabalala and M. S. Scurrill, *Catalysis Communications*, 2015, **72**, 49-52.
88. A. Zaker, G. A. Tompsett, S. Wang, J. Q. Bond and M. T. Timko, *Fuel*, 2022, **310**, 122360.
89. C. Song, M. Y. Gim, Y. H. Lim and D. H. Kim, *Fuel*, 2019, **251**, 404-412.
90. G. Xu, P. Zhang, J. Cheng, L. Xu, J. Fan, X. Zhu and F. Yang, *Microporous and Mesoporous Materials*, 2022, **330**, 111494.
91. P. He, J. Jarvis, L. Liu and H. Song, *Fuel*, 2019, **239**, 946-954.
92. Q. Li, F. Zhang, J. Jarvis, P. He, M. M. Yung, A. Wang, K. Zhao and H. Song, *Fuel*, 2018, **219**, 331-339.
93. M. V. Luzgin, V. A. Rogov, S. S. Arzumanov, A. V. Toktarev, A. G. Stepanov and V. N. Parmon, *Catalysis Today*, 2009, **144**, 265-272.
94. M. V. Luzgin, A. A. Gabrienko, V. A. Rogov, A. V. Toktarev, V. N. Parmon and A. G. Stepanov, *The Journal of Physical Chemistry C*, 2010, **114**, 21555-21561.
95. P. He, A. Wang, S. Meng, G. M. Bernard, L. Liu, V. K. Michaelis and H. Song, *Catalysis Today*, 2019, **323**, 94-104.



96. P. He, J. S. Jarvis, S. Meng, Q. Li, G. M. Bernard, L. Liu, X. Mao, Z. Jiang, H. Zeng, V. K. Michaelis and H. Song, *Applied Catalysis B: Environmental*, 2019, **250**, 99-111.
97. M. Ellouh, Z. S. Qureshi, A. Aitani, M. N. Akhtar, Y. Jin, O. Koseoglu and H. Alasiri, *ChemistrySelect*, 2020, **5**, 13807-13813.
98. M. Ronda-Lloret, T. K. Slot, N. P. van Leest, B. de Bruin, W. G. Sloof, E. Batyrev, A. Sepúlveda-Escribano, E. V. Ramos-Fernandez, G. Rothenberg and N. R. Shiju, *ChemCatChem*, 2022, **14**, e202200446.
99. M. Ronda-Lloret, L. Yang, M. Hammerton, V. S. Marakatti, M. Tromp, Z. Sofer, A. Sepúlveda-Escribano, E. V. Ramos-Fernandez, J. J. Delgado, G. Rothenberg, T. Ramirez Reina and N. R. Shiju, *ACS Sustainable Chemistry & Engineering*, 2021, **9**, 4957-4966.
100. M. Ronda-Lloret, V. S. Marakatti, W. G. Sloof, J. J. Delgado, A. Sepúlveda-Escribano, E. V. Ramos-Fernandez, G. Rothenberg and N. R. Shiju, *ChemSusChem*, 2020, **13**, 6401-6408.
101. E. Devid, M. Ronda-Lloret, Q. Huang, G. Rothenberg, N. R. Shiju and A. Kleyn, *Chinese Journal of Chemical Physics*, 2020, **33**, 243-251.
102. C. Brady, Q. Debruyne, A. Majumder, B. Goodfellow, R. Lobo, T. Calverley and B. Xu, *Chemical Engineering Journal*, 2021, **406**, 127168.
103. N. Madaan, N. R. Shiju and G. Rothenberg, *Catalysis Science & Technology*, 2016, **6**, 125-133.
104. S.-H. Chung, V. Lachman, T. K. Slot and N. R. Shiju, *Catalysis Communications*, 2023, **182**, 106754.
105. S. Shirazimoghaddam, I. Amin, J. A. Faria Albanese and N. R. Shiju, *ACS Engineering Au*, 2023, **3**, 37-44.
106. E. S. Gnanakumar, N. Chandran, I. V. Kozhevnikov, A. Grau-Atienza, E. V. Ramos Fernández, A. Sepulveda-Escribano and N. R. Shiju, *Chemical Engineering Science*, 2019, **194**, 2-9.
107. N. R. Shiju and V. V. Gulians, *ChemPhysChem*, 2007, **8**, 1615-1617.
108. E. V. Ramos-Fernandez, N. R. Shiju and G. Rothenberg, *RSC Advances*, 2014, **4**, 16456-16463.

View Article Online
DOI: 10.1039/D4RE00384E



View Article Online
DOI: 10.1039/D4RE00384E

Data Availability Statement

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

