



Cite this: *Org. Biomol. Chem.*, 2017, **15**, 6342

## Stabilizing bubble and droplet interfaces using dipeptide hydrogels

Fernando Aviño, <sup>a</sup> Andrew B. Matheson, <sup>a</sup> Dave J. Adams <sup>b</sup> and Paul S. Clegg <sup>\*,a</sup>

Hydrophobic dipeptide molecules can be used to create interfacial films covering bubbles and droplets made from a range of oils. At high pH, the dipeptide molecules form micelles which transform into a hydrogel of fibres in response to the addition of salt. We characterize the properties of the hydrogel for two different salt (MgSO<sub>4</sub>) concentrations and then we use these gels to stabilize interfaces. Under high shear, the hydrogel is disrupted and will reform around bubbles or droplets. Here, we reveal that at low dipeptide concentration, the gel is too weak to prevent ripening of the bubbles; this then reduces the long-term stability of the foam. Under the same conditions, emulsions prepared from some oils are highly stable. We examine the wetting properties of the oil droplets at a hydrogel surface as a guide to the resulting emulsions.

Received 30th April 2017,  
Accepted 4th July 2017

DOI: 10.1039/c7ob01053b

rscl.li/obc

## Introduction

Proteins have been used by cooks to stabilize foams and emulsions for many centuries.<sup>1</sup> The proteins are typically trapped on the interface and can denature, especially at liquid/air interfaces. By comparison, small peptides can potentially improve performance in two diametrically opposed ways. (1) Isolated small peptides will be adsorbed to the interface more quickly which can aid bubble or droplet formation.<sup>2</sup> This tends to be the more challenging route. (2) These small molecules may self-assemble into larger structures which retain their order at the interface;<sup>2–9</sup> the trapping at the interface can be much stronger than for individual proteins. Proteins have also been used as subunits within robust composite particles which themselves are interfacially active.<sup>10–14</sup> Nonetheless, short peptide sequences offer the distinct advantages of ease of synthesis and design as well as the tendency to self-assemble at very low concentration.

Recently, the behaviour of very short peptide sequences at liquid/air interfaces has begun to be explored.<sup>6,7</sup> Here naphthalene-protected diphenylalanine (2NapFF) molecules have been investigated most. One approach was to investigate the self-assembly of the dipeptide at the air/water interface prepared *via* drop-casting. A thin interfacial film formed from a dispersion of 2NapFF at high-pH on contact with a low-pH

subphase. FTIR and pH variation tests show that this self-assembly behaviour is associated with the carboxylic acid group of the dipeptide becoming rapidly protonated at the interface. The film was made up of self-assembled fibres and behaved like an elastic sheet.<sup>6</sup> The same dipeptide (2NapFF) also formed a hydrogel *via* the addition of metal ions. This hydrogel can be used to stabilise aqueous foams for weeks. The dipeptides at 1 wt% concentration self-assemble into fibre-like networks at both, the air/water interface and in the bulk. Raman spectroscopy hinted at a possible change in the balance between  $\pi$ -stacking and hydrogen bonding, with the latter appearing to drive self-assembly close to the interface. The dipeptide concentration as well as the type and concentration of metal ions, affects the foam stability.<sup>7</sup> When the bulk hydrogel had a yield stress larger than the Laplace pressure of the bubbles, ripening was suppressed.

Separately, the stabilization of emulsions using di-, tri- and hepta-peptides has also been investigated.<sup>2,5,8,9</sup> Initial experiments showed that it was possible to stabilize chloroform droplets for months using an interfacial network of dipeptide fibres. Here the dipeptide sequence was protected by *N*-(fluorenyl-9-methoxycarbonyl) (Fmoc) with self-assembly being driven by  $\pi$ -stacking and hydrogen bonding. The fibres were self-assembled nanostructures and, for a well-chosen dipeptide sequence, remained stable in the presence of added salt or when the temperature was raised. Curiously, using the tri-peptide sequence Fmoc-FFF it was possible to stabilize water droplets in chloroform, demonstrating the importance of the hydrophobicity of the fibres.<sup>5</sup> Unprotected tripeptide emulsifiers divided into two classes: those that self-assembled into fibres prior to adsorption and those that adsorbed to

<sup>a</sup>School of Physics and Astronomy, University of Edinburgh, James Clerk Maxwell Building, Peter Guthrie Tait Road, Edinburgh, EH9 3FD, UK.

E-mail: paul.clegg@ed.ac.uk

<sup>b</sup>School of Chemistry, College of Science and Engineering, University of Glasgow, Glasgow, G12 8QQ, UK




Org. Biomol. Chem., 2017, 15, 6342–6348 | 6343

and gelation times initially differed between ostensibly identical hydrogels prepared using the ultrasonic bath presumably due to the  $\pm 8$  °C variation in the bath temperature. For this reason, we established two temperatures ( $<35$  °C and 50 °C) for dispersing the dipeptide. The rate of dipeptide dispersion (unsurprisingly) and the subsequent gelation time (unexpectedly) was found to be faster for the hydrogels prepared at 50 °C compared to those prepared at  $<35$  °C. Our final protocol was to place the sample in an ultrasonic bath (at a controlled temperature) for 0.5 h until a translucent slightly viscous solution was formed, Fig. 1b.

By leaving dispersions (prepared using either ultrasound or a magnetic stirrer) to stand for 24 hours at a room temperature (22 °C), we found that self-supported gels, able to pass the inversion vial test, sometimes formed (see Fig. 1c and d). Structural transitions, linked to increases in viscosity, have been observed before in 2NapFF dispersions which have been warmed in the temperature range of our bath (albeit at higher concentration). These changes in organization can then become trapped.<sup>22</sup> We suggest that we might be seeing similar behaviour here. To avoid this, all of our hydrogels were prepared by the addition of salt within 5 minutes of removal from the ultrasound bath. Figures 1e and f demonstrate how the temperature of the ultrasound bath influences the speed of subsequent behaviour. Dipeptide dispersed at 50 °C has begun to gel within two minutes of the addition of salt. Typical hydrogels for two different concentrations of  $\text{MgSO}_4$  are shown in Fig. 1g and h.

The evolution of shear modulus was measured (see Experimental section) as a function of time to study the strength of hydrogels prepared at 18 mM and 142 mM  $\text{MgSO}_4$  (Fig. 1i).  $G'$  and  $G''$  of hydrogels with high salt concentration rise faster than hydrogels with low salt concentration within the first 10 000 seconds. At this point,  $G'$  and  $G''$  of hydrogels with high salt concentration hardly increase, reaching their maximum at 6 kPa for  $G'$  after a few thousand seconds, while  $G'$  and  $G''$  of low salt concentration hydrogels continue to increase even after 63 000 seconds. Salt induced gelators which become weaker at higher salt concentration have been seen previously. The strength of a hydrogel prepared at 0.5 wt% of 2NapFF and  $\text{Ca}^{2+}$  salt was found to reach its maximum value at a concentration of 2 : 1  $\text{Ca}^{2+}$  to dipeptide. Increasing further the concentration of  $\text{Ca}^{2+}$  resulted in weaker gels.<sup>16</sup>

Fig. 2a and c shows foams formed from dispersions prepared at  $<35$  °C which were gelled with 18 mM and 142 mM  $\text{MgSO}_4$ , respectively. The formation method is described in the Experimental section. Foams with low salt concentration (Fig. 2a) resulted in higher-quality foams with small average bubble size and a higher volume of liquid entrained in the foam compared to those prepared at a high salt concentration (Fig. 2c). The bubble size is often related to foam stability due to the enhanced buoyancy of large bubbles; however, in this case we find that after 0.5 h it is the foam with smaller bubbles that has collapsed more, Fig. 2b and d. Evidently, while these hydrogels provide a good environment for creating bubbles the interfacial layer and sparse bulk gel are unable to

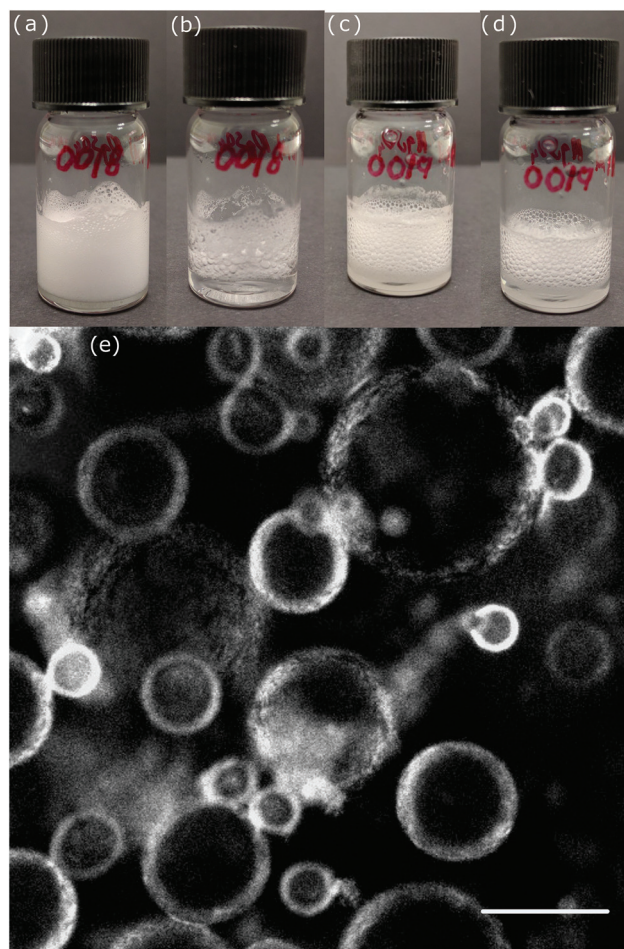

**Fig. 2** Illustrates fresh foams (a, c) and foams after 0.5 hours (b, d) prepared from 2 mM 2NapFF and dispersed at  $<35$  °C; (a, b) 18 mM  $\text{MgSO}_4$  and (c, d) 142 mM  $\text{MgSO}_4$ . (e) Shows a confocal micrograph of a fresh foam prepared at 2 mM 2NapFF, 142 mM,  $\text{MgSO}_4$  and dispersed at 50 °C. Dipeptides are dyed using Nile Blue; scale bar 100  $\mu\text{m}$ .

prevent rapid coalescence. This is especially true with small bubbles which consume a greater proportion of fibres as the interfacial layer.


Fluorescence confocal microscopy was carried out to try to understand the foam performance. Fig. 2e shows the organization of a fresh foam prepared at 142 mM  $\text{MgSO}_4$  and 50 °C. The nanofibers prefer to adsorb at the air/aqueous interface (similar to ref. 23) rather than being dispersed in the continuous phase, Fig. 2e. However, over the next hour hydrogel begins to emerge between bubbles. This is very much reminiscent of the foams reported in ref. 7 which were created at significantly higher dipeptide concentration and gelled using  $\text{CaCl}_2$ . In that work, the hydrogel initially formed on the bubble interfaces but then steadily appeared between the bubbles but now over a timescale of days rather than tens of minutes. At our very low concentrations of the dipeptide the foam lifetime is only two hours, indicating that the remnant hydrogel between the bubbles is now too weak to prevent coalescence and ripening.






Emulsions with four different oils (isopropyl myristate, silicone oil, dodecane, octanol) were prepared in a similar manner to the foams described above. Three out of four emulsions remained stable for months (Fig. 4a,c and e). Isopropyl myristate emulsions (Fig. 4a) appeared the most ideal in that there was no creaming. At the other end of the range, octanol emulsions (Fig. 4g) could not be stabilised, phase separating immediately after preparation. Indeed it appears that the

It is tempting to consider the role of the interfacial dipeptide fibres to be similar to the interfacial particles in a Pickering emulsion.<sup>24</sup> Under this scenario, whether the dipeptide fibres become trapped at the interface depends on their wettability by the two fluid phases. To explore this idea we have carried out an experiment to observe the wetting behaviour of the oils† at an interface between the hydrogel and an aqueous phase of the same salt concentration, Fig. 5a. If the hydrogel surface was precisely horizontal and reasonably flat we would be able to use the angle with which the droplet or bubble meets the hydrogel surface (measured through the aqueous phase) as a quantitative measurement of the wettability of the hydrogel. Unfortunately, since the surface is somewhat rough it is not possible to be quantitative. The air and the dodecane appear to make approximately similar (small) angles to the hydrogel surface (Fig. 5c and d). This suggests that in both cases the hydrogel greatly prefers contact with the aqueous phase over contact with the droplet/bubble. By contrast, isopropyl myristate makes a more gentle angle with the surface of the gel, Fig. 5b. The preference of the hydrogel for contact with the aqueous phase is significantly less marked, this is consistent with the formation of a stable emulsion. If the behaviour of octanol, described above, was because of the wetting characteristics of this oil at a hydrogel surface then we would expect to see the droplet spread out to maximize the contact area with the hydrogel. This would be reflected in a large three phase contact angle. What we see, Fig. 5e, is a quite standard contact angle as though the octanol only partially wets the hydrogel. Evidently, the behaviour of

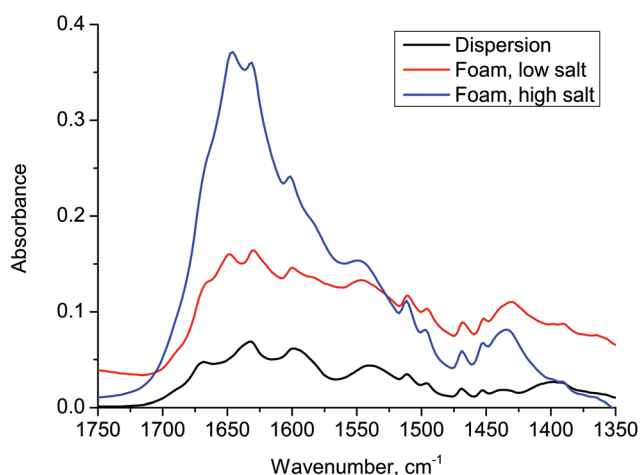

† We have not considered the behaviour of the silicone oil because it is density matched with the aqueous phase and hence does not rise to meet the hydrogel interface.

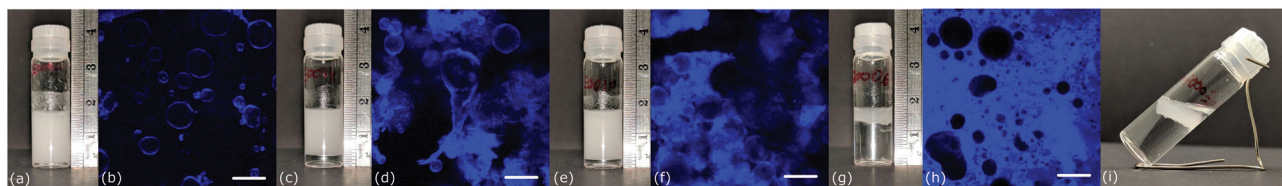

**Fig. 4** Shows the macroscopic and microscopic characteristics of four emulsions prepared at 2 mM 2NapFF, 18 mM  $\text{MgSO}_4$  at 50 °C; in the confocal micrographs the dipeptide has been dyed using Nile blue and the scale bar is 100  $\mu\text{m}$ . The oil is (a, b) isopropyl myristate; (c, d) silicone oil; (e, f) dodecane; (g, h) octanol. (i) Shows the octanol sample tipped to one side, indicating that there is a light solid plug floating on a bath of aqueous phase.



**Fig. 5** (a) The experimental apparatus used to evaluate the wetting characteristics of droplets and bubbles. The hydrogel is visible via the Nile blue dye; scale bar 18 mm. Droplets/bubbles of (b) isopropyl myristate (c) air (d) dodecane (e) octanol.

this system does not fit easily within the Pickering emulsion picture. We note that the droplet is becoming darker, which might point to more complex changes taking place.

## Conclusions

Following previous studies stabilizing emulsions and foams using dipeptide hydrogels, we have investigated the behaviour of one dipeptide system at low concentration with the gelation induced by the addition of salt. We have presented a route to achieving repeatable gel formation based on the dipeptide 2NapFF and using the salt  $\text{MgSO}_4$ . Using this gel system we have demonstrated that foams become less stable at low dipeptide concentration. The fibre behaviour is found to be closely similar to that at higher concentrations but evidently the gel structure is now too weak. By contrast, we have been able to form long lived emulsions using three out of the four oil phases that we have tested. Here the droplets could be stabilized by an interfacial film (isopropyl myristate) or by hydrogel both in the aqueous phase and on the interface (dodecane and silicone oil). The oil which could not be emulsified in this way (octanol) could not be described simply using the wetting characteristics of the hydrogel. This observation warns against a simple comparison between the behavior of these self-assembled fibres and the particulate emulsifiers used in Pickering emulsions. The new process, not observed in Pickering emulsions, is that some components partition into the oil phase but apparently not the intact fibres which are preferentially wet by the aqueous phase.

## Experimental

### Hydrogel preparation

2NapFF was synthesised as described previously.<sup>25</sup> All chemicals were purchased from Sigma-Aldrich and Fisher Chemicals and used as received. Vials and instruments were cleaned with hexane, followed by methanol and rinsed with ultra pure water before use. An equimolar quantity of NaOH (1 M, aq) was added to millipore water (resistivity = 18.2  $\text{M}\Omega\text{ cm}$ ) to give a basic solution ( $\text{pH } 11 \pm 0.5$ ). Then 2 mM 2NapFF was added and the mixture was dispersed. Ultimately this was carried out using an ultrasound bath (VWR model USC 300 T with power 80 W). The pH was  $11 \pm 0.5$  measured with a Seven Easy pH probe (Mettler Toledo AG).

Gelation was triggered by adding  $\text{MgSO}_4 \cdot 7\text{H}_2\text{O}$  or  $\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$  aliquots on top of the translucent dispersion. The form of addition matters. By adding the salt already dissolved,



Following gelation, additional salt solution was added above the hydrogel. This two-phase cell was then inverted with the use of a petri dish. A droplet of oil or a bubble of air was added using a syringe with a U-shaped needle, Fig. 5a.

## Acknowledgements

We are grateful to the BBSRC for funding *via* grant BB/M027597/1. DA thanks the EPSRC for a Fellowship (EP/L021978/1).

## References

- 1 S. Damodaran, *J. Food Sci.*, 2005, **70**, R54–R66.
- 2 G. G. Scott, P. J. McKnight, T. Tuttle and R. V. Uljin, *Adv. Mater.*, 2016, **28**, 1381–1386.
- 3 A. F. Dexter, A. S. Malcolm and A. P. J. Middelberg, *Nat. Mater.*, 2006, **5**, 502–506.
- 4 A. F. Dexter and A. P. J. Middelberg, *J. Phys. Chem. C*, 2007, **111**, 10484–10492.
- 5 S. Bai, C. Pappas, S. Debnath, P. W. Frederix, J. Leckie, S. Fleming and R. V. Uljin, *ACS Nano*, 2014, **8**, 7005–7013.
- 6 T. Li, M. Kalloudis, A. Z. Cardoso, D. J. Adams and P. S. Clegg, *Langmuir*, 2014, **30**, 13854–13860.
- 7 T. Li, F. Nudelman, J. W. Tavacoli, H. Vass, D. J. Adams, A. Lips and P. S. Clegg, *Adv. Mater. Interfaces*, 2016, **3**, 1500601.
- 8 I. P. Moreira, I. R. Sasselli, D. A. Cannon, M. Hughes, D. A. Lamprou, T. Tuttle and R. V. Uljin, *Soft Matter*, 2016, **12**, 2623–2631.
- 9 S. Mondal, M. Varenik, D. N. Bloch, Y. Atsmon-Raz, G. Jacoby, L. Adler-Abramovich, L. J. Shimon, R. Beck, Y. Miller, O. Regev and E. Gazit, *Nat. Commun.*, 2017, **8**, 14018.
- 10 J. T. Russell, Y. Lin, A. Böker, L. Su, P. Carl, H. Zettl, J. He, K. Sill, R. Tangirala, T. Emrick, K. Littrell, P. Thiyagarajan, D. Cookson, A. Fery, Q. Wang and T. P. Russell, *Angew. Chem., Int. Ed.*, 2005, **44**, 2420–2426.
- 11 L. Isa, J.-M. Jung and R. Mezzenga, *Soft Matter*, 2011, **7**, 8127.
- 12 A. Ye, X. Zhu and H. Singh, *Langmuir*, 2013, **29**, 14403–14410.
- 13 M. Sarker, N. Tomczak and S. Lim, *ACS Appl. Mater. Interfaces*, 2017, **9**, 11193–11201.
- 14 Z. Gao, J. Zhao, Y. Huang, X. Yao, K. Zhang, Y. Fang, K. Nishinari, G. O. Phillips, F. Jiang and H. Yang, *LWT–Food Sci. Technol.*, 2017, **76**, 1–8.
- 15 Y. Nishida, A. Tanaka, S. Yamamoto, Y. Tominaga, N. Kunikata, M. Mizuhata and T. Maruyama, *Angew. Chem., Int. Ed.*, 2017, DOI: 10.1002/anie.201704731.
- 16 L. Chen, G. Pont, K. Morris, G. Lotze, A. Squires, L. C. Serpell and D. J. Adams, *Chem. Commun.*, 2011, **47**, 12071–12073.

## Confocal microscopy

The measurements were carried out by using a Zeiss AxioObserver.Z1 inverted microscope and a Zeiss LSM 700 scanning system 9 with a 20× (0.40 NA) objective. Nile Blue at a concentration of 0.55 mM was used to label the dipeptides; this was excited using a 633 nm semiconductor laser.

## FTIR

IR spectra were measured using a Smiths Illuminat IR module coupled to a Renishaw inVia Raman microscope. Each spectrum was scanned between 4000 and 650  $\text{cm}^{-1}$  at a resolution of 2  $\text{cm}^{-1}$  and corrected for the influence of the optics and the substrate.

### Contact angle

The hydrogel (blue) was created, using our standard protocol, in the base of a sample vial in the presence of Nile blue dye.

- 17 A. Z. Cardoso, L. L. E. Mears, B. N. Cattoz, P. C. Griffiths, R. Schweins and D. J. Adams, *Soft Matter*, 2016, **12**, 3612–3621.
- 18 C. Colquhoun, E. Draper, R. Schweins, M. Marcello, L. Serpell, D. Vadukul and D. Adams, *Soft Matter*, 2017, **13**, 1914–1919.
- 19 J. Shi, Y. Gao, Y. Zhang, Y. Pan and B. Xu, *Langmuir*, 2011, **27**, 14425–14431.
- 20 L. Chen, T. O. McDonald and D. J. Adams, *RSC Adv.*, 2013, **3**, 8714.
- 21 D. J. Adams, E. Draper, H. Su, C. Brasnett, R. Poole, S. Rogers, H. Cui and A. Seddon, *Angew. Chem., Int. Ed.*, 2017, DOI: 10.1002/anie.201705604.
- 22 A. Z. Cardoso, Personal Communication.
- 23 R. G. Alargova, D. S. Warhadpande, V. N. Paunov and O. D. Velev, *Langmuir*, 2004, **20**, 10371–10374.
- 24 B. P. Binks, *Curr. Opin. Colloid Interface Sci.*, 2002, **7**, 21–41.
- 25 L. Chen, S. Revel, K. Morris, L. C. Serpell and D. J. Adams, *Langmuir*, 2010, **26**, 13466–13471.

