



Cite this: *RSC Adv.*, 2018, 8, 25065

Design of diverse nanostructures by hydrothermal and microemulsion routes for electrochemical water splitting

Anirban Das and Ashok Kumar Ganguli *

Hydrothermal and microemulsion methods are low temperature methods used to obtain nanostructures of definite morphologies, sizes, facet termination and other structural features which result in the corresponding unique response to chemical, electrochemical or photochemical stimuli. An efficient catalyst to electrochemically split water to produce hydrogen and oxygen is of scientific, economic and societal relevance, especially due to the abundance of the starting material, water, and due to the product hydrogen, which is an ideal fuel, due to its highest mass density and clean combustion in air. In this review we focus on the hydrogen evolution reaction, HER, and the oxygen evolution reaction, OER, activity of the electrocatalysts produced by hydrothermal or microemulsion methods. The variation in electrochemical response resulting from the unique shape, composition and nano-architecture is discussed. Broadly, the catalysts were categorized as binary and ternary metal alloys as well as metal chalcogenides and oxides. This compilation would aid in the design of more effective water splitting electrocatalysts as well as in the selection of appropriate candidates for advanced mechanistic studies.

Received 15th May 2018

Accepted 5th July 2018

DOI: 10.1039/c8ra04133d

rsc.li/rsc-advances

1. Introduction

Fabrication of novel nanomaterials with programmable organization of nanoscale building blocks is a fundamental vision of nanotechnology. These functional nanomaterials show shape


and size dependent properties,^{1–4} thus it is imperative to develop synthetic methodologies which can precisely control the structural details of nanomaterials. Hydrothermal and microemulsion methods are two very useful techniques as these allow directed syntheses of nano-sized materials. The directed syntheses aid in obtaining definite geometries, surface termination, crystallinity, and new nanoscale physical properties which in turn influence the chemical properties and thus

Department of Chemistry, Indian Institute of Technology, Hauz Khas, New Delhi 110016, India. E-mail: ashokganguliitd@gmail.com; ashok@chemistry.iitd.ernet.ac.in



Dr Anirban Das obtained a BSc (Chemistry Honours) degree from Delhi University, India, an MS (Chemistry) from the University of Toledo, Ohio (Prof. Mark Mason, 2007) and a PhD (Inorganic Chemistry) from the University of Idaho (Prof. Chien Wai, 2012). Thereafter, he held postdoctoral positions at Northwestern University (Prof. Eric Weitz, 2012–2014), University of California (Prof. Francisco


Zaera, 2014–2015) and at the Wayne State University (Prof. Eranda Nikolla 2015–2017). Currently he is a CSIR Pool Scientist at IIT Delhi, India working with Prof. Ashok Kumar. Ganguli. His current interests include development of photo and electrocatalysts for water splitting applications.

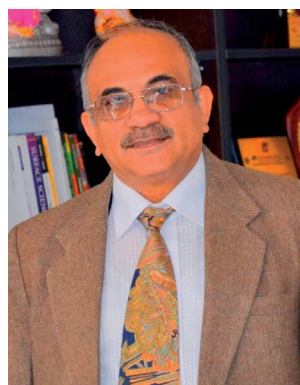

Dr Ganguli is a Professor of Chemistry at IIT Delhi and also the founding Director of the Institute of Nano Science and Technology in Mohali, Punjab. His areas of interest are in the design of nanostructured materials for several applications and also high temperature superconductivity. He has published more than 250 papers and filed five patents. He is a recipient of several awards

including the National Award of Nano Science and Nanotechnology given by DST, Government of India and also a fellow of various science academies. Dr Ganguli is very passionate for promoting education in schools and colleges in underprivileged areas.




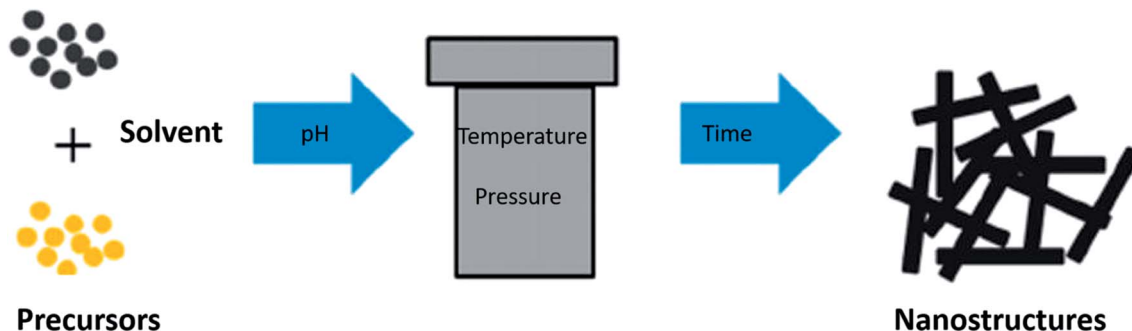

Scheme 1 The general process involved in a hydrothermal synthesis.

catalytic performance. The main advantage of the hydrothermal method is that it allows the synthesis at lower temperatures than the traditional high temperature routes and at times allows stabilization of metastable phases. It allows for direct crystallization of multi-element oxides without the need for annealing at elevated temperature to induce crystallization.^{5–8} The general process involved in a hydrothermal synthesis is depicted in Scheme 1. Microemulsions containing reverse micelles can be used effectively for the synthesis of nanoparticles of controlled size and structure, where the synthesis of nanoparticles occurs inside the volume defined by water droplets. Reverse micelles have been used for the synthesis of a variety of nanoparticles including metal nanoparticles, alloys, semiconducting oxides, and chalcogenides to exploit among


others their optical, magnetic and catalytic properties.^{9–12} The shape of the nanoparticles inside the reverse micellar system can be altered by modulating the parameters affecting (a) film rigidity of reverse micelles and (b) kinetics of crystal growth in the constrained environment. The reverse micellar film rigidity can be controlled^{13,14} by the following parameters: (i) water-to-surfactant molar ratio (W_0), (ii) intermicellar exchange rate, (iii) nature of the bulk organic solvent, (iv) nature of the surfactant and co-surfactant, and (v) packing parameter. The general process involved in a reverse microemulsion synthesis is depicted in Scheme 2.¹⁵ Our group has been working extensively for more than a decade, to understand the role of various parameters of microemulsions which matter in the tailored synthesis of nanostructures.^{16–21}

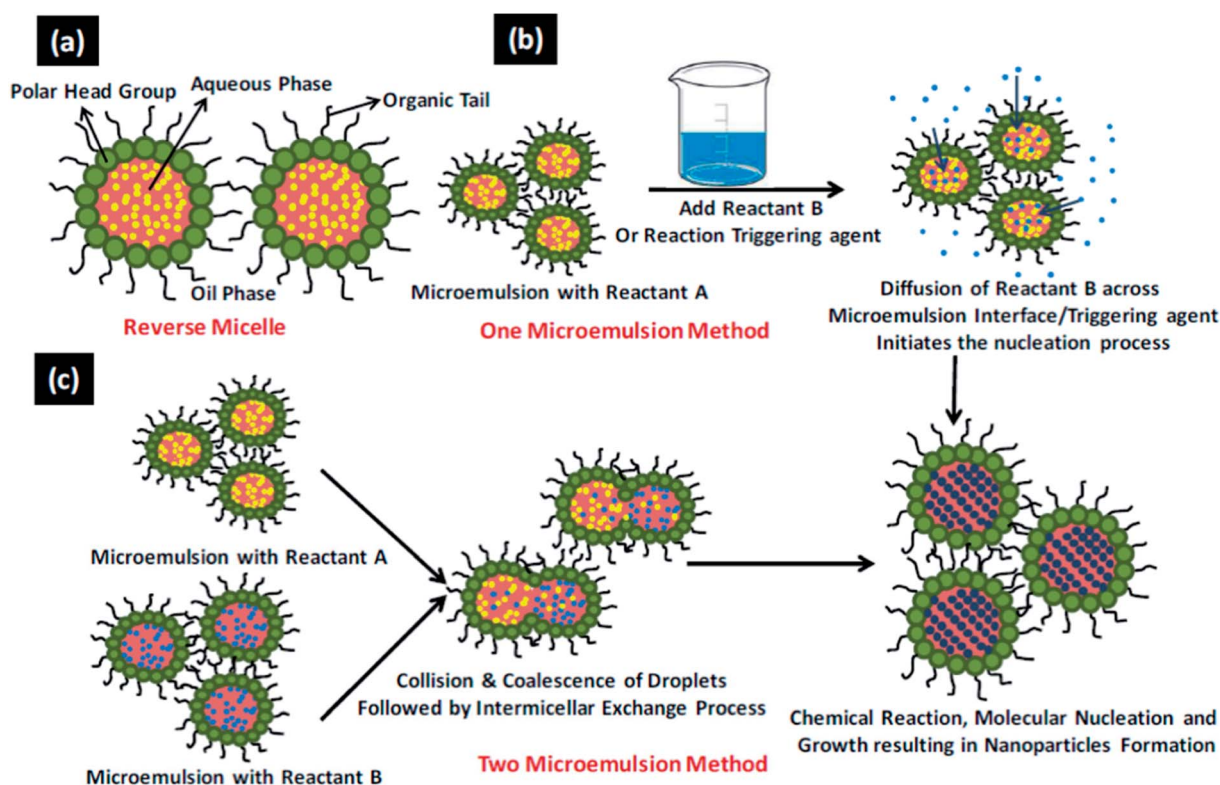



Scheme 2 ¹⁵The general process involved in a reversed microemulsion method. (a) A reverse micellar system (b) one microemulsion method and (c) two microemulsion method. Reproduced from ref. 15 with permission from the Royal Society of Chemistry.



Water splitting is the process of catalytic conversion of liquid water to gaseous oxygen and hydrogen. It is the one of the most widely studied electrocatalytic reactions²² and often used as a benchmark to evaluate different electrocatalysts. The overall reaction of water splitting is (eqn (1)):



Thermodynamically, this reaction is up-hill and non-spontaneous process. The minimum energy required to split one water molecule is 2.46 eV ($\Delta G = 237 \text{ kJ mol}^{-1}$). As overall it is a 2e process, the minimum potential required to split water is 1.23 V. However, experimentally, most of the electrolyzers require a potential greater than this to overcome the electrokinetic barrier of the electrode. Electrochemical water splitting takes place *via* two half reaction: oxygen evolution reaction (OER) on anode and hydrogen evolution reaction (HER) on cathode (eqn (2) and (3)).



The water oxidation is a 4e⁻ transfer process and thus is kinetically sluggish with a minimum required potential of 1.23 V (*vs.* NHE), while HER, a 2e process is kinetically and thermodynamically facile (0 V *vs.* NHE). The overall water splitting is energy driven and this energy may be derived from solar/light energy (photocatalytic process) or electrical energy (electrochemical process) or combination of both solar and electrical energy (photoelectrochemical PEC process). The efficiency of an electrocatalyst for OER or HER may be evaluated on the basis of the many electrocatalytic kinetic parameters such as overpotential (η), exchange current density (i_0) and (*c*) Tafel slope. When an electrochemical reaction proceeds on application of a reasonable potential, it is kinetically controlled. Apart from the required thermodynamic potential, in practice an additional potential to overcome the kinetic factors such as ion mobility (diffusion), circuit resistance and entropy. This excess potential required is termed the overpotential. The intrinsic rate of electron transfer between an analyte in solution and the electrode is reflected by the exchange current density. Thus, the effectiveness of a catalyst for a given electrochemical reaction under a given set of conditions can be quantified. Tafel slopes (*b*) are derived from the linear portion of the graph of overpotential *versus* the logarithm of the current density for a particular electrocatalyst catalyzing a particular reaction. Thus, it quantifies the change in electrocatalytic performance of an electrocatalyst over a given potential range. Catalysts with smaller values of the slopes need smaller increments of overpotential to give higher current density, thus making them more effective. While comparing different catalysts, in general, ones with higher i_0 at lower η and a smaller value of *b* are said to be more active though other factors such as stability under operating conditions and the tendency of the constituent metals to get oxidized at higher η has also to be considered. Currently, the benchmark catalyst(s) for HER is Pt/C and for

OER they are IrO₂ and RuO₂. However, Pt/C performs best in acidic medium and has limited OER in alkaline medium. Additionally, IrO₂ and RuO₂ perform excellent as catalysts for OER in alkaline media in which they have poor HER activity. Research is ongoing to (a) find cheaper alternatives to the currently used precious metal based catalyst for these processes (b) more versatile catalysts *e.g.* the same catalyst being able to perform multiple transformations like HER and ORR (oxygen reduction reaction), HER and OER and (c) more robust catalysts in terms of stability under acidic or basic conditions.

Our group has produced several classes of inorganic materials, synthesized by hydrothermal or microemulsion routes that demonstrated electrocatalytic water splitting, OER or HER activity. This included (a) metal nanoparticles (b) bimetallic alloy nanoparticles of Co, Ni Fe and Cu (c) ternary alloy nanoparticles (d) metal cobaltites and manganites as well as (e) metal chalcogenide based composites. The catalysts were adequately characterized and their electrocatalytic activity was evaluated by the usual techniques. In the following sections we shall briefly describe our work and comprehensively review the reports of catalysts of similar nature that have been synthesized by microemulsion and hydrothermal routes and have demonstrated electrocatalytic water splitting, OER and HER activity.

2. Hydrogen and oxygen evolution (HER and OER) activity of electrocatalysts prepared by hydrothermal and microemulsion methods

Hydrothermal methods have been used to modify the properties of nanostructures as well as synthesize nanostructures with unique shapes, sizes, morphology and other physical and chemical properties that have shown better electrochemical performance. For *e.g.* the hydrothermal treatment was used to improve the electrochemical activity of surface oxidized MWCNT for OER, HER and ORR (Fig. 1).²³ The oxygen content was not appreciably reduced and the significance of this treatment is that this is relatively mild as compared to the high temperature methods. Hydrothermal treatment resulted in enhanced surface hydrophilicity, tuning of the oxygen functional group composition and reduction in defective sites and thus subsequently improvement of electrical conductivity of the MWCNT. This was attributed to increase in C=O containing functional groups which have stronger electron withdrawing abilities.

The microemulsion technique, as discussed above is also another widely reported low temperature method used to engineer the morphology, shape, size and such physical characteristics of the nanostructures. These variations in morphology and other physical characteristics have been shown to deeply influence the electrochemical response of these nanostructures. Our group reported the microemulsion synthesis of nanocrystalline Cu nanoparticles of varying morphology²⁴ and evaluated their HER and OER performance.



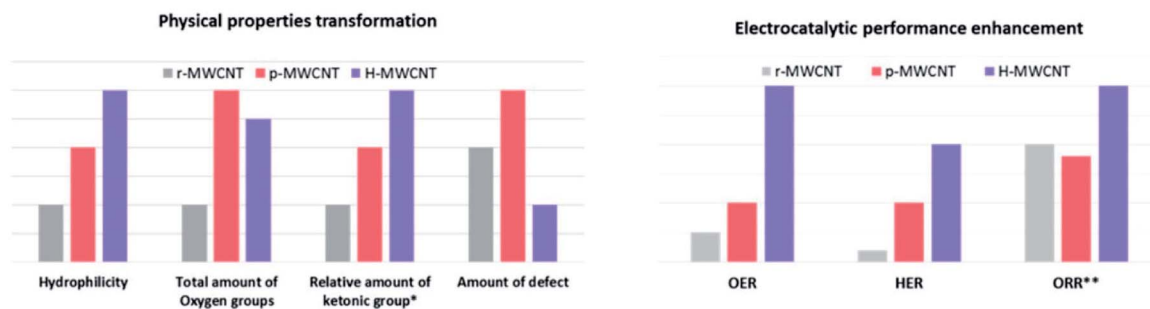


Fig. 1 Enhancement of electrocatalytic property and modification of physical properties by hydrothermal treatment.²³ Reprinted with permission from *ACS Appl. Mater. Interfaces*, 2016, 8(51), 35513–35522. Copyright 2016 American Chemical Society.

Nanocubes (~50 nm) nanorods (diameter of ~3 nm and length of ~50 nm) and nanospheres (5 nm) were synthesized and subsequently reduced at 400 °C in a hydrogen atmosphere. It was observed that the cube-shaped nanoparticles show significantly higher hydrogen and oxygen evolution efficiencies as compared to the nanorods and spherical nanoparticles. The nanospheres show better hydrogen and oxygen evolution efficiencies than the nanorods, though from the similar Tafel slopes (−0.16 mV per decade to −0.25 mV per decade) it was inferred that the mechanism of electron transfer is same for all morphologies. HER reactions were carried out in 0.1 M Cl[−] while OER were carried out in 0.1 M KOH. We also reported the synthesis of Cu nanoparticles from Cu-oxalate precursors synthesized by microemulsion techniques.²⁵ HER and OER experiments were carried out in alkaline medium. In the case of HER the current densities were found to be 12 mA cm^{−2} (over glassy carbon electrode) and 46 mA cm^{−2} (over Pt electrode) which were significantly higher than previously reported values (maximum 1 mA cm^{−2}). For OER, the current density was found to be 1.6 mA cm^{−2} (that was slightly higher) for the glassy carbon electrode and 15 mA cm^{−2} for Pt as the working electrode, values that were 4–30 times higher than earlier reports. The high efficiency was thought to be related to the high surface area (34 m² g^{−1}) of these crystalline Cu nanoparticles. Additionally, these particles show good stability as electrocatalysts and retain their activity after even 50 cycles.

2.1 Binary alloys

Our group reported the synthesis of Cu–Co core–shell nanoparticles²⁶ by microemulsion methods and evaluated the

electrochemical activity of these particles by means of HER by splitting water. Electrochemical studies of these nanocrystalline Cu–Co alloy particles indicate higher HER efficiencies (~5 times) compared to bulk (micrometer-sized) Cu–Co alloy particles. We also reported that binary Fe–Co nanoparticles show significant enhancement of electrocatalytic activity as compared to bulk alloys.²⁷ The microemulsion based synthesis of these alloys was reported for the first time and various alloys of the composition Fe₇₅Co₂₅, Fe₆₇Co₃₃, Fe₅₀Co₅₀, and Fe₃₃Co₆₇ with an average size of 20, 25, 10, and 40 nm, respectively, were obtained. Nanoparticles of the alloy with composition Fe₃₃Co₆₇ exhibit the highest hydrogen and oxygen evolution efficiencies (~100 times higher) as compared to other Fe–Co alloys in nanocrystalline or in bulk form (Fig. 2). It was postulated that this composition performs best due to the higher concentration of Co, which was reported to be a better electrocatalyst. NiTe nanostructures anchored on three-dimensional nickel foam were synthesized using the microemulsion method were reported as high-performance catalyst for electrochemical water oxidation by Li *et al.*²⁸ The high efficiency was attributed to the 2D NiTe ultrathin nanosheets which have large number of exposed active sites and 3D hierarchical porous structure.

2.2 Ternary alloys

Our group has reported the HER activity of two ternary alloy catalysts^{17,29} both prepared by the microemulsion method. Cu–Fe–Ni ternary alloy²⁹ nanoparticles of varying compositions (1 : 1 : 1, 1 : 2 : 1 and 1 : 1 : 2) and sizes (55–80 nm) were prepared using CTAB as the surfactant, 1-butanol as co surfactant and iso-octane as the oil phase. When these nanostructured alloys were evaluated



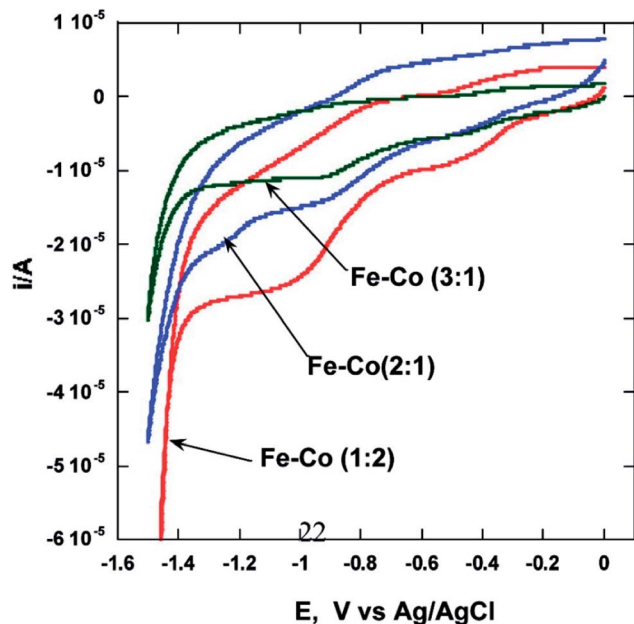


Fig. 2 Cyclic voltammograms showing the effect²⁷ of composition on the electrocatalytic properties of Fe–Co alloys. Reprinted with permission from *J. Phys. Chem. C*, 2010, 114(44), 18779–18784. Copyright 2010 American Chemical Society.

for HER in a basic medium a very high current density of 228 mA cm⁻² at an overpotential of 545 mV with an onset of -267 mV was achieved for the 1 : 1 : 1 alloy. Two metals, one with weak M–H binding affinity (Fe) and the other with strong M–H binding affinity (Cu) were alloyed with Ni, which is the most appropriate choice for a low cost catalyst for HER. Spherical Cu–Co–Ni alloy nanoparticles¹⁷ of composition, 1 : 1 : 1, 1 : 1 : 2 and 1 : 2 : 1 were synthesized by reverse micellar method. These were evaluated for HER activity in the acidic medium with the 1 : 1 : 1 composition demonstrating the best performance exhibiting a low onset overpotential (257 mV) and a small Tafel slope (102 mV dec⁻¹) at current densities of -10 mA cm⁻². The catalyst was stable for over 500 cycles. Xie *et al.*³⁰ performed hydrothermal sulfurization on the surface of AgCuZn alloy to obtain AgCuZn sulfide nanoparticles, which on electrochemical treatment resulted in CuO–Ag₂O nanowire arrays on the alloy surface. The composites were reported to be efficient and stable electrocatalysts for water splitting OER reactions. An Au based alloy, AuCuCo prepared hydrothermally³¹ was reported to exhibit comparable electrocatalytic activity and better stability towards OER in alkaline media as compared to commercial Pt/C and IrO₂/C catalyst. Additionally, this catalyst was active for ORR too. The improved electrocatalytic activity of AuCuCo was attributed to its unique three-dimensional structure, the abundance of twin crystals, and change in the electronic structure of Au by alloying. However, the exact reasons for better performance at this juncture requires further studies for a complete understanding.

2.3 Metal chalcogenides and supported metal chalcogenides

The most studied material for electrochemical applications that falls in this category is MoS₂. Our group reported MoS₂

functionalized Mo₂N nanostructures.³² The MoS₂ nanosheets were prepared by hydrothermal methods. Additionally, different morphologies of Mo₂N (hexagonal, triangular and nanowires) were also synthesized by hydrothermal methods. HER activity of the composites (MoS₂–Mo₂N) were evaluated in an acidic medium and it was determined that the presence of interfaces and junctions contributed significantly to the electrocatalytic activity as evident from the low charge transfer resistance. It was also demonstrated that the HER activity of the Mo₂N–MoS₂ composites is superior as compared to the bare MoS₂ and Mo₂N nanostructures. Additionally the triangular composites had the best electrochemical response (Fig. 3).

A Co doped 2H–MoS₂ ultrathin nanomesh with high defect concentration and large porosity was demonstrated to improve the electrochemical performance for HER.³³ A 3D reduced graphene oxide (RGO) scaffold acted as channels for fast electron and ion transport. This 3D defect-rich MoS₂ nanomesh/RGO foam can be easily obtained through a one-pot cobalt acetate/graphene oxide (GO) co-assisted hydrothermal reaction, in which GO, Co and acetate ions are co-morphology-controlling agents and defect inducers. The experimental studies were complemented by DFT calculations that indicate that the defects result in formation of Co–Mo–S structures, thus releasing inert basal planes to active sites. Layer expanded MoS₂ nanosheets/carbon fiber nanocomposites were synthesized by the hydrothermal method by an *in situ* reduction of ammonium tetrathiomolybdate on carbon fibers and evaluated for HER.³⁴ The HER studies show that the composites with Mo/C molar ratio of 0.04 has the highest catalytic activity with the lowest overpotential (131 mV vs. RHE) and the highest current density (10 mA cm⁻² at 200 mV vs. RHE). This was attributed to a balance between the number of exposed active edge sites of MoS₂ and fast transport paths for electrons provided by carbon fibers. EIS spectra indicate low charge transfer resistance indicating fast faradaic process and superior HER studies. Composites of graphene with amorphous transition-metal chalcogenides (MoS_x, WS_x) that were synthesized by hydrothermal techniques were reported as electrocatalysts for HER in acidic media.³⁵ MoS_x/graphene composites perform much superior to WS_x/graphene composites. This was attributed to the surface oxidation in the WS_x based composites, as inferred from XPS studies. The onset potential was close to the HER onset potential of industrially used platinum catalysts. MoS₂/Ni₃S₂ nanorod arrays aligned on Ni foam (Fig. 4) were demonstrated to function as electrodes for overall water splitting reaction.³⁶ The catalysts were stable and a high current density at low overpotential was achieved. To achieve current density of 10, 100, 200 and 300 mA cm⁻² in an electrolyzer, potentials of 1.467, 1.593, 1.640 and 1.661 are required. EIS studies indicate low charge transfer resistance indicating fast electron transport efficiency in the composite.

Li *et al.*³⁷ reported SnS₂ modified TiO₂ nanobelt based electrocatalysts which displayed significant enhancement of electrocatalytic properties w.r.t. OER. This performance was explained based on large contact area of the TiO₂ nanobelts and the stability of the SnS₂ nanosheets. Additionally, the exposed crystal facets of TiO₂ and the change in “valence bond



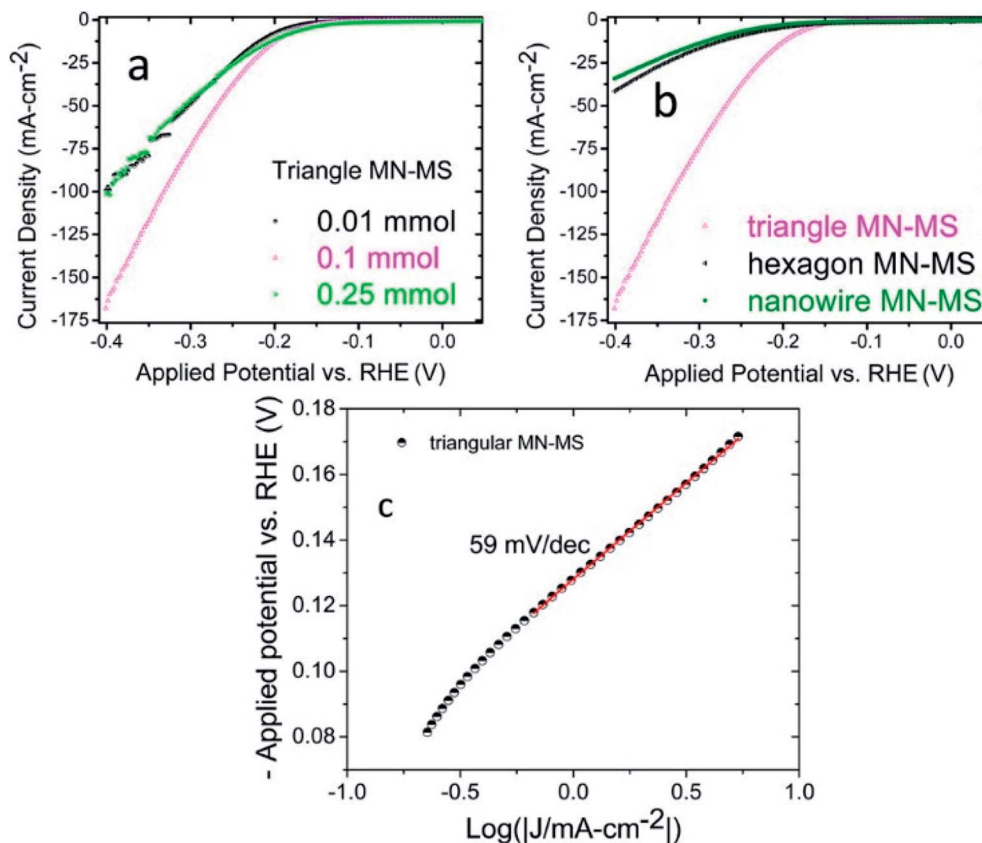


Fig. 3 (a) Linear sweep voltammetry graphs depicting the current densities of triangular MN–MS composites with various components of MoS₂ (b) LSV curves of Mo₂N–MoS₂ components with differing morphologies (c) Tafel plot obtained from the LSV curve of triangular MN–MS. A Tafel slope of 59 mV per decade is observed.³² Reprinted with permission from *ACS Appl. Mater. Interfaces*, 2017, 9(23), 19455–19461. Copyright 2017 American Chemical Society.

environment” due to formation of heterostructures was attributed to the electrochemical properties. An overpotential of 570 mV with a current density of 10 mA cm⁻² and a low Tafel slope of 107 mV per decade was reported. Nickel sulfide nanosheets directly grown on Ni foam were reported to be efficient and stable as electrocatalysts used for water reduction and oxidation in alkaline medium.³⁸ A hydrothermal-sulfurization method in Na₂S solution was used to obtain Ni₃S₄ nanosheets directly grown on Ni foam. For HER, only a low overpotential of -122 mV is needed to achieve a current density of 10 mA cm⁻² with a small Tafel slope of 69 mV dec⁻¹. For OER, it delivers a current density of 20 mA cm⁻² at the overpotential of 320 mV and a Tafel slope of 71 mV dec⁻¹. When used in an electrolyzer (catalyst acts as both an anode and cathode), for overall water splitting, a potential of 1.61 V was required to achieve a current density of 10 mA cm⁻²; while the corresponding potential required to achieve a current density of 20 mA cm⁻² was 1.67 V. The high electrocatalytic activity was attributed to the facile mass transport due to the unique 3D structure. Ni₃S₂/ball-milled silicon powder was prepared by hydrothermal techniques and was reported as a bi-functional electrocatalyst for HER and OER.³⁹ The catalyst was prepared by grafting heazlewoodite (Ni₃S₂) on the silicon powder ((Ni₃S₂/Si) – ball-milled and a control non-ball milled) silicon powder through

a hydrothermal process. The products were then etched using the HF solution to prepare the modified porous silicon based composites. These catalysts exhibited electrocatalytic activity towards both alkaline and acidic HER with Tafel slopes of 74 and 52 mV dec⁻¹ respectively. An electrocatalytic activity for the OER (in 1 M KOH) with an overpotential of 164 mV dec⁻¹ was reported. The catalyst with a porous structure and a ball milled support exhibited the highest efficiency. The use of this bifunctional catalyst in an overall water splitting electrolyzer was not discussed.

As mentioned earlier, most of the studies conducted usually deal with synthesis of new nanostructures and/or composites and evaluation of their activity towards OER or HER reaction. Thereafter, based on the activity, qualitative explanations based on interaction of the components of the composite or those based on surface area are used to explain the activity of the materials. It is essential to have a more focused study to understand the efficiency of a specific nanocomposite towards HER and OER reactions. Chia *et al.*⁴⁰ performed a detailed study on the role of the structural features of layered orthorhombic SnS as compared to hexagonal SnS₂ that led to higher inherent electro-activity in SnS₂. Three distinct cathodic signals were obtained in SnS₂ as opposed to a broad reduction peak in the largely electro-inactive SnS. Additionally, SnS₂ exhibits a faster



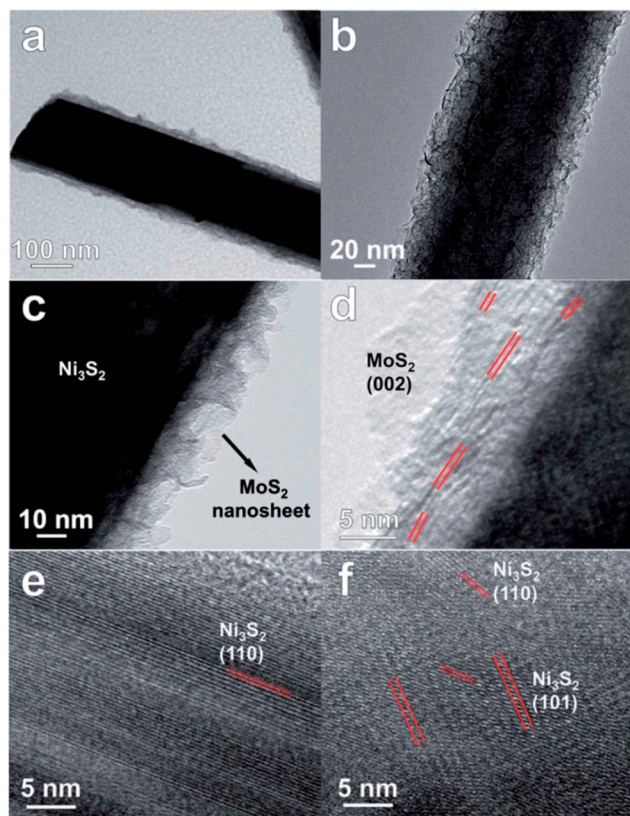


Fig. 4 (a–c) TEM and (d–f) HRTEM images of MoS₂/Ni₃S₂ nanorod arrays aligned on Ni foam. Reproduced from ref. 36 with permission from the Royal Society of Chemistry.

heterogeneous electron transfer (HET) rate than SnS. It may be mentioned though that both SnS and SnS₂ show much lower current density than the glassy carbon electrode. For the OER and ORR, these electrocatalysts do not perform well. However, both these catalysts perform very well as HER electrocatalysts, their performance surpassing the GC electrode. Amongst the two chalcogenides, SnS₂ has better performance for the HER. The difference in HER performance was investigated and explained by means of HER electrode kinetics and density functional theory (DFT) calculation. By means of electrochemical impedance spectroscopy (EIS), SnS₂ demonstrated a significantly faster HER kinetics than SnS. The DFT study unveiled that the high electrocatalytic performance of SnS₂ originated from the favorable ΔG_{H} at the S edges. ΔG_{H} of SnS at all edges are disadvantageous for HER. In another study,⁴¹ the absolute electronic energy levels have been investigated in AgInS₂ by varying the relative composition of the elements and crystallographic phases. These structures were synthesized using solvothermal methods and found to have a good electrocatalytic activity towards HER that were strongly dependent on the composition and the crystal structure of these nanocrystals. The monoclinic structures were found to be the most active as HER electrocatalyst, whereas cubic AgInS₂ was observed to be the least active of the studied crystallographic phases and compositions. The electrocatalytic activity of the monoclinic structures is almost comparable to the MoS₂-based

nanocrystals reported in the literature. From these studies it was understood that the Fermi level of these nanocrystals is an important factor for deciding the electrocatalytic efficiency. Ni-Fe sulfides supported on Ni foam (NF) were synthesized by a hydrothermal sulfurization method and reported as efficient catalysts for OER.⁴² NiFeS/NF exhibits an overpotential of 65 mV at 10 mA cm⁻², much lower than most Ni-based electrocatalysts. Additionally, at 100 mA cm⁻² the overpotential is 189 mV suggesting promising OER activity for large scale applications. However, the catalyst suffers from stability issues and to remedy the situation a layer of Fe was electrodeposited on this, which however resulted in lower performance.

Monoclinic Co₃Se₄ nanowire electrodes on cobalt foam (Co₃Se₄/CF) were synthesized by a hydrothermal method using selenourea and evaluated for OER.⁴³ In an electrolyzer where Co₃Se₄/CF acted both as a cathode and anode respectively for overall water splitting, a potential of 1.55 V was required for a current density of 10 mA cm⁻² while for a current density of 20 mA cm⁻² a potential of 1.63 V was required. Significantly, the electrolyzer operated at 10 mA cm⁻² for over 3500 h and at 100 mA cm⁻² for at least 2000 h without noticeable degradation.

2.4 Metal oxides

Our group has reported the electrocatalytic properties of nanostructured dimagnesium manganese oxide (Mg₂MnO₄ – spinel structure) obtained from metal oxalate precursors synthesized by a microemulsion route.⁴⁴ The anisotropy of the metal oxalate is retained in the oxide and rod shaped structures are obtained. These nanostructured Mg₂MnO₄ (Mn is in +IV state) are efficient anode materials for OER displaying a current density of 14 mA cm⁻² (vs. Ag/Ag⁺). The anodes are stable over at least 30 cycles of oxidation and reduction in an alkaline medium. Cobalt magnetites (Mn_xCo_{3-x}O₄, $x = 1$) based electrocatalysts was reported earlier by our group for water splitting applications.⁴⁵ These magnetites were synthesized by hydrothermal methods and two nanocrystalline phases, cubic Co₂MnO₄ and tetragonal CoMn₂O₄ were successfully synthesized by varying the stoichiometric ratio of Co and Mn salts. The cubic Co₂MnO₄ nanocubes displayed five times higher activity towards ORR than tetragonal CoMn₂O₄ nanocubes while the latter phase is a better electrocatalyst towards OER (Fig. 5). XPS analysis shows the presence of two types of O on the surface, (lattice O and surface adsorbed O) and the electrocatalytic activity can be correlated to the oxygen binding ability on the catalyst surface. Additionally, it was determined that Co(III) and Mn(III) dominated over Mn(IV).

Orthorhombic molybdenum oxide (α -MoO₃) nanobelts that were greater than 10 nm wide and less than 200 nm long were synthesized by hydrothermal methods.⁴⁶ These belts displayed satisfactory properties for HER reactions and their electrochemical performance (evaluated by means of Tafel plots) was ~ 1.7 times superior to the commercially available MoO₃. Co or Ru doped α -MnO₂ nanorods were produced by a continuous hydrothermal synthesis process (10 g h⁻¹) and were reported to be efficient catalysts for OER reactions.⁴⁷ DFT calculations complemented experimental studies to evaluate the role of the



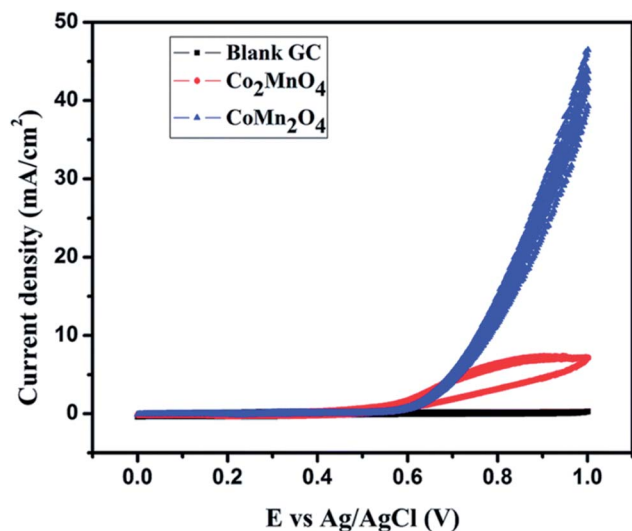


Fig. 5 ⁴⁵Cyclic voltammogram depicting OER activity of Co_2MnO_4 in 1 M KOH electrolyte. Reproduced from ref. 45 with permission from the Royal Society of Chemistry.

dopants on $\alpha\text{-MnO}_2$ support. The OER and ORR activity were found to be comparable to the commercially available RuO_2 and Pt/C catalysts. Ultrafine PtO_2 nanoparticles coupled with a Co(OH)F nanowire array on a TiO_2 mesh were prepared by hydrothermal techniques and were evaluated for electrochemical HER. ⁴⁸ This composite was reported to be highly active and durable for the HER in alkaline media (Fig. 6). This high efficiency has been attributed to a strong synergetic effect

between spatially separated ultrafine PtO_2 nanoparticles and Co(OH)F . The above hydrothermal process, wherein anion exchange of $[\text{PtCl}_6]^{2-}$ with OH^- leads to an *in situ* generation of PtO_2 nanoparticles on Co(OH)F nanoarray/titania mesh, is simple and maybe easy to be scaled up. DFT calculations indicated a nearly barrierless water dissociation and optimal free energy of H adsorption (ΔG_{H^*}) on the interface of PtO_2 and Co(OH)F . However further investigation on the nature and identity of the active site is warranted to obtain an in-depth insight of the reaction mechanism. Chen *et al.*⁴⁹ studied the OER activity of Co_3O_4 nanoflakes synthesized using microwave assisted hydrothermal methods (Scheme 3). These mesoporous nanoflakes exhibited OER active properties as well as good catalytic stability. This was attributed to both the stability of unique mesoporous structure and highly reactive facets. The active electrocatalyst was postulated to be a Co(IV) species.

Hydrothermal synthesis of Co_3O_4 nanowire electrocatalysts for oxygen evolution reaction was reported.⁵⁰ Glycerol was used as a morphology directing agent which led to short nanorods in ~ 4 h while a longer reaction ($\sim 12\text{--}16$ h) produced longer rods which were termed as nanowires. The aspect ratio of the nanowires after 16 h reaction time was 28 : 1. After ~ 24 h it was observed that the nanowires had assembled into bundles. The Co_3O_4 nanowires obtained after ~ 12 h of reaction were found to be electrocatalytically most active due to highest surface area. A close correlation of the OER catalytic activity is observed with the oxidation state and the density of active sites of the catalyst exposed to the electrolyte solution. Though both Co_3O_4 nanowires and nanoparticles exhibited a considerable loss in OER


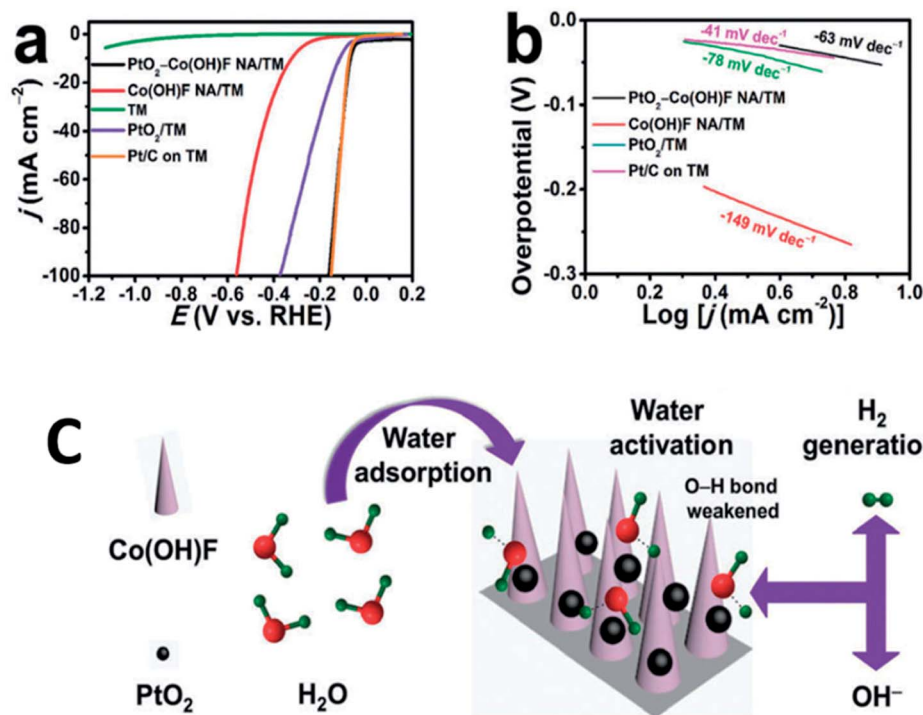


Fig. 6 (a) LSV curves recorded at a scan rate of 5 mV s^{-1} and (b) the resulting Tafel plots. (c) Schematic of water adsorption, water activation, and hydrogen generation processes for $\text{PtO}_2\text{-Co(OH)F NA/TM}$. Nano Array = NA; Titania Mesh = TM. Reproduced from ref. 48 with permission from the Royal Society of Chemistry.



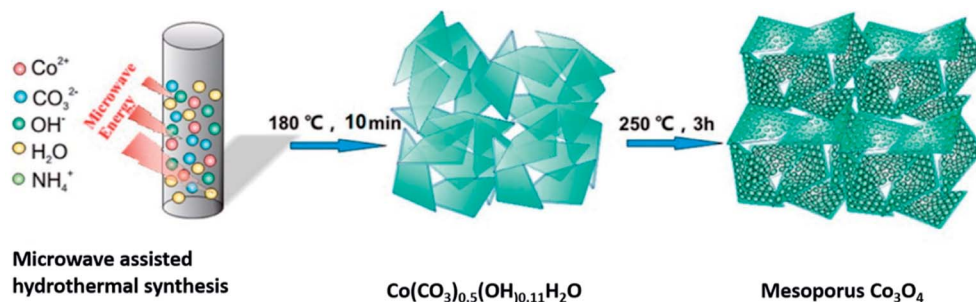

Scheme 3 Synthesis of mesoporous Co₃O₄ nanoflakes⁴⁹ using microwave-assisted hydrothermal technique. Reprinted with permission from *ACS Appl Mater Interfaces* 2015, 7(5), 3306–13. Copyright 2015 American Chemical Society.

activity during the stability studies, the former produced higher catalytic current than the latter which was attributed to a slightly higher stability. NiO nanoparticles supported on C nanobelts were synthesized by direct oxidation of Ni foam using hydrothermal techniques and these composites were found to be active for both OER and HER.⁵¹ The NiO nanobelt/C has a much lower HER efficiency than the bare NiO nanobelt electrodes and Pt electrodes which was attributed to a layer of nanocarbon deposition on the nanobelt. However, the OER performance was better for the composite due to the N doped C layer. The source of N was dopamine that was used as a precursor for the C supports. The C layer was also predicted to mechanically protect the nanostructure and enhance electrochemical stability. However, an indepth study is required to elucidate the role of the C and N on the electrocatalytic process. Even though the same catalyst was active for both HER and OER, in this report its performance for overall water splitting activity in an electrolyzer (where the same catalyst is used as a cathode and anode in a single cell) was not evaluated. NiCo₂O₄ rods over Co₃O₄ nanosheets synthesized by a two-step hydrothermal method were reported as efficient catalyst for water splitting reactions.⁵² The OER activity of the composite (peak current: 4.18 mA cm⁻²) was an approx. 2.25 times higher than that of commercial RuO₂ catalyst (1.84 mA cm⁻²). The satisfactory electrochemical performance of the composite material was attributed to the oxygen-deficient 3D architecture providing more catalytic active sites. NiCo₂O₄ nanowire arrays⁵³ prepared by hydrothermal techniques were reported to catalyze the OER in 1 M KOH electrolyte. The catalyst exhibits higher catalytic activity than Co₃O₄ and NiO which is attributed to a larger surface area, one-dimensional architecture, higher conductivity and synergy between the components in the bifunctional catalyst. The current density observed was 90 mA cm⁻² at 0.9 V vs. SCE and the Tafel slope was reported to be 62 mV per decade. Zn⁵⁴ and Cu⁵⁵ doped Co₂O₄ quantum dots (Zn-Co and Cu-Co bimetallic oxide) on N-doped carbon nanotubes prepared by hydrothermal methods were evaluated electrocatalytic water splitting activity. The former exhibited OER activity, while the latter exhibited both OER and HER. The electrolyte used for evaluating both catalysts was 0.1 M KOH. For the Zn doped material⁵⁴ a current density of 10 mA cm⁻² was observed at 1.65 V (OER), which was comparable to IrO₂ on N doped carbon

nanotubes. When the Cu-Co₂O₄ based catalyst was evaluated for OER, a current density of 10 mA cm⁻² was observed at 0.7 V (vs. SCE) while for HER a current density of -5.5 mA cm⁻² was observed at -0.7 V (vs. SCE).

An interesting report demonstrates *in situ* activation (by electrochemical oxidation reduction cycle-EORC) of stainless steel rust (mixture of Ni and Fe oxides) towards “low-cost, efficient, free-standing, and recoverable oxygen evolution electrodes.”⁵⁶ The process developed could “mimic and expedite” the corrosion process, and thus activate stainless steel as free-standing OER electrodes. The production of electrolyte-accessible Fe/(Ni) oxyhydroxides, as well as the high conductivity and mechanical stability, this electrode exhibited good OER performance including low overpotential, fast kinetics, and long-term durability. Another interesting aspect is that the minor degradation in current after long-term use could be handled *in situ* by an EORC. Mn doped Co tungstates, Co_{1-x}Mn_xWO₄ (x = 0 to 1) were reported as bifunctional catalysts for OER and ORR.⁵⁷ These nanocrystalline oxides with selective termination of low surface energy planes were synthesized by hydrothermal method. Substituting Mn enhances the catalytic activity leading to a negative shift in the Co²⁺/Co³⁺ redox wave and onset of the OER, indicating a strong Mn-Co electronic interaction. Co_{0.5}Mn_{0.5}WO₄ was found to be the most efficient catalyst in the series for both the OER and ORR with a combined overpotential of 0.89 V. It exhibited an OER current density of 10 mA cm⁻² at an overpotential of 400 mV. DFT calculations indicated that the substitution of Mn in CoWO₄ elevates the 3d metal d band center closer to the Fermi energy and hence eases the electron transfer to facilitate ORR and OER. Au/NiCo₂O₄ arrays prepared hydrothermally were reported.⁵⁸ These nanoarrays exhibited OER activity that was several folds higher than the well-known catalyst Ir/C (at 1.75 V vs. RHE). The 2 wt% Au loading was the most active catalyst with a small Tafel slope (63 mV per decade) and an overpotential of 370 mV to achieve a current density of 10 mA cm⁻². The activity of the catalysts with lower loadings (1.5 wt% Au) and higher loadings (3.7 wt% Au) catalysts were much lower. The catalysts show good stability in alkaline solution, making them suitable for water oxidation catalysis. It was hypothesized that the incorporation of Au acts as an electron sink and facilitates the oxidation of Co to +IV state, thus contributing to enhanced electrocatalytic activity. Au





Table 1 Literature reports of relevant water splitting OER and HER electrocatalysts synthesized by hydrothermal and microemulsion routes

Electrocatalyst	OER/HER	Current density (j mA cm ⁻²) @ potential (mV)	Tafel slope (mV per decade)	Remarks	Ref.
H-MWCNT, Hydrothermally treated MWCNT	OER + HER	3.4 mA cm ⁻² @ 1.7 V (OER) 10 mA cm ⁻² @ 680 mV (HER)	71.35 (HER)	OER: 0.1 M KOH, onset 1.57 V HER: 0.5 M H ₂ SO ₄ , onset 50 mV	23
Cu nanoparticles	HER + OER	HER: 12 mA cm ⁻² @ -1.5 V (GC) 46 mA cm ⁻² @ -1.5 V (Pt) OER: 1.6 mA cm ⁻² @ -800 mV (GC) 15 mA cm ⁻² @ -800 mV (Pt) 15 mA cm ⁻² @ -1.4 V (vs. Ag/AgCl) 300 mA @ 410 mV	95	0.5 M KOH	26
Cu-Co core-shell nanoparticles	HER	15 mA cm ⁻² @ -1.4 V (vs. Ag/AgCl)	160	1 M KOH	28
NiTe nanosheets on Ni foam	OER	130 mA cm ⁻² @ 570 mV	36	0.1 M KOH	17
Cu-Co-Ni alloy	OER	10 mA cm ⁻² @ 596 mV	95	3 M KCl	31
AuCuCo alloy	HER			Alkaline medium, best composition	33
Co doped 2H-MoS ₂	OER	130 mA cm ⁻² @ 570 mV	36	Ag : Cu : Zn = 43 : 48 : 8	30
AgCuZn sulfide	OER		46.9	0.5 M H ₂ SO ₄ Highest activity Mo/C molar ratio 0.04	33
2H-MoS ₂ ultrathin nanomesh	HER	10 mA @ 200 mV vs. RHE	35	0.5 M H ₂ SO ₄	34
MoS ₂ nanosheets/carbon fibers	HER	10 mA @ 320 mV	90 (HER)	Acidic media	35
Graphene - amorphous MoS _x composites	OER + HER	10, 100, 200, 300 mA @ 187, 274, 300, 320 mV respectively (OER) 10, 100, 200, 300 mA @ 217, 275, 313, 335 mV respectively	38 (OER)	Best OER and HER for Mo : S = 1 : 10, exchange current density 0.107 mA cm ⁻²	36
MoS ₂ /Ni ₃ S ₂ nanorods aligned on Ni foam	HER & OER	10 mA @ 570 mV	107	HER in 1.0 M KOH, OER in 0.1 M KOH	37
SnS ₂ modified TiO ₂ nanobelt	HER	10 mA @ 122 mV (HER)	69 (HER)	1 M NaOH	38
Ni ₃ S ₄ /Ni foam	HER & OER	20 mA @ 320 mV (OER)	71 (OER)	0.1 M KOH	38
Ni ₃ S ₂ /Si powder	HER and OER	10 mA @ 450 mV (HER-acidic)	74 (HER-alkaline) 52 (HER-acidic)	0.5 M KOH	39
SnS ₂ and SnS	HER	15 mA @ 210 mV (OER) 10 mA @ 880 mV (SnS)	187 (OER) 96 (SnS)	0.5 M H ₂ SO ₄	40
AgInS ₂	HER	10 mA @ 730 mV (SnS ₂)	152 (SnS ₂)	0.5 M H ₂ SO ₄	41
NiFeS/Ni foam	OER	20 mA @ 160 mV 10 mA @ 65 mV 100 mA @ 189 mV	119.4	0.1 M KOH	42
Monoclinic Co ₃ Se ₄ /Co foam	OER	397 mA @ 320 mV	44	1 M KOH	44
Mg ₂ MnO ₄	OER	14 mA @ 1 V (Ag/Ag ⁺)		KOH	44
CoMn ₂ O ₄	OER	45 mA @ 1 V (Ag/Ag ⁺)		1 M KOH	45
α -MoO ₃ nanobelts	HER	14.4 mA @ 150 mV	131	Onset 96 mV	46
PtO ₂ /Co(OH)F/TiO ₂ mesh	HER	4 mA @ 39 mV	63	Near zero onset, 0.1 M KOH	48
Co ₃ O ₄ nanoflakes	OER	10 mA @ 380 mV	48	1 M KOH, onset (0.452 vs. Ag/AgCl) microwave based hydrothermal technique	49
Co ₃ O ₄ nanowire	OER	1 mA @ 348 mV	57	0.1 M KOH	50
NiCo ₂ O ₄ nanowire arrays	OER	90 mA cm ⁻² @ 0.9 V (vs. SCE)	62	1 M KOH	53
CuCo ₂ O ₄ quantum dots on N-doped CNT	HER and OER	5.5 mA cm ⁻² @ -0.7 V (vs. SCE (HER))	76.5 (HER)	0.1 M KOH	55



Table 1 (Contd.)

Electrocatalyst	OER/HER	Current density (j mA cm ⁻²) @ potential (mV)	Tafel slope (mV per decade)	Remarks	Ref.
ZnCo ₂ O ₄ quantum dots on N-doped CNT	OER	10 mA cm ⁻² @ 0.7 V (vs. SCE (OER))	83 (OER)	0.1 M KOH	54
NiO NP/C nanobelts	OER + HER	10 mA cm ⁻² @ 1.6 V 50 mA @ 426 mV 100 mA @ 500 mV (OER)	70.6 150 (HER) 92 (OER)	1 M KOH	51
Co/Ru doped α -MoO ₂	OER	1 mA @ MnO ₂ -7.6% Co: 650 mV MnO ₂ -9.4% Ru: 590 mV (vs. Ag/Ag ⁺)	MnO ₂ -7.6% Co: 57 MnO ₂ -9.4% Ru: 62	MnO ₂ -7.6% Co ($\eta = 0.77$) MnO ₂ -9.4% Ru ($\eta = 0.68$)	47
NiCo ₂ O ₄ rods/Co ₃ O ₄ nanosheets	OER	4.11 mA @ 1 V (vs. Hg/HgO)	79	0.1 M KOH	52
EOEC activated stainless steel rust	OER	10 mA @ 280 mV	32	1 M KOH	56
Co _{1-x} Mn _x WO ₄	OER	10 mA @ 400 mV	84	0.1 M KOH	57
Au/NiCo ₂ O ₄ (2 wt% Au)	OER	10 mA @ 370 mV	63	1 M KOH	58
Au/ZnCo ₂ O ₄ on CNT	OER	10 mA cm ⁻² @ 1.67 V (vs. RHE)	46.2	1 M KOH	59
(Na _{0.33} Ce _{0.67}) ₂ -(Ir _{1-x} Ru _x)O ₇ ($x = 1$)	OER	10 mA @ 214 mV	48.6	0.5 M H ₂ SO ₄	60
Cu/Cu ₂ O	HER and OER	99.6 mA @ -1.5 V (HER) 1.6 mA @ 1.0 V		0.5 M KOH	61

was also hypothesized to be helpful in the formation of the OOH intermediate that is highly unstable and decomposes to molecular O₂ rapidly. A composite of spinel ZnCo₂O₄ and Au nanodots on CNT prepared by hydrothermal methods was evaluated for OER.⁵⁹ The catalytic activity increases with increased Au loading and surpasses IrO₂. A current density of 10 mA cm⁻² was observed at 1.67 V (vs. RHE) while 97.8 mA cm⁻² (vs. RHE) was observed at 1.8 V when 1 M KOH was used as an electrolyte. RuO₂ is the most active catalyst for the OER but it is unstable and known to oxidize to RuO₄. IrO₂ is more stable, but has a lower activity. To address these shortcomings in the individual Ru and Ir based catalysts, a pyrochlore based solid solution (Na_{0.33}Ce_{0.67})₂-(Ir_{1-x}Ru_x)₂O₇ ($0 < x < 1$), containing Ru IV and Ir IV at the B-site was evaluated as a catalyst for OER in acidic conditions.⁶⁰ This catalyst was prepared by hydrothermal methods and the atomically mixed Ru and Ir as well as their nanocrystalline form allows effective fabrication of electrode coatings with improved charge density over the well-known (Ru, Ir)₂O₇ catalysts. Using XANES spectroscopy an *in situ* study of the catalyst at the Ir L III and Ru K edges indicated that both Ru and Ir participate in the redox chemistry at OER conditions and that Ru is more active than Ir. Ru gets oxidized by almost one oxidation state at maximum applied potential, additionally, there was no evidence for presence of ruthenate or iridate in oxidation states of +6 or higher. The above studies can potentially be used for future catalyst development.

2.5 Other miscellaneous materials

Our group has reported the electrocatalytic activity of Cu/Cu₂O nanocomposites which were obtained from precursors synthesized by microemulsion methods.⁶¹ HER and OER were undertaken using these catalyst on glassy carbon as working electrodes in an alkaline solution. In HER experiments, these Cu/Cu₂O nanocomposites produce ~8 times higher current density than Cu and ~4.5 times higher than Cu₂O. In the case of OER studies, the current density is 36 times higher than Cu and 2.9 times higher than Cu₂O. The higher activity in the composites was attributed to the fast electron transfer rate at the interfaces in the nanocomposites. The electrocatalyst (Cu/Cu₂O) was stable over 50 cycles. Synthesis of Ag nanoparticles decorated hematite “nano-dendrite” electro-catalysts and its methanol assisted water splitting application has been investigated.⁶² The performance of catalyst synthesized by chemical precipitation was found to show better catalytic activity than the one prepared by hydrothermal methods. The observed enhancement in electro-catalytic properties was attributed to the synergistic effect of hematite dendrites as well as on the larger surface area of dendrite structure leading to higher loading of Ag NPs, however no concrete evidence to support this was provided. Fe-doped Ni₂P nanosheet arrays were reported as bifunctional catalysts (both HER and OER) for overall water splitting.⁶³ These catalysts were synthesized by hydrothermal method followed by *in situ* phosphorization. The (Ni_{0.33}Fe_{0.67})₂P exhibited good activity towards OER with a small overpotential of ~214 mV to achieve a current density of 50 mA cm⁻². However, there was strong evidence that active species for OER

was an oxidized species MO_x/MOOH ($\text{M} = \text{Ni}, \text{Fe}$)/Fe-doped Ni_2P rather than the phosphide species $(\text{Ni}_{0.33}\text{Fe}_{0.67})_2\text{P}$ itself. When used in an electrolyzer, a potential of 1.49 V was required to achieve a current density of 10 mA cm^{-2} . Cobalt carbonate hydroxide supported on a carbon (CCH/C) catalyst synthesized *via* a hydrothermal method was reported to be an active catalyst for OER and ORR reactions.⁶⁴ It was found that changing the reaction time leads to a phase transition from orthorhombic to monoclinic after 16 h. The electrocatalytic properties of the composite were strongly dependent on the crystalline phase of the CCH. Ni_2P nanoparticles decorating the surface of $\text{MoO}_2@\text{MoS}_2$ ($\text{Ni}_2\text{P}/\text{MoO}_2$, MoS_2) were reported to be active for both HER and OER.⁶⁵ The precursor, NiMoO_4 wires growing on Ti foil were synthesized *via* a modified hydrothermal reaction. Incorporation of different classes of materials (*viz* oxides, phosphides and chalcogenides) in the same catalyst helps to achieve a unique multifunctional catalyst. Such techniques may be used for synthesis of various other multifunctional catalysts that are not limited to water splitting applications. Table 1 summarizes the water splitting activity of some of the catalysts that were synthesized by hydrothermal/microemulsion methods.

3. Conclusions and current challenges

Electrocatalysts synthesized by low temperature hydrothermal and microemulsion methods for water splitting applications were reviewed. Various categories of electrocatalysts like metal nanoparticles, binary and ternary alloys, metal oxides and metal chalcogenides have been discussed. The choice of electrocatalysts broadly corresponds to the classes of materials, synthesized by these above-mentioned techniques, that have been investigated by our group in the past. In general for the design of the catalysts, the different approaches adopted are (1) alloy different transition metals (2) synthesize composites with a large surface area, high crystallinity, large interlayer spacing and porous structure and (3) synthesize 3D structures supported usually on supports such as Ni foam, Cu foam *etc.* The shape and morphology of the nanoparticles was definitely found to influence the electrocatalytic properties. Thus, low temperature techniques like hydrothermal and microemulsion processes that allow control of morphology and similar physical properties are highly suitable for development of water splitting catalysts. However, one of the primary drawbacks for the use of microemulsion and hydrothermal based synthesis of electrocatalysts is the inherent difficulty in removal of the surfactants post synthesis. These surfactants are usually charged and may contain heteroatoms. Even though calcination results in removal of carbonaceous species, the role of other species, *e.g.* bromide ions in CTAB (a commonly used surfactant) that may interfere in electrocatalytic process is often ignored in literature. A more intensive approach to screen and address this issue is highly desirable. It is recommended that the scientific community

use the available analytical tools to specifically look for probable interfering ions that may originate from surfactants.

Though some electrolyzers have been developed where overall water splitting to produce H_2 and O_2 have been reported, an electrocatalyst which is bifunctional in terms of catalyzing both HER and OER in the same electrolyte is still a challenge. All the bifunctional catalysts (active for both HER and OER) reported here require more than 1.4 V to achieve a current density of 10 mA cm^{-2} . At such high potentials, there are ample possibilities for a change in oxidation states of the constituent transition metals. It was seen, that in literature, a majority of the bifunctional catalysts, that catalyze both HER and OER have Ni as a constituent. It is noteworthy though that Cu/ Cu_2O reported by us is bifunctional for both these reactions. Co based electrocatalysts are active towards OER reactions. There are reports of using multiple functionalities (*viz* oxides, phosphides and chalcogenides) in the same catalyst helps to achieve a unique multifunctional catalyst with favorable electrocatalytic properties. However, in such composites, the specific role of each component/functionality would be difficult to elucidate and thus a modular, bottom up approach with lesser number of components is recommended. Additionally, use of complex compositions may lead to waste management issues and the corresponding environmental ramifications. In general Co and Ni based catalysts are the best candidates for exploring overall water splitting applications. Though there have been reports of doping noble metals to enhance activity, industrial relevance based on economic viability should be considered. 2D transition metal dichalcogenides based on Mo are also potentially promising building blocks for such catalysts.

Additional challenges in the field are benchmarking, scalability and determination of the electrocatalytically active site. Benchmarking issues arise due to the use of non-standard conditions, electrolytes and their concentrations. As seen from Table 1, there is a lot of diversity in the choice of electrolyte for the HER and OER studies. Further, the role of the electrolyte and the possibility of interfering ions inherently present in them is often ignored. There are a few recent studies that⁶⁶ have rigorously removed interfering ions (in this case Fe ions) from the electrolyte (KOH), however, such practices are not usually carried out. Another point to note is that often, especially in some of the earlier studies, the role of impurities from the reaction vessel was ignored. Usually glass vessels were used and the highly basic conditions especially in OER reactions makes them prone to etching. The role of silica and the additives (that are etched out), were not thoroughly examined in these highly sensitive electrocatalytic experiments. Teflon vessels are now used as alternatives, however, still in these highly basic environments, the role of constituent ions such as fluoride in these is still an open question. Another aspect is the quality and the uniformity of the catalyst film on the electrode. Even though the proportion of the binder (*e.g.* Nafion) to the catalyst/support is usually reported, the actual process of physical deposition of the slurry on to the electrode is highly non-standard and the quality of the film depends on the “experimental hand” of the experimentalist. Often, this is also not reproducible, even in the same lab. Moreover, there is the issue of film degradation due to



bubble formation resulting from the hydrogen and oxygen evolved. Adequate post catalysis studies are often not carried out to address the issue of stability and determination of the electrocatalytically active site.

Another major point that the current research is lacking is the scalability and stability. Preparation of catalyst loaded electrodes that can perform water splitting on an industrial scale for a reasonable number of cycles that would make it cost effective is still a challenge. As of 2016, the catalytic splitting of water to form hydrogen and molecular oxygen *via* electrolysis provides only 4% of the world's hydrogen.⁶⁷ Thus, there is ample scope of development of better performing electrocatalysts for water splitting using hydrothermal and microemulsion techniques.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

AKG acknowledges the support of nanoscale research facility, IIT Delhi for part of the work described. AD acknowledges the support from the Council of Scientific and Industrial Research (CSIR-India) for financial support in form of SRA (Senior Research Associate – Pool Scheme) fellowship.

References

- 1 C. Burda, X. B. Chen, R. Narayanan and M. A. El-Sayed, *Chem. Rev.*, 2005, **105**, 1025–1102.
- 2 L. M. Liz-Marzan, *Langmuir*, 2006, **22**, 32–41.
- 3 A. Gocalinska, M. Saba, F. Quochi, M. Marceddu, K. Szendrei, J. Gao, M. A. Loi, M. Yarema, R. Seyrkammer, W. Heiss, A. Mura and G. Bongiovanni, *J. Phys. Chem. Lett.*, 2010, **1**, 1149–1154.
- 4 M. Nasilowski, B. Mahler, E. Lhuillier, S. Ithurria and B. Dubertret, *Chem. Rev.*, 2016, **116**, 10934–10982.
- 5 G. Demazeau, *J. Mater. Chem.*, 1999, **9**, 15–18.
- 6 M. Nyman, M. A. Rodriguez, L. E. Shea-Rohwer, J. E. Martin and P. P. Provencio, *J. Am. Chem. Soc.*, 2009, **131**, 11652–11653.
- 7 D. R. Modeshia and R. I. Walton, *Chem. Soc. Rev.*, 2010, **39**, 4303–4325.
- 8 R. E. Riman, W. L. Suchanek and M. M. Lencka, *Ann. Chimie Sci. Materiaux.*, 2002, **27**, 15–36.
- 9 J. L. West and N. J. Halas, *Annu. Rev. Biomed. Eng.*, 2003, **5**, 285–292.
- 10 X. C. Li, W. J. Zheng, G. H. He, R. Zhao and D. Liu, *ACS Sustainable Chem. Eng.*, 2014, **2**, 288–295.
- 11 M. P. Pileni, *J. Phys. Chem.*, 1993, **97**, 6961–6973.
- 12 M. P. Pileni, *J. Exp. Nanosci.*, 2006, **1**, 13–27.
- 13 M. P. Pileni, *J. Phys. Chem. C*, 2007, **111**, 9019–9038.
- 14 M. P. Pileni, *Langmuir*, 1997, **13**, 3266–3276.
- 15 C. Dhand, N. Dwivedi, X. J. Loh, A. N. Jie Ying, N. K. Verma, R. W. Beuerman, R. Lakshminarayanan and S. Ramakrishna, *RSC Adv.*, 2015, **5**, 105003–105037.
- 16 T. Ahmad and A. K. Ganguli, *J. Am. Ceram. Soc.*, 2006, **89**, 3140–3146.
- 17 S. Saha, K. V. Ramanujachary, S. E. Lofland and A. K. Ganguli, *Mater. Res. Express*, 2016, **3**, 016501.
- 18 T. Ahmad and A. K. Ganguli, *J. Mater. Res.*, 2004, **19**, 2905–2912.
- 19 T. Ahmad, G. Kavitha, C. Narayana and A. K. Ganguli, *J. Mater. Res.*, 2005, **20**, 1415–1421.
- 20 S. Vaidya, T. Ahmad, S. Agarwal and A. K. Ganguli, *J. Am. Ceram. Soc.*, 2007, **90**, 863–869.
- 21 T. Ahmad, K. V. Ramanujachary, S. E. Lofland and A. K. Ganguli, *J. Chem. Sci.*, 2006, **118**, 513–518.
- 22 I. Roger, M. A. Shipman and M. D. Symes, *Nat. Rev. Chem.*, 2017, **1**, 0003.
- 23 B. H. R. Suryanto, S. Chen, J. J. Duan and C. Zhao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 35513–35522.
- 24 J. Ahmed, P. Trinh, A. M. Mugweru and A. K. Ganguli, *Solid State Sci.*, 2011, **13**, 855–861.
- 25 B. Kumar, S. Saha, M. Basu and A. K. Ganguli, *J. Mater. Chem. A*, 2013, **1**, 4728–4735.
- 26 J. Ahmed, A. Ganguly, S. Saha, G. Gupta, P. Trinh, A. M. Mugweru, S. E. Lofland, K. V. Ramanujachary and A. K. Ganguli, *J. Phys. Chem. C*, 2011, **115**, 14526–14533.
- 27 J. Ahmed, B. Kumar, A. M. Mugweru, P. Trinh, K. V. Ramanujachary, S. E. Lofland, Govind and A. K. Ganguli, *J. Phys. Chem. C*, 2010, **114**, 18779–18784.
- 28 Y. Li and C. Zhao, *Adv. Mater. Lett.*, 2017, **8**, 916–921.
- 29 S. Saha, S. Vaidya, K. V. Ramanujachary, S. E. Lofland and A. K. Ganguli, *Bull. Mater. Sci.*, 2016, **39**, 433–436.
- 30 M. H. Xie, S. Q. Ai, J. Yang, Y. D. Yang, Y. H. Chen and Y. Jin, *ACS Appl. Mater. Interfaces*, 2015, **7**, 17112–17121.
- 31 H. Gong, W. Zhang, F. Li and R. Yang, *Electrochim. Acta*, 2017, **252**, 261–267.
- 32 K. Ojha, S. Saha, S. Banerjee and A. K. Ganguli, *ACS Appl. Mater. Interfaces*, 2017, **9**, 19455–19461.
- 33 K. Zhang, H. J. Kim, J. T. Lee, G. W. Chang, X. Shi, W. Kim, M. Ma, K. J. Kong, J. M. Choi, M. S. Song and J. H. Park, *Chemosuschem*, 2014, **7**, 2489–2495.
- 34 Y. Zhou, H. Q. Xiao, S. T. Wang, X. Pan, Z. J. Wang, C. H. An and J. Zhang, *Mater. Chem. Phys.*, 2016, **183**, 18–23.
- 35 J. Luxa, V. Mazanek, D. Bousa, D. Sedmidubsky, M. Pumera and Z. Sofer, *ChemElectroChem*, 2016, **3**, 565–571.
- 36 N. Zhang, J. Lei, J. Xie, H. Huang and Y. Yu, *RSC Adv.*, 2017, **7**, 46286–46296.
- 37 M. Y. Li, H. Liu, T. Lv and M. Ding, *J. Mater. Chem. A*, 2018, **6**, 3488–3499.
- 38 J.-T. Ren and Z.-Y. Yuan, *ACS Sustainable Chem. Eng.*, 2017, **5**, 7203–7210.
- 39 A. A. Ensafi, M. Jafari-Asl, A. Nabiyan and B. Rezaei, *Energy*, 2016, **116**, 392–401.
- 40 X. Y. Chia, P. Lazar, Z. Sofer, J. Luxa and M. Pumera, *J. Phys. Chem. C*, 2016, **120**, 24098–24111.
- 41 P. Saji, A. K. Ganguli, M. A. Bhat and P. P. Ingole, *ChemPhysChem*, 2016, **17**, 1195–1203.
- 42 B. Dong, X. Zhao, G. Q. Han, X. Li, X. Shang, Y. R. Liu, W. H. Hu, Y. M. Chai, H. Zhao and C. G. Liu, *J. Mater. Chem. A*, 2016, **4**, 13499–13508.



- 43 W. Li, X. Gao, D. Xiong, F. Wei, W.-G. Song, J. Xu and L. Liu, *Adv. Energy Mater.*, 2017, 7, 1602579.
- 44 N. Garg, Menaka, K. V. Ramanujachary, S. E. Lofland and A. K. Ganguli, *J. Solid State Chem.*, 2013, 197, 392–397.
- 45 N. Garg, M. Mishra, Govind and A. K. Ganguli, *RSC Adv.*, 2015, 5, 84988.
- 46 H. Sinaim, D. J. Ham, J. S. Lee, A. Phuruangrat, S. Thongtem and T. Thongtem, *J. Alloys Compd.*, 2012, 516, 172–178.
- 47 M. Luebke, A. Sumboja, L. McCafferty, C. F. Armer, A. D. Handoko, Y. Du, K. McColl, F. Cora, D. Brett, Z. Liu and J. A. Darr, *ChemistrySelect*, 2018, 3, 2613–2622.
- 48 Z. Q. Wang, Z. Liu, G. Du, A. M. Asiri, L. Wang, X. N. Li, H. J. Wang, X. P. Sun, L. Chen and Q. J. Zhang, *Chem. Commun.*, 2018, 54, 810–813.
- 49 S. Chen, Y. Zhao, B. Sun, Z. Ao, X. Xie, Y. Wei and G. Wang, *ACS Appl. Mater. Interfaces*, 2015, 7, 3306–3313.
- 50 S. Xu, J. Tong, Y. Liu, W. Hu, G. Zhang and Q. Xia, *J. Renewable Sustainable Energy*, 2016, 8, 044703.
- 51 Q. Dong, C. Sun, Z. Dai, X. Zang and X. Dong, *ChemCatChem*, 2016, 8, 3484–3489.
- 52 P. Sennu, H. S. Park, K. U. Park, V. Aravindan, K. S. Nahm and Y.-S. Lee, *J. Catal.*, 2017, 349, 175–182.
- 53 Y.-Z. Su, Q.-Z. Xu, G.-F. Chen, H. Cheng, N. Li and Z.-Q. Liu, *Electrochim. Acta*, 2015, 174, 1216–1224.
- 54 L. Zhao-Qing, C. Hui, L. Nan, M. T. Yi and S. Yu-Zhi, *Adv. Mater.*, 2016, 28, 3777–3784.
- 55 C. Hui, L. Mei-Ling, S. Chang-Yuan, L. Nan and L. Zhao-Qing, *Adv. Funct. Mater.*, 2017, 27, 1701833.
- 56 H. Zhong, J. Wang, F. Meng and X. Zhang, *Angew. Chem., Int. Ed.*, 2016, 55, 9937–9941.
- 57 G. Karkera, T. Sarkar, M. D. Bharadwaj and A. S. Prakash, *ChemCatChem*, 2017, 9, 3681–3690.
- 58 X. J. Liu, J. F. Liu, Y. P. Li, Y. J. Li and X. M. Sun, *ChemCatChem*, 2014, 6, 2501–2506.
- 59 H. Cheng, C.-Y. Su, Z.-Y. Tan, S.-Z. Tai and Z.-Q. Liu, *J. Power Sources*, 2017, 357, 1–10.
- 60 K. Sardar, E. Petrucco, C. I. Hiley, J. D. B. Sharman, P. P. Wells, A. E. Russell, R. J. Kashtiban, J. Sloan and R. I. Walton, *Angew. Chem., Int. Ed.*, 2014, 53, 10960–10964.
- 61 B. Kumar, S. Saha, K. Ojha and A. K. Ganguli, *Mater. Res. Bull.*, 2015, 64, 283–287.
- 62 P. Chaudhary and P. P. Ingole, *Int. J. Hydrogen Energy*, 2018, 43, 1344–1354.
- 63 Y. Li, H. Zhang, M. Jiang, Q. Zhang, P. He and X. Sun, *Adv. Funct. Mater.*, 2017, 27, 1702513.
- 64 Y. Wang, W. Ding, S. Chen, Y. Nie, K. Xiong and Z. Wei, *Chem. Commun.*, 2014, 50, 15529–15532.
- 65 Y. Wang, T. Williams, T. Gengenbach, B. Kong, D. Zhao, H. Wang and C. Selomulya, *Nanoscale*, 2017, 9, 17349–17356.
- 66 M. Burke, M. G. Kast, L. Trotochaud, A. Smith and S. W. Boettcher, *J. Am. Chem. Soc.*, 2015, 137, 3638–3648.
- 67 Engineers Ireland, Electrochemical water splitting: a new dawn for the hydrogen economy, <http://www.engineersjournal.ie/2016/07/12/electrochemical-water-splitting-hydrogen-economy/>.

