

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)

Cite this: *Polym. Chem.*, 2025, **16**, 821

Sunflower oil-based thermosets *via* the Passerini three-component reaction†

Luis Santos Correa,<sup>a</sup> Silas Leidenheimer<sup>b</sup> and Michael A. R. Meier<sup>\*a,b</sup>

Tricarboxylic acids are molecules of interest for the synthesis of cross-linked polymers. Herein, a recently established route to a tricarboxylic acid from high oleic sunflower oil was utilized to synthesize renewable cross-linked polymers *via* the Passerini three-component reaction. Ten different polymers were synthesized by varying the diisocyanide and monoaldehyde components and subsequently characterized *via* infrared spectroscopy, swelling tests, thermogravimetric analysis, differential scanning calorimetry, and tensile tests. The characterization of the insoluble polymeric networks was complemented by the synthesis of model compounds to enable analysis in solution *via* nuclear magnetic resonance spectroscopy. Due to the fast curing of all polymers at room temperature, adhesive tests were performed to demonstrate their potential application as glues. Finally, one Passerini polymer was chemically reused by transesterification with methanol and catalytic amounts of sulfuric acid to establish a proof-of-concept of the circularity of these materials. Azelaic acid dimethyl ester, an industrially relevant compound used for the synthesis of polyamides, and a difunctional  $\alpha$ -hydroxyamide were recovered in a yield of 75%. Repolymerization of the  $\alpha$ -hydroxyamide to a polyurethane was performed to demonstrate a potential second life cycle of these compounds.

Received 28th November 2024,  
Accepted 23rd December 2024

DOI: 10.1039/d4py01358a

[rsc.li/polymers](https://rsc.li/polymers)

## Introduction

The development and production of new polymeric materials from renewable resources are of paramount importance to reduce humanity's high dependency on depleting fossil resources. For instance, in 2022, a concerningly small share of less than 1% of the worldwide plastic production of >400 Mt was bio-based.<sup>1</sup> Plant oils and fatty acids are the most important renewable feedstock of the chemical industry for polymer applications. In 2019, approximately 25% of the annual global production of 208 Mt vegetable oils was already used industrially for the production of biodiesel, oleochemicals, and other applications to substitute fossil-resources.<sup>2</sup> In polymer chemistry, fatty acids are either functionalized at the carboxylic acid moiety by esterification or at their double bonds *via* oxidation, thiol-ene reaction, olefin metathesis or isomerizing functionalization to synthesize difunctional monomers that

can be polymerized.<sup>3,4</sup> Polyfunctional derivatives can be obtained from oils by functionalization of the triglyceride double bonds.<sup>5</sup> Alternatively, cross-linked polymers can be synthesized from triglycerides by direct polymerization of the double bonds *via* acyclic triene metathesis polymerization or cationic/radical polymerization.<sup>3</sup>

Besides the use of renewable feedstocks, chemical reactions must adhere as much as possible to the 12 principles of green chemistry, as established by Anastas and Warner in 1998.<sup>6,7</sup> These principles act as guidelines to develop more sustainable processes and address topics such as waste production, atom economy, toxicity of the involved chemicals, the design of inherently safer chemistry, utilization of renewable resources, and the development of catalysts to reduce energy consumption.

Multicomponent reactions (MCRs) align with many of the 12 principles of green chemistry and are defined as reactions that combine at least three different starting compounds in a single one-pot reaction, in which most of the atoms of the starting materials are incorporated in the final product.<sup>8,9</sup> Hence, waste generation is kept to a minimum due to the high atom economy of these reactions, and usually only benign by-products such as water, alcohols or amines are formed.<sup>10</sup> The isocyanide based Passerini three-component reaction (P-3CR) was discovered in 1921 and describes the addition reaction between a carboxylic acid, an aldehyde, and an isocyanide to form an  $\alpha$ -acyloxy amide.<sup>11,12</sup> The high versatility of this reac-

<sup>a</sup>Laboratory of Applied Chemistry, Institute of Biological and Chemical Systems-Functional Molecular Systems (IBCS-FMS), Karlsruhe Institute of Technology (KIT), 76344 Eggenstein-Leopoldshafen, Germany. E-mail: [m.a.r.meier@kit.edu](mailto:m.a.r.meier@kit.edu)

<sup>b</sup>Laboratory of Applied Chemistry, Institute of Organic Chemistry (IOC), Karlsruhe Institute of Technology (KIT), Kaiserstraße 12, 76131 Karlsruhe, Germany

†Electronic supplementary information (ESI) available: Analytical data of the synthesized compounds, details about the carboxylic acid value determination, and all tensile and adhesive test measurements. See DOI: <https://doi.org/10.1039/d4py01358a>



tion enables its use in step economic syntheses of several natural products and active pharmaceutical ingredients.<sup>12–14</sup>

Although the Passerini reaction is known to achieve near quantitative conversions at room temperature, its utilization as step-growth polymerization reaction was first reported 90 years after its discovery.<sup>15</sup> Meier *et al.* reported polyesters with high molecular weights of up to 56 kDa that were obtained by a combination of a dicarboxylic acid, a dialdehyde, and a monoisocyanide at a reaction temperature of only 40 °C. Shortly after, several syntheses of new poly(ester-amide)s,<sup>16</sup> polyamides,<sup>17</sup> and polyesters<sup>18</sup> were achieved by simple permutation of the starting materials' functional groups. The multicomponent polymerization approach moreover easily allows the polymers to be grafted onto by the introduction of additional functional groups during the MCR step.<sup>17,18</sup> So far, the synthesis of cross-linked polymers *via* isocyanide based MCRs has however been reported scarcely. Most studies focused on the synthesis of hydrogels from carboxylic acid group bearing polysaccharides such as alginic acid,<sup>19–22</sup> hyaluronic acid,<sup>22,23</sup> and carboxymethylcellulose<sup>22,24</sup> *via* the P-3CR or the Ugi four-component reaction. Furthermore, the polysaccharide chitosan was used as a polyamine component for the synthesis of Ugi-4CR based microgels.<sup>25</sup> However, in all of these reports, the cross-linking was only performed with already polymeric starting materials. To the best of our knowledge, so far only one report by Xie *et al.* describes the synthesis of a cross-linked P-3CR polymer from terephthalaldehyde, 1,6-diisocyanohexane, and sebacic acid.<sup>26</sup> However, due to the high molar excess of 50 mol% terephthalaldehyde, it is most likely that these materials exhibited a low degree of cross-linking and a high share of unreacted aldehyde groups. In addition, both the hydrogel approach and the polymer reported by Xie *et al.* used solvents during the polymerization, which is not desired as this generates additional waste.

Thus, we herein report for the first time the solvent-free synthesis of ten different P-3CR thermosets from a tricarboxylic acid, two diisocyanides, and five monoaldehydes. All components were by design chosen to be liquid to allow the facile preparation of solvent-free formulations. Moreover, isocyanide and aldehyde components were chosen to be at least in principle renewable in order to further increase the sustainability of these new materials. The used tricarboxylic acid is fully renewable and was synthesized from high oleic sunflower oil with a literature reported procedure.<sup>27</sup>

## Experimental

### Materials

All starting materials, solvents and reagents were purchased from chemical suppliers and used without further purification unless stated otherwise.

**Used solvents.** Cyclohexane (VWR, HPLC grade), ethyl acetate (VWR, HPLC grade), methanol (Thermo Fisher Scientific, HPLC grade) and *tert*-butanol (Acros Organics, 99.5%) were used without further purification.

Dichloromethane (OQEMA, technical) was purified by distillation prior to use. DMSO-*d*<sub>6</sub> (<99.8% D) and CDCl<sub>3</sub> (<99.8% D) were purchased from Eurisotop. Trifluoroacetic acid-*d* (99.5% D) was purchased from Sigma-Aldrich.

**Used compounds.** High oleic sunflower oil was bought at the local supermarket dm in Karlsruhe, Germany. Acetaldehyde (Acros Organics, 99.5%), butanal (Acros Organics, 99%), bromocresol green (TCI, >99%), cerium(IV) sulfate (ChemPUR, 98%), 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane (Sigma-Aldrich, 95%), 1,6-diaminohexane (Sigma-Aldrich, ≥97.5%), 1,9-diaminononane (abcr, 98%), 2-ethylbutyraldehyde (Sigma-Aldrich, ≥92%), ethyl formate (Thermo Scientific, ≥98%), formic acid (Acros Organics, 99%), hexanal (Sigma-Aldrich, 98%), hexamethylene diisocyanate (Sigma-Aldrich, for synthesis), *n*-hexylamine (Sigma-Aldrich, 99%), hydrogen peroxide (abcr, 35% aqueous solution), *endo-N*-hydroxy-5-norbornene-2,3-dicarboximide (Alfa Aesar, 97%), nonanal (Alfa Aesar, 97%), phosphomolybdic acid (Sigma-Aldrich, >99%), potassium carbonate (Sigma-Aldrich, >99%), potassium permanganate (Sigma-Aldrich, >99%), pyridine (Sigma-Aldrich, >99%), pyridine-2,6-dicarboxylic acid (Acros Organics, 99%), ruthenium(III) acetylacetonate (abcr, 99%), sodium carbonate (Carl Roth, ≥99.5%), sodium chloride (Sigma-Aldrich, >99%), sodium hydroxide (Sigma-Aldrich, >99%), sodium sulfate (Thermo Fisher Scientific, 99%), sulfuric acid (Sigma-Aldrich, 98%) and *p*-toluenesulfonyl chloride (Sigma-Aldrich, ≥99%) were used without further purification.

### Methods

**Thin-layer chromatography (TLC).** Aluminum plates coated with fluorescent silica gel of the type F<sub>254</sub> obtained from Sigma-Aldrich were used for TLC measurements. TLC plates with the applied samples were placed in a glass chamber filled with an eluent (filling height *ca.* 0.5 cm). The plates were removed once the eluent front had reached a height of ~3 cm and cautiously dried with a heat gun. The compounds on the plates were visualized using potassium permanganate stain (solution of 1.5 g potassium permanganate, 10 g potassium carbonate, 1.25 ml of 10 wt% sodium hydroxide solution, 200 ml water), Seebach stain (2.0 g cerium(IV) sulfate, 5.0 g phosphomolybdic acid, 16 ml sulfuric acid, 200 ml water) or bromocresol green stain (40 mg bromocresol green in 100 ml ethanol and subsequent addition of 0.1 M sodium hydroxide solution until a persistent blue color appears).

**Flash column chromatography.** The purification of compounds by flash column chromatography was conducted according to the publication of W. C. Still *et al.*<sup>28</sup> Silica gel, obtained from Sigma Aldrich, with a pore size of 60 Å, a mesh size of 230–240, and a particle size of 40–63 µm was used as the stationary phase.

**Distillation.** A Büchi Labortechnik Kugelrohr model B-585 was used for distillations of volumes smaller than 5 ml.

**Addition of liquids with a syringe pump.** The slow addition of liquids over time was performed with a Landgraf Laborsysteme syringe pump model LA-30.



## Instruments

**Infrared (IR) spectroscopy.** The infrared spectra of all compounds were recorded on a Bruker Alpha Fourier transform infrared spectrometer with attenuated total reflection technology in the range from 4000  $\text{cm}^{-1}$  to 400  $\text{cm}^{-1}$ . The resulting absorbance spectra are averaged over 24 scans per measurement. By convention, the signals are noted from large to small wavenumbers. Characterization of the absorption bands was performed depending on the absorption strength with the following abbreviations: vs (very strong), s (strong), m (medium), w (weak), vw (very weak).

**Nuclear magnetic resonance (NMR) spectroscopy.**  $^1\text{H}$  NMR spectra were recorded either on a Bruker Ascend™ 400 spectrometer at 400 MHz with 16 scans and a delay time  $D_1$  of 1 s at 298 K or on a Bruker Avance DRX spectrometer at 500 MHz with 16 scans and a delay time  $D_1$  of 1 s at 298 K. The chemical shift  $\delta$  is reported in parts per million and referenced to the solvent signal of DMSO- $d_5$  at 2.50 ppm,  $\text{CHCl}_3$  at 7.26 ppm, or trifluoroacetic acid at 11.5 ppm. Additionally, gradient selected correlation spectroscopy (COSY) was carried out for signal assignment of protons. The following abbreviations are used to describe the proton splitting pattern: s = singlet, d = doublet, t = triplet, and m = multiplet. All coupling constants  $J$  are given in Hz and in decreasing order.  $^{13}\text{C}$  NMR spectra were recorded either on a Bruker Ascend™ 400 spectrometer at 101 MHz with 1024 scans and a delay time  $D_1$  of 2 s at 298 K or on a Bruker Avance DRX spectrometer at 126 MHz with 1024 scans and a delay time  $D_1$  of 2 s at 298 K. The chemical shift  $\delta$  is reported in parts per million and referenced to the solvent signal of DMSO- $d_6$  at 39.52 ppm,  $\text{CDCl}_3$  at 77.16 ppm, or trifluoroacetic acid- $d$  at 164.2 ppm. Furthermore, phase-edited heteronuclear single quantum coherence (HSQC $_{\text{ed}}$ ) and heteronuclear multiple bond correlation (HMBC) spectroscopy were carried out for signal assignment of carbon atoms and structural elucidation. Signals of carbon atoms are specified as follows:  $\text{C}_\text{q}$  = quaternary carbon atom,  $\text{CH}$ ,  $\text{CH}_2$ , or  $\text{CH}_3$ . Quantitative  $^{31}\text{P}$  NMR spectra were recorded on a Bruker Avance DRX spectrometer at 202 MHz with an inverse gated decoupling pulse program, 1024 scans and a delay time  $D_1$  of 10 s at 298 K.

**Mass spectrometry (MS).** Electrospray ionization (ESI) experiments were performed on a Q Exactive Plus (Orbitrap) mass spectrometer (Thermo Fisher Scientific) equipped with a HESI II probe to record high resolution. The spectra of most compounds were evaluated from molecular signals  $[\text{M}]^+$ , signals of protonated molecules  $[\text{M} + \text{H}]^+$ , and characteristic fragment peaks and indicated with their mass-to-charge ratio ( $m/z$ ). Moreover, the spectra of carboxylic acids were evaluated from the signals of deprotonated molecules  $[\text{M} - \text{H}]^-$ .

**Melting point.** The melting point of diol **6** was recorded on a Stanford Research Systems OptiMelt – Automated Melting Point System with Digital Image Processing Technology. The measurement was performed from 25 °C to 200 °C with a heating rate of 10  $\text{K min}^{-1}$ .

**Size exclusion chromatography (SEC).** SEC analyses were performed on one of the two following systems. *System I (Oligo*

*THF SEC)*: a PSS SECcurity<sup>2</sup> SEC system based on Agilent Infinity 1260 II hardware was used for the measurements. The system was equipped with a refractive index detector SECcurity<sup>2</sup> RI, a column oven (Bio)SECcurity<sup>2</sup> column compartment TCC6500, a standard SECcurity<sup>2</sup> autosampler, and an isocratic pump SECcurity<sup>2</sup> isocratic pump. Anhydrous tetrahydrofuran stabilized with 250 ppm butylated hydroxytoluene (BHT,  $\geq 99.9\%$ ) was used at a flow rate of 1.0  $\text{ml min}^{-1}$  and at 30 °C as the mobile phase. The analysis was performed on the following column system: a PSS SDV analytical precolumn (3  $\mu\text{m}$ , 8 mm  $\times$  50 mm) with two PSS SDV analytical columns (3  $\mu\text{m}$ , 8 mm  $\times$  300 mm, 1000 Å). For the calibration, narrow linear poly(methyl methacrylate) standards (Polymer Standards Service, PSS, Germany) ranging from 102 to 62 200 Da were used. *System II (DMAc SEC)*: a PSS SECcurity<sup>2</sup> SEC system based on Agilent Infinity 1260 II hardware was used for the measurements. The system was equipped with a refractive index detector. DMAc with 0.03 wt% lithium bromide was used at a flow rate of 1.0  $\text{ml min}^{-1}$  and at 35 °C as the mobile phase. The analysis was performed on the following column system: Agilent Mixed-C column and Agilent Mixed-E column. For the calibration, polystyrene standards ranging from 370 to 2 520 000 Da were used. For sample preparation, 2.00 mg of analyte was dissolved in 1.50 ml of the solvent used in the respective system. All samples were filtered with a syringe filter prior to use, to avoid plugging of the injection setup or the column.

**Differential scanning calorimetry (DSC).** DSC measurements were performed on a Mettler Toledo DSC3 STAR<sup>c</sup> system. All experiments were carried out under a nitrogen atmosphere using 40  $\mu\text{l}$  aluminum crucibles and a sample mass of 4–7 mg. The samples were measured using the following program: first heating from 25 °C to 250 °C, then cooling from 250 °C to –70 °C and finally heating from –70 °C to 250 °C with a heating/cooling rate of 10  $\text{K min}^{-1}$ . The glass transition temperature ( $T_g$ ) was determined from the second heating run to eliminate possible interference from the polymer's thermal history.

**Thermogravimetric analysis (TGA).** TGA measurements were performed on a TA Instruments TGA 5500 under a nitrogen atmosphere using platinum TGA sample pans and a heating rate of 10  $\text{K min}^{-1}$  over a temperature range from 25 °C to 600 °C.  $T_{\text{d},5\%}$  is defined as the temperature of 5% weight loss.

**Tensile strength measurements.** Tensile strength measurements were performed on an Inspect table 10 kN from Hegewald & Peschke equipped with a 1.5 kN load cell. Tensile strength measurements and adhesive tests were performed with an elongation of 5  $\text{mm min}^{-1}$  and 1  $\text{mm min}^{-1}$ , respectively.

#### Oxidative cleavage of high oleic sunflower oil

In a 100 ml three-necked flask, high oleic sunflower oil (39.8 g, 45.0 mmol (based on the molecular weight of triolein (885.5  $\text{g mol}^{-1}$ )), 1.00 equiv.), ruthenium(III) acetylacetonate (359 mg, 900  $\mu\text{mol}$ , 2.00 mol%) and pyridine-2,6-dicarboxylic acid (3.01 g, 18.0 mmol, 40.0 mol%) were dissolved in a mixture of



*tert*-butanol (405 ml) and water (135 ml). The reaction mixture was stirred magnetically (400 rpm with a cross shaped stirring bar) at 80 °C for 24 h. After the reaction temperature reached 80 °C, hydrogen peroxide (35% aq. sol., 92.9 ml, 1.08 mol, 24.0 equiv.) was added slowly to the reaction solution using a syringe pump with a flow rate of 77.4  $\mu\text{l min}^{-1}$  over a period of 20 h. After the entire reaction time passed, the reaction solution was diluted with water (200 ml) and *tert*-butanol was removed under reduced pressure to ensure easier phase separation during extraction. The aqueous phase was extracted with ethyl acetate (3  $\times$  150 ml) and the combined organic layers were washed with saturated sodium chloride solution (3  $\times$  100 ml), dried over sodium sulfate, filtered and the solvent was removed under reduced pressure. The reaction was conducted twice. Both reactions were combined and distilled in a Zinke apparatus *in vacuo* (100 °C, 0.1 mbar) to remove the cleavage product nonanoic acid (29.2 g, 185 mmol, 90%). The residue of the distillation was purified by flash column chromatography (cyclohexane/ethyl acetate, 4:1 + 1% formic acid, then 2:1 + 1% formic acid, and then 2:1 without formic acid) to obtain three fractions (fraction 1: residual nonanoic acid (2.50 g, 15.8 mmol, 8%), fraction 2: side product with low carboxylic acid content (18.0 g, 31%), fraction 3: sunflower oil-based triacid (20.8 g, 36%)) after the removal of the solvent and formic acid under reduced pressure. Analytical data for sunflower oil-based triacid:  $^1\text{H}$  NMR (400 MHz, DMSO- $d_6$ , ppm):  $\delta$  = 11.95 (s, 3H), 5.18 (tt,  $J$  = 6.9, 3.7 Hz, 1H), 4.25 (dd,  $J$  = 12.0, 3.7 Hz, 2H), 4.12 (dd,  $J$  = 12.0, 6.5 Hz, 2H), 2.34–2.22 (m, 6H), 2.17 (t,  $J$  = 7.4 Hz, 6H), 1.49 (ddd,  $J$  = 14.6, 9.6, 5.5 Hz, 12H), 1.25 (d,  $J$  = 3.8 Hz, 18H), 0.89–0.78 (m, 0.17H);  $^{13}\text{C}$  NMR (126 MHz, DMSO- $d_6$ , ppm):  $\delta$  = 174.5 ( $\text{C}_q$ ,  $\text{CO}_2\text{H}$ ), 174.4 ( $\text{C}_q$ ,  $\text{CO}_2\text{H}$ ), 172.5 ( $\text{C}_q$ ,  $\text{C}_{\text{ester}}$ ), 172.2 ( $\text{C}_q$ ,  $\text{C}_{\text{ester}}$ ), 68.8 (CH,  $\text{C}_{\text{glyceryl}}$ ), 61.8 ( $\text{CH}_2$ ,  $\text{C}_{\text{glyceryl}}$ ), 33.6 ( $\text{CH}_2$ ), 33.5 ( $\text{CH}_2$ ), 33.3 ( $\text{CH}_2$ ), 28.4 ( $\text{CH}_2$ ), 28.3 ( $\text{CH}_2$ ), 28.2 ( $\text{CH}_2$ ), 24.4 ( $\text{CH}_2$ ), 24.4 ( $\text{CH}_2$ ), 24.3 ( $\text{CH}_2$ ); IR (ATR,  $\text{cm}^{-1}$ ):  $\tilde{\nu}$  = 3223 (vw), 2929 (m), 2857 (w), 1738 (vs), 1703 (vs), 1456 (w), 1413 (w), 1378 (w), 1232 (m), 1160 (vs), 1133 (s), 1094 (m), 1033 (w), 938 (w), 728 (w); ESI-MS ( $[\text{M} - \text{H}]^-$ ,  $\text{C}_{30}\text{H}_{49}\text{O}_{12}$ ): calcd: 601.3230, found: 601.3229.

### Quantitative $^{31}\text{P}$ NMR spectroscopy

The amount of carboxylic acids and hydroxyl groups per mg of sample was determined by derivatization of the sunflower oil-based triacid sample using the phosphitylation agent 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane (2-Cl-TMDP), according to a modified procedure of the one published by Kilpeläinen *et al.*<sup>29,30</sup> First, the internal standard solution was prepared by dissolving *endo*-*N*-hydroxy-5-norbornene-2,3-dicarboximide (550 mg, 3.07 mmol) in pyridine (15 ml) and  $\text{CDCl}_3$  (10 ml). This resulted in a final concentration of 22  $\text{mg ml}^{-1}$  or 123  $\text{mmol l}^{-1}$ . Then, under a standard atmosphere (no argon box), 28–32 mg of the analyte were weighed into a 10 ml screw-cap vial.  $\text{CDCl}_3$  (1 ml), pyridine (200  $\mu\text{l}$ , 2.48 mmol) and the internal standard solution of *endo*-*N*-hydroxy-5-norbornene-2,3-dicarboximide (650  $\mu\text{l}$ ) were added and the mixture was agitated with a vortex mixer until the sample was fully dissolved (approximately 1 min). Finally, 2-Cl-TMDP (200  $\mu\text{l}$ ,

1.26 mmol) was added and the mixture was agitated for 1 min. Then, 1.0 ml of the solution was transferred to an NMR tube.  $^{31}\text{P}$  NMR measurements were performed immediately after the sample was prepared. The carboxylic acid and hydroxyl content was calculated according to eqn (S3) and (S4), ESI.†

### Synthesis of formamides and isocyanides

The syntheses of all formamides and isocyanides were conducted according to a literature reported procedure for the synthesis of aliphatic isocyanides.<sup>31</sup> All syntheses and their analytical data are described in detail in the ESI.†

### General procedure for the synthesis of model compounds M1 to M5

Sunflower oil-based triacid (200 mg, 990  $\mu\text{mol}$ , 1.00 equiv. of carboxylic acids), *n*-hexylisocyanide (165 mg, 1.49 mmol, 1.50 equiv. based on carboxylic acids), and the respective aldehyde (1.50 equiv. based on carboxylic acids) were weighed into a glass vial and the vial was sealed. Then, dichloromethane (1 ml) was added and the reaction mixture was stirred at room temperature for 3 days. The solvent was removed under reduced pressure and the crude product was purified by flash column chromatography (cyclohexane/ethyl acetate) to obtain the respective model compound. Exemplary analytical data for **M4** (data of all other model compounds can be found in the ESI†):  $^1\text{H}$  NMR (400 MHz,  $\text{CDCl}_3$ , ppm):  $\delta$  = 6.10–5.89 (m, 3H, NH), 5.23 (p,  $J$  = 5.0 Hz, 1H,  $\text{H}_{\text{glyceryl}}$ ), 5.13 (t,  $J$  = 6.0 Hz, 3H), 4.27 (dd,  $J$  = 11.9, 4.4 Hz, 2H,  $\text{H}_{\text{glyceryl}}$ ), 4.12 (dd,  $J$  = 11.9, 5.9 Hz, 2H,  $\text{H}_{\text{glyceryl}}$ ), 3.34–3.13 (m, 6H), 2.36 (t,  $J$  = 7.5 Hz, 6H,  $\alpha$ - $\text{H}_{\text{ester}}$ ), 2.29 (t,  $J$  = 7.4 Hz, 6H,  $\alpha$ - $\text{H}_{\text{ester}}$ ), 1.89–1.72 (m, 6H), 1.69–1.54 (m, 12H,  $\beta$ - $\text{H}_{\text{ester}}$ ), 1.48 (p,  $J$  = 7.0 Hz, 6H), 1.34–1.00 (m, 72H), 0.95–0.78 (m, 18H);  $^{13}\text{C}$  NMR (101 MHz,  $\text{CDCl}_3$ , ppm):  $\delta$  = 173.2 ( $\text{C}_q$ ,  $\text{C}_{\text{ester}}$ ), 172.8 ( $\text{C}_q$ ,  $\text{C}_{\text{ester}}$ ), 172.5 ( $\text{C}_q$ ,  $\text{C}_{\text{ester}}$ ), 169.9 ( $\text{C}_q$ ,  $\text{C}_{\text{amide}}$ ), 74.1 (CH), 69.0 (CH,  $\text{C}_{\text{glyceryl}}$ ), 62.2 ( $\text{CH}_2$ ,  $\text{C}_{\text{glyceryl}}$ ), 39.3 ( $\text{CH}_2$ ), 34.3 ( $\text{CH}_2$ ,  $\alpha$ - $\text{C}_{\text{ester}}$ ), 34.2 ( $\text{CH}_2$ ,  $\alpha$ - $\text{C}_{\text{ester}}$ ), 34.0 ( $\text{CH}_2$ ,  $\alpha$ - $\text{C}_{\text{ester}}$ ), 32.0 ( $\text{CH}_2$ ), 31.9 ( $\text{CH}_2$ ), 31.5 ( $\text{CH}_2$ ), 29.6 ( $\text{CH}_2$ ), 29.5 ( $\text{CH}_2$ ), 29.4 ( $\text{CH}_2$ ), 29.3 ( $\text{CH}_2$ ), 29.0 ( $\text{CH}_2$ ), 29.0 ( $\text{CH}_2$ ), 28.9 ( $\text{CH}_2$ ), 26.6 ( $\text{CH}_2$ ), 24.9 ( $\text{CH}_2$ ), 24.8 ( $\text{CH}_2$ ), 24.8 ( $\text{CH}_2$ ), 22.7 ( $\text{CH}_2$ ), 22.6 ( $\text{CH}_2$ ), 14.2 ( $\text{CH}_3$ ), 14.1 ( $\text{CH}_3$ ); IR (ATR,  $\text{cm}^{-1}$ ):  $\tilde{\nu}$  = 3303 (w), 2952 (m), 2924 (vs), 2854 (s), 1741 (vs), 1656 (vs), 1537 (m), 1460 (m), 1418 (w), 1377 (w), 1299 (w), 1237 (m), 1159 (vs), 1132 (s), 1094 (s), 724 (w); ESI-MS ( $[\text{M} + \text{H}]^+$ ,  $\text{C}_{78}\text{H}_{144}\text{N}_3\text{O}_{15}$ ): calcd: 1363.0592, found: 1363.0494.

### General procedure for Passerini three component polymerization

Sunflower oil-based triacid (600 mg, 1.00 equiv. of carboxylic acids) and the respective diisocyanide component (0.50 equiv. of carboxylic acids) were weighed into a 10 ml screw-cap vial and cooled to  $-20$  °C with a sodium chloride ice cooling bath. The aldehyde component (1.00 equiv. of carboxylic acids) was freshly distilled and then weighed into the cooled vial. All compounds were mixed while cooling was maintained. The mixture was then poured into a poly(tetrafluoroethylene) form to produce bone shaped samples for tensile strength measurements (ESI chapter 2.5.5†). Polymers **P1a** to **P3b** were first





cured at 5 °C for 30 minutes to prevent evaporation of the volatile aldehyde components, while polymers **P4a** to **P5b** were cured at room temperature for 30 minutes. All polymers were further cured at 50 °C for 24 h to guarantee full conversion of functional groups.

### Swelling tests for gel content determination

Each polymer sample (50–100 mg) was weighed and immersed in tetrahydrofuran for 3 days at room temperature. The sample was then removed from the solvent, dried at 70 °C and 10 mbar, and weighed again to determine the gel content (eqn (1)).

### Lap shear force adhesive tests

Test samples were prepared by cutting each substrate material (aluminum alloy, stainless-steel, wood, poly(methyl methacrylate), and glass) into rectangular pieces (ESI chapter 2.5.6†). For sample preparation, the respective monomers were premixed at 0 °C and then applied onto two rectangular pieces of the same substrate (gluing area of 2.25 cm<sup>2</sup>). The two surfaces were pressed together and cured at room temperature for 2 h. Afterwards, the two pieces were pulled apart in a tensile measurement to determine the ultimate tensile strength.

### Chemical recycling of the P-3CR polymer

Polymer **P4a** (3.00 g, 14.6 mmol ester groups, 1.00 equiv.) was suspended in methanol (120 ml, 2.96 mol, 203 equiv.) and sulfuric acid (96%, 286 mg, 2.91 mmol, 0.20 equiv.) was added. The reaction mixture was stirred for 5 h at 65 °C until **P4a** dissolved completely due to depolymerization. While cooling to room temperature, the diol compound **6** precipitated. The reaction volume was reduced to 60 ml and then filtered to isolate the diol (1.23 g, 2.69 mmol, 74%). The solvent methanol was removed from the filtrate and ethyl acetate (60 ml) was added. The organic phase was washed with water (3 × 40 ml) to remove glycerol and sulfuric acid, dried over sodium sulfate, and the solvent was removed under reduced pressure. The residue was then distilled in a Kugelrohr oven *in vacuo* (10 mbar, 150 °C) to isolate azelaic acid dimethyl ester (1.18 g, 5.45 mmol, 75%). Finally, the aqueous phase from the washing step was neutralized with sodium hydroxide (116 mg,


2.91 mmol, 0.20 equiv.) and distilled in a Kugelrohr oven to obtain glycerol (68 mg, 738 μmol, 30%). Analytical data for diol **6**: *T*<sub>m</sub>: 162 °C; <sup>1</sup>H NMR (500 MHz, TFA-*d*, ppm): δ = 4.63 (dd, *J* = 8.7, 3.5 Hz, 2H), 3.44 (t, *J* = 7.3 Hz, 4H), 1.96–1.83 (m, 2H), 1.81–1.68 (m, 2H), 1.68–1.56 (m, 4H), 1.48–1.39 (m, 4H), 1.39 (s, 4H), 1.34–1.15 (m, 20H), 0.79 (t, *J* = 6.6 Hz, 6H); <sup>13</sup>C NMR (126 MHz, TFA-*d*, ppm): δ = 180.7 (C<sub>q</sub>, C<sub>amide</sub>), 73.8 (CH), 43.4 (CH<sub>2</sub>), 35.9 (CH<sub>2</sub>), 33.6 (CH<sub>2</sub>), 31.1 (CH<sub>2</sub>), 30.9 (CH<sub>2</sub>), 30.8 (CH<sub>2</sub>), 29.9 (CH<sub>2</sub>), 27.9 (CH<sub>2</sub>), 26.7 (CH<sub>2</sub>), 24.3 (CH<sub>2</sub>), 14.7 (CH<sub>3</sub>); IR (ATR, cm<sup>-1</sup>):  $\tilde{\nu}$  = 3242 (s), 2953 (m), 2918 (vs), 2873 (w), 2849 (vs), 1638 (vs), 1622 (vs), 1543 (vs), 1468 (s), 1441 (w), 1373 (s), 1334 (m), 1327 (m), 1268 (w), 1176 (w), 1136 (w), 1082 (vs), 1034 (w), 802 (w), 722 (m), 704 (w), 679 (s), 552 (w), 480 (w), 466 (w); ESI-MS ([M + H]<sup>+</sup>, C<sub>26</sub>H<sub>53</sub>N<sub>2</sub>O<sub>4</sub>): calcd: 457.4000, found: 457.3996.

### Repolymerization

Diol **6** (200 mg, 438 μmol, 1.00 equiv.) and hexamethylene diisocyanate (70.8 μl, 73.7 mg, 438 μmol, 1.00 equiv.) were added into a 1.5 ml screw-cap vial. The mixture was heated to 160 °C until a homogeneous solution formed and was then stirred for another 1 h. After cooling to room temperature, the reaction mixture was dissolved in hexafluoroisopropanol and precipitated into cold methanol. The precipitate was filtered, washed with methanol and dried at 70 °C and 10 mbar to obtain 125 mg of polymer (46%).

## Results and discussion

A literature known ruthenium catalyzed oxidative cleavage was used to synthesize the tricarboxylic acid glyceryl triazolate from high oleic sunflower oil (Scheme 1).<sup>32</sup> The catalytic reaction was first reported by Behr *et al.* in 2013 for the oxidative cleavage of methyl oleate and was further optimized for the oxidative cleavage of high oleic sunflower oil (Scheme 1) by Meier *et al.*<sup>27</sup> Its key features are the use of hydrogen peroxide as a greener oxidant, use of the benign solvents *tert*-butanol and water, and the tolerance towards ester groups as they remain uncleaved during this transformation. The successful isolation of the sunflower oil-based tricarboxylic acid was con-

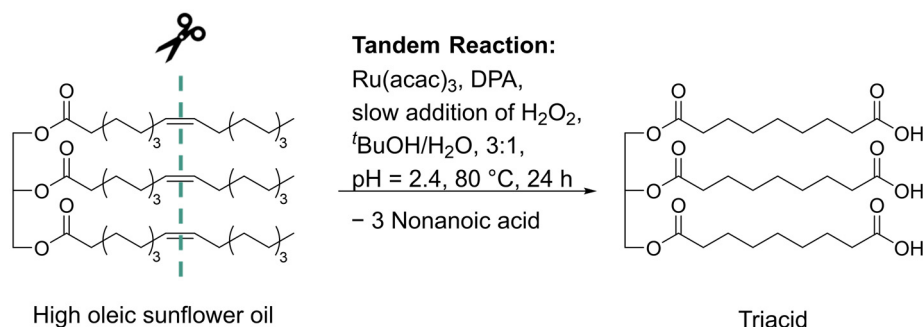

**Scheme 1** Ruthenium catalyzed oxidative cleavage of high oleic sunflower oil (DPA: pyridine-2,6-dicarboxylic acid and Ru(acac)<sub>3</sub>: ruthenium(III) acetylacetonate).




firmed by  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR, and IR spectroscopy as well as mass spectrometry (ESI $^+$ ). In the  $^1\text{H}$  NMR spectrum, a minor methyl proton integral is visible at 0.85 ppm (Fig. S3 $^\dagger$ ). It was assumed that this signal corresponds to the formation of a dicarboxylic acid due to the presence of saturated fatty acid residues in the used sunflower oil, which are inert to the performed reaction. This is reasonable, since the used sunflower oil contained 7% saturated palmitic acid and stearic acid. The small integral of 0.17 corresponds to approximately 5% dicarboxylic acids. Hence, the isolated compound is practicably a tricarboxylic acid and will therefore be referred to as “triacid” in the following. The amount of carboxylic acid groups per gram of sample was determined quantitatively by  $^{31}\text{P}$  NMR spectroscopy according to a procedure introduced by Kilpeläinen *et al.*<sup>29,30</sup> In this method, the carboxylic acid and hydroxyl groups of the sample are first transformed to their corresponding phosphite esters by reaction with 2-chloro-4,4,5,5-tetramethyl-1,3,2-dioxaphospholane and then quantified by  $^{31}\text{P}$  NMR spectroscopy using an internal standard. The determined carboxylic acid value of 4.95  $\mu\text{mol CO}_2\text{H}$  per mg of sample is almost identical to the carboxylic acid value of glyceryl triazolate (4.98  $\mu\text{mol CO}_2\text{H}$  per mg), again confirming the successful synthesis of the desired triacid.

Five model substances (**M1–M5**) were synthesized from the sunflower oil-based triacid, *n*-hexylisocyanide, and the five aldehydes acetaldehyde (**1**), butanal (**2**), hexanal (**3**), nonanal (**4**), and 2-ethylbutyraldehyde (**5**) to investigate the suitability of the triacid for Passerini three-component reactions and to obtain soluble compounds that allow full molecular characterization (Scheme 2). Each model compound was synthesized by stirring all three components for 3 days at room temperature. After purification by flash column chromatography, good

yields between 50% and 70% were achieved. All model compounds were fully characterized by  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR and IR spectroscopy as well as mass spectrometry (ESI $^+$ ). Exemplarily, the  $^1\text{H}$  NMR spectrum of compound **M4** is depicted in Fig. 1. The characteristic signals of Passerini products such as amide protons at 6.03 ppm as well as CH protons of the newly formed  $\alpha$ -acyloxy amide group at 5.13 ppm were detected.<sup>17,18</sup> Moreover, the signals of the glyceryl ester moiety at 5.23 ppm and 4.12–4.27 ppm and those of the  $\alpha$ -CH $_2$  protons of ester groups at 2.29 ppm and 2.36 ppm were observed and they confirmed the successful isolation of the trifunctional Passerini product as a proof of concept.

The sunflower oil-based triacid was then reacted with aldehydes **1–5** and the two difunctional isocyanides 1,6-diisocyanohexane (**a**) and 1,9-diisocyanononane (**b**) for the synthesis of ten different cross-linked polymers *via* the Passerini three-component reaction (Scheme 2). All aldehyde and isocyanide components were chosen to be aliphatic and at least in principle renewable. For instance, 1,6-diisocyanohexane was synthesized from hexamethylenediamine, which can be produced from adiponitrile by hydrogenation.<sup>33</sup> Adiponitrile can be synthesized from ammonia and adipic acid, which in turn can be produced biotechnologically from sugars.<sup>34–36</sup> Another feasible route to hexamethylenediamine from adipic acid is the reduction of adipic acid ester to 1,6-hexanediol, which is then reacted with ammonia to yield the diamine.<sup>33</sup> 1,9-Diaminononane, the starting material for 1,9-diisocyanononane, can most likely be produced in the same way from azelaic acid, which is obtained industrially by oxidative cleavage of oleic acid.<sup>37,38</sup> A biotechnological route to 1,9-diaminononane starting from oleic acid was recently reported by Park *et al.*<sup>39</sup> All unbranched aldehydes occur in natural oils and can

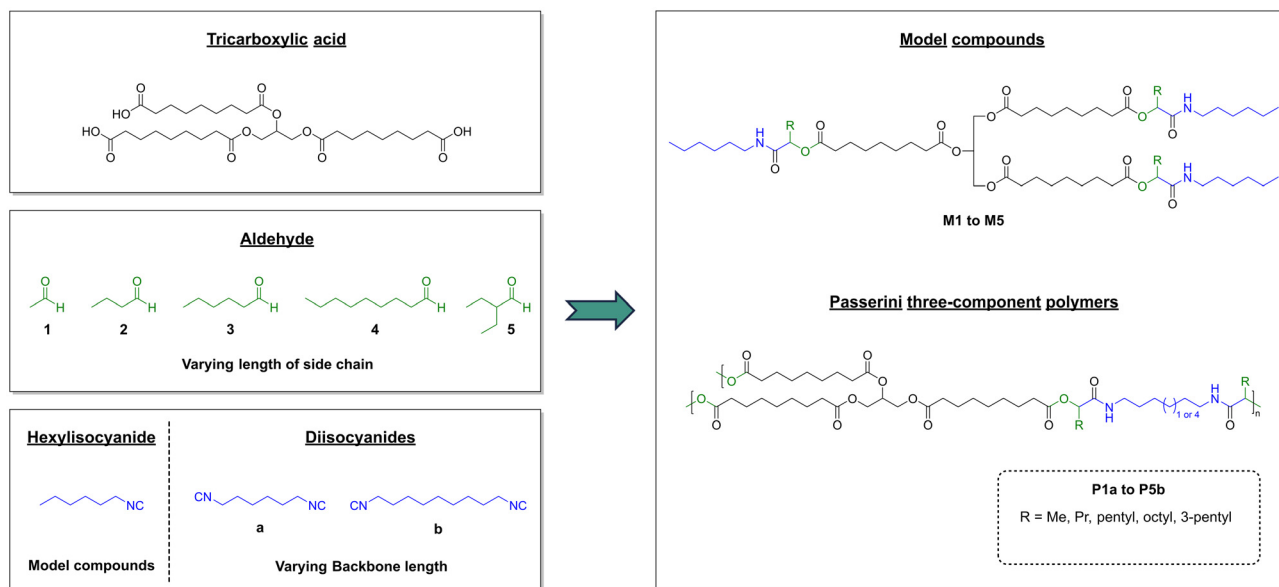

**Scheme 2** Synthesis of model compounds **M1–M5** (top right) and polymers **P1a–P5b** (bottom right) *via* Passerini three-component reaction from the sunflower oil-based tricarboxylic acid, the five aldehydes acetaldehyde (**1**) butanal (**2**), hexanal (**3**), nonanal (**4**), and 2-ethylbutyraldehyde (**5**), and the three isocyanides *n*-hexylisocyanide, 1,6-diisocyanohexane (**a**) and 1,9-diisocyanononane (**b**).





Fig. 1  $^1\text{H}$  NMR spectrum of **M4** in  $\text{CDCl}_3$ . Integrals are referenced to protons **4** of the glyceryl moiety.

further be synthesized by dehydrogenation of the primary alcohols.<sup>40–42</sup> 2-Ethylbutyraldehyde is obtained by aldol condensation of butanal with acetaldehyde and subsequent hydrogenation.<sup>42</sup>

All polymerizations were performed in bulk, as all compounds were liquid at room temperature. First, the three components were mixed at  $-20^\circ\text{C}$  to guarantee a homogeneous mixture of all compounds before the polymerization started, as very rapid curing was observed in bulk. Then, the mixture was cast into a poly(tetrafluoroethylene) form to produce bone shaped samples for tensile strength measurements. Polymers **P1a** to **P3b** (please see Scheme 1 for compound labeling) were cured at  $5^\circ\text{C}$  for 30 minutes to prevent the evaporation of the volatile aldehyde components, while polymers **P4a** to **P5b** were cured at room temperature for 30 minutes. All polymers were further cured at  $50^\circ\text{C}$  for 24 h to guarantee full conversion of functional groups. For polymers **P4a** and **P4b**, a fast reaction was observed as the samples completely solidified after 5 minutes of curing at room temperature, while polymers **P5a** and **P5b** with the sterically more demanding 2-ethylbutyraldehyde took longer to solidify (10 minutes). It is therefore potentially possible to further increase the curing time by incorporating sterically more demanding and/or less reactive substrates into the polymer formulation. The reaction completeness was investigated qualitatively *via* infrared spectroscopy. The IR spectra of the sunflower-oil based triacid, nonanal (**4**), 1,6-diisocyanohexane (**a**), model compound **M4**, and polymer **P4a** are exemplarily depicted in Fig. 2. The characteristic IR signals of the starting materials, such as the  $\text{C}=\text{O}$  stretching vibration of carboxylic acids at  $1703\text{ cm}^{-1}$ , the  $\text{COH}$  combination band of aldehydes at  $2823\text{ cm}^{-1}$  and  $2714\text{ cm}^{-1}$ , and the stretching vibration of isocyanides at  $2146\text{ cm}^{-1}$  were neither visible in the IR spectra of the model compound **M4** nor for polymer **P4a**. In the IR spectrum of **M4**, the characteristic signals of



Fig. 2 Stacked IR spectra of sunflower oil-based tricarboxylic acid, nonanal (**4**), 1,6-diisocyanohexane (**a**), model compound **M4**, and polymer **P4a**. Each IR spectrum is normalized to the strongest absorbance vibration.

amide groups, such as the  $\text{N-H}$  stretching vibration ( $3305\text{ cm}^{-1}$ ), the  $\text{C}=\text{O}$  stretching vibration ( $1655\text{ cm}^{-1}$ ), and  $\text{N-H}$  deformation vibration ( $1537\text{ cm}^{-1}$ ) were observed. The IR spectrum of polymer **P4a** was identical to that of **M4**, thereby confirming the successful P-3CR polymerization with near quantitative conversion of all functional groups.

Swelling tests of all polymers were performed to further evaluate the degree of cross-linking. Each polymer was weighed and immersed in tetrahydrofuran for 3 days at room temperature to allow the complete solubilization of residual unreacted monomeric and oligomeric compounds inside the



material. The polymer was then removed from the solvent, dried at 70 °C and 10 mbar, and weighed again. The gel content is the percentage of mass that is insoluble in THF and is therefore calculated by the division of the dried sample's mass  $m_1$  by the initial sample's mass  $m_0$  (eqn (1)).

$$\text{Gel content (\%)} = \frac{m_1}{m_0} \times 100 \quad (1)$$

The determined values for the gel content of all polymers were between 96% and 99% (Table 1). Hence, both the results obtained from IR spectroscopy and the high gel contents from the swelling tests show that the P-3CR polymerization is suitable for thermosetting applications, as very high conversions and high degrees of cross-linking were achieved.

The thermal stability of all materials was analyzed using thermogravimetric analysis (TGA). The obtained values for the temperature of 5 wt% loss ( $T_{d,5\%}$ ) of polymers **P1a–P5b** ranged from 340 °C to 365 °C and were approximately 20 °C higher than the  $T_{d,5\%}$  values of model compounds **M1–M5** (321 °C to 344 °C). The variation of aldehyde and isocyanide components had almost no influence on the thermal stability, as all polymers and all model compounds decomposed in a temperature range of 10 °C, respectively. Studies by Li *et al.* reported a  $T_{d,5\%}$  value of 335 °C for a P-3CR polymer synthesized from adipaldehyde, 1,6-diisocyanohexane, and undecanoic acid as well as  $T_{d,5\%}$  values ranging from 291 °C to 316 °C for polycaprolactone derivatives synthesized *via* P-3CR from 6-oxohexanoic acid and aliphatic isocyanides.<sup>17,18</sup> For aliphatic poly (ester-amide)s,  $T_{d,5\%}$  values ranging from 267 °C to 290 °C were reported.<sup>43</sup> A degradation temperature of 313 °C was reported for renewable isosorbide containing P-3CR polymers.<sup>44</sup> The herein synthesized cross-linked polymers therefore exhibit an improved thermal stability compared to many linear P-3CR polymers.

Differential scanning calorimetry experiments revealed that all polymers showed glass transition temperatures ( $T_g$ ) below room temperature (Table 1). Exemplarily, all DSC measurements of the polymer series **a** are depicted in Fig. 3.

The glass transition temperature decreased gradually with an increasing aldehyde side chain length from acetaldehyde (**P1a**) at 9 °C to nonanal (**P4a**) at −12 °C. The  $T_g$  of **P5a** was

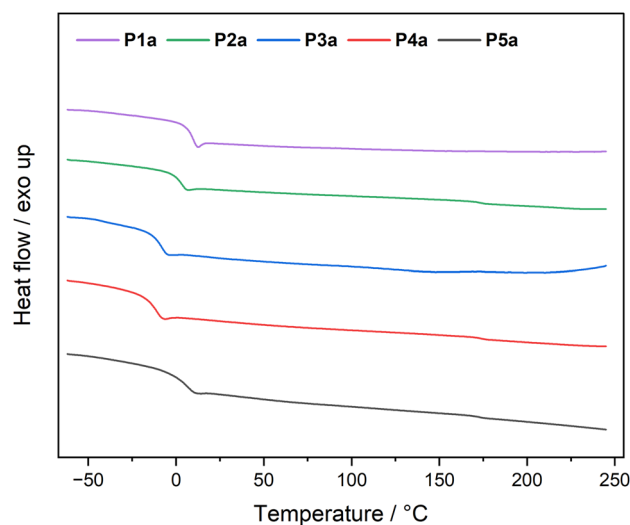


Fig. 3 Differential scanning calorimetry measurements of polymer series **a**.

identical to that of **P2a**, presumably due to the similar steric hindrance of 2-ethylbutyraldehyde and butanal.

The same relationship between  $T_g$  and side chain length was observed for the polymer series **b** (Table 1 and Fig. S31†). Interestingly, every **a** polymer had a slightly higher  $T_g$  than the respective polymer from the **b** series. 1,9-Diisocyanononane (series **b**) is three carbon atoms longer than 1,6-diisocyanohexane (series **a**), resulting, on the one hand, in a lower density of amide groups per repeating unit and thus in less hydrogen bonding and on the other hand in a larger mesh size. Both factors contribute to a higher  $T_g$  in the **a** series.

Tensile strength measurements were performed to evaluate the mechanical properties of all samples. The manufactured samples and one exemplary measurement of **P4a** are depicted in Fig. 4a. All samples were flexible and could be bent by 180 °C without breaking. Moreover, linear elastic regions of at least 20% were observed for each measurement (Fig. S33–S42†). The determined Young's moduli are in the region on rubber-like materials and ranged from 1.24 MPa to 2.16 MPa (Table 1).

Table 1 Polymers **P1a** to **P5b** with their gel content in tetrahydrofuran, temperature of 5 weight% loss ( $T_{d,5\%}$ ), glass transition temperature ( $T_g$ ), Young's modulus, ultimate tensile strength, and their elongation at break. The given error values are standard deviations calculated from three measurements

Polymer	Gel content in THF/%	$T_{d,5\%}/^{\circ}\text{C}$	$T_g/^{\circ}\text{C}$	Young's modulus/MPa	Ultimate tensile strength/MPa	Elongation at break/%
<b>P1a</b>	98 ± 2	363	9	2.16 ± 0.41	1.64 ± 0.29	104 ± 8
<b>P1b</b>	96 ± 2	362	4	1.78 ± 0.40	1.34 ± 0.31	101 ± 2
<b>P2a</b>	96 ± 1	346	3	1.84 ± 0.10	1.45 ± 0.20	105 ± 10
<b>P2b</b>	98 ± 1	365	1	2.11 ± 0.08	1.68 ± 0.21	109 ± 13
<b>P3a</b>	97 ± 2	357	−8	1.86 ± 0.08	1.24 ± 0.03	84 ± 4
<b>P3b</b>	96 ± 2	363	−12	1.44 ± 0.09	0.92 ± 0.14	81 ± 16
<b>P4a</b>	97 ± 1	362	−12	1.24 ± 0.02	0.85 ± 0.01	91 ± 1
<b>P4b</b>	97 ± 1	364	−18	1.27 ± 0.04	0.87 ± 0.05	90 ± 6
<b>P5a</b>	98 ± 1	333	3	1.35 ± 0.04	2.20 ± 0.33	214 ± 26
<b>P5b</b>	99 ± 1	343	0	1.95 ± 0.05	1.98 ± 0.23	146 ± 14







**Fig. 4** Dog bone sample of polymer **P4a** with the associated tensile strength measurements (a) and adhesive test samples prepared from polymer **P5a** and different substrates (aluminum, stainless, wood, PMMA, and borosilicate glass) with the adhesive tests of stainless-steel after 2 h of curing at room temperature (b).

Ultimate tensile strengths were in the range of 0.85 MPa to 2.20 MPa and the determined elongations at break ranged from 81% up to a maximum of 214%. It was observed that the Young's modulus decreases slightly but gradually with an increasing side chain length from **P1a** to **P4b**. Polymers **P2a** to **P5b** showed great reproducibility in the preparation of samples and had standard deviations between 1% and 5% for the Young's modulus and a maximum of 15% for the ultimate tensile strength. The high standard deviations of approximately 20% for **P1a** and **P1b** are attributed to the low boiling point of acetaldehyde and hence a more difficult reproducibility.

Due to the fast curing of all polymers at room temperature, a potential application as "three component glues" was imagined. For this proof of concept, polymer **P5a** was chosen since the sterically more demanding 2-ethylbutyraldehyde significantly increased the curing time and enabled a reproducible manufacturing of adhesive test samples. The substrates to be glued together were prepared by cutting aluminum alloy, stainless-steel, wood, poly(methyl methacrylate), and borosilicate glass into rectangular pieces. Polymer **P5a** was freshly prepared and applied onto two pieces of the same substrate. The two surfaces were then pressed together and cured at room temperature for 2 h. Afterwards, each substrate was measured in triplicate to determine the ultimate tensile strength. The prepared samples and the measurements performed with stainless-steel as the substrate are depicted in Fig. 4b.


The adhesion of **P5a** ranged from 0.94 MPa to 1.17 MPa for all surfaces except for stainless-steel, for which a stronger

adhesion of 1.88 MPa was accomplished. In further experiments, wood surfaces were glued together and measured after 30 minutes, 60 minutes, and 120 minutes had passed (Fig. S46†). Already after 60 minutes of curing at room temperature, no further increase of the tensile strength could be detected, indicating a fully cured glue. These results prove that a multicomponent approach can be used to manufacture new thermosetting glues and that different substrates can be glued efficiently.

Finally, chemical degradation of polymer **P4a** was investigated to demonstrate a possible way to reutilize all components in a second life cycle after the materials reached their end of life. It was assumed that transesterification of **P4a** with methanol yields the three products glycerol, azelaic acid dimethyl ester, and the difunctional  $\alpha$ -hydroxyamide **6** (Scheme 3).

It should be noted that this approach of P-3CR and subsequent transesterification has already been utilized in the literature for the targeted synthesis of  $\alpha$ -hydroxyamides.<sup>45,46</sup> Hence, three grams of **P4a** were suspended in methanol and catalytic amounts of sulfuric acid were added. Intriguingly, the thermoset had completely dissolved after heating the reaction mixture to 65 °C for 5 h. Diol **6** precipitated as a white powder from the reaction mixture while cooling to room temperature and was thus easily isolated by filtration in a yield of 74% (1.26 g). The compound had a high melting point of 162 °C and was poorly soluble in common organic solvents due to the strong hydrogen bonding that originates from its amide groups. The molecular structure was confirmed by mass spec-



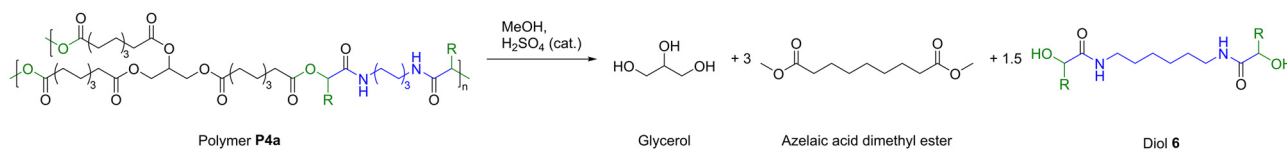

**Scheme 3** Chemical recycling of polymer **P4a** by transesterification with methanol and catalytic amounts of sulfuric acid.

trometry and by NMR spectroscopy in deuterated trifluoroacetic acid (Fig. S49 and S50†). In the  $^1\text{H}$  NMR spectrum, the  $\alpha$  amide proton signal is shifted downfield to 4.63 ppm due to the electron withdrawing effect of the hydroxy group. This was further confirmed by heteronuclear multiple bond correlation (HMBC) spectroscopy that showed correlation between this signal and the quaternary carbon atom of the amide at 180.7 ppm (Fig. S51†). Moreover, the characteristic signals of the amide functionality such as the C=O stretching vibration at  $1638\text{ cm}^{-1}$ , the N–H stretching vibration at  $3243\text{ cm}^{-1}$ , and the N–H deformation vibration at  $1543\text{ cm}^{-1}$  were observed in IR spectroscopy.

Methanol was then removed from the filtrate under reduced pressure. The residue that still contained a mixture of azelaic acid dimethyl ester and glycerol was extracted with ethyl acetate and washed with water to separate both compounds. Azelaic acid dimethyl ester was obtained in high purity by vacuum distillation of the organic phase in a yield of 75% (1.18 g) and glycerol was isolated by vacuum distillation of the aqueous phase in a yield of 30% (68 mg). The low glycerol yield is attributed to the small scale of recycling as 227 mg of glycerol corresponded to 100% yield. The chemical recycling of **P4a** was therefore successful with a simple transesterification approach. Noteworthy, azelaic acid dimethyl ester is an industrially relevant compound, which is used for cosmetic applications and the manufacture of polymers such as polyamides and polyesters.<sup>47–49</sup> It was desired to repolymerize diol **6** with azelaic acid dimethyl ester to show that the recycled compounds can directly be incorporated into a new material. However, several polymerization efforts in bulk at  $160\text{ }^\circ\text{C}$  under 1,5,7-triazabicyclo[4.4.0]dec-5-ene (TBD) catalysis yielded only oligomeric compounds with an average molecular weight of 1900 Da (Fig. S54†). Unfortunately, also other catalysts (*i.e.*  $\text{KOtBu}$  or  $\text{Sb}_2\text{O}_3$ ) did not lead to successful polymerization. The apparently low reactivity of **6** towards transesterification renders this diol with secondary hydroxyl groups impractical for poly(ester-amide) synthesis. Alternatively, it was discovered that diol **6** reacted readily with isocyanates in bulk. A reaction with hexamethylene diisocyanate yielded a poly(amide-urethane) with an average molecular weight of 17 kDa after one hour of reaction time at  $160\text{ }^\circ\text{C}$  (Fig. S55†). The polymer structure was further elucidated *via* NMR spectroscopy (Fig. S56 and S57†). In the  $^1\text{H}$  NMR spectrum, characteristic amide and urethane protons were visible at 6.89 ppm and 5.85 ppm, respectively. The corresponding quaternary carbon signals were observed at 171.5 ppm and 155.8 ppm in the  $^{13}\text{C}$  NMR spectrum. Although the use of isocyanates is rather

unsustainable, we have demonstrated one possible way to reuse this difunctional  $\alpha$ -hydroxyamide. Apart from this polymer application,  $\alpha$ -hydroxyamides are found in pharmaceutical and natural products.<sup>50,51</sup>

## Conclusions

A multicomponent polymerization approach for the synthesis of thermosets from a sunflower oil-derived tricarboxylic acid is presented. The triacid was produced from commercial sunflower oil *via* a ruthenium catalyzed oxidative cleavage, which uses hydrogen peroxide as a greener oxidant.<sup>27,32</sup> As proof of concept for the multicomponent approach, five model compounds were synthesized *via* the Passerini three-component reaction (P-3CR) and fully characterized *via*  $^1\text{H}$  NMR,  $^{13}\text{C}$  NMR, and IR spectroscopy and mass spectrometry. Afterwards, a set of ten P-3CR thermosets was synthesized from the triacid in combination with five monoaldehydes and two diisocyanides. The polymerization proceeds readily at room temperature and was performed without any additional solvents, rendering this process more sustainable. IR spectroscopy of the cured thermosets indicated a quantitative conversion of all aldehyde and isocyanide groups. Gel contents between 96% and 99% in THF point towards high degrees of cross-linking in all materials. Differential scanning calorimetry experiments revealed structure–property relationships, and it was possible to fine-tune the glass transition temperature in a range from  $-18\text{ }^\circ\text{C}$  to  $9\text{ }^\circ\text{C}$  by variation of aldehyde and diisocyanide components. With increasing side chain length and increasing length of the diisocyanide, a gradual decrease of the  $T_g$  was observed. In tensile strength measurements, Young's moduli ranging from 1.24 MPa to 2.16 MPa, and elongations at break between 81% and 214% were determined. The presented system can be used as a “three component glue” since all compounds are liquid and no additional heating was required for curing. After 60 minutes of curing at room temperature, the adhesive exhibited ultimate tensile strengths between 0.94 MPa and 1.88 MPa on aluminum, steel, wood, PMMA, and glass surfaces. Finally, chemical reuse of polymer **P4a** was achieved by transesterification with methanol and catalytic amounts of sulfuric acid. The difunctional  $\alpha$ -hydroxyamide **6** precipitated during recycling and was isolated in a good yield of 74%, while azelaic acid dimethyl ester was obtained by vacuum distillation in a yield of 75%. Eventually, a new polyurethane was synthesized from diol **6** and hexamethylene diisocyanate to exemplify a second life cycle of the recycled compound.



## Author contributions

Luis Santos Correa: conceptualization, data curation, formal analysis, investigation (synthesis and analytics), visualization, and writing – original draft; Silas Leidenheimer: investigation (synthesis); Michael A. R. Meier: conceptualization, resources, supervision, and writing – review & editing.

## Data availability

The data supporting this article have been included within the article and as part of the ESI.†

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors thank Prof. Dr Manfred Wilhelm and Dr Valerian Hirschberg for their support with tensile strength measurements and Alexander Jaks for manufacturing the required customized poly(tetrafluoroethylene) forms. Furthermore, the authors thank Prof. Dr Stefan Bräse, Prof. Dr Jörg Lahann, Prof. Dr Patrick Théato, and Birgit Huber for TGA measurements, Lara Hirsch for mass spectrometric measurements, Timo Sehn for fruitful discussions, and Severin Stalter for his help in the synthesis of a few compounds.

## References

- 1 PlasticsEurope Deutschland e. V., Plastics – the fast Facts 2023, 2023, <https://plasticseurope.org/knowledge-hub/plastics-the-fast-facts-2023/>; access date: 07.11.2024.
- 2 U. Biermann, U. T. Bornscheuer, I. Feussner, M. A. R. Meier and J. O. Metzger, *Angew. Chem., Int. Ed.*, 2021, **60**, 20144–20165.
- 3 L. Montero de Espinosa and M. A. R. Meier, *Eur. Polym. J.*, 2011, **47**, 837–852.
- 4 S. Pandey, B. S. Rajput and S. H. Chikkali, *Green Chem.*, 2021, **23**, 4255–4295.
- 5 J. C. Ronda, G. Lligadas, M. Galià and V. Cádiz, *Eur. J. Lipid Sci. Technol.*, 2011, **113**, 46–58.
- 6 P. T. Anastas and J. C. Warner, *Green Chemistry: Theory and Practice*, Oxford University Press, New York, 1998.
- 7 H. C. Erythropel, J. B. Zimmerman, T. M. de Winter, L. Petitjean, F. Melnikov, C. H. Lam, A. W. Lounsbury, K. E. Mellor, N. Z. Janković, Q. Tu, L. N. Pincus, M. M. Falinski, W. Shi, P. Coish, D. L. Plata and P. T. Anastas, *Green Chem.*, 2018, **20**, 1929–1961.
- 8 I. Ugi, A. Dömling and W. Hörl, *Endeavour*, 1994, **18**, 115–122.
- 9 A. Dömling, W. Wang and K. Wang, *Chem. Rev.*, 2012, **112**, 3083–3135.
- 10 R. C. Cioc, E. Ruijter and R. V. A. Orru, *Green Chem.*, 2014, **16**, 2958–2975.
- 11 M. Passerini, *Gazz. Chem. Ital.*, 1921, **51**, 126–129.
- 12 A. Dömling and I. Ugi, *Angew. Chem., Int. Ed.*, 2000, **39**, 3168–3210.
- 13 L. Banfi, A. Basso, C. Lambruschini, L. Moni and R. Riva, *Chem. Sci.*, 2021, **12**, 15445–15472.
- 14 I. Akritopoulou-Zanze, *Curr. Opin. Chem. Biol.*, 2008, **12**, 324–331.
- 15 O. Kreye, T. Tóth and M. A. R. Meier, *J. Am. Chem. Soc.*, 2011, **133**, 1790–1792.
- 16 X.-X. Deng, L. Li, Z.-L. Li, A. Lv, F.-S. Du and Z.-C. Li, *ACS Macro Lett.*, 2012, **1**, 1300–1303.
- 17 Y.-Z. Wang, X.-X. Deng, L. Li, Z.-L. Li, F.-S. Du and Z.-C. Li, *Polym. Chem.*, 2013, **4**, 444–448.
- 18 J. Zhang, M. Zhang, F.-S. Du and Z.-C. Li, *Macromolecules*, 2016, **49**, 2592–2600.
- 19 S. König and I. Ugi, *Z. Naturforsch., B*, 1991, **46**, 1261–1266.
- 20 H. Bu, A.-L. Kjøniksen, K. D. Knudsen and B. Nyström, *Biomacromolecules*, 2004, **5**, 1470–1479.
- 21 H. Bu, A.-L. Kjøniksen and B. Nyström, *Eur. Polym. J.*, 2005, **41**, 1708–1717.
- 22 A. E. J. de Nooy, D. Capitani, G. Masci and V. Crescenzi, *Biomacromolecules*, 2000, **1**, 259–267.
- 23 V. Crescenzi, A. Francescangeli, D. Capitani, L. Mannina, D. Renier and D. Bellini, *Carbohydr. Polym.*, 2003, **53**, 311–316.
- 24 A. E. J. de Nooy, G. Masci and V. Crescenzi, *Macromolecules*, 1999, **32**, 1318–1320.
- 25 N. Hauck, N. Seixas, S. P. Centeno, R. Schlüsler, G. Cojoc, P. Müller, J. Guck, D. Wöll, L. A. Wessjohann and J. Thiele, *Polymers*, 2018, **10**, 1055.
- 26 W. Lin, T. Sun, M. Zheng, Z. Xie, Y. Huang and X. Jing, *RSC Adv.*, 2014, **4**, 25114–25117.
- 27 L. Santos Correa and M. A. R. Meier, *Eur. J. Lipid Sci. Technol.*, 2023, **125**, 2200171.
- 28 W. C. Still, M. Kahn and A. Mitra, *J. Org. Chem.*, 1978, **43**, 2923–2925.
- 29 A. W. T. King, J. Jalomäki, M. Granström, D. S. Argyropoulos, S. Heikkinen and I. Kilpeläinen, *Anal. Methods*, 2010, **2**, 1499–1505.
- 30 X. Meng, C. Crestini, H. Ben, N. Hao, Y. Pu, A. J. Ragauskas and D. S. Argyropoulos, *Nat. Protoc.*, 2019, **14**, 2627–2647.
- 31 K. A. Waibel, R. Nickisch, N. Möhl, R. Seim and M. A. R. Meier, *Green Chem.*, 2020, **22**, 933–941.
- 32 A. Behr, N. Tenhumberg and A. Wintzer, *RSC Adv.*, 2013, **3**, 172–180.
- 33 B. D. Herzog and R. A. Smiley, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2012.
- 34 M. T. Musser, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2000.
- 35 J. Rios, J. Lebeau, T. Yang, S. Li and M. D. Lynch, *Green Chem.*, 2021, **23**, 3172–3190.
- 36 R. A. Sheldon, *J. Mol. Catal. A: Chem.*, 2016, **422**, 3–12.



- 37 Emery Expands Ozonolysis Plant, *Chem. Eng. News*, 1959, **37**, 25–26.
- 38 C. G. Goebel, A. C. Brown, H. F. Oehlschlaeger and R. P. Rolfes, Method of making azelaic acid, US 2813113, 1957.
- 39 S.-Y. Hwang, J.-M. Woo, G. E. Choi, D.-K. Oh, J.-H. Seo and J.-B. Park, *ACS Catal.*, 2024, **14**, 4130–4138.
- 40 M. Eckert, G. Fleischmann, R. Jira, H. M. Bolt and K. Golka, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2006.
- 41 D. K. Raff, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2013.
- 42 C. Kohlpaintner, M. Schulte, J. Falbe, P. Lappe, J. Weber and G. D. Frey, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2013.
- 43 Y.-T. Guo, C. Shi, T.-Y. Du, X.-Y. Cheng, F.-S. Du and Z.-C. Li, *Macromolecules*, 2022, **55**, 4000–4010.
- 44 Z. Söyler, K. N. Onwukamike, S. Grelier, E. Grau, H. Cramail and M. A. R. Meier, *Green Chem.*, 2018, **20**, 214–224.
- 45 R. M. Carrillo, A. G. Neo, L. López-García, S. Marcaccini and C. F. Marcos, *Green Chem.*, 2006, **8**, 787–789.
- 46 M. Shiri, Z. Gholami-Koupaei, F. Bandehali-Naeini, M.-S. Tonekaboni, S. Soheil-Moghaddam, D. Ebrahimi, S. Karami and B. Notash, *Synthesis*, 2020, 3243–3252.
- 47 A. Fitton and K. L. Goa, *Drugs*, 1991, **41**, 780–798.
- 48 A. Köckritz and A. Martin, *Eur. J. Lipid Sci. Technol.*, 2011, **113**, 83–91.
- 49 B. Cornils and P. Lappe, in *Ullmann's Encyclopedia of Industrial Chemistry*, 2014, pp. 1–18.
- 50 H. A. Schenck, P. W. Lenkowski, I. Choudhury-Mukherjee, S.-H. Ko, J. P. Stables, M. K. Patel and M. L. Brown, *Bioorg. Med. Chem.*, 2004, **12**, 979–993.
- 51 M. R. Wood, K. M. Schirripa, J. J. Kim, S. D. Kuduk, R. K. Chang, C. N. Di Marco, R. M. DiPardo, B.-L. Wan, K. L. Murphy, R. W. Ransom, R. S. L. Chang, M. A. Holahan, J. J. Cook, W. Lemaire, S. D. Mosser, R. A. Bednar, C. Tang, T. Prueksaritanont, A. A. Wallace, Q. Mei, J. Yu, D. L. Bohn, F. C. Clayton, E. D. Adarayn, G. R. Sitko, Y. M. Leonard, R. M. Freidinger, D. J. Pettibone and M. G. Bock, *Bioorg. Med. Chem. Lett.*, 2008, **18**, 716–720.

