

## CRITICAL REVIEW

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *RSC Sustainability*, 2025, 3, 1084

# Phosphorus recovery from animal manures through pyrolysis: phosphorus transformations, release mechanisms, and applications of manure biochars in agriculture

Jesper T. N. Knijnenburg, <sup>a</sup> Siraprapa Suwanree, <sup>b</sup> Duncan Macquarrie, <sup>c</sup> Pornnapa Kasemsiri <sup>b</sup> and Kaewta Jetsrisuparb <sup>\*b</sup>

Phosphorus (P) is a vital element to enhance crop growth, but the excessive application of water-soluble P fertilizers has led to dwindling global P resources and elevated P levels in surface and ground waters. At the same time, high levels of P are excreted by livestock and poultry industries. These animal manures present an attractive source of secondary P, but the direct application of manures to farmlands may cause issues with P losses and environmental and health risks. To overcome this, pyrolysis (the thermal conversion of a biomass in oxygen-poor conditions) has been used in some situations without a full understanding of the impacts of the pyrolysis process on P forms and availability in the manure. This article critically reviews the use of pyrolysis to recover P from three types of animal manures (cow, swine, and poultry) in the form of biochars for applications in agriculture. Specific emphasis is paid to the P species in manures and their transformations during the pyrolysis process with the help of spectroscopic techniques (e.g., <sup>31</sup>P NMR and XANES) and P fractionation schemes. The P concentrations, species, and availability are highly dependent on manure composition and especially pyrolysis conditions. During pyrolysis, the P is concentrated in the solid phase (biochar) and transformed into more inorganic (orthophosphate) and more crystalline forms as the pyrolysis temperature increases. Higher pyrolysis temperatures reduce the P extractability, which lowers the risk for P losses but may also affect plant P uptake. Strategies to modify P availability are presented and critical perspectives are given on the risks and limitations of manure-derived biochar application in agriculture.

Received 28th August 2024

Accepted 27th January 2025

DOI: 10.1039/d4su00524d

[rsc.li/rscsus](https://rsc.li/rscsus)

## Sustainability spotlight

The pyrolysis of animal manures to recover phosphorus in the form of biochars addresses sustainability issues by contributing to both waste management (*i.e.*, the transformation of manures into clean, phosphorus-rich materials), agriculture (*i.e.*, enhancing soil fertility and crop growth by returning phosphorus to the soil), and reduced dependence on phosphorus fertilizers derived from increasingly scarce phosphorus deposits. The P concentrations and species transformation in the manure biochars and their agronomic effectiveness are highly dependent on the manure composition and pyrolysis conditions, which are reviewed in this work. This aligns with the UN sustainable development goals on zero hunger (SDG 2), clean water and sanitation (SDG 6), and responsible consumption and production (SDG 12).

## 1. Introduction

Phosphorus (P) is an indispensable element for all life, and large amounts of P are required in agriculture to meet crop demands to feed the growing world population.<sup>1</sup> Nearly all P in fertilizers originates from non-renewable phosphate rock, of which the largest deposits are in Morocco, Western Sahara,<sup>2</sup> and (as recently discovered) in Norway.<sup>3</sup> Some estimates suggest that

phosphate rock may be depleted within the next 30–300 years.<sup>4</sup> Furthermore, the use of P in agriculture is largely a linear process (from phosphate rock into P sinks). It is estimated that only around 20% of the mined P is consumed by humans,<sup>5</sup> and approximately 3–10% of the P applied to croplands is lost through runoff, erosion, and leaching.<sup>6–8</sup> In the former EU15 countries, these losses have been estimated at approximately 0.1 Tg P per year,<sup>7,8</sup> while globally, combined losses from runoff, erosion, and leaching are estimated at 3.0 Tg P per year.<sup>6</sup> Although P losses from agricultural lands have greatly decreased in the last decades, agriculture still heavily relies on synthetic P fertilizers from non-renewable P sources like phosphate rock.<sup>5,6</sup> The agricultural P flows urgently need to be

<sup>a</sup>International College, Khon Kaen University, Khon Kaen 40002, Thailand<sup>b</sup>Department of Chemical Engineering, Khon Kaen University, Khon Kaen 40002, Thailand. E-mail: [kaewta@kku.ac.th](mailto:kaewta@kku.ac.th); Fax: +6643362142; Tel: +6643362240<sup>c</sup>Department of Chemistry, University of York, York YO10 5DD, UK

converted into a fully circular system by using P from secondary raw materials,<sup>9,10</sup> which can only be done if P in waste streams is effectively fed back to the soil into the food chain.

At the same time, P-rich waste streams are produced in large quantities. Animal manures are comprised of animal excreta (feces and urine) mixed with bedding materials and wasted feed that is used for fertilization of land. Manure presents an ideal secondary P source because it is renewable, has high P concentration, and is available in large quantities on livestock farms. In the United States alone it was estimated that approximately  $1.4 \times 10^{12}$  kg (1.5 billion tons) of manure was produced in 2017, the large majority of which is from beef cattle (78%) followed by dairy (19%), horse (3%), poultry (0.07%), and swine (0.04%).<sup>11</sup> The excreted P in these manures sums up to a total of  $2.3 \times 10^9$  kg per year in 2017.<sup>11,12</sup> Phosphorus excretion rates per animal have been estimated at 9–28 kg P per individual per year for cows, 3 kg P per individual per year for swine, and 0.12–0.35 kg P per individual per year for poultry.<sup>13</sup> Manure thus presents a considerable source of P that is cycled back into the soil and enhances crop yields. Historically, there was little reliance on external P sources and all P from both farm and domestic wastes was recycled back onto the farmlands. But with the emergence of P fertilizers, the fraction of such recycled P has decreased; approximately 50% of P on agricultural lands originated from animal manures in 1961, which dropped to 32% in 2013.<sup>6</sup> At the same time, livestock farming has become significantly more intensive during the past few decades, leading to increased manure production. The manure is often applied to relatively small agricultural areas, typically with the aim to meet N requirements of the crops, which results in nutrient surpluses in the soil.<sup>11,14–16</sup> This overapplication of manures to farmlands may lead to environmental issues and the subsequent leaching of P into rivers by both surface and subsurface pathways, causing significant deterioration in water quality and biodiversity.<sup>17,18</sup> In addition, animal manures may contain heavy metals, pathogenic bacteria, hormones and antibiotics, and the direct disposal of manure to the environment could result in the release of such pollutants to soil, air, and water bodies.<sup>19</sup> Moreover, the improper storage and handling of manure presents a risk to human and animal life due to the potential transmission of zoonotic pathogens to food and water.<sup>20</sup>

Biochars are produced by the thermochemical conversion (pyrolysis) of a biomass under oxygen-limited conditions. During pyrolysis, the organic matrix is largely thermally decomposed and a carbonaceous material rich in inorganics is left behind. In the case of manure, when manure undergoes pyrolysis the solid material has a greatly reduced volume compared to the unpyrolyzed manure, resulting in higher P concentrations and easier storage and transportation. Pyrolysis can eliminate pathogens, antibiotics, steroids, and other micropollutants,<sup>14,21</sup> which reduces the environmental and health risks of biochars compared to the raw manure. When the thermal treatment is carried out in a closed system under wet conditions, the process is known as hydrothermal carbonization (HTC), which produces a hydrochar.<sup>22</sup> The HTC process has distinct advantages over pyrolysis when wet biomasses are used

since drying of the feedstock is not necessary, and a lower energy input is required because of the lower operating temperatures (typically 180–250 °C) than pyrolysis.<sup>22</sup> Compared to (hydro)thermal treatment, alternative P recovery approaches from manure such as pelleting or composting have high transportation cost, whereas precipitation of P through the formation of Ca phosphates and/or Mg phosphates is limited by the high organic matter contents of manure.<sup>18</sup> Pyrolysis has some advantages over incineration in that pyrolysis results in the generation of combustible gases that can be used for energy generation, and P availability from biochars is generally higher than from ashes.<sup>18,23</sup> Moreover, compared to other manure management techniques, pyrolysis leads to lower greenhouse gas emissions.<sup>14</sup>

Several authors have reviewed the P transformations in thermal conversion of biomasses.<sup>14,24–29</sup> Most notably, the article by Huang *et al.*<sup>27</sup> provides an excellent review of P speciation and transformation in (hydro)thermal treatment of a wide range of solid biowastes, and the extensive article by Lidman Olsson *et al.*<sup>28</sup> gives a very comprehensive insight into the P chemistry in thermal conversion of biomasses. Rathnayake *et al.*<sup>14</sup> provide a holistic view of the potential and limitations of manure pyrolysis to provide energy and biochar. Other reviews have focused specifically on the P recovery from sewage sludges through thermal processes.<sup>9,30</sup> Recent review articles on livestock manures present P recovery techniques<sup>31</sup> and a bibliometric review on the established literature,<sup>32</sup> or focus on manure pyrolysis for bioenergy<sup>33</sup> or soil remediation.<sup>34</sup> The P transformations in manures and other biomasses during HTC and comparisons with pyrolysis have been discussed in several recent review articles.<sup>25,27,30,35</sup>

This critical review provides specific insight into the P recovery from manures through pyrolysis for applications in agriculture. The article focuses on P species in primarily three types of manures (cow, swine, and poultry). Transformations of the P species during pyrolysis are discussed with the focus on spectroscopic techniques, fractionation schemes, solubility/extractability, and availability to plants. Furthermore, process steps to enhance the P availability are briefly discussed and the article finishes with a critical discussion on limitations and provides future perspectives.

## 2. Phosphorus content and species in manures

### 2.1 Concentrations of phosphorus and metal cations in manures

Fig. 1 provides an overview of the typical P concentrations together with major cations in manures of different animals. Generally, poultry and swine manures contain higher P contents than cow manure. Phytate, the main P storage form in plant seeds, cannot be broken down by monogastric animals like swine and poultry because of the low activity of phytase enzymes in the gut.<sup>71</sup> To overcome this, the feed has been traditionally supplemented with inorganic P sources, which has led to higher P excretion.<sup>72,73</sup> Nowadays it is more common to



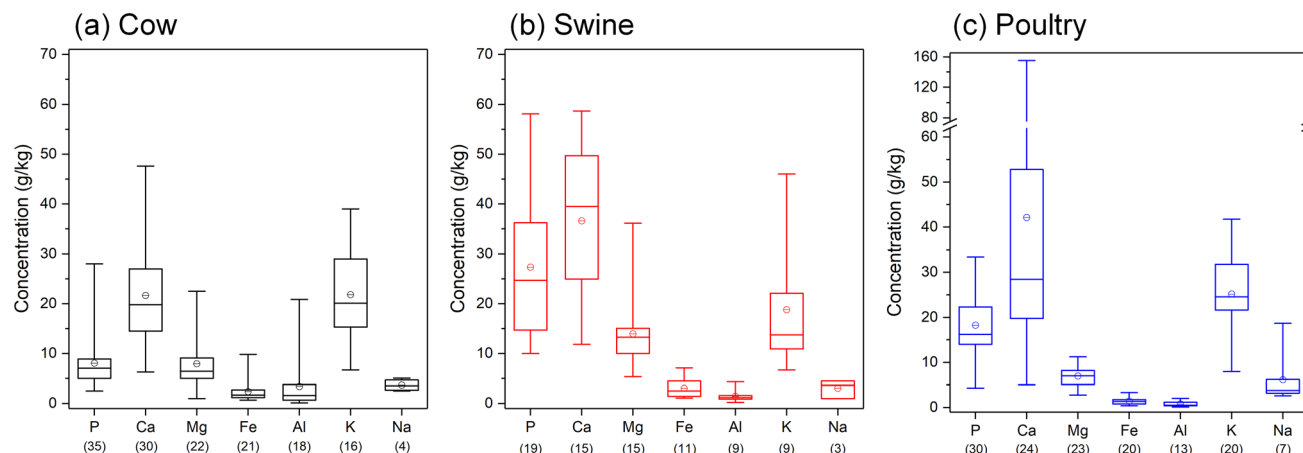


Fig. 1 Typical concentrations of P and major cations in manures of (a) cow, (b) swine, and (c) poultry. The values in the boxes represent the median (middle line) with the first (25%) and third (75%) quartiles, and whiskers represent the minimum and maximum values. Circles indicate the mean values. The values in brackets below each element indicate the number of data points used for that element. Figures are compiled from various literature sources for cow,<sup>36–54</sup> swine,<sup>21,36,38–40,43,45–48,54–60</sup> and poultry manures.<sup>36,38,40,43–45,47,51,53–55,59,61–70</sup>

add phytase in the diet of monogastric animals to break down the organic P, which substantially increases the P availability and utilization and in turn reduces P excretion.<sup>73–75</sup> Even though ruminant animals (like cows and sheep) can digest phytate, the P use efficiency is only about 40%, and consequently a large proportion of the P is excreted.<sup>73</sup> Within species, manure P contents may differ due to, *e.g.*, diet, growth stage, physiology, size, and manure handling.

The P in manures does not exist as free (ortho)phosphate ions but is frequently bound to metal cations. When considering the recovery and availability of P, the presence of such cations should be considered as well, because the binding ion may (greatly) affect the P release. In all manures, the major cation is calcium (Ca), which is typically present in the order of 10–50 g kg<sup>−1</sup> but may be as high 160 g kg<sup>−1</sup>. The presence of Ca and magnesium (Mg) is especially important; several studies have demonstrated that the P mobility is related to the Ca and Mg concentrations in manures, and that high Ca contents decrease the P release.<sup>36,76–78</sup> After Ca, the second most abundant metal is potassium (K, 6–46 g kg<sup>−1</sup>) followed by Mg (1–36 g kg<sup>−1</sup>). Concentrations of iron (Fe), aluminum (Al), and sodium (Na) are relatively minor and are generally below 5 g kg<sup>−1</sup>.

## 2.2 Phosphorus species in manures

In addition to the P content, the form in which the P is present in manures is also crucial to understand because the species greatly influences its release, mobility, and bioavailability, and may also affect the P recovery approach. The P forms and their availability may be affected by a number of factors such as manure storage,<sup>79–81</sup> drying conditions,<sup>39,82</sup> and animal diet.<sup>42</sup> The most common P forms in manures are highlighted in Fig. 2.<sup>83,84</sup> The simplest form is orthophosphate, which can be present as deprotonated (PO<sub>4</sub><sup>3−</sup>) or protonated (HPO<sub>4</sub><sup>2−</sup> and H<sub>2</sub>PO<sub>4</sub><sup>−</sup>) forms. Two orthophosphate molecules can condense to form a pyrophosphate (P<sub>2</sub>O<sub>7</sub><sup>4−</sup>) molecule. Further condensation leads to the formation of polyphosphates, the length of

which may reach up to several thousand units.<sup>85</sup> Inorganic P accounts typically for 50–75% of the total P in manures,<sup>43,45</sup> but also higher values have been reported.<sup>36</sup> Organic P in biomasses is where the P is bound to carbon in the form of phosphoester (P–O–C) linkages. Examples of phosphate monoesters include phytate (inositol hexakisphosphate), which is the main P storage form in seeds. Phosphate diesters include DNA, RNA, and phospholipids. Examples of organic pyrophosphates and triphosphates are ADP and ATP, respectively.

The identification and quantification of the P species in the manures is challenging because of the complex and varying nature of the manure composition. A powerful tool that can be used to provide insight into the P species is <sup>31</sup>P nuclear magnetic resonance (NMR) spectroscopy. Compared to solid state NMR spectroscopy, solution <sup>31</sup>P NMR has the advantages of narrow peaks that can be easily defined, but a disadvantage is that the P needs to be extracted from the matrix first. Among extractants, most commonly a NaOH-EDTA solution has been used.<sup>86</sup> However, the use of improper extraction conditions could affect the P extractability and the disappearance of peaks for specific P forms.<sup>61,87,88</sup> Other extractants like DI water may be preferred in some situations.<sup>89</sup> Fig. 3 provides an overview of the P species that have been identified in manures with solution <sup>31</sup>P

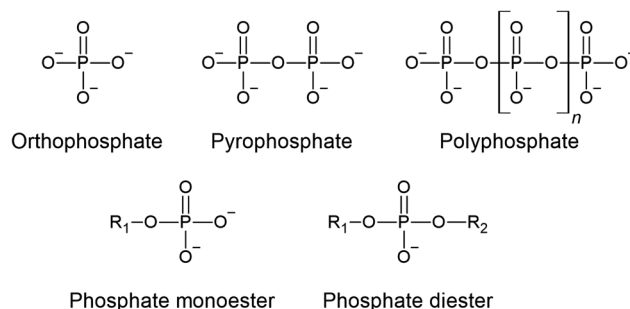


Fig. 2 Structures of typical P forms found in animal manures.



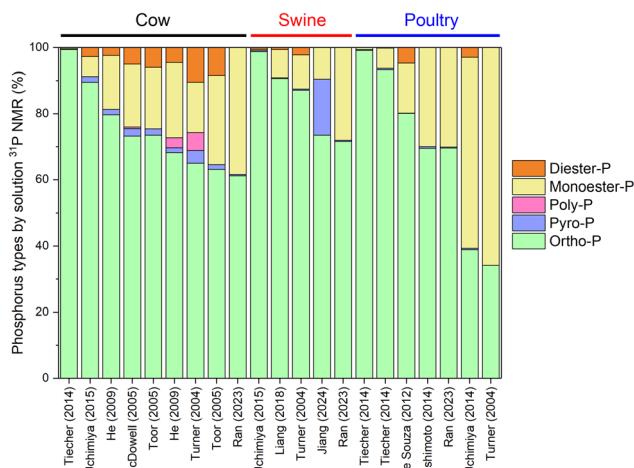


Fig. 3 Overview of phosphorus types in cow, swine, and poultry manures as analyzed by liquid phase  $^{31}\text{P}$  NMR spectroscopy using data from various sources.<sup>21,36,42,45,57,61,77,90–94</sup>

NMR spectroscopy. By far, the most common P form in manures is orthophosphate, which in most manures accounts for more than half of the total P present. Small amounts of condensed phosphates like pyrophosphate or polyphosphate may be present, but these usually contribute only a small fraction of the P. Monoester phosphates make up another large fraction, primarily in the form of phytate. When comparing manures of different animals, poultry manure tends to have higher organic P concentrations than swine and cow manures. Unlike ruminant animals like cows and sheep, monogastric animals like swine and poultry have insufficient phytase activity in the gut, so the phytic acid cannot be digested and dietary phytate will be excreted if no phytase is included in the diet.<sup>71</sup>

A different approach to specify the P species in manures is by fractionation based on the different solubilities of the different P forms.<sup>79,95–98</sup> Hedley *et al.*<sup>99</sup> developed a protocol to separate P forms in soils, which was later adapted for manures,<sup>91,95,100</sup> digestates,<sup>97</sup> and biochars.<sup>101,102</sup> In this procedure, the solid is sequentially extracted with extractants of increasing strength, typically DI water, 0.5 M  $\text{NaHCO}_3$ , 0.1 M NaOH, and 1 M HCl. Durations of each step and solid:liquid ratios may vary between laboratories. The obtained P fractions can be described as readily water-soluble P ( $\text{H}_2\text{O-P}$ ), labile P that is readily available to plants ( $\text{NaHCO}_3\text{-P}$ ), lesser available inorganic P that is associated with Al and Fe compounds ( $\text{NaOH-P}$ ), and inorganic P associated with or trapped in acid-soluble minerals such as apatites ( $\text{HCl-P}$ ).<sup>103,104</sup> Any P that is not extracted in these combined steps is the residual P ( $\text{Res-P}$ ). Higher  $\text{H}_2\text{O-P}$  values may suggest a higher risk for short-term P losses.<sup>102,105,106</sup> The inorganic P (*i.e.*, orthophosphate) concentrations in each fraction are usually measured with UV-vis spectroscopy *via* either molybdenum blue method or malachite green method. To determine the total P in each fraction, each liquid extract undergoes digestion to convert all organic and condensed P into orthophosphate.<sup>107</sup> The total P (now in orthophosphate form) is measured spectroscopically, and the organic P (which also

includes condensed P forms) is taken as the difference between total P and inorganic P. Fractionation procedures have been employed in combination with  $^{31}\text{P}$  NMR measurements<sup>38,46,108</sup> or enzymatic hydrolysis<sup>40,63,81,109</sup> to get further insight into the P species.

Fig. 4a provides an overview of typical distributions of sequential P extracts from cow, swine, and poultry manures. Generally, the P in cow manures is highly labile: the majority (50–87%) of the P is found in the labile P fractions ( $\text{H}_2\text{O-P} + \text{NaHCO}_3\text{-P}$ ), suggesting a high P availability. Because water-extractable P concentrations can estimate the P in runoff from soil-applied livestock manures,<sup>106</sup> highly labile P may thus also indicate a high risk for P dissolution into runoff. The NaOH-P fraction of cow manure contains 6–21% of total P, and the HCl-P and Res-P together may contain 5–37% of total P. Similar P distributions are found in swine manure, with  $\text{H}_2\text{O-P} + \text{NaHCO}_3\text{-P}$  (labile P) values of 38–78%, NaOH-P of 5–51%, and HCl-P + Res-P ranging from 11 to 46%. Compared with cow manure, swine manure tends to have less labile P and more NaOH-P. The P in poultry manures, on the other hand, is less readily extractable with a large fraction in HCl-P. The labile P ( $\text{H}_2\text{O-P} + \text{NaHCO}_3\text{-P}$ ) accounts for 31–69%, NaOH-P is around 3–20% and HCl-P + Res-P is 17–59%. Similar distributions in P species were found with other fractionation procedures.<sup>36</sup>

The extracted P fractions can be further separated into inorganic and organic P. The  $\text{H}_2\text{O-P}$  and  $\text{NaHCO}_3\text{-P}$  fractions of cow, swine, and poultry manures consist mostly of inorganic P

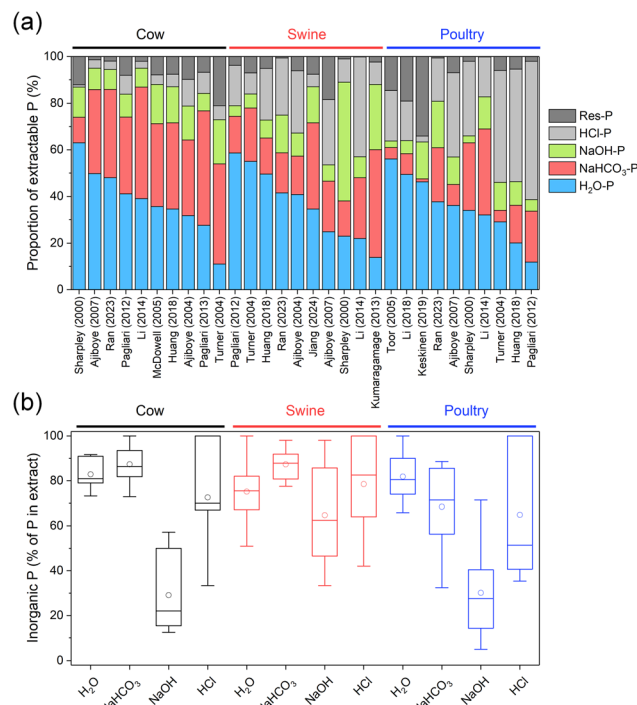


Fig. 4 (a) Phosphorus distribution in sequential extracts of cow, swine, and poultry manures based on data from various sources.<sup>38–41,43,45,57,61,67,77,90,100,110–112</sup> (b) Percentage of inorganic P in each extract for cow ( $n = 7$ ), swine ( $n = 6$ ), and poultry manures ( $n = 8$ ), based on data from various sources.<sup>38,40,43,45,63,100,111</sup>



(Fig. 4b), whereas the NaOH fractions are richest in organic P. As confirmed by  $^{31}\text{P}$  NMR measurements, the labile P fractions ( $\text{H}_2\text{O-P}$  and  $\text{NaHCO}_3\text{-P}$ ) contain mainly orthophosphate whereas organic P (mainly phytate) is primarily extracted in the NaOH fraction.<sup>38,46,108</sup> Others have used P K-edge X-ray absorption near edge spectroscopy (XANES) spectroscopy to identify the P species in fractional extracts of various manures.<sup>38,77</sup> Pagliari and Laboski<sup>40</sup> analyzed manure samples from 7 species (beef and dairy cattle, swine, chicken, turkey, dairy goat, horse, and sheep) by sequential fractionation. They found a clear division between ruminant + horse and non-ruminant animals. For manures from ruminants and horse, most inorganic P was extracted with  $\text{H}_2\text{O}$  and  $\text{NaHCO}_3$ , whereas in non-ruminant species a large inorganic P fraction was also extracted with HCl. Non-ruminant animals had much higher total P and inorganic P contents in manure than ruminant + horse.

The Standards, Measurements, and Testing (SMT) harmonized protocol was developed by Ruban *et al.*<sup>113</sup> for extractable P contents in freshwater sediments. This non-sequential procedure divides the P forms into five fractions: NaOH-extractable P (NaOH-P, which is P bound to Al, Fe, and Mn oxides and hydroxides), HCl-extractable P (HCl-P, which is P associated with Ca), inorganic P (IP), organic P (OP), and total P (TP). The NaOH-P and HCl-P are frequently referred to as non-apatite inorganic P (NAIP) and apatite P (AP), respectively.<sup>96</sup> While developed for sediments, this protocol has been occasionally used for P speciation in manures. García-Albacete *et al.*<sup>96</sup> found that pig slurry consisted mainly of inorganic P (95% of total P), which in turn consisted largely of AP (51% of total P) followed by NAIP (35% of total P). Tuszynska *et al.*<sup>98</sup> found that the P fractions in livestock manures decreased in order  $\text{AP} > \text{NAIP} > \text{OP}$ . Similarly, Zuo *et al.*<sup>114</sup> measured that chicken manure consisted of 16% OP, 41% NAIP, and 43% AP, and dairy manure contained 7% OP, 60% NAIP, and 33% AP.

Solid state characterization techniques have been applied mainly to provide a qualitative indication of the P species. For example, using solid state  $^{31}\text{P}$  NMR analysis, different P species have been identified in poultry manure,<sup>115</sup> dairy manure,<sup>42</sup> swine feces,<sup>56</sup> and sheep feces.<sup>116</sup> Other researchers have used P K-edge XANES to differentiate between P forms.<sup>21,38,57,77,91,110,117</sup> X-ray diffraction (XRD) has been used to analyze crystalline P forms of manures.<sup>45,56,57,116,117</sup> However, due to the limited resolution of solid-state techniques,<sup>118</sup> researchers have primarily employed liquid-phase techniques to quantify different P species with higher specificity.

### 3. Phosphorus transformations during pyrolysis of manures

#### 3.1 Phosphorus concentration in manure biochars

Pyrolysis is the thermochemical conversion of a carbonaceous feedstock in an oxygen-limited environment at temperatures usually ranging from 300 to 800 °C. As the temperature is increased during pyrolysis, weight loss takes place by moisture loss followed by decomposition of hemicellulose, cellulose, and lignin.<sup>119</sup> Different products are generated, namely gases ( $\text{CO}_2$ ,

$\text{CO}$ ,  $\text{CH}_4$ , and small hydrocarbons), liquid (bio-oil), and solid (biochar), with their relative proportions depending on the operating conditions. For example, fast pyrolysis has high heating rates ( $\sim 10\text{--}200\text{ K s}^{-1}$  but can be up to  $2500\text{ K s}^{-1}$  for flash pyrolysis) and short residence times ( $\sim 0.5\text{--}10\text{ s}$ ) and is used for the maximization of bio-oil production. Slow pyrolysis, on the other hand, uses extended residence times (order of minutes to hours) with modest heating rates ( $\sim 0.1\text{--}2\text{ K s}^{-1}$ ) and maximizes the formation of biochar.<sup>120,121</sup> Most studies have used slow pyrolysis for the recovery of P from animal manures due to the simple and cost-effective setup, although fast pyrolysis has been investigated as well.<sup>122,123</sup>

Phosphorus retention in manure biochars is high, and on average 89.9% (ranging from 68.5 to 118.6%) of the P is retained (Fig. 5). These values are based on measurements of biochar yield and P concentrations in the manure and biochars, and values deviating from 100% are likely due to measurement uncertainties and possibly losses due to particle entrainment in the gas flow.<sup>28</sup> Measurements on pyrolysis of wetland plants have shown that small amounts of P may escape the solid phase and end up in the gaseous or liquid products.<sup>125,126</sup> The transfer of P to the gas phase *via* carbothermic reduction and possibly decomposition of organically bound phosphorus may take place but is generally neglectable below 900 °C.<sup>28,127</sup> Thus, practically all P is retained in the biochar.

The main factors that affect the biochar properties (including P content, species, and availability) are the pyrolysis temperature, raw material, and the duration of the pyrolysis process (also called the holding time or residence time).<sup>24</sup> Compared to other parameters, the holding time tends to be less influential on the biochar properties,<sup>52,128–130</sup> and the effect

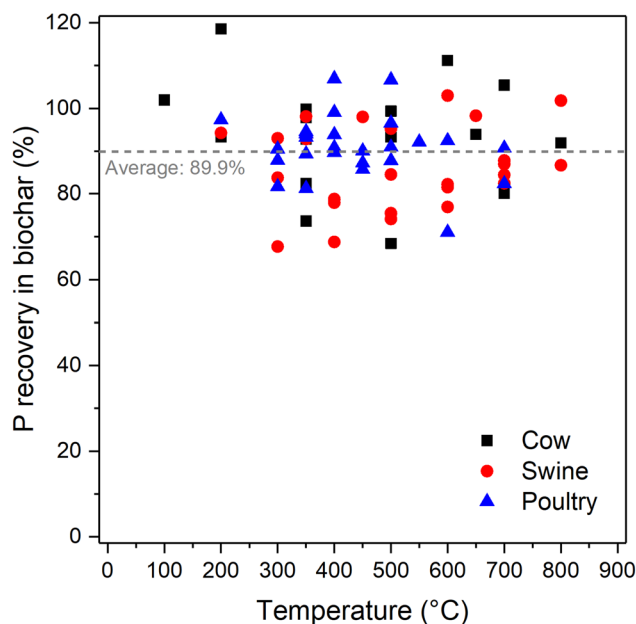


Fig. 5 Phosphorus recovery in biochars produced from cow ( $n = 15$ ), swine ( $n = 25$ ), and poultry manure ( $n = 25$ ). The average value of 89.9% is calculated over all temperatures and manure types. Values are based on data from various sources.<sup>47–50,56,57,59,65,68–70,124</sup>



of holding time is greater at low temperatures than at high temperatures.<sup>131</sup> In biochars prepared from agricultural residues, longer pyrolysis times (1, 2, and 4 h) increased or did not affect the total P and water-soluble P concentrations, depending on the feedstock composition and pyrolysis temperature.<sup>129</sup> Across all pyrolysis temperatures and biomass types, Zhang *et al.*<sup>24</sup> concluded that pyrolysis processes that are longer than 2 h increase the proportion of stable P when compared to holding times of 2 hours or less.

Because of the thermal decomposition of the organic matrix and retention of P in the solid material, the biochar yield decreases<sup>132</sup> and P concentration in biochars increases with pyrolysis temperature (Fig. 6a–c). Total P concentrations up to 79 mg g<sup>-1</sup> have been reported,<sup>56</sup> depending on the manure and the pyrolysis temperature. Raw materials with a higher innate P concentration will result in more P-rich biochars. For example, Liu *et al.*<sup>48</sup> reported that the P content in cow manure biochar increased from 13.7 mg g<sup>-1</sup> (raw manure) to 15.6, 26.5, 29.4, 32.3, and 32.5 mg g<sup>-1</sup> when pyrolyzed at 200, 350, 500, 650, and 800 °C, respectively. At the same temperatures, the P concentration of pig manure biochars were higher and increased from 20.8 mg g<sup>-1</sup> to 23.3, 37.5, 43.1, 44.8, and 44.5, respectively,

whereas P concentrations in sheep manure biochars were lower (from 8.0 mg g<sup>-1</sup> to 8.9, 13.9, 16.0, 17.4, and 17.9 mg g<sup>-1</sup>, respectively).<sup>48</sup> When normalized by the P concentration, a common trend is observed across all manure types (Fig. 6d–f). The P concentration is approximately doubled at around 400–500 °C and in some cases may reach triple the initial concentration at higher temperatures. This is a good prospect for agriculture and waste management, providing a solid material with a high P concentration and low volume.

### 3.2 Transformation of P species during pyrolysis

To track the P species during the thermal conversion process, various authors have used <sup>31</sup>P NMR spectroscopy on alkaline (NaOH-EDTA) extracts of the manure biochars.<sup>21,56,57,92,93</sup> Example of liquid phase <sup>31</sup>P NMR spectra of NaOH-EDTA extracts of swine manure and its derived biochars prepared at 300–700 °C are shown in Fig. 7a from the work of Liang *et al.*<sup>21</sup> Swine manure presented peaks of orthophosphate, pyrophosphate, monoester-P, and diester-P. The monoester-P and diester-P signals have disappeared upon pyrolysis >400 °C. At the same time, the pyrophosphate signal increased at 300 °C

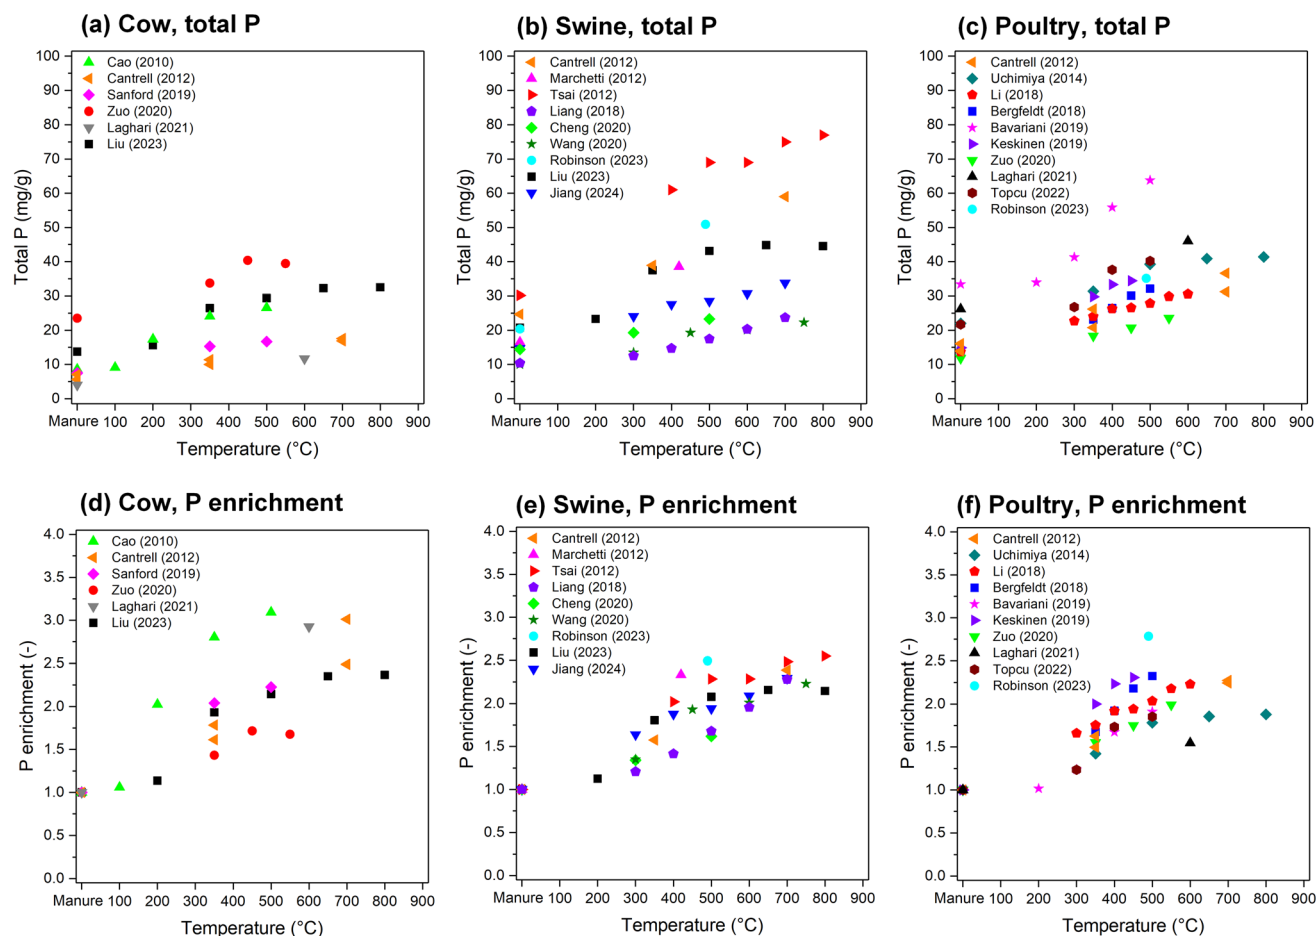


Fig. 6 (a–c) Total P and (d–f) P enrichment (P concentration in biochar divided by P concentration in the manure) of biochars prepared from (a and d) cow, (b and e) swine, and (c and f) poultry manures as function of pyrolysis temperature. Data were taken from various sources and references are indicated in the figures.<sup>21,47–51,56–59,65,67,69,70,92,101,112,114</sup>

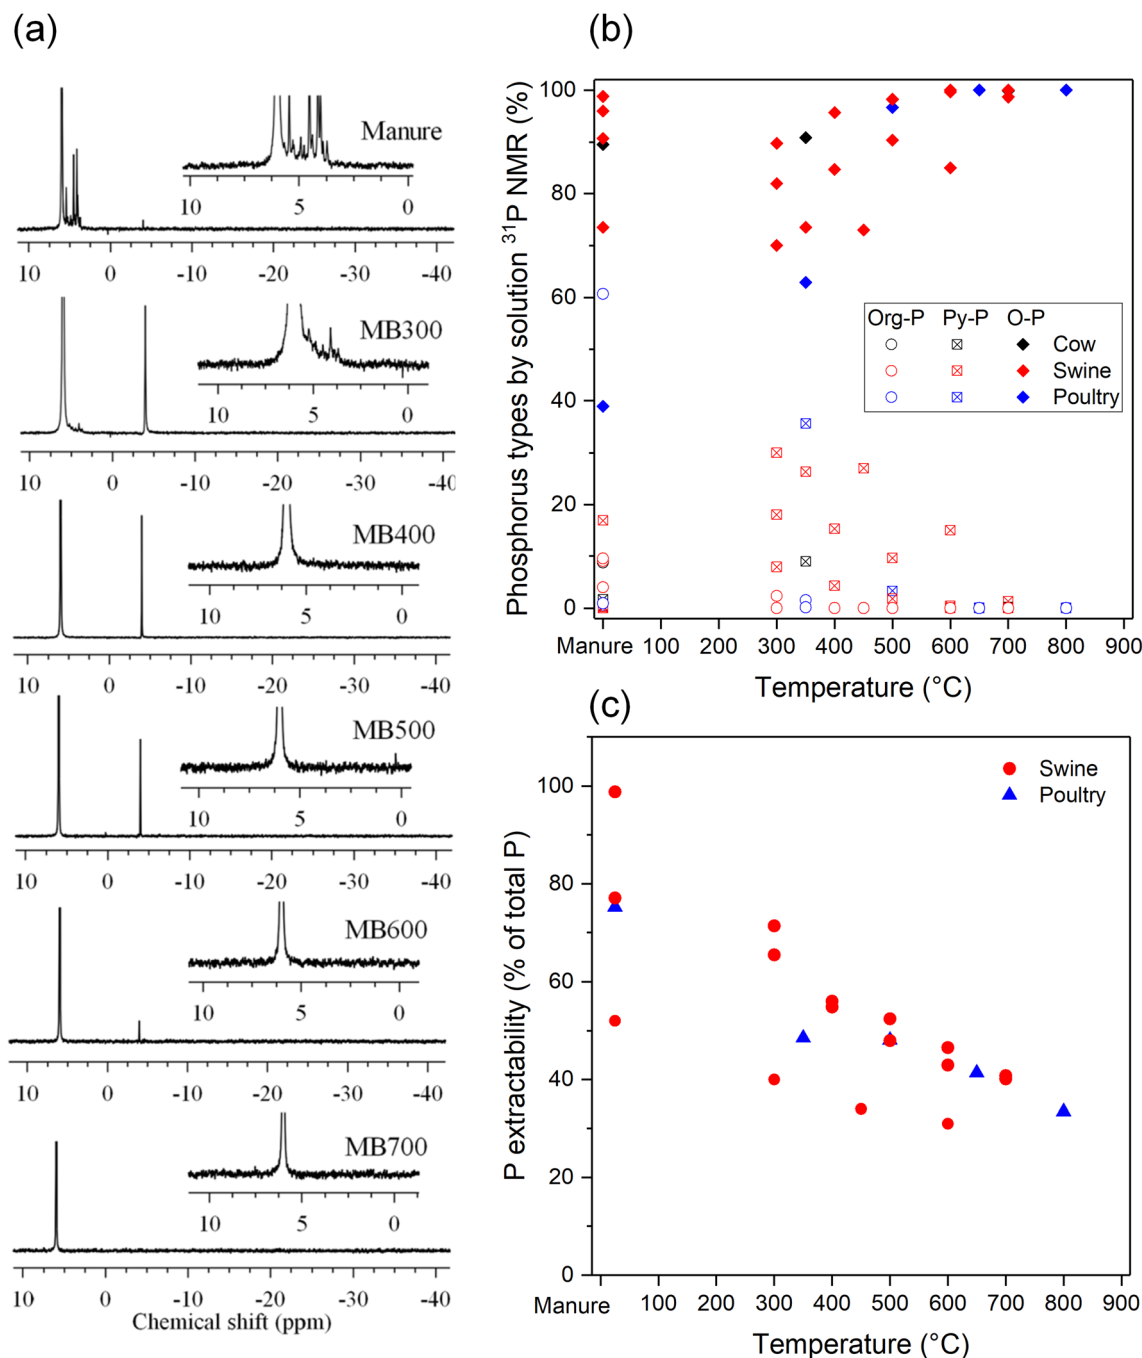


Fig. 7 (a) Liquid phase  $^{31}\text{P}$  NMR spectra of NaOH-EDTA extracts of swine manure and its derived biochars prepared at 300–700  $^{\circ}\text{C}$ . Peaks were assigned to orthophosphate ( $\delta = 6.0$  ppm), pyrophosphate ( $-4.12$  ppm), monoester-P (approx. 5.8 to 4.0 ppm), and diester-P (approx. 1.41 to  $-0.71$  ppm). Reproduced from ref. 21 with permission from Springer Nature, copyright 2017; (b) quantification of P species from  $^{31}\text{P}$  NMR spectra of NaOH-EDTA extracts of manure biochars produced at different temperatures. Data taken from various sources.<sup>21,56,57,92,93</sup> (c) Extractability of P in NaOH-EDTA decreases with increasing pyrolysis temperatures. Data taken from various sources.<sup>21,56,57</sup>

and then gradually decreased with higher temperatures, and at 700  $^{\circ}\text{C}$  only orthophosphate was detected.

Fig. 7b gives an overview of the concentrations of organic P, orthophosphate and pyrophosphate as function of pyrolysis temperatures based on  $^{31}\text{P}$  NMR measurements. These P transformations during biochar pyrolysis can be generalized as follows. At relatively low temperatures, organic P species are

degraded first; thermal decomposition of phytic acid may start at 150  $^{\circ}\text{C}$ .<sup>133</sup> Uchimiya and Hiradate<sup>92</sup> reported that the organic P concentration of broiler litter decreased from 61% to 1% after pyrolysis at 350  $^{\circ}\text{C}$  and was not found at 500  $^{\circ}\text{C}$  and higher. At the same time, pyrophosphate is formed as an intermediate species with a maximum concentration at 300–400  $^{\circ}\text{C}$ , where up to 36% of the P may be in pyrophosphate form.<sup>92</sup> At higher



temperatures, pyrophosphate concentrations gradually decrease and orthophosphate becomes more abundant. Throughout the pyrolysis process the orthophosphate concentrations increase and at  $>700\text{ }^{\circ}\text{C}$  only orthophosphate is detected.

However, these results from liquid phase  $^{31}\text{P}$  NMR analysis should be interpreted with care because only a fraction of P can be extracted from the biochar which decreases with pyrolysis temperature (Fig. 7c), resulting in the under- or over-estimation of some species. Furthermore, as mentioned previously, the extraction solution may alter the P species, so care should be taken as the NMR spectra may not be fully representative of the P forms in the biochars.

Phosphates in biochars tend to crystallize with Ca because of the high Ca contents in manures, and the most frequently detected crystalline phosphate phases in manure biochars are whitlockite (including  $(\text{Ca,Mg})_3(\text{PO}_4)_2$  and similar compounds) and apatites (mainly hydroxyapatite,  $\text{Ca}_5(\text{PO}_4)_3(\text{OH})$ ).<sup>28</sup> Additionally, different orthophosphates (e.g.,  $\text{KCaPO}_4$ ,  $\text{MgNH}_4\text{PO}_4 \cdot 6\text{H}_2\text{O}$ ) and pyrophosphates (e.g.,  $\text{Ca}_2\text{P}_2\text{O}_7$ ,  $\text{K}_2\text{CaP}_2\text{O}_7$ ,  $\text{K}_4\text{P}_2\text{O}_7$ ) are sometimes observed,<sup>56,70,134</sup> and the XRD patterns commonly contain non-phosphate phases such as  $\text{SiO}_2$  (quartz), KCl (sylvite), and  $\text{CaCO}_3$  (calcite). For example, whitlockite was formed when dairy manure was pyrolyzed at  $450\text{ }^{\circ}\text{C}$  (ref. 135) and  $500\text{ }^{\circ}\text{C}$ ,<sup>49</sup> and whitlockite and hydroxyapatite were found in swine manure biochars produced at  $600$  and  $700\text{ }^{\circ}\text{C}$ .<sup>57</sup> Poultry manures may already contain some crystalline hydroxyapatite, which is further crystallized upon pyrolysis.<sup>136</sup> Nevertheless, XRD can only detect crystalline P phases and may thus provide an incomplete picture of the P species present.

To provide a more comprehensive insight into the P transformations taking place within the solid, spectroscopic techniques like P K-edge XANES and solid state  $^{31}\text{P}$  NMR spectroscopy have been employed. For example, Jiang *et al.*<sup>136</sup> pyrolyzed poultry litter at  $200$ – $600\text{ }^{\circ}\text{C}$  and used solid state  $^{31}\text{P}$  NMR, XRD, and FTIR spectroscopy to monitor P transformations (Fig. 8). The XRD patterns confirmed the presence of hydroxyapatite in the poultry litter and all biochars, which became more crystalline at higher pyrolysis temperatures. Solid state  $^{31}\text{P}$  NMR measurements indicated that poultry litter contained orthophosphate, phytate, and hydroxyapatite groups (Fig. 8a). Increasing pyrolysis temperatures converted water-bound  $\text{HPO}_4^{2-}$  and phytates into hydroxyapatite. Phytates were decomposed above  $300\text{ }^{\circ}\text{C}$ , and farringtonite ( $\text{Mg}_3(\text{PO}_4)_2$ ) formed above  $500\text{ }^{\circ}\text{C}$ . According to the solid state  $^{31}\text{P}$  NMR analysis, the P in the raw poultry litter was 21% in the form of hydroxyapatite, which increased to more than 70% at  $600\text{ }^{\circ}\text{C}$  (Fig. 8b). At the same time, water-extractable P concentrations greatly decreased from  $2.9\text{ g kg}^{-1}$  in raw poultry litter to less than  $0.2\text{ g kg}^{-1}$  at  $400$ – $600\text{ }^{\circ}\text{C}$  (Fig. 8c). Li *et al.*<sup>112</sup> made similar observations in the solid state  $^{31}\text{P}$  NMR spectra of pyrolyzed poultry litter at  $300$ – $600\text{ }^{\circ}\text{C}$ . Liang *et al.*<sup>21</sup> monitored the transformation of organic P (inositol hexaphosphate) to  $\text{Ca}_3(\text{PO}_4)_2$  during pyrolysis of swine manure by P XANES analysis supported by liquid phase  $^{31}\text{P}$  NMR measurements. The authors also identified small amounts of hydroxyapatite (10–15%) and pyrophosphates (3–8%) in the biochars.

Huang *et al.*<sup>110</sup> performed solid state P XANES analysis of cow, swine, and poultry manures. The  $\text{H}_2\text{O}$ -extractable P fraction rapidly decreased and the HCl-extractable P fraction gradually increased when the pyrolysis temperature was raised, which was ascribed to the degradation of organic phosphates and gradual crystallization of Ca phosphates. The authors found a similar speciation between manure types because all manures had Ca as major P-binding element. Robinson *et al.*<sup>55</sup> also found that pyrolysis increased the hydroxyapatite content in poultry manure from 34 to 48% and a small amount of pyrophosphate ( $\text{Mg}_2\text{P}_2\text{O}_7$ ) was identified in the biochar. The P species in pig slurry, however, were hardly altered after pyrolysis.

## 4. Phosphorus availability from biochars

### 4.1 Phosphorus extractability and release

The P extractability has been evaluated in various aqueous media in order to understand the potential risk losses and predict the potential availability to crops. Water-soluble P generally decreases with increasing pyrolysis temperatures,<sup>23,47,49,64,70,112,134,136–139</sup> suggesting that the P release risk from biochars is lower than from manures. For example, the water-soluble P in fresh and pelletized chicken manure decreased from 50–60% to 3–9% after pyrolysis at  $500$ – $700\text{ }^{\circ}\text{C}$ .<sup>64</sup> Cantrell *et al.*<sup>47</sup> measured a decrease in soluble P after pyrolysis of 5 types of manure biochars prepared at  $350$  and  $700\text{ }^{\circ}\text{C}$ . Among manures, swine solids had highest soluble P in manure but the lowest soluble P in the biochars. According to Cao and Harris,<sup>49</sup> when dairy manure was pyrolyzed at  $100$ – $500\text{ }^{\circ}\text{C}$ , the water-soluble P first increased up to  $200\text{ }^{\circ}\text{C}$  and then decreased with higher temperatures. The initial increase in P solubility was ascribed to an increase in total P by biomass reduction but may also be due to the increased fraction of P in orthophosphate form (the form that is detected with the molybdenum blue method).

Different extractants have been used to get an indication for the P availability to crops. The P extractability (both absolute and relative to the total P content in the biochar) in organic acids like 2% citric acid, 2% formic acid, or acidic ammonium oxalate is generally high<sup>23,70,92,101,134,140,141</sup> and tends to be higher from manure biochars than from plant biochars.<sup>92,140</sup> Increasing pyrolysis temperatures result in decreased P extractability in 0.01 M HCl from poultry litter biochars.<sup>68</sup> The P fraction that was extractable in 1 M HCl was 68% for poultry litter manure and increased to 87–99.8% after pyrolysis at  $300$ – $600\text{ }^{\circ}\text{C}$ , with the highest extractability at  $450\text{ }^{\circ}\text{C}$ .<sup>112</sup> The P extractable in neutral ammonium citrate (NAC) tends to be around 70–90% of total P,<sup>70,101,141</sup> but also lower values have been reported.<sup>134</sup>

A number of studies have adapted soil tests for P to measure extractability in biochars, such as Olsen P,<sup>48,65,112,137,142</sup> Bray-1,<sup>112</sup> Bray-2,<sup>140</sup> Mehlich-3,<sup>92,112,143</sup> and Colwell.<sup>140</sup> Higher pyrolysis temperatures may decrease<sup>48,65</sup> or increase Olsen P,<sup>137</sup> or may go through a maximum at intermediate pyrolysis temperatures.<sup>112,142</sup> The Mehlich-3 extractable P values were low ( $<4\%$ )



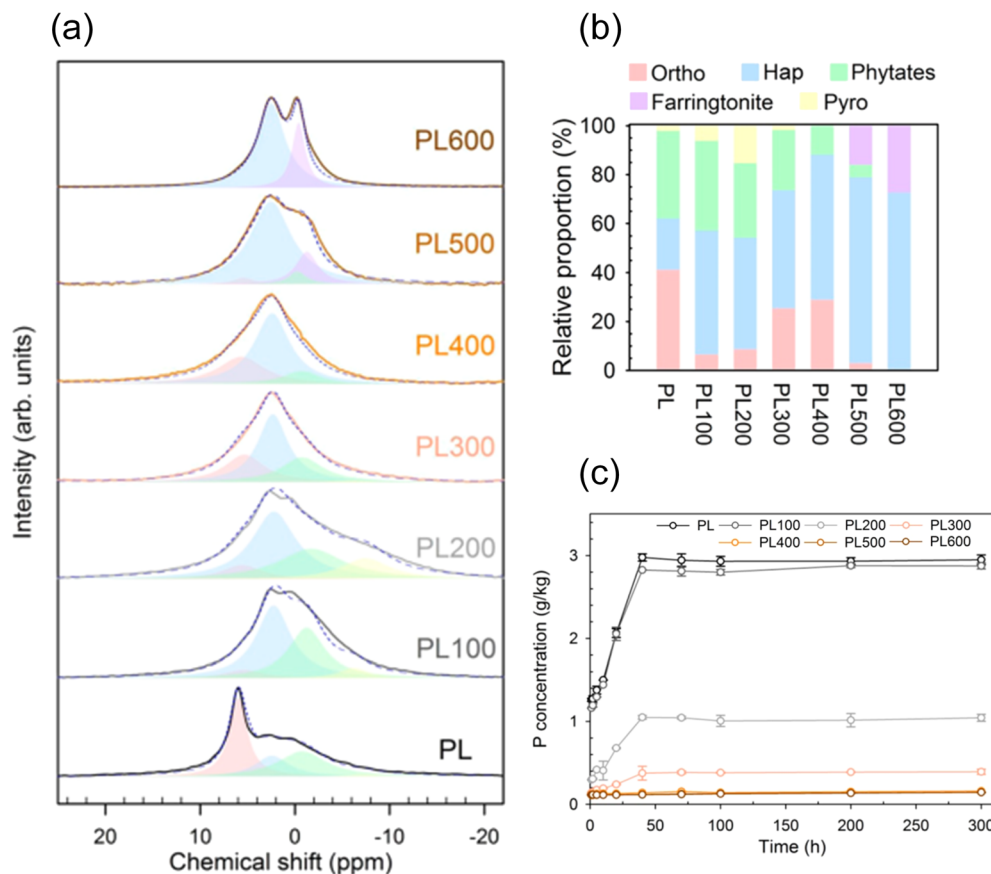


Fig. 8 (a)  $^{31}\text{P}$  SP/MAS NMR spectra and the deconvoluted forms and (b) relative proportion (%) of the main P species in raw poultry litter (PL) and PL pyrolyzed at 200–600 °C. Ortho, hap, phytates, farringtonite, and pyro refer to the deconvoluted peaks of protonated sodium orthophosphate ( $\delta = 6.1$  ppm), hydroxyapatite ( $\delta = 2.6$  ppm), phytates ( $\delta = 0.6$  ppm), farringtonite ( $\delta = -0.4$  ppm), and pyrophosphates ( $\delta = -7$  ppm), respectively; (c) phosphorus release from raw and pyrolyzed poultry litter in deionized water. Reproduced (adapted) from ref. 136 with permission from the American Chemical Society, copyright 2019.

for poultry litter and its biochars,<sup>92</sup> but were >75% for poultry litter biochars produced at pyrolysis temperatures up to 450 °C and only dropped at higher temperatures.<sup>112</sup> Tsai and Chang<sup>143</sup> observed a behavior in between, with high fraction of total P extracted in Mehlich-3 at low temperatures and decreasing values with increasing temperature.

However, there is no clear consensus on which test is best to predict the P phytoavailability from biochars. Li *et al.*<sup>112</sup> suggested that Bray-1 was appropriate for predicting medium-term available P and Mehlich-3 for long-term available P. Rose *et al.*<sup>140</sup> concluded that Bray-2 and water extractable P correlated best with P uptake in ryegrass, whereas Wang *et al.*<sup>141</sup> proposed 2% formic acid as best extractant to predict P availability from high ash biochars, and others have obtained good results with 0.5 M  $\text{NaHCO}_3$  extraction to predict shoot biomass and P uptake from secondary raw materials and wastes.<sup>144,145</sup> Because biochars contain a large diversity in phosphate phases with widely varying solubilities, standard extractants cannot reliably predict plant P uptake.<sup>146</sup> Alternative methods have been proposed, such as sink-based P extraction with ion exchange membranes<sup>147</sup> or iron bags,<sup>145,148</sup> and diffusive gradient in thin films (DGT),<sup>148</sup> but such methods have not been evaluated in

detail on the P availability from biochars.<sup>23,149,150</sup> Hernandez-Mora *et al.*<sup>151</sup> compared 6 P extraction methods ( $\text{H}_2\text{O}$ , NAC, electro-ultrafiltration, iron bags,  $\text{NaHCO}_3$ , and DGT) for compliance testing of 30 recycled P fertilizers that were chemically diverse. The DGT procedure provided the most accurate prediction of fertilization efficiency. However, due to the complexity of the DGT procedure, the authors recommend NAC as a routine extractant because of the simplicity, high throughput, and low cost, despite its limitations to predict fertilization efficiency of Fe phosphate-containing fertilizers.

Fractionations of P from biochars have been widely used to understand transformations of P species. Overall, pyrolysis tends to decrease the available P forms and increase the stable P.<sup>24</sup> Examples of results from sequential (Hedley) fractionations are shown in Fig. 9 for swine<sup>57</sup> and poultry biochars<sup>112</sup> produced at different temperatures. It can be seen that generally the labile (combined  $\text{H}_2\text{O-P} + \text{NaHCO}_3\text{-P}$ , which are similar to Olsen  $\text{P}^{152}$ ) and  $\text{NaOH-P}$  fractions decrease, while the  $\text{HCl-P}$  and  $\text{Res-P}$  tend to increase, which was also confirmed in other studies.<sup>67,101,110</sup>

Using a modified extraction procedure based on soil tests, Liu *et al.*<sup>48</sup> found that the more soluble (*i.e.*, soluble and loosely bound inorganic P, aluminum-bound inorganic P, and organic



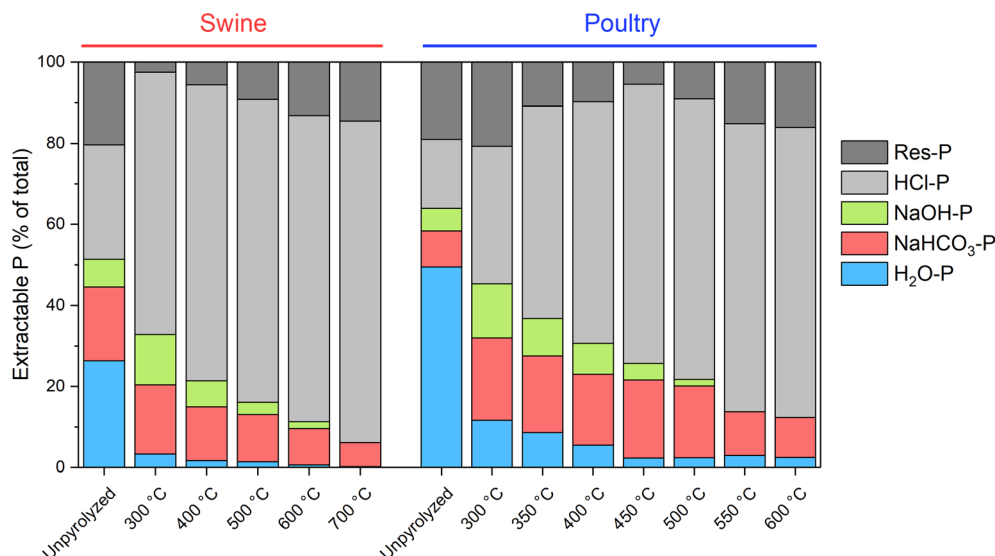


Fig. 9 Sequential fractionation of biochars produced at different temperatures from swine manure (data taken from Jiang *et al.*<sup>57</sup>) and poultry litter (data taken from Li *et al.*<sup>112</sup>). Increasing the pyrolysis temperature decreases the H<sub>2</sub>O-P fraction and increases the HCl-P fraction.

P) in manure decreased with increasing pyrolysis temperature and transformed into less soluble P forms (*i.e.*, calcium-bound inorganic P and oxide-occluded inorganic P). The Fe-bound inorganic P concentrations were higher for cow manure than for pig and sheep manure.

The SMT protocol has occasionally been used to provide an indication for availability transformations of P in pyrolysis. For example, in the pyrolysis of chicken manure and dairy manure, Zuo *et al.*<sup>114</sup> found that higher pyrolysis temperatures (350 to 550 °C) resulted in transformation from NAIP to AP, suggesting lower availability. Chicken manure biochars contained consistently higher AP concentrations than dairy manure biochars. Simbolon *et al.*<sup>64</sup> also measured a higher AP content in biochars compared to fresh and pelletized chicken litter. However, conclusions about P availability from these transformations should be interpreted with great care. Becker and Kruse<sup>152</sup> have recently highlighted that the SMT protocol may not accurately capture the solubility transformations taking place during (hydro)thermal treatment of sewage sludges, which may lead to misleading conclusions about P availability.

The continuous P release in water has been evaluated by suspending the biochar in DI water which is kept under continuous shaking for a number of days. This procedure has been used to measure the P release from biochars produced from different manures<sup>21,101,135,137,138,153–156</sup> and also other biochars.<sup>157–161</sup> Fitting of the experimental data to kinetic equations (*e.g.*, (pseudo)-first order, (pseudo)-second order, intraparticle diffusion, or Elovich equation) can provide insight into the P release mechanism. An overview of measured P release from manures and their biochars is shown in Fig. 10. The raw manures rapidly release P and between 10 and 60% of P has been dissolved within the first 120 h. Pyrolysis greatly decreases the rate of P dissolution, the effect being stronger for higher temperatures. For example, Liang *et al.*<sup>135</sup> showed that dairy manure pyrolyzed at 450 °C presented a slow, continuous

P release over 240 h in water compared to raw dairy manure, which had a rapid initial release and was constant after 24 h. The inhibition of P leaching after pyrolysis was ascribed to the formation of poorly soluble whitlockite ((Ca,Mg)<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub>).<sup>135</sup> A similar characteristic was found in the release of P from swine<sup>21,101</sup> and poultry manure biochars.<sup>101,153</sup> Sun *et al.*<sup>56</sup> have studied the P release from swine manure biochar produced at 450 °C. After 120 hours, 19% of the total P in the biochar (consisting of 11% orthophosphate and 8% pyrophosphate) was released, which was lower than the release from corn stover biochar (45% of total P). The authors suggested that the P

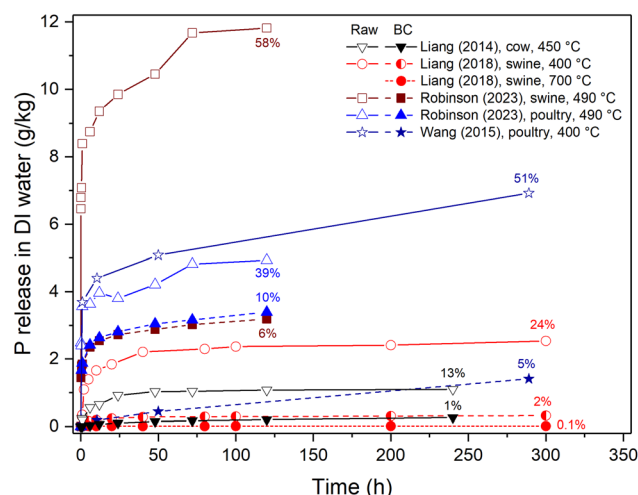


Fig. 10 Phosphorus release from manures and their biochars in DI water. Open symbols indicate the raw (unpyrolyzed) manure, and filled and semi-filled symbols indicate the biochars (BC) produced at the indicated temperatures. The values at the end points give the percentage of the total P present in the sample that has been dissolved at that point. Figure was produced using data from various sources.<sup>21,101,135,153</sup>



dissolution from the swine manure biochar was limited by the formation of crystalline phases like  $(\text{Ca,Mg})_3(\text{PO}_4)_2$  and  $\text{Mg}_2\text{P}_2\text{O}_7/\text{Ca}_2\text{P}_2\text{O}_7$ . The cation to which the P is bound in the biochar has a strong effect on the P release. For example, Ca-rich biochars present a lower kinetic P release in water than Mg-rich biochars, which is related to the higher solubility of Mg-containing phosphates.<sup>158</sup> Using a series of batch experiments, Hadroug *et al.*<sup>162</sup> found that the P release kinetics in water (pH 5.6) from poultry litter decreased at higher pyrolysis temperatures. The authors also studied the effect of pH and dose.

The long-term P release in soil from biochars has been evaluated by a number of authors. Compared to raw dairy manure, manure biochar showed the slow release of P in soil (pH 6.85) controlled by the stable P form  $(\text{Ca,Mg})_3(\text{PO}_4)_2$  in biochar over 210 days.<sup>135</sup> A similar behavior was reported by Wang *et al.*,<sup>153</sup> where the P release from the soil (sandy loam, pH 6.5) along with poultry litter biochar (400 °C) was significantly slower than the P release from poultry litter. Piash *et al.*<sup>163</sup> studied the P release in soil over 120 days from dairy manure and chicken manure biochar produced at 300 and 500 °C, applied at 2 wt% on a dry basis. The P release in DI water was affected by various factors such as ambient temperature, pH, and anions. The P release from biochars produced at 500 °C was 1.38 times (chicken manure) and 1.10 times (dairy manure) greater than the biochars produced at 300 °C. Sanford *et al.*<sup>50</sup> pyrolyzed dairy manure at 350 and 500 °C and found that the available (Bray-1) P decreased with higher pyrolysis temperature after incubation in two types of soil (loam and sandy loam) over 182 days. At a low application rate (34.5 mg P per kg) there was no difference between the biochars and manure treatments, but at a high rate (172.4 mg P per kg) the 500 °C biochar resulted in lower P availability than 350 °C biochar and manure. In a 98 days incubation study, swine manure biochar application (0.5 and 1.5 wt%) in clay loam and silt loam soils increased available (Olsen) P, increased orthophosphate and pyrophosphate concentrations, and enhanced alkaline phosphomonoesterase activity in a dose-dependent manner.<sup>164</sup> In a column experiment, alkaline sandy soil (pH 8.1) amended with 5 and 8 wt% poultry manure biochar presented a slow but continuous P release over 40 days.<sup>165</sup>

## 4.2 Plant studies

The conversion of animal manure to biochar not only retains large amounts of P but also prolongs the release of P for plants in the form of P available for plants. However, the available P in animal manure biochar depends on various factors such as pyrolysis temperature and type of manure. Organic P in manures such as phytate, lipids, and DNA are slowly available for plant uptake due to the strong binding of phytate to soils.<sup>166</sup> Plants primarily take up P in the form of orthophosphate and condensed phosphates undergo hydrolysis into orthophosphate before being absorbed.<sup>167</sup>

In a recent systematic review of 26 meta-analyses covering more than 1600 articles, Schmidt *et al.*<sup>168</sup> concluded that biochar application has overall beneficial effects on agronomic indicators like plant yield, root development, and soil microbial

activity. While biochars have higher P concentrations than the raw manures, a high P application to soil and high P content in the biochar may not necessarily translate into a higher P uptake in crops. Two meta-analyses concluded that biochar application to soil can significantly increase P availability in soils<sup>169,170</sup> and also increase P uptake in crops compared to unamended soils.<sup>170</sup> For example, yak manure biochars (300 kg ha<sup>-1</sup>) increased growth of barley compared to an unfertilized control, even though there was no effect on soil N and P levels.<sup>171</sup> Both meta-analyses<sup>169,170</sup> concluded that the extent of the P efficacy depends on the pyrolysis conditions and soil properties. Soil available P greatly decreases with pyrolysis temperature, and low temperature biochars were more effective in increasing available P in the soil compared to high temperature biochars. Subedi *et al.*<sup>172</sup> studied the P availability from biochars produced from swine manure and poultry litter in two different soil types (silt-loam with pH 6.1 and sandy with pH 8.3). When applied at 2 wt% per dry soil, the low temperature (400 °C) biochars significantly increased both shoot and root dry matter yield of ryegrass compared to an unfertilized control in the silt-loam soil, while biochars produced at high temperature (600 °C) had no effect on either shoot or root dry matter yield. The low temperature biochars had approximately 2.0–3.5 times higher P uptake efficiencies than the high temperature biochars in both soils. When applied at 7.5 t ha<sup>-1</sup> (but not at 5 t ha<sup>-1</sup>), Wang *et al.*<sup>141</sup> found that a biochar produced from a dairy manure-wood mixture at 450 °C resulted in a higher yield of ryegrass compared to pyrolysis at 250 and 550 °C. Overall, Tesfaye *et al.*<sup>170</sup> concluded that there was no apparent effect of pyrolysis temperature on plant P uptake, suggesting that low P availability may not necessarily mean low P uptake.

Concerning soil properties, biochar application tends to be more effective in soils with low pH, fine texture and low available P concentrations.<sup>169,170</sup> Subedi *et al.*<sup>172</sup> measured a higher P uptake in ryegrass from swine manure and poultry litter biochars application in acidic silt-loam soil compared to alkaline sandy soil. On the other hand, some authors have reported good efficacy in alkaline soil: in a clay loam soil with pH 7.98, Gunes *et al.*<sup>173</sup> reported that poultry litter biochar (10 g biochar per kg soil) increased dry weight and P uptake of lettuce compared to unfertilized control, to a similar level as the unpyrolyzed poultry litter at an equivalent P application (20 g poultry litter per kg soil).

There is an effect of crop type and experiment type (laboratory *versus* field),<sup>170</sup> but the duration of the experiment does not influence the efficacy.<sup>169</sup> Whereas Glaser and Lehr<sup>169</sup> did not find any influence of the feedstock, Tesfaye *et al.*<sup>170</sup> concluded that manure biochars were more effective in increasing soil available P and plant P uptake compared to other feedstocks (*i.e.*, crop residues, wood, and sewage sludge). This was possibly due to the higher P concentration and more favorable pH of manure biochars. In both the absence and presence of a commercial P fertilizer, chicken manure biochar was more effective in increasing P uptake in wheat than wheat chaff biochar, but also increased P leaching.<sup>174</sup>

While most studies have demonstrated positive effects of biochar compared to unamended soils, manure biochars often produced similar or lower results compared to unpyrolyzed



manure or commercial fertilizers. Both chicken manure and its biochar (prepared at 400 °C) were as effective as commercial superphosphate in increasing shoot dry matter of rye when applied at 100 mg P per kg soil.<sup>148</sup> Both poultry litter biochar and cow manure biochar were equally effective as water-soluble  $\text{KH}_2\text{PO}_4$  in increasing shoot biomass of ryegrass grown in a neutral sandy soil at 50 mg total P per kg soil. Cow manure biochar, however, resulted in lower shoot P concentrations compared to poultry litter biochar and  $\text{KH}_2\text{PO}_4$ .<sup>140</sup> After 6 harvests, biochars produced from a dairy manure-wood mixture at 5 and 7.5 t ha<sup>-1</sup> were as effective as commercial fertilizers at comparable or lower P applications in increasing yield, but not P uptake in ryegrass.<sup>141</sup> Sheep manure biochar was more effective in increasing barley yield than sheep manure and vermicompost when applied at 2 wt% per dry soil.<sup>175</sup> However, the authors did not control the application rates of N, P, or any other nutrients, and these differences in treatment composition may have been at least partially responsible for the observed differences.


Recently, Hernandez-Mora *et al.*<sup>176</sup> compared the fertilizer efficiency of 30 recycled P sources to triple superphosphate in pot trials across 3 European locations in wheat, barley, and ryegrass. The fertilizers, including a pelletized product containing chicken manure and grape residue, a poultry litter biochar, and a pyrolyzed pig slurry digestate, were applied at 50 mg P per kg growing media, and the P species in each fertilizer were identified using P K-edge and  $\text{L}_{2,3}$ -edge XANES. At two of the three locations, all three manure-based materials had equivalent mineral replacement values (MRV) and agronomic

mineral replacement values (aMRV), but at the third location the performance decreased in the following order: chicken manure and grape residue pellets > poultry litter biochar > pyrolyzed pig slurry digestate. All fertilizers that contained hydroxyapatite/tricalcium phosphate (such as pyrolyzed pig slurry digestate) had significantly lower MRV and aMRV values than triple superphosphate, while those containing dicalcium phosphate (like chicken manure and grape residue and poultry litter biochar) had a comparable performance.<sup>176</sup> The authors classified all three fertilizers as 'effective' based on the MRV values above 60%.<sup>151</sup>

A meta-analysis on biochar applications in European soils did not find sufficient supporting evidence for the agronomic efficiency of biochars compared to mined and synthetic P fertilizers, primarily due to a lack of data.<sup>10</sup> Also Sarvi *et al.*<sup>177</sup> demonstrated that in sandy soil (pH 6.5), pyrolyzed broiler manure was less effective than granulated broiler manure in ryegrass when applied at 100 mg P per kg soil. Over 4 consecutive harvests the yield of granulated broiler manure was 36% higher and total P uptake was 53% higher. This was related to the lower P extractability from the biochar in the sequential extraction procedure. The authors stated that the pyrolyzed broiler litter may be suitable as slow release P fertilizer in acidic soils. Vanden Nest *et al.*<sup>178</sup> compared several organic fertilizers applied at equivalent P rates of 39.3 kg P per ha in sandy loam soil, and found that the P use efficiency in ryegrass decreased in order animal manure > digestate > compost > biochar, which was ascribed to the presence of apatite present in the biochar and compost.

**Table 1** Examples of strategies to modify the P availability of manure biochars through co-pyrolysis

Manure type	Additive	Pyrolysis conditions	Key findings on manure P	Reference
Swine	$\text{CaCl}_2 \cdot 2\text{H}_2\text{O}$ , $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ , KCl, NaCl, polyvinyl chloride (PVC)	700 °C, 2 h	SMT protocol: higher AP in order $\text{CaCl}_2$ (93%) > $\text{MgCl}_2$ (92%) > PVC (91%) > unmodified (84%) > NaCl (82%) > KCl (79%) $\text{CaCl}_2$ , $\text{MgCl}_2$ , and PVC: Formation of chlorapatite, stanfieldite (only $\text{MgCl}_2$ ) and possibly $\text{Ca}_3(\text{PO}_4)_2$	Xu <i>et al.</i> (2023) <sup>179</sup>
Swine	$\text{CH}_3\text{COOK}$	500–700 °C, 27 min	Higher water-extractable and NAC-extractable P	Buss <i>et al.</i> (2022) <sup>180</sup>
Swine	KOH, $\text{K}_2\text{CO}_3$ , $\text{CH}_3\text{COOK}$ , $\text{C}_6\text{H}_5\text{K}_3\text{O}_7$	700 °C, 2 h	Slightly lower total P No effect on water-extractable P Higher P extractability in $\text{NaHCO}_3$ , NAC, and FA Hedley extraction: higher fraction in $\text{NaHCO}_3$ and NaOH, lower fraction in HCl Stronger effect for organic K than inorganic K Formation of $\text{CaKPO}_4$	Liu <i>et al.</i> (2024) <sup>181</sup>
Poultry	$\text{CaCl}_2$ , $\text{MgCl}_2 \cdot 6\text{H}_2\text{O}$ , $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$	250–550 °C, 1 h	Total P hardly/not affected Lower extractable (Olsen) P in order unmodified > $\text{MgCl}_2$ > $\text{CaCl}_2$ > $\text{FeCl}_3$ Lower P release in water	Xiao <i>et al.</i> (2018) <sup>137</sup>
Poultry	Ca-bentonite	300 °C, 1 h	Lower P release	Piash <i>et al.</i> (2022) <sup>182</sup>
Poultry	$\text{MgCl}_2$	500–900 °C, 4 h	Lower extractable P at pH 5.0 Formation of $\text{Mg}_3(\text{PO}_4)_2$	Padilla <i>et al.</i> (2023) <sup>183</sup>
Poultry	$\text{Mg}(\text{OH})_2$	300–700 °C, 30 min	Total P increased at high temperature but decreased at low temperature Lower water-soluble P Lower kinetic P release in water Higher extractable P in 2% citric acid and 2% formic acid (but not at 700 °C) Formation of $\text{MgNH}_4\text{PO}_4$ and $\text{Mg}_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$	Leite <i>et al.</i> (2023) <sup>138</sup>



In summary, most plant studies have compared biochar application to unamended soils and generally find positive responses, and various studies concluded that biochars can have beneficial effects that are not different from (but in most cases do not exceed) the raw manure. The availability of P from manure biochars depends on the pyrolysis conditions, feedstock, and soil and crop conditions, but is often lower than that of the raw manure. However, there is a lack of studies that directly compared manure biochar to raw manure at equivalent total P application rates on P-responsive soils, while also accounting for the confounding effects of biochar application on crop growth (for example, changes in soil pH and salinity, concentrations and availability of other nutrients, soil organic matter, soil structure, and soil microbial activity).

### 4.3 Strategies to modify P availability

In order to tailor the P species and its availability, several studies have performed co-pyrolysis of manures with other compounds and some examples are given in Table 1. Whereas the co-pyrolysis of manure with K compounds increases the P extractability,<sup>180,181</sup> co-pyrolysis with Mg compounds may either increase<sup>138</sup> or decrease the P extractability,<sup>137,183</sup> and Ca generally reduced P extractability.<sup>137,182</sup> To enhance the total/available P in manure biochars, several authors have enriched manure biochars by co-pyrolysis with P-containing compounds.<sup>154–156,184</sup> Other researchers have explored biochar activation through different means. For example, poultry litter biochar was activated with methanesulfonic acid at 400–700 °C, which resulted in higher total P and lower water-extractable P (except at 400 °C), lower pH and electrical conductivity, and a higher water holding capacity.<sup>66</sup> Post-treatment of biochars has also been done by char oxidation and steam gasification to increase P availability in soils.<sup>51</sup>

Most of the modification methods have been carried out on sewage sludges and their biochars, and such approaches may also be used for manure biochars. For example, treatment of sludge-derived biochar with H<sub>2</sub>SO<sub>4</sub> and NaOH increased H<sub>2</sub>O-P, NaHCO<sub>3</sub>-P and NaOH-P and decreased HCl-P, which resulted in an increase in shoot dry matter and P uptake of maize, whereas treatment with Ca(OH)<sub>2</sub> had little effect.<sup>185</sup> Li *et al.*<sup>186</sup> carried out the co-pyrolysis of sewage sludge with CaO or MgO. Using the SMT protocol, the authors found that CaO increased the total P concentration, enhanced XRD peaks of hydroxyapatite and Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub>, and resulted in transformation of NAIP to AP (suggesting a higher P stability). When MgO was added in the pyrolysis process, the total P levels in the biochar were increased, peaks of Mg<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub> were observed, but the NAIP and AP concentrations were hardly affected. Other authors observed similar effects when sewage sludge was co-pyrolyzed with Ca compounds (CaO, Ca(OH)<sub>2</sub>, Ca<sub>3</sub>(PO<sub>4</sub>)<sub>2</sub>).<sup>187,188</sup>

## 5. Challenges and future perspectives

Pyrolysis of animal manures has various benefits, such as volume reduction (meaning easier storage and transportation), reduced nutrient leaching, reduction of greenhouse gas

emissions, energy recovery in the form of combustible gases, and elimination of pathogens, organic contaminants, and odor.<sup>14,18,33</sup> And despite the generally good prospects of P recovery from manures through pyrolysis for direct applications in agriculture, this approach still presents several concerns. Recent review articles have highlighted the negative impact of biochar applications in soil.<sup>189–192</sup> For example, animal manures may contain significant levels of heavy metals (*e.g.*, Zn, Cu, Ni, Cr, Pb, Cd, As, Cr, and Hg).<sup>193</sup> During pyrolysis, heavy metals are largely retained in the biochar and their concentrations generally increase with higher treatment temperatures.<sup>53,66,142,194–196</sup> Small (usually <5%) fractions of some more volatile elements (like Cd, Pb, and As) may be lost in the gas phase,<sup>193</sup> and their concentrations in biochars may decrease at ≥600 °C.<sup>66,194,195</sup> Most biochars contain heavy metal concentrations within permissible levels,<sup>53,66</sup> although elevated concentrations of for example Zn, Ni, and Cr have been reported.<sup>64,196</sup> Pyrolysis converts the heavy metals from more available into less available forms, and the environmental risk is reduced compared to the raw manure, but not completely eliminated; these may still present a potential for long-term ecotoxicity.<sup>193–195</sup>

Secondly, there are concerns about the toxicity of biochars. Pyrolysis may result in the generation of volatile organic compounds (VOCs) and polycyclic aromatic hydrocarbons (PAHs),<sup>14</sup> and several studies have confirmed the potentially toxic effects of VOCs and PAHs to different organisms.<sup>192,197–200</sup> The concentrations of both VOCs and PAHs (as well as the toxicity) are strongly dependent on the feedstock and pyrolysis conditions.<sup>14,192</sup>

In addition to P, the value of other nutrients such as N and K should be considered as well. Pyrolysis at low temperatures (<400 °C) may initially increase the N concentrations of biochars, but losses at higher temperatures decrease the total N concentrations.<sup>68,70,201,202</sup> At the same time, extractable N concentrations in biochars decrease with increasing pyrolysis temperatures<sup>130,137</sup> as N is converted into organic N species like pyridinic-N and pyrrolic-N.<sup>201</sup> As a consequence, the N availability from biochars is lower than that of unpyrolyzed manure.<sup>14,203</sup> To reduce N losses during pyrolysis, the separation of water-soluble N from the manure prior to pyrolysis is necessary, which can then be combined with the biochar to form a biochar-based fertilizer.<sup>14</sup> Compared to N and P, the aqueous release of K from biochars is generally high and may even increase at higher pyrolysis temperatures.<sup>68,70,163</sup> Manure is also an excellent source of soil organic matter,<sup>204,205</sup> and the C losses during pyrolysis and the increased aromaticity and stability of C in the biochar may affect soil properties in both short- and long-term.<sup>206–209</sup>

While most plant trials have demonstrated that P from manure biochars is phytoavailable, further agricultural trials are needed to demonstrate whether manure pyrolysis is beneficial from an agronomic and economic point of view. Such trials should directly compare the performance of manure biochar to that of raw manure at equivalent total P application rates under carefully controlled conditions. Several studies have estimated that animal manure pyrolysis is financially beneficial (including the P value in the char as well as energy value from



char, oil, and fuel).<sup>123,210</sup> For example, Azuara *et al.*<sup>123</sup> estimated that fast pyrolysis of pig manure would cost around 0.4–4.4 € per ton with an estimated overall benefit of 3.98–5.13 € per ton, which is financially more beneficial than transportation of the manure. Other studies have much higher cost estimates (*e.g.*, 218–274 \$ per ton (ref. 211)). There is a very high variability and uncertainty in estimating the cost and benefits of pyrolysis,<sup>212–214</sup> so careful consideration through a thorough cost-benefits analysis is required to decide whether pyrolysis is a viable option.

## Data availability

No primary research results, software or code have been included and no new data were generated or analysed as part of this review.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

The authors would like to thank Vince Knijnenburg for his assistance with the preparation of the figures. This research was supported by the Fundamental Fund of Khon Kaen University. The research on “Product development and investment feasibility study of innovations from waste and by-product from agricultural production” by the Faculty of Engineering and International College at Khon Kaen University has received funding support from the National Science, Research and Innovation Fund (NSRF), Thailand.

## References

- 1 M. R. Hart, B. F. Quin and M. L. Nguyen, *J. Environ. Qual.*, 2004, **33**, 1954–1972.
- 2 C. E. Nedelciu, K. V. Ragnarsdottir, P. Schlyter and I. Stjernquist, *Global Food Secur.*, 2020, **26**, 100426.
- 3 D. Jones and A. Deuss, *OECD Food, Agriculture and Fisheries Papers*, No. 208, 2024, DOI: [10.1787/18156797](https://doi.org/10.1787/18156797).
- 4 D. Cordell and S. White, *Sustainability*, 2011, **3**, 2027–2049.
- 5 D. Cordell, J. O. Drangert and S. White, *Global Environ. Change*, 2009, **19**, 292–305.
- 6 M. Chen and T. E. Graedel, *Global Environ. Change*, 2016, **36**, 139–152.
- 7 P. J. A. Withers, K. C. van Dijk, T. S. S. Neset, T. Nesme, O. Oenema, G. H. Rubæk, O. F. Schoumans, B. Smit and S. Pellerin, *Ambio*, 2015, **44**, 193–206.
- 8 C. Ott and H. Rechberger, *Resour., Conserv. Recycl.*, 2012, **60**, 159–172.
- 9 X. Meng, Q. Huang, J. Xu, H. Gao and J. Yan, *Waste Disposal Sustainable Energy*, 2019, **1**, 99–115.
- 10 D. Huygens and H. G. M. Saveyn, *Agron. Sustainable Dev.*, 2018, **38**, 52.
- 11 P. Pagliari, M. Wilson and Z. He, in *Animal Manure: Production, Characteristics, Environmental Concerns, and Management*, ed. H. M. Waldrip, P. Pagliari and Z. He, 2020, pp. 1–14.
- 12 Z. Bian, H. Tian, Q. Yang, R. Xu, S. Pan and B. Zhang, *Earth Syst. Sci. Data*, 2021, **13**, 515–527.
- 13 M. J. Russell, D. E. Weller, T. E. Jordan, K. J. Sigwart and K. J. Sullivan, *Biogeochemistry*, 2008, **88**, 285–304.
- 14 D. Rathnayake, H. P. Schmidt, J. Leifeld, J. Mayer, C. A. Epper, T. D. Bucheli and N. Hagemann, *GCB Bioenergy*, 2023, **15**, 1078–1104.
- 15 J. K. Whalen and C. Chang, *J. Environ. Qual.*, 2001, **30**, 229–237.
- 16 H. M. Waldrip, P. H. Pagliari, Z. He, R. D. Harmel, N. A. Cole and M. Zhang, *Soil Sci. Soc. Am. J.*, 2015, **79**, 1601–1614.
- 17 M. Kacprzak, K. Malińska, A. Grosser, J. Sobik-Szotysek, K. Wystalska, D. Drózd, A. Jasińska and E. Meers, *Crit. Rev. Environ. Sci. Technol.*, 2023, **53**, 914–938.
- 18 O. F. Schoumans, F. Bouraoui, C. Kabbe, O. Oenema and K. C. van Dijk, *Ambio*, 2015, **44**, 180–192.
- 19 P. R. Rout, D. S. Pandey, M. Haynes-Parry, C. Briggs, H. L. C. Manuel, R. Umaphathi, S. Mukherjee, S. Panigrahi and M. Goel, *Waste Biomass Valorization*, 2023, **14**, 553–582.
- 20 G. Ström, A. Albiñ, T. Jinnerot, S. Boqvist, A. Andersson-Djurfeldt, S. Sokerya, K. Osbjör, S. San, H. Davun and U. Magnusson, *Sci. Total Environ.*, 2018, **621**, 193–200.
- 21 X. Liang, Y. Jin, M. He, C. Niyungeko, J. Zhang, C. Liu, G. Tian and Y. Arai, *Environ. Sci. Pollut. Res.*, 2018, **25**, 25780–25788.
- 22 D. Lachos-Perez, P. César Torres-Mayanga, E. R. Abaide, G. L. Zabot and F. De Castilhos, *Bioresour. Technol.*, 2022, **343**, 126084.
- 23 W. Christel, S. Bruun, J. Magid and L. S. Jensen, *Bioresour. Technol.*, 2014, **169**, 543–551.
- 24 S. Zhang, L. Wei, L. Trakal, S. Wang, S. M. Shaheen, J. Rinklebe and Q. Chen, *Sci. Total Environ.*, 2024, **906**, 167418.
- 25 G. Chen, J. Wang, F. Yu, X. Wang, H. Xiao, B. Yan and X. Cui, *Chemosphere*, 2022, **301**, uc134646.
- 26 D. Sun, L. Hale, G. Kar, R. Soolanayakanahally and S. Adl, *Chemosphere*, 2018, **194**, 682–691.
- 27 R. Huang, C. Fang, X. Lu, R. Jiang and Y. Tang, *Environ. Sci. Technol.*, 2017, **51**, 10284–10298.
- 28 E. O. Lidman Olsson, P. Glarborg, K. Dam-Johansen and H. Wu, *Energy Fuels*, 2023, **37**, 6907–6998.
- 29 M. Uchimiya, in *Applied Manure and Nutrient Chemistry for Sustainable Agriculture and Environment*, ed. Z. He and H. Zhang, 2014, pp. 53–68.
- 30 Z. Fang, X. Zhuang, X. Zhang, Y. Li, R. Li and L. Ma, *Fuel*, 2023, **333**, 126544.
- 31 X. He, Y. Wang, Y. Zhang, C. Wang, J. Yu, H. Ohtake and T. Zhang, *Mater. Sci. Energy Technol.*, 2023, **6**, 94–104.
- 32 X. Ran, Y. Deng, N. S. T. Uppuluri, B. Li, Y. Zheng, P. Chen, R. Dong, J. Müller, J. Guo and H. Oechsner, *Sci. Total Environ.*, 2023, **892**, 164346.
- 33 G. Su, H. C. Ong, N. W. Mohd Zulkifli, S. Ibrahim, W. H. Chen, C. T. Chong and Y. S. Ok, *J. Cleaner Prod.*, 2022, **343**, 130965.



- 34 S. Tan, G. Zhou, Q. Yang, S. Ge, J. Liu, Y. W. Cheng, P. N. Y. Yek, W. A. Wan Mahari, S. H. Kong, J. S. Chang, C. Sonne, W. W. F. Chong and S. S. Lam, *Sci. Total Environ.*, 2023, **864**, 160990.
- 35 C. I. Aragón-Briceño, A. K. Pozarlik, E. A. Bramer, L. Niedzwiecki, H. Pawlak-Kruczek and G. Brem, *Renewable Energy*, 2021, **171**, 401–415.
- 36 T. Tiecher, M. Zafar, F. J. K. Mallmann, E. C. Bortoluzzi, M. A. Bender, L. H. Ciotti and D. R. d. Santos, *Rev. Bras. Cienc. Solo*, 2014, **38**, 1506–1514.
- 37 R. McDowell, Z. Dou, J. Toth, B. Cade-Menun, P. Kleinman, K. Soder and L. Saporito, *J. Environ. Qual.*, 2008, **37**, 741–752.
- 38 B. Ajiboye, O. O. Akinremi, Y. Hu and D. N. Flaten, *J. Environ. Qual.*, 2007, **36**, 1563–1576.
- 39 B. Ajiboye, O. O. Akinremi and G. J. Racz, *J. Environ. Qual.*, 2004, **33**, 1062–1069.
- 40 P. H. Pagliari and C. A. M. Laboski, *J. Environ. Qual.*, 2012, **41**, 901–910.
- 41 P. H. Pagliari and C. A. M. Laboski, *Biol. Fertil. Soils*, 2013, **49**, 987–999.
- 42 Z. He, C. W. Honeycutt, T. S. Griffin, B. J. Cade-Menun, P. J. Pellechia and Z. Dou, *J. Environ. Qual.*, 2009, **38**, 1909–1918.
- 43 G. Li, H. Li, P. A. Leffelaar, J. Shen and F. Zhang, *PLoS One*, 2014, **9**, e102698.
- 44 A. L. Shober, D. L. Hesterberg, J. T. Sims and S. Gardner, *J. Environ. Qual.*, 2006, **35**, 1983–1993.
- 45 X. Ran, N. S. T. Uppuluri, Y. Deng, Y. Zheng, R. Dong, J. Müller, H. Oechsner, B. Li and J. Guo, *Sci. Total Environ.*, 2023, **874**, 162547.
- 46 B. L. Turner and A. B. Leytem, *Environ. Sci. Technol.*, 2004, **38**, 6101–6108.
- 47 K. B. Cantrell, P. G. Hunt, M. Uchimiya, J. M. Novak and K. S. Ro, *Bioresour. Technol.*, 2012, **107**, 419–428.
- 48 F. Liu, Z. Xiao, J. Fang and H. Li, *Sustainability*, 2023, **15**, 9215.
- 49 X. Cao and W. Harris, *Bioresour. Technol.*, 2010, **101**, 5222–5228.
- 50 J. R. Sanford, D. Johnstone and R. A. Larson, *Bioresour. Technol. Rep.*, 2022, **19**, 101169.
- 51 M. Laghari, D. S. Müller-Stöver, M. Puig-Arnavat, T. P. Thomsen and U. B. Henriksen, *Waste Biomass Valorization*, 2021, **12**, 5517–5532.
- 52 J. Guo, L. Zheng, Z. Li, X. Zhou, S. Cheng, L. Zhang and Q. Zhang, *J. Cleaner Prod.*, 2021, **311**, 127458.
- 53 M. Z. Hossain, M. M. Bahar, B. Sarkar, S. W. Donne, P. Wade and N. Bolan, *J. Anal. Appl. Pyrolysis*, 2021, **155**, 105043.
- 54 T. Komiyama, T. Ito and M. Saigusa, *Soil Sci. Plant Nutr.*, 2014, **60**, 196–207.
- 55 J. S. Robinson, K. Baumann, Y. Hu, P. Hagemann, L. Kebelmann and P. Leinweber, *Ambio*, 2018, **47**, 73–82.
- 56 K. Sun, M. Qiu, L. Han, J. Jin, Z. Wang, Z. Pan and B. Xing, *Sci. Total Environ.*, 2018, **634**, 1300–1307.
- 57 R. Q. Jiang, G. W. Yu, L. H. Yu, Y. Wang, C. J. Li, Z. J. Xing, X. M. Xue, Y. Wang and C. Yu, *Sci. Total Environ.*, 2024, **915**, 170116.
- 58 Y. Cheng, L. Luo, J. Lv, G. Li, B. Wen, Y. Ma and R. Huang, *Environ. Sci. Technol.*, 2020, **54**, 9008–9014.
- 59 W. T. Tsai, S. C. Liu, H. R. Chen, Y. M. Chang and Y. L. Tsai, *Chemosphere*, 2012, **89**, 198–203.
- 60 K. Wang, N. Peng, G. Lu and Z. Dang, *Waste Biomass Valorization*, 2020, **11**, 613–624.
- 61 B. L. Turner, *J. Environ. Qual.*, 2004, **33**, 757–766.
- 62 E. E. Codling, *Soil Sci.*, 2006, **171**, 858–864.
- 63 Z. He, Z. N. Senwo, R. N. Mankolo and C. W. Honeycutt, *J. Food, Agric. Environ.*, 2006, **4**, 304–312.
- 64 L. M. Simbolon, D. S. Pandey, A. Horvat, J. J. Leahy, S. A. Tassou and M. Kwapinska, *Biomass Convers. Biorefin.*, 2023, **14**, 26443–26457.
- 65 N. S. Topcu, G. Duman, H. Olgun and J. Yanik, *ACS Omega*, 2022, **7**, 20710–20718.
- 66 S. Katuwal, A. J. Ashworth, N.-A.-S. Rafsan and P. Kolar, *Biomass*, 2022, **2**, 209–223.
- 67 R. Keskinen, J. Hyväluoma, L. Sohlo, H. Help and K. Rasa, *Biochar*, 2019, **1**, 259–270.
- 68 W. Song and M. Guo, *J. Anal. Appl. Pyrolysis*, 2012, **94**, 138–145.
- 69 M. Zolfi Bavariani, A. Ronaghi and R. Ghasemi, *Commun. Soil Sci. Plant Anal.*, 2019, **50**, 402–411.
- 70 B. Bergfeldt, M. T. Morgano, H. Leibold, F. Richter and D. Stapf, *Agriculture*, 2018, **8**, 187.
- 71 E. Humer and Q. Zebeli, *Anim. Feed Sci. Technol.*, 2015, **209**, 1–15.
- 72 M. R. Bedford, *Anim. Feed Sci. Technol.*, 2000, **86**, 1–13.
- 73 E. Kebreab and A. B. Leytem, in *Clinical Aspects of Natural and Added Phosphorus in Foods*, ed. O. M. Gutierrez, K. Kalantar-Zadeh and R. Mehrota, 2017, pp. 123–131.
- 74 A. Bougouin, J. A. D. R. N. Appuhamy, E. Kebreab, J. Dijkstra, R. P. Kwakkel and J. France, *Poult. Sci.*, 2014, **93**, 1981–1992.
- 75 P. Rosenfelder-Kuon, W. Siegert and M. Rodehutschord, *Arch. Anim. Nutr.*, 2020, **74**, 1–18.
- 76 V. D. Nair, D. A. Graetz and D. O. Dooley, *Food Agric. Environ.*, 2003, **1**, 217–223.
- 77 G. S. Toor, J. D. Peak and J. T. Sims, *J. Environ. Qual.*, 2005, **34**, 687–697.
- 78 A. B. Leytem, P. W. Plumstead, R. O. Maguire, P. Kwanyuen and J. Brake, *J. Environ. Qual.*, 2007, **36**, 453–463.
- 79 P. Peperzak, A. Caldwell, R. Hunziker and C. Black, *Soil Sci.*, 1959, **87**, 293–302.
- 80 C. A. E. Peirce, R. J. Smernik and T. M. McBeath, *Plant Soil*, 2013, **373**, 359–372.
- 81 Z. He, C. W. Honeycutt and T. S. Griffin, *Biol. Fertil. Soils*, 2003, **38**, 78–83.
- 82 H. W. Dail, Z. He, M. S. Erich and C. W. Honeycutt, *Commun. Soil Sci. Plant Anal.*, 2007, **38**, 1879–1895.
- 83 P. H. Pagliari, in *Applied Manure and Nutrient Chemistry for Sustainable Agriculture and Environment*, ed. Z. He and H. Zhang, 2014, pp. 141–161.



- 84 Z. He, P. H. Pagliari and H. M. Waldrip, *Pedosphere*, 2016, **26**, 779–816.
- 85 M. J. Seufferheld and M. J. Curzi, *Plant Mol. Biol. Rep.*, 2010, **28**, 549–559.
- 86 B. J. Cade-Menun, *Talanta*, 2005, **66**, 359–371.
- 87 P. Leinweber, L. Haumaier and W. Zech, *Biol. Fertil. Soils*, 1997, **25**, 89–94.
- 88 B. Cade-Menun and C. W. Liu, *Soil Sci. Soc. Am. J.*, 2014, **78**, 19–37.
- 89 B. J. Cade-Menun, Z. He and Z. Dou, *Commun. Soil Sci. Plant Anal.*, 2015, **46**, 1698–1712.
- 90 R. W. McDowell and I. Stewart, *J. Environ. Qual.*, 2005, **34**, 598–607.
- 91 Y. Hashimoto, A. Takamoto, R. Kikkawa, K. Murakami and N. Yamaguchi, *Environ. Sci. Technol.*, 2014, **48**, 5486–5492.
- 92 M. Uchimiya and S. Hiradate, *J. Agric. Food Chem.*, 2014, **62**, 1802–1809.
- 93 M. Uchimiya, S. Hiradate and M. J. Antal, *ACS Sustainable Chem. Eng.*, 2015, **3**, 1642–1649.
- 94 C. R. de Souza, A. K. Ghosh, I. R. da Silva, E. S. de Alvarenga, R. F. Novais and G. L. de Jesus, *Rev. Bras. Cienc. Solo*, 2012, **36**, 1516–1527.
- 95 Z. Dou, J. D. Toth, D. T. Galligan, C. F. Ramberg Jr and J. D. Ferguson, *J. Environ. Qual.*, 2000, **29**, 508–514.
- 96 M. García-Albacete, A. Martín and M. C. Cartagena, *Waste Manage.*, 2012, **32**, 1061–1068.
- 97 K. Dinkler, B. Li, J. Guo, B. Hülsemann, G. C. Becker, J. Müller and H. Oechsner, *Bioresour. Technol.*, 2021, **331**, 125038.
- 98 A. Tuszyńska, K. Czerwionka and H. Obarska-Pempkowiak, *J. Environ. Manage.*, 2021, **278**, 111468.
- 99 M. Hedley, J. Stewart and B. Chauhan, *Soil Sci. Soc. Am. J.*, 1982, **46**, 970–976.
- 100 A. Sharpley and B. Moyer, *J. Environ. Qual.*, 2000, **29**, 1462–1469.
- 101 J. S. Robinson and P. Leinweber, *Waste Manage.*, 2023, **172**, 358–367.
- 102 G. Xu, Y. Zhang, H. Shao and J. Sun, *Sci. Total Environ.*, 2016, **569–570**, 65–72.
- 103 S. Buehler, A. Oberson, I. M. Rao, D. K. Friesen and E. Frossard, *Soil Sci. Soc. Am. J.*, 2002, **66**, 868–877.
- 104 T. T. Qian and H. Jiang, *ACS Sustainable Chem. Eng.*, 2014, **2**, 1411–1419.
- 105 X. Cui, X. Yang, K. Sheng, Z. He and G. Chen, *ACS Sustainable Chem. Eng.*, 2019, **7**, 16520–16528.
- 106 P. J. A. Kleinman, A. N. Sharpley, A. M. Wolf, D. B. Beegle and P. A. Moore Jr, *Soil Sci. Soc. Am. J.*, 2002, **66**, 2009–2015.
- 107 P. J. Worsfold, L. J. Gimbert, U. Mankasingh, O. N. Omaka, G. Hanrahan, P. C. Gardolinski, P. M. Haygarth, B. L. Turner, M. J. Keith-Roach and I. D. McKelvie, *Talanta*, 2005, **66**, 273–293.
- 108 Z. He, C. W. Honeycutt, B. J. Cade-Menun, Z. N. Senwo and I. A. Tazisong, *Soil Sci. Soc. Am. J.*, 2008, **72**, 1425–1433.
- 109 Z. He, T. S. Griffin and C. W. Honeycutt, *J. Environ. Qual.*, 2004, **33**, 1528–1534.
- 110 R. Huang, C. Fang, B. Zhang and Y. Tang, *Environ. Sci. Technol.*, 2018, **52**, 3016–3026.
- 111 D. Kumaragamage, O. O. Akinremi and L. Grieger, *J. Environ. Qual.*, 2013, **42**, 1863–1871.
- 112 W. Li, X. Feng, W. Song and M. Guo, *Front. Sustainable Food Syst.*, 2018, **2**, 20.
- 113 V. Ruban, J. López-Sánchez, P. Pardo, G. Rauret, H. Muntau and P. Quevauviller, *Fresenius' J. Anal. Chem.*, 2001, **370**, 224–228.
- 114 L. Zuo, R. Lin, Q. Shi and S. Xu, *Water, Air, Soil Pollut.*, 2020, **231**, ac553.
- 115 S. Hunger, H. Cho, J. T. Sims and D. L. Sparks, *Environ. Sci. Technol.*, 2004, **38**, 674–681.
- 116 C. A. Shand, G. Coutts, S. Hillier, D. G. Lumsdon, A. Chudek and J. Eubeler, *Environ. Sci. Technol.*, 2005, **39**, 9205–9210.
- 117 K. Güngör, A. Jürgensen and K. G. Karthikeyan, *J. Environ. Qual.*, 2007, **36**, 1856–1863.
- 118 F. Kizewski, Y. T. Liu, A. Morris and D. Hesterberg, *J. Environ. Qual.*, 2011, **40**, 751–766.
- 119 H. Yang, R. Yan, H. Chen, D. H. Lee and C. Zheng, *Fuel*, 2007, **86**, 1781–1788.
- 120 T. R. Brown, M. M. Wright and R. C. Brown, *Biofuels, Bioprod. Biorefin.*, 2011, **5**, 54–68.
- 121 T. Y. A. Fahmy, Y. Fahmy, F. Mobarak, M. El-Sakhawy and R. E. Abou-Zeid, *Environ. Dev. Sustainability*, 2020, **22**, 17–32.
- 122 D. S. Pandey, G. Katsaros, C. Lindfors, J. J. Leahy and S. A. Tassou, *Sustainability*, 2019, **11**, 2533.
- 123 M. Azuara, S. R. A. Kersten and A. M. J. Kootstra, *Biomass Bioenergy*, 2013, **49**, 171–180.
- 124 R. Keskinen, J. Hyväluoma, J. Nikama, T. Sainio and K. Ylivainio, *Environ. Technol. Innovation*, 2023, **32**, r103401.
- 125 A. C. Acosta, C. A. Arias, P. Biller, N. K. Wittig, I. A. Baragau, M. J. Alhnidi, G. Ravenni, Z. Sárossy, L. Benedini, L. E. Abramiuc, D. G. Popescu, W. Negassa, V. F. Marulanda, D. S. Müller-Stöver and H. Brix, *Chem. Eng. J.*, 2024, **492**, 151916.
- 126 W. J. Liu, F. X. Zeng, H. Jiang and H. Q. Yu, *Bioresour. Technol.*, 2011, **102**, 3471–3479.
- 127 Q. Zhang, H. Liu, W. Li, J. Xu and Q. Liang, *Energy Fuels*, 2012, **26**, 2830–2836.
- 128 N. Touray, W. T. Tsai and M. H. Li, *Waste Biomass Valorization*, 2014, **5**, 1029–1033.
- 129 S. Wang, H. Zhang, H. Huang, R. Xiao, R. Li and Z. Zhang, *Process Saf. Environ. Prot.*, 2020, **139**, 218–229.
- 130 Y. Yue, Q. Lin, Y. Xu, G. Li and X. Zhao, *J. Anal. Appl. Pyrolysis*, 2017, **124**, 355–361.
- 131 J. Sun, F. He, Y. Pan and Z. Zhang, *Acta Agric. Scand., Sect. B*, 2017, **67**, 12–22.
- 132 S. Li, S. Harris, A. Anandhi and G. Chen, *J. Cleaner Prod.*, 2019, **215**, 890–902.
- 133 A. L. M. Daneluti and J. R. Matos, *Braz. J. Pharm. Sci.*, 2013, **49**, 275–283.
- 134 M. T. Morgano, B. Bergfeldt, H. Leibold, F. Richter and D. Stapf, *Chem. Eng. Trans.*, 2018, **65**, 649–654.
- 135 Y. Liang, X. Cao, L. Zhao, X. Xu and W. Harris, *J. Environ. Qual.*, 2014, **43**, 1504–1509.
- 136 Y. Jiang, C. Ren, H. Guo, M. Guo and W. Li, *Environ. Sci. Technol.*, 2019, **53**, 13841–13849.



- 137 R. Xiao, J. J. Wang, L. A. Gaston, B. Zhou, J. H. Park, R. Li, S. K. Dodla and Z. Zhang, *Waste Manage.*, 2018, **78**, 802–810.
- 138 A. D. A. Leite, L. C. A. Melo, L. C. C. Hurtarte, L. Zuin, C. D. Piccola, D. Werder, I. Shabtai and J. Lehmann, *Chemosphere*, 2023, **331**, 138759.
- 139 J. A. Rodriguez, J. F. Lustosa Filho, L. C. A. Melo, I. R. de Assis and T. S. de Oliveira, *J. Anal. Appl. Pyrolysis*, 2021, **155**, 105036.
- 140 T. J. Rose, C. Scheffe, Z. H. Weng, M. T. Rose, L. van Zwieten, L. Liu and A. L. Rose, *Plant Soil*, 2019, **443**, 233–244.
- 141 T. Wang, M. Camps-Arbestain, M. Hedley and P. Bishop, *Plant Soil*, 2012, **357**, 173–187.
- 142 G. Gascó, J. Paz-Ferreiro, M. L. Álvarez, A. Saa and A. Méndez, *Waste Manage.*, 2018, **79**, 395–403.
- 143 C.-C. Tsai and Y.-F. Chang, *Agronomy*, 2021, **11**, 1692.
- 144 N. H. Christiansen, P. Sørensen, R. Labouriau, B. T. Christensen and G. H. Rubæk, *J. Plant Nutr. Soil Sci.*, 2020, **183**, 416–428.
- 145 O. Duboc, A. Hernandez-Mora, W. W. Wenzel and J. Santner, *Sci. Total Environ.*, 2022, **806**, 150486.
- 146 S. Kratz, C. Vogel and C. Adam, *Nutr. Cycling Agroecosyst.*, 2019, **115**, 1–39.
- 147 S. Nanzer, A. Oberson, U. Eggenberger and E. Frossard, *J. Environ. Qual.*, 2019, **48**, 746–754.
- 148 O. Duboc, J. Santner, A. Golestani Fard, F. Zehetner, J. Tacconi and W. W. Wenzel, *Sci. Total Environ.*, 2017, **599–600**, 1160–1170.
- 149 S. Bruun, S. L. Harmer, G. Bekiaris, W. Christel, L. Zuin, Y. Hu, L. S. Jensen and E. Lombi, *Chemosphere*, 2017, **169**, 377–386.
- 150 C. Hong, Y. Su and S. Lu, *Environ. Sci. Pollut. Res.*, 2018, **25**, 30547–30556.
- 151 A. Hernandez-Mora, O. Duboc, E. K. Bünemann, K. Ylivainio, E. Lombi, S. Symanczik, D. Horn, A. Delgado, N. Abu Zahra, L. Zuin, C. L. Doolette, H. Eigner and J. Santner, *Environ. Technol. Innovation*, 2025, **37**, 103913.
- 152 G. C. Becker and A. Kruse, *ACS Sustainable Chem. Eng.*, 2023, **11**, 15841–15850.
- 153 Y. Wang, Y. Lin, P. C. Chiu, P. T. Imhoff and M. Guo, *Sci. Total Environ.*, 2015, **512–513**, 454–463.
- 154 J. F. Lustosa Filho, E. S. Penido, P. P. Castro, C. A. Silva and L. C. A. Melo, *ACS Sustainable Chem. Eng.*, 2017, **5**, 9043–9052.
- 155 J. S. D. S. Carneiro, I. C. A. Ribeiro, B. O. Nardis, C. F. Barbosa, J. F. Lustosa Filho and L. C. A. Melo, *Sci. Total Environ.*, 2021, **760**, 143955.
- 156 V. Vimal, A. A. Karim, M. Kumar, A. Ray, K. Biswas, S. Maurya, D. Subudhi and N. K. Dhal, *Chemosphere*, 2022, **300**, 134512.
- 157 F. Yu, J. Wang, X. Wang, Y. Wang, Q. Guo, Z. Wang, X. Cui, Y. Hu, B. Yan and G. Chen, *Biochar*, 2023, **5**, 82.
- 158 K. Jetsrisuparb, T. Jeejaila, C. Saengthip, P. Kasemsiri, Y. Ngernyen, P. Chindaprasirt and J. T. N. Knijnenburg, *RSC Adv.*, 2022, **12**, 30539–30548.
- 159 J. T. N. Knijnenburg, P. Kasemsiri, W. Kaewpradit, T. Tarinta, W. Jantapa, T. Jeejaila, C. Saengthip and K. Jetsrisuparb, *Biomass Convers. Biorefin.*, 2024, **14**, 15351–15361.
- 160 J. T. N. Knijnenburg, K. Laohasurayotin, P. Khemthong and W. Kangwansupamonkon, *Chemosphere*, 2019, **223**, 310–318.
- 161 S. Suwanree, J. T. N. Knijnenburg, P. Kasemsiri, W. Kraithong, P. Chindaprasirt and K. Jetsrisuparb, *Biomass Bioenergy*, 2022, **156**, 106304.
- 162 S. Hadroug, S. Jellali, J. J. Leahy, M. Kwapinska, M. Jeguirim, H. Hamdi and W. Kwapinski, *Water*, 2019, **11**, 2271.
- 163 M. I. Piash, K. Iwabuchi, T. Itoh and K. Uemura, *Geoderma*, 2021, **397**, 115100.
- 164 Y. Jin, X. Liang, M. He, Y. Liu, G. Tian and J. Shi, *Chemosphere*, 2016, **142**, 128–135.
- 165 S. Hadroug, S. Jellali, M. Jeguirim, M. Kwapinska, H. Hamdi, J. J. Leahy and W. Kwapinski, *Sustainability*, 2021, **13**, 1–26.
- 166 S. C. Lung and B. L. Lim, *Plant Soil*, 2006, **279**, 187–199.
- 167 L. O. Torres-Dorante, N. Claassen, B. Steingrobe and H. W. Olf, *J. Plant Nutr. Soil Sci.*, 2005, **168**, 352–358.
- 168 H. P. Schmidt, C. Kammann, N. Hagemann, J. Leifeld, T. D. Bucheli, M. A. Sánchez Monedero and M. L. Cayuela, *GCB Bioenergy*, 2021, **13**, 1708–1730.
- 169 B. Glaser and V. I. Lehr, *Sci. Rep.*, 2019, **9**, 9338.
- 170 F. Tesfaye, X. Liu, J. Zheng, K. Cheng, R. Bian, X. Zhang, L. Li, M. Drosos, S. Joseph and G. Pan, *Environ. Sci. Pollut. Res.*, 2021, **28**, 34108–34120.
- 171 J. Zhang, B. Huang, L. Chen, Y. Li, W. Li and Z. Luo, *Chem. Speciation Bioavailability*, 2018, **30**, 57–67.
- 172 R. Subedi, N. Taupe, I. Ikoyi, C. Bertora, L. Zavattaro, A. Schmalenberger, J. J. Leahy and C. Grignani, *Sci. Total Environ.*, 2016, **550**, 924–933.
- 173 A. Gunes, A. Inal, M. Taskin, O. Sahin, E. Kaya and A. Atakol, *Soil Use Manage.*, 2014, **30**, 182–188.
- 174 O. F. Madiba, Z. M. Solaiman, J. K. Carson and D. V. Murphy, *Biol. Fertil. Soils*, 2016, **52**, 439–446.
- 175 M. Najafi-Ghiri, T. Razeghizadeh, M. S. Taghizadeh and H. R. Boostani, *Commun. Soil Sci. Plant Anal.*, 2019, **50**, 2610–2625.
- 176 A. Hernandez-Mora, O. Duboc, E. Lombi, E. K. Bünemann, K. Ylivainio, S. Symanczik, A. Delgado, N. Abu Zahra, J. Nikama, L. Zuin, C. L. Doolette, H. Eigner and J. Santner, *J. Cleaner Prod.*, 2024, **467**, 142957.
- 177 M. Sarvi, M. Hagner, S. Velmala, H. Soinne, R. Uusitalo, R. Keskinen, K. Ylivainio, J. Kaseva and K. Rasa, *Environ. Technol. Innovation*, 2021, **23**, 101584.
- 178 T. Vanden Nest, F. Amery, L. Fryda, C. Boogaerts, J. Bilbao and B. Vandecasteele, *Sci. Total Environ.*, 2021, **750**, 141699.
- 179 Y. Xu, F. Qi, Y. Yan, W. Sun, T. Bai, N. Lu, H. Luo, C. Liu, B. Yuan and Z. Sheng, *Waste Manage.*, 2023, **169**, 52–61.
- 180 W. Buss, C. Wurzer, M. Bach, J. Heberling, T. Appel, H. Gerber and O. Mašek, *J. Environ. Manage.*, 2022, **314**, 115035.
- 181 T. Liu, T. Shao, J. Jiang, W. Ma, R. Feng, D. Dong, Y. Wang, T. Bai and Y. Xu, *Sci. Rep.*, 2024, **14**, 21069.



- 182 M. I. Piash, K. Iwabuchi and T. Itoh, *Sci. Total Environ.*, 2022, **822**, 153509.
- 183 J. T. Padilla, D. W. Watts, J. M. Novak, V. Cerven, J. A. Ippolito, A. A. Szogi and M. G. Johnson, *Biochar*, 2023, **5**, 64.
- 184 W. Jantapa, K. Jetsrisuparb, D. Macquarrie, P. Kasemsiri, P. Chindaprasirt and J. T. N. Knijnenburg, *Waste Biomass Valorization*, 2024, DOI: [10.1007/s12649-024-02824-6](https://doi.org/10.1007/s12649-024-02824-6).
- 185 C. Kopp, P. Sica, A. G. Eising, D. E. Madsen, J. Magid and D. S. Müller-Stöver, *Waste Biomass Valorization*, 2024, **15**, 4291–4307.
- 186 J. Li, Y. Li, F. Liu, X. Zhang, M. Song and R. Li, *J. Anal. Appl. Pyrolysis*, 2023, **173**, 106065.
- 187 S. Tang, F. Yan, C. Zheng and Z. Zhang, *ACS Sustainable Chem. Eng.*, 2018, **6**, 9167–9177.
- 188 J. Chen, S. Tang, F. Yan and Z. Zhang, *Water Res.*, 2020, **171**, 115450.
- 189 M. Brtnicky, R. Datta, J. Holatko, L. Bielska, Z. M. Gusiati, J. Kucerik, T. Hammerschmidt, S. Danish, M. Radziemska, L. Mravcova, S. Fahad, A. Kintl, M. Sudoma, N. Ahmed and V. Pecina, *Sci. Total Environ.*, 2021, **796**, 148756.
- 190 P. Godlewska, Y. S. Ok and P. Oleszczuk, *J. Hazard. Mater.*, 2021, **403**, 123833.
- 191 L. Xiang, S. Liu, S. Ye, H. Yang, B. Song, F. Qin, M. Shen, C. Tan, G. Zeng and X. Tan, *J. Hazard. Mater.*, 2021, **420**, 126611.
- 192 H. Zheng, B. Liu, G. Liu, Z. Cai and C. Zhang, in *Biochar from Biomass and Waste: Fundamentals and Applications*, 2018, pp. 349–384.
- 193 S. Li, D. Zou, L. Li, L. Wu, F. Liu, X. Zeng, H. Wang, Y. Zhu and Z. Xiao, *Chemosphere*, 2020, **247**, 125962.
- 194 T. Bai, W. Qu, Y. Yan, K. Ma, Y. Xu, X. Zhou, Y. Chen and Y. Xu, *J. Environ. Sci. Health, Part B*, 2020, **55**, 941–950.
- 195 F. Li, X. Wu, W. Ji, X. Gui, Y. Chen, J. Zhao, C. Zhou and T. Ren, *J. Anal. Appl. Pyrolysis*, 2020, **152**, 104945.
- 196 K. Wystalska, K. Malińska, J. Sobik-Szołtysek, D. Drózd and E. Meers, *Materials*, 2023, **16**, 6392.
- 197 A. G. Rombolà, G. Marisi, C. Torri, D. Fabbri, A. Buscaroli, M. Ghidotti and A. Hornung, *J. Agric. Food Chem.*, 2015, **63**, 6660–6667.
- 198 C. R. Smith, E. M. Buzan and J. W. Lee, *ACS Sustainable Chem. Eng.*, 2013, **1**, 118–126.
- 199 Y. Y. Wang, X. R. Jing, L. L. Li, W. J. Liu, Z. H. Tong and H. Jiang, *ACS Sustainable Chem. Eng.*, 2017, **5**, 481–488.
- 200 P. Oleszczuk, I. Joško and M. Kuśmierz, *J. Hazard. Mater.*, 2013, **260**, 375–382.
- 201 L. Leng, S. Xu, R. Liu, T. Yu, X. Zhuo, S. Leng, Q. Xiong and H. Huang, *Bioresour. Technol.*, 2020, **298**, 122286.
- 202 P. Cely, G. Gascó, J. Paz-Ferreiro and A. Méndez, *J. Anal. Appl. Pyrolysis*, 2015, **111**, 173–182.
- 203 T. Wang, M. Camps Arbestain, M. Hedley and P. Bishop, *Org. Geochem.*, 2012, **51**, 45–54.
- 204 A. Gross and B. Glaser, *Sci. Rep.*, 2021, **11**, 5516.
- 205 E. Maillard and D. A. Angers, *Global Change Biol.*, 2014, **20**, 666–679.
- 206 M. Uchimiya, T. Ohno and Z. He, *J. Anal. Appl. Pyrolysis*, 2013, **104**, 84–94.
- 207 S. Schouten, J. W. van Groenigen, O. Oenema and M. L. Cayuela, *GCB Bioenergy*, 2012, **4**, 751–760.
- 208 A. Gross, T. Bromm, S. Polifka, D. Fischer and B. Glaser, *Sci. Total Environ.*, 2024, **954**, 176340.
- 209 A. Gross, T. Bromm and B. Glaser, *Agronomy*, 2021, **11**, 2474.
- 210 M. Fernandez-Lopez, M. Puig-Gamero, D. Lopez-Gonzalez, A. Avalos-Ramirez, J. Valverde and L. Sanchez-Silva, *Bioresour. Technol.*, 2015, **182**, 184–192.
- 211 E. Struhs, A. Mirkouei, Y. You and A. Mohajeri, *Appl. Energy*, 2020, **279**, 115782.
- 212 R. R. Bora, Y. Tao, J. Lehmann, J. W. Tester, R. E. Richardson and F. You, *ACS Sustainable Chem. Eng.*, 2020, **8**, 5763–5775.
- 213 R. R. Bora, M. Lei, J. W. Tester, J. Lehmann and F. You, *ACS Sustainable Chem. Eng.*, 2020, **8**, 8436–8447.
- 214 L. Champion, M. Bekchanova, R. Malina and T. Kuppens, *J. Cleaner Prod.*, 2023, **408**, 137138.

