



Faraday Discussions

The Lesser Purple Emperor, *Apatura ilia*: from mimesis to biomimetics

Journal:	<i>Faraday Discussions</i>
Manuscript ID	FD-ART-03-2020-000036.R1
Article Type:	Paper
Date Submitted by the Author:	27-Mar-2020
Complete List of Authors:	Schenk, Franziska; Birmingham City University, School of Art Stavenga, Doekele; University Groningen, Computational Physics

SCHOLARONE™
Manuscripts

1 **The Lesser Purple Emperor butterfly, *Apatura ilia*: from mimesis to biomimetics**

2

3 **Franziska Schenk^{1,*} and Doekele G. Stavenga²**4 ¹ School of Art, Birmingham Institute of Art and Design, Birmingham City University,
5 Birmingham, U.K.6 ² Zernike Institute for Advanced Materials, University of Groningen, Groningen, the
7 Netherlands8 * E-Mail: Franziska.Schenk@bcu.ac.uk

9

10 **Abstract.** Until now, hues as dynamic as those adorning the *Apatura* Emperor butterflies have
11 never been encountered in the painting world. Unlike and unmatched by the chemical pigments
12 traditionally found on the painter's palette, the Emperor's wings are studded with strongly
13 reflecting iridescent scales that are structured like those of the iconic morpho butterflies. The
14 scale ridges act as diffractive multilayers, giving rise to narrow-band reflectance spectra. All
15 scales together create a vividly purple iridescent wing colouration that is observed within a
16 narrow angular range only. Recently, synthetic structures analogous to the multilayer reflectors
17 found on butterfly wings have been developed, referred to as effect pigments. Artists can obtain
18 vital clues on how to adapt and adopt these challenging new materials for painting, by tracing the
19 origin of biomimetics back to the ancient concept of mimesis and building on the knowledge
20 accumulated by optical studies. By selecting various effect pigments, and using the Lesser Purple
21 Emperor butterfly, *Apatura ilia*, as exemplar, we have accurately mimicked the butterfly's
22 iridescence in art. The resulting artwork, like the butterfly, fluctuates in perceived colour
23 depending on the direction of illumination and viewing. These nature-inspired-colouration and
24 biomimetic-application methods extend the canon of art.

25

26 **Keywords:** biophotonics – optical art – colour – multilayers - effect pigments27 **Short title:** Biomimetics of the Lesser Purple Emperor

28

29 **Introduction**

30 Located at the interface of art and science, and drawing on relevant findings from optical
31 physics and material science, this paper argues that the scientific field of biomimetics has the
32 potential to lead to and enable 'smarter' art. In tracing the origin of biomimetics back to the
33 ancient concept of mimesis (defined by Aristotle as 'imitation of nature' both via form and
34 material), we illuminate analogies that exist between the two concepts. In nature as well as art,

35 colour often plays a key role. For centuries, artists, in their attempts to faithfully render
36 natural appearances, forms and colours, have inevitably drawn on the most suitable materials
37 and ‘technologies’ nature provides. As we will see, new synthetic materials modelled on those
38 occurring in nature are continuously being added to the artist’s palette.

39 Two types of colouration are usually distinguished, namely pigmentary and structural.
40 Whereas pigmented media emit incident light diffusely, structural coloured objects generally
41 reflect light very directionally, with the colours shifting hue dependent on the direction of
42 illumination and viewing. This so-called iridescence thus is intimately connected to structural
43 colouration.

44 In art, virtually all colours are generated by chemical pigments, and their use is firmly
45 embedded in painting practice and theory. Structural colours are hardly found in art, however.
46 The search to artificially reproduce natural iridescences began at least 3000 years ago when,
47 as proven by an ancient Chinese document, humans already tried to imitate the lustre of
48 precious pearls by mixing different substances [1]. From the mid-20th century, sustained
49 attempts by industry to synthesise various lead, arsenic and bismuth salts for application as
50 pearl lustre pigments finally came to fruition in the mid 1930s. It has since taken industry a
51 further seventy years, and a succession of pearl lustre pigment-generations, i.e., basic lead
52 carbonate in the 1960s, bismuth oxychloride platelets in the 1970’s, followed by mica/metal
53 oxide platelets since the late 1970’s. Eventually, in the late 1990’s, synthetic multilayered
54 pigments capable of mimicking nature’s iridescent hues were realized [2]. Unlike chemical
55 pigments, the new synthetic, so-called effect pigments, consist of alternating layers of
56 transparent, colourless materials with differing refractive indices. They create colour by
57 wavelength-dependent light interference instead by light absorption, similar as the multilayer
58 reflectors found in pearls and butterflies, for example [3].

59 Although industry has exploited the novel properties of iridescent flakes for nearly two
60 decades, fine art painting has remained slow to assimilate them. Difficulties in sourcing the
61 materials are partly to blame. Although paints based on first-generation mica technology can
62 now be bought from specialist art suppliers, latest multilayer pigments unfortunately often can
63 only be purchased by industry, are prohibitively expensive and unavailable as artist paints. An
64 additional major hindrance is confusion caused by the incompatibility of the material’s
65 properties with the common colour theory as applied in painting [4]. Centuries of extensive
66 experience with light-absorbing pigments have led to firm rules of subtractive colour mixing.
67 As effect pigments are, as a raw material, a whitish powder (no matter what the colour on the
68 label), it immediately becomes apparent that the rules of easel painting no longer hold. In fact,

69 quite in contrast, styling with transparent, interference-effect pigments is additive, a concept
 70 alien to most painters. The central tenet of this paper is, however, that the new technology
 71 allows mimicking nature's optical technology. And that systematic analysis of the
 72 mechanisms causing iridescent colour-mixes in animals can inspire analogous artistic
 73 methods.

74 Gradually introduced since the late 1990's, the principal author of the present paper
 75 has since adapted and adopted effect pigments in fine art painting [5]. Building on earlier
 76 work on liquid crystals [6,7], Schenk has demonstrated that the considerable challenges posed
 77 by the new technology can be overcome by adopting a biomimetic approach [5,8,9]. For
 78 instance, the angle-dependent colours of jewel beetles could be faithfully mimicked in large-
 79 scale paintings [10].

80 As will be shown in this paper, due to the unique expertise thus gained, it has become
 81 possible to simulate the dynamic, metallic-like colouration of butterflies on canvas. Perhaps
 82 most notably, *Morpho* butterflies, a subfamily of the Nymphalidae, are famous for their bright
 83 blue coloured wings. Their wings are covered by scales, which have an upper lamina
 84 consisting of ridges that act as optical multilayer reflectors. Due to interference, the
 85 multilayers reflect incident light in a narrow (blue) wavelength range and into a narrow spatial
 86 angle [11,12]. The identical optical mechanism causes the iridescent blue colouration
 87 displayed by many butterfly species belonging to another nymphalid subfamily, the
 88 Apaturinae (the Emperors). These beautiful butterflies combine iridescent, structural colours
 89 with pigmentary colouration,

90



91

92

93 Fig. 1. The Lesser Purple Emperor butterfly, *Apatura ilia* (male). **A** UV image. **B, C** RGB
 94 images. **A, B** About normal illumination. **C** Oblique illumination. Scale bar: 2 cm

95

96 Here we put at the centre stage the Lesser Purple Emperor (*Apatura ilia*; Fig. 1), a
 97 butterfly species that has featured in several classical paintings. We first present the optical
 98 characteristics of this butterfly, and subsequently hone in on particular historical moments

99 during which *A. ilia* has come to short-lived prominence in works of art, such as in late
100 Antiquity, the Baroque and the Contemporary. To introduce how we have attempted to
101 artistically reproduce *A. ilia*'s rich gamut of colours, we analyse a number of effect pigments
102 suitable for our goal. We finally describe the procedures allowing to faithfully apply the novel
103 medium in art.

104


105 **Optical characteristics of wings and wing scales of *Apatura ilia***

106 The butterfly species *Apatura ilia* (Denis et Schiffermüller, 1775) is distributed in riparian
107 forests from Europe to the Amur region in Pacific Asia. In the whole range, two phenotypes
108 exist: dark *forma ilia* and light *forma clytie*. The dark phenotype mainly occurs in cooler
109 regions, where the larval development is long, while the light phenotype inhabits warmer
110 habitats, where the caterpillars grow faster [13]. All members of the genus are sexual
111 dimorphic, with only the males displaying iridescent colouration on the dorsal wing side. The
112 structural colour of males is visible in flight when the movements of the wings are noticeable
113 within a certain range of angles, thus forming an excellent contrast to the forest canopy.

114 The optical phenomena are readily explained by the architecture of the wing scales.
115 Scanning and transmission electron microscopy demonstrated that the iridescence resides in
116 the cover scales. Their scale ridges consist of a stack of chitinous lamellae interspersed with
117 air layers, so creating a multilayer reflector [14]. The multilayered cover scales are found
118 across the entirety of the dorsal forewings and part of the hindwings, as is revealed by UV
119 photography (Fig. 1A). These cover scales are transparent for incident light with wavelengths
120 in the visible range, which hence will reach the underlying ground scales (Fig. 1B). The
121 ground scales contain various amounts of melanin pigment, as is most clearly seen when
122 applying oblique illumination, so that the iridescence is outside the camera's aperture (Fig.
123 1C). In areas where the pigment density is high, the ground scales function as a strongly
124 absorbing, non-reflecting backing, so that with normal illumination only bright ultraviolet to
125 blue reflections are seen, but in areas with low pigment density, part of the light that passed
126 the cover scales will be reflected by the ground scales and thus will add to the visual signal,
127 leaving light blue to whitish reflections (Fig. 1B).

128 We also studied the spatial reflection properties of single cover scales by applying
129 imaging scatterometry [10,15]. To this end, the scales were isolated from the wing and glued
130 to a thin glass micropipette (Fig. 2A,B). Illumination of the upper side of a cover scale with a
131 narrow aperture beam of white light yields a purplish reflection, similar as seen at the intact
132 wings (Fig. 2C). The scatterogram appears to be restricted to about a planar spatial

133 distribution (Fig. 2C), closely resembling the scatterograms obtained from *Morpho* cover
 134 scales [15]. This is due to the ridges of the scale's upper lamina acting as long and slender
 135 multilayers, diffracting light into a plane almost perpendicular to the long axis of the ridges
 136 [12]. The scale's lower lamina approximates a thin plate with a bluish reflection (Fig. 2D). Its
 137 scatterogram is restricted to about a single spatial direction (Fig. 2E), showing that the lower
 138 lamina acts as a blue reflecting thin film, which further enhances the scale's violet-blue-
 139 peaking reflectance.
 140

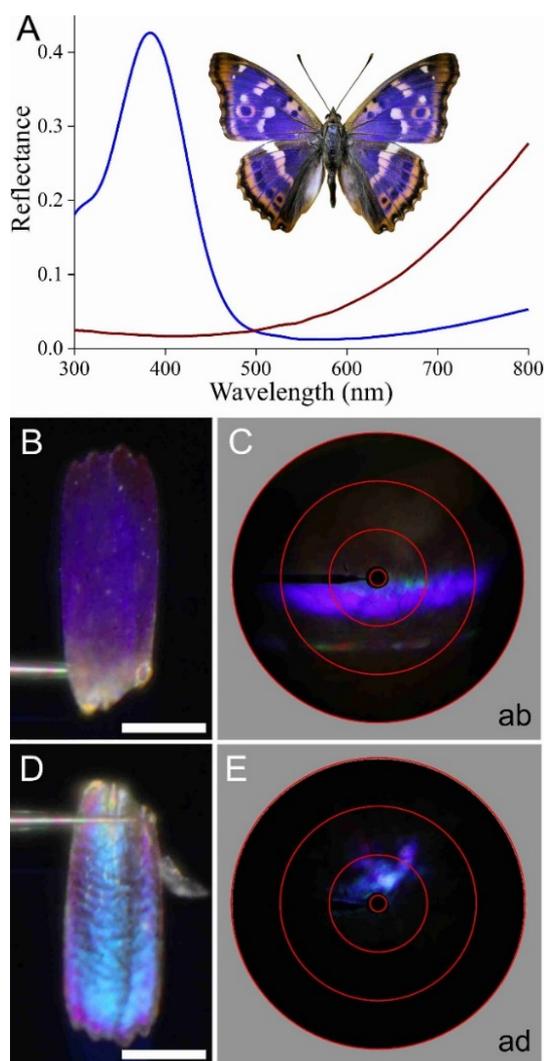

141

142

143 Fig. 2. Spectrophotometry and scatterometry of *A. ilia* wings and scales. **A** Reflectance
 144 spectra measured with a bifurcated reflection probe of the dorsal forewing with illumination
 145 about normal and obliquely to the scale multilayers (blue and brown curves, respectively). **B**
 146 An isolated cover scale photographed at the abwing (upper) side. **C** Scatterogram of the
 147 abwing side of the scale of **B**. **D** The scale of **B** seen at the adwing (lower) side. **E**
 148 Scatterogram of the adwing side of the scale of **D**.

149

150 **Historic attempts to mimic *Apatura ilia* and iridescence in art**

151 *Apatura ilia* acquired its scientific name only in the 18th century. Fabricius, the Danish
 152 entomologist who christened the species, apparently made up *Apatura* based on the Greek
 153 *apatao*, meaning to deceive, so possibly attempting a learned joke by inventing pseudo-Greek
 154 nomenclature to hint at, and employ, deception (Ref. 16, pp. 140-141). The male Lesser
 155 Purple Emperor's mantle is somber brown one minute and the next an electric brilliant purple,
 156 indeed a matter of 'now you see it, now you don't'. Arguably, it may precisely be this dual
 157 quality of alternately concealing and revealing the underlying darkness that has made, and
 158 continues to make, the Emperors a symbol most apt for inclusion in a particular genre of art,
 159 namely the *momento mori*, the Latin phrase for "remember you will die", that originated in
 160 ancient Rome.

161



162

163

164 Fig 3. *Memento Mori*, Pompeii (House cum workshop I, 5, 2, triclinium), 30 BCE-14CE, Inv.
 165 No. 109982, Napels National Archaeological Museum. **A** The complete mosaic. **B** Detail.
 166 (from <https://pompeitourguide.me/2013/07/30/memento-mori-at-pompeii/>)

167

168 An emblem most striking for the clarity of its allegorical representation was excavated
169 from the ruins of Pompeii beneath the volcanic ash in 79 AD (Fig. 3A). Sandwiched between
170 a skull and wheel is a butterfly with what appear to be iridescent purple wings. Although
171 Marren (Ref. 16, p. 159) identified the butterfly as the Lesser Purple Emperor, *Apatura ilia*,
172 and particularly the phenotype *Apatura ilia f. clytie*, the actual specimen differs distinctly in
173 the number of eyespots (Fig. 1, 3). Clearly some artistic licence has been taken here, possibly
174 to create the illusion of the eyes following round the viewer.

175 Most likely it was the gem-like purple colouration that singled out *Apatura* for
176 inclusion in Ancient art, adorned as they are with a colouration resembling that of the
177 amethyst. For according to Pliny, it is the amethyst that displays the best purple of all [17]¹.
178 Apparently, the Ancients, in their search for the best purple dyestuff, were looking for a gem-
179 like lustre ‘the colour of clotted blood, dark by reflected, and brilliant by transmitted light
180 [18]². However, not even purple of Tyre, the most precious of Ancient dye, which is based on
181 chemical dyes, equals the iridescent lustre displayed by the Lesser Purple Emperor. Only
182 amethyst comes close, owing to its violet colour created by impurities of iron suspended in an
183 otherwise transparent quartz crystal nanostructure [19].

184 In the Pompeiian floor mosaic, *Apatura*’s gem-like quality was captured not via
185 brushstrokes of purple dye, but via the use of small cubes, some of which made of coloured
186 glass; the latter were beginning to be manufactured at the time in order to mimic precious
187 stone and iridescence alike [20]. To suggest the wings’ iridescent colour-play, tesserae, small
188 tiles usually formed in the shape of a cube, were selected that gradually transitioned from a
189 light orange to a deep ruby and dark purple. Although, to our knowledge, no material analysis
190 has been conducted on this particular mosaic, archeometric investigations conducted on
191 comparable Pompeiian mosaics suggest that the opaque oranges and reds might perhaps be
192 due to cuprite (copper) aggregates dispersed in a lead-rich matrix and that the presence of
193 manganese in a soda-lime-silica glass matrix creates the more translucent deep purples [21].
194 At the time, glass manufacture underwent rapid innovation and growth, enabling and
195 triggering a new emphasis on clear and translucent coloured varieties, the latter affording a
196 much higher degree of gem-like depth and lustre [22].


¹ Following Classical precedence, Bede characterizes the purple amethyst as emblematic of Heaven. This heavenly connotation of purple passed during the Middle Ages increasingly to blue, especially in its precious form of lapis lazuli, although the purple cast of this latter was prized as late as the fourteenth century; see Ref. 16, p. 73.

² Pliny, Natural History, IX, xxxvi, 126, in Ref. 9, p. 222.

197 These early developments in glass making in turn kick-started a century-long quest by
 198 the Romans to imitate the jewel-like quality of iridescence, as is evidenced by the famous
 199 Lycurgus Cup of the 4th Century AD. Arguably the pinnacle of Roman glass-technology, the
 200 cup is dichroic. In direct light it resembles jade, but in transmitted light it turns to a translucent
 201 blood-red ruby colour. Actually, unbeknown to the Romans themselves, they were
 202 nanotechnology pioneers, because colloidal silver-gold alloy nano-particles were generated
 203 via heat-treating a suspension of minute amounts of gold and silver in a soda-lime-silica glass
 204 matrix coloured with manganese [23].

205 Butterflies have been mostly absent from high art during the Middle Ages, but made a
 206 temporary return to prominence in the 17th century in the context of the Vanitas still-life
 207 genre, a thoroughly Baroque take on the Roman *momento mori*. In 1618, Marchello
 208 Provenzale (1575-1639) used small glass stones in an attempt to mimic iridescence [24].
 209 Resembling green bottled glass, these particular stones emitted green ‘flames’ owing to an
 210 additional distinguishing feature: they were faceted like diamonds. In these ‘structurally
 211 coloured’ tesserae, it is the stone’s structure that causes a beam-like reflection, with pigments
 212 playing a filtering role.

213

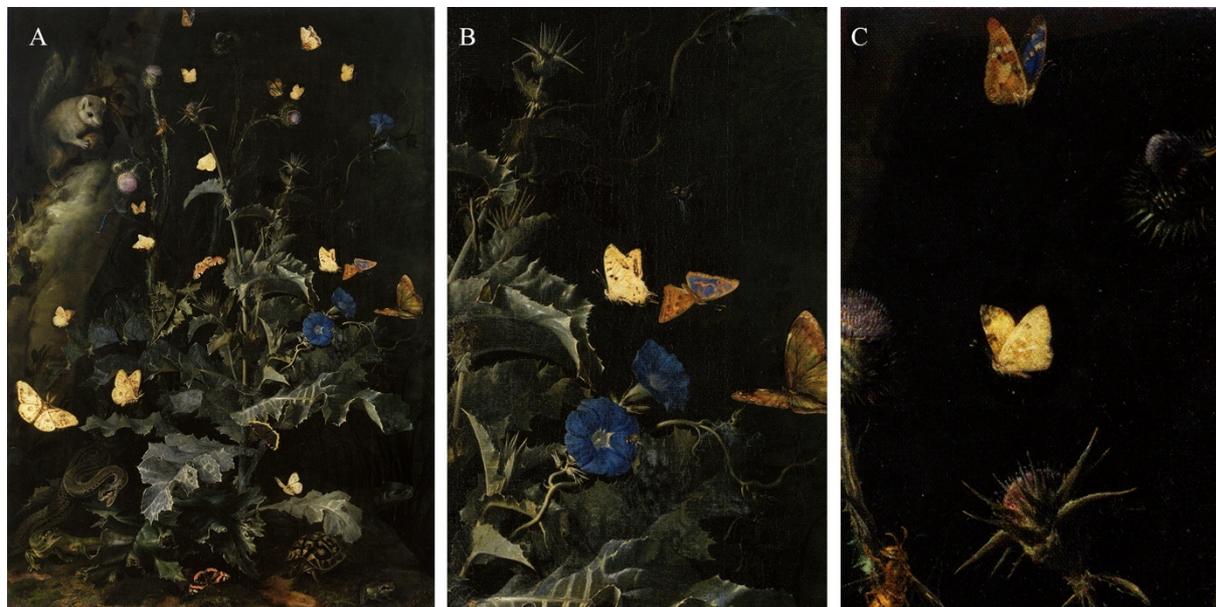

214


215

216 Fig. 4. Painting featuring *A. ilia*. Otto Marseus van Schrieck, ‘The Large Thistle’, c.1670,
 217 canvas, 132.6 x 93.5cm , Munich, Alte Pinakothek, Inv.no. 1966 **A** The complete canvas. **B**
 218 Detail one. **C** Detail two.

219

220 The Amsterdam painter Otto Marseus van Schrieck (c. 1620-1678) included *Apatura*
 221 *ilia* and many other butterflies in his ‘forest floor’ still-lifes (Fig. 4). In particular the arrival of

222 the microscope, a novel tool used by Marseus van Schrieck to conduct animal and plant
 223 studies in preparation for his paintings, does echo the era's newfound fascination with the
 224 infinitesimal [25]. In fact, when depicting butterflies, he pressed butterfly wings into the wet
 225 paint, embedding their scales into the canvas so that the insect's natural iridescence became
 226 part of the work (Carroll, 2017; [https://www.nybooks.com/daily/2017/11/15/marseus-in-the-](https://www.nybooks.com/daily/2017/11/15/marseus-in-the-land-of-snakes/)
 227 [land-of-snakes/](https://www.nybooks.com/daily/2017/11/15/marseus-in-the-land-of-snakes/)). In the absence of suitable paints, butterfly iridescence was reproduced by
 228 using actual iridescent butterfly wings.
 229

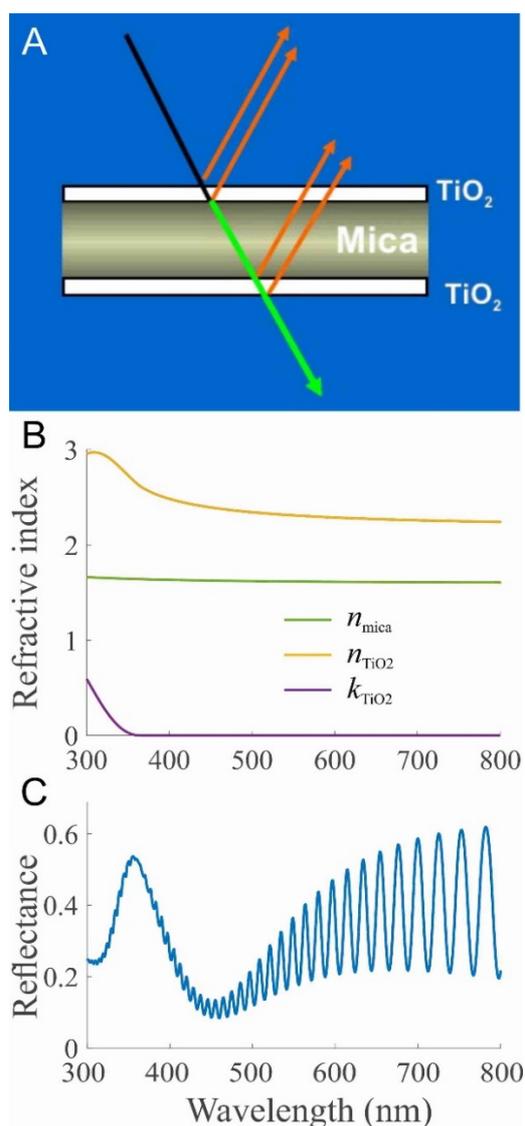

230
 231
 232 Fig. 5. Modelling the reflectance of a mica-flake. **A** Schematic flake of mica with on both
 233 sides a TiO₂ thin film. **B** Real parts of the refractive indices, n , of mica and TiO₂, and the
 234 imaginary part, k , of TiO₂ as a function of wavelength (from
 235 [https://www.filmetrics.com/refractive-index-database/TiO2+-+Amorphous/Titanium-](https://www.filmetrics.com/refractive-index-database/TiO2+-+Amorphous/Titanium-Dioxide)
 236 [Dioxide](https://www.filmetrics.com/refractive-index-database/TiO2+-+Amorphous/Titanium-Dioxide)). **C** Reflectance spectrum of a mica flake with variable thickness between 5.9 and 6.0
 237 μm , with on both sides 95 nm thick TiO₂ thin films in air.
 238


239 **Mimicking *Apatura ilia*'s iridescence**

240 Adopting a biomimetic approach, the scientific data on *A. ilia*'s colour mechanisms presented
241 above was drawn on to arrive at vital clues on how to best reproduce the butterfly in painting.
242 The various attempts and procedures leading to this result are described below. To faithfully
243 reproduce the colour of *A. ilia*, the most suitable multilayer pigments currently available were
244 investigated. We hereby considered that nature's metallic-looking reflectors are non-metallic,
245 i.e. they consist of dielectric materials that are often colour-less and transparent. Hence, while
246 special effect pigments do exist that are based on metal (i.e. metallic effect pigments), we
247 instead focused our search for suitable materials on pearlescent technology and the respective
248 pigment lines. The multilayer reflectors present in butterfly wing scales consist of alternating
249 thin plates of chitin and air, which have refractive indices of about 1.6 and 1.0, respectively
250 [26]. To achieve a high reflectance of a wing scale then requires several layers. The cover
251 scales of *A. ilia* therefore have 5-6 overlapping lamellae, meaning 10-12 layers [27] (some
252 morphos have even scales with up to >10 stacked lamellae [12]).

253 In effect pigments, however, materials with a very high refractive index are selected.
254 For instance, the (real part of the) refractive index of TiO₂ is 2.3-2.5 in the visible wavelength
255 range, which makes it a highly powerful candidate for strongly reflecting materials, because a
256 high reflectance can already be realized with a few layers (Fig. 5). As an example, a mica-
257 flake (refractive index ~1.6) with thickness varying between 5.9 and 6.0 μm and on both sides
258 a 95 nm thick TiO₂ thin film creates a high reflectance peaking at ~400 nm; the high
259 frequency modulation is due to the total thickness of the flake of ~6 μm (Fig. 5).

260 To mimic the violet colouration of *A. ilia*, we investigated a number of violet
261 interference 'pigments', each based on a different substrate, and each belonging to a different
262 effect pigment family. Firstly, Pyrisma® Color Space Violet is an effect pigment based on a
263 natural mica flake coated with a specially developed layer of titanium dioxide, together with a
264 narrow particle size distribution (5-35 μm). Xirallic® Amethyst Dream, on the other hand,
265 belongs to a transparent 'High Chroma Crystal Effect Pigment' family based on aluminum
266 oxide flakes (alumina flakes), produced using a crystal growth process. The extraordinary
267 colour purity and transparency of the resulting pigments obtained by coating Al₂O₃-flakes
268 with high-refractive metal oxides (in this instance with titanium dioxide) can be attributed to
269 the synthesis procedure yielding single-crystalline thin flakes. The pigment, possessing a
270 narrow particle size distribution of about 5 to 30 μm as well as a high aspect ratio, displays an
271 intensive glitter effect - the so-called crystal effect or sparkle. Previously, the resulting sparkle
272 effect could not be achieved with small-sized effect pigments. In contrast, Firemist® Violet,

273 while also a sparkle pigment, relies on a smooth surface and larger particle-size distribution
 274 (5-300 μm) to create a brilliant, star-like glitter. Based on TiO_2 -coated borosilicate glass-
 275 flakes, Firemist[®] Violet combines both unique colour purity with high transparency, intensive
 276 light reflection and noticeable narrowband colour travel.
 277

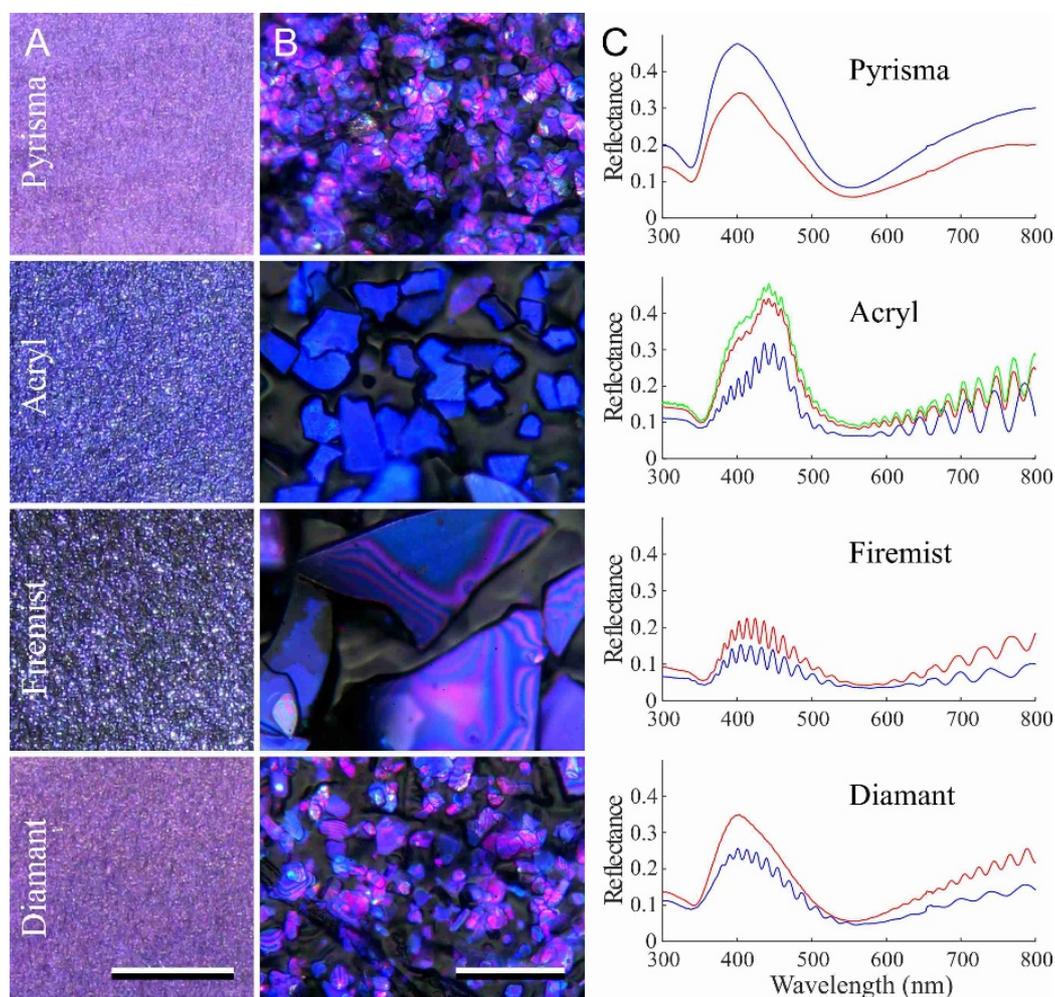


278
 279

280 Fig. 6. Photographs and reflectance spectra of four effect pigments, i.e. Pyrisma (Color Space
 281 Violet), Acryl (Helicone Sapphire), Firemist (Violet), and Diamant (Xirallic Amethyst
 282 Dream). **A** The pigments on black paper. **B** Micrographs showing the flaky composition of the
 283 effect paints. **C** Reflectance spectra measured with a bifurcated reflection probe from various
 284 areas of **A**. Scale bars: **A** 10 mm, **B** 0.1 mm.
 285

286 In addition, we investigated another type of interference Acryl-glass pigment, LCP
 287 Helicone[®] Sapphire, which incidentally belongs to the first ever effect pigment family
 288 (introduced in the mid 1990's) to generate distinct angle-dependent colour effects. A subtle
 289 point to be emphasised here is that the Helicone[®] effect pigments are not classical thin-film
 290 multilayer reflectors, but a subtype based on liquid-crystal polymers (LCP), known as

291 cholesteric effect pigments. Unlike thin-film multilayers, LCP's do not consist of alternating
 292 layers of two or more isotropic materials, but instead the helicoidal orientation of a single type
 293 of a birefringent unit provides the change in refractive index necessary for reflectivity [3]. In
 294 other words, while cholesteric pigments also take the form of a transparent, colourless layered
 295 platelet, here all layers are composed of the same material, namely a highly cross-linked,
 296 liquid crystalline organic polymer with a helical superstructure, the pitch of which determines
 297 the reflected colour.

298 We selected four effect pigments that produced colourations resembling that of our
 299 butterfly, Pyrisma (Color Space Violet), Acryl (Helicone Sapphire), Firemist (Violet), and
 300 Diamant (Xirallic Amethyst Dream), and prepared paint samples on black paper (Fig. 6A).
 301 Micrographs show that the flake size considerably varies between the different materials (Fig.
 302 6B). The reflectance spectra measured from the different samples compared with those from
 303 the butterflies confirm that the iridescent colouration of *A. ilia* can indeed be matched (Fig.
 304 6C).

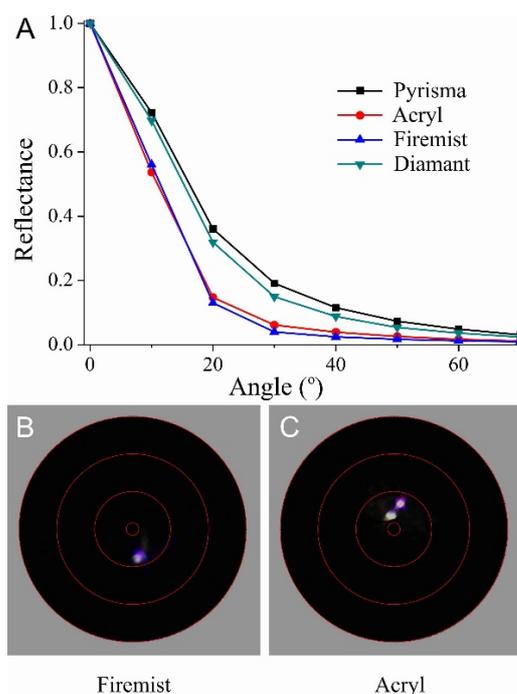


305
 306
 307
 308
 309
 310
 311

307 Fig. 7. Angle dependence of the reflectance of the effect pigments and imaging scatterometry.
 308 **A** Reflectance as a function of angle of reflection of normally illuminated paint samples. **B**
 309 Scatterograms of Firemist- and Acryl/Helicone-samples created by local illumination with a
 310 narrow aperture white light beam.

312 To quantify the spatial properties of the effect pigments, we applied angle-dependent
 313 reflectance measurements. Normal illumination with a narrow-aperture light beam and then
 314 measuring the reflectance at the sample's peak wavelength as a function of the angle of

315 reflection yielded reflected light distributions with full width at half maximum between 20°
 316 and 30°, demonstrating that the reflections are very directionally indeed (Fig. 7A). Actually,
 317 imaging scatterometry showed that very local illuminations with a narrow-aperture beam
 318 create almost perfect specular reflections (Fig. 7B). However, the directions appeared to
 319 depend on the location, clearly being the consequence of the variability in the planar
 320 orientation of the flakes (Fig. 6B), as is also illustrated by Fig. 7C, where two flakes were hit
 321 by the light beam. The not fully specular reflections of the pigment samples are clearly the
 322 result of the not fully planar orientation of the flakes in the samples.

323

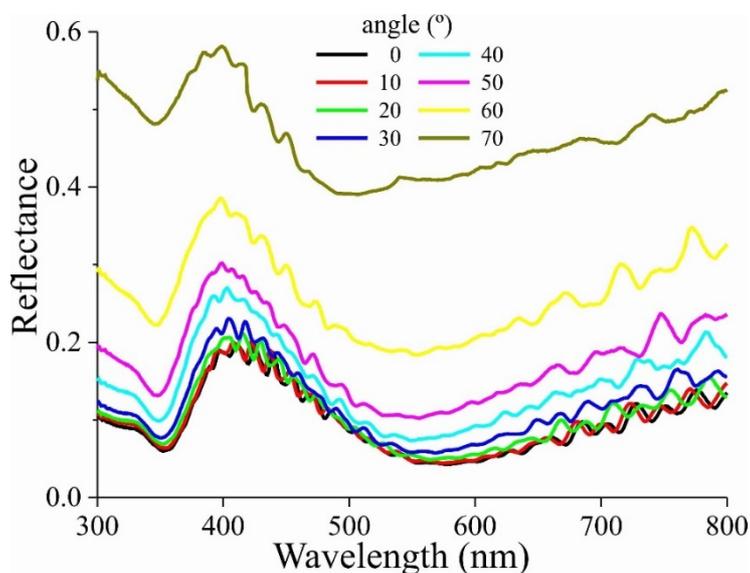

324

325

326 Fig. 8. Angle-dependent reflectance of Firemist at black paper measured with two fibers
 327 positioned mirror-wise, i.e. one fiber delivered the light and the other fiber was in the mirror
 328 position.

329

330 Figure 8 presents reflectance spectra as a function of angle of light incidence for the
 331 Firemist sample. We measured the reflectance in the mirror angle for both TE-(transverse
 332 electric) and TM-(transverse magnetic) polarised light, which showed the classical behaviour
 333 that the reflectance of TE-polarised light steadily increases with the angle of incidence, while
 334 the reflectance of TM-polarised light stays low over a large spatial angle. As the human eye is
 335 incapable of polarisation vision, we averaged the TE- and TM-spectra (Fig. 8). As expected
 336 from classical multilayer theory, the spectra shift to the shorter wavelengths with increasing
 337 angle of light incidence. Because the diameter of the detection area was ~0.5 cm, the signal
 338 was also the average of numerous flakes. The spectra nevertheless feature a clear ripple,
 339 indicating that the dimensions and orientations of the flakes are still rather uniform.

340

341 **The role of reflecting structures and absorbing pigments in *A. ilia***

342 An important point to reiterate here is that in many butterflies both structures and pigments
343 contribute to the visual signal. This is the case in the male *A. ilia*, as mentioned above. The
344 scale coat on the butterfly's dorsal forewings consists of pigmentary ground scales
345 overlaid with structurally-coloured cover scales. All cover scales strongly reflect UV-blue
346 light, and the ground scales will partly reflect and backscatter the incident light, depending on
347 their melanin concentration (Fig. 1). The light flux reflected by the wing hence is the sum of
348 the reflections of the cover and ground scales. In the eye spots, where the ground scales are
349 strongly pigmented (and therefore black), normal illumination causes a deep-blue colour due
350 to only the cover scale reflections. However, in the wing areas that are distinctly white with
351 oblique illumination, the ground scales are unpigmented, so that the reflection with normal
352 illumination consists of reflected light emerging from both the cover and ground scales,
353 resulting in a very faint blue-white. With intermediate pigmentation of the ground scales, the
354 reflections are blue-orange or blue-brown, overall resulting in a distinctly-patterned wing-
355 display (Fig. 1).


356 Similar cases have been studied in other butterflies. Most morphos feature more or less
357 homogeneous blue-reflecting wings, due to a backing of melanin below the strongly reflecting
358 scale ridges, but *Morpho cypris* features a striped wing pattern, due to selective areas with
359 strongly pigmented vs unpigmented scales [28]. In the blue wing areas of nymphaline
360 butterflies, the lower lamina of the cover scales acts as a blue-reflecting thin film and the
361 ground scales are black due to a high melanin content. Yet, the same cover scales when
362 backed by unpigmented ground scales result in whitish wing areas [29].

363

364 **The final artwork**

365 In order to accurately replicate *A. ilia* in painting, we need to realise that the pigmentary
366 colouration of a material always exists due to the medium's inhomogeneities that reflect and
367 scatter the incident light, which is in turn selectively absorbed by the embedded pigment, so
368 that only the non-absorbed, backscattered light is observed. Structural colouration, however,
369 exists only when the material contains inhomogeneities with nanoscale dimensions, which
370 then reflect light in a specific wavelength range due to interference. Hence for our replication
371 two types of materials had to be combined: 1) paints based on chemical pigments, and 2)
372 structurally-coloured materials.

373 To fully mimic *A. ilia*'s dynamic on-off colour display, firstly, a detailed
 374 underpainting was created. Traditional pigment-based paints were used to replicate in
 375 meticulous detail the entire wing pattern, which, for example, includes eyespots and white
 376 bands. Subsequently this pigmentary base was then overpainted with various layers of UV-
 377 blue reflecting interference paint. Both LCP Helicone[®] Sapphire and Firemist[®] Violet flakes
 378 were incorporated into the final paint that was specially formulated for this particular purpose.
 379 In the process, areas of differing pigmentary background colour (ranging from white to orange
 380 and brown to black) were overlaid with the same blue-violet interference flake mix.

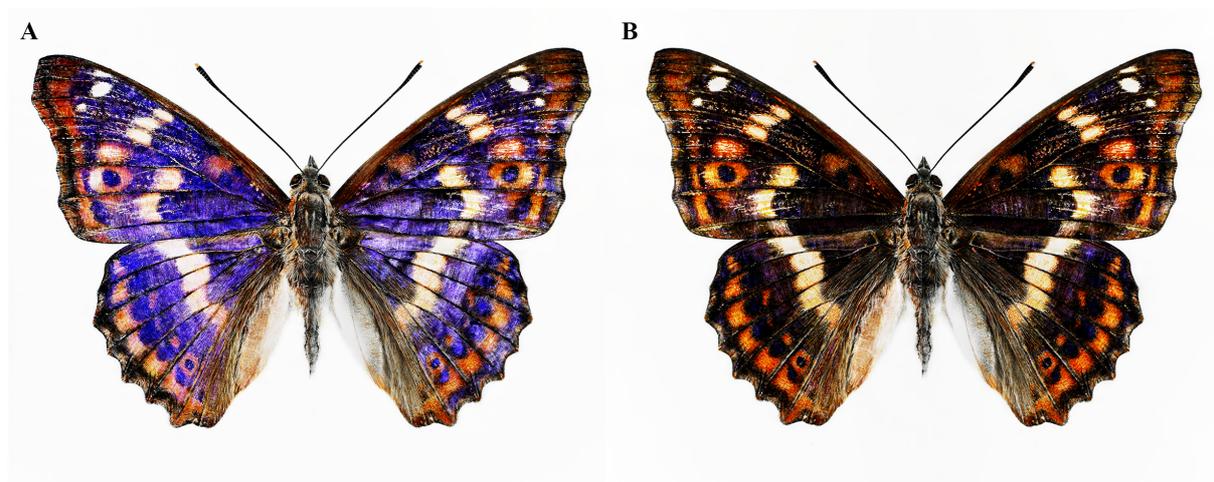

381
 382 Fig. 9. The final painting (160 x 185 cm), © F. Schenk. **A** About normal illumination. **B**
 383 Oblique illumination.
 384

385 The resulting optical effects indeed perfectly matched what can be observed in the
 386 actual *A. ilia* specimen (Fig. 9). For example, depending on the viewing angle, the centre of an
 387 eyespot appears either intensely blue (Fig. 9A) or turns into a pure black 'pupil' (Fig. 9B), due
 388 to the blue-reflection generated by the effect pigment flakes switching on and off to
 389 conceal/reveal the strongly absorbing black background below. In other areas with a brown
 390 pigmented ground, the reflection colour shifts further towards violet; and on orange further
 391 towards pink-red.

392 If one observes in the painting the white bands adorning *A. ilia*'s dorsal wings, the
 393 resulting effect is that the angle-dependent blue-violet reflection switches on and off to reveal
 394 a muted yellow-green underneath (Fig. 9A, B). The interference flakes' layered structure
 395 effectively reflects light in the blue-violet wavelength range, but light with longer
 396 wavelengths is transmitted and then reaches the white ground, which thus yields a yellow-
 397 green back scattering. Thus, both light components become visible. At face angle we see a
 398 blue-violet reflection and at oblique angle its complementary transmission colour – the

399 yellow-green. Evidently, the ultimate colour effect does much depend on what lies below the
400 reflector. Depending on the background's hue and tonal value, the same narrowband structure
401 can produce vivid pure metallic-like effects, and subtle two-colour opalescence.

402

403 **Conclusion**

404 To arrive at the final artwork, in the absence of ready-made paints and rules of application, the
405 flakes selected had to initially be turned into paint suitable for fine art application. Only once
406 an appropriate binder and formula had been found was it possible to consider potential artistic
407 strategies, eventually pinpointing "old-masterly" techniques as a possible way forward.
408 Incidentally, so-called "traditional" methods (e.g. involving a tonal "under-painting" overlaid
409 with semi-transparent glazes) are most in keeping with the complex layering present in *A. ilia*,
410 where the overall colour pattern displayed is due to differing hues and tones of melanin
411 overlaid with the same structural colour. Notably, as colour mixing is at work here, the
412 pigmentary base is crucial in determining the overall colour effect.

413 With this in mind, as a first step, a detailed pigmented "under-painting" of the
414 butterfly's dorsal side was created, also featuring a textured surface. Finally, drawing on our
415 optical measurements, this was overlaid with iridescent paint based on the most suitable effect
416 pigment mix selected to fully mimic *A. ilia*'s colouration. Satisfactorily, the final painting
417 (Fig. 9), just like the model (Fig. 1), changes with every minute variation of the angle of light
418 incidence and viewing. This introduces a fully novel element of change, movement and
419 transience into the medium of painting, which traditionally is inert and static.

420 In conclusion, whereas artists have been able to reproduce pigmentary colours in
421 paintings since human's earliest memory, until now this has not been the case for structural
422 colours. The example of *A. ilia* demonstrates that, with the help of latest iridescent colour
423 technology, biological structural colours can finally be simulated in painting. Effect pigments,
424 based on light interference, when used as paint are beginning to open up a completely new era
425 of artistic activity. Thus, for the first time, an important segment of natural reflection can be
426 recreated in art, potentially leading to novel artistic expressions and experiences.

427 It is hoped that this overview of pearlescent effect pigments, together with the
428 associated optical principles introduced, will provide artists with the intimate specialist
429 knowledge essential to take full advantage of the manifold creative opportunities the
430 technology has to offer, encouraging them to extend both their palette and repertoire. By
431 harking back to the exemplar of the Renaissance painter as chemist, material scientist and, in
432 this case, physicist, future generations of painters will inevitably develop diverse and

433 imaginative ways in which to creatively employ this emerging technology. Basic ground rules
 434 for artistic application derived from biomimetics will, no doubt, further aid this process, thus
 435 helping to overcome the major challenges interference flakes continue to present to the
 436 contemporary painter. For, given time and continued research, iridescent colour technology
 437 has the potential to revolutionise fine art painting.

438

439 **Acknowledgements**

440 This study was financially supported by AFOSR/EOARD grant FA9550-15-1-0068 (to DGS).

441

442 **Conflicts of interest**

443 There are no conflicts to declare.

444

445 **References**

- 446 [1] A. Krüger, *Perlen*. Bibl. d. Unterhaltung und des Wissens, Stuttgart: Union Deutsche
 447 Verlagsgesellschaft, 1919.
- 448 [2] F. J. Maile, G. Pfaff & P. Reynders, Effect pigments—past, present and future. *Prog. Org.*
 449 *Coat.* 2005, **54**, 150-163.
- 450 [3] G. Pfaff, *Special effect pigments: technical basics and applications*. Vincentz Network
 451 GmbH & Co KG, 2008.
- 452 [4] H. Küppers, *Color; origin, systems, uses*. Van Nostrand Reinhold, 1972.
- 453 [5] F. Schenk, Nature's fluctuating colour captured on canvas? *Int. J. Des. Nat. Ecodyn.*, 2009,
 454 **4**, 274-284.
- 455 [6] R. Lemberg, Liquid crystals: a new material for artists. *Leonardo* (MIT) **2**, 1969, 45-50.
- 456 [7] Y. Charnay, A new medium for expression: painting with liquid crystals. *Leonardo* (MIT),
 457 1982, **15**, 219-221.
- 458 [8] F. Schenk, A. Parker, Iridescent color: from nature to the painter's palette. *Leonardo*
 459 (MIT), **44**, 2011, 108-115.
- 460 [9] P. Ball, Nature's fantastical palette. *Sci. Am.*, 2012, **306**, 74-79.
- 461 [10] F. Schenk, B. D. Wilts & D. G. Stavenga, The Japanese jewel beetle: a painter's
 462 challenge. *Bioinspir. Biomim.*, 045002, 2013, **8**.
- 463 [11] S. Kinoshita, S. Yoshioka & K. Kawagoe, Mechanisms of structural colour in the
 464 *Morpho* butterfly: cooperation of regularity and irregularity in an iridescent scale.
 465 *Proc. R. Soc. Lond. B*, 2002, **269**, 1417-1421.
- 466 [12] M. A. Giraldo, S. Yoshioka, C. Liu, & D. G. Stavenga, Coloration mechanisms and
 467 phylogeny of *Morpho* butterflies. *J. Exp. Biol.*, 2016, **219**, 3936-3944.
- 468 [13] Z. Vértésy, K. Kertész, Zs. Bálint, Gy. Molnár, M. Erös, L. P. Biró, SEM and TEM
 469 investigations in the scales of the European nymphalid butterfly *Apatura ilia* dark and
 470 light phenotypes. *BioPhot Meeting Abstract Book: Reserach Institute for Technical*
 471 *Physics and Materials Science, Budapest*, 2007.
- 472 [14] D. Pantelić., S. Čurčić, S. Savić-Šević, A. Korać, A. Kovačević, B. Čurčić, et al. High
 473 angular and spectral selectivity of purple emperor (*Lepidoptera: Apatura iris* and *A.*
 474 *ilia*) butterfly wings. *Opt. Express*, 2011, **19**, 5817-5826.
- 475 [15] D. G. Stavenga, H.L. Leertouwer, P. Pirih & M. F. Wehling, Imaging scatterometry of
 476 butterfly wing scales. *Opt. Express*, 2009, **17**, 193-202.

- 477 [16] P. Marren, *Rainbow Dust: Three Centuries of Butterfly Delight*. London:
478 Penguin/Vintage, 2015.
- 479 [17] J. Gage, *Color and meaning: Art, science, and symbolism*. London: Thames and Hudson
480 1999.
- 481 [18] J. Gage, *La couleur dans l'art*. London: Thames and Hudson, 2009.
- 482 [19] N. N. Greenwood, A. Earnshaw, *Chemistry of the Elements*, Butterworth-Heinemann,
483 1997.
- 484 [20] A. Allen, *Roman Glass in Britain*. Buckinghamshire: Shire Publications, 1991.
- 485 [21] R. Arletti, S. Quartieri & G. Vezzalini, Glass mosaic tesserae from Pompeii: an
486 archeometrical investigation. *Periodico di Mineralogia*, 2006, **75**, 25-38.
- 487 [22] D. F. Grose, Early imperial Roman cast glass: the translucent coloured and colourless
488 fine wares. In: M. Newby, K. Painter editors, *Roman Glass: Two Centuries of Art and*
489 *Invention*, London: Society of Antiquaries of London, 1991, 1-18.
- 490 [23] I. Freestone, N. Meeks, M. Sax & C. Higgitt, The Lycurgus cup—a roman
491 nanotechnology. *Gold Bull.*, 2007, **40**, 270-277.
- 492 [24] A. Parker, *Seven deadly colours: the genius of nature's palette and how it eluded Darwin*.
493 Gardners Books, 2005.
- 494 [25] G. Seelig, *Medusa's Menagerie: Otto Marseus van Schrieck and the Scholars*. Hirmer
495 Publishers, 2017.
- 496 [26] H. L. Leertouwer, B. D. Wilts & D.G. Stavenga, Refractive index and dispersion of
497 butterfly scale chitin and bird feather keratin measured by interference microscopy.
498 *Opt. Express*, 2011, **19**, 24061-24066.
- 499 [27] S. B. Ćurčić, D. V. Pantelić, B. P. M. Ćurčić, S. N. Savić-Šević, S. E. Makarov, V. B.
500 Lačković, et al., Micro- and nanostructures of iridescent wing scales in purple emperor
501 butterflies (Lepidoptera: *Apatura ilia* and *A. iris*). *Microsc. Res. Tech.*, 2012, **75**, 968-
502 976.
- 503 [28] S. Yoshioka, S. Kinoshita, Structural or pigmentary? Origin of the distinctive white stripe
504 on the blue wing of a *Morpho* butterfly. *Proc. R. Soc. B*, 2006, **273**, 129-134.
- 505 [29] D. G. Stavenga, H. L. Leertouwer & B. D. Wilts, Coloration principles of nymphaline
506 butterflies - thin films, melanin, ommochromes and wing scale stacking. *J. Exp. Biol.*,
507 2014, **217**, 2171-2180.