

Cite this: *RSC Adv.*, 2019, 9, 21075

Preparation of a poly(acrylic acid) based hydrogel with fast adsorption rate and high adsorption capacity for the removal of cationic dyes†

Zhenyu Yuan,^a Jie Wang,^a ^{*,a} Yiming Wang,^b Qian Liu,^b Yujie Zhong,^a Yu Wang,^a Li Li,^a ^a Stephen F. Lincoln^c and Xuhong Guo ^{ad}

A biocompatible Dex-MA/PAA hydrogel was prepared through copolymerization of glycidyl methacrylate substituted dextran (Dex-MA) with acrylic acid (AA), which was applied as the adsorbent to remove cationic dyes from aqueous solutions. Dex-MA/PAA hydrogel presented a fast adsorption rate and the removal efficiency of Methylene Blue (MB) and Crystal Violet (CV) reached 93.9% and 86.4%, respectively within one minute at an initial concentration of 50 mg L⁻¹. The adsorption equilibrium data fitted the Sips isotherm model well with high adsorption capacities of 1994 mg g⁻¹ for MB and 2390 mg g⁻¹ for CV. Besides, dye adsorption occurred efficiently over the pH range 3–10 and the temperature range 20–60 °C. Moreover, the removal efficiencies for MB and CV were still >95% even after five adsorption/desorption cycles which indicates the robust nature of the Dex-MA/PAA hydrogel and its potential as an eco-friendly adsorbent for water treatment.

Received 25th April 2019

Accepted 1st July 2019

DOI: 10.1039/c9ra03077h

rsc.li/rsc-advances

1. Introduction

The growing use of dyes in cosmetics, papermaking, medicine and food has caused serious environmental pollution, especially in water sources and aquatic ecosystems.^{1,2} Most of these dyes are aromatic compounds which exhibit varying degrees of toxicity and are not readily degraded by light, heat, oxidizing agents, and biological agents.³ Consequently, it is necessary to remove these dyes from the polluted water generated during their usage.

A series of physicochemical techniques, such as adsorption,⁴ photocatalytic degradation,⁵ electro-kinetic coagulation,⁶ precipitation,⁷ membrane filtration,⁸ and flocculation,⁹ have been developed for the removal of dyes from waste water. Of these methods, adsorption emerges as a superior industrial water treatment method due to the simplicity of design, low cost, stability and reusability of the adsorbents.^{10,11} In some cases the adsorbent is biodegradable.¹²

In designing dye adsorbents, we are particularly interested in hydrogels which are three-dimensional hydrophilic polymer

networks which absorb large amounts of water.¹³ These characteristics, in combination with the substitution of appropriate functional groups to give the required adsorbent properties, render hydrogels versatile adsorbents which earlier studies have shown to be readily regenerated for reuse. Thus, substituent hydroxyl and carboxylate groups can selectively interact with cationic dyes or metal ions at appropriate pH values.¹⁴

Natural polysaccharides are attractive materials for adsorbent hydrogel construction for water purification because of their ready availability and biodegradability. Chitosan,¹⁵ cellulose,¹⁶ starch¹⁷ and guar gum¹⁸ have been widely applied for construction of adsorbents and shows good adsorption properties, such as those combined with amino, carboxyl, cyclodextrin and other inorganic composition. Among various natural polysaccharides, dextran is an important starting material for new functional materials with promising properties.¹⁹ Due to its common solubility, biocompatibility, and biodegradability, dextran is already successfully applied in the medical and biomedical field,^{20–22} however, the applications in adsorbents were seldom reported. Here, we synthesized a hydrogel adsorbent based on dextran. The numerous hydroxyl groups of dextran render it amenable to substitution with other groups according to the requirements of the substituted product. Accordingly, we substituted dextran through reaction with glycidyl methacrylate (GMA) to produce the double bond modified dextran (Dex-MA), which has been used for building hydrogel or micro-gels and recently applied in the area of hemostatic agent and micro carriers.²³ Then Dex-MA was copolymerized with acrylic acid (AA) to give the Dex-MA/PAA hydrogel. The carboxylic group can interact with various

^aState Key Laboratory of Chemical Engineering, East China University of Science and Technology, 200237 Shanghai, P. R. China. E-mail: jiewang2010@ecust.edu.cn

^bDepartment of Chemical Engineering, Delft University of Technology, 2629 HZ Delft, The Netherlands

^cSchool of Physical Sciences, University of Adelaide, Adelaide, SA 5005, Australia

^dEngineering Research Center of Materials Chemical Engineering of Xinjiang Bingtuan, Shihezi University, 832000 Xinjiang, P. R. China

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c9ra03077h

This journal is © The Royal Society of Chemistry 2019

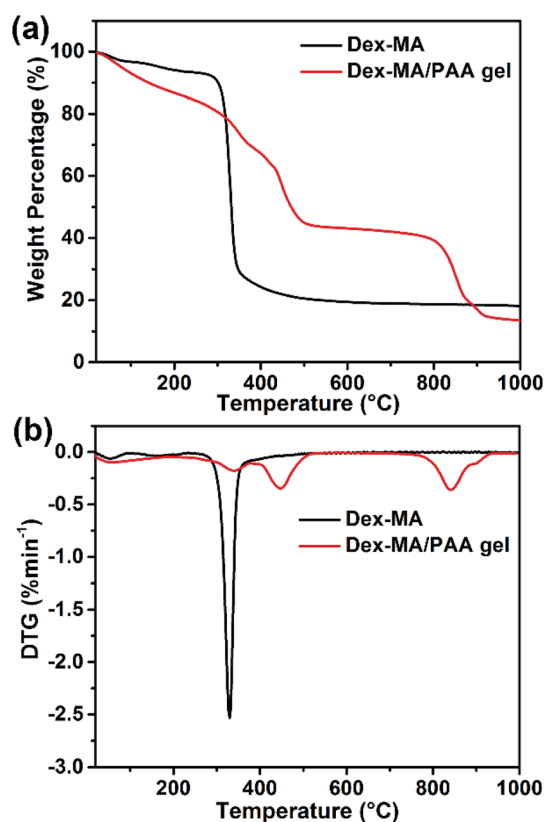



Fig. 2 FT-IR spectra of dextran, Dex-MA and Dex-MA/PAA hydrogel.

the Dex-MA/PAA hydrogel adsorbent was determined to be 6.6, as shown in Fig. S2.† All of the Dex-MA/PAA carboxyl groups were protonated at $\text{pH} < 6.6$ but become increasingly deprotonated at $\text{pH} > 6.6$ such that the adsorbent surface is increasingly negatively charged as required for the adsorption of cationic dyes.^{31,32}

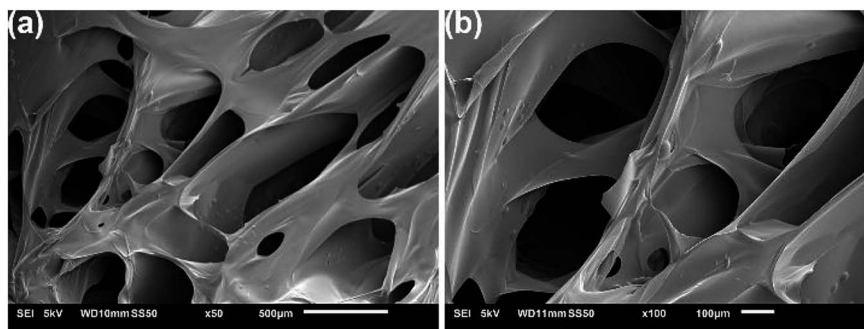


Fig. 4 SEM images of the fracture surface of the freeze-dried Dex-MA/PAA hydrogel at two magnifications.

The variation of the dye removal efficiency of the Dex-MA/PAA hydrogel adsorbent at $\text{pH}_{\text{initial}}$ ranging from 2 to 10 for MB and CV is shown in Fig. 5a. At $\text{pH}_{\text{initial}}$ 2.0 the removal efficiency for MB and CV were 47.8% and 56.9%, respectively. When the $\text{pH}_{\text{initial}}$ slightly increased to 3.0, the removal efficiency for both dyes were higher than 96%. However, further increases in $\text{pH}_{\text{initial}}$ to 10.0 produced no additional increase in the removal efficiency for the dyes. Overall, these data show that the Dex-MA/PAA hydrogel adsorbs MB and CV particularly

effectively over the $\text{pH}_{\text{initial}}$ range of 3–10 due to its strong buffer ability.

This dye adsorption pattern coincided with changes from $\text{pH}_{\text{initial}}$ to pH_{final} , after adding the Dex-MA/PAA hydrogel to the dye solutions as a consequence of variations in the extent of protonation of the carboxylate groups. Thus, there was a larger increase of pH_{final} from $\text{pH}_{\text{initial}} = 3$ to 4, lesser increases from $\text{pH}_{\text{initial}} = 4$ to 10 (Fig. 5b). These changes are a consequence of buffering by the Dex-MA/PAA hydrogel centered on $\text{pH}_{\text{PZC}} = 6.6$. The adsorption of MB and CV in solutions with $\text{pH}_{\text{final}} < \text{pH}_{\text{PZC}}$ in particular indicates that both dyes strongly compete with protons for electrostatic interaction with Dex-MA/PAA carboxylate groups.

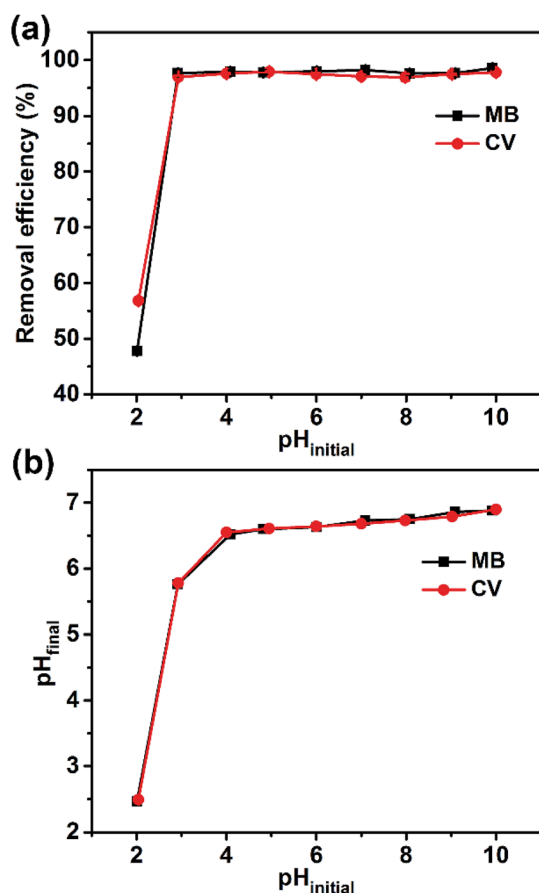


Fig. 5 (a) Effect of initial solution pH on the removal efficiency by the Dex-MA/PAA hydrogel and (b) final pH changes after adding the Dex-MA/PAA hydrogel. Dex-MA/PAA hydrogel dose: 1 g L⁻¹, dye concentration: 50 mg L⁻¹, contact time: 3 h.

3.3 Effect of NaCl concentration on dye adsorption

The differing effects of NaCl concentration on the absorption of Dex-MA/PAA hydrogel for MB and CV are shown Fig. 6. The removal efficiency of MB changed from >97% to 4.3% when sodium chloride concentration was increased from 0 to 400 mM, and that of CV changed from >97% to 43.9%. This is consistent with Na⁺ competitively interacting with the Dex-MA/PAA carboxylate groups to produce a screening effect which decreases cationic dye adsorption as found in other studies.^{33,34}

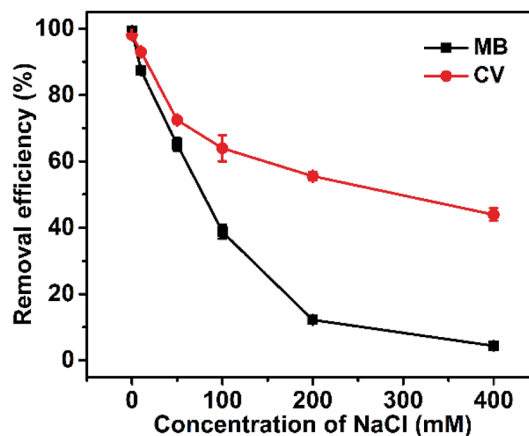


Fig. 6 Effect of NaCl concentration on removal efficiency of Dex-MA/PAA hydrogel (Dex-MA/PAA hydrogel dose: 1 g L^{-1} , dye concentration: 50 mg L^{-1} , contact time: 3 h, initial pH 8.0).

3.4 Effect of temperature on dye adsorption

The adsorption of the dyes onto the Dex-MA/PAA hydrogel decreased slightly with increase in temperature from 293 K to 333 K as shown by the decreases of 1.3% and 2.2% in the removal efficiency for MB and CD, respectively, in Fig. 7. A similarly small absorption decrease has been reported for MB adsorption on other adsorbents.¹⁵

The free energy change, enthalpy change and entropy change for dye adsorption, ΔG^0 , ΔH^0 and ΔS^0 , were determined through the following equations:

$$K_d = \frac{C_0 - C_e}{C_e} \quad (5)$$

$$\Delta G^0 = -RT \ln K_d \quad (6)$$

$$\Delta G^0 = \Delta H^0 - T\Delta S^0 \quad (7)$$

$$\ln(K_d) = \frac{\Delta S^0}{R} - \frac{\Delta H^0}{RT} \quad (8)$$

where K_d is the equilibrium constant, C_0 and C_e are the initial and equilibrium dye concentrations (mg L^{-1}), R is the gas constant and T is the temperature (K). Van't Hoff plots of $\ln K_d$ against $1/T$ shown as insets in Fig. 7 and the ΔH^0 and ΔS^0 were calculated from the slope ($-\Delta H^0/R$) and intercept ($\Delta S^0/R$). The

derived thermodynamic parameters appear in Table 1. For both dyes ΔG^0 becomes less negative with increase in temperature consistent with the corresponding decrease in removal efficiency and dye adsorption was a spontaneous process.^{4,27} The negative ΔH^0 for adsorption indicated that the dye adsorption process was exothermic, while the negative ΔS^0 were indicated the decreased randomness at the solid/liquid interface in the adsorption process.^{35,36}

Response surface methodology was also applied for optimization of dyes, and pH (A), salt concentration (B) and temperature (C) were selected as three factors. The results of variance analyses were shown in Table S3 and S4.† According to p value, the A, B, AB, B^2 were significant for removal efficiency of MB, and A, B, AB, A^2 , B^2 were significant for removal efficiency of CV, which were also confirmed by F value.

3.5 Adsorption kinetics

The adsorption kinetics were characterized by monitored the amount of dye adsorbed against time. Within the first minute the removal efficiencies of MB and CV have reached 93.9% and 86.4%, respectively (Fig. 8). Thereafter, the removal efficiency of MB and CV leveled off at $\sim 98\%$ within ~ 5 min and ~ 15 min, respectively, as is seen qualitatively for MB and CV solutions before and after adsorption by Dex-MA/PAA in Fig. S6.† This rapid adsorption process is ascribed to the large pore size of the hydrogel networks and their multiple carboxylate groups, indicating the potential usefulness of the Dex-MA/PAA hydrogel as an adsorbent in wastewater treatment.

Generally, the dye adsorption processes are considered to occur in three steps: (1) bulk diffusion of the dye from solution to the adsorbent surface; (2) intra-particle diffusion and electrostatic interactions between the dye and the adsorbent; and (3) the equilibrium state wherein the dye exchanges on and off adsorption sites.^{26,37} To determine the nature of the kinetics of adsorption, the experimental q_t data were fitted to a pseudo-first order (PFO),³⁸ a pseudo-second order (PSO),³⁹ and the Elovich kinetic model,^{40,41} and then to the intra-particle diffusion model (Fig. 9).^{28,42}

For the PFO kinetic model:

$$q_t = q_e(1 - e^{-k_1 t}) \quad (9)$$

For the PSO kinetic model:

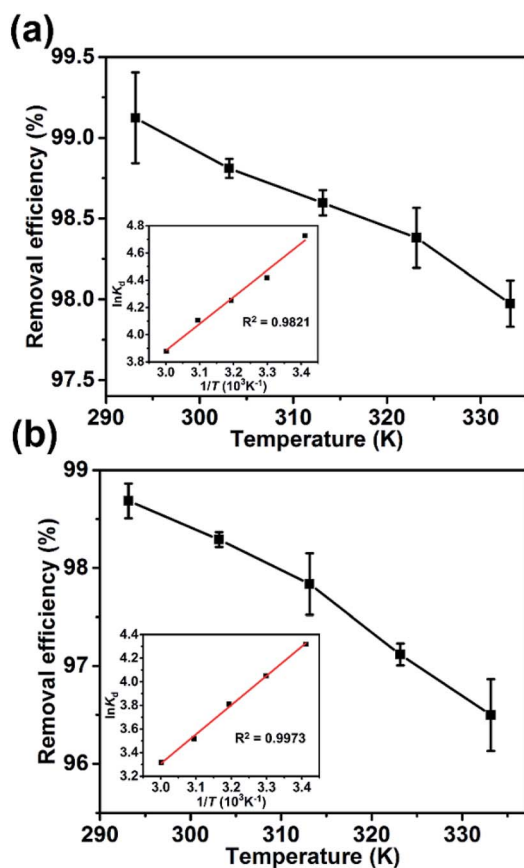


Fig. 7 The effect of temperature on the removal efficiency: (a) MB and (b) CV (inset: Van't Hoff plots for the adsorption of MB and CV on Dex-MA/PAA).

Table 1 Thermodynamics parameters for MB and CV adsorption on Dex-MA/PAA at different temperatures

Parameters	ΔG^0 (kJ mol^{-1}) of dyes	
T (K)	MB	CV
293	−11.52	−10.52
303	−11.14	−10.21
313	−11.07	−9.92
323	−11.03	−9.45
333	−10.74	−9.19
ΔH^0 (kJ mol^{-1})	−16.38	−20.61
ΔS^0 ($\text{J mol}^{-1} \text{K}^{-1}$)	−16.84	−34.34





Fig. 8 Effect of contact time, t , on the dye removal efficiency. Hydrogel adsorbent dose: 1 g L^{-1} , dye concentration: 50 mg L^{-1} , $\text{pH}_{\text{initial}}$ 8.0.

$$q_t = \frac{k_2 q_e^2 t}{1 + k_2 q_e t} \quad (10)$$

where q_t (mg g^{-1}) is the adsorption capacity at time t (min), and q_e (mg g^{-1}) is the equilibrium adsorption capacity; k_1 (min^{-1}) and k_2 ($\text{g mg}^{-1} \text{ min}^{-1}$) are the adsorption rate constant for the pseudo-first order and pseudo-second order kinetics models, respectively.

The Elovich kinetic model:

$$q_t = \frac{1}{\beta} \ln(\alpha\beta) + \frac{1}{\beta} \ln t \quad (11)$$

where α ($\text{mg g}^{-1} \text{ min}^{-1}$) is the adsorption rate constant and β (g mg^{-1}) is the desorption rate constant.

The intra-particle diffusion model:

$$q_t = k_{\text{di}} t^{0.5} + C_i \quad (12)$$

where k_{di} ($\text{mg g}^{-1} \text{ min}^{-0.5}$) is the intra-particle diffusion rate constant, $t^{0.5}$ ($\text{min}^{-0.5}$) is the square root of time, and C_i (mg g^{-1}) is the intercept related to the resistance to diffusion.

The best fits of the four kinetic models to the experimental data are shown in Fig. 9 and the derived kinetic parameters and determination coefficients (R^2) appear in Table 2. It is seen from Fig. 9a and b that the PSO kinetic model best fits experimental data, which is consistent with the high R^2 values and the theoretical adsorption capacities ($q_{\text{e(cal)}}$) calculated from the PSO model being comparable to the experimental values ($q_{\text{e(exp)}}$) (Table 2). This implies that the adsorption rate is controlled by chemisorption due to electron sharing or exchange between the dyes and the Dex-MA/PAA hydrogel.^{40,43,44}

The fitting plots for the intra-particle diffusion model for the adsorption of MB and CV were displayed in Fig. 9c and d. The experimental data for MB and CV adsorption separate into three linear regions indicative of a three-stage adsorption process. It

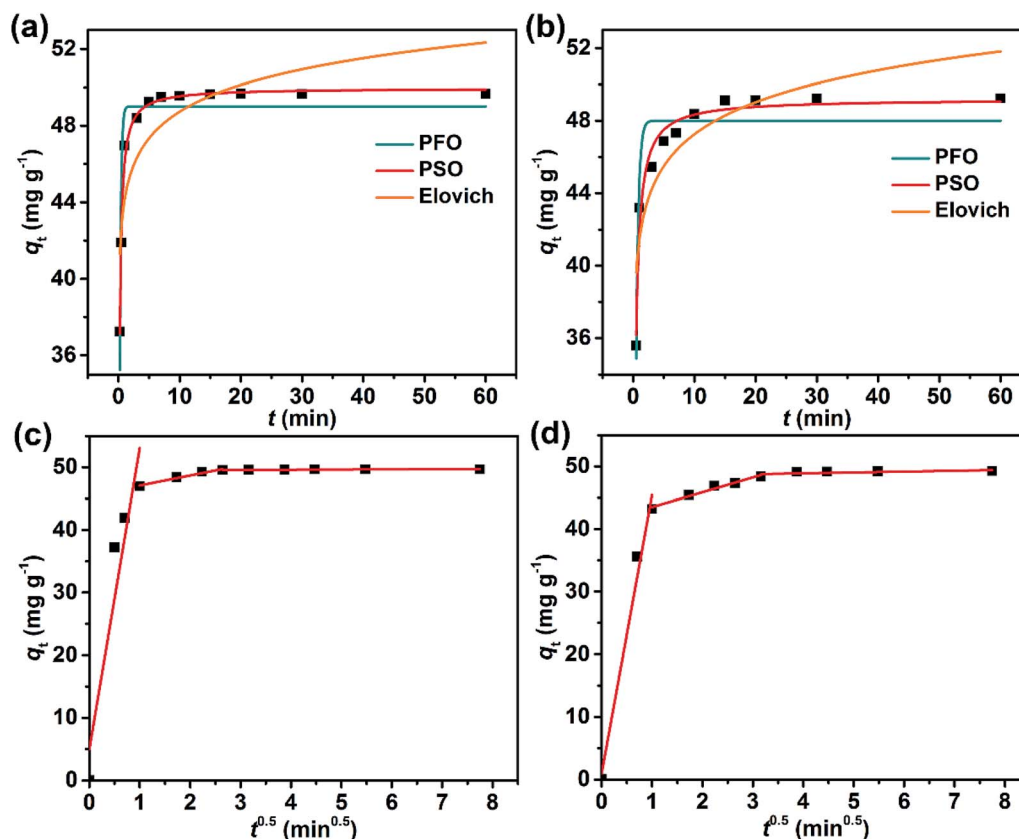


Fig. 9 Dye adsorption on Dex-MA/PAA as a function of time: pseudo-first order (PFO), pseudo-second order (PSO) and Elovich kinetic plots of (a) MB and (b) CV; intra-particle diffusion kinetic plots of (c) MB and (d) CV.



Table 2 Parameters for pseudo-first order, pseudo-second order and Elovich kinetic models, and intra-particles diffusion model for MB and CV adsorption

	Parameter	Adsorbing dye	
		MB	CV
Pseudo-first order	$q_{e(cal)}$	49.0	48.0
	k_1	5.08	2.60
	R^2	0.8664	0.8912
Pseudo-second order	$q_{e(cal)}$	49.9	49.2
	k_2	0.23	0.11
	R^2	0.9896	0.9666
Elovich	$\alpha(\times 10^9)$	6.63	0.03
	β	0.50	0.40
	R^2	0.6997	0.7716
Intra-particle diffusion			
Stage 1	k_{d1}	48.2	44.5
	C_1	4.95	0.93
	R^2	0.8491	0.9698
Stage 2	k_{d2}	1.60	2.37
	C_2	45.5	41.1
	R^2	0.9528	0.9661
Stage 3	k_{d3}	0.028	0.032
	C_3	49.5	49.0
	R^2	0.5653	0.7519

is seen from Table 2 that the diffusion rate constants for MB and CV for each step follows the order of: $k_{d1} > k_{d2} > k_{d3}$, while the intercept C follows the order of: $C_1 < C_2 < C_3$ and provides the information about the thickness of the boundary layer or resistance to diffusion⁴⁵ The first stage had the highest diffusion constant, k_{d1} , and lowest intercept, C_1 , consistent with rapid diffusion of the dye from the bulk solution to the Dex-MA/PAA hydrogel surface. In the second stage, adsorption slows as the dye diffuses less rapidly into the pores of the hydrogel (intra-particle diffusion) where it adsorbs through electrostatic interactions. With increasing dye adsorption onto the hydrogel surface, dye adsorption slows further as equilibrium is reached and dye adsorption and desorption reach a kinetic balance in the third stage. Consequently, k_{d3} decreases while C_3 increases. All these observations are consistent with the MB and CV adsorption processes occurring in three stages and being partially controlled by intra-particle diffusion.^{37,45} The adsorption kinetics at 100 mg mL⁻¹ of dyes were also confirmed and showed similar results (Fig. S7, S8 and Table S5†).

3.6 Dye adsorption isotherms for Dex-MA/PAA

The character of the dye adsorption isotherms for the Dex-MA/PAA hydrogel was determined from the equilibrium q_e and C_e at different initial concentration of dyes. The variations of q_e with C_i for MB and CV are shown in Fig. 10a and b, respectively. In both cases q_e increased linearly for most of the C_i range before reaching a plateau at 1800 mg L⁻¹ for MB and 2300 mg L⁻¹ for CV consistent with saturation of the Dex-MA/PAA carboxylate sites. The q_e at saturation were 1984 mg g⁻¹ for MB and 2405 mg g⁻¹ for CV.

These adsorption data were fitted to four adsorption isotherm models expressed as follows:

The Freundlich isotherm model:

$$q_e = k_F C_e^{\frac{1}{n_F}} \quad (13)$$

where k_F (mg g⁻¹ (L mg⁻¹)^{1/ n_F}) is the Freundlich isotherm constant and n_F (dimensionless) is the heterogeneity factor related to the adsorption. This model assumes adsorption to occur on an energetically heterogeneous surface.⁴

The Temkin isotherm model:

$$q_e = \frac{RT}{b_T} \ln(k_T C_e) \quad (14)$$

where R (8.314 J K⁻¹ mol⁻¹) is the universal gas constant, T (K) is the absolute temperature, b_T (dimensionless) is related to the heat of adsorption and k_T (L mg⁻¹) is the Temkin isotherm constant. This model assumes heat adsorption to decrease as surface coverage increases.²⁶

The Langmuir isotherm model:

$$q_e = \frac{q_m k_L C_e}{1 + k_L C_e} \quad (15)$$

where q_m (mg g⁻¹) is the maximum adsorption capacity; k_L (L mg⁻¹) present the adsorption energy. This model assumes that adsorption occurs on a homogeneous monolayer surface.⁴⁶

The Sips isotherm model:

$$q_e = \frac{q_m (k_s C_e)^{\frac{1}{n_s}}}{1 + (k_s C_e)^{\frac{1}{n_s}}} \quad (16)$$

where k_s (L mg⁻¹) is related the adsorption energy and the n_s is the heterogeneity factor related to the adsorption. Besides, the Sips model incorporates both heterogeneity and saturation and effectively combines the Freundlich and Langmuir models.^{27,47}

The isotherm parameters calculated through fitting the adsorption data to the four models appear in Table 3, and the best-fit curves for MB and CV adsorption appear in Fig. 10c and d respectively. On the basis of the R^2 values, the experimental data were best-fitted by the Sips isotherm model. The maximum adsorption capacity $q_{m(cal)}$ of MB (1994 mg g⁻¹, 6.23 mmol) and CV (2390 mg g⁻¹, 5.86 mmol) calculated through the Sips isotherm model are similar to the experimental maximum adsorption capacities $q_{m(exp)}$ (Table 3). The calculated k_s of MB (0.12 L mg⁻¹) was less than that of CV (0.19 L mg⁻¹), indicating that CV has a higher affinity for adsorption by the Dex-MA/PAA hydrogel than MB. The heterogeneity factor, n_s for both MB (0.40) and CV (0.14) are both significantly less than unity indicating that their adsorption processes are only moderately heterogeneous in nature.⁴⁷

3.7 Comparison with other polysaccharide based adsorbents

The maximum adsorption capacities of Dex-MA/PAA hydrogel adsorbent for MB and CV are compared with other polysaccharide based adsorbents in Table 4. On the basis of the q_m data it is seen that the Dex-MA/PAA hydrogel possessed





Fig. 10 The variation of the amount of dye adsorbed at equilibrium by Dex-MA/PAA, q_e , with initial dye concentrations, C_0 , for (a) MB and (b) CV. The fitting curves for the Freundlich, Temkin, Langmuir and Sips isotherms for (c) MB and (d) CV. Dex-MA/PAA dose: 1 g L^{-1} , $\text{pH}_{\text{initial}} 8.0$.

Table 3 Derived parameters for the Freundlich, Temkin, Langmuir and Sips isotherm models for MB and CV adsorption

Isotherm	Parameters	Adsorbing dye	
		MB	CV
	$q_{\text{e(exp)}} (\text{mg g}^{-1})$	1984	2405
Freundlich	k_F	350	856
	n_F	2.72	4.53
	R^2	0.6992	0.4734
Temkin	k_T	0.80	2.13
	b_T	5.27	5.18
	R^2	0.8415	0.5915
Langmuir	$q_{\text{m(max)}}$	2364	3380
	k_L	0.073	0.10
	R^2	0.8838	0.5730
Sips	$q_{\text{m(max)}}$	1994	2390
	k_S	0.12	0.19
	n_S	0.40	0.14
	R^2	0.9861	0.9838

a relative high adsorption capacity for MB and an even higher one for CV by comparison with other adsorbents. These results indicated that the Dex-MA/PAA hydrogel can be recognized as a promising adsorbent for removing the cationic dyes.

The performance of Dex-MA/PAA hydrogel in the presence of both cationic dyes were also measured (MB 50 mg L^{-1} , CV

50 mg L^{-1}). The results showed that both removal efficiency of MB and CV were higher than 98% due to the high adsorption capacity of Dex-MA/PAA hydrogel (Fig. S9†). Besides, humic acid is one of the natural organic matter (NOM) existing in the river and soil. Several studies have shown that the presence of humic acid can significant affect the adsorption of organic pollutant from their aqueous solutions, and the pollutants will gradually accumulate in the river and soil.^{47,48} Here, humic acid was mixed with MB and CV and the removal efficiency was investigated under Dex-MA/PAA hydrogel. As shown in Fig. S10,† the removal efficiency of MB and CV were nearly invariant even at 50 mg L^{-1} of humic acid, and the Dex-MA/PAA hydrogel presented strong adsorption ability to MB and CV. This was probably because the humic acid could not compete with MB and CV onto adsorption sites. Meanwhile, the pH of the solution was stable due to the excellent buffer ability, which decrease the influence of humic acid.

3.8 Dye desorption and reuse studies

The regeneration of an adsorbent is crucial for its practical applications. As shown in Fig. 11, five adsorption/desorption cycles were performed with the Dex-MA/PAA hydrogel to evaluate its reusability. The removal efficiencies for MB and CV were >95% and showed very small variations over the five cycles, demonstrating the excellent recycling performance and stability of the Dex-MA/PAA hydrogel.



Table 4 Maximum adsorption capacities of polysaccharide based adsorbents

Dye	Adsorbent	$q_{m(cal)}$ (mg g ⁻¹)	Reference
MB	Chitosan-g-poly(acrylic acid)/rice husk ash	1841	15
	Polyacrylic acid-grafted quaternized cellulose	1735	16
	Gum ghatti-g-poly(acrylic acid)	909	18
	Salecan-g-(acrylamide-co-itaconic acid)	107	49
	Starch-g-poly(acrylic acid)	1532	17
	Dex-MA/PAA hydrogel	1994	This study
CV	Triphenylene-modified chitosan	2283	50
	Oxidized cellulose	1118	51
	Xanthan gum-g-poly(<i>N</i> -vinyl imidazole)	453	14
	Alginate/acid activated bentonite beads	582	52
	Starch-derived carbon aerogels	1515	53
	Dex-MA/PAA hydrogel	2390	This study



Fig. 11 Removal efficiencies for (a) MB and (b) CV were >95% after five Dex-MA/PAA hydrogel adsorption/desorption cycles. Dex-MA/PAA hydrogel dose: 1 g L⁻¹, dye concentration: 50 mg L⁻¹, pH_{initial} 8.0.

4. Conclusions

In this study, the Dex-MA/PAA hydrogel adsorbent was prepared by using glycidyl methacrylate modified dextran (Dex-MA) as the

biocompatible cross-linker and acrylic acid as the functional group. Dex-MA/PAA hydrogel presented high removal efficiency on Methylene Blue (MB) and Crystal Violet (CV) over a wide range of pH (3–10) due to the strong buffer ability. The adsorbent presented fast adsorption rate with short equilibrium for MB (5 min) and CV (15 min). Besides, the equilibrium data were well simulated by Sips model, and the calculated maximum adsorption capacity was 1994 mg g⁻¹ for MB and 2390 mg g⁻¹ for CV, which were higher than other polysaccharides based adsorbents. Moreover, the adsorbents were regenerated and reused for 5 times without a significant efficiency loss. These data show that the Dex-MA/PAA hydrogel is a promising candidate for a use as an efficient adsorbent in water treatment.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the NSFC Grants (51761135128, 51403062, and 51773061) and Key Scientific and Technological Project of Xinjiang Bingtuan (2018AB025), China Scholarship Council (CSC).

References

- 1 T. Ngulube, J. R. Gumbo, V. Masindi and A. Maity, *J. Environ. Manage.*, 2017, **191**, 35–57.
- 2 W. S. W. Ngah, L. C. Teong and M. Hanafiah, *Carbohydr. Polym.*, 2011, **83**, 1446–1456.
- 3 A. Kausar, M. Iqbal, A. Javed, K. Aftab, Z. I. H. Nazli, H. N. Bhatti and S. Nouren, *J. Mol. Liq.*, 2018, **256**, 395–407.
- 4 Y. Chen, F. He, Y. Ren, H. Peng and K. Huang, *Chem. Eng. J.*, 2014, **249**, 79–92.
- 5 Y. Zhang, Z.-R. Tang, X. Fu and Y.-J. Xu, *ACS Nano*, 2010, **4**, 7303–7314.
- 6 H. Sarkka, A. Bhatnagar and M. Sillanpaa, *J. Electroanal. Chem.*, 2015, **754**, 46–56.
- 7 M. Ali, A. Sarkar, M. D. Pandey and S. Pandey, *Anal. Sci.*, 2006, **22**, 1051–1053.



- 8 Y. Han, Z. Xu and C. Gao, *Adv. Funct. Mater.*, 2013, **23**, 3693–3700.
- 9 A. K. Verma, R. R. Dash and P. Bhunia, *J. Environ. Manage.*, 2012, **93**, 154–168.
- 10 M. A. M. Salleh, D. K. Mahmoud, W. Karim and A. Idris, *Desalination*, 2011, **280**, 1–13.
- 11 T. I. Tikhomirova, G. R. Ramazanov and V. V. Apyari, *J. Anal. Chem.*, 2017, **72**, 917–934.
- 12 M. T. Yagub, T. K. Sen, S. Afroze and H. M. Ang, *Adv. Colloid Interface Sci.*, 2014, **209**, 172–184.
- 13 Y. M. Wang, J. Wang, Z. Y. Yuan, H. Y. Han, T. Li, L. Li and X. H. Guo, *Colloids Surf., B*, 2017, **152**, 252–259.
- 14 R. R. Mohamed, M. H. Abu Elella, M. W. Sabaa and G. R. Saad, *Cellulose*, 2018, **25**, 6513–6529.
- 15 M. G. Vaz, A. G. B. Pereira, A. R. Fajardo, A. C. N. Azevedo and F. H. A. Rodrigues, *Water, Air, Soil Pollut.*, 2017, **228**, 1–14.
- 16 Y. Wang, C. Zhang, L. Zhao, G. Meng, J. Wu and Z. Liu, *Fibers Polym.*, 2017, **18**, 891–899.
- 17 X. W. Liu and Q. Y. Wei, *RSC Adv.*, 2016, **6**, 79853–79858.
- 18 E. Fosso-Kankeu, H. Mittal, S. B. Mishra and A. K. Mishra, *J. Ind. Eng. Chem.*, 2015, **22**, 171–178.
- 19 M. Naessens, A. Cerdobbel, W. Soetaert and E. J. Vandamme, *J. Chem. Technol. Biotechnol.*, 2005, **80**, 845–860.
- 20 E. Cho, M. N. Tahir, J. M. Choi, H. Kim, J.-H. Yu and S. Jung, *Carbohydr. Polym.*, 2015, **133**, 221–228.
- 21 C. Demirbilek and C. O. Dinc, *Carbohydr. Polym.*, 2012, **90**, 1159–1167.
- 22 E. Cho, M. N. Tahir, H. Kim, J.-H. Yu and S. Jung, *RSC Adv.*, 2015, **5**, 34327–34334.
- 23 Q. Liu, M. Zhao, S. Mytnyk, B. Klemm, K. Zhang, Y. Wang, D. Yan, E. Mendes and J. H. van Esch, *Angew. Chem., Int. Ed.*, 2019, **58**, 547–551.
- 24 H. C. Chiu, Y. F. Lin and Y. H. Hsu, *Biomaterials*, 2002, **23**, 1103–1112.
- 25 A. Abbadessa, M. M. Blokzijl, V. H. M. Mouser, P. Marica, J. Malda, W. E. Hennink and T. Vermonden, *Carbohydr. Polym.*, 2016, **149**, 163–174.
- 26 Y. Zhou, M. Zhang, X. Hu, X. Wang, J. Niu and T. Ma, *J. Chem. Eng. Data*, 2013, **58**, 413–421.
- 27 F. Zhao, E. Repo, D. Yin, Y. Meng, S. Jafari and M. Sillanpää, *Environ. Sci. Technol.*, 2015, **49**, 10570–10580.
- 28 J. Ma, G. Zhou, L. Chu, Y. Liu, C. Liu, S. Luo and Y. Wei, *ACS Sustainable Chem. Eng.*, 2017, **5**, 843–851.
- 29 W. N. E. van Dijk-Wolthuis, O. Franssen, H. Talsma, M. J. van Steenbergen, J. J. Kettenes-van den Bosch and W. E. Hennink, *Macromolecules*, 1995, **28**, 6317–6322.
- 30 C. J. Yan, T. H. Yang, S. K. Zhu and H. Wu, *J. Mater. Chem. B*, 2017, **5**, 3697–3705.
- 31 S. Chowdhury and P. Das, *Environ. Prog. Sustainable Energy*, 2012, **31**, 415–425.
- 32 S. Y. Wang, K. M. Chen, Y. S. Xu, X. J. Yu, W. H. Wang, L. Li and X. H. Guo, *Soft Matter*, 2013, **9**, 11276–11287.
- 33 H. Mittal, A. Maity and S. S. Ray, *Chem. Eng. J.*, 2015, **279**, 166–179.
- 34 W. Wang, L. Li, K. Henzler, Y. Lu, J. Wang, H. Han, Y. Tian, Y. Wang, Z. Zhou, G. Lotze, T. Narayanan, M. Ballauff and X. Guo, *Biomacromolecules*, 2017, **18**, 1574–1581.
- 35 V. K. Gupta, A. Mittal, V. Gajbe and J. Mittal, *Ind. Eng. Chem. Res.*, 2006, **45**, 1446–1453.
- 36 Y. Shao, L. Zhou, C. Bao, J. Ma, M. Liu and F. Wang, *Chem. Eng. J.*, 2016, **283**, 1127–1136.
- 37 P. Wu, Z. Cai, H. Jin and Y. Tang, *Sci. Total Environ.*, 2019, **650**, 671–678.
- 38 X. X. Ruan, Y. H. Chen, H. Chen, G. R. Qian and R. L. Frost, *Chem. Eng. J.*, 2016, **297**, 295–303.
- 39 J.-P. Simonin, *Chem. Eng. J.*, 2016, **300**, 254–263.
- 40 K. C. Bedin, A. C. Martins, A. L. Cazetta, O. Pezoti and V. C. Almeida, *Chem. Eng. J.*, 2016, **286**, 476–484.
- 41 X. L. Li, Y. Zhang, L. Y. Jing and X. H. He, *Chem. Eng. J.*, 2016, **292**, 326–339.
- 42 W. Konicki, K. Cendrowski, X. C. Chen and E. Mijowska, *Chem. Eng. J.*, 2013, **228**, 824–833.
- 43 Y. S. Ho and G. McKay, *Process Biochem.*, 1999, **34**, 451–465.
- 44 L. M. Cui, Y. G. Wang, L. Gao, L. H. Hu, L. G. Yan, Q. Wei and B. Du, *Chem. Eng. J.*, 2015, **281**, 1–10.
- 45 Z. Wu, H. Zhong, X. Yuan, H. Wang, L. Wang, X. Chen, G. Zeng and Y. Wu, *Water Res.*, 2014, **67**, 330–344.
- 46 B. Chen, H. N. Zhao, S. J. Chen, F. X. Long, B. Huang, B. Q. Yang and X. J. Pan, *Chem. Eng. J.*, 2019, **356**, 69–80.
- 47 W. Huang, Y. Hu, Y. Li, Y. Zhou, D. Niu, Z. Lei and Z. Zhang, *J. Taiwan Inst. Chem. Eng.*, 2018, **82**, 189–197.
- 48 Z. D. Wen, D. W. Gao, Z. Li and N. Q. Ren, *Chem. Eng. J.*, 2013, **223**, 298–303.
- 49 X. Qi, W. Wei, T. Su, J. Zhang and W. Dong, *Carbohydr. Polym.*, 2018, **195**, 368–377.
- 50 F. Yang, X. Bai, B. Xu and H. Guo, *Cellulose*, 2013, **20**, 895–906.
- 51 L. R. Martins, J. A. V. Rodrigues, O. F. H. Adarme, T. M. S. Melo, L. V. A. Gurgel and L. F. Gil, *J. Colloid Interface Sci.*, 2017, **494**, 223–241.
- 52 A. A. Oladipo and M. Gazi, *J. Water Process Eng.*, 2014, **2**, 43–52.
- 53 X. H. Chang, D. R. Chen and X. L. Jiao, *Polymer*, 2010, **51**, 3801–3807.

