



Cite this: *RSC Adv.*, 2021, 11, 1354

Self-supporting V_2O_5 nanofiber-based electrodes for magnesium–lithium-ion hybrid batteries†

Achim M. Diem, Kevin Hildenbrand, Leila Raafat, Joachim Bill and Zaklina Burghard *

The increasing demand for high energy, sustainable and safer rechargeable electrochemical storage systems for portable devices and electric vehicles can be satisfied by the use of hybrid batteries. Hybrid batteries, such as magnesium–lithium-ion batteries (MLIBs), using a dual-salt electrolyte take advantage of both the fast Li^+ intercalation kinetics of lithium-ion batteries (LIBs) and the dendrite-free anode reactions. Here we report the utilization of a binder-free and self-supporting V_2O_5 nanofiber-based cathode for MLIBs. The V_2O_5 cathode has a high operating voltage of ~ 1.5 V vs. Mg/Mg^{2+} and achieves storage capacities of up to 386 mA h g^{-1} , accompanied by an energy density of 280 W h kg^{-1} . Additionally, a good cycling stability at 200 mA g^{-1} over 500 cycles is reached. The structural integrity of the V_2O_5 cathode is preserved upon cycling. This work demonstrates the suitability of the V_2O_5 cathode for MLIBs to overcome the limitations of LIBs and MIBs and to meet the future demands of advanced electrochemical storage systems.

Received 9th December 2020
Accepted 18th December 2020

DOI: 10.1039/d0ra10384e

rsc.li/rsc-advances

1 Introduction

The increasing demand of electrochemical storage systems for various portable devices and electric vehicles is accelerating the development of batteries, especially lithium-ion batteries (LIBs).^{1,2} The electrochemical performance of LIBs is so far incomparable due to their high energy density, fast Li^+ insertion kinetics, rate capability and long-term stability.^{2,3} However, lithium is a highly reactive metal, has restricted natural resources, and safety hazards. In particular, the thermal runaway caused by dendrite formation on the anode side limits the application of LIBs. These drawbacks encouraged the research of alternative mono- and multivalent metal-ion battery systems.^{4–6} Among them, magnesium-ion batteries (MIBs) are very promising, as magnesium is more abundant and its theoretical volumetric capacity of 3832 mA h cm^{-3} is roughly twice as that of lithium.⁵ Furthermore, magnesium anodes do not form dendrites which improves the safety of the entire electrochemical storage system. However, the sluggish Mg^{2+} solid state diffusion within most cathode materials, restricting the storage capacity and rate capability of MIBs, has to be overcome.⁷ Accordingly, suitable cathode materials, which can host Mg^{2+} , still have to be developed and optimized. Another important issue is utilizing a non-corrosive and stable

electrolyte, which does not form blocking layers, as it is the case for conventional perchlorates in organic solvents.⁴

To overcome the drawbacks of LIBs and MIBs and simultaneously exploit their advantages, the hybrid magnesium–lithium-ion battery (MLIB) is a favorable candidate. A lithium-intercalation cathode and magnesium anode are thereby used, in combination with a dual-salt electrolyte, containing both Mg^{2+} and Li^+ .⁵ This approach utilizes the fast Li^+ insertion kinetics into the cathode and therefore, high storage capacities and high rate capabilities can be reached. Furthermore, on the anode side Mg^{2+} is stripped and deposited without dendrite formation during the electrochemical cycling.^{8,9} Specifically, during the charge process, Li^+ is de-intercalated from the cathode and Mg^{2+} is deposited on the Mg anode, whereas during the discharge process the reactions are *vice versa* (Fig. 1a).

The concept of MLIBs and therefore their development is still in its early stages. Hence, only a limited number of cathode materials are investigated. These include Mo_6S_8 ,⁹ dichalcogenides,^{10–14} phosphates¹⁵ and metal oxides.^{16–21} Although the working principle and intercalation mechanisms of these cathode materials has been proven, some of them lag behind in working voltage and energy density. Therefore, the development of MLIBs requires further research in respect to high voltage cathode materials delivering high energy densities.

A promising intercalation compound for a variety of mono- and multivalent ions is vanadium pentoxide (V_2O_5) with its rich redox chemistry promoting high storage capacities and energy densities. V_2O_5 nanofibers are suitable as cathode material for MLIBs as they comprise a spacious bilayer of chain-like VO_5

Institute for Materials Science, University of Stuttgart, Stuttgart, Germany. E-mail: zaklina.burghard@imw.uni-stuttgart.de

† Electronic supplementary information (ESI) available. See DOI: 10.1039/d0ra10384e



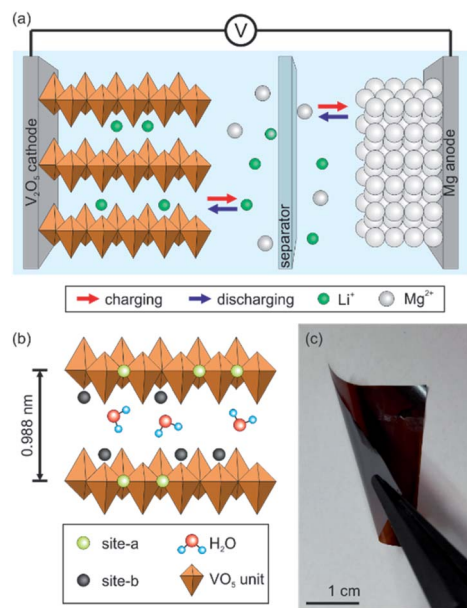


Fig. 1 (a) Schematic depiction of the design and working principle of hybrid batteries using a dual-salt electrolyte and Mg anode. The working principle includes the de-intercalation of Li⁺ from the cathode and the deposition of Mg²⁺ on the Mg anode during charging. For the discharging process the reactions are *vice versa*. (b) Scheme of the V₂O₅ bilayer with its intercalation sites, site-a and site-b, the incorporated water molecules assuring that the interlayer distance is large enough to enable ion intercalation. (c) Digital image showing the high flexibility of the self-supporting V₂O₅ nanofiber-based cathode.

units (Fig. 1b). The space between them contains water molecules, which keep the distance large enough to host intercalating ions and facilitate their insertion.^{22,23} Additionally, the chain-like bilayer provides two different intercalation sites (site-a and site-b, Fig. 1b). Specifically, site-a is near the planar oxygen atom, whereas site-b is around the apical oxygen atoms of the VO₅ units.²⁴ Furthermore, the nanofibers can be self-assembled into binder-free and self-supporting paper-like thin films having a uniform layered sheet-like structure providing a high mechanical flexibility. Such electrodes can be beneficial for the overall cell performance, as parasitic side reactions found in conventional slurry-based electrodes are prevented.

Herein, we report the usage of a binder-free and self-supporting V₂O₅ nanofiber-based cathode for MLIBs. The V₂O₅ cathode is fabricated by a self-assembly approach, following a reported procedure.^{25,25,26} The commonly all phenyl complex (APC) electrolyte for MLIBs was used in this work as it has proven its stability over the required electrochemical potential window. The APC electrolyte was prepared by dissolving aluminum chloride (AlCl₃) in tetrahydrofuran (THF), followed by the addition of a phenyl magnesium chloride solution in THF. An appropriate amount of LiCl is added, leading to 0.25 M APC and 1 M LiCl.²⁷ The V₂O₅ cathode was assembled in an argon-filled glovebox in Swagelok-type cells with Mo as current collectors, as stainless steel is unstable in the APC electrolyte (ESI, Fig. S1†). Mg metal is used as anode, since lithium metal reacts within the electrolyte (ESI, Fig. S2†). Glass

fiber and polypropylene membranes were employed as the separator.

2 Experimental section

2.1. Synthesis of the V₂O₅ nanofibers

The V₂O₅ nanofiber dispersion was prepared by adding 1 g ammonium-vanadate (Fluka) and 10 g of Dowex50W8 50-100 (Alfa Aesar) as acidic ion exchanger to 200 ml deionized water. The mixture was heated for 10 min at 80 °C in an oil bath and is subsequently slowly cooled down to room temperature and aged for six weeks.

2.2. Electrode fabrication

The obtained V₂O₅ nanofiber dispersion was diluted with deionized water (1 : 1), from which 9 ml were poured into a glass beaker on a freshly cleaned Si(100) p-type wafer (Wacker, Sitronic). After complete evaporation of the water, the V₂O₅ film could be detached from the Si wafer in a water bath to obtain the self-supporting thin film. The latter was further treated in a two-step procedure, utilizing a climatic chamber (VC7018, Vötsch). The first step included a temperature and relative humidity increase within 15 minutes to 40 °C and 80%, respectively. This temperature was fixed for 15.5 hours, whereas the humidity was only held for 1 hour, followed by its decrease to 20% within 10 hours and kept for 4.5 hours. In the second annealing step the temperature was increased from 25 °C to 150 °C over 30 minutes and kept for two hours, followed by a temperature reduction to room temperature. The annealed self-supporting films were coated from both sides with ~10 nm carbon (SCD 040, Balzers Union).

2.3. Electrolyte preparation

The synthesis of the APC electrolyte was performed in an argon filled glovebox (<1 ppm oxygen and water) following a procedure previously reported by Mizrahi and coworkers.¹ 3.33 g anhydrous aluminum chloride (AlCl₃, 99.99%, Sigma Aldrich) were slowly added and dissolved in 75 ml tetrahydrofuran (THF) under vigorous stirring for 12 hours. 25 ml of the phenyl magnesium chloride solution (2 M in THF, Sigma Aldrich) were then added and the solution was stirred for 12 hours. Finally, 1 M anhydrous lithium chloride (LiCl, 99%, Alfa Aesar) was added to the 0.25 M APC solution, followed by stirring for 12 hours.

2.4. Cell assembly

Swagelok-type cells made of polytetrafluoroethylene (PTFE) were assembled in an argon filled glovebox (<1 ppm oxygen and water), using molybdenum current collectors. A polypropylene membrane and a glass fiber membrane (Grade 934-AH, Whatman), each with a diameter of 10.5 mm, were added atop the V₂O₅ cathode (8 mm diameter), followed by the addition of the APC-based electrolyte. Freshly polished Mg discs with a diameter of 10 mm were used for the stability tests and impedance measurements. For all other electrochemical measurements, a Mg disc with a diameter of 8 was used as anode.



© 2021 The Author(s). Published by the Royal Society of Chemistry

characterizing capacitive or surface-controlled processes. The plot of anodic peak current *vs.* the square root of the scan rate, showing a linear relation between *I* and $\nu^{1/2}$, implies that the electrochemical processes are diffusion-controlled (ESI, Fig. S5a†). This indication is corroborated by the non-linear relationship of *I* and ν plot (ESI, Fig. S5b†). These results confirm, that Mg^{2+} is mainly irreversibly intercalated and not just adsorbed on the surface of the V_2O_5 nanofibers.

To further characterize the V_2O_5 cathode in terms of storage capacity, rate capability and cycling stability, galvanostatic charge and discharge experiments were conducted. Fig. 3a shows the determined specific discharge capacity of the cathode. In particular, a maximum discharge capacity of 386, 174, 93 and 4 mA h g^{-1} were obtained for 10, 100, 200 and 500 mA g^{-1} , respectively. Stable discharge capacities for the first 20 cycles were observed for all investigated current densities except for 10 mA g^{-1} . Notably, for the latter fast fading of the specific capacity was observed. This observation can be attributed the irreversible Mg^{2+} intercalation and its occupancy of the Li^+ intercalation sites, as concluded from the CV measurements. Interestingly, at a current density of 200 mA g^{-1} (Fig. 3b) the storage capacity continuously increased over the first 70 cycles, from 33 mA h g^{-1} up to 48 mA h g^{-1} . This increase can be ascribed to the formation of an interphase that supports the ion diffusion between the electrode and electrolyte leading to a more efficient de-/intercalation process. After 500 cycles the V_2O_5 cathode still delivers $\sim 20 \text{ mA h g}^{-1}$. The accompanied Coulomb efficiency is almost 100% over all 500 cycles, showing the high reversibility of the electrochemical processes.

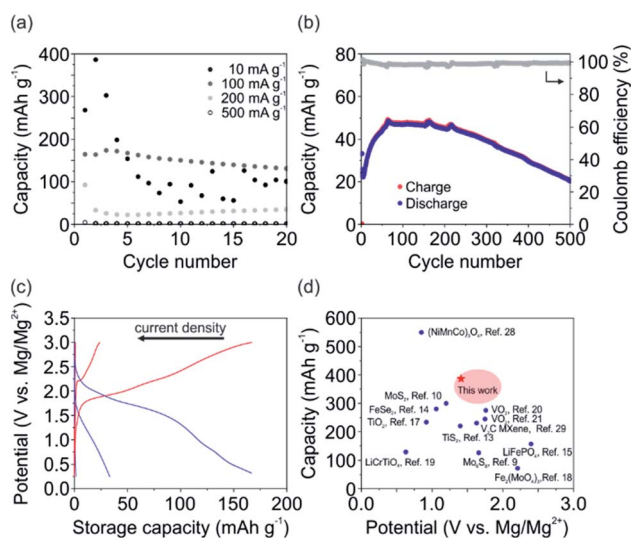


Fig. 3 Galvanostatic charge and discharge experiments using the APC + LiCl electrolyte. (a) Determined discharge capacity of the V_2O_5 cathode in dependence of the applied current density. (b) Charge and discharge capacity, as well as the Coulomb efficiency over 500 cycles for the V_2O_5 at a current density of 200 mA g^{-1} . (c) Voltage–capacity profiles (2nd cycle) for the current densities of 500, 200 and 100 mA g^{-1} . (d) Comparison of the V_2O_5 cathode to other cathode materials, including oxides,^{8,17–21,28} sulfides,^{9,10,13} carbides,²⁹ selenides¹⁴ and phosphates.¹⁵

The voltage–capacity profiles for the current densities of 100, 200, 500 mA g^{-1} are shown in Fig. 3c, with corresponding discharge capacities of 167, 33 and 1.5 mA h g^{-1} and energy densities of 174, 25, 0.6 W h kg^{-1} . For the current density of 10 mA g^{-1} the discharge capacity of the 2nd cycle is 386 mA h g^{-1} with an accompanied energy density of 280 W h kg^{-1} . The profile corresponding to 100 mA g^{-1} shows two de-/intercalation plateaus, similar to the CV measurements for low scan rates (Fig. 2b). This further supports the assumption that Li^+ occupy the two distinct intercalation sites of the V_2O_5 host lattice (Fig. 1b). Specifically, intercalation close to the center of the square-planar oxygen at higher potentials ($\sim 1.9 \text{ V}$) and intercalation around the apical oxygen of the VO_5 unit at lower potentials ($\sim 1.5 \text{ V}$) are reported for the insertion of Li^+ .²⁴

To validate the superior performance of our V_2O_5 cathode to reported MLIB cathode materials, the discharge capacity is plotted *vs.* the intercalation potential (Fig. 3d). The reported cathode materials include oxide-based materials,^{8,17–21,28} sulfides,^{9,10,13} carbides,²⁹ selenides¹⁴ and phosphates.¹⁵ The comparison reveals that our V_2O_5 nanofiber-based cathode with its high storage capacity of 386 mA h g^{-1} is superior to almost all other reported cathode materials. Additionally, the high intercalation potentials of $\sim 1.4 \text{ V}$ and $\sim 2 \text{ V}$ *vs.* Mg/Mg^{2+} of our V_2O_5 cathode are comparable and even higher than other oxide-based cathode materials. The high intercalation potentials are important for achieving high energy densities, crucial in the development of rechargeable metal-ion batteries for portable devices and electric vehicles. Our V_2O_5 cathode with its binder-free and self-supporting design using V_2O_5 nanofibers, therefore renders the cathode as a promising candidate for MLIBs.

To investigate the cathode's structural stability during electrochemical processes, X-ray diffraction (XRD), Fourier-transform infrared spectroscopy (FTIR) and scanning electron microscopy (SEM) was performed for the pristine V_2O_5 cathode and after 150 cycles at a current density of 100 mA g^{-1} . The XRD

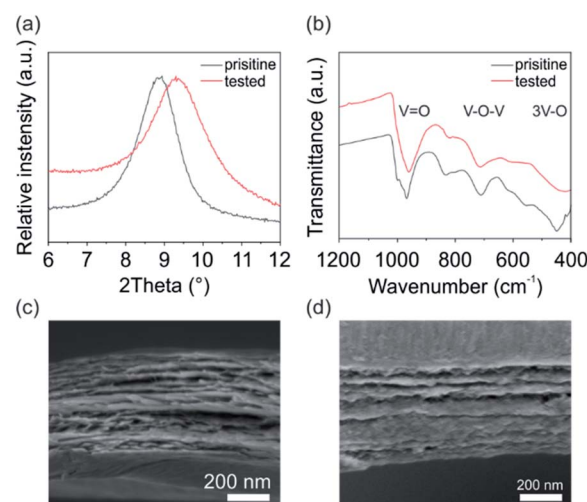


Fig. 4 Investigation of the pristine and electrochemical tested V_2O_5 cathode by (a) XRD and (b) FTIR. SEM cross-section images of the (c) pristine and (d) tested cathode, showing the preservation of the structural integrity of the V_2O_5 cathode upon electrochemical cycling.

pattern (Fig. 4a) for both the pristine and the tested V_2O_5 cathode show the typical (001) reflection for bilayered monoclinic $V_2O_5 \cdot nH_2O$ (space group $C2/m$),^{25,31} revealing the preservation of the structural integrity of the cathode upon cycling. The shift of the reflection around 9° indicates the decrease of the interlayer distance, specifically from 0.988 nm for the pristine to 0.950 nm for the tested cathode. This reduction of the interlayer distance is attributed to the stronger interaction between the intercalated positive species and the negatively charged VO_5 units.³² The FTIR measurements (Fig. 4b) verify the presence of the typical adsorption bands for $V=O$ and $V-O-V$ stretching at around 970 and 715 cm^{-1} , respectively, and the 3 $V-O$ stretching below 500 cm^{-1} found for V_2O_5 .²⁴ Specifically, the $V=O$ stretching of the tested cathode is more pronounced and shifted to lower wavenumbers. Contrary, the $V-O-V$ stretching is weakened upon electrochemical cycling. These changes of bonding confirm the findings of the CV and charge/discharge experiments, that ions are mainly intercalated around the apical oxygen atoms of the VO_5 units (site-b). In addition, the SEM cross-section images (Fig. 4c) before and after the electrochemical cycling show the uniform stacking of V_2O_5 sheets, which are formed during the self-assembly process.^{22,25} The SEM investigation further reveals no delamination of the film and no crack formation upon cycling. The preservation of the structural integrity of the V_2O_5 nanofiber-based cathode shows, that the cathode is able to host and accommodate ions and that the occurring stresses during intercalation are well distributed.

4 Conclusion and outlook

In summary, we presented a proof-of-concept and the potential of the utilization of a binder-free and self-supporting V_2O_5 cathode in MLIBs. The V_2O_5 nanofiber-based cathode shows reversible Li^+ intercalation at high potentials of ~ 1.5 V and ~ 2 V vs. Mg/Mg^{2+} . Storage capacities of up to 386 $mA\ h\ g^{-1}$ with an accompanied energy density of 280 $W\ h\ kg^{-1}$ at a current density of 10 $mA\ g^{-1}$ were thereby achieved. In addition, a good cycling stability at 200 $mA\ g^{-1}$ over 500 cycles was observed. Notably, the structural integrity of the V_2O_5 self-supporting cathode was preserved upon electrochemical cycling. FTIR measurements confirmed ion intercalation specific sites of the V_2O_5 host lattice. In conclusion, this work shows the feasibility of implementing a V_2O_5 nanofiber-based cathode in MLIBs, enabling high storage capacities and high intercalation potentials. To this end, a major challenge, which still has to be addressed, is the improvement of the self-supporting and binder-free V_2O_5 cathode electrical conductivity. In this regard, a combination with mechanically flexible graphene or reduced graphene oxide sheets, or chemical doping of the V_2O_5 nanofibers could be considered as promising approaches.

Author contributions

This manuscript was written with the contributions of all authors. All authors have read and agreed to the published version. Conceptualization, A. M. D. and Z. B.; methodology,

A. M. D., K. H. and L. R.; validation, A. M. D., L. R. J. B. and Z. B.; investigation, A. M. D., K. H.; writing—original draft preparation, A. M. D.; writing—review and editing, A. M. D., L. R., J. B. and Z. B.; supervision, J. B. and Z. B.; project administration, Z. B.; funding acquisition, Z. B.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

The authors are thankful to the group of J. Spatz and M. Sitti from the Max Planck Institute in Stuttgart for equipment use and technical support. The authors greatly appreciate T. Wörner for engineering support and T. Jahnke for fruitful discussions. The financial support provided by the Vector Stiftung (project no. 0090018) is highly appreciated.

Notes and references

- 1 M. Armand and J.-M. Tarascon, *Nature*, 2008, **451**, 652–657.
- 2 M. Li, J. Lu, Z. Chen and K. Amine, *Adv. Mater.*, 2018, **30**, 1800561.
- 3 M. S. Whittingham, *Chem. Rev.*, 2004, **104**, 4271–4302.
- 4 Z. Ma, D. R. MacFarlane and M. Kar, *Batteries Supercaps*, 2019, **2**, 115–127.
- 5 Y. Cheng, H. J. Chang, H. Dong, D. Choi, V. L. Sprenkle, J. Liu, Y. Yao and G. Li, *J. Mater. Res.*, 2016, **31**, 3125–3141.
- 6 Y. Zhang, S. Liu, Y. Ji, J. Ma and H. Yu, *Adv. Mater.*, 2018, **30**, 1706310.
- 7 Z. Li, L. Han, Y. Wang, X. Li, J. Lu and X. Hu, *Small*, 2019, **15**, 1900105.
- 8 M. Rashad, X. Li and H. Zhang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 21313–21320.
- 9 Y. Cheng, Y. Shao, J.-G. Zhang, V. L. Sprenkle, J. Liu and G. Li, *Chem. Commun.*, 2014, **50**, 9644–9646.
- 10 X. Fan, R. R. Gaddam, N. A. Kumar and X. S. Zhao, *Adv. Energy Mater.*, 2017, **7**, 1700317.
- 11 S. M. de la Parra-Arciniega, E. González-Juárez, R. A. Hernández-Carrillo, R. Briones-Martínez, R. M. Jiménez-Barrera, N. A. García-Gómez and E. M. Sánchez, *J. Mater. Sci.: Mater. Electron.*, 2020, **31**, 14702–14713.
- 12 Y. Meng, Y. Zhao, D. Wang, D. Yang, Y. Gao, R. Lian, G. Chen and Y. Wei, *J. Mater. Chem. A*, 2018, **6**, 5782–5788.
- 13 H. D. Yoo, Y. Liang, Y. Li and Y. Yao, *ACS Appl. Mater. Interfaces*, 2015, **7**, 7001–7007.
- 14 C. Zhang, L. Zhang, N. Li and X. Zhang, *Energies*, 2020, **13**, 4375.
- 15 Z. Zhang, H. Xu, Z. Cui, P. Hu, J. Chai, H. Du, J. He, J. Zhang, X. Zhou, P. Han, G. Cui and L. Chen, *J. Mater. Chem. A*, 2016, **4**, 2277–2285.
- 16 S. Su, Y. NuLi, Z. Huang, Q. Miao, J. Yang and J. Wang, *ACS Appl. Mater. Interfaces*, 2016, **8**, 7111–7117.
- 17 C. Zhu, Y. Tang, L. Liu, R. Sheng, X. Li, Y. Gao and Y. NuLi, *J. Colloid Interface Sci.*, 2021, **581**, 307–313.



- 18 N. Wang, H. Yuan, Y. NuLi, J. Yang and J. Wang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 38455–38466.
- 19 C. Zhu, Y. Tang, L. Liu, X. Li, Y. Gao and Y. NuLi, *ACS Sustainable Chem. Eng.*, 2019, **7**, 14539–14544.
- 20 Y. Cen, S. Li, Y. Zhou, X. Cai, X. Wang, Q. Xiang, B. Hu, D. Yu, Y. Liu and C. Chen, *J. Electrochem. Soc.*, 2019, **166**, A1660.
- 21 C. Pei, F. Xiong, J. Sheng, Y. Yin, S. Tan, D. Wang, C. Han, Q. An and L. Mai, *ACS Appl. Mater. Interfaces*, 2017, **9**, 17060–17066.
- 22 A. M. Diem, A. Knöller, Z. Burghard and J. Bill, *Nanoscale*, 2018, **10**, 15736–15746.
- 23 J. Livage, *Chem. Mater.*, 1991, **3**, 578–593.
- 24 D. Imamura and M. Miyayama, *Solid State Ionics*, 2003, **161**, 173–180.
- 25 Z. Burghard, A. Leineweber, P. A. van Aken, T. Dufaux, M. Burghard and J. Bill, *Adv. Mater.*, 2013, **25**, 2468–2473.
- 26 A. M. Diem, B. Fenk, J. Bill and Z. Burghard, *Nanomaterials*, 2020, **10**, 247.
- 27 O. Mizrahi, N. Amir, E. Pollak, O. Chusid, V. Marks, H. Gottlieb, L. Larush, E. Zinigrad and D. Aurbach, *J. Electrochem. Soc.*, 2008, **155**, A103.
- 28 M. Asif, M. Rashad, Z. Ali and I. Ahmed, *Nanoscale*, 2020, **12**, 924–932.
- 29 F. Liu, Y. Liu, X. Zhao, K. Liu, H. Yin and L.-Z. Fan, *Small*, 2020, **16**, 1906076.
- 30 V. Augustyn, P. Simon and B. Dunn, *Energy Environ. Sci.*, 2014, **7**, 1597–1614.
- 31 A. Moretti and S. Passerini, *Adv. Energy Mater.*, 2016, **6**, 1600868.
- 32 S. Tepavcevic, Y. Liu, D. Zhou, B. Lai, J. Maser, X. Zuo, H. Chan, P. Král, C. S. Johnson, V. Stamenkovic, N. M. Markovic and T. Rajh, *ACS Nano*, 2015, **9**, 8194–8205.

