



Cite this: *Analyst*, 2022, **147**, 5121

Exploration of defined 2-dimensional working electrode shapes through additive manufacturing†

Alejandro Garcia-Miranda Ferrari, Nicholas J. Hurst, Elena Bernalte, Robert D. Crapnell, Matthew J. Whittingham, Dale A. C. Brownson and Craig E. Banks *

In this work, the electrochemical response of different morphologies (shapes) and dimensions of additively manufactured (3D-printing) carbon black (CB)/poly-lactic acid (PLA) electrodes are reported. The working electrodes (WE) are printed using standard non-conductive PLA based filament for the housing and commercial Protopasta (carbon black/PLA) filament for the electrode and connection parts. Discs, squares, equilateral triangles and six-point stars with varying working electrode (WE) widths from 2 to 10 mm are evaluated herein towards the well-known near-ideal outer sphere redox probe hexaamineruthenium(III) chloride (RuHex). The results obtained show that triangular and squared electrodes exhibit a faster heterogeneous electron transfer (HET) rate constant (k^0) than those of discs and stars, the latter being the slowest one. The results reported here also show a trend between the WE dimension and the reversibility of the electrochemical reaction, which decreases as the WE size increases. It is also observed that the ratio of the geometrical and electroactive area ($\%real_{area}$) decreases as the overall WE size increases. On the other hand, these four WE shapes were applied toward the well-known and benchmarking detection of ascorbic acid (AA), uric acid (UA), β -nicotinamide adenine dinucleotide (NADH) and dopamine (DA). Moreover, electroanalytical detection of real acetaminophen (ACOP) samples is also showcased. The different designs for the working electrode proposed in this manuscript are easily changed to any other desired shapes thanks to the additive manufacturing methodology, these four shapes being just an example of what additive manufacturing can offer to experimentalists and to electrochemists in particular. Additive manufacturing is shown here as a versatile and rapid prototyping tool for the production of novel electrochemical sensing platforms, with scope for this work to be able to impact a wide variety of electroanalytical applications.

Received 26th August 2022,
Accepted 6th October 2022

DOI: 10.1039/d2an01412b

rsc.li/analyst

Introduction

Additive manufacturing (AM)/3D-printing has become recently popular in research due to its ability to create intricate designs, quick and affordable prototyping turnaround, and its bespoke capabilities. In electrochemistry research, additive manufacturing has been reported for the production of tailored cell designs,^{1,2} flow cells,³ thermal sensing,^{4,5} fully printed all-in-one setups^{6,7} and many others. Most of the work regarding the manufacture of tailored electrodes has been focusing on fused filament fabrication (FFF) methods, which allows a very affordable point of entry, low-waste and rapid prototypings.⁸ FFF feeds a heated thermoplastic filament continu-

ously through an extruder which will allow for the controlled deposition of the final product layer-by-layer.⁹

Historically, mercury electrodes were one of the first choices for working electrode materials in the last century; however, in the last decades, they have been replaced due to their known dangers¹⁰ by solid precious metals (gold (Au), silver (Ag) and platinum (Pt)) and later carbon/graphitic electrodes, which are known by their overall low background currents, wide potential range and chemical inertness.^{11,12} It is because of these features that graphite, in its many forms, is a great material of choice when designing conductive filaments for AM applications. These can be manufactured by embedding carbon black or graphene into a thermoplastic filament matrix, such as PLA or acrylonitrile butadiene styrene (ABS). Conductive FFF filaments can be widely purchased, however it is becoming a trend the bespoke production of them for some applications such as batteries,¹³ water splitting¹⁴ and electrochemical sensing.¹⁵ It is important to also note that, when applied to electroanalytical sensing, the performance of these

Faculty of Science and Engineering, Manchester Metropolitan University, Chester Street, M1 5GD, UK. E-mail: c.banks@mmu.ac.uk; Tel: +44 (0)1612471196

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2an01412b>



AM electrodes is directly related to the characteristics of the WE's surface, being the activation of WE a point of attention when optimising their sensing performance. Electrochemical cycling,⁸ laser treatment¹⁶ or chemical reductions¹⁷ are often the applied strategies to remove the excess of plastic to unveil and increase the amount of carbon within the surface of the working electrode. Since the application of AM to the electrochemistry field, majority of the experimentalists do not use a defined electrode area for their experiments, being the "lollipop" design the most common due to its easiness of printing^{14,15,18–28} and similarities to the well-studied screen-printed platforms. The lollipop design is a simple flat disc with a rectangular tab for connecting the electrode to the potentiostat, being an easy to design and print figure. However, the issue with this design is the incapacity to fully control the area of the electrode which is immersed in the solution and in contact with the electrolyte.

In this manuscript we explore, for the first time, the effect of geometrical shape and dimensions of additively manufactured carbon black (CB)-based PLA working electrodes towards their electrochemical performance. Accordingly, heterogeneous electron transfer (HET) are evaluated using the near-ideal outer sphere hexaamineruthenium(III) chloride (RuHex) as redox probe and subsequently, the electroanalytical performances of the different WE's shapes are critically analysed towards other well-known redox species such as ascorbic acid, uric acid, β -nicotinamide adenine dinucleotide and dopamine. Finally, we demonstrate in this work the applicability of the best WE shape to detect acetaminophen in real pharmaceutical sample.

Experimental section

Materials

All chemicals used were of analytical grade and were used as received without any further purification. All solutions were prepared with deionised water of resistivity not less than 18.2 M Ω cm. Hexaamineruthenium(III) chloride (RuHex), ascorbic acid (AA), uric acid (UA), β -nicotinamide adenine dinucleotide (NADH), dopamine (DA), phosphate buffered saline (PBS) tablets and sodium hydroxide were purchased from Merck (Gillingham, UK). Potassium chloride was purchased from Fisher Scientific (Loughborough, UK). The commercial conductive PLA/carbon black filament (ProtoPasta) was purchased from Farnell (Leeds, UK). Note that we have utilised this filament in a different system and more details of its physiochemical characterisation can be found in ref. 6. The working electrodes (WE) shapes are discs, squares, equilateral triangles and six-point stars with varying widths of working electrodes from 2 to 10 mm as shown in Fig. S1.† The connection tab for these was chosen to be 18 mm, which corresponds to the shortest connection possible that allows comfortable use and connection of the devices. Note that it has recently been reported the effect of graphitic screen-printed electrode's connection lengths to their electrochemical performance.²⁹ Real

samples were sourced from a local shop, consisting of 500 mg tablet of acetaminophen (ACOP).

Additive manufacturing

The additive manufacturing electrodes (AMEs) were produced using fused filament fabrication (FFF), on a RAISE3D E2 independent dual-extruder (IDEX) printer (RAISE3D, California, US) using commercial conductive PLA/carbon black (PLA/CB, ProtoPasta, 1.75 mm) and non-conductive Premium PLA (RAISE3D, 1.75 mm). All designs and STL files were produced using Autodesk® Fusion 360®, then sliced and converted to G-code files using ideaMaker 4.0.1 (RAISE3D, California, US). The printing orientation is horizontal, where the non-conductive PLA was printed using a layer height of 0.1 mm, shell width of 1 mm with a gyroid infill of 20% and infill speed of 70 mm s⁻¹. The conductive PLA/CB was printed with 100% infill at 35 mm s⁻¹ speed. The prints had a purge block located close to the cells, as well as a skirt to help prime the nozzle prior to printing the first layer and between each extruder change.

Electrochemical experiments

An μ -Autolab type (III) potentiostat (Utrecht, the Netherlands) was used in conjunction with NOVA 2.1.4 (Utrecht, the Netherlands) to carry out electrochemical measurements using a three-electrode configuration. The AMEs were used as the working electrodes, a nickel wire coil was used as the counter electrode and an Ag/AgCl electrode was used as the reference. Solutions of RuHex were degassed thoroughly for at least 15 minutes with nitrogen prior to any electrochemical measurement.

Activation of the AMEs was achieved electrochemically in NaOH as described in the literature.³⁰ Briefly, the AMEs were connected as the working electrode in conjunction with a nickel wire coil counter and Ag/AgCl reference electrode and placed in a solution of NaOH (0.5 M). Chronoamperometry was used to activate the AME by applying a set voltage of +1.4 V for 200 s, followed by applying -1.0 V for 200 s. The AMEs were then thoroughly rinsed with deionised water and dried under nitrogen before further use.

The HET rate constants, k_{obs}° , were calculated as an average of 3 sets of 10 different scan rates (5, 10, 15, 25, 50, 75, 100, 150, 250 and 500 mV s⁻¹), where each set used a new AME. These were performed using the near ideal outer-sphere redox probe RuHex (in 0.1 M KCl) using the well-known³¹ and widely utilised Nicholson method,³² for quasi-reversible electrochemical reactions *via* the following formula:³³

$$\varphi = k_{\text{obs}}^{\circ} [\pi D n \nu F / RT]^{-1/2} \quad (1)$$

where φ is a kinetic parameter, D is the diffusion coefficient for RuHex ($D = 9.1 \times 10^{-6}$ cm² s⁻¹),³¹ n is the number of electrons that are taking part in the process, F is the faraday constant, ν is the scan rate, R is the gas constant and T is the temperature in kelvin. In order to calculate the HET rate constant, we use the peak to peak separation (ΔE_p) to deduce φ ,



Analyst, 2022, **147**, 5121–5129 | **5123**

Electrochemical characterisation

As mentioned before, circular disc, square, equilateral triangle and (6 point) star were the chosen WE's shapes as shown in Fig. S1.[†] These designs were manufactured in the following 5 different dimensions: 2, 2.5, 5, 7.5 and 10 mm of WE widths, respectively.

A

i) ii) iii) iv)

Current / μA

Potential / V (vs Ag/AgCl)

2 mm
2.5 mm
5 mm
7.5 mm
10 mm

B

Current density / $\mu\text{A cm}^{-2}$

Potential / V (vs Ag/AgCl)

Disc
Square
Triangle
Star

222.2 mV
210.0 mV
191.2 mV
169.4 mV

C

HET k^0 / $\mu\text{A cm}^{-1} \text{s}^{-1}$

Diameter / mm

Disc
Square
Triangle
Star

Fig. 2 (A) Voltammetric comparison of 1 mM RuHex (in 0.1 M KCl) using the range of electrodes shapes (disc (i), square (ii), triangle (iii) and star (iv)) and dimensions. (B) Current density comparison of 1 mM RuHex (0.1 M KCl). (C) Heterogeneous electron transfer (HET) rate constant (k^0) comparison for range of electrode dimensions. Voltammograms extracted from full scan rate studies, 50 mV s⁻¹ shown herein (vs. Ag/AgCl).

Fig. 2C, it is evident the decrease of the k^o values when the dimension of the electrode increases despite their shape. The highest k^o value ($10.1 \times 10^{-3} \text{ cm s}^{-1}$) was recorded for the 2 mm width square, while the lowest k^o value ($1.51 \times 10^{-3} \text{ cm s}^{-1}$) was recorded for the 10 mm star AME. This could also be due to the increase in the internal pathway of the graphite composite electrodes, leading to an increase in their internal resistance.²⁹ Please note that these differences do not seem to be statistically significant to draw any conclusive difference among the different AME shapes.

Attention was next turned to calculating the electroactive area (A_{real}) of the range of different AM electrodes using their respective Randles–Ševčík equation³⁷ (see Experimental Section for further details). The A_{real} for the different electrodes is included in Table 1, including the ratio between the geometrical and electroactive area expressed as a percentage (% $\text{real}_{\text{area}}$). The overall % $\text{real}_{\text{area}}$ values follow a decreasing trend when the dimensions of the electrode increase for all the different shapes, meaning that the electroactive area does not increase as much as the geometric one. This could be due to the internal electrode resistance and polymeric nature of the graphite/PLA filament, where PLA is electrochemically inactive (in contrast to traditional electrodes such as glassy carbon, where all the material is active and a linear increase of % $\text{real}_{\text{area}}$ would be expected). Overall, the above results indicate that as the dimension of the working electrode increases, the reversibility of the electrochemical reaction (and therefore its HET kinetics) decreases, so does the electroactive area for all the four electrodes' shapes tested herein. The AME shape with the



Table 1 Electrochemical characterisation of disc, square, triangle and star AM electrodes determined from cyclic voltammetry using 1 mM RuHex probe in 0.1 M KCl ($N = 3$) (vs. Ag/AgCl)

	WE Ø/mm	Disc	Square	Triangle	Star
$a_{\text{geo}}/\text{cm}^2$	2	0.0314	0.0314	0.0314	NP ^a
	2.5	0.0491	0.491	0.492	0.491
	5	0.196	0.196	0.196	0.196
	7.5	0.466	0.466	0.466	0.466
	10	0.785	0.785	0.785	0.785
Avg. $k^0/\text{cm s}^{-1}$	2	$8.49 (\pm 0.49) \times 10^{-3}$	$1.01 (\pm 0.073) \times 10^{-2}$	$9.32 (\pm 0.70) \times 10^{-3}$	NP ^a
	2.5	$7.85 (\pm 1.14) \times 10^{-3}$	$9.90 (\pm 1.43) \times 10^{-3}$	$9.42 (\pm 0.85) \times 10^{-3}$	$9.99 (\pm 0.075) \times 10^{-3}$
	5	$5.03 (\pm 0.25) \times 10^{-3}$	$6.69 (\pm 0.089) \times 10^{-3}$	$8.04 (\pm 0.88) \times 10^{-3}$	$4.19 (\pm 0.43) \times 10^{-3}$
	7.5	$2.89 (\pm 0.040) \times 10^{-3}$	$3.51 (\pm 0.020) \times 10^{-3}$	$6.30 (\pm 1.81) \times 10^{-3}$	$2.65 (\pm 0.24) \times 10^{-3}$
	10	$1.73 (\pm 0.031) \times 10^{-3}$	$3.13 (\pm 0.18) \times 10^{-3}$	$3.46 (\pm 2.31) \times 10^{-3}$	$1.55 (\pm 0.98) \times 10^{-3}$
$\Delta E_p/\text{mV}$ (at 50 mV s^{-1})	2	125	112	129	NP ^a
	2.5	130	132	127	111
	5	200	168	162	225
	7.5	286	260	231	394
	10	374	341	315	413
Avg. $A_{\text{real}}/\text{cm}^2$	2	0.030 (± 0.0018)	0.023 (± 0.0043)	0.023 (± 0.0014)	NP ^a
	2.5	0.049 (± 0.0027)	0.037 (± 0.0042)	0.038 (± 0.0038)	0.038 (± 0.00083)
	5	0.200 (± 0.0059)	0.159 (± 0.010)	0.145 (± 0.0059)	0.153 (± 0.012)
	7.5	0.433 (± 0.015)	0.321 (± 0.0029)	0.345 (± 0.0043)	0.311 (± 0.029)
	10	0.636 (± 0.057)	0.536 (± 0.0027)	0.559 (± 0.016)	0.503 (± 0.042)
%Real _{area}	2	94.8 (± 5.6)	72.7 (± 13.8)	74.7 (± 4.5)	NP ^a
	2.5	99.5 (± 5.5)	75.1 (± 8.6)	77.3 (± 7.6)	78.4 (± 1.7)
	5	102.1 (± 3.0)	80.9 (± 5.3)	73.7 (± 3.0)	77.7 (± 6.3)
	7.5	93.0 (± 3.2)	68.9 (± 0.6)	74.1 (± 0.9)	66.7 (± 6.2)
	10	80.9 (± 7.3)	68.2 (± 0.3)	71.2 (± 1.9)	64.0 (± 5.4)

^a NP = not printable.

highest %real_{area} across all sizes is the disc (varying from 80.9 to 102.1%), while the lowest %real_{area} is exhibited by the star electrode (ranging from 64.0 to 78.4%).

Electroanalytical applications

We now turn to exploring the electroanalytical performance of the AMEs towards the detection of relevant biological analytes, namely ascorbic acid (AA), uric acid (UA), β -nicotinamide adenine dinucleotide (NADH) and dopamine (DA) using the 2.5 mm width electrodes, as it was almost the one exhibiting the faster HET values for all geometric forms and it could be successfully 3D-printed for all shapes. Like for other carbon electrodes,⁴⁷ it is described in the literature the need of a post-printing enhancement of the electrochemical properties so called “activation method” prior the utilisation of AMEs in electroanalytical applications. Note that this method is unnecessary for the above RuHex studies, due to the near ideal outer-sphere nature of the redox probe, being this method only beneficial for the further electroanalytical sensing applications. Several literature reports have addressed this pre-conditioning of the electrode's surface by chemical, physical or electrochemical treatments to successfully increase the active surface area and its electron transfer rates.^{6,7} Herein, we apply the method developed by Kalinke *et al.*⁸ Such method is based on the use of NaOH while a potential-controlled electrochemical method (namely chronoamperometry) is applied to

promote PLA's saponification, which exposes the active material's active sites and electrochemical active area. This results in the increasing of the C/O ratio and therefore the improvement of the electrochemical performance of inner-sphere redox probes.

The calibration plots for AA, UA, NADH and DA using all the electrode shapes are depicted in Fig. 3, with examples of the respective calibration voltammograms as insets. These were AA with disc electrodes, UA with square electrodes, NADH with triangle electrodes and DA with star electrodes. Fig. S2† includes all the voltammograms for each of the four analytes and each of the four electrodes shapes. The electrochemical sensitivity, limit of detection (LOD) and coefficient of determination (R^2) values are included in Table 2. A very good linear behaviour is observed for all AMEs in all redox probes as R^2 values are successfully ranged between 0.994 and 0.999. Moreover, it is observed that there are no significant differences between the four electrodes shapes in terms of their electroanalytical performance towards AA, UA, and DA. This is likely to indicate that the observed differences can be attributed to their respective calculated deviations. It is detected, however, a higher variation in the sensitivity of the four AMEs in the detection of NADH possibly due to the more complexity of the redox process of this molecule. Note that no significant differences between the four electrode shapes are observed herein, and, although small LOD differences are observed



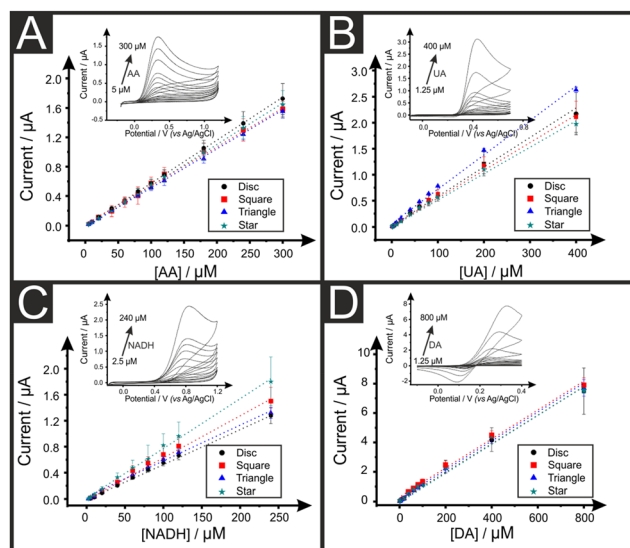


Fig. 3 Calibration plots of ascorbic acid (A; AA), uric acid (B; UA), NADH (C) and dopamine (DA; D) in PBS pH 7.4 using the range of disc, square, triangle and star 2.5 mm electrodes. Scan rate 50 mV s⁻¹ (vs. Ag/AgCl). Insets are the respective voltammograms from the calibration plots for AA with disc electrodes, UA with square electrodes, NADH with triangle electrodes and DA with star electrodes.

between the different electrode shapes, the higher LODs are reported when using square electrodes, which are likely due to their slightly higher background noise in their recorded voltammograms. These observations could be due to the sizes of the electrodes and their current distributions, in addition to the diffusion regimes where the AMEs being big enough that planar diffusion governs the electrochemical process and therefore the shape of the electrode does not play a relevant part with these dimensions.⁴⁵ Also again, please note that these differences do not seem to be statistically significant.

Lastly, we apply the AMEs to the electrochemical determination of acetaminophen (ACOP) and the analysis of this compound in a commercial tablet accordingly diluted in PBS (0.01

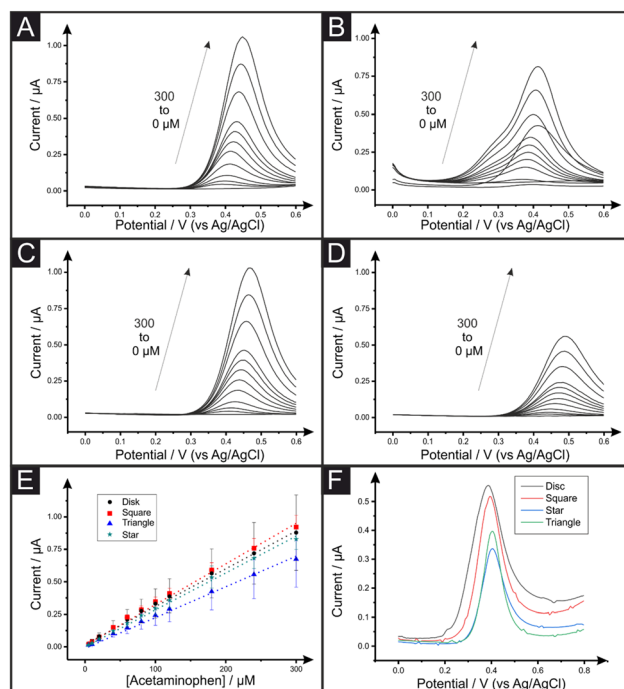


Fig. 4 (A) Differential pulse voltammetry for the detection of ACOP (5–300 μM ; $N = 3$) in PBS (0.01 M; $\text{pH} = 7.4$) for the square (A), triangle (B), disc (C) and star (D) shaped AMEs. (E) Calibration curves corresponding to the voltammetric determination of ACOP for these AMEs. (F) Differential pulse voltammograms for the diluted ACOP tablet sample with the AMEs.

M, pH = 7.4). A series of calibration plots was performed for each AME shape by differential pulse voltammetry (DPV). Fig. 4 shows the DPV signals of increasing amounts of ACOP for the square (A), triangle (B), disc (C) and star (D) shaped electrodes and their respective calibration plot of ACOP (E). The analytical sensitivity, limit of detection (LOD) and coefficient of determination (R^2) are reported in Table 3. The analytical sensitivity for the ACOP determination varies from 5.89×10^{-3} to 6.55×10^{-3} $\mu\text{A } \mu\text{M}^{-1}$ with star and disc electrodes

Table 2 Comparison of the analytical sensitivities (in $\mu\text{A } \mu\text{M}^{-1}$), limit of detection (LOD; $3 \times \text{Sy/S}$) and coefficient of determination (R^2) obtained at the various electrode shapes towards the detection of ascorbic acid, uric acid, NADH and dopamine in PBS pH 7.4 (calculated from gradient of calibration plots depicted in Fig. 3); scan rate 50 mV s^{-1} (vs. Ag/AgCl) ($N = 3$)

		Shape			
Analyte		Disc	Square	Triangle	Star
AA	Sensitivity/ $\mu\text{A } \mu\text{M}^{-1}$	6.55×10^{-3}	6.01×10^{-3}	6.33×10^{-3}	5.89×10^{-3}
	LOD/ μM	0.54	2.13	0.75	0.64
	R^2	0.999	0.998	0.999	0.999
UA	Sensitivity/ $\mu\text{A } \mu\text{M}^{-1}$	5.51×10^{-3}	5.35×10^{-3}	5.03×10^{-3}	6.65×10^{-3}
	LOD/ μM	0.12	0.36	0.26	0.19
	R^2	0.996	0.995	0.995	0.995
NADH	Sensitivity/ $\mu\text{A } \mu\text{M}^{-1}$	5.44×10^{-3}	6.40×10^{-3}	7.64×10^{-3}	5.60×10^{-3}
	LOD/ μM	0.79	0.53	0.50	0.48
	R^2	0.998	0.995	0.997	0.996
DA	Sensitivity/ $\mu\text{A } \mu\text{M}^{-1}$	9.43×10^{-3}	9.91×10^{-3}	9.52×10^{-3}	9.74×10^{-3}
	LOD/ μM	0.37	1.29	0.50	0.64
	R^2	0.994	0.993	0.994	0.997

		Shape			
		Disc	Square	Triangle	Star
ACOP	Sensitivity/ $\mu\text{A } \mu\text{M}^{-1}$	6.55×10^{-3}	6.01×10^{-3}	6.33×10^{-3}	5.89×10^{-3}
	LOD/ μM	0.54	2.13	0.75	0.64
	R^2	0.999	0.998	0.999	0.999
	Sample recovery/%	102.3	96.9	122.6	80.3

Analyst, 2022, **147**, 5121–5129 | **5127**

- trodes: electrochemical characterisation and exploration towards the hydrogen evolution reaction, *Nanoscale*, 2020, **12**(35), 18214–18224.
- 4 K. Betlem, A. Kaur, A. D. Hudson, R. D. Crapnell, G. Hurst, P. Singla, M. Zubko, S. Tedesco, C. E. Banks and K. Whitehead, Heat-Transfer Method: A Thermal Analysis Technique for the Real-Time Monitoring of *Staphylococcus aureus* Growth in Buffered Solutions and Digestate Samples, *ACS Appl. Bio Mater.*, 2019, **2**(9), 3790–3798.
 - 5 R. D. Crapnell, W. Jesadabundit, A. Garcia-Miranda Ferrari, N. C. Dempsey-Hibbert, M. Peeters, A. Tridente, O. Chailapakul and C. E. Banks, Toward the Rapid Diagnosis of Sepsis: Detecting Interleukin-6 in Blood Plasma Using Functionalized Screen-Printed Electrodes with a Thermal Detection Methodology, *Anal. Chem.*, 2021, **93**(14), 5931–5938.
 - 6 R. D. Crapnell, E. Bernalte, A. Garcia-Miranda Ferrari, M. J. Whittingham, R. J. Williams, N. J. Hurst and C. E. Banks, All-in-One Single-Print Additively Manufactured Electroanalytical Sensing Platforms, *ACS Meas. Sci. Au*, 2021, 167–176.
 - 7 M. J. Whittingham, R. D. Crapnell, E. J. Rothwell, N. J. Hurst and C. E. Banks, Additive manufacturing for electrochemical labs: an overview and tutorial note on the production of cells, electrodes and accessories, *Talanta Open*, 2021, 100051.
 - 8 R. M. Cardoso, C. Kalinke, R. G. Rocha, P. L. Dos Santos, D. P. Rocha, P. R. Oliveira, B. C. Janegitz, J. A. Bonacin, E. M. Richter and R. A. Munoz, Additive-manufactured (3D-printed) electrochemical sensors: A critical review, *Anal. Chim. Acta*, 2020, **1118**, 73–91.
 - 9 B. Redwood, F. Schöffner and B. Garret, *The 3D printing handbook: technologies, design and applications*, 3D Hubs, 2017.
 - 10 J. Wang, Stripping Analysis, in *Encyclopedia of Electrochemistry*, 2007.
 - 11 A. Hayat and J. L. Marty, Disposable Screen Printed Electrochemical Sensors: Tools for Environmental Monitoring, *Sensors*, 2014, **14**(6), 10432–10453.
 - 12 R. W. Murray, A. G. Ewing and R. A. Durst, Chemically modified electrodes. Molecular design for electroanalysis, *Anal. Chem.*, 1987, **59**(5), 379A–390A.
 - 13 V. Gupta, F. Alam, P. Verma, A. Kannan and S. Kumar, Additive manufacturing enabled, microarchitected, hierarchically porous polylactic-acid/Lithium iron phosphate/carbon nanotube nanocomposite electrodes for high performance Li-Ion batteries, *J. Power Sources*, 2021, **494**, 229625.
 - 14 J. P. Hughes, P. L. dos Santos, M. P. Down, C. W. Foster, J. A. Bonacin, E. M. Keefe, S. J. Rowley-Neale and C. E. Banks, Single step additive manufacturing (3D printing) of electrocatalytic anodes and cathodes for efficient water splitting, *Sustainable Energy Fuels*, 2020, **4**(1), 302–311.
 - 15 C. W. Foster, H. M. Elbardisy, M. P. Down, E. M. Keefe, G. C. Smith and C. E. Banks, Additively manufactured graphitic electrochemical sensing platforms, *Chem. Eng. J.*, 2020, **381**, 122343.
 - 16 D. P. Rocha, V. N. Ataíde, A. de Siervo, J. M. Gonçalves, R. A. Muñoz, T. R. Paixão and L. Angnes, Reagentless and sub-minute laser-scribing treatment to produce enhanced disposable electrochemical sensors via additive manufacture, *Chem. Eng. J.*, 2021, 130594.
 - 17 E. Redondo, J. Muñoz and M. Pumera, Green activation using reducing agents of carbon-based 3D printed electrodes: Turning good electrodes to great, *Carbon*, 2021, **175**, 413–419.
 - 18 C. W. Foster, M. P. Down, Y. Zhang, X. Ji, S. J. Rowley-Neale, G. C. Smith, P. J. Kelly and C. E. Banks, 3D Printed Graphene Based Energy Storage Devices, *Sci. Rep.*, 2017, **7**(1), 42233.
 - 19 C. Y. Foo, H. N. Lim, M. A. Mahdi, M. H. Wahid and N. M. Huang, Three-Dimensional Printed Electrode and Its Novel Applications in Electronic Devices, *Sci. Rep.*, 2018, **8**(1), 7399.
 - 20 P. L. dos Santos, V. Katic, H. C. Loureiro, M. F. dos Santos, D. P. dos Santos, A. L. B. Formiga and J. A. Bonacin, Enhanced performance of 3D printed graphene electrodes after electrochemical pre-treatment: Role of exposed graphene sheets, *Sens. Actuators, B*, 2019, **281**, 837–848.
 - 21 C. Kalinke, N. V. Neumsteir, G. d. O. Aparecido, T. V. d. B. Ferraz, P. L. dos Santos, B. C. Janegitz and J. A. Bonacin, Comparison of activation processes for 3D printed PLA-graphene electrodes: electrochemical properties and application for sensing of dopamine, *Analyst*, 2020, **145**(4), 1207–1218.
 - 22 A. M. López Marzo, C. C. Mayorga-Martinez and M. Pumera, 3D-printed graphene direct electron transfer enzyme biosensors, *Biosens. Bioelectron.*, 2020, **151**, 111980.
 - 23 K. P. A. Kumar, K. Ghosh, O. Alduhaish and M. Pumera, Metal-plated 3D-printed electrode for electrochemical detection of carbohydrates, *Electrochem. Commun.*, 2020, **120**, 106827.
 - 24 C. Iffelsberger, S. Ng and M. Pumera, Catalyst coating of 3D printed structures via electrochemical deposition: Case of the transition metal chalcogenide MoS_x for hydrogen evolution reaction, *Appl. Mater. Today*, 2020, **20**, 100654.
 - 25 L. Wang and M. Pumera, Covalently modified enzymatic 3D-printed bioelectrode, *Microchim. Acta*, 2021, **188**(11), 374.
 - 26 C. Kalinke, N. V. Neumsteir, R. de Oliveira, P. Janegitz, B. C. Bonacin and J. A. , Sensing of L-methionine in biological samples through fully 3D-printed electrodes, *Anal. Chim. Acta*, 2021, **1142**, 135–142.
 - 27 J. Muñoz and M. Pumera, 3D-Printed COVID-19 immunosensors with electronic readout, *Chem. Eng. J.*, 2021, **425**, 131433.
 - 28 C. Kalinke, P. R. de Oliveira, N. V. Neumsteir, B. F. Henriques, G. de Oliveira Aparecido, H. C. Loureiro, B. C. Janegitz and J. A. Bonacin, Influence of filament aging and conductive additive in 3D printed sensors, *Anal. Chim. Acta*, 2022, **1191**, 339228.



- 29 M. J. Whittingham, N. J. Hurst, R. D. Crapnell, A. Garcia-Miranda Ferrari, E. Blanco, T. J. Davies and C. E. Banks, Electrochemical Improvements Can Be Realized via Shortening the Length of Screen-Printed Electrochemical Platforms, *Anal. Chem.*, 2021, **93**(49), 16481–16488.
- 30 E. M. Richter, D. P. Rocha, R. M. Cardoso, E. M. Keefe, C. W. Foster, R. A. Munoz and C. E. Banks, Complete additively manufactured (3D-printed) electrochemical sensing platform, *Anal. Chem.*, 2019, **91**(20), 12844–12851.
- 31 A. Garcia-Miranda Ferrari, C. W. Foster, P. Kelly, D. A. C. Brownson and C. E. Banks, Determination of the Electrochemical Area of Screen-Printed Electrochemical Sensing Platforms, *Biosensors*, 2018, **8**(2), 53.
- 32 R. S. Nicholson, Theory and Application of Cyclic Voltammetry for Measurement of Electrode Reaction Kinetics, *Anal. Chem.*, 1965, **37**(11), 1351–1355.
- 33 S. J. Rowley-Neale, D. A. C. Brownson and C. E. Banks, Defining the origins of electron transfer at screen-printed graphene-like and graphite electrodes: MoO₂ nanowire fabrication on edge plane sites reveals electrochemical insights, *Nanoscale*, 2016, **8**(33), 15241–15251.
- 34 D. Brownson and C. E. Banks, *The Handbook of Graphene Electrochemistry*, 2014, p. 208.
- 35 F. E. Galdino, C. W. Foster, J. A. Bonacin and C. E. Banks, Exploring the electrical wiring of screen-printed configurations utilised in electroanalysis, *Anal. Methods*, 2015, **7**(3), 1208–1214.
- 36 C. W. Foster, M. P. Down, Y. Zhang, X. Ji, S. J. Rowley-Neale, G. C. Smith, P. J. Kelly and C. E. Banks, 3D Printed Graphene Based Energy Storage Devices, *Sci. Rep.*, 2017, **7**, 42233.
- 37 A. Bard and L. Faulkner, *Electrochemical Methods: Fundamentals and Applications*. John Wiley & Sons, Inc, 2001.
- 38 R. H. Rousselot and S. Barnartt, Répartition du potentiel et du courant dans les électrolytes, *J. Electrochem. Soc.*, 1960, **107**(2), 40C.
- 39 J. Deconinck, The Current Distribution in Electrochemical Systems, in *Current Distributions and Electrode Shape Changes in Electrochemical Systems*, Springer Berlin Heidelberg, Berlin, Heidelberg, 1992, pp. 1–55.
- 40 W. Jaenicke, *Chem. Ing. Tech.*, 1974, **46**, 125–125, Electrochemical Systems, Von J. S. Newman., Prentice-Hall, Inc., London – Englewood Cliffs 1973. XIV, 432 S., zahlr. Abb., geb. £ 9.50, DOI: [10.1002/cite.330460315](https://doi.org/10.1002/cite.330460315).
- 41 N. Ibl, *Distribution du courant dans les systemes électrochimiques*, Techniques de L'ingénieur D, 1976, vol. 902, pp. 1–78.
- 42 N. Ibl, Current Distribution, in *Comprehensive Treatise of Electrochemistry: Electrodicts: Transport*, ed. E. Yeager, J. O. M. Bockris, B. E. Conway and S. Sarangapani, Springer US, Boston, MA, 1983, pp. 239–315.
- 43 R. C. Alkire, P. N. Barlett and J. Lipkowski, *Electrochemistry of Carbon Electrodes*, Wiley, 2016, vol. 1, p. 450.
- 44 D. A. C. Brownson, A. Garcia-Miranda Ferrari, S. Ghosh, M. Kamruddin, J. Iniesta and C. E. Banks, Electrochemical properties of vertically aligned graphenes: tailoring heterogeneous electron transfer through manipulation of the carbon microstructure, *Nanoscale Adv.*, 2020, 5319–5328.
- 45 R. G. Compton and C. E. Banks, *Understanding Voltammetry*, World Scientific Publishing Company, 3rd edn, 2018.
- 46 A. D. Clegg, N. V. Rees, O. V. Klymenko, B. A. Coles and R. G. Compton, Marcus Theory of Outer-Sphere Heterogeneous Electron Transfer Reactions: Dependence of the Standard Electrochemical Rate Constant on the Hydrodynamic Radius from High Precision Measurements of the Oxidation of Anthracene and Its Derivatives in Nonaqueous Solvents Using the High-Speed Channel Electrode, *J. Am. Chem. Soc.*, 2004, **126**(19), 6185–6192.
- 47 M. Mahbubur Rahman and J.-J. Lee, Sensitivity control of dopamine detection by conducting poly(thionine), *Electrochem. Commun.*, 2021, **125**, 107005.

